

We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

4,800

Open access books available

122,000

International authors and editors

135M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities



WEB OF SCIENCE™

Selection of our books indexed in the Book Citation Index
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?
Contact book.department@intechopen.com

Numbers displayed above are based on latest data collected.
For more information visit www.intechopen.com



The Synthesis and Characterization of Nickel and Cobalt Ferrite Nanopowders Obtained by Different Methods

Ilmars Zalite, Gundega Heidemane, Janis Grabis and Mikhail Maiorov

Additional information is available at the end of the chapter

<http://dx.doi.org/10.5772/intechopen.76809>

Abstract

The single-phase NiFe_2O_4 and CoFe_2O_4 ferrites were synthesized by four methods: the high-frequency plasma chemical synthesis ("plasma"), sol-gel self-propagating combustion method ("combust"), and co-precipitation technology, combined with the hydrothermal synthesis ("hydrotherm") or spray-drying ("spray"). The specific surface area (SSA), crystallite size, and magnetic properties of the synthesized products have been determined. The synthesized ferrites are nanocrystalline single-phase materials with crystallite size of 5-40 nm. The SSA of nanoparticles synthesized in plasma is 28-30 m^2/g , the particle size distribution is in the range of 10-100 nm, with some individual particles up to 200 nm. The SSA of the ferrites obtained by the self-combustion and hydrothermal synthesis is 40 ± 3 and 60 ± 5 m^2/g , respectively. The SSA of the samples obtained by the spray-drying method is 80-90 m^2/g , and the calculated particle size is 13-15 nm. In this process, pellets up to 10 μm are obtained. After synthesis, CoFe_2O_4 are characterized by the saturation magnetization M_s of 75 emu/g ("plasma"), 53 emu/g ("combust") and 57 emu/g ("hydrotherm"). The M_s of NiFe_2O_4 is 44, 29, and 30 emu/g, respectively. The products obtained by the spray-drying method are partially X-ray amorphous and show magnetic properties only after heating above 450°C. These nanopowders were used in sintering studies.

Keywords: NiFe_2O_4 , CoFe_2O_4 , nanoparticles, synthesis, properties

1. Introduction

Ferrites are a wide range of minerals and synthetic materials, which have attracted a wide range of scientists' interest due to their various applications. Ferrites are technologically significant

materials due to their unique electrical, dielectric, electronic, mechanical, magnetic, optical and catalytic properties. These ferrites are characterized by good magnetic properties [1], low (NiFe_2O_4) [2] or high (CoFe_2O_4) [3] magnetic coercivity, high electrical resistivity and negligible eddy current loss for high-frequency electromagnetic wave propagation [2], chemical stability and fairly high mechanical hardness [4], low dielectric losses and high Curie temperature [5]. CoFe_2O_4 has a high permeability in the radio frequency range [6], high thermal stability [7], moderate saturation magnetization [3] and electrical conductivity [8].

The most significant and most popular use of ferrites is in optics, electronics, mechanics and other technical fields [9]. Ferrites also play a major role in medicine, biomedical applications, as chemical catalysis and special coatings (antistatic, electromagnetic shielding). Scientific articles contain extensive information on hyperthermia. This method introduces ferrite nanoparticles into living organisms and, under controlled conditions, nanoparticles are transported to the cancerous areas of the body, and cancer cells are destroyed in a magnetic field by heat treatment [10].

Ferrites have become suitable for many technological applications such as microwave devices [11] and telecommunication devices, electric motors and generators, as excellent core material for power transformers in electronics, antenna rods, loading coils and read/write heads for high speed digital tape [1], tape recorders and discs [3], high-density information storage and recording devices and as permanent magnets [11], sensors [12], and so on. Magnetic nanoparticles and in particular magnetic fluids (ferrofluids) are particularly important in biotechnology and biomedicine—the supply of biomedical drugs and as contrast media [12], in medical diagnostics [13]. Ferrite materials are widely used in catalysts [12]. In recent years, ferrite materials have been used to prevent and eliminate radio frequency interference in audio systems [4], as polarized ferroelectric ceramics in acoustic elements in underwater converters [14] and microwave absorbing materials [15], including ferrite-containing radar absorbing paints for masking military aircraft [16]. Lately, it has been discovered that cobalt ferrite nanoparticles can also act as photomagnetic material that shows interesting light-induced coercivity changes [17].

Ferrites in a nanocrystalline state (i.e., below single domain sizes [9]) are often found to have unique physical and mechanical properties compared to coarse-grained polycrystalline materials [18]. It is known that the properties of nanocrystalline ferrite materials, including dielectric constant, conductivity, permeability, and other magnetic properties are determined by their microstructure [19], which, in turn, is influenced by the method of their production [8], that is, the synthesis methods [1]. It is well known that the microstructure, in particular the crystallite size, essentially determines the parameters of the hysteresis loop of soft ferromagnetic materials [20]. Samples obtained with different synthesis methods show different electrical and magnetic properties [4]. Therefore, many new nanoparticle production techniques have been developed in recent years.

Ferrites, as the majority of ceramic materials, are obtained by reactions of solid phase from various oxides [21]. The development of nanotechnological processes has resulted in the development of several liquid phase and gas phase synthesis methods—chemical co-precipitation

method [22], the sol-gel method [23], combustion reaction synthesis [24], hydrolysis [25], hydrothermal synthesis [26], salt melt technique [6], pyrolysis, various microwave synthesis methods [1] including microwave refluxing [27], microwave plasma [28] and microwave hydrothermal methods [29], high energy ball milling techniques [30], microemulsion methods [31], sono-chemical reactions [32], vapor deposition [33], precursor methods [34] and plasma synthesis [35].

In this work, we have tried to summarize our research results on ferrite nanoparticles produced by different methods and to compare their properties, including magnetic properties.

2. Experimental procedure

In research, nickel and cobalt ferrite nanopowders are obtained by the chemical sol-gel self-propagating combustion ("combust.") method [36], the co-precipitation technology in combination with hydrothermal synthesis ("hydrotherm.") [37] or spray-drying ("spray") [38] method and high-frequency plasma chemical synthesis ("plasma") [39]. The obtained nanopowders have been studied for mechanical and magnetic properties.

The synthesis of cobalt and nickel ferrites by the sol-gel self-propagating combustion method was carried out using reagent grade chemicals: $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$, $\text{Ni}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$, $\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$, glycine, nitric acid [36]. A 100 ml 0.1 M cobalt (or nickel) nitrate solution was added to a 200 ml 0.1 M iron nitrate solution. The glycine was separately dissolved in 100 ml of distilled water, nitric acid added and both added to the nitrate mixture. Glycine (Gly) was used as a self-combustion agent with a molar ratio $\text{Me}/\text{Gly} = 1: 0.8$ and $\text{Gly}/\text{Nitr.} = 1:4$. The mixture was evenly stirred until the mixture has congealed. Then the mixture was heated until it ignited, and the heating was continued at 300°C for 4 h.

By the co-precipitation method, cobalt and nickel ferrites were synthesized using reagent grade chemicals: $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$, urea, $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ or $\text{Ni}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$, NaOH [37]. The precursor was obtained as follows: urea was hydrolyzed for 3 h in a $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$ solution (molar ratio of 3: 1) at 70–75°C. Cobalt or nickel nitrate was added the cooled reaction mixture. The molar ratio $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}: \text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ or $\text{Ni}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ corresponds to the metal ion stoichiometry in ferrite. Continually stirring the suspension with 40% NaOH solution, cobalt or nickel hydroxide was slowly precipitated until the pH of the suspension reached 9–10. Then the suspension was placed in an ultrasonic bath for 20 min and then treated for 24 h at 40°C. The sediment was then washed with distilled water by decantation until the presence of Cl ions was no longer detected. Next are two processing options:

- A. by the hydrothermal method, the volume of the hydroxides mixture is reduced by decanting to 250 ml, poured into the reaction vessel and placed in an autoclave. The hydroxide mixture was then treated hydrothermally at different temperatures (200–250°C, 1–3 h, $p = 17\text{--}17.5$ MPa). After hydrothermal treatment, the formed precipitate was filtered with a water jet pump using a 5 μm membrane filter and washed with distilled water and dried at 40°C;

- B.** for spraying the hydroxide mixture with the spray-drying method, the pelleting machine was used developed by RTU Institute of Inorganic Chemistry. Main parameters of the suspension spray: hot air temperature and consumption of 370°C and 24 m³/h, temperature in evaporating chamber 120–130°C.

Technological equipment developed by the Institute of Inorganic Chemistry of the Riga Technical University [35] was used for the production of ferrites by means of high-frequency (HF) plasma chemical synthesis. Commercial metals and metal oxides (Ni, Co, NiO, CoO and FeO) powders were evaporated in HF plasma to obtain ferrites. All raw materials in stoichiometric ratios (to obtain NiFe₂O₄ and CoFe₂O₄) were injected into nitrogen plasma at an average temperature of 5800–6200 K. After evaporation of the raw materials, the vapor was cooled very quickly with the cooling gas (air) and the product condensed on the filter in the form of nanosized ferrite particles.

Ferrite nanopowders for sintering were prepared as follows: the ferrite nanopowder samples were mechanically mixed for 1 h in a planetary mill with 3% by weight of stearic acid (400 rpm, ZrO₂ container, ZrO₂ ball material) using isopropanol as a dispersing medium. Stearic acid was used for better pressing. After mixing, the samples were dried in an oven at 80°C and sieved through a 200 µm sieve. For sintering without pressure samples were pressed (200 MPa) as tablets with a diameter of 12 mm and a height of 4–6 mm. Stearic acid was burned out at 600°C. Samples were sintered at 900–1300°C in an air atmosphere at a rate of 10°C/min in an oven LHT-08/18 (Nabertherm GmbH) for 2 h.

All samples were analyzed using the X-ray diffractometer Advance 8 (Bruker AXS). The size of the crystallites was calculated using the Scherer's equation. The magnetic properties of the synthesized ferrites were analyzed using vibrating sample magnetometry (VSM Lake Shore Cryotronics, Inc., Model 7404 VSM). The SSA was measured using the BET single point method. The size and morphology of the particles as well as the microstructure of the sintered material were studied using transmission electron microscope JEM-100S (JEOL) and a scanning electron microscope Mira/Tescan and Tescan Lyra-3 on the fracture surfaces. The density and open porosity of the sintered samples were determined by the Archimedes method.

3. Results

The characteristics of synthesized ferrites are given in **Table 1** and **Figures 1–5**. It has been found that all synthesized ferrites, with the exception of the spray-drying method, are nanocrystalline stoichiometric single-phase powders (**Figure 1**) with a SSA in the wide range of 30–55 m²/g depending on the synthesis method and calculated (average) particle size of 20–40 nm (**Table 1**, **Figure 2**). The crystallite size of these ferrites is also in the range of 10–40 nm. During the spray-drying process high-dispersity nanoparticles, mainly consisting of cobalt or nickel ferrite, iron hydroxide FeO(OH), and X-ray amorphous part of the sample [38] were obtained. The SSA of these samples was in the range of 80–90 m²/g (**Table 1**), but the calculated average particle size was 13–15 nm [38]. In this process, pellets of up to 10 µm were obtained (**Figure 3**).

The finer particles were obtained in the spray-drying process, hydrothermal and sol-gel self-propagating combustion synthesis, but the distribution of the particle size of ferrites obtained

Sample	SSA, m ² /g	d ₅₀ , nm*	Crystallite size, nm	Phase composition	M _s , emu/g	M _r , emu/g	H _c , Oe
CoFe ₂ O ₄ (plasma)	29	39	40	CoFe ₂ O ₄	75.4	32.0	780
CoFe ₂ O ₄ (combust.)	37	31	20	CoFe ₂ O ₄	53.4	20.3	1170
CoFe ₂ O ₄ (hydrotherm.)	54	21	10–12	CoFe ₂ O ₄	50.1	12.6	390
CoFe ₂ O ₄ (spray)	84	14	—	p.a. CoFe ₂ O ₄ , FeO(OH)	—	—	—
NiFe ₂ O ₄ (plasma)	29	38	40	NiFe ₂ O ₄	44.2	10.0	74
NiFe ₂ O ₄ (combust.)	43	26	10	NiFe ₂ O ₄	21.4	2.3	81
NiFe ₂ O ₄ (hydrotherm.)	42	26	22	NiFe ₂ O ₄	39.0	2.6	23
NiFe ₂ O ₄ (spray)	85	13	—	p.a. NiFe ₂ O ₄ , FeO(OH)	—	—	—

*Average particle size calculated from SSA.

p.a. – partially amorphous; M_s – saturation magnetization; M_r – remanent magnetization; H_c – coercivity

Table 1. Properties of synthesized ferrite nanopowders.

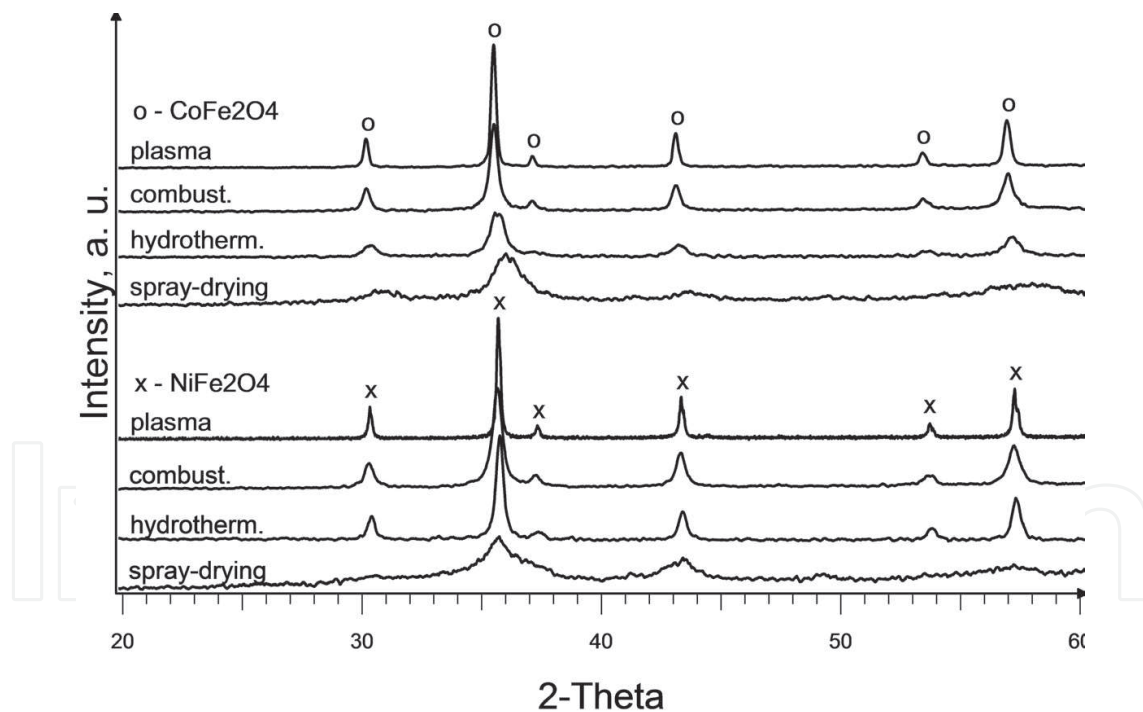


Figure 1. XRD pattern of ferrite nanopowders.

by the plasma synthesis is the most extensive (20–100 nm) with individual particles up to 200 nm. Plasma-derived particles are spherical.

The samples obtained at the optimal synthesis conditions were very clean because any other additional phase (usually magnetite, maghemite, hematite or other metal oxides) was not found by

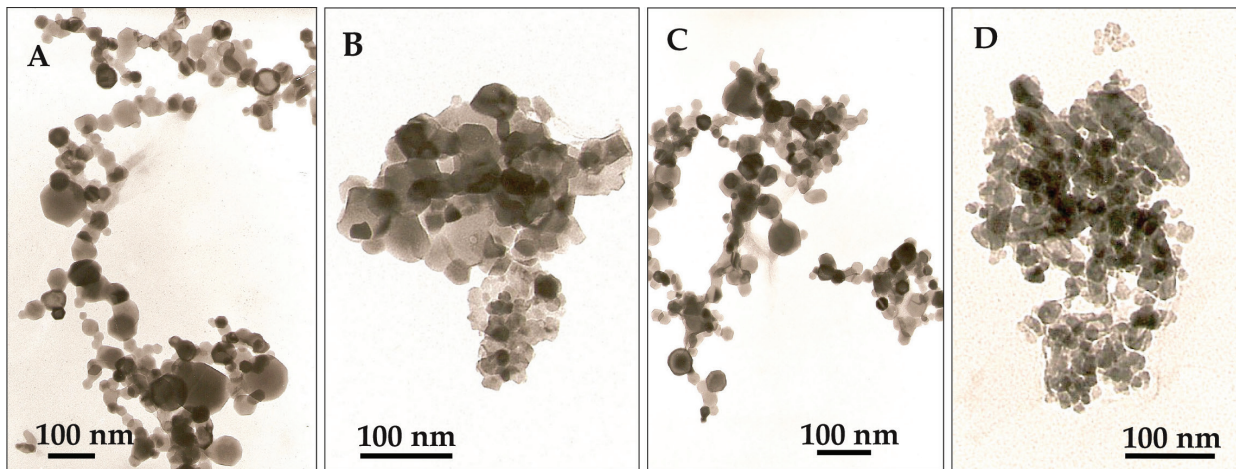


Figure 2. The electron microscope image of CoFe_2O_4 (A, C) and NiFe_2O_4 (B, D) obtained by the plasma synthesis (A), self-combustion (B), hydrothermal (C) and spray (D) methods.

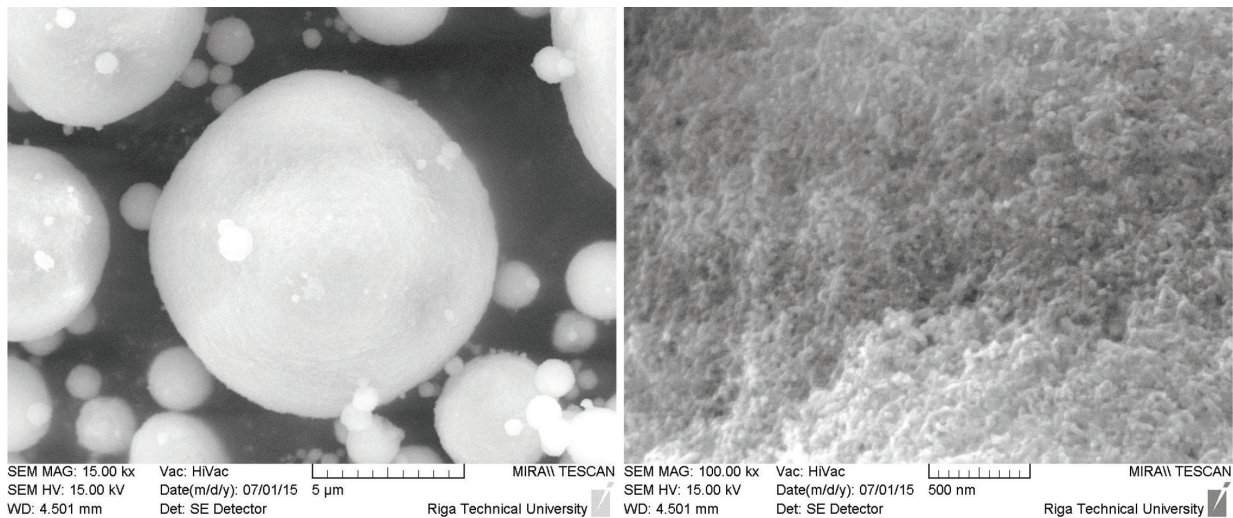


Figure 3. The electron microscope (SEM) images of spray-dried NiFe_2O_4 at different enlargements.

the X-ray analysis. By analyzing samples of ferrites produced by different methods, slight differences in relative intensity and width of reflexes, indicating differences in crystallite size (**Figure 1**), can be seen in the X-ray images. The self-combustion and hydrothermal synthesis methods give nanopowders with a lower crystallite size than those obtained by plasma synthesis (**Table 1**).

The magnetic properties of the nanoparticles obtained by the plasma synthesis process (**Table 1**, **Figure 4**) are very close to those of the standard dense material (CoFe_2O_4 magnetic saturation values are 80 emu/g and NiFe_2O_4 50 emu/g [40]). In contrast, the samples prepared by self-combustion and hydrothermal method have different magnetic properties than those obtained by plasma synthesis. This is probably due to difference in the size of nanoparticles obtained by plasma, self-combustion and hydrothermal synthesis. The products obtained by the spray-drying method have magnetic properties only after heat treatment at 400–450°C at 550°C, the saturation magnetization of nickel ferrite is 16.9 emu/g, while for the cobalt ferrite is 51.3 emu/g.

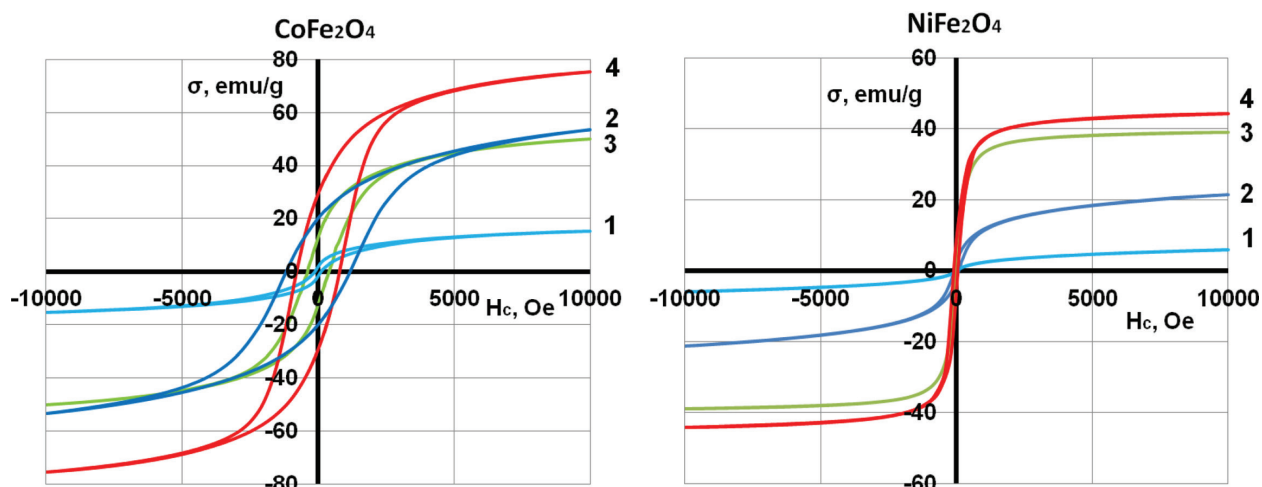


Figure 4. Magnetic properties of ferrites synthesized by the spray-drying (1) at 450°C, sol-gel self-combustion (2) and hydrothermal (3) method and in plasma (4).

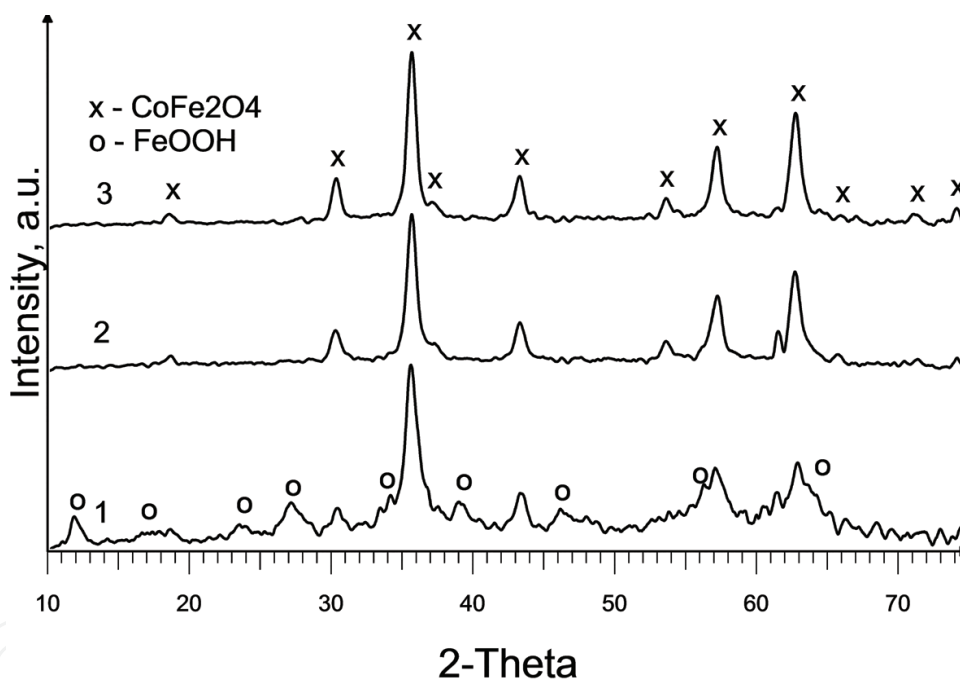


Figure 5. XRD pattern of the hydrothermally synthesized CoFe_2O_4 nanopowder prepared at: 1–200°C, 1 h; 2–230°C, 1 h; 3–250°C, 1 h.

Another interesting feature of nanoparticles synthesized in this study is their magnetic behavior, that is, although for all synthesized powders the particle size is below the critical size of a single domain (about 70 nm [41]), quasi-supermagnetic behavior is observed only for plasma-synthesized NiFe_2O_4 nanoparticles.

As an example of the impact of synthesis parameters, CoFe_2O_4 hydrothermal synthesis can be mentioned. Synthesizing at 200°C for 1 h, the product contains also $\text{FeO}(\text{OH})$ in addition to the basic phase (Figure 5). The product has weak magnetic properties (Table 2). Experiments

No	Mode, °C/h	SSA, m ² /g	d ₅₀ , nm*	Crystallite size, nm	XRD phases	Magnetic properties		
						M _s , emu/g	M _r , emu/g	H _c , Oe
1	200/1	58	20	~10	CoFe ₂ O ₄ , FeO(OH)	13.2	2.6	105
2	200/3	59	19	13–14	CoFe ₂ O ₄	—	—	—
3	230/1	63	18	10–13	CoFe ₂ O ₄	50.0	10.2	494
4	230/3	55	21	15–16	CoFe ₂ O ₄	58.9	17.8	643
5	250/1	61	19	12–13	CoFe ₂ O ₄	57.3	17.3	566
6	250/3	62	18	10–12	CoFe ₂ O ₄	59.8	16.8	574

*Calculated from SSA.

Table 2. Characteristics of CoFe₂O₄ nanopowders prepared hydrothermally.

have shown that the optimum synthesis temperature, when the pure one-phase product is formed, is from 230°C. Increasing the processing temperatures (up to 250°C) and time (up to 3 h) does not significantly affect the size of the specific surface area and crystallite. Increasing of the synthesis temperature and hydrothermal treatment time results in a small increase in magnetic characteristics (saturation magnetization M_s, remanent magnetization M_r and coercivity H_c) (**Table 2**).

After thermal treatment at higher temperatures, ferrite nanopowders synthesized by self-combustion, hydrothermal and spray-drying method, tend to decrease their SSA, but the particle size and crystallite size increase (**Figure 6**). This trend can be explained by the fact that the particles recrystallize and grow at higher temperatures, so the specific surface decreases. With the increase of crystallite size, the saturation magnetization and remanent magnetization of ferrites increase (**Tables 3 and 4, Figures 7 and 8**). For example, after thermal treatment of CoFe₂O₄ obtained by self-combustion and hydrothermal method at 800°C and more, the saturation magnetization increases to 80 and 72 emu/g, respectively.

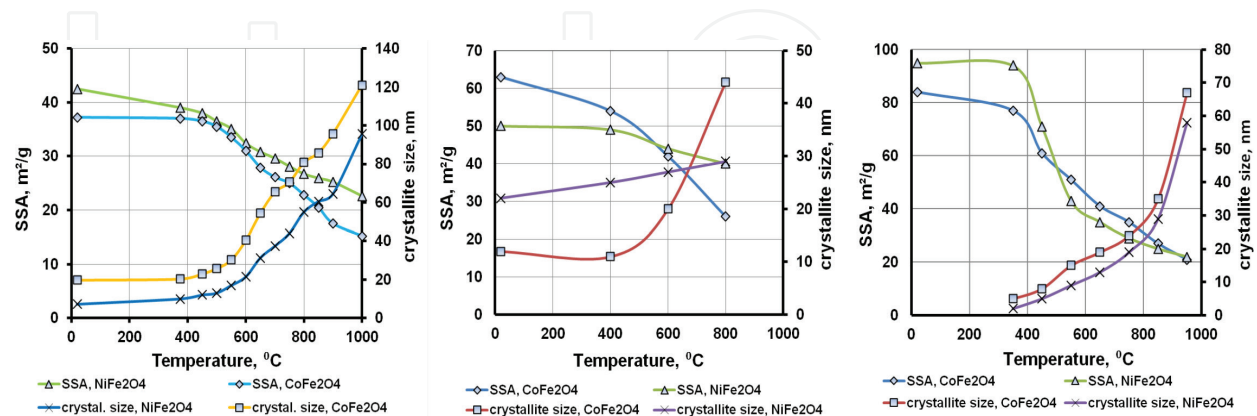


Figure 6. Specific surface area (SSA) and crystallite size comparison depending on temperature for NiFe₂O₄ and CoFe₂O₄ synthesized by the sol-gel self-combustion (A), the hydrothermal (B) and spray-drying (C) method.

Samples	Heating temperature, °C	M_s , emu/g	M_r , emu/g	H_c , Oe
CoFe ₂ O ₄ combust.	Raw powder	53.4	20.3	1170
	450	55.0	21.7	1190
	650	76.1	39.3	1350
	850	79.9	35.7	930
	900	79.8	31.3	980
CoFe ₂ O ₄ hydrotherm.	Raw powder	50.0	10.2	495
	400	50.1	12.6	390
	600	62.8	22.4	760
	800	71.6	28.9	875
	950	76.8	34.1	1067
CoFe ₂ O ₄ spray	Raw powder	—	—	—
	350	—	—	—
	550	51.3	14.7	649
	750	61.1	22.3	878
	950	76.8	34.1	1067

Table 3. Magnetic properties of CoFe₂O₄ synthesized by the sol-gel self-combustion, hydrothermal and spray-drying methods after thermal treatment (2 h at different temperatures).

The spray-dried powder after the synthesis and granulation is partially amorphous and contains a small amount of FeO(OH). After heat treatment, starting from 400 to 450°C, a stoichiometric, single-phase nanocrystalline powder (NiFe₂O₄ or CoFe₂O₄) (**Figure 9**) was formed, with SSA from 100 (at 350°C) to 20 m²/g (at 950°C) (**Figure 6**). The crystallite size at 350°C is 4 and 6 nm, respectively for NiFe₂O₄ and CoFe₂O₄, which increases with the increase of the processing temperature. The saturation magnetization (M_s) of the NiFe₂O₄ and CoFe₂O₄ ferrites increases, respectively, from 6 and 15 emu/g (at 450°C) to 40 and 77 emu/g (at 950°C) (**Tables 3 and 4, Figure 8**).

The relative density of samples before sintering was of 51–52% for plasma synthesized products and of 31–33% for products obtained by other methods. This shows that the ferrite nanopowders obtained by these methods are more difficult to compress because their particles are finer than ferrite powders synthesized in plasma.

Nanosized ferrite powders were sintered at 900–1300°C. The density of ferrites after the heat treatment is shown in **Table 5**.

The sintering process of plasma synthesis products is the fastest compared with all investigated nanopowders: they have a high density at 900°C, but above 1000°C, the density is approaching already 100%. CoFe₂O₄ ferrites synthesized by other methods have a relatively high density at 1100°C, while NiFe₂O₄ ferrites require the temperature of 1200°C or higher to achieve high density. Although the sintering temperature of the ferrites obtained by the

Samples	Heating temperature, °C	M_s , emu/g	M_r , emu/g	H_c , Oe
NiFe ₂ O ₄ combust.	Raw powder	29.0	6.0	120
	450	31.4	4.8	130
	650	37.4	9.1	200
	850	45.2	14.8	145
	900	47.4	15.0	135
NiFe ₂ O ₄ hydrotherm.	Raw powder	37.4	2.6	23
	400	36.7	3.8	34
	600	40.2	5.2	55
	800	42.6	5.0	70
NiFe ₂ O ₄ spray	Raw powder	—	—	—
	350	—	—	—
	550	16.9	1.1	57
	750	21.6	4.5	214
	950	40.0	8.6	151

Table 4. Magnetic properties of NiFe₂O₄ synthesized by the sol-gel self-combustion, hydrothermal and spray-drying methods after thermal treatment (2 h at different temperatures).

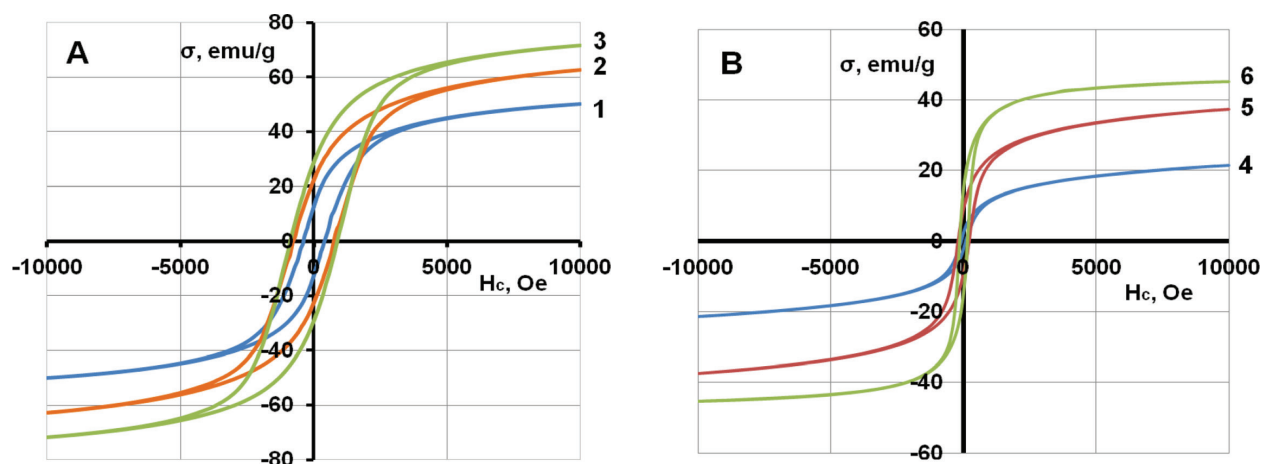


Figure 7. The magnetic properties of the sample CoFe₂O₄ prepared by the hydrothermal synthesis (A) after thermal treatment at 400°C (1), 600°C (2) and 800°C (3), NiFe₂O₄ prepared by the self-combustion synthesis (B) after thermal treatment at 450°C (4), 650°C (5) and 850°C (6).

spray method is slightly higher, they could be the most promising on the technological point of view among all these nanopowders because they are flowing and can be pressed without further treatment.

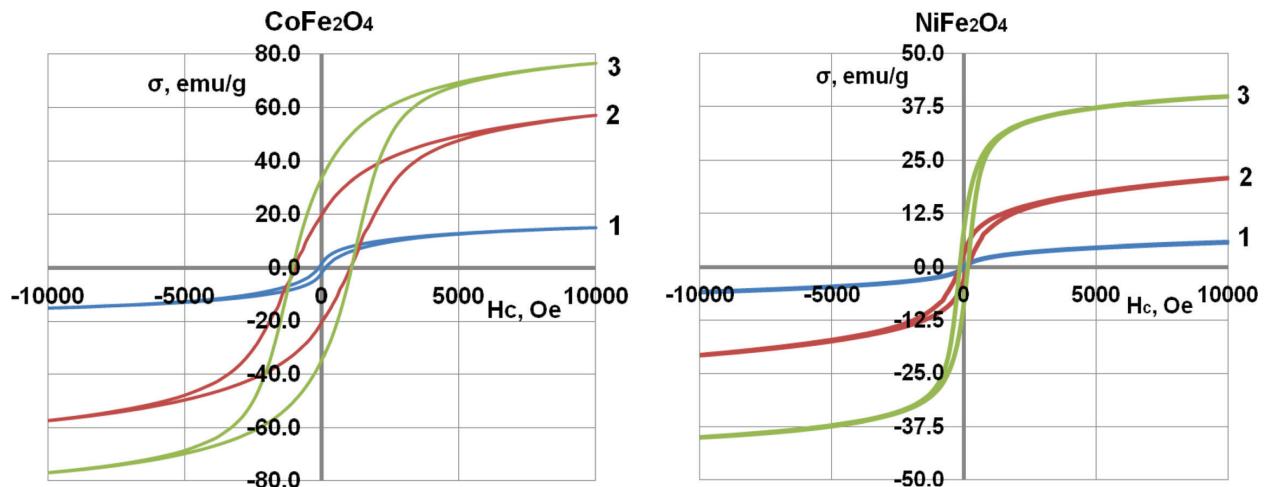


Figure 8. The magnetic properties of samples of CoFe_2O_4 and NiFe_2O_4 after thermal treatment at 450 (1), 650 (2) and 950 (3)°C prepared by the spray-drying method.

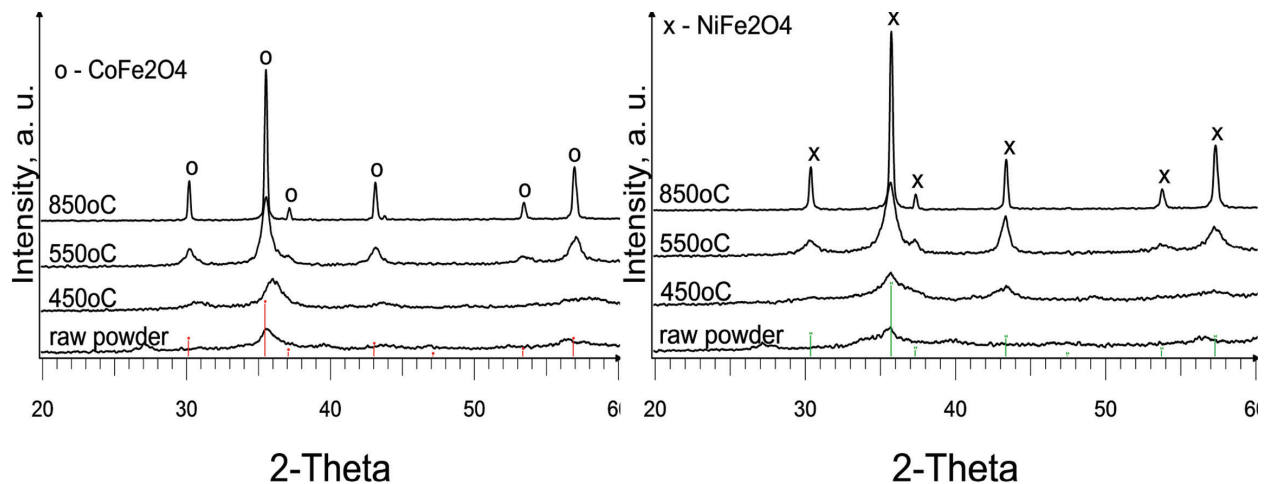


Figure 9. XRD pattern of spray-dried CoFe_2O_4 and NiFe_2O_4 ferrite nanopowders.

The crystallite size grows slightly during sintering: from 70 to 80 nm at 1100°C to 120–140 nm at 1300°C. For example, the crystallite size of hydrothermal CoFe_2O_4 varies from 10 to 13 nm in the raw powder to 75 nm (1000°C) and 150 nm (sintered at 1200°C). The grain size of samples sintered at 1200°C, obtained from self-combustion, hydrothermal and spray-dried powders, does not exceed 1 to 6 μm (**Figure 10**). As a result of high sintering activity, the grain size of plasma-synthesized ferrite outweighs: 10–15 μm for NiFe_2O_4 and 10–30 μm for CoFe_2O_4 .

Compared with the ferrite nanopowders, ceramic materials have a higher saturation magnetization (**Figure 11**) and lower coercivity. This could be explained by the increase in grain size and crystallite size. An increase in the temperature of the sintering results in the increase of the grain size and magnetization for all ferrite materials, while coercivity decreases (**Table 6**).

Sample	Sintering temperature, °C									
	900		1000		1100		1200		1300	
	ρ , %	P_{op} , %	ρ , %	P_{op} , %	ρ , %	P_{op} , %	ρ , %	P_{op} , %	ρ , %	P_{op} , %
CoFe ₂ O ₄ (plasma)	82.6	16.0	97.0	0.2	98.5	0.1	97.9	0	—	—
CoFe ₂ O ₄ (combust.)	—	—	65.7	33.4	78.3	21.6	93.4	3.1	—	—
CoFe ₂ O ₄ (hydrotherm.)	—	—	81.3	14.2	94.3	0.8	95.0	0.1	—	—
CoFe ₂ O ₄ (spray)	—	—	62.3	35.5	90.0	8.8	90.8	4.7	95.1	0.7
NiFe ₂ O ₄ (plasma)	87.9	12.1	99.4	0.2	99.9	0.1	100.0	0	—	—
NiFe ₂ O ₄ (combust.)	—	—	72.4	25.5	87.7	9.4	96.1	1.6	—	—
NiFe ₂ O ₄ (hydrotherm.)	—	—	—	—	79.1	19.8	85.8	12.0	—	—
NiFe ₂ O ₄ (spray)	—	—	52.2	44.0	69.5	27.6	85.3	12.1	90.7	7.1

ρ —density; P_{op} —open porosity.

Table 5. The relative density and open porosity of ferrites depending on sintering temperature (after 2 h sintering).

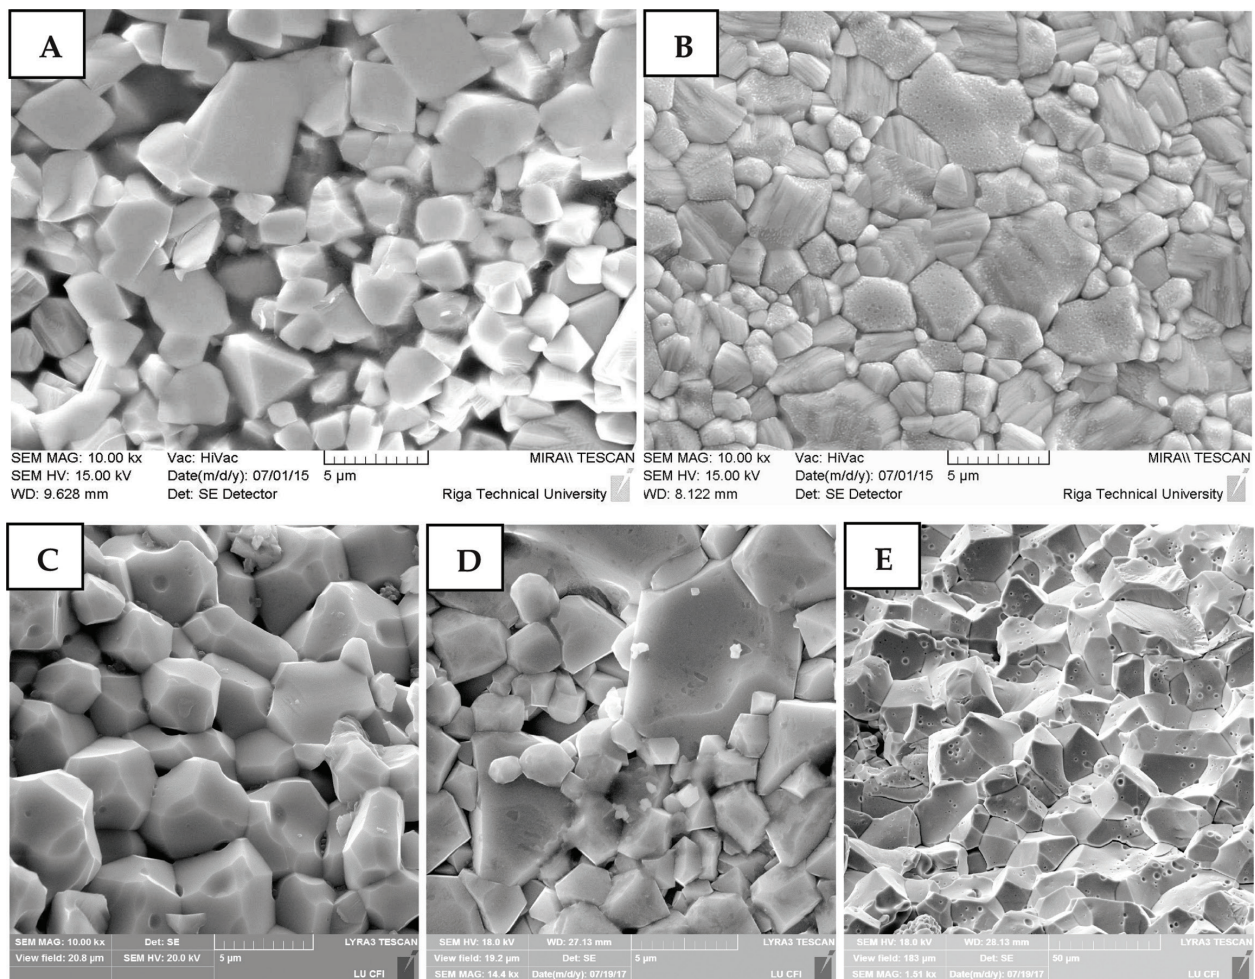


Figure 10. Typical SEM image of NiFe₂O₄ (a, D) and CoFe₂O₄ (B, C, E) ceramics sintered at 1200°C 2 h. The powders are prepared by hydrothermal (A, B), sol-gel self-propagating combustion (C), spray-drying (D) and plasma (E) methods.

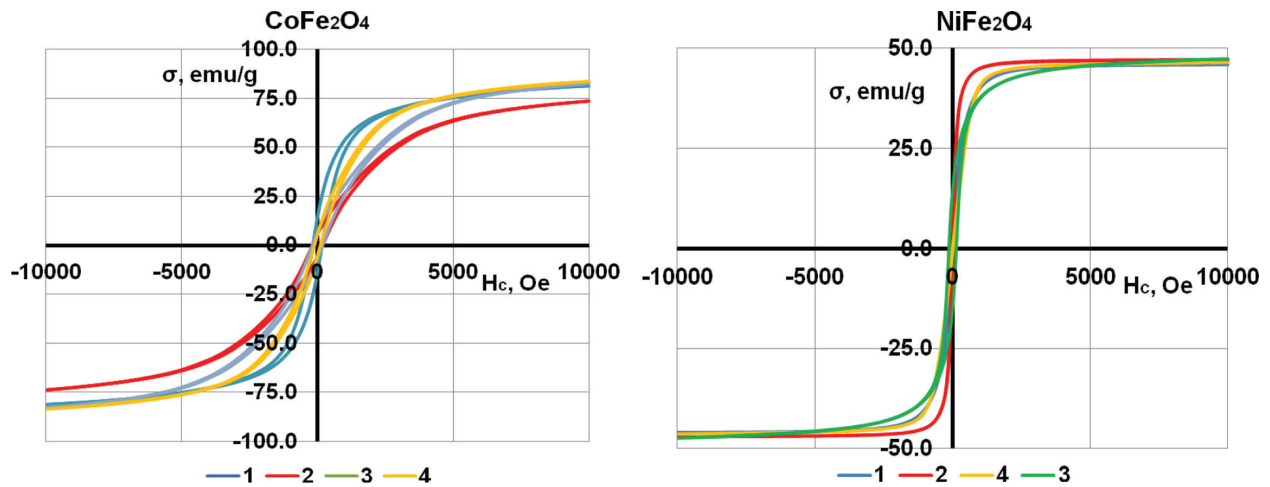


Figure 11. Magnetic properties of CoFe_2O_4 (a) and NiFe_2O_4 (B) ferrite, sintered at 1200°C from different powders: 1—hydrothermal, 2—spray-drying, 3—combustion, 4—plasma.

Heating temperature, $^\circ\text{C}$	CoFe_2O_4		NiFe_2O_4			
	M_s , emu/g	M_r , emu/g	H_c , Oe	M_s , emu/g	M_r , emu/g	H_c , Oe
Self-combustion						
1200	82.6	6.9	190	—	—	—
Hydrothermal						
1100	77.0	20.7	493	40.4	6.5	102
1200	81.3	14.1	169	46.0	1.7	15
Spray						
1100	74.6	15.3	427	48.0	3.0	35
1300	73.8	5.9	187	47.0	2.4	11
Plasma						
1100	81.8	14.0	258	45.7	3.8	35
1200	83.6	8.0	110	46.3	0.7	11

Table 6. Magnetic properties of CoFe_2O_4 and NiFe_2O_4 ceramics after 2 h sintering.

The magnetic properties of the samples sintered at 1200°C are almost the same regardless of the method of extracting ferrite powders: saturation magnetization for CoFe_2O_4 is of 80–84 emu/g and 46–48 emu/g for NiFe_2O_4 .

4. Conclusions

Single-phase nickel and cobalt ferrite nanopowders can be successfully synthesized by the chemical sol-gel self-propagating combustion and co-precipitation method combined with

hydrothermal synthesis or spray-drying method as well as high-frequency plasma synthesis. The magnetic properties of synthesized ferrite powders depend on their synthesis method.

Comparing the methods for obtaining ferrite nanopowders described earlier, we can say that plasma synthesis currently is the most productive method resulting in the highest magnetic properties (75 emu/g for CoFe_2O_4 and 44 emu/g for NiFe_2O_4). The disadvantage of this method is the presence of particles exceeding the size of 100 nm in a product that is not acceptable in all applications.

The chemical sol-gel self-propagating combustion and hydrothermal synthesis methods enables the production of smaller particles ($\text{SSA} = 35\text{--}55 \text{ m}^2/\text{g}$; average particle size 20–30 nm) with less explicated magnetic properties (50–55 emu/g for CoFe_2O_4 and 20–40 emu/g for NiFe_2O_4) after synthesis, which can be increased after heat treatment at temperatures up to 800°C. The lack of these methods is a time-consuming process of filtering nanoparticles.

The filtration process can be bypassed by the spray-drying method. Here, the smallest particles of the powder ($\text{SSA} = 80\text{--}90 \text{ m}^2/\text{g}$, average particle size 10–15 nm) are obtained, but due to the low processing temperatures, they have no explicated magnetic properties. Magnetic properties are observed after additional treatment starting at 400–450°C. However, the granular product is well suited for automated pressing processes for production of ceramic materials.

Sintered materials have higher magnetic properties than nanopowders. Magnetic properties of samples sintered at 1200°C are almost the same regardless of the method of obtaining ferrite powders: the saturation magnetization of CoFe_2O_4 is 80–84 emu/g and 46–48 emu/g for NiFe_2O_4 .

Author details

Ilmars Zalite^{1*}, Gundega Heidemane¹, Janis Grabis¹ and Mikhail Maiorov²

*Address all correspondence to: ilmars.zalite@rtu.lv

1 Institute of Inorganic Chemistry, Riga Technical University, Riga, Latvia

2 Institute of Physics, University of Latvia, Salaspils, Latvia

References

- [1] Costa ACFM, Tortella E, Morelli MR, Kiminami RHGA. Synthesis, microstructure and magnetic properties of Ni–Zn ferrites. *Journal of Magnetism and Magnetic Materials*. 2003;**256**:174–182. DOI: 10.1016/S0304-8853(02)00449-3
- [2] Priyadharsini P, Pradeep A, Chandrasekaran G. Novel combustion route of synthesis and characterization of nanocrystalline mixed ferrites of Ni–Zn. *Journal of Magnetism and Magnetic Materials*. 2009;**321**:1898–1903. DOI: 10.1016/j.jmmm.2008.12.005
- [3] Hou C, Yu H, Zhang Q, Li Y, Wang H. Preparation and magnetic property analysis of monodisperse Co–Zn ferrite nanospheres. *Journal of Alloys and Compounds*. 2010;**491**:431–435. DOI: 10.1016/j.jallcom.2009.10.217

- [4] Gul IH, Ahmed W, Maqsood A. Electrical and magnetic characterization of nanocrystalline Ni-Zn ferrite synthesis by co-precipitation route. *Journal of Magnetism and Magnetic Materials*. 2008;**320**:270-275. DOI: 10.1016/j.jmmm.2007.05.032
- [5] Yadoji P, Peelamedu R, Agrawal D, Roy R. Microwave sintering of Ni-Zn ferrites: Comparison with conventional sintering. *Materials Science and Engineering: B*. 2003;**98**:269-278. DOI: 10.1016/S0921-5107(03)00063-1
- [6] Jadhav SS, Patange SM, Jadhav KM. Dielectric behaviour study of nanocrystalline Co-Zn ferrite. *Journal of Biomedical and Bioengineering*. 2010;**1**:21-29
- [7] Ahmed MA, EL-Khawlani AA. Enhancement of the crystal size and magnetic properties of Mg-substituted Co ferrite. *Journal of Magnetism and Magnetic Materials*. 2009;**321**:1959-1963. DOI: 10.1016/j.jmmm.2008.12.021
- [8] Gul IH, Abbasi AZ, Amin F, Anis-ur-Rehman M, Maqsood A. Structural, magnetic and electrical properties of $\text{Co}_{1-x}\text{Zn}_x\text{Fe}_2\text{O}_4$ synthesized by co-precipitation method. *Journal of Magnetism and Magnetic Materials*. 2007;**311**:494-499. DOI: 10.1016/j.jmmm.2006.08.005
- [9] Xue B, Liu R, Xu ZD, Zheng YF. Microwave Fabrication and Magnetic Property of Hierarchical Spherical $\alpha\text{-Fe}_2\text{O}_3$ Nanostructures. *Chemistry Letters*. 2008;**37**:1058-1059. DOI: 10.1246/cl.2008.1058
- [10] Fortin JP, Wilhelm C, Servais J, Menager C, Bacri JCF, Gazeau J. Size sorted anionic iron oxide nanomagnets as colloidal mediators for magnetic hyperthermia. *Chemical Society*. 2007;**129**:2628-2635. DOI: 10.1021/ja067457e
- [11] Gul IH, Amin F, Abbasi AZ, Anis-ur-Rehman M, Maqsood A. Physical and magnetic characterization of co-precipitated nanosize Co-Ni ferrites. *Scripta Materialia*. 2007;**56**:497-500. DOI: 10.1016/j.scriptamat.2006.11.020
- [12] Slatineanu T, Iordan AR, Oancea V, Palamaru MN, Dumitru I, Constantin CP, Caltun OF. Magnetic and dielectric properties of Co-Zn ferrite. *Materials Science and Engineering: B*. 2013;**178**:1040-1047. DOI: 10.1016/j.mseb.2013.06.014
- [13] Arulmurugan R, Jeyadevan B, Vaidyanathan G, Sendhilnathan S. Effect of zinc substitution on Co-Zn and Mn-Zn ferrite nanoparticles prepared by co-precipitation. *Journal of Magnetism and Magnetic Materials*. 2005;**288**:470-477. DOI: 10.1016/j.jmmm.2004.09.138
- [14] Tawfik A. Electromechanical properties of $\text{Co}_{0.6}\text{Zn}_{0.4}\text{Fe}_2\text{O}_4$ ferrite transducer. *Journal of Magnetism and Magnetic Materials*. 2001;**237**:283-287. DOI: 10.1016/S0304-8853(01)00466-8
- [15] Kumar S, Singh V, Aggarwal S, Mandal UK, Kotnala RK. Monodisperse Co, Zn-Ferrite nanocrystals: Controlled synthesis, characterization and magnetic properties. *Journal of Magnetism and Magnetic Materials*. 2012;**324**:3683-3689. DOI: 10.1016/j.jmmm.2012.05.048
- [16] Gul IH, Maqsood A. Structural, magnetic and electrical properties of cobalt ferrites prepared by the sol-gel route. *Journal of Alloys and Compounds*. 2008;**465**:227-231. DOI: 10.1016/j.jallcom.2007.11.006

- [17] Giri AK, Kirkpatrick EM, Moongkhamklang P, Majetich SA. Photomagnetism and structure in cobalt ferrite nanoparticles. *Applied Physics Letters*. 2002;**80**:2341. DOI: 10.1063/1.1464661
- [18] Suryanarayana C. Nanocrystalline materials. *International Materials Reviews*. 1995; **40**:41-64. DOI: 10.1179/imr.1995.40.2.41
- [19] van der Zaag PJ, Ruigrok JJM, Noordermeer A, van Delden MHW. The initial permeability of polycrystalline MnZn ferrites: The influence of domain and microstructure. *Journal of Applied Physics*. 1993;**74**:4085-4095. DOI: 10.1063/1.354454
- [20] Chicinas I. Soft magnetic nanocrystalline powders produced by mechanical alloying routes. *Journal of Optoelectronics and Advanced Materials*. 2006;**8**:439-448
- [21] Akther Hossain AKM, Tabata H, Kawai T. Magnetoresistive properties of $Zn_{1-x}Co_xFe_2O_4$ ferrites. *Journal of Magnetism and Magnetic Materials*. 2008;**320**:1157-1162. DOI: 10.1016/j.jmmm.2007.11.009
- [22] Ferreira TAS, Waerenborgh JC, Mendonça MHRM, Nunes MR, Costaa FM. Structural and morphological characterization of $FeCo_2O_4$ and $CoFe_2O_4$ spinels prepared by a coprecipitation method. *Solid State Sciences*. 2003;**5**:383-392. DOI: 10.1016/S1293-2558(03)00011-6
- [23] Tang DQ, Zhang DJ, Ai H. Fabrication of magnetic core-shell $CoFe_2O_4/Al_2O_3$ nanoparticles as immobilized metal chelate affinity support for protein adsorption. *Chemistry Letters*. 2006;**35**:1238-1239. DOI: 10.1246/cl.2006.1238
- [24] Zhou Z, Zhang Y, Wang Z, Wei W, Tang W, Shi J, Xiong R. Electronic structure studies of the spinel $CoFe_2O_4$ by X-ray photoelectron spectroscopy. *Applied Surface Science*. 2008;**254**:6972-6975. DOI: 10.1016/j.apsusc.2008.05.067
- [25] Duong GV, Hanh N, Linh DV, Groessinger R, Weinberger P, Schafler E, Zehetbauer M. Monodispersed nanocrystalline $Co_{1-x}Zn_xFe_2O_4$ particles by forced hydrolysis: Synthesis and characterization. *Journal of Magnetism and Magnetic Materials*. 2007;**311**:46-50. DOI: 10.1016/j.jmmm.2006.11.167
- [26] Millot N, Gallet SL, Aymes D, Bernard F, Grin Y. Spark plasma sintering of cobalt ferrite nanopowders prepared by coprecipitation and hydrothermal synthesis. *Journal of the European Ceramic Society*. 2007;**27**:921-926. DOI: 10.1016/j.jeurceramsoc.2006.04.141
- [27] Giri J, Sriharsha T, Bahadur D. Optimization of parameters for the synthesis of nano-sized $Co_{1-x}Zn_xFe_2O_4$ ($0 \leq x \leq 0.8$) by microwave refluxing. *Journal of Materials Chemistry*. 2004;**14**:875-880. DOI: 10.1039/B310668C
- [28] Chau JLH, Hsu MK, Kao CC. Microwave plasma synthesis of Co and SiC-coated Co nanopowders. *Materials Letters*. 2006;**60**:947-951. DOI: 10.1016/j.matlet.2005.10.054
- [29] Kim CK, Lee JH, Katoh S, Murakami R, Yoshimura M. Synthesis of Co-, Co-Zn and Ni-Zn ferrite powders by the microwave-hydrothermal method. *Materials Research Bulletin*. 2001;**36**:2241-2250. DOI: 10.1016/S0025-5408(01)00703-6

- [30] Jiang JZ, Wynn P, Mørup S, Okada T, Berry FJ. Magnetic structure evolution in mechanically milled nanostructured ZnFe_2O_4 particles. *Nanostructured Materials*. 1999;**12**:737-740. DOI: 10.1016/S0965-9773(99)00228-7
- [31] Hocheplied JF, Bonville P, Pileni MP. Nonstoichiometric zinc ferrite nanocrystals: Syntheses and unusual magnetic properties. *The Journal of Physical Chemistry B*. 2000;**104**:905-9122. DOI: 10.1021/jp991626i
- [32] Shafi KVPM, Gedanken A, Prozorov R, Balogh J. Sonochemical preparation and size-dependent properties of nanostructured CoFe_2O_4 particles. *Chemistry of Materials*. 1998;**10**:3445-3450. DOI: 10.1021/cm980182k
- [33] Jalaly M, Enayati MH, Karimzadeh F, Kameli P. Mechanochemical synthesis of nanostructured magnetic Ni-Zn ferrite. *Powder Technology*. 2009;**193**:150-153. DOI: 10.1016/j.powtec.2009.03.008
- [34] Li F, Liu J, Evans DG, Duan X. Stoichiometric synthesis of pure MFe_2O_4 (M = Mg, Co, and Ni) spinel ferrites from tailored layered double hydroxide (hydrotalcite-like) precursors. *Chemistry of Materials*. 2004;**16**:1597-1602. DOI: 10.1021/cm035248c
- [35] Grabis J, Zalite I. Nanosize powders of refractory compounds for obtaining of fine-grained ceramic materials. *Materials Science Forum*. 2007;**555**:267-272. DOI: 10.4028/www.scientific.net/MSF.555.267
- [36] Zalite I, Heidemane G, Kodols M, Grabis J, Maiorov M. The synthesis, characterization and sintering of nickel and cobalt ferrite nanopowders. *Materials Science (Medžigotyra)*. 2012;**18**:3-7. DOI: 10.5755/j01.ms.18.1.1332
- [37] Zalite I, Heidemane G, Kuznetsova L, Maiorov M. Hydrothermal synthesis of cobalt ferrite nanosized powders. *IOP Conference Series: Materials Science and Engineering*. 2015;**77**:5. DOI: 10.1088/1757-899X/77/1/012011
- [38] Zalite I, Heidemane G, Palcevskis E, Maiorov M. Properties of nanosized ferrite powders and sintered materials prepared by the Co-precipitation technology, combined with the spray-drying method. *Key Engineering Materials*. 2016;**721**:295-299. DOI: 10.4028/www.scientific.net/KEM.721.295
- [39] Zalite I, Heidemane G, Kuznetsova L, Kodols M, Grabis J, Maiorov M. The synthesis and characterization of nickel and cobalt ferrite nanopowders obtained by different methods. *Chemical Technology*. 2016;**67**:53-57. DOI: 10.5755/j01.ct.67.1.15824
- [40] Smit J, Wijn HPJ. *Ferrites: Physical properties of ferrimagnetic oxides in relation to their technical applications*. Eindhoven, The Netherlands: Philips Technical Library; 1959. p. 384
- [41] Song Q, Zhang ZJ. Correlation between spin-orbital coupling and the superparamagnetic properties in magnetite and cobalt ferrite spinel nanocrystals. *Journal of Physical Chemistry B*. 2006;**110**:11205-11209. DOI: 10.1021/jp060577o

