

We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

4,800

Open access books available

122,000

International authors and editors

135M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities



WEB OF SCIENCE™

Selection of our books indexed in the Book Citation Index
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?
Contact book.department@intechopen.com

Numbers displayed above are based on latest data collected.

For more information visit www.intechopen.com



Improving the Mechanical Properties of Natural Fiber Composites for Structural and Biomedical Applications

Owonubi J. Shesan, Agwuncha C. Stephen, Anusionwu G. Chioma, Revaprasadu Neerish and Sadiku E. Rotimi

Abstract

Natural fiber composites are designed for different purposes including structural and non-structural ones. These natural fiber composites vary greatly in their properties including mechanical properties. Mechanical properties which include the tensile and flexural properties are highly dependent on factors such as matrix type, filler type, processing, post processing treatment and many more, factors which are quite application specific. However, many research works develop their natural fiber composite before considering the possible applications. This chapter intends to X-ray the factors that affect the mechanical properties as it relates to structural and biomedical applications and suggest ways of improving the mechanical properties.

Keywords: natural composites, mechanical properties, structural applications, property improvement

1. Introduction

In recent times, the application of natural fiber polymer composites (NFPCs) for structural purposes has increased [1–7]. In the past, carbon fibers and basalt fibers reinforced polymer composites were commonly used due to their high performance to cost and high strength to weight ratios [8–15]. However, due to fundamental concerns, such as high cost of materials, durability, bonding integrity and gap in the development of standards for practice of abrading or wearing of machines among others, their uses have been limited [16–19]. More importantly is the environmental concerns, which has strengthened the call for complete replacement of all synthetic fibers. Hence, the increase in research output for possible replacement of synthetic fibers with natural fibers in polymer composites [20–22].

Structural materials required for structural applications encompass materials that are primarily for the purpose of stress transmission or support. Structural materials may be in transportation (aircraft and automobiles), construction (building and roads), or in components used for the purpose of protecting the body (helmets and body armor), energy production (turbine blades), etc. [23–25]. Also,

those used in microelectronics, are designed to meet specific performance requirements. Structural requirements may vary based on end use; hence the requirement for a material to be used for vehicle part may differ widely from what is required for manufacturing casing for electronic equipment. Generally, of more interest are the following properties: mechanical, thermal, electrical conductivity, dimension stability, water absorbability, etc. [26–31]. This work intends to critically review the mechanical requirements and suggest ways of improving the mentioned properties for structural and biomedical applications.

2. Mechanical properties of NFPCs

NFPCs are different depending on the type of polymers or fibers employed, the processing condition and the characteristic properties developed after processing [32, 33]. The use of these NFPCs for structural applications depends more on the mechanical properties. There are different mechanical evaluations carried out on a material and some are very specific to individual application. However, the general focus of most researchers is on a few tests including tensile test, flexural test, impact test, compression test and hardness. These few tests can describe the mechanical behavior of any material to a large extent and also gives an insight to other possible areas of applications.

2.1 Tensile properties

Tensile test is one of the fundamental and common types of mechanical test widely used for testing polymeric materials. It is also known as tension testing; it is used to determine the stress-strain behavior under tension [32]. In tensile testing, tensile force (pulling force) is applied to a material and the specimens' response to that applied force (stress) is measured. Under this test condition, samples are subjected to controlled tension until failure occurs. Tensile test determines how strong a material is and how long it can be stretched. Important information that can be obtained from tensile test includes; Young's modulus, yield strength, percentage elongation and ultimate tensile strength (UTS).

2.2 Flexural properties

Flexural test is used to determine the capability of a material to resist bending forces applied perpendicularly to its longitudinal axis and often called the transverse beam test. Flexural test properties are among the major parameters used in assessing the suitability of composite materials for structural applications. Parameters such as flexural load, flexural Young's modulus, flexural strength and deflection at break are measured and used to interpret the mechanical behavior under flexural stress.

2.3 Impact properties

Impact test is employed in assessing the impact strength, toughness and notch sensitivity of structural materials. In summary it is the capability of the material in question to withstand high rate loading. Toughness is the total of energy absorbed per unit volume of material before rupturing. The toughness is a measure of balance between strength and ductility of the material. Impact test is very critical for most polymer materials because it relates to the product performance and service life. It also influences other properties related to product safety and liability.

2.4 Compressive properties

Compressive tests evaluate the materials behavior when subjected to uniaxial compression load at a relatively low and uniform loading rate. These tests are very important for product design analysis, especially materials for building purposes. Compressive strength and compressive Young's modulus are the two major properties that are used; however, there are also compressive strain, deformation beyond yield point, and compressive yield stress.

2.5 Hardness properties

Hardness is that property of an engineering material which enables it to resist scratching, indentation, penetration and plastic deformation. It is a very significant property for any structural material from the engineering point of view, because hardness generally leads to increase in wear resistance by either erosion by water, oil and steam or friction.

2.6 Crashworthiness

This is the degree to which a vehicle or aircraft will protect its occupant from the effect of an accident [34]. It is the most important concept in vehicle defect cases. That is, the ability to prevent injuries to the occupant in the event of collision. Therefore, crashworthiness focuses on occupant protection to reduce fatality in the case of an accident. Different criteria can be used to determine crashworthiness depending on the nature of the impact and vehicle involved [35].

In general for composites, these properties depend on other factors such as fiber length, fiber weight percentage content and the extent of polymer/fiber interactions as will be discussed later.

3. Natural fiber polymer composites in structural purposes

Natural fiber reinforced polymer composites are attracting widespread interest for purposes which are sensitive to the materials weight, because their strength and stiffness combine well with their low density, however, their toughness is a major concern [36]. NFPCs are prepared using plant fiber as fillers, which are hydrophilic in nature and do not interact well with hydrophobic polymer matrix [37–39]. NFPCs are a set of important materials developed for numerous areas application; medical, pharmaceutical, food packaging, electronics, aerospace, automobile, construction, building, transport and many more [40–43]. This is because of the many unique qualities these materials possess or can be designed to possess. Qualities which include, but are not limited to; light weight, resistant to chemical attraction, resistant to corrosion, ability to be molded to any shape, can be processed using existing technology, environmental friendliness and sustainability. That is why the interest in these materials has grown tremendously in the last two decades [36, 44–46].

Dweib et al. fabricated bio-based composites for roof structures in the form of paper sheets, entirely from cellulose fibers and soy oil-based resins [47]. These developed sheets were tested for structural unit beams and were established to have given the necessary strength and stiffness for consideration in roof construction. Also Bektas et al. manufactured panels with a density of 0.7 g/cm^3 with a sunflower stalks percentage of 25, 50 and 75% fiber contents [48]. From the results of the mechanical tests, the panels were observed to have the required properties as required for general purpose-use particle board by normal standards.

Wood fibers/plastic composites have been used in large quantities for applications in window and door frames, decks, docks and molded panel components [49–51]. Natural fiber composites have been used to replace asbestos in the building industry, because of their health related issues [52]. The European Union policy tagged “end of life vehicle (ELV)” regulations, promulgated in 2003 and amended in 2005 and 2010, projected reduction of the final waste to be disposed at the end of life of vehicles to 5% by the year 2015. In the stated regulations, 85% of material used in manufacture of the vehicle must be recoverable through reuse or through recycling mechanically [49, 53]. This has generally increased interest and widespread use of NFPCs worldwide. It is noteworthy that this policy was promoted basically because of environmental and social concerns and not necessarily because of economic or technological reasons.

NFPCs durability and the availability of technology has allowed for large and complex shaped manufacturing of NFPCs, making them appealing in the automobile industries [54–56]. In Brazil, automobile industries consume, on average, 10–12.7 kg of natural fiber reinforcement per vehicle. These are circulated through the vehicle, such as rear door liners, front doors, boot liners, parcel shelves, sun roof interior shields and headrests [54]. Although NFPCs have gained tremendous interest in the industries, their applications are not unconnected to their environmental sustainability, low cost and renewability [57–60]. According to a review by Kiruthika [61], the challenge of replacing synthetic fibers completely in widespread applications is far from being overcome, with the improvement to the mechanical properties of composites being the major challenge.

4. Factors influencing the mechanical properties of NFPCs

NFPCs are prepared by compounding polymer matrix (either pristine or blend) with natural plant fibers. The fibers can be single or hybrid, microcellulose or nanocellulose. The natural fibers are made up of different chemical constituents and are exposed to different physical and chemical treatments, therefore, the properties of the resulting composites varied widely. Factors influencing their eventual composite(s) include the following:

4.1 Fiber type

Plant fibers are categorized based on the parts of the plant they are extracted from. Fibers can be extracted from the seeds, leaves or bast of the plants. Bast fiber is collected from the “inner bark” or the surrounding of the stem of certain dicotyledonous plants [61], like banana, flax, hemp, jute kenaf and ramie. These fibers have higher tensile strength and are mostly used in the packaging and paper industries [62, 63]. Sisal, pineapple and many others are extracted from the plant leaves while coir, cotton and abaca are examples of fibers extracted from plant seed. Generally, plant fibers give higher strength and stiffness; however their properties depend mainly on their structure and chemical composition. These invariably relate to the source of fibers, method of extraction, maturity, growing conditions, harvesting period, degree of retting and modification [64–67].

4.2 Fiber length, orientation and weight percentage loading

NFPCs properties are affected by the length of the fibers used, their distribution, the percentage of the fiber volume or volume fraction and their orientation within the matrix. For polymer composites, stress is transferred by the matrix through the fibers both at the interface along the fiber length and at the ends of the fibers by

shear [68, 69]. Hence, the degree of load conveyed from the matrix to the fibers is a function of: (i) fiber length, which is referred to as critical fiber length or aspect ratio, (ii) orientation of the fibers and their direction relative to each other. If the fiber orientation and direction is not in the line of the applied stress, failure is bound to occur easily. Unidirectional fiber composites tend to transmit external stress better, that is why hand laid fiber composites performs better mechanically [70, 71].

Depending on the fibers in the matrix's orientation and direction, we can obtain three different types of reinforcement which include (i) longitudinally aligned fiber-filled composites, (ii) transversely aligned fiber-filled composites and (iii) randomly oriented short fiber composites [68, 72, 73]. While the longitudinally filled composites have low compression strength due to buckling of fibers and high tensile strength, the transversely filled composites on the other hand have low tensile strength. However, in the randomly oriented composites, it is far more difficult to predict the mechanical properties, due to the complexities of the distribution of load along the interface of the fiber and the matrix. Hence, considerable control over such elements as orientation dispersion and aspect ratio of the fibers, considerable improvement in the mechanical properties of the composites can be attained.

In general, high performance NFPCs can be obtained mainly by using materials with high fiber content, hence the effect of fiber loading on the properties of the NFPCs is of great significance. Also it is noteworthy to mention that additional fiber content of the composites invariably causes to increased tensile properties [74, 75].

4.3 Fiber-matrix adhesion

The effect of fiber-matrix adhesion cannot be over emphasized. A good number of researchers have reported their experimental results on the effect or importance of a good and strong fiber-matrix adhesion in the fabrication of composites with good mechanical properties [76, 77]. The type of bonds existing at the fiber-matrix interface greatly influences the mechanical properties of any fabricated composites. For a good transmission of stress from the matrix to the fiber to occur, the bond existing among the two components must be strong [64]. Due to the hydrophilic nature of the natural fibers, the interaction between the fibers and the hydrophobic polymer matrix is very weak [4, 78, 79]. Hence, the need to modify the fibers and introduce organic moiety that makes them more hydrophobic is necessary.

Fiber-matrix interface has been described as the reaction zone which plays a significant role in characterizing the composites mechanical properties [80]. A poor interaction between the two surfaces leads to poor transmission of load and therefore poor mechanical performance [81–83]. In addition, plant fibers need chemical modification for the distention or enlargement of the crystalline region, removal of surface impurities and elimination of hydrophilic hydroxyl groups for improvement to some of its relative properties [68].

4.4 Choice of polymer matrix

Polymer matrix could be either a thermoset or a thermoplastic, with varying preparation procedures and conditions, the performances of polymer matrix are affected quite differently. Thermoset are made in such a way that they develop good bonding with the fibers, especially during curing stage. However, the processes involved are time and energy consuming. Although in the case of tensile loading of the composites, the significance of matrix is evident, some researchers have reported good improvement with the same fiber when the matrices are changed. However, for compressive, in-plane shear and inter-laminar strength, they are highly influenced by the type of matrix used [84].

4.5 Processing conditions

The properties of NFPCS have been shown to vary from one processing technique to another [85–89]. Common techniques for the preparation of NFPCs include injection, extrusion, compression and resin transfer molding. These techniques use different processing conditions or parameters even when the materials being processed are the same. Changes in factors such as mixing speed, pressure and temperature can change the properties of the final product with any slight change [90]. For example, the preparation of sisal fiber polyester composites by employing both the compression molding and resin transfer molding technique (RTM) gave products with varying mechanical properties. The products of the RTM gave a composite with higher Young's modulus, tensile strength and flexural strength than the product of the compression molding [90]. Vacuum molding technique is one of the simplest manufacturing methods for plastic materials [91]. It is suitably adapted for molding a required shape from a plastic sheet material. In this molding technique, a plastic sheet is heated up to its molding temperature using electric heat; it is then transferred to a molded shape. To obtain the shape, a vacuum is created between the mold and the sheet. Vacuum molding is an inexpensive method when compared to other molding methods. It has numerous applications including, aircraft, skin tight packing, disposable tray and caps. It is a low cost method already being employed in many areas of endeavors as mentioned. A lot of research work is being carried out on how to improve the vacuum forming method, for instance, vacuum-assisted resin transfer (VARI), also known as vacuum infusion process (VIP) which was reported by [92] to be considered as an attractive method for the production of NFPCs low cost and good performance. It uses low-cost one-sided tooling and injects low-viscosity resin into dry fiber that was performed under low pressure. The method was found to be economically suitable for the manufacturing of large composite structures, such as boat hull, wind turbine blade and aircraft structures with low or high volumes of production.

However for vacuum forming method the cycle time of production is still much affected by the cool rate and time, amount of pressure applied and the fiber content [93]. These factors can greatly affect the mechanical properties of the final product.

4.6 Presence of void

The introduction of fibers into the matrix during processing is accompanied with the introduction of air and other volatile substances. These substances which are mostly trapped in the fibers may form voids in the composites after processing and curing along the individual fibers. This can negatively affect the composites mechanical properties. In addition, the rate of cooling during processing can also result to the formation of voids [73]. When the void content is too high, it leads to greater affinity for water diffusion, lowering fatigue resistances and increased disparity in mechanical properties [94].

4.7 Thermal stability

The importance of the stability in the preparation of the composites cannot be over emphasized as it affects the mechanical properties considerably. The different components of plant fibers are sensitive to different range of temperatures, i.e., hemicellulose, cellulose, pectin [95, 96]. Most fibers start degrading thermally at 220°C, thereby limiting the composites thermally [68]. In recent reports, the thermal stability of these fibers were greatly improved by removing maximally the lignin, hemicellulose and other alkaline soluble substances in the fiber through physical, chemical or biological means [97].

In general, the above mentioned factors do not influence the mechanical properties of NFPCs individually or in isolation. Rather, in the fabrication of a composite, the cumulative effect of two or more of these factors may be responsible for the composites mechanical failures. Jain et al. evaluated the effect of inter-fiber interactions of different class of reinforced polymer composites on the mechanical properties and the relation to stress field [98]. The research findings highlighted the important role of microstructural arrangement in the determination of the final response of the composites. They reportedly concluded that the local fiber matrix arrangement and their neighborhood density are highly influenced and sensitive to the stress and overall strain energy.

5. Methods for improving mechanical properties of NFPCs

There are different methods which can be employed for mechanical properties improvement of NFPCs. These methods are not rigid formulas that once applied will result in massive enhancements, rather improving mechanical properties of NFPCs is an active area which is ongoing. Mechanical improvement in one area of application may not necessarily yield the same result in another area of application. For example, improving stiffness of a material might be good for the construction and building industries but may not be required or worthwhile for biomedical applications, as it might prefer improvement in flexibility and toughness. Therefore all possible options will be provided; it is left for the researchers to select as appropriate. Furthermore, these methods can be combined to produce synergistic effect.

5.1 Surface modification

There are many literatures and reviews on the benefits of surface modification of natural fibers to the enhancement of fibers mechanical properties and by extension, the composites [99–101]. The mechanical properties of plant fibers depend greatly on the chemical structure, chemical composition and the structural arrangement of cellular fibrils [101]. Other factors such as climatic conditions, age, extraction procedures, growth condition and time of harvest also influence the mechanical properties of natural fibers. All these affect the percentage composition of cellulose in the fibers. Furthermore, the hemicelluloses and lignin are less thermally stable compared to cellulose, modification is one way of reducing the percentage content of hemicelluloses and lignin or even eliminating them completely.

Graphical sample of cellulose structure which consists of amorphous (untreated) and crystalline (treated) regions is shown in **Figure 1** [69]. There exist strong intra-molecular hydrogen bonds with large molecules in the crystalline regions of the cellulose ensuring the crystalline region is very compact and this makes it difficult for chemical penetration. On the other hand, the amorphous region is loose and allows penetration for possible modification.

Surface modification of plant fibers involves the treatment given to the plant fibers in order to increase its cellulose content, improve its interaction with the polymer matrix and also improve their mechanical, thermal and dimensional stability properties. Surface modification can be physical, chemical or biological [11, 21, 79, 102, 103].

Chemical modification involves chemical reaction with the fiber components, thereby making them soluble so that they can be removed by repeated washing. Alkali treatment also known as mercerization involve the use of alkali solution to dissolve all soluble contents of the fibers including wax, oil, pectin, lignin and some part of hemicelluloses [11, 104–107]. Alkali treatment makes the fibers surface rougher and reduce the fibers to fibrils [108, 109]. It improves the aspect ratio and

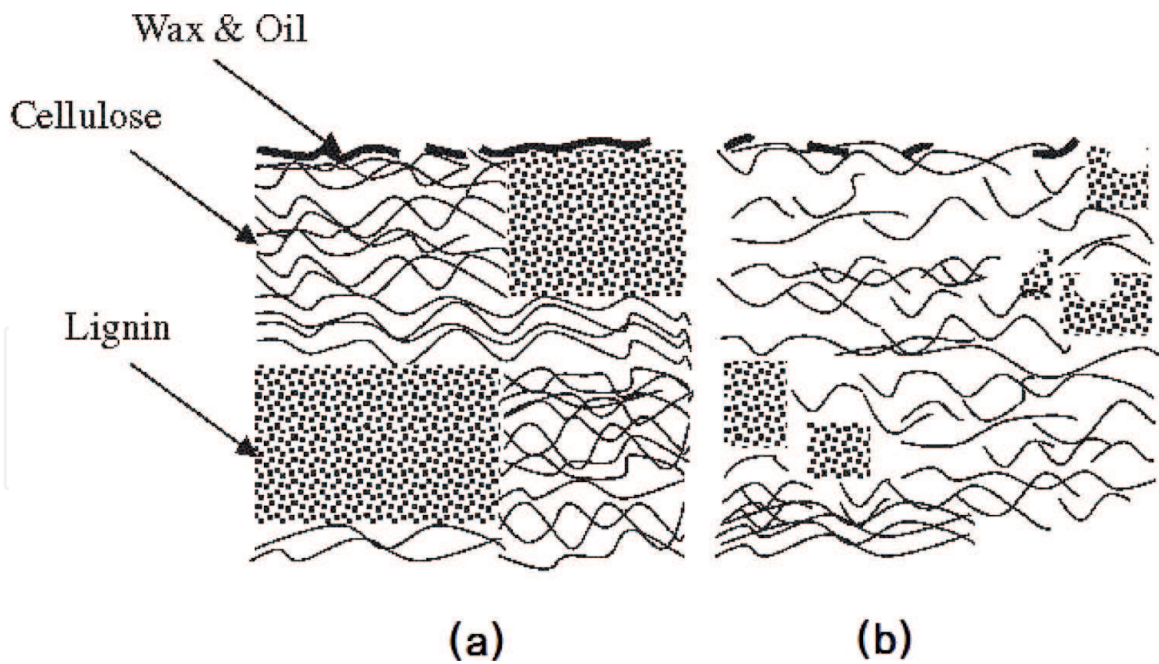


Figure 1. Schematic diagram showing the crystalline (a)/amorphous (b) regions in a fiber material [69].

creates room for mechanical interlocking in composites [23, 110–112]. To improve chemical interactions in NFPCs which may lead to improved mechanical properties, more chemical treatments are required other than alkali treatment. Another advantage of alkali treatment is that it exposes the OH group on the cellulose chains which can again be utilized for further chemical modification in some cases and in others it can allow for chemical treatment to introduce functional groups onto the surfaces of the fibers. These functional groups can then be used for chemical interaction during the preparation of the composites [27, 113, 114]. Such chemical treatments include silane, sodium silicate, oxidization treatments with DCP, or KMnO_4 treatments.

Biological methods involve the degradation by biological organism of all other components of the fiber except the cellulose. This is because the cellulose is highly crystalline and so cannot be easily degraded. Biological treatments are more environmentally friendly, produces more crystalline cellulose with better mechanical and thermal properties and it is cost effective. However, it is laborious and time consuming [115–121].

Physical methods of surface modification involve the use of plasma and corona treatment to change the fiber surface physically. This helps to create rough surfaces that are beneficial for mechanical interlocking [122–124]. However, plasma treatment can be used to introduce chemical functionality onto the fibers so that they can undergo chemical reaction with the polymer matrix [122–124]. Surface treatment introduces rigidity and stiffness to the fibers and by extension, the composites will be suitable for possible structural applications in industries such as building, aerospace marine, packaging, automobile, etc.

Liu et al. [125] reported the improved mechanical characteristics, resulting from alkali treatment on Indian grass fiber used as reinforcement. The tensile Young's modulus of grass fiber reinforced composites treated with 30 wt% alkali improved by 60%, while their impact and flexural strengths improved by 30 and 40% respectively when compared to the 30 wt% raw fiber reinforced composites. The structural and morphological changes of alkali modified kenaf fibers modified using: 3, 6 and 9% NaOH solutions were reported by Edeerozey et al. [126]. From their SEM results, it was found that 6% and 9% NaOH treatment gave better results. However, the 9% NaOH treatment was considered to be too strong for the fibers, as it led to low tensile properties.

5.2 Blending

Polymer blends have been defined as the combination of two or more polymers, prepared to enhance the properties of the products as well as to lessen the cost. Blends of polymer can simply be viewed as a polymer alloy. Therefore, blending is the mixing of two or more distinct polymers, in a way that gives a new material which has properties that are slightly different from the singular polymers involved. Polymer blending is a versatile procedure to obtain new polymer materials with characteristics far better than the individual polymers [127, 128]. It is a well-recognized option to solving emerging problem related to application requirements.

The ability to combine existing polymers into new one with superior qualities that are commercially acceptable makes blending a better option [129]. There are large numbers of polymer blends reported in literature by researchers in academics and industry [130–132]. Polymer blending can give rise to miscible or phase separated blends. For miscible blends, mixing approaches a molecular dimensional scale and the properties of the new polymer blend are more like those of a single polymer. While phase separated blends still exhibit the different properties of the polymers involved [133–136]. Although, miscibility is extremely rare in blends, the advantage of miscible blends over phase separated blends is in the property profile, especially mechanical properties. Most phase separated blends exhibit inconsistency in their mechanical properties due to the poor adhesion at the interface of the blend phases. However, researchers have developed specific methods by which these phase separation problems can be alleviated [129]. Hence, polymer matrix can be designed to suit the required properties expected of the composites. Blending also helps to modify the matrix with specific chemical functionality that could be added deliberately to enable good interaction between the fibers and the blended matrix. Many researchers have shown that the performance properties of blends can be heightened significantly by reinforcing them with either synthetic or natural fibers [137–141]. However, bio-fiber reinforcements have gained ground in recent time because of their numerous advantages over glass and carbon fibers [142].

According to Linares et al. [143], polymer blends have a recognized potential to produce high performance materials, however the polymer combination must be carefully selected. Müller-Buschbaum et al. [144] showed that blend composition has great influence on surface topography which is just one of the many factors that may affect the properties of the blend. Therefore, in the preparation of any blend, the selection of complementary polymers that will give the right kind of material hybrid with the required properties is the most important step. For a biodegradable polymer that will be green in all its ramifications, a blend of biopolymer material with a biodegradable counterpart is highly desirable. Among these, are: polycaprolactone, polybutylene succinate, etc. The use of blend started some decades ago [145], however, in the present day, the understanding of miscibility has undergone several changes [146]. The broad range of application of polymer materials requires varying properties according to the specific application area. With homopolymers, the range usually calls for special surface treatment or in some cases new polymer synthesis for each and every application. However, an economical alternative could be the preparing blends from specifically designated homopolymers [144].

5.3 Compatibilization

Compatibilization is described as the addition of a chemical substance to an immiscible or phase separated blend that help increase their stability. Compatibilizers are also referred to as coupling agents. They react at the interface of the blend to stabilize the phases. That is, they help to improve the compatibility

between the two phases and increase miscibility [146]. The high interfacial tension caused by coalescence phase separated blends can be reduced by the compatibilizers, allowing a continuous flow of externally applied stress from the matrix to the fibers [130]. Compatibilization can be done by (i) introduction of specific interacting groups, (ii) in-situ polymerization grafting, (iii) addition of a ternary polymeric component, (iv) addition of block co-polymers of the blend polymers, (v) interpenetrating networks of crosslinked system and (vi) using reactive compatibilization methods [147–150]. For instance, polyhydroxyether of bisphenol A (Phenoxy: PHE) a non-reactive compatibilizer has been noted in some reports to have provided improved interfacial adhesion between immiscible and marginally compatible polymer blends [129]. Specifically, the addition of PHE to some polymers blends led to the blends yielding improved dispersion of the polymers within the blend, gave uniform injection molded surfaces and considerably increased the notched impact strength of the blends (polysulfone (PDF)/ABS; PSF/PA, PMMA/PA6 and PHE/PBT) [129, 151, 152]. Also reactive compatibilizers can be design to react with the fiber when introduced during processing. This method will involve modifying the fiber surfaces prior to the composite preparation. If successful, this method has the capability to improve interfacial interaction and subsequently improve mechanical properties.

5.4 Addition of nanoparticles

The use of nanoparticles to enhance the properties of NFPCs have been widely reported [99, 153, 154]. Nanoparticles are inorganic materials which possess a very high surface to volume ratio in which one or its entire dimension is less than 100 nm [155]. The addition of these nanoparticles influences the crystallization process during the solidification of the polymer composites leading to improved mechanical and thermal properties. These particles can be modified to selectively interact with a particular phase of the composites in a controlled manner [23, 156–158]. They can also be modified to act as a compatibilizer and react with both the matrix and the fibers to bring about good interaction and a better composite with stress transfer behavior.

Vargas et al. [159] reported the influence of nanofillers on some properties of polypropylene including mechanical properties. Their findings revealed that the nanofillers, in the presence of PP grafted MA, improved the tensile strength and Young's modulus properties which are indicative of the synergistic effect between the nanoparticles and compatibilizers. According to Lee and Youn [160], the addition of layered silicates worsened tensile properties of PP nanocomposites prepared by them. Similar investigation was presented by Rault et al. revealing that the addition of a maximum 1 wt% led to improvement in tensile properties but above the maximum, the silicate nanoparticle caused difficulties for processing the composites due to the formation of aggregates [161]. However, Joshi et al. [162] has reported improvement in tensile properties of PP/nanoclay composites. Therefore, we can conclude with certainty that there are other factors interfering in the positive influence expected from the addition of nanoparticle such as clay. According the Vargas et al. [159], fibers geometry plays a vital role in determining the composites eventual properties. Nanoparticles of different shapes and sizes were used to prepare polyamide 6 (PA6) composites in some research work conducted by Vlasveld et al. [163]. Their findings revealed that the rheological properties of the composites samples were highly dependent on the aspect ratio of the nanoparticle used. Therefore utmost care must be taken when the option of nanoparticles are being considered. Other nanoparticles have been used and their influence on the mechanical properties have been positive and very encouraging [164, 165].

5.5 Hybridization

Hybrid composites involve the combination of two or more different types, shapes or sizes of reinforcement in one composite material [166]. The hybrid composite properties have been reported to depend on many factors such as; fibers individual property, fiber-matrix compatibility, roughness of fiber surfaces, orientation of fibers and the extent of their intermingling [167]. Recently, investigations on the hybrid composites properties were based on the natural/synthetic fibers, natural/natural fiber and natural/synthetic/additive modified reinforced polymer composites. The popularity of these types of composites are increasing rapidly owing to their capability to provide freedom to tailor the composites and realizing properties that cannot be obtained in fabricated composites containing singular type reinforcement [21, 79].

Fiber-based hybrid composites have been reported to have improved properties compared with the unhybridized composites having single reinforcement [168–170]. Many research reports have shown that the addition of synthetic fibers at various amount to form hybrid fibers have composites of better-quality, especially in respect to their mechanical properties [171–179]. According to Ashik and Sharma [180], in one of their reviews, they listed some factors that may impact the mechanical properties of natural fiber hybrid polymeric composites, with the processing parameters featuring as one of the factors. Also, Nunna et al. [181] listed fiber content, fiber treatment, and the environmental conditions as some of the conditions that affect the properties of hybrid composites. For hybrid natural/synthetic fibers, it has been reported that as wt% of the synthetic fiber rises, the mechanical properties also rises. However, at a certain wt% of the synthetic fiber content added, the properties of the composites mechanical properties starts dropping and this may be ascribed to poor interfacial adhesion, high fiber-to-fiber contact, and poor wettability.

Mishra et al. [182] prepared hybrid glass fiber (GF) and pineapple leaf fiber (PLF) polyester composite with a total fiber content of 25 wt%. The tensile strength was observed to have increased as the GF was increased from 0 to 7.5 wt% to approximately 70 MPa, after which the strength started dropping. The flexural strength kept increasing as glass content increased from 4.3 to 12.9 wt%, in the hybrid biocomposite. The authors also prepared a similar hybrid biocomposite, but this time with 30 wt% total fibers (sisal and glass fibers). They reportedly observed a major improvement in tensile strength as the GF content was increased to 5.7 wt%. After this, the tensile strength was almost static even as the GF content was increased above this value. A similar trend was observed for the flexural strength. However, comparing the hybrid biocomposites with the biocomposites containing only pineapple or sisal fibers, the hybrid showed better improvement. Nevertheless, more evidence is available to show that the overall properties of hybrid composites depend greatly on (i) the percentage elongation at break and (ii) Young's modulus of the reinforcing fibers present.

Shahzad [183] presented the impact and fatigue properties of hybrid biocomposites of hemp and chopped strand mat glass fibers using unsaturated polyester resin as the matrix. Two different variations of hybrids composites were prepared. The first denoted with "A" containing 35.8 wt% hemp fiber and 11.1 wt% GF, while the second denoted with "B" had 36.6 wt% and 11.3 wt% hemp and glass fibers respectively. From the results, "A" had 70.1 ± 10.2 MPa, 8.3 ± 0.4 GPa and $1.31 \pm 0.25\%$ for tensile strength, Young's modulus and strain to failure respectively, while "B" showed 81.6 ± 3.7 MPa, 7.7 ± 0.3 GPa and $1.73 \pm 0.08\%$ for tensile strength, Young's modulus and strain to failure improvement respectively when compared with biocomposites reinforced only with hemp fibers, having

46.4 ± 4.6 MPa, 7.2 ± 0.9 and 1.03% respectively. The increase in the percentage of GF led to the observed increase in tensile strength and better strain to failure in “B” as compare to “A.” The hemp fiber is a low strain to failure fiber while the glass fiber is a high strain to failure fiber. Their combination, leads to enhance strain to failure composites. This is referred to as “hybrid effect” and it has being well observed in hybrid composites. Therefore the increase in strain to failure of the hemp-glass fiber composites can be attributed to the hybrid effect. Also, there was an observed improvement in the fatigue strength of hybrid biocomposites while the fatigue sensitivity showed no improvements when compared to hemp only fiber composites.

Hybrid of glass/natural fibers have been reported to have improved impact, tensile and flexural strength [182]. Furthermore, Velmurugan and Manikandan [184] reported that good strength, especially mechanical strength is achieved when the synthetic fiber is placed at the ends of the composite for laminated composites.

In another research work, Ahmed and Vijayarangan [185] prepared composites with jute only and jute/glass fibers hybrid reinforced polyester composites, keeping the total weight fraction of fibers constant at 42 wt%. From their results, the composites consisting of 40:60 ratio of jute:glass fibers, the reinforced hybrid laminate gave an increase in the tensile strength, Young’s modulus, flexural strength and flexural Young’s modulus of 53, 30, 31 and 62% respectively over those of the jute only fiber composites. They further indicated that in the event properties, environmental impact and costs were to be considered, composites with 60:40 fiber fraction of jute:glass fibers ratio gave optimum material combination. This clearly highlights that the type of matrix and/or fiber, method of preparation, fiber content and fiber modification have a huge impact on the mechanical properties of hybrid biocomposites.

5.6 Other factors

In the preparation of NFPCs, there are many other additives or processes that can also influence the final properties of the composites but are seldom considered, for example impurities in the polymer matrix are introduced via fibers addition. These elements can influence the process of crystallization, just like the nanoparticles, although, this depends greatly on their chemical nature. Also it is worthy to mention that the annealing of the composites allows the crystals to grow to their maximum size. Thus, the temperature at which the materials are annealed is also very influential to the final properties of the composite obtained. Therefore from the selection of materials to the final product, care must be taken to achieve the properties desired.

Liu et al. [186] assessed the influence of processing method on the physical properties, especially mechanical properties, of kenaf fiber reinforced biocomposites prepared using soy fiber. The compression molded specimens were observed to have similar Young’s modulus to those from injection molding at room temperature. However, at elevated temperature, the heat deflection temperature (HDT) and notched Izod impact strength were higher compared to those obtained from injection molded specimen. The improvements observed with the compression molded samples were attributed to a surge in Young’s modulus at high temperature and fiber bridging effects.

Generally, biomedical applications desire for fabrication of grafts which are biocompatible and enable cell differentiation and expression with apt mechanical properties, but the ability to achieve such mechanical capacity has been a challenge for decades. As over the years, the focus and efforts have been geared towards biocompatibility and not necessarily mechanical prowess. But the formation of stresses occurring in implant locations due to mechanically inept implant materials have

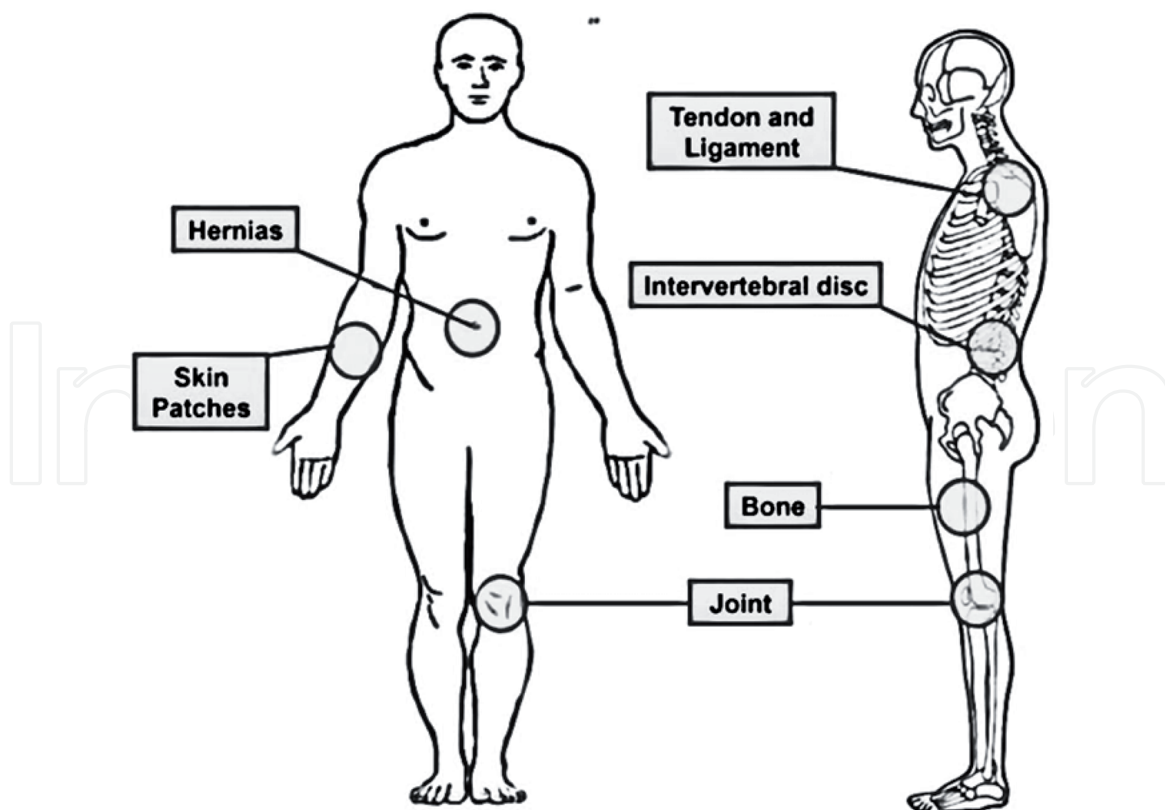


Figure 2.

Illustration of potential application of collagen fibers embedded in a hydrogel bio-composite for medical applications with adjusted mechanical properties that provide support and allow motion and flexibility of the tissue under repair [187].

| No. | Patent title | Patent no. | Year |
|-----|---|----------------|------|
| 1. | Medical balloon with incorporated fibers | W0/2013/148399 | 2013 |
| 2. | Polyester cool-fiber antibacterial pillow | CN102715804 | 2012 |
| 3. | Medical natural porous fiber filler and vacuum sealing drainage device thereof | CN102715983 | 2012 |
| 4. | Manufacturing process of antibacterial bamboo pulp used for high-wet-modulus fiber | CN102677504 | 2012 |
| 5. | Flushable moist wipe or hygiene tissue | CN102665510- | 2012 |
| 6. | Far-infrared fiber fabric functional bellyband by utilizing nano-selenium, germanium and zinc elements traditional Chinese medicine | CN101703317 | 2010 |
| 7. | Medical device for insertion into a joint | US20090234459 | 2008 |
| 8. | Medical device for insertion into a joint | EU1896088 | 2008 |
| 9. | Antiviral fiber and producing method and use thereof | CN1609336 | 2006 |
| 10. | Manufacturing of nano-fibers, from natural fibers, agro based fibers and root fibers | CA2437616 | 2005 |
| 11. | Natural antibacterial material and its use | CN461827 | 2003 |
| 12. | Absorbable protective coatings for wound with the use of sponge and process for producing the same | W0/20021054998 | 2006 |
| 13. | Medical prosthesis, especially for aneurysms, with a connection between its liner and its structure | EPOB18184 | 1998 |

Table 1.

Summary of some patents published employing nature fibers for biomedical applications (adapted from Namvar et al. [188]).

led to numerous implant failures and lead to investigations to improve mechanical properties of biomedical devices for diverse applications (**Figure 2**).

There have been quite a number of patents registered over the years of researchers employing natural fiber for biomedical applications and **Table 1** presents a summary of some of these patents.

6. Conclusion

The natural fiber polymer composites have gained a lot of ground in terms of acceptance and applications. For these interests to increase continuously, the materials must be designed to meet certain requirements for their specific applicability. For structural applications, the most important property that is of concern is the mechanical properties as they help to predict the behavior of the materials under stress. As discussed in this chapter, NFPCs are being applied in the building and construction works, automobiles, aerospace, packaging, electronics and biomedical devices. The mechanical strength and toughness require by these various industries are quite different and can vary widely from one application to another. Even though the mechanical requirement varies, the factors that determine the mechanical properties are the same. These factors include type of fibers used, source of the fibers, surface treatment and modification carried out on the fibers, type of polymer matrix used (pristine and blended), type of fiber-matrix bond formed, and the internal arrangement which depends on the type of curing treatment after processing or annealing. In addition to this list are the fiber length, fiber orientation and distribution, fiber loading or volume fraction, the type of functionality present and the extent of modification. All these factors can be manipulated to give a combination of the right measure of mechanical strength and stiffness or toughness required for the application it is being designed for. The use of compatibilizers and nanoparticles to modify the composites for specific purpose has been widely reported to improve the mechanical properties as well, but proper integrations must be considered. Furthermore, the use of hybrid fibers has also gained wide acceptance because of the improved stiffness and strength owing to the synergy observed in such fiber combination. The possibilities of NFPCs can be best imagined with the right improvement in their mechanical properties and this chapter has highlighted some of these benefits as presented by numerous research investigations across diverse fields.

Acknowledgements

The financial assistance of the University of Zululand and the National Research Foundation, South Africa through the South African Research Chair Initiative (SARChI) is hereby acknowledged. OSJ thanks the National Research Foundation (NRF) for a postdoctoral fellowship and funding under South African Research Chair for Nanotechnology.

IntechOpen

Author details

Owonubi J. Shesan^{1*†}, Agwuncha C. Stephen^{2†}, Anusionwu G. Chioma³,
Revaprasadu Neerish¹ and Sadiku E. Rotimi^{4,5}

1 Department of Chemistry, University of Zululand, Kwadlangezwa,
KwaZulu-Natal, South Africa

2 Department of Chemistry, Ibrahim Badamasi Babangida University, Lapai,
Nigeria

3 Department of Applied Chemistry, University of Johannesburg,
Johannesburg, South Africa

4 Department of Chemical, Metallurgical and Material Engineering,
Tshwane University of Technology, Pretoria, South Africa

5 Institute of Nano Engineering Research (INER), Tshwane University of
Technology, Pretoria, South Africa

*Address all correspondence to: oshesan@gmail.com

† These authors contributed equally.

IntechOpen

© 2019 The Author(s). Licensee IntechOpen. This chapter is distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/3.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited. 

References

- [1] Gao H, Wang J, Chen X, Wang G, Huang X, Li A, et al. Nanoconfinement effects on thermal properties of nanoporous shape-stabilized composite PCMs: A review. *Nano Energy*. 2018;**53**:769-797
- [2] Kargarzadeh H, Mariano M, Huang J, Lin N, Ahmad I, Dufresne A, et al. Recent developments on nanocellulose reinforced polymer nanocomposites: A review. *Polymer*. 2017;**132**:368-393
- [3] Farah S, Anderson DG, Langer R. Physical and mechanical properties of PLA, and their functions in widespread applications—A comprehensive review. *Advanced Drug Delivery Reviews*. 2016;**107**:367-392
- [4] Kahl C, Feldmann M, Sälzer P, Heim H-P. Advanced short fiber composites with hybrid reinforcement and selective fiber-matrix-adhesion based on polypropylene—Characterization of mechanical properties and fiber orientation using high-resolution X-ray tomography. *Composites Part A: Applied Science and Manufacturing*. 2018;**111**:54-61
- [5] Thakur VK, Thakur MK. Processing and characterization of natural cellulose fibers/thermoset polymer composites. *Carbohydrate Polymers*. 2014;**109**:102-117
- [6] Deepa B, Abraham E, Cordeiro N, Mozetic M, Mathew AP, Oksman K, et al. Utilization of various lignocellulosic biomass for the production of nanocellulose: A comparative study. *Cellulose*. 2015;**22**(2):1075-1090
- [7] Lee H-R, Kim K, Mun SC, Chang YK, Choi SQ. A new method to produce cellulose nanofibrils from microalgae and the measurement of their mechanical strength. *Carbohydrate Polymers*. 2018;**180**:276-285
- [8] da Luz FS, Ramos FJHTV, Nascimento LFC, da Silva Figueiredo AB-H, Monteiro SN. Critical length and interfacial strength of PALF and coir fiber incorporated in epoxy resin matrix. *Journal of Materials Research and Technology*. 2018;**7**(4):528-534
- [9] Raju B, Hiremath S, Mahapatra DR. A review of micromechanics based models for effective elastic properties of reinforced polymer matrix composites. *Composite Structures*. 2018;**204**:607-619
- [10] Sen T, Reddy HJ. Various industrial applications of hemp, kinaf, flax and ramie natural fibres. *International Journal of Innovation, Management and Technology*. 2011;**2**(3):192
- [11] Nechyporchuk O, Belgacem MN, Bras J. Production of cellulose nanofibrils: A review of recent advances. *Industrial Crops and Products*. 2016;**93**:2-25
- [12] Mittal G, Rhee KY, Mišković-Stanković V, Hui D. Reinforcements in multi-scale polymer composites: Processing, properties, and applications. *Composites Part B: Engineering*. 2018;**138**:122-139
- [13] Spitalsky Z, Tasis D, Papagelis K, Galiotis C. Carbon nanotube–polymer composites: Chemistry, processing, mechanical and electrical properties. *Progress in Polymer Science*. 2010;**35**(3):357-401
- [14] Naveen MH, Gurudatt NG, Shim Y-B. Applications of conducting polymer composites to electrochemical sensors: A review. *Applied Materials Today*. 2017;**9**:419-433
- [15] Merlini C, Soldi V, Barra GM. Influence of fiber surface treatment and length on physico-chemical properties of short random banana

- fiber-reinforced castor oil polyurethane composites. *Polymer Testing*. 2011;**30**(8):833-840
- [16] Thoppul SD, Finegan J, Gibson RF. Mechanics of mechanically fastened joints in polymer–matrix composite structures—A review. *Composites Science and Technology*. 2009;**69**(3-4):301-329
- [17] Thakur A, Purohit R, Rana R, Bandhu D. Characterization and evaluation of mechanical behavior of epoxy-CNT-bamboo matrix hybrid composites. *Materials Today: Proceedings*. 2018;**5**(2):3971-3980
- [18] Zhao W, Li T, Li Y, O'Brien DJ, Terrones M, Wei B, et al. Mechanical properties of nanocomposites reinforced by carbon nanotube sponges. *Journal of Materiomics*. 2018;**4**:157-164
- [19] Chung D. Processing-structure-property relationships of continuous carbon fiber polymer-matrix composites. *Materials Science and Engineering: R: Reports*. 2017;**113**:1-29
- [20] Supian A, Sapuan S, Zuhri M, Syams Z, Ya HH. Hybrid reinforced thermoset polymer composite in energy absorption tube application: A review. *Defence Technology*. 2018;**14**:291-305
- [21] Väisänen T, Das O, Tomppo L. A review on new bio-based constituents for natural fiber-polymer composites. *Journal of Cleaner Production*. 2017;**149**:582-596
- [22] Ferreira F, Dufresne A, Pinheiro I, Souza D, Gouveia R, Mei L, et al. How do cellulose nanocrystals affect the overall properties of biodegradable polymer nanocomposites: A comprehensive review. *European Polymer Journal*. 2018;**108**:274-285
- [23] Zhang X, Xu Y, Zhang X, Wu H, Shen J, Chen R, et al. Progress on the layer-by-layer assembly of multilayered polymer composites: Strategy, structural control and applications. *Progress in Polymer Science*. 2018;**89**:76-107
- [24] Del Nobile MA, Conte A, Buonocore GG, Incoronato A, Massaro A, Panza O. Active packaging by extrusion processing of recyclable and biodegradable polymers. *Journal of Food Engineering*. 2009;**93**(1):1-6
- [25] Seabra AB, Bernardes JS, Fávoro WJ, Paula AJ, Durán N. Cellulose nanocrystals as carriers in medicine and their toxicities: A review. *Carbohydrate Polymers*. 2018;**181**:514-527
- [26] Feng Y-H, Cheng T-Y, Yang W-G, Ma P-T, He H-Z, Yin X-C, et al. Characteristics and environmentally friendly extraction of cellulose nanofibrils from sugarcane bagasse. *Industrial Crops and Products*. 2018;**111**:285-291
- [27] Arrieta MP, Fortunati E, Dominici F, López J, Kenny JM. Bionanocomposite films based on plasticized PLA–PHB/cellulose nanocrystal blends. *Carbohydrate Polymers*. 2015;**121**:265-275
- [28] Bourmaud A, Beaugrand J, Shah DU, Placet V, Baley C. Towards the design of high-performance plant fibre composites: How can we best define the diversity and specificities of plant cell walls? *Progress in Materials Science*. 2018;**97**:347-408
- [29] Chávez-Guerrero L, Sepúlveda-Guzmán S, Silva-Mendoza J, Aguilar-Flores C, Pérez-Camacho O. Eco-friendly isolation of cellulose nanoplatelets through oxidation under mild conditions. *Carbohydrate Polymers*. 2018;**181**:642-649
- [30] Ayre D. Technology advancing polymers and polymer composites towards sustainability: A review. *Current Opinion in Green and Sustainable Chemistry*. 2018;**13**:108-112

- [31] Brand J, Pecastaings G, Sèbe G. A versatile method for the surface tailoring of cellulose nanocrystal building blocks by acylation with functional vinyl esters. *Carbohydrate Polymers*. 2017;**169**:189-197
- [32] Campo EA. *Selection of Polymeric Materials: How to Select Design Properties from Different Standards*. Norwich, NY: William Andrew; 2008
- [33] Zweben C. Tensile strength of hybrid composites. *Journal of Materials Science*. 1977;**12**(7):1325-1337
- [34] Fernandes F, Tavares J, de Sousa RA, Pereira A, Esteves J. Manufacturing and testing composites based on natural materials. *Procedia Manufacturing*. 2017;**13**:227-234
- [35] Ptak M, Kaczyński P, Wilhelm J, Margarido J, Marques P, Pinto S, et al. Graphene-enriched agglomerated cork material and its behaviour under quasi-static and dynamic loading. *Materials*. 2019;**12**(1):151
- [36] Swolfs Y, Gorbatiikh L, Verpoest I. Fibre hybridisation in polymer composites: A review. *Composites Part A: Applied Science and Manufacturing*. 2014;**67**:181-200
- [37] García A, Gandini A, Labidi J, Belgacem N, Bras J. Industrial and crop wastes: A new source for nanocellulose biorefinery. *Industrial Crops and Products*. 2016;**93**:26-38
- [38] Chen J, Yan L, Song W, Xu D. Interfacial characteristics of carbon nanotube-polymer composites: A review. *Composites Part A: Applied Science and Manufacturing*. 2018;**114**:149-169
- [39] Benkaddour A, Jradi K, Robert S, Daneault C. Study of the effect of grafting method on surface polarity of tempo-oxidized nanocellulose using polycaprolactone as the modifying compound: Esterification versus click-chemistry. *Nanomaterials*. 2013;**3**(4):638-654
- [40] Osman B, Özer ET, Beşirli N, Güçer Ş. Development and application of a solid phase extraction method for the determination of phthalates in artificial saliva using new synthesised microspheres. *Polymer Testing*. 2013;**32**(4):810-818
- [41] Boufi S, Belgacem MN. Modified cellulose fibres for adsorption of dissolved organic solutes. *Cellulose*. 2006;**13**(1):81-94
- [42] Bas O, De-Juan-Pardo EM, Catelas I, Hutmacher DW. The quest for mechanically and biologically functional soft biomaterials via soft network composites. *Advanced Drug Delivery Reviews*. 2018;**132**:214-234
- [43] Benyahia H, Tarfaoui M, El Moumen A, Ouinas D, Hassoon O. Mechanical properties of offshoring polymer composite pipes at various temperatures. *Composites Part B: Engineering*. 2018;**152**:231-240
- [44] De Greef N, Gorbatiikh L, Godara A, Mezzo L, Lomov SV, Verpoest I. The effect of carbon nanotubes on the damage development in carbon fiber/epoxy composites. *Carbon*. 2011;**49**(14):4650-4664
- [45] De Greef N, Gorbatiikh L, Lomov SV, Verpoest I. Damage development in woven carbon fiber/epoxy composites modified with carbon nanotubes under tension in the bias direction. *Composites Part A: Applied Science and Manufacturing*. 2011;**42**(11):1635-1644
- [46] Qian H, Greenhalgh ES, Shaffer MS, Bismarck A. Carbon nanotube-based hierarchical composites: A review. *Journal of Materials Chemistry*. 2010;**20**(23):4751-4762
- [47] Dweib M, Hu B, Shenton H III, Wool R. Bio-based composite roof

- structure: Manufacturing and processing issues. *Composite Structures*. 2006;**74**(4):379-388
- [48] Bektas I, Guler C, Kalaycioglu H, Mengeloglu F, Nacar M. The manufacture of particleboards using sunflower stalks (*Helianthus annuus* L.) and poplar wood (*Populus alba* L.). *Journal of Composite Materials*. 2005;**39**(5):467-473
- [49] John MJ, Thomas S. Biofibres and biocomposites. *Carbohydrate Polymers*. 2008;**71**(3):343-364
- [50] Li Q, Matuana LM. Surface of cellulosic materials modified with functionalized polyethylene coupling agents. *Journal of Applied Polymer Science*. 2003;**88**(2):278-286
- [51] Owonubi SJ, Linganiso LZ, Motaung TE, Songca SP. Wood and its byproducts: Cascading utilisation for biomass (re)generation. In: Linganiso LZ, Motaung TE, editors. "Waste-to-Profit" (W-t-P): Circular Economy in the Construction Industry for a Sustainable Future. Unites States of America: Nova Publishers; 2018
- [52] Coutts RS. A review of Australian research into natural fibre cement composites. *Cement and Concrete Composites*. 2005;**27**(5):518-526
- [53] Peijs T. Composites for recyclability. *Materials Today*. 2003;**4**(6):30-35
- [54] Dunne R, Desai D, Sadiku R, Jayaramudu J. A review of natural fibres, their sustainability and automotive applications. *Journal of Reinforced Plastics and Composites*. 2016;**35**(13):1041-1050
- [55] Bos HL. The potential of flax fibres as reinforcement for composite materials. Eindhoven: Technische Universiteit Eindhoven; 2004
- [56] Brief L. Opportunities in Natural Fiber Composites. Irving (TX): Lucintel LLC; 2011
- [57] La Mantia F, Morreale M. Green composites: A brief review. *Composites Part A: Applied Science and Manufacturing*. 2011;**42**(6):579-588
- [58] Marsh G. Next step for automotive materials. *Materials Today*. 2003;**6**(4):36-43
- [59] La Mantia F, Morreale M. Mechanical properties of recycled polyethylene ecocomposites filled with natural organic fillers. *Polymer Engineering & Science*. 2006;**46**(9):1131-1139
- [60] Netravali AN, Chabba S. Composites get greener. *Materials Today*. 2003;**4**(6):22-29
- [61] Kiruthika A. A review on physico-mechanical properties of bast fibre reinforced polymer composites. *Journal of Building Engineering*. 2017;**9**:91-99
- [62] Plackett D, Andersen TL, Pedersen WB, Nielsen L. Biodegradable composites based on L-poly lactide and jute fibres. *Composites Science and Technology*. 2003;**63**(9):1287-1296
- [63] Li Y, Mai Y-W, Ye L. Sisal fibre and its composites: A review of recent developments. *Composites Science and Technology*. 2000;**60**(11):2037-2055
- [64] Senthilkumar K, Saba N, Rajini N, Chandrasekar M, Jawaid M, Siengchin S, et al. Mechanical properties evaluation of sisal fibre reinforced polymer composites: A review. *Construction and Building Materials*. 2018;**174**:713-729
- [65] Pickering KL, Efendy MA, Le TM. A review of recent developments in natural fibre composites and their mechanical performance. *Composites Part A: Applied Science and Manufacturing*. 2016;**83**:98-112
- [66] Pickering KL, Beckermann G, Alam S, Foreman NJ. Optimising

- industrial hemp fibre for composites. *Composites Part A: Applied Science and Manufacturing*. 2007;**38**(2):461-468
- [67] Saba N, Paridah M, Jawaid M. Mechanical properties of kenaf fibre reinforced polymer composite: A review. *Construction and Building Materials*. 2015;**76**:87-96
- [68] Kabir M, Wang H, Lau K, Cardona F. Chemical treatments on plant-based natural fibre reinforced polymer composites: An overview. *Composites Part B: Engineering*. 2012;**43**(7):2883-2892
- [69] Kabir M, Wang H, Aravinthan T, Cardona F, Lau K-T. Effects of natural fibre surface on composite properties: A review. In: *Proceedings of the 1st International Postgraduate Conference on Engineering, Designing and Developing the Built Environment for Sustainable Wellbeing (eddBE2011)*. Australia: Queensland University of Technology; 2011
- [70] Phillips DM, Pierce MR, Baur JW. Mechanical and thermal analysis of microvascular networks in structural composite panels. *Composites Part A: Applied Science and Manufacturing*. 2011;**42**(11):1609-1619
- [71] Megiatto JD Jr, Silva CG, Ramires EC, Frollini E. Thermoset matrix reinforced with sisal fibers: Effect of the cure cycle on the properties of the biobased composite. *Polymer Testing*. 2009;**28**(8):793-800
- [72] Fakirov S, Bhattacharyya D. *Handbook of Engineering Biopolymers: Homopolymers, Blends, and Composites*. Germany: Carl Hanser Verlag GmbH Co KG; 2007
- [73] Joseph P. *Studies on Short Sisal Fibre Reinforced Isotactic Polypropylene Composites*. 2001. Available from: <http://shodhganga.inflibnet.ac.in:8080/jspui/handle/10603/6193?mode=full>
- [74] Ku H, Wang H, Pattarachaiyakooop N, Trada M. A review on the tensile properties of natural fiber reinforced polymer composites. *Composites Part B: Engineering*. 2011;**42**(4):856-873
- [75] Ahmad I, Baharum A, Abdullah I. Effect of extrusion rate and fiber loading on mechanical properties of Twaron fiber-thermoplastic natural rubber (TPNR) composites. *Journal of Reinforced Plastics and Composites*. 2006;**25**(9):957-965
- [76] Kargarzadeh H, Huang J, Lin N, Ahmad I, Mariano M, Dufresne A, et al. Recent developments in nanocellulose-based biodegradable polymers, thermoplastic polymers, and porous nanocomposites. *Progress in Polymer Science*. 2018;**87**:197-227
- [77] Ji X, Xu Y, Zhang W, Cui L, Liu J. Review of functionalization, structure and properties of graphene/polymer composite fibers. *Composites Part A: Applied Science and Manufacturing*. 2016;**87**:29-45
- [78] Inácio AL, Nonato RC, Bonse BC. Mechanical and thermal behavior of aged composites of recycled PP/EPDM/talc reinforced with bamboo fiber. *Polymer Testing*. 2018;**72**:357-363
- [79] Lila MK, Singhal A, Banwait SS, Singh I. A recyclability study of bagasse fiber reinforced polypropylene composites. *Polymer Degradation and Stability*. 2018;**152**:272-279
- [80] Wang B, Panigrahi S, Tabil L, Crerar W. Pre-treatment of flax fibers for use in rotationally molded biocomposites. *Journal of Reinforced Plastics and Composites*. 2007;**26**(5):447-463
- [81] Alamri H, Low IM. Mechanical properties and water absorption behaviour of recycled cellulose fibre reinforced epoxy composites. *Polymer Testing*. 2012;**31**(5):620-628

- [82] Dhal JP, Mishra SC. Processing and properties of natural fiber-reinforced polymer composite. *Journal of Materials*. 2012;**2013**:6. Article ID: 297213
- [83] Vroman I, Tighzert L. Biodegradable polymers. *Materials*. 2009;**2**(2):307-344
- [84] Mallick PK. *Fiber-reinforced Composites: Materials, Manufacturing, and Design*. Boca Raton, Florida, United States: CRC Press; 2007
- [85] Angelov I, Wiedmer S, Evstatiev M, Friedrich K, Mennig G. Pultrusion of a flax/polypropylene yarn. *Composites Part A: Applied Science and Manufacturing*. 2007;**38**(5):1431-1438
- [86] Rodríguez E, Petrucci R, Puglia D, Kenny JM, Vazquez A. Characterization of composites based on natural and glass fibers obtained by vacuum infusion. *Journal of Composite Materials*. 2005;**39**(3):265-282
- [87] Tungjitpornkull S, Sombatsompop N. Processing technique and fiber orientation angle affecting the mechanical properties of E-glass fiber reinforced wood/PVC composites. *Journal of Materials Processing Technology*. 2009;**209**(6):3079-3088
- [88] Siaotong B, Tabil L, Panigrahi S, Crerar W. Determination of optimum extrusion parameters in compounding flax fiber-reinforced polyethylene composites. In 2006 ASAE annual meeting. Michigan: American Society of Agricultural and Biological Engineers; 2006
- [89] Li X, Panigrahi S, Tabil L. A study on flax fiber-reinforced polyethylene biocomposites. *Applied Engineering in Agriculture*. 2009;**25**(4):525-531
- [90] Sreekumar P, Joseph K, Unnikrishnan G, Thomas S. A comparative study on mechanical properties of sisal-leaf fibre-reinforced polyester composites prepared by resin transfer and compression moulding techniques. *Composites Science and Technology*. 2007;**67**(3-4):453-461
- [91] Hussain B, Safiulla M. Comparative study of cooling systems for vacuum forming tool. *Materials Today: Proceedings*. 2018;**5**(1):30-36
- [92] Hammami A, Gebart B. Analysis of the vacuum infusion molding process. *Polymer Composites*. 2000;**21**(1):28-40
- [93] Gu Y, Tan X, Yang Z, Zhang Z. Hot compaction and mechanical properties of ramie fabric/epoxy composite fabricated using vacuum assisted resin infusion molding. *Materials & Design (1980-2015)*. 2014;**56**:852-861
- [94] Vaxman A, Narkis M, Siegmann A, Kenig S. Void formation in short-fiber thermoplastic composites. *Polymer Composites*. 1989;**10**(6):449-453
- [95] Mwaikambo LY, Ansell MP. Chemical modification of hemp, sisal, jute, and kapok fibers by alkalization. *Journal of Applied Polymer Science*. 2002;**84**(12):2222-2234
- [96] Xie W, Zhu W, Shen Z. Synthesis, isothermal crystallization and micellization of mPEG-PCL diblock copolymers catalyzed by yttrium complex. *Polymer*. 2007;**48**(23):6791-6798
- [97] Kalia S, Thakur K, Celli A, Kiechel MA, Schauer CL. Surface modification of plant fibers using environment friendly methods for their application in polymer composites, textile industry and antimicrobial activities: A review. *Journal of Environmental Chemical Engineering*. 2013;**1**(3):97-112
- [98] Jain D, Vats S, Bera TK. Micromechanical interactions and their relation to stress field

for different classes of reinforced polymer composites. *Materials Today: Proceedings*. 2018;5(9):19944-19953

[99] Ibrahim ID, Jamiru T, Sadiku RE, Kupolati WK, Agwuncha SC. Dependency of the mechanical properties of sisal fiber reinforced recycled polypropylene composites on fiber surface treatment, fiber content and nanoclay. *Journal of Polymers and the Environment*. 2017;25(2):427-434

[100] Ibrahim ID, Jamiru T, Sadiku ER, Kupolati WK, Agwuncha SC. Impact of surface modification and nanoparticle on sisal fiber reinforced polypropylene nanocomposites. *Journal of Nanotechnology*. 2016;9. Article ID: 4235975

[101] Khoathane MC, Sadiku ER, Agwuncha CS. Surface Modification of natural fiber composites and their potential applications. In: *Surface Modification of Biopolymers*. Hoboken, NJ, USA: John Wiley & Sons, Inc.; 2015. pp. 370-400

[102] Shekar HS, Ramachandra M. Green composites: A review. *Materials Today: Proceedings*. 2018;5(1):2518-2526

[103] Li Y, Hu C, Yu Y. Interfacial studies of sisal fiber reinforced high density polyethylene (HDPE) composites. *Composites Part A: Applied Science and Manufacturing*. 2008;39(4):570-578

[104] Sanjay M, Madhu P, Jawaid M, Sentharamaiah P, Senthil S, Pradeep S. Characterization and properties of natural fiber polymer composites: A comprehensive review. *Journal of Cleaner Production*. 2018;172:566-581

[105] Alavi-Soltani S, Sabzevari S, Koushyar H, Minaie B. Thermal, rheological, and mechanical properties of a polymer composite cured at different isothermal cure temperatures. *Journal of Composite Materials*. 2012;46(5):575-587

[106] Liu X, Dai G. Surface modification and micromechanical properties of jute fiber mat reinforced polypropylene composites. *Express Polymer Letters*. 2007;1(5):299-307

[107] Tao Y, Yan L, Jie R. Preparation and properties of short natural fiber reinforced poly (lactic acid) composites. *Transactions of Nonferrous Metals Society of China*. 2009;19:s651-s655

[108] Yuan X, Zhu B, Cai X, Qiao K, Zhao S, Yu J. Influence of different surface treatments on the interfacial adhesion of graphene oxide/carbon fiber/epoxy composites. *Applied Surface Science*. 2018;458:996-1005

[109] Doan T-T-L, Gao S-L, Mäder E. Jute/polypropylene composites I. Effect of matrix modification. *Composites Science and Technology*. 2006;66(7-8):952-963

[110] Mondal S. Preparation, properties and applications of nanocellulosic materials. *Carbohydrate Polymers*. 2017;163:301-316

[111] Fortunati E, Luzi F, Yang W, Kenny JM, Torre L, Puglia D. *Bio-Based Nanocomposites in Food Packaging, in Nanomaterials for Food Packaging*. United Kingdom: Elsevier; 2018. pp. 71-110

[112] Fortunati E, Peltzer M, Armentano I, Jiménez A, Kenny JM. Combined effects of cellulose nanocrystals and silver nanoparticles on the barrier and migration properties of PLA nano-biocomposites. *Journal of Food Engineering*. 2013;118(1):117-124

[113] Alila S, Besbes I, Vilar MR, Mutjé P, Boufi S. Non-woody plants as raw materials for production of microfibrillated cellulose (MFC): A comparative study. *Industrial Crops and Products*. 2013;41:250-259

[114] El Achaby M, Kassab Z, Barakat A, Aboulkas A. Alfa fibers as viable

sustainable source for cellulose nanocrystals extraction: Application for improving the tensile properties of biopolymer nanocomposite films. *Industrial Crops and Products*. 2018;**112**:499-510

[115] Jonas R, Farah LF. Production and application of microbial cellulose. *Polymer Degradation and Stability*. 1998;**59**(1-3):101-106

[116] Brown AJ. XLIII. On an acetic ferment which forms cellulose. *Journal of the Chemical Society, Transactions*. 1886;**49**:432-439

[117] Delmer DP, Amor Y. Cellulose biosynthesis. *The Plant Cell*. 1995;**7**(7):987

[118] Shoda M, Sugano Y. Recent advances in bacterial cellulose production. *Biotechnology and Bioprocess Engineering*. 2005;**10**(1):1

[119] Panesar P, Chavan Y, Bera M, Chand O, Kumar H. Evaluation of *Acetobacter* strain for the production of microbial cellulose. *Asian Journal of Chemistry*. 2009;**21**(10):99-102

[120] Embuscado ME, Marks JS, BeMiller JN. Bacterial cellulose. I. Factors affecting the production of cellulose by *Acetobacter xylinum*. *Food Hydrocolloids*. 1994;**8**(5):407-418

[121] Steinbüchel, A. and S.K. Rhee, Polysaccharides and Polyamides in the Food Industry: Properties, Production, and Patents. Weinheim, Germany: Wiley-VCH Verlag GmbH & CO. KGaA; 2005

[122] Kale KH, Desai A. Atmospheric pressure plasma treatment of textiles using non-polymerising gases. *Indian Journal of Fibre & Textile Research*. 2011;**36**(3):289-299

[123] Kim B, Nguyen M, Hwang B, Lee S. Effect of plasma treatment on the mechanical properties of natural fiber/

PP composites. *WIT Transactions on the Built Environment*. 2008;**97**:159-166

[124] Wolter M, Bornholdt S, Häckel M, Kersten H. Atmospheric pressure plasma jet for treatment of polymers. *Journal of Achievements in Materials and Manufacturing Engineering*. 2009;**37**(2):730-734

[125] Liu W, Mohanty AK, Askeland P, Drzal LT, Misra M. Influence of fiber surface treatment on properties of Indian grass fiber reinforced soy protein based biocomposites. *Polymer*. 2004;**45**(22):7589-7596

[126] Edeerozey AM, Akil HM, Azhar A, Ariffin MZ. Chemical modification of kenaf fibers. *Materials Letters*. 2007;**61**(10):2023-2025

[127] Stelescu DM, Airinei A, Homocianu M, Fifere N, Timpu D, Aflori M. Structural characteristics of some high density polyethylene/EPDM blends. *Polymer Testing*. 2013;**32**(2):187-196

[128] Farsi M. Thermoplastic matrix reinforced with natural fibers: A study on interfacial behavior. In: *Some Critical Issues for Injection Molding*. United Kingdom: INTECH; 2012

[129] Robeson LM. Polymer blends. A Comprehensive Review. In: *Polymer Blends*. München: Carl Hanser Verlag GmbH & Co. KG; 2007. pp. I-XII. Available from: <https://www.hanser-elibrary.com/doi/pdf/10.3139/9783446436503.fm>. eBook ISBN: 978-3-446-43650-3. Print ISBN: 978-3-446-22569-5 2007

[130] Yatigala NS, Bajwa DS, Bajwa SG. Compatibilization improves physico-mechanical properties of biodegradable biobased polymer composites. *Composites Part A: Applied Science and Manufacturing*. 2018;**107**:315-325

[131] Fox DM, Lee J, Citro CJ, Novy M. Flame retarded poly (lactic acid)

- using POSS-modified cellulose. 1. Thermal and combustion properties of intumescent composites. *Polymer Degradation and Stability*. 2013;**98**(2):590-596
- [132] Lin JH, Lu CT, He CH, Huang CC, Lou CW. Preparation and evaluation of artificial bone complex material: Chitosan/poly(lactic acid) complex braids. *Journal of Composite Materials*. 2011;**45**(19):1945-1951
- [133] Kemala T, Budianto E, Soegiyono B. Preparation and characterization of microspheres based on blend of poly(lactic acid) and poly(ϵ -caprolactone) with poly(vinyl alcohol) as emulsifier. *Arabian Journal of Chemistry*. 2012;**5**(1):103-108
- [134] Choi NS, Kim CH, Cho KY, Park JK. Morphology and hydrolysis of PCL/PLLA blends compatibilized with P(LLA-co- ϵ CL) or P(LLA-b- ϵ CL). *Journal of Applied Polymer Science*. 2002;**86**(8):1892-1898
- [135] Tuba F, Oláh L, Nagy P. Characterization of reactively compatibilized poly(d, l-lactide)/poly(ϵ -caprolactone) biodegradable blends by essential work of fracture method. *Engineering Fracture Mechanics*. 2011;**78**(17):3123-3133
- [136] Younas M, Noreen A, Sharif A, Majeed A, Hssan A, Tabasum S, et al. A review on versatile applications of blends and composites of CNC with natural and synthetic polymers with mathematical modeling. *International Journal of Biological Macromolecules*. 2018;**124**:591-626
- [137] Ho M-P, Wang H, Lau K-T, Lee J-H, Hui D. Interfacial bonding and degumming effects on silk fibre/polymer biocomposites. *Composites Part B: Engineering*. 2012;**43**(7):2801-2812
- [138] Das D, Mukhopadhyay S, Kaur H. Optimization of fiber composition in natural fiber-reinforced composites using a simplex lattice design. *Journal of Composite Materials*. 2012;**46**(26):3311-3319
- [139] Kaleemullah M, Khan SU, Kim J-K. Effect of surfactant treatment on thermal stability and mechanical properties of CNT/polybenzoxazine nanocomposites. *Composites Science and Technology*. 2012;**72**(16):1968-1976
- [140] Fang K, Wang B, Sheng K, Sun XS. Properties and morphology of poly(lactic acid)/soy protein isolate blends. *Journal of Applied Polymer Science*. 2009;**114**(2):754-759
- [141] Graupner N. Improvement of the mechanical properties of biodegradable hemp fiber reinforced poly(lactic acid) (PLA) composites by the admixture of man-made cellulose fibers. *Journal of Composite Materials*. 2009;**43**(6):689-702
- [142] Wambua P, Ivens J, Verpoest I. Natural fibres: Can they replace glass in fibre reinforced plastics? *Composites Science and Technology*. 2003;**63**(9):1259-1264
- [143] Linares EM, Rippel MM, Galembeck F. Clay platelet partition within polymer blend nanocomposite films by EFTEM. *ACS Applied Materials & Interfaces*. 2010;**2**(12):3648-3653
- [144] Müller-Buschbaum P, Gutmann JS, Stamm M. Influence of blend composition on phase separation and dewetting of thin polymer blend films. *Macromolecules*. 2000;**33**(13):4886-4895
- [145] White RP, Lipson JE, Higgins JS. New correlations in polymer blend miscibility. *Macromolecules*. 2012;**45**(2):1076-1084
- [146] Utracki LA. Compatibilization of polymer blends. *The Canadian*

Journal of Chemical Engineering.
2002;**80**(6):1008-1016

[147] Yavas BH, Tanriver N, Benli B, Kizilcan N. In situ polymerization of sepiolite modified polysulfone. *Procedia-Social and Behavioral Sciences*. 2015;**195**:2206-2209

[148] Cao E, Duan W, Wang F, Wang A, Zheng Y. Natural cellulose fiber derived hollow-tubular-oriented polydopamine: In-situ formation of Ag nanoparticles for reduction of 4-nitrophenol. *Carbohydrate Polymers*. 2017;**158**:44-50

[149] Rask M, Madsen B, Sørensen BF, Fife JL, Martyniuk K, Lauridsen EM. In situ observations of microscale damage evolution in unidirectional natural fibre composites. *Composites Part A: Applied Science and Manufacturing*. 2012;**43**(10):1639-1649

[150] Zapata P, Quijada R, Retuer J, Moncada E. Preparation of nanocomposites by in situ polymerization. *Journal of the Chilean Chemical Society*. 2008;**53**(1):1359-1360

[151] Remiro P, Nazabal J. Phase behavior of ternary PBT-PC/phenoxy blends. *Journal of Applied Polymer Science*. 1991;**42**(5):1475-1483

[152] Robeson LM, Claus Jr WD, Batleman HL. Poly (aryl ether) containing blends. Google Patents. 1983

[153] Agwuncha SC, Ray SS, Jayaramudu J, Khoathane C, Sadiku R. Influence of boehmite nanoparticle loading on the mechanical, thermal, and rheological properties of biodegradable polylactide/poly (ϵ -caprolactone) blends. *Macromolecular Materials and Engineering*. 2015;**300**(1):31-47

[154] Ibrahim ID, Jamiru T, Sadiku ER, Kupolati WK, Agwuncha SC, Ekundayo G. Mechanical properties of sisal fibre-reinforced polymer

composites: A review. *Composite Interfaces*. 2016;**23**(1):15-36

[155] Owonubi SJ, Mukwevho E, Revaprasadu N. Nanoparticle-based delivery of plant metabolites. In: Goyal MR et al., editors. *The Therapeutic Properties of Medicinal Plants: Health-Rejuvenating Bioactive Compounds of Native Flora*. New York: CRC Press; 2019

[156] Bounor-Legaré V, Cassagnau P. In situ synthesis of organic-inorganic hybrids or nanocomposites from sol-gel chemistry in molten polymers. *Progress in Polymer Science*. 2014;**39**(8):1473-1497

[157] Eichner E, Heinrich S, Schneider G. Influence of particle shape and size on mechanical properties in copper-polymer composites. *Powder Technology*. 2018;**339**:39-45

[158] Huang X, Netravali AN. Characterization of nano-clay reinforced phytigel-modified soy protein concentrate resin. *Biomacromolecules*. 2006;**7**(10):2783-2789

[159] Vargas AF, Orozco VH, Rault F, Giraud S, Devaux E, López BL. Influence of fiber-like nanofillers on the rheological, mechanical, thermal and fire properties of polypropylene: An application to multifilament yarn. *Composites Part A: Applied Science and Manufacturing*. 2010;**41**(12):1797-1806

[160] Lee SH, Youn JR. Properties of polypropylene/layered-silicate nanocomposites and melt-spun fibers. *Journal of Applied Polymer Science*. 2008;**109**(2):1221-1231

[161] Rault F, Campagne C, Rochery M, Giraud S, Devaux E. Polypropylene multifilament yarn filled with clay and/or graphite: Study of a potential synergy. *Journal of Polymer Science Part B: Polymer Physics*. 2010;**48**(11):1185-1195

- [162] Joshi SV, Drzal L, Mohanty A, Arora S. Are natural fiber composites environmentally superior to glass fiber reinforced composites? *Composites Part A: Applied Science and Manufacturing*. 2004;**35**(3):371-376
- [163] Vlasveld D, Groenewold J, Bersee H, Picken S. Moisture absorption in polyamide-6 silicate nanocomposites and its influence on the mechanical properties. *Polymer*. 2005;**46**(26):12567-12576
- [164] Özdilek C, Kazimierczak K, van der Beek D, Picken SJ. Preparation and properties of polyamide-6-boehmite nanocomposites. *Polymer*. 2004;**45**(15):5207-5214
- [165] Kim D, Krishnamoorti R. Interfacial activity of poly [oligo (ethylene oxide)–monomethyl ether methacrylate]-grafted silica nanoparticles. *Industrial & Engineering Chemistry Research*. 2015;**54**(14):3648-3656
- [166] Ashori A. Hybrid composites from waste materials. *Journal of Polymers and the Environment*. 2010;**18**(1):65-70
- [167] Saba N, Jawaid M, Alothman OY, Paridah M. A review on dynamic mechanical properties of natural fibre reinforced polymer composites. *Construction and Building Materials*. 2016;**106**:149-159
- [168] Thwe MM, Liao K. Effects of environmental aging on the mechanical properties of bamboo–glass fiber reinforced polymer matrix hybrid composites. *Composites Part A: Applied Science and Manufacturing*. 2002;**33**(1):43-52
- [169] Jawaid M, Khalil HA. Cellulosic/synthetic fibre reinforced polymer hybrid composites: A review. *Carbohydrate Polymers*. 2011;**86**(1):1-18
- [170] Jacob M, Francis B, Thomas S, Varughese K. Dynamical mechanical analysis of sisal/oil palm hybrid fiber-reinforced natural rubber composites. *Polymer Composites*. 2006;**27**(6):671-680
- [171] Birnin-Yauri AU, Ibrahim NA, Zainuddin N, Abdan K, Then YY, Chieng BW. Enhancement of the mechanical properties and dimensional stability of oil palm empty fruit bunch-kenaf core and oil palm mesocarp-kenaf core hybrid fiber-reinforced poly (lactic acid) biocomposites by borax decahydrate modification of fibers. *BioResources*. 2016;**11**(2):4865-4884
- [172] Fu S-Y, Lauke B, Mäder E, Yue C-Y, Hu X. Tensile properties of short-glass-fiber-and short-carbon-fiber-reinforced polypropylene composites. *Composites Part A: Applied Science and Manufacturing*. 2000;**31**(10):1117-1125
- [173] Jacob M, Thomas S, Varughese KT. properties of sisal/oil palm hybrid fiber reinforced natural rubber composites. *Composites Science and Technology*. 2004;**64**(7-8):955-965
- [174] Zhu Z, Ye C, Fu W, Wu H. Improvement in mechanical and thermal properties of polylactic acid biocomposites due to the addition of hybrid sisal fibers and diatomite particles. *International Journal of Polymer Analysis and Characterization*. 2016;**21**(5):365-377
- [175] Hamid MRY, Ab Ghani MH, Ahmad S. Effect of antioxidants and fire retardants as mineral fillers on the physical and mechanical properties of high loading hybrid biocomposites reinforced with rice husks and sawdust. *Industrial Crops and Products*. 2012;**40**:96-102
- [176] Ma P-C, Liu M-Y, Zhang H, Wang S-Q, Wang R, Wang K, et al. Enhanced electrical conductivity of nanocomposites containing hybrid fillers of carbon nanotubes and carbon

black. ACS Applied Materials & Interfaces. 2009;1(5):1090-1096

[177] Bao L, Zang J, Li X. Flexible Zn₂SnO₄/MnO₂ core/shell nanocable– carbon microfiber hybrid composites for high-performance supercapacitor electrodes. Nano Letters. 2011;11(3):1215-1220

[178] Hayase G, Kanamori K, Abe K, Yano H, Maeno A, Kaji H, et al. Polymethylsilsesquioxane–cellulose nanofiber biocomposite aerogels with high thermal insulation, bendability, and superhydrophobicity. ACS Applied Materials & Interfaces. 2014;6(12):9466-9471

[179] Jacob M, Varughese K, Thomas S. Dielectric characteristics of sisal–oil palm hybrid biofibre reinforced natural rubber biocomposites. Journal of Materials Science. 2006;41(17):5538-5547

[180] Ashik K, Sharma RS. A review on mechanical properties of natural fiber reinforced hybrid polymer composites. Journal of Minerals and Materials Characterization and Engineering. 2015;3(05):420

[181] Nunna S, Chandra PR, Shrivastava S, Jalan A. A review on mechanical behavior of natural fiber based hybrid composites. Journal of Reinforced Plastics and Composites. 2012;31(11):759-769

[182] Mishra S, Mohanty A, Drzal L, Misra M, Parija S, Nayak S, et al. Studies on mechanical performance of biofibre/glass reinforced polyester hybrid composites. Composites Science and Technology. 2003;63(10):1377-1385

[183] Shahzad A. Impact and fatigue properties of hemp–glass fiber hybrid biocomposites. Journal of Reinforced Plastics and Composites. 2011;30(16):1389-1398

[184] Velmurugan R, Manikandan V. Mechanical properties of palmyra/

glass fiber hybrid composites. Composites Part A: Applied Science and Manufacturing. 2007;38(10):2216-2226

[185] Ahmed KS, Vijayarangan S. Tensile, flexural and interlaminar shear properties of woven jute and jute-glass fabric reinforced polyester composites. Journal of Materials Processing Technology. 2008;207(1-3):330-335

[186] Liu W, Drzal LT, Mohanty AK, Misra M. Influence of processing methods and fiber length on physical properties of kenaf fiber reinforced soy based biocomposites. Composites Part B: Engineering. 2007;38(3):352-359

[187] Benayahu D, Sharabi M, Pomeraniec L, Awad L, Haj-Ali R, Benayahu Y. Unique collagen fibers for biomedical applications. Marine Drugs. 2018;16(4):102

[188] Namvar F, Jawaid M, Tanir PM, Mohamad R, Azizi S, Khodavandi A, et al. Potential use of plant fibres and their composites for biomedical applications. BioResources. 2014;9(3):5688-5706