

# We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

4,800

Open access books available

122,000

International authors and editors

135M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities



WEB OF SCIENCE™

Selection of our books indexed in the Book Citation Index  
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?  
Contact [book.department@intechopen.com](mailto:book.department@intechopen.com)

Numbers displayed above are based on latest data collected.  
For more information visit [www.intechopen.com](http://www.intechopen.com)



# Hexachlorinated Boron(III) Subphthalocyanine as Acceptor for Organic Photovoltaics: A Brief Overview

*Georgy L. Pakhomov, Vlad V. Travkin and Pavel A. Stuzhin*

## Abstract

A boron(III) complex of peripherally hexachlorinated subphthalocyanine, Cl<sub>6</sub>SubPc is a very promising small-molecule acceptor for application in organic photovoltaics. In this chapter the recent experimental results in the field are compared, and a critical review is given of the published works on the solar cells with the planar or bulk heterojunction architectures. The thin film properties of Cl<sub>6</sub>SubPc are also considered. The approaches to the further modification of the molecular structure of boron(III) subphthalocyanine-type compounds for the enhancement of their photoelectrical properties are discussed.


**Keywords:** boron(III) subphthalocyanines, acceptors, organic electronics

## 1. Introduction

Recent achievements in the synthetic chemistry of subphthalocyanine-type compounds have led to an appearance of numerous molecular structures in a variety of shapes with markedly different redox and optical properties [1–3] and durability. However, only a few of those structures deserve the close attention of engineers involved in organic electronics.

The thin film electronic devices utilizing both subphthalocyanines and diverse phthalocyanine-type compounds are traditionally classified as organic light-emitting diodes (OLEDs), organic field-effect transistors (OFETs), and organic photovoltaic cells (OPVC) [1, 4–7]. Of course, these fascinating heterocyclic molecules find their way into other areas of application such as resistive memory or molecular switches [8, 9], but those are incomparably inferior to the above three types of thin film devices in terms of practical achievements.

The light-emitting properties of conventional phthalocyanines in the undoped films do not appear to be very promising, so they are included in the OLED scheme mostly as the charge transporting components [1, 4, 10, 11]. Plint et al., who are continuing a long-term research in this field, proposed two SubPc derivatives as dopant emitters for an (8-hydroxyquinolinato)<sub>3</sub>Al matrix to obtain the white light from a standard multilayer OLED made by the high-vacuum sublimation technique [12]. Also worth mentioning here is the earlier work of Torres' group [13], in which the solution-processable OLED structures incorporating variously substituted SubPcs were fabricated and tested.

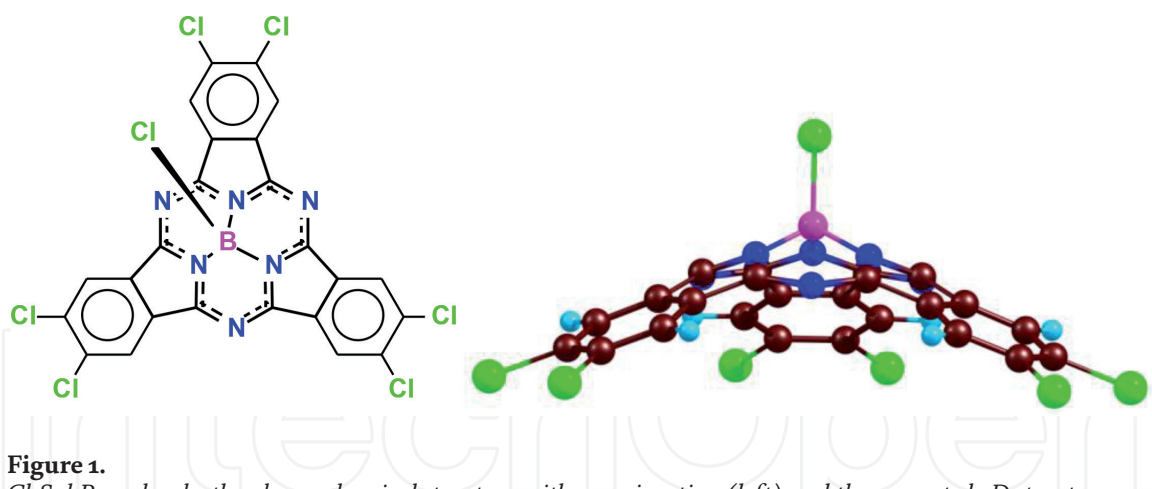

**Figure 1.**

*Cl<sub>6</sub>SubPc molecule: the planar chemical structure with  $\pi$ -conjugation (left) and the computed 3D structure illustrating the conical geometry (right). Green balls show chlorine atoms, one in the axial position (extraligand) and six on the periphery of the benzene rings.*

As to the applications in OFETs, the readers should turn to the review in Ref. [14]. In short, the charge carrier mobilities measured using the standard transistor geometry in subphthalocyanine films are lower than in the films of four-leaf phthalocyanines that are capable of forming highly ordered structures in the channel. A noteworthy work was published more than 10 years ago by Yasuda and Tsutsui [15] who observed sign inversion (from N- to P-) in the majority charge carriers when transferring the SubPc-based OFETs with gold S/D electrodes from the glove box to ambient air. This adds intrigue to the current discussion of whether SubPc acts as a P- or N-type layer in the junction with another molecular material: a possible reason for that may be the unintentional doping from the adjacent layers or the unevenness of fabrication/measurement conditions for different prototypes.

The most impressive results today appear in the field of photovoltaics. We therefore will discuss SubPcs only from the viewpoint of their behavior in thin film photovoltaic cells, particularly in cells with an organic or hybrid heterojunction based on the hexachlorinated subphthalocyanine derivative Cl<sub>6</sub>SubPc (**Figure 1**). This compound is gaining practical importance, though many other peripherally halogen-substituted SubPc derivatives have been synthesized over the last decade [1–5, 16]. To the best of our knowledge, only one hexachlorinated derivative with an extraligand other than chlorine was used in a photovoltaic cell [17]. Despite the availability of many sound publications that deal with Cl<sub>6</sub>SubPc as the photovoltaic material, little is known about its fundamental (intrinsic) properties in a solid. In addition, we have found some inconsistencies in the discussions and speculations unsupported by the relevant experimental data.

## 2. Properties of Cl<sub>6</sub>SubPc thin films

After the introduction of electron-withdrawing chlorine atoms on the periphery of a macrocycle, the Cl<sub>6</sub>SubPc molecule behaves as the electron acceptor with respect to the molecule on the other side of the heterointerface (e.g., unsubstituted SubPc [6, 18–22]), thereby participating in the separation of the photogenerated charges. In the bulk phase, addition of chlorine atoms to the conjugated macrocycle assists in getting the electron transporting organic semiconductors [7]. Therefore, judging from its chemical formulae (**Figure 1**), Cl<sub>6</sub>SubPc is a priori assumed to be the acceptor or N-type material for the organic photovoltaic cells. Perhaps, it is due to this assumption that too little effort has been made to

fundamentally characterize N-type conductivity in the Cl<sub>6</sub>SubPc solid, except for a series of electro-physical experiments on the vacuum-deposited thin films, carried out by Beaumont et al. in [23].

The energy level alignment at SubPc/Cl<sub>6</sub>SubPc heterojunction was recently discussed in detail [21] with the emphasis on the interface gap  $E_G = E_{HOMO}^{Donor} - E_{LUMO}^{Acceptor}$  that determines the maximum achievable open-circuit voltage in a photovoltaic device with a D/A junction. The interface gap  $E_G$  of 1.95 eV was derived from soft XPS and XAS, with the use of DFT (**Table 1**) [21]. This value of  $E_G$  is much greater than what is attainable through pairing the SubPc donor with the conventional N-type acceptor C<sub>60</sub>, which explains the popularity of Cl<sub>6</sub>SubPc among the so-called “non-fullerene” acceptors for organic photovoltaics [5, 16, 17, 21, 25, 27, 30, 32, 33]. The DFT calculations on a Cl<sub>6</sub>SubPc molecule were also performed in Refs. [6, 33], including the visualization of the most important frontier MOs. However, even in the abovementioned studies, such parameters as transport

Parameter	Value	Ref.	Comment
Sublimation temperature, °C	270–290	[24]	Greater than for many halogen <sub>x</sub> SubPc
Color	Purple	[24]	In powder and in toluene solution
$\lambda_{max}(Q)$ , nm, In solution	576	[25]	In chloroform
	569	[24]	In toluene
	570	[26]	In dichloromethane
	In sublimed film	585–590	[18, 19, 24]
$E_{opt}$ , eV	2.1	[20]	Link to Ref. [28]
	2.16	[27]	Not specified
	2.1	[28]	From $\lambda_{max}(Q)$ in solid film
	2.19	[24]	From $\lambda_{max}(Q)$ in solution
$E_{act}$ , eV	1.38	[24]	From thermally activated conductivity in thin vacuum-deposited films
HOMO, eV <sup>a</sup>	6.69	[6]	From UPS
	5.9	[20, 23]	Adopted from [28]
	6.0	[21]	From XPS, XAS, and DFT
	5.8	[22]	From cyclic voltammetry
	6.06	[27]	From cyclic voltammetry
	6.0	[28, 29]	Adopted from [22]
LUMO, eV <sup>a</sup>	3.8	[20, 23]	Adopted from [28]
	3.9	[21]	From XPS, XAS, and DFT
	3.7	[22]	From HOMO- $E_{opt}$ difference
	3.61	[30]	From cyclic voltammetry
	3.90	[27]	From HOMO- $E_{opt}$ difference
	3.6	[28, 29]	From HOMO- $E_{opt}$ difference
Charge carrier mobility $\mu$ , cm <sup>2</sup> V <sup>-1</sup> s <sup>-1</sup> at RT	$8 \pm 2 \times 10^{-7}$	[23]	Vertical zero-field electron mobility, from impedance spectroscopy
	$8.3 \times 10^{-6}$	[27]	Blend with PTB7-Th, vertical electron mobility, from SCLC
	$7.6 \times 10^{-5}$	[31]	Charge carrier mobility of the sum of holes and electrons $\Sigma\mu$ , from flash-photolysis time-resolved microwave conductivity

<sup>a</sup>These are actually negative, below vacuum level.

Methods: UPS = ultraviolet photoelectron spectroscopy, XPS = X-ray photoelectron spectroscopy, XAS = X-ray absorption spectroscopy, DFT = density functional theory, SCLC = space-charge-limited current.

**Table 1.**  
 Cl<sub>6</sub>SubPc, some experimental data.

gap, exciton binding energy  $E_{bi}$ , or diffusion lengths  $L_D$ , which are of paramount importance when constructing a heterojunction-based device [6, 34], have not been estimated<sup>1</sup>.

**Table 1** summarizes the data on some solid-state properties of Cl<sub>6</sub>SubPc available in the literature. As expected, the most frequently discussed values are the positions of the highest occupied and lowest vacant molecular orbitals (HOMO and LUMO) since they can be used for deriving  $E_G$  and, further, for constructing the band diagrams that predict the basic photoconversion parameters of the devices employing various donor/acceptor pairs [20–23, 28–30, 35].

As seen from **Table 1**, the HOMO-LUMO values obtained by various methods/research groups fluctuate within the range of  $\pm 0.2$  eV. Moreover, different numbers can be reported in the articles by the same authors ([20] *vs.* [28] or [21] *vs.* [22]). Such discrepancies are not surprising, considering the diversity of approaches/methods used for estimation [36]. Certain caution should therefore be taken when comparing the data from different sources and, especially, when relying on them in the interpretation of the device characteristics [30, 36]. For instance, in the same Ref. [30],  $E_G$  for the SubPc/Cl<sub>6</sub>SubPc pair was calculated to be equal to 1.83 eV, i.e., the value did not coincide with that from the Ref. [21]. Importantly, the optical bandgap  $E_{opt}$  is smaller than the fundamental bandgap (the difference between the ionization potential and the electron affinity of a molecule) by the value of the electron–hole pair binding energy. Thus, the HOMO-LUMO difference obtained from the quantum chemical calculations with various levels of accuracy provides an approximation to the fundamental gap and needs to be amended before used as equivalent of  $E_{opt}$  (**Table 1**). The situation gets more complicated in a solid, where the transport of charge carriers or quasiparticles (excitons) occurs. Due to the polarization/stabilization effects,  $E_{bi}$  differs from the binding energy of electron–hole pair created within a (single) photoexcited molecule in the gas phase [36].

Cl<sub>6</sub>SubPc sublimates in a high vacuum without noticeable decomposition, which allows one to obtain thin films on various functional substrates. The vacuum-deposited films are intensively purple colored, homogeneous, and smooth [24]. This favors their application in multilayer photovoltaic devices. However, they are electrically resistive [21, 24, 35], with the charge carrier mobility (electrons) much lower than in fullerenes (**Table 1**). In the literature, the Cl<sub>6</sub>SubPc films are commonly treated as amorphous [21]. As recently shown, a correct choice of deposition surface and temperature contributes to the production of crystalline films of Cl<sub>6</sub>SubPc with improved conductivity, which in turn upgrades the parameters of photovoltaic devices [24, 35]. To our knowledge, the effect of intentional or unintentional (e.g., atmospheric) doping of the Cl<sub>6</sub>SubPc matrix on its conducting properties has not been investigated so far.

### 3. Fabrication of Cl<sub>6</sub>SubPc-based heterojunctions for photovoltaic cells

Roughly, there are two types of heterojunctions with clear geometrical dissimilarity: flat heterojunction (PHJ) and bulk heterojunction (BHJ). Cl<sub>6</sub>SubPc can be used in both—Refs. [5, 18–23, 25, 28–30, 35] and [5, 6, 27, 33], respectively. Such flexibility is accounted for by the increased, as compared to phthalocyanines, solubility of Cl<sub>6</sub>SubPc, and subphthalocyanines in general, although a rigorous study of

<sup>1</sup> We have found only one source [Barito AJ. Cascade Organic Photovoltaics [thesis]. University of Michigan; 2015] unsupported by the relevant peer-reviewed journal publication, in which  $L_D = 4.5$  nm and exciton lifetime  $\tau = 0.53$  ns are reported for the vacuum-deposited Cl<sub>6</sub>SubPc films.



the solvation processes does not permit unambiguous attribution of conventional SubPc to the classical dyes, it is pigment-like rather [26, 37].

PHJ is prepared by sequentially depositing thin layers of donor and Cl<sub>6</sub>SubPc. The most common A-on-D order of deposition gives a normal PHJ, assuming the cathode located on top of the device, while the D-on-A configuration with the anode on top is termed as inverted PHJ. The thickness of layers is of paramount importance, and it should be adjusted individually not only for the donor but also for Cl<sub>6</sub>SubPc, since the experimental setup, deposition sequence, additional functional materials, etc. may vary in each research group. Thicker photoactive layers are likely to capture more incident photons and protect against leakages, but short  $L_D$  and rapidly increasing serial resistance require that the layers be kept sufficiently thin. Typical thickness of Cl<sub>6</sub>SubPc in PHJ does not exceed few tens nanometers. Deposition process is carried out mostly via the vacuum evaporation technique, but the examples of solution-processed PHJ with subphthalocyanines are also known [38, 39].

To obtain a BHJ, a donor component and Cl<sub>6</sub>SubPc should be dissolved in the chlorobenzene (various additives like 1,8-diiodooctane (DIO) or 1-chloronaphthalene (CN) are recommended) and then deposited using the spin-coating technique. Both the solution chemistry and post-deposition treatment of thus made blend affect the resulting device parameters [17, 27, 33].

It is generally believed that the efficiency of power conversion (*PCE*) in the photovoltaic cells with BHJ must be greater than in the PHJ-based cells, this being due to the morphological reasons [38–40]. Quite surprisingly, in all the works dealing with both solution- and vacuum-processed BHJ with a Cl<sub>6</sub>SubPc acceptor, the actual morphology of the photoactive layer(s) remains highly uncertain. In Ref. [6], the morphology of 20 nm thick films consisting of a co-evaporated in vacuum SubPc<sub>x</sub>:Cl<sub>6</sub>SubPc<sub>1-x</sub> blend has not been elucidated. In Ref. [27], the polymer: Cl<sub>6</sub>SubPc mixture termed as BHJ was spin-coated and annealed to obtain 75 nm thick photoactive layers (**Table 2**), but the transmission electron microscopy (TEM) images showed a homogeneous blend without a noteworthy phase separation. This led authors to a conclusion that the pure phase domains are absent. Notably, the nanocrystalline domains with high local carrier mobility of at least one of the two components of BHJ are required for efficient dissociation of the charge transfer (CT) states into free charge carriers at the D/A interface [27].

A broader morphological study in Ref. [33] included atomic force microscopy (AFM), TEM, and X-ray diffraction (XRD) measurements on the spin-coated mixtures of substituted subphthalocyanines, including Cl<sub>6</sub>SubPc, with a polymer, also termed as BHJ. However, a thorough examination of the published images reveals that neither AFM nor TEM indicates a formation of a long-enough fibrillary structure in the films (unspecified thickness), although authors stated otherwise<sup>2</sup>. The XRD patterns display the changes in the intensity of a single diffraction peak corresponding to the polymeric component of the blend relative to the pure phase of the polymer (at only one D/A ratio) [33], which cannot be regarded as a proof of BHJ.

In neither of the above studies, a relevant morphological model has been developed based on the instrumental analysis. The “phase diagram” attributing the morphological changes to the composition of a binary phase [43–45] is missing as well. The well-known “mosaic” picture of the polymer: subphthalocyanine BHJ published in 2009 [38] seems to be borrowed from the sketches of the polymeric solution-made BHJ [16, 45] without being confirmed by adequate morphological analysis. Contrary to what is drawn, the authors stated at the end of the article [38] that the films stayed amorphous even for the 1:5 blend (from grazing incidence

<sup>2</sup> Authors claimed in the supplementary materials section that their Cl<sub>6</sub>SubPc-based cells outperform the BHJ-based cells fabricated in Ref. [27], which is not true (**Table 2**).

Ref.	Schematic of cells <sup>*</sup>	Junction type	Parameters			
			$J_{sc}$ (mA/cm <sup>2</sup> )	$V_{oc}$ (V)	FF	PCE (%)
[18, 19]	A1	PHJ	3.10	1.33	0.59	2.39
	A2		3.62	1.29	0.47	2.20
	A3		3.28	1.32	0.63	2.70
[22]	B	PHJ	3.53	1.31	0.58	2.68
[23, 28]	C1	PHJ	2.54	0.89	0.50	1.12
	C2		2.09	0.50	0.48	0.50
[30]	D1	PHJ	6.17	1.00	0.66	3.96
	D2		10.1	1.04	0.67	6.86
[25]	E1	PHJ	9.0	1.03	0.71	6.4
	E2		9.0	1.02	0.68	6.1
	E3		9.2	1.03	0.58	5.4
[28, 29]	F1	PHJ	5.72	0.60	0.56	1.89
	F2		2.13	0.44	0.57	0.52
[35]	G	PHJ	6.43	0.55	0.48	1.71
[27]	H	BHJ	10.7	0.77	0.48	4.0
[33]	K	BHJ	7.79	0.66	0.48	2.48
[41]	L	PHJ/ BHJ	8.6	0.92	56	4.46
Cells with SubNc as acceptor or donor						
[42]	M	PHJ	14.55	0.96	61	8.40
[39]	N1	BHJ	10.3	0.90	41	3.8
	N2		12.1	0.74	47	4.2

<sup>\*</sup>Description of the schematic (thickness of layers in nm is given in the parentheses, if specified by authors): A1 = ITO/MoO<sub>x</sub>(5 nm)/SubPc(15)/Cl<sub>6</sub>SubPc(20)/BCP(8)/Al, normal; A2 = ITO/BCP(8)/Cl<sub>6</sub>SubPc(15)/SubPc(15)/MoO<sub>x</sub>(40)/Al, inverted; A3 = ITO/MoO<sub>x</sub>(5)/SubPc(14)/Cl<sub>6</sub>SubPc(30)/BCP(5)/Al, optimized; B = ITO/MoO<sub>x</sub>(5)/SubPc(10)/Cl<sub>6</sub>SubPc(27)/BCP(8)/Al; C1 = ITO/MoO<sub>x</sub>(5)/Tc(60)/Cl<sub>6</sub>SubPc(35)/BCP(8)/Al(100); C2 = ITO/MoO<sub>x</sub>(5)/Pent(60)/Cl<sub>6</sub>SubPc(25)/BCP(8)/Al(100); D1 = ITO/MoO<sub>3</sub>(5)/SubNc(14)/Cl<sub>6</sub>SubPc(8)/BCP:C<sub>60</sub>(50)/Ag; D2 = ITO/PEDOT:PSS/DIP(5)/SubNc(14)/Cl<sub>6</sub>SubPc(8)/BCP:C<sub>60</sub>(50)/Ag; E1 = ITO/PEDOT:PSS/DIP(5)/SubNc(12)/Cl<sub>6</sub>SubPc(10)/BCP:C<sub>60</sub>(45)/Ag; E2 = ITO/PEDOT:PSS/DIP(5)/SubNc(12)/Cl<sub>6</sub>SubPc(10)/C<sub>60</sub>(35)/BCP(10)/Ag; E3 = ITO/PEDOT:PSS/DIP(5)/SubNc(19)/Cl<sub>6</sub>SubPc(10)/BCP:Yb(45)/Ag; F1 = ITO/PEDOT:PSS/α6T(55, evaporated)/Cl<sub>6</sub>SubPc(20)/BCP(10)/Ag(100); F2 = ITO/PEDOT:PSS/P3HT(55, spin-coated)/Cl<sub>6</sub>SubPc(20)/BCP(10)/Ag(80); G = ITO/MoO<sub>x</sub>(3)/CuI(60)/Cl<sub>6</sub>SubPc(45)/BCP(6)/Al(100), structured; H = ITO/ZnO(40)/PTB7-Th:Cl<sub>6</sub>SubPcCl (~75, solution)/MoO<sub>x</sub>(10)/Ag(100); K = ITO/PEDOT:PSS(40)/PBDB-T:Cl<sub>6</sub>SubPcCl(?, solution)/Ca(20)/Al(100); L = ITO/MoO<sub>x</sub>(10)/DPSQ(13)/C<sub>60</sub>(15)/C<sub>60</sub>:ZCl:Cl<sub>6</sub>SubPc(60,2:1:1 co-evaporated blend)/BCP(10)/Al(100); M = ITO/PEDOT:PSS(20)/α6T(60)/SubNc(12)/SubPc(18)/BCP(7)/Ag(120); N1 = ITO/MoO<sub>3</sub>(5)/SubNc:PC<sub>70</sub>BM(75,1:5 solution)/BCP(6)/Al(100); N2 = ITO/MoO<sub>3</sub>(5)/SubNc:C<sub>70</sub>(75,1:5 co-evaporated blend)/BCP(6)/Al(100).

Donors: SubPc = unsubstituted subphthalocyanine; Tc = tetracene; Pent = pentacene; SubNc = unsubstituted subnaphthalocyanine; α6T = α-sexithiophene; P3HT = poly(3-hexylthiophene); PTB7-Th = polymer with linear formula (C<sub>49</sub>H<sub>57</sub>FO<sub>2</sub>S<sub>6</sub>)<sub>n</sub>; PBDB-T = polymer with linear formula (C<sub>68</sub>H<sub>78</sub>O<sub>2</sub>S<sub>8</sub>)<sub>n</sub>; DPSQ = 2,4-bis[4-(N,N-diphenylamino)-2,6-dihydroxyphenyl] squaraine.

Other device components: ITO = indium-tin oxide, In<sub>2</sub>O<sub>3</sub>:SnO<sub>2</sub>; MoO<sub>x</sub> or MoO<sub>3</sub> = molybdenum trioxide, usually substoichiometric; PEDOT:PSS = poly(2,3-dihydrothieno-1,4-dioxin)-poly(styrenesulfonate); BCP = bathocuproine; DIP = diindenoperylene (C<sub>32</sub>H<sub>16</sub>), CuI = cuprous iodide, ZnO = zinc oxide; ZCl = chlorinated zinc dipyrin; PC<sub>70</sub>BM = [6,6]-phenyl-C<sub>71</sub>-butyric acid methyl ester.

**Table 2.**

Parameters of the photovoltaic cells with Cl<sub>6</sub>SubPc as acceptor.

wide-angle X-ray scattering) and that “work is under way to improve the crystallinity of SubPc derivatives” [38].

Therefore, the researchers rely only on the fact that a film containing a mixture of two components is a BHJ. But rigorously speaking, there are certain morphological features that determine the ultrafast charge transport—the reason behind the success

of the BHJ concept in organic photovoltaics [45]. The most important of them is the formation of bicontinuous interpenetrating 3D networks of components within a D/A blend. These networks, often thought of as columnar (pipelines), comb-like, or interdigital structures, should accomplish the transport of photogenerated charge carriers to the respective electrodes. Obviously, breaking the continuity will lower the charge collection efficiency. There is ample experimental evidence of the existence of such interdigitation in the classical solution-processed polymer: fullerene blends obtained by a set of independent, complementary analytical techniques, including the secondary ion mass spectrometry (SIMS) with depth profiling [45, 46].

We have found out that the misconception about any two-component layer as being truly a BHJ rests on the analogy with few examples of the photovoltaic cells, in which the (sub)phthalocyanine is mixed with C<sub>60</sub>. Vacuum-deposited SubPc:C<sub>60</sub> blends are widely known in organic photovoltaics due to availability and high efficiency; they are often used as a model system in many theoretical and experimental works. However, there is only one work where their microstructure was sufficiently detailed. Pandey et al. [44] conducted a comprehensive characterization of thin films of a mixture of SubPc:C<sub>60</sub>, involving XRD, TEM, optical spectroscopy, and selected area electron diffraction. At only one mixing ratio of 1:4, they found some signs of crystallinity of SubPc dispersed in the nanocrystalline C<sub>60</sub> matrix, whereas other compositions resulted in amorphous films. The *PCE* of the photovoltaic cells with thus optimized composition of the photoactive layer was only 9% higher than in a similar cell, in which the composition was not optimized (1:9). Besides, the morphology characterization and photovoltaic measurements were carried out on different substrates and films of different thickness, which requires further refinement<sup>3</sup>.

Even for the metal-phthalocyanine complexes that tend to self-assemble (crystallize) due to a strong intermolecular interaction, a reliable experimental observation of the anticipated nanostructuring in co-evaporated blends turned out to be very problematic. As-deposited phthalocyanine: fullerene mixtures (commonly used ratio is 1:1) adopt fully amorphous structure, as witnessed via a combination of several independent analytical techniques [40, 51–55]. Again, it points to a lack of the phase separation, which is a prerequisite toward the formation of the interpenetrating D/A network typical of BHJ [45]. Only through considerable effort, by thoroughly selecting the annealing temperature, mixing ratio, or seed layer, the microscale organization of a blend can be initiated, and the pure crystalline phthalocyanine domains become visible [44, 52–54]. Unlike phthalocyanines, the SubPc molecules weakly interact in a solid, which makes their self-assembly rather difficult. As such, the formation of a well-established charge carrier percolation pathways in the SubPc:C<sub>60</sub> blend will be less probable than in the phthalocyanine-based blends.

Crystallographic studies show that interactions between the neighboring Cl<sub>6</sub>SubPc molecules in a solid are stronger than those in SubPc [23], but the formation (and observation) of a well-organized BHJ incorporating subphthalocyanine-type acceptor is still a challenging task.

<sup>3</sup> In mid 1990s, studies of the photoconductivity in thick films of the C<sub>60</sub>-doped zinc phthalocyanine revealed the formation of a charge transfer complex that amplifies the photosensitivity of the blend [47, 48]. This was confirmed in Refs. [49, 50] using several optical methods, but later the authors sided with another model more closely associated with the BHJ, again with no morphological indications. In either way, the formation of a bimolecular CT complex means that the uniformly 1:1 mixed phase cannot be treated in terms of individual organic semiconductors any longer. Here, it is worthwhile to look further into the matter by proposing the new insights on the photoconductivity mechanisms instead of pursuing adaptation of the standard polymeric BHJ concept to the amorphous small-molecule based blends [51].



In any heterojunction type, the charge transfer across the D/A interface could also be influenced by the dipole moment of a molecule of one or both components. It bound to occur in the pyramidal subphthalocyanine molecules bearing axially attached halogen (**Figure 1**) and can further be tuned by the axial/peripheral substitution [4, 26, 56–59]. Mutual orientation of the acceptor/donor molecules at the interface affects both the dissociation distance and the local electric field during the charge transfer and separation, thus modifying the resulting  $V_{oc}$  of the device [59]. Morris et al. [59] experimentally investigated and modeled the characteristics of PHJ-based photovoltaic cells with two subphthalocyanines containing either chlorine or fluorine extraligand paired with the  $C_{60}$  acceptor. These donor molecules have nearly identical structure, except for a permanent electrical dipole, which allows the analysis of the variations in  $V_{oc}$  in terms of D/A separation width, polaron pair binding energy, and dipole orientation, other morphological factors being neglected.

Unfortunately, this interesting issue has not been given enough attention in the experiments. Theoretical considerations regarding the influence of a molecular dipole in a series of, mostly hypothetical, subphthalocyanines on the photovoltaic parameters were recently published [58]. The first-principles DFT calculations were also performed in [60] to characterize the electronic structure of the axially substituted SubPc molecules interfaced with  $C_{60}$ . A strong correlation between the experimentally measured  $V_{oc}$  and the computed CT excited state energy was found. One concluding remark hints that the dependence of these parameters on the actual interface morphology can be greater in significance than the modification of the ionization potential induced by change in the chemistry. Another prediction is that to gain a higher value of  $V_{oc}$ , the D/A interaction should be lowered, e.g., by increasing the spatial separation through the introduction of steric hindrances [60]. A fundamental theoretical study of relative arrangements of the donor and acceptor molecules was carried out by a large group of authors using the pentacene/ $C_{60}$  system as an example [61]. It was shown that the interfacial dipole originates mostly in polarization effects rather than a partial charge transfer from donor to acceptor. Next, the calculations demonstrate that the measurement of the macroscopic dipole averaged over the interface is not a representative of the local dipoles that can be induced by individual molecules at the interface. The local dipole was found to fluctuate in sign and magnitude over the interface and appears as if a sensitive probe of the relative arrangements of the pentacene and  $C_{60}$  molecules.

Note that theoretical findings are usually done under the assumption of an inert, molecularly sharp, regular, and pure PHJ (which almost never occurs in the experiments) and lack systematic verification in a representative series of the prototypical devices. For instance, the experimental evidence on the formation of a Diels-Adler adduct at the pentacene/ $C_{60}$  interface was recently found [62], thus casting doubt on the above results.

These and many other morphological issues are also addressed in the monograph, Chapter 2 in Ref. [63]. This book in general is strongly recommended for the readers interested in organic photovoltaic devices and materials.

#### 4. Analysis of the cell performance

**Table 2** summarizes the efficiency metrics for the prototypical solar cells exploiting  $Cl_6$ SubPc adopted from various sources, along with a description of the device schematics. For comparison, a few examples of the cells with subphthalocyanine are included in the last two rows. Other data collections describing the performances of variously designed photovoltaic devices based on SubPc-type compounds can also be found in Refs. [1, 4, 5, 28, 64].

As seen from **Table 2**, the single-junction photovoltaic cells with Cl<sub>6</sub>SubPc as the acceptor can generate open-circuit voltage  $V_{oc}$  in the range of 0.44–1.33 V, usually about 1 V or above. Expectedly, the decisive contribution in the resulting *PCE* makes the short-circuit current  $J_{sc}$ ; its value varies several times among different devices, while fill-factor *FF* lies within a range of  $0.57 \pm 0.12$ . The reported parameters largely depend on the device scheme, adjacent functional materials, and measurement conditions used in a particular study, which make their comparison difficult. Nonetheless, there are several points to ponder on when looking at the collected data:

1. Pairing Cl<sub>6</sub>SubPc with the congener donors, SubNc or SubPc, results in the photovoltages exceeding 1 V. This value is greater than ever reported for the analogous PHJ utilizing structurally dissimilar small-molecule acceptors, like perhalogenated phthalocyanines or perylenes. Presumably, the structural similarity of the pairing conical molecules allows them to form a more intimately bound D/A pairs at the interface. This would mean, for example, a good quality of the (less distant) physical contact at the P/N junction. Second, as discussed above, certain orientations of electrical dipole of the donor molecule relative to the intrinsic dipole of acceptor, if one exists, could favor the charge separation. Macroscopic interfacial dipole at the SubPc/Cl<sub>6</sub>SubPc junction was found to be small (0.15 eV) in [21], but in principle its role can be significant [51, 57, 59, 61, 63]<sup>4</sup>.
2. The devices obtained entirely by the vacuum deposition techniques usually exhibit better characteristics than devices with the solution-processed heterojunction (**Table 2**). At least two reasons could be suggested, taking into account that in reality the metallic contacts and oxide buffer layers are vacuum-evaporated even in the cells referred to by the authors as “solution-processed.” First, the combination of wet and dry laboratory techniques used for the growth of multilayered heterostructures incurs problems with the compatibility of materials, transfer of semi-finished samples to the evaporator and back, etc. Using the vacuum methods only, the fabrication of the entire sample can be realized within a single run without breaking the growth process, from etching of substrates to deposition of the top electrode (including characterization tools, most of which require high vacuum). Second, the simplicity and robustness of the solution-based deposition techniques are somewhat overrated in the case of BHJ based on small-molecules. This is illustrated in the preceding section that describes the difficulties in obtaining the phase-separated bicontinuous networks with SubPcs. The BHJ concept does not provide the expected benefit in efficiency and is particularly unuseful for improving  $V_{oc}$ .
3. The champion efficiency of 8.4% reported for the PHJ-based photovoltaic cells so far has been obtained for the  $\alpha 6T$ /SubNc/SubPc cascade [42], which geometrically is a sequence of vacuum-evaporated PHJs. Here, both SubNc and SubPc behave as acceptors with respect to the thiophene molecules while being donors when paired with fullerenes or halogenated subphthalocyanines (**Table 2**). The excitons freely migrate across the relatively thick layers from

<sup>4</sup> In Ref. [65], a complex study of the “copper phthalocyanine/C<sub>60</sub>” interface by DFT, UPS, and SIMS suggests that the local net charge-induced electric field, rather than the spontaneous charge transfer across the interface, is responsible for the interface dipole, in accordance with the theoretical predictions [61]. Authors observed a sizable interface dipole of electrostatic nature (up to 0.27 eV, depending on molecular orientation with respect to the deposition surface and on the deposition sequence), which rules out the charge transfer as the origin of the interface dipole.

the wide-bandgap to the smaller-bandgap acceptor with a subsequent dissociation at the donor interface via a long-range Förster energy transfer, which is in turn a function of the relative orientation of the transition dipole moments and distance between the molecules. The mechanisms explaining why both acceptors actively contribute to the photocurrent caused an active response in the organic photovoltaic community and spawned a large number of emulations. The attempt of Bender et al. [20] to use Cl<sub>6</sub>SubPc as the donor component of the cascade cell with the scheme “Cl<sub>6</sub>SubPc/μ-oxo-SubPc/C<sub>70</sub>” was unsuccessful, highly likely due to the wrongly cascading LUMOs (but a very small layer thickness permitted enough efficiency). The cascade cells in Refs. [25, 30], although the authors do not consider them as such, demonstrated a high photovoltaic performance (**Table 2**).

It should be noted that SubNcs hold the second position in the ranking of SubPc-type compounds after parent SubPc; their properties and optoelectronic applications deserve a separate circumstantial review.

## 5. Current status and perspectives

Work on design of D/A junctions with various halogen-substituted subphthalocyanines was initiated back in 2009 [64]. In the last few years it is Cl<sub>6</sub>SubPc that has become one of the most efficient acceptors in both bilayer and blended heterojunctions. Many authors now use Cl<sub>6</sub>SubPc as a reference when introducing their newly synthesized compounds belonging to the subphthalocyanine family in photovoltaic devices [16, 17, 24, 27, 28, 31–33, 66], as was commonly done earlier with C<sub>60</sub>. However, the critical analysis of the current literature suggests that Cl<sub>6</sub>SubPc still holds the lead among competitors. It combines availability (ease of synthesis and good yield), versatility of deposition (both wet and dry methods are available), appropriate color characteristics (position and intensity of the Q-band), and stability. Such benefits stimulate appearance of new heterojunctions designs employing this compound and steady interest in future research. For instance, such drawbacks as low charge carrier mobility in thin films can be overcome using morphology engineering [35]. Doping of the Cl<sub>6</sub>SubPc molecular matrix with appropriate agents could be another option for improvement of the conducting properties [30]. Or vice versa, Cl<sub>6</sub>SubPc can be doped into (mixed with) another acceptor to form a ternary blended junction [41].

Meanwhile, the search for new electron acceptors for photovoltaics among the subphthalocyanines with electron-withdrawing substituents on the periphery is underway. Two interesting approaches have been proposed last year by Torres and coworkers, who are the main newsmakers in this field. The first one consists in the synthesis of subphthalocyanines hexacyanated at the same peripheral positions as in Cl<sub>6</sub>SubPc [31]. Unfortunately, due to the inherent instability of hexa-substituted derivatives, only slightly cyanated compounds were obtained and characterized, which have two cyano groups in only one isoindole unit, while the other two still bear two chlorines each, as in the parent Cl<sub>6</sub>SubPc (**Figure 1**). Even for such CN<sub>4</sub>Cl<sub>2</sub>SubPc complex, there are indications on the increased mobility of charge carriers in vacuum-deposited films [31].

The second approach addresses the synthesis of new SubNc-type compounds with chlorines in the outer benzene rings [66]. Authors chose to directly use the dodeca-substituted derivative having four Cl atoms in each outer benzene ring, which unluckily is insoluble, whereas the entire work was targeted at making



devices with a solution-processed BHJ<sup>5</sup> only. In this respect another work of Bender et al. [67] is worth mentioning, in which the authors argue that due to the nature of synthesis all of the SubNcs, both commercially available or obtained using the published protocols, in fact represent a mixture of derivatives randomly chlorinated at bay position. That is, in addition to the axial chlorine, part of the molecules inevitably contains chlorine atoms attached to the inner benzene rings of the naphthalene moieties. The outer benzene rings remain always hydrogenated. The presence of 1.13–2.96 chlorines per molecule on average was estimated [67]. Curiously, chlorination of all available bay positions in this compound would yield the Cl<sub>6</sub>SubNc compound that has not been described yet.

The electron-accepting properties of the Cl<sub>6</sub>SubPc molecule can be further enhanced by substituting the carbon atoms not bonded to chlorine with the more electronegative nitrogen. Such subporphyrine-type compounds are synthesized in our group [24, 68]. However, the deep-lying HOMOs often cause a decrease in the specific conductivity of the bulk material. As with many other synthetic approaches, an exact balance must be maintained between the individual properties of a molecule and the photoelectrical properties (including morphological issues) of a solid.

Eventually, the group from Kyushu University developed the SubPc-type compounds, in which two chlorines in each benzene ring are (a) replaced by the -S-(C=O)-S- semicircle, or (b) peripheral benzenes in SubPc were directly replaced with the electron-withdrawing 1,3-dithiole-2-one units [69]. The deep bowl depths and curvatures of the formed SubPc and SubPz cores (*cf.* **Figure 1**) motivated authors to investigate the bimolecular concave-convex interactions with fullerenes in the co-crystals, as a first step to the fabrication of photovoltaically active materials.

## 6. Conclusion

Molecular properties of the Cl<sub>6</sub>SubPc compound, such as redox potentials and positions of the absorption bands, fluorescence quantum yield, solubility, and stability, make it a material of choice when it comes to fabrication of a small-molecule based optoelectronic device, with almost any schematic. After a proper optimization of the donor material in the P/N junction (N = Cl<sub>6</sub>SubPc) and with corresponding device composition, the open-circuit voltages above 1.3 V can be achieved. Further progress in the power conversion efficiency is limited mostly by the density of current leaking through the illuminated device, a parameter strongly dependent on the mutual arrangement of Cl<sub>6</sub>SubPc molecules either in a layer (for PHJ) or in the interpenetrating network (if it exists) and on the morphology of the heterointerface at the nanoscale. The questions whether the electrical dipole or symmetry of the molecule could affect the generation of charge carriers by the junction do not seem to be of serious practical importance, but are very interesting for fundamental understanding of the photovoltaic process proper.

<sup>5</sup> The authors claimed that SubNcs have never been tested as either donors or acceptors in solution-processed BHJ solar cells [66]. This is not correct since in 2013, Yang and coworkers have published their data on both solution-processed and vacuum-evaporated BHJ with SubNc donor (acceptor was PC<sub>70</sub>BM or C<sub>70</sub>, respectively) [39]. The optimized devices showed promising efficiency of 4.0 and 4.4% at room temperature (**Table 2**).



## **Acknowledgements**

This work was supported by the Russian Science Foundation (grant #17-13-01522).

## **Conflict of interest**

The authors declare no conflict of interest.

## **Author details**

Georgy L. Pakhomov<sup>1,2</sup>, Vlad V. Travkin<sup>2</sup> and Pavel A. Stuzhin<sup>1\*</sup>

1 Ivanovo State University of Chemistry and Technology, Ivanovo, Russia

2 Institute for Physics of Microstructures of the Russian Academy of Sciences, Nizhny Novgorod, Russia

\*Address all correspondence to: [stuzhin@isuct.ru](mailto:stuzhin@isuct.ru)

## **IntechOpen**

© 2019 The Author(s). Licensee IntechOpen. This chapter is distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/3.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited. 

## References

- [1] Claessens CG, González-Rodríguez D, Rodríguez-Morgade MS, Medina A, Torres T. Subphthalocyanines, subporphyrines, and subporphyrins: Singular nonplanar aromatic systems. *Chemical Reviews*. 2014;**114**:2192-2277. DOI: 10.1021/cr400088w
- [2] Shimizu S, Kobayashi N. Structurally-modified subphthalocyanines: Molecular design towards realization of expected properties from the electronic structure and structural features of subphthalocyanine. *Chemical Communications*. 2014;**50**:6949-6966. DOI: 10.1039/C4CC01526F
- [3] Rio Y, Rodriguez-Morgade MS, Torres T. Modulating the electronic properties of porphyrinoids: A voyage from the violet to the infrared regions of the electromagnetic spectrum. *Organic & Biomolecular Chemistry*. 2008;**6**:1877-1894. DOI: 10.1039/b800617b
- [4] Morse GE, Bender TP. Boron subphthalocyanines as organic electronic materials. *ACS Applied Materials & Interfaces*. 2012;**4**:5055-5068. DOI: 10.1021/am3015197
- [5] Grant TM, Josey DS, Sampson KL, Mudigonda T, Bender TP, Lessard BH. Boron subphthalocyanines and silicon phthalocyanines for use as active materials in organic photovoltaics. *The Chemical Record*. 2019;**19**:1-21. DOI: 10.1002/tcr.201800178
- [6] Schwarze M, Tress W, Beyer B, Gao F, Scholz R, Poelking C, et al. Band structure engineering in organic semiconductors. *Science*. 2016;**352**:1446-1449. DOI: 10.1126/science.aaf0590
- [7] Tang ML, Oh JH, Reichardt AD, Bao Z. Chlorination: A general route toward electron transport in organic semiconductors. *The Journal of the American Chemical Society*. 2009;**131**:3733-3740. DOI: 10.1021/ja809045s
- [8] Shao JY, Cui BB, Tang JH, Zhong YW. Resistive memory switching of transition-metal complexes controlled by ligand design. *Coordination Chemistry Reviews*. 2019;**393**:21-36. DOI: 10.1016/j.ccr.2019.05.010
- [9] Martynov AG, Safonova EA, Tsivadze AY, Gorbunova YG. Functional molecular switches involving tetrapyrrolic macrocycles. *Coordination Chemistry Reviews*. 2019;**387**:325-347. DOI: 10.1016/j.ccr.2019.02.004
- [10] Hohnholz D, Steinbrecher S, Hanack M. Applications of phthalocyanines in organic light emitting devices. *Journal of Molecular Structure*. 2000;**521**:231-237. DOI: 10.1016/S0022-2860(99)00438-X
- [11] Sakakibara Y, Bera RN, Mizutani T, Ishida K, Tokumoto M, Tani T. Photoluminescence properties of magnesium, chloroaluminum, bromoaluminum, and metal-free phthalocyanine solid films. *The Journal of Physical Chemistry B*. 2001;**105**:1547-1553. DOI: 10.1021/jp002943o
- [12] Plint TG, Lessard BH, Bender TP. Doping chloro boron subnaphthalocyanines and chloro boron subphthalocyanine in simple OLED architectures yields warm white incandescent-like emissions. *Optical Materials*. 2018;**75**:710-718. DOI: 10.1016/j.optmat.2017.11.028
- [13] Diaz DD, Bolink HJ, Cappelli L, Claessens CG, Coronado E, Torres T. Subphthalocyanines as narrow band red-light emitting materials. *Tetrahedron Letters*. 2007;**48**:4657-4660. DOI: 10.1016/j.tetlet.2007.05.036

- [14] Melville OA, Lessard BH, Bender TP. Phthalocyanine-based organic thin-film transistors: A review of recent advances. *ACS Applied Materials & Interfaces*. 2015;7:13105-13118. DOI: 10.1021/acsami.5b01718
- [15] Yasuda T, Tsutsui T. n-channel organic field-effect transistors based on boron-subphthalocyanine. *Molecular Crystals and Liquid Crystals*. 2007;462:3-9. DOI: 10.1080/15421400601009278
- [16] Zhang J, Tan HS, Guo X, Facchetti A, Yan H. Material insights and challenges for non-fullerene organic solar cells based on small molecular acceptors. *Nature Energy*. 2018;3:720-731. DOI: 10.1038/s41560-018-0181-5
- [17] Ebenhoch B, Prasetya NBA, Rotello VM, Cooke G, Samuel IDW. Solution-processed boron subphthalocyanine derivatives as acceptors for organic bulk-heterojunction solar cells. *Journal of Materials Chemistry A*. 2015;3:7345-7352. DOI: 10.1039/C5TA00715A
- [18] Hancox I, New E, Jones TS. Utilising solution processed zirconium acetylacetonate as an electron extracting layer in both regular and inverted small molecule organic photovoltaic cells. *Organic Electronics*. 2015;23:105-109. DOI: 10.1016/j.orgel.2015.04.019
- [19] Sullivan P, Schumann S, Da Campo R, Howells T, Duraud A, Shipman M, et al. Ultra-high voltage multijunction organic solar cells for low-power electronic applications. *Advanced Energy Materials*. 2013;3:239-244. DOI: 10.1002/aenm.201200560
- [20] Castrucci JS, Garner RK, Dang JD, Thibau E, Lu ZH, Bender TP. Characterization of  $\mu$ -oxo-(BsubPc)<sub>2</sub> in multiple organic photovoltaic device architectures: Comparing against and combining with Cl-BsubPc. *ACS Applied Materials & Interfaces*. 2016;8:24712-24721. DOI: 10.1021/acsami.6b06717
- [21] Lee H, Ahn SW, Ryu SH, Ryu BK, Lee MH, Cho SW, et al. Interfacial electronic structure of Cl<sub>6</sub>SubPc non-fullerene acceptors in organic photovoltaics using soft X-ray spectroscopies. *Physical Chemistry Chemical Physics*. 2017;19:31628-31633. DOI: 10.1039/C7CP04876A
- [22] Sullivan P, Duraud A, Hancox I, Beaumont N, Mirri G, Tucker JHR, et al. Halogenated boron subphthalocyanines as light harvesting electron acceptors in organic photovoltaics. *Advanced Energy Materials*. 2011;1:352-355. DOI: 10.1002/aenm.201100036
- [23] Beaumont N, Castrucci JS, Sullivan P, Morse GE, Paton AS, Lu ZH, et al. Acceptor properties of boron subphthalocyanines in fullerene free photovoltaics. *The Journal of Physical Chemistry C*. 2014;118:14813-14823. DOI: 10.1021/jp503578g
- [24] Travkin V, Yunin P, Stuzhin P, Pakhomov G. Characterization of vacuum-deposited films of hexachloro-substituted subphthalocyanines for photovoltaic applications. *Materials Today Proceedings*. 2019. DOI: 10.1016/j.matpr.2019.07.708
- [25] Verreet B, Cnops K, Cheyngs D, Heremans P, Stesmans A, Zango G, et al. Decreased recombination through the use of a non-fullerene acceptor in a 6.4% efficient organic planar heterojunction solar cell. *Advanced Energy Materials*. 2014;4:1301413. DOI: 10.1002/aenm.201301413
- [26] Sampson KL, Jiang X, Bukuroshi E, Dovijarski A, Raboui H, Bender TP, et al. A comprehensive scope of peripheral and axial substituent effect on the spectroelectrochemistry of boron subphthalocyanines. *The Journal of Physical Chemistry A*.

2018;**122**:4414-4424. DOI: 10.1021/acs.jpca.8b02023

[27] Duan C, Zango G, Iglesias MG, Colberts FJM, Wienk MM, Martinez-Diaz MV, et al. The role of the axial substituent in subphthalocyanine acceptors for bulk-heterojunction solar cells. *Angewandte Chemie, International Edition*. 2017;**56**:148-152. DOI: 10.1002/anie.201608644

[28] Castrucci JS, Josey DS, Thibau E, Lu ZH, Bender TP. Boron subphthalocyanines as triplet harvesting materials within organic photovoltaics. *The Journal of Physical Chemistry Letters*. 2015;**6**:3121-3125. DOI: 10.1021/acs.jpcllett.5b01254

[29] Josey DS, Castrucci JS, Dang JD, Lessard BH, Bender TP. Evaluating thiophene electron-donor layers for the rapid assessment of boron subphthalocyanines as electron acceptors in organic photovoltaics: Solution or vacuum deposition? *A European Journal of Chemical Physics and Physical Chemistry*. 2015;**16**:1245-1250. DOI: 10.1002/cphc.201402751

[30] Cnops K, Zango G, Genoe J, Heremans P, Martinez-Diaz MV, Torres T, et al. Energy level tuning of non-fullerene acceptors in organic solar cells. *Journal of the American Chemical Society*. 2015;**137**:8991-8997. DOI: 10.1021/jacs.5b02808

[31] Zango G, Sakurai T, Urones B, Saeki H, Matsuda W, Martinez-Diaz MV, et al. Peripherally cyanated subphthalocyanines as potential n-type organic semiconductors. *Chemistry-A European Journal*. 2018;**24**: 8331-8342. DOI: 10.1002/chem.201801190

[32] Huang X, Hu M, Zhao X, Li C, Yuan Z, Liu X, et al. Subphthalocyanine triimides: Solution processable bowl-shaped acceptors for bulk heterojunction solar cells. *Organic*

*Letters*. 2019;**21**:3382-3386. DOI: 10.1021/acs.orglett.9b01130

[33] Hang H, Wu X, Xu Q, Chen Y, Li H, Wang W, et al. Star-shaped small molecule acceptors with a subphthalocyanine core for solution-processed non-fullerene solar cells. *Dyes and Pigments*. 2019;**160**:243-251. DOI: 10.1016/j.dyepig.2018.07.050

[34] Hains AW, Liang Z, Woodhouse MA, Gregg BA. Molecular semiconductors in organic photovoltaic cells. *Chemical Reviews*. 2010;**110**:6689-6735. DOI: 10.1021/cr9002984

[35] Yunin PA, Travkin VV, Sachkov YI, Koptyaev AI, Stuzhin PA, Pakhomov GL. Increasing efficiency of hybrid p-CuI/n-Cl<sub>6</sub>SubPc heterojunction through the interface engineering. *Applied Surface Science*. submitted

[36] Bredas JL. Mind the gap! *Materials Horizons*. 2014;**1**:17-19. DOI: 10.1039/c3mh00098b

[37] Morse GE, Paton AS, Lough A, Bender TP. Chloro boron subphthalocyanine and its derivatives: Dyes, pigments or somewhere in between? *Dalton Transactions*. 2010;**39**:3915-3922. DOI: 10.1039/b922199a

[38] Ma B, Miyamoto Y, Woo CH, Fréchet JM, Zhang F, Liu Y. Solution processable boron subphthalocyanine derivatives as active materials for organic photovoltaics. In: *Proceedings of the SPIE; 7416 Organic Photovoltaics X*. 2009. p. 74161E. DOI: 10.1117/12.825372

[39] Chen G, Sasabe H, Sano T, Wang X-F, Hong Z, Kido J, et al. Chloroboron (III) subnaphthalocyanine as an electron donor in bulk heterojunction photovoltaic cells. *Nanotechnology*. 2013;**24**:484007. DOI: 10.1088/0957-4484/24/48/484007



- [40] Verreet B, Müller R, Rand BP, Vasseur K, Heremans P. Structural templating of chloro-aluminum phthalocyanine layers for planar and bulk heterojunction organic solar cells. *Organic Electronics*. 2011;**12**:2131-2139. DOI: 10.1016/j.orgel.2011.08.031
- [41] Trinh C, Kirlikovali KO, Bartynski AN, Tassone CJ, Toney MF, Burkhard GF, et al. Efficient energy sensitization of C<sub>60</sub> and application to organic photovoltaics. *Journal of the American Chemical Society*. 2013;**135**:11920-11928. DOI: 10.1021/ja4043356
- [42] Cnops K, Rand BP, Cheyng D, Verreet B, Empl MA, Heremans P. 8.4% efficient fullerene-free organic solar cells exploiting long-range exciton energy transfer. *Nature Communications*. 2014;**5**:3406. DOI: 10.1038/ncomms4406
- [43] Wild M, Berner S, Suzuki H, Yanagi H, Schlettwein D, Ivan S, et al. A novel route to molecular self-assembly: Self-intermixed monolayer phases. *A European Journal of Chemical Physics and Physical Chemistry*. 2002;**3**:881-885. DOI: 10.1002/1439-7641(20021018)3:10<881:AID-CPHC881>3.0.CO;2-P
- [44] Pandey R, Gunawan AA, Mkhoyan KA, Holmes RJ. Efficient organic photovoltaic cells based on nanocrystalline mixtures of boron subphthalocyanine chloride and C<sub>60</sub>. *Advanced Functional Materials*. 2012;**22**:617-624. DOI: 10.1002/adfm.201101948
- [45] Huang Y, Kramer EJ, Heeger AJ, Bazan GC. Bulk heterojunction solar cells: morphology and performance relationships. *Chemical Reviews*. 2014;**114**:7006-7043. DOI: 10.1021/cr400353v
- [46] Drozdov MN, Drozdov YN, Pakhomov GL, Travkin VV, Yunin PA, Razumov VF. Depth profiling of fullerene-containing structures by time-of-flight secondary ion mass spectrometry. *Technical Physics Letters*. 2013;**39**:1097-1100. DOI: 10.1134/S1063785013120183
- [47] Chen WX, Xu ZD, Li WZ. Photoconductivity of C<sub>60</sub>-doped phthalocyanine composites. *Journal of Photochemistry and Photobiology, A: Chemistry*. 1995;**88**:179-182. DOI: 10.1016/1010-6030(94)03999-B
- [48] Chen ZH, Xie YM, Li J, Zhan MX. Studies on the formation of charge transfer complex between fullerene and zinc phthalocyanine. *Chemical Journal of Chinese Universities*. 1997;**18**:1534-1536. Available from: <http://www.cjcu.jlu.edu.cn/EN/Y1997/V18/I9/1534>
- [49] Ruani G, Dediu V, Liess M, Lunedei E, Michel R, Muccini M, et al. Photoinduced charge transfer in complex architected films of C<sub>60</sub> and donor-like molecules. *Synthetic Metals*. 1999;**103**:2392-2394. DOI: 10.1016/S0379-6779(98)00297-5
- [50] Ruani G, Fontanini C, Murgia M, Taliani C. Weak intrinsic charge transfer complexes: A new route for developing wide spectrum organic photovoltaic cells. *The Journal of Chemical Physics*. 2002;**116**:1713-1719. DOI: 10.1063/1.1429235
- [51] Maennig B, Drechsel J, Gebeyehu D, Simon P, Kozlowski F, Werner A, et al. Organic p-i-n solar cells. *Applied Physics A*. 2004;**79**:1-14. DOI: 10.1007/s00339-003-2494-9
- [52] Meiss J, Merten A, Hein M, Schuenemann C, Schäfer S, Tietze M, et al. Fluorinated zinc phthalocyanine as donor for efficient vacuum-deposited organic solar cells. *Advanced Functional Materials*. 2012;**22**:405-414. DOI: 10.1002/adfm.201101799

- [53] Pfuetzner S, Mickel C, Jankowski J, Hein M, Meiss J, Schuenemann C, et al. The influence of substrate heating on morphology and layer growth in C<sub>60</sub>:ZnPc bulk heterojunction solar cells. *Organic Electronics*. 2011;12:435-441. DOI: 10.1016/j.orgel.2010.12.007
- [54] Gilchrist JB, Basey-Fisher TH, Chang S, Scheltens F, McComb DW, Heutz S. Uncovering buried structure and interfaces in molecular photovoltaics. *Advanced Functional Materials*. 2014;24:6473-6483. DOI: 10.1002/adfm.201400345
- [55] Simon P, Maennig B, Lichte H. Conventional electron microscopy and electron holography of organic solar cells. *Advanced Functional Materials*. 2004;14:669-676. DOI: 10.1002/adfm.200304498
- [56] Ferro VR, Garcia VJM, Claessens CG, Poveda LA, Gonzalez-Jonte RH. The axial coordination in subphthalocyanines. Geometrical and electronic aspects. *Journal of Porphyrins and Phthalocyanines*. 2001;5:491-499. DOI: 10.1002/jpp.338
- [57] Ferro VR, Poveda LA, Gonzalez-Jonte RH, VJM G, Torres T, del Rey B. Molecular electronic structure of subphthalocyanine macrocycles. *Journal of Porphyrins and Phthalocyanines*. 2000;4:611-620. DOI: 10.1002/1099-1409(200009/10)4:6<611::AID-JPP230>3.0.CO;2-A
- [58] Waters MJ, Hashemi D, Shi G, Kioupakis E, Kieffer J. Predictive simulations for tuning electronic and optical properties of SubPc derivatives. *Journal of Electronic Materials*. 2019;48:2962-2970. DOI: 10.1007/s11664-019-06961-w
- [59] Morris SE, Bilby D, Sykes ME, Hashemi H, Waters MJ, Kieffer J, et al. Effect of axial halogen substitution on the performance of subphthalocyanine based organic photovoltaic cells. *Organic Electronics*. 2014;15:3660-3665. DOI: 10.1016/j.orgel.2014.09.048
- [60] Isaacs EB, Sharifzadeh S, Ma B, Neaton JB. Relating trends in first-principles electronic structure and open-circuit voltage in organic photovoltaics. *The Journal of Physical Chemistry Letters*. 2011;2:2531-2537. DOI: 10.1021/jz201148k
- [61] Linares M, Beljonne D, Cornil J, Lancaster K, Bredas JL, Verlaak S, et al. On the interface dipole at the pentacene-fullerene heterojunction: A theoretical study. *The Journal of Physical Chemistry C*. 2010;114:3215-3224. DOI: 10.1021/jp910005g
- [62] Breuer T, Karthäuser A, Witte G. Effects of molecular orientation in acceptor-donor interfaces between pentacene and C<sub>60</sub> and diels-alder adduct formation at the molecular interface. *Advanced Materials Interfaces*. 2016;3:1500452. DOI: 10.1002/admi.201500452
- [63] Rand BP, Richter H, editors. *Organic Solar Cells: Fundamental, Devices and Upscaling*. 1st ed. Boca Raton: CRC press, Taylor & Francis Group; 2014. 810p. DOI: 10.1201/b17301
- [64] Gommans H, Aernouts T, Verreert B, Heremans P, Medina A, Claessens CG, et al. Perfluorinated subphthalocyanine as a new acceptor material in a small-molecule bilayer organic solar cell. *Advanced Functional Materials*. 2009;19:3435-3439. DOI: 10.1002/adfm.200900524
- [65] Sai N, Gearba R, Dolocan A, Tritsch JR, Chan WL, Chelikowsky JR, et al. Understanding the interface dipole of copper phthalocyanine (CuPc)/C<sub>60</sub>: Theory and experiment. *The Journal of Physical Chemistry Letters*. 2012;3:2173-2177. DOI: 10.1021/jz300744r
- [66] Duan C, Guzmán D, Colberts FJM, Janssen RAJ, Torres T.

Subnaphthalocyanines as electron acceptors in polymer solar cells: Improving device performance by modifying peripheral and axial substituents. *Chemistry–A European Journal*. 2018;**24**:6339-6343. DOI: 10.1002/chem.201800596

[67] Dang JD, Josey DS, Lough AJ, Li Y, Sifate A, Luc ZH, et al. The mixed alloyed chemical composition of chloro-(chloro)n-boron subnaphthalocyanines dictates their physical properties and performance in organic photovoltaic devices. *Journal of Materials Chemistry A*. 2016;**4**:9566-9577. DOI: 10.1039/C6TA02457B

[68] Stuzhin PA, Skvortsov IA, Zhabanov YA, Somov NV, Razgonyaev OV, Nikitin IA, et al. Subphthalocyanine azaanalogues–Boron(III) subporphyrazines with fused pyrazine fragments. *Dyes and Pigments*. 2019;**162**:888-897. DOI: 10.1016/j.dyepig.2018.11.006

[69] Wang Y, Uchihara K, Mori S, Furuta H, Shimizu S. 1,3-Dithiole-2-one-fused subphthalocyanine and subporphyrazine: Synthesis and properties arising from the 1,3-Dithiole-2-one units. *Organic Letters*. 2019;**21**:3103-3107. DOI: 10.1021/acs.orglett.9b00752