Chapter

Triboelectric Nanogenerators: Design, Fabrication, Energy Harvesting, and Portable-Wearable Applications

Venkateswaran Vivekananthan, Arunkumar Chandrasekhar,
Nagamalleswara Rao Alluri, Yuvasree Purusothaman,
Gaurav Khandelwal and Sang-Jae Kim

Abstract

Scavenging energy from our day-to-day activity into useful electrical energy be the best solution to solve the energy crisis. This concept entirely reduces the usage of batteries, which have a complex issue in recycling and disposal. For electrical harvesting energy from vibration energy, there are few energy harvesters available, but the fabrication, implementation, and maintenances are quite complicated. Triboelectric nanogenerators (TENG) having the advantage of accessible design, less fabrication cost, and high energy efficiency can replace the battery in low-power electronic devices. TENGs can operate in various working modes such as contact-separation mode, sliding mode, single-electrode mode, and free-standing mode. The design of TENGs with the respective operating modes employed in generating electric power as well as can be utilized as a portable and wearable power source. The fabrication of triboelectric layers with micro-roughness could enhance the triboelectric charge generation. The objective of this chapter is to deal with the design of triboelectric layers, creating micro structured roughness using the soft-lithographic technique, fabrication of TENGs using different working modes, energy harvesting performance analysis, powering up commercial devices (LEDs, displays, and capacitors), and portable-wearable applications.

Keywords: triboelectric nanogenerators, micro-roughness, soft-lithography, TENG working modes, portable-wearable

1. Introduction

In the last few decades, the boom in consumer electronics rapidly creates the need for a sustainable portable and wearable power source. There are too many low-power electronic devices that are introduced to enhance the quality of our life, such as sensors, communication devices, GPS devices, implantable, and health monitoring devices [1–4]. All these electronic gadgets require electric power in the range of few microwatts to milliwatts. With the invention of batteries, these devices can use in various portable applications. However, the drawback in batteries limits the purpose and be an obstacle to miniaturize the sensors. As per the batteries in concern, the batteries require periodical replacement, and the recycling of batteries is still a significant challenge. The precursor used for the fabrication of the batteries is highly hazards to human life and creates pollution to the environment [5]. The disposal has many concerns regarding soil and water contamination as they contain a lot of heavy metals. The future of electronics depends on the portable and wearable sensors such as flexible electronics [6, 7], e-skin-based sensor devices [8], and implantable bio-medical electronic systems [9]. Operating the low-power electronic devices, a sustainable and highly reliable power source is required. The power sources should scavenge power from waste mechanical energy. The majority of energy that we consume today is from many nonrenewable sources such as thermal power plants that operate on coal, and diesel power plants operating with the help of oil. These natural resources are limited in supply, and it takes thousands of years to regenerate. The usage of fossil fuels such as coal and oil in the generation of electricity creates massive pollution, and it leads to the reduction of life span to humans. To overcome this issue, an alternative energy harvesting approach had been introduced across the globe to protect humanity and overcome the growing energy crisis.

The conventional approach to generate electrical energy is by using an electromagnetic generator (EMG). These generators harvest effectively under the high frequency of mechanical energy inputs [10]. However, there is an abundant low-frequency mechanical energy around the globe as well as from various sources such as vibration, wind, water wave, human motions, and vehicle motions. These low-frequency motions cannot be harvested effectively using an EMG. The solution to this problem addressed in 2006 with the invention of nanogenerators (NGs) [11]. The NGs with various classifications and effects such as piezoelectric nanogenerator (PNG) [12–15], triboelectric nanogenerator (TENG) [16], thermoelectric generator (TEG) [17], and pyroelectric generator (PYG) [18] had been introduced in the past decades for a variety of energy harvesting and self-powered applications.

Furthermore, the energy harvesters are performing some real-time applications by integrating it with battery or other storage devices. Apart from energy harvesting, these NG can work as a self-powered sensors such as pH sensors [19], glucose sensors [20], chemical sensors [21], humidity sensors [22, 23], temperature sensors [24], air pressure sensors [25], motion sensor [26], optical sensor [27, 28], and strain sensors [29]. To enhance the output power of the TENG devices, researchers across the globe performed the hybridization of these devices and studied the possibility of its use in extensive applications. To be used for a wide range of applications, TENG-PENG [30] hybrid had been reported with high instantaneous power density. Similarly, there are many reports for scavenging the water wave energy by TENG-EMG hybrid configuration [31]. The generated output is much higher and can use for GPS tracking and positioning system. A similar concept is demonstrating by using magnetic particles instead of magnets in the EMG component [32]. The motion of particles activates the triboelectric part of the hybrid device. The issues that TENGs have faced so far are its bio-compatibility, performance reduction concerning humidity. The problems rectified by introducing a biodegradable, edible TENG [33], and a fully packed water-resistant TENG. The fully packed TENG [34] can protect the device from humidity issues and maintains its performance for a more extended period. The further advancements in NGs lead to the design of flexible electronic-skin-based devices for sensing various parameters, microfluidic-based devices [35], and other portable-wearable devices making NGs a sustainable power source. This chapter covers the basics of TENG, fundamental working modes of TENG and fabrication, and energy harvesting and its application in portable and wearable technologies.

2. Working modes of TENG

The mechanism behind TENG is triboelectrification and electrostatic induction effects; with the rapid advancement in the field of nanogenerators and TENG, the exploration leads to the investigation of fundamental working modes of TENG, which covers four basic modes. The modes include a vertical contact separation mode, linear sliding mode, single-electrode mode, and free-standing mode. These modes require two different triboelectric materials with proper electrode connections with proper insulation between each layer. The combination may be either dielectric-dielectric or metal-dielectric arrangements. The basic principle behind all the four modes is that whenever there is a displacement in any of the triboelectric layers, the electrostatic charge movements break the electrostatic status present, leading to the development of potential difference between the electrodes. In the repeated mechanical actuation of layers with forward and reverse direction makes the triboelectric layer to generate forward and reverse potential between the electrodes, making the positive and negative peaks in the TENG output generating the AC signal. The four different working modes are shown schematically in **Figure 1**.

2.1 Contact separation mode

In the contact separation mode TENG, the triboelectrification occurs by the contact and separation process of two triboelectric materials or layers, as shown in **Figure 1a**. The process may either happen between two different dielectric materials or may be a dielectric and metallic layers. This model has a significant advantage with its simple design, easy fabrication, and low cost. This mode of TENG is also the first developed and demonstrated for powering low-power electronics. This mode of TENG can also make as a multi-unit stacking for the enhanced output performance.

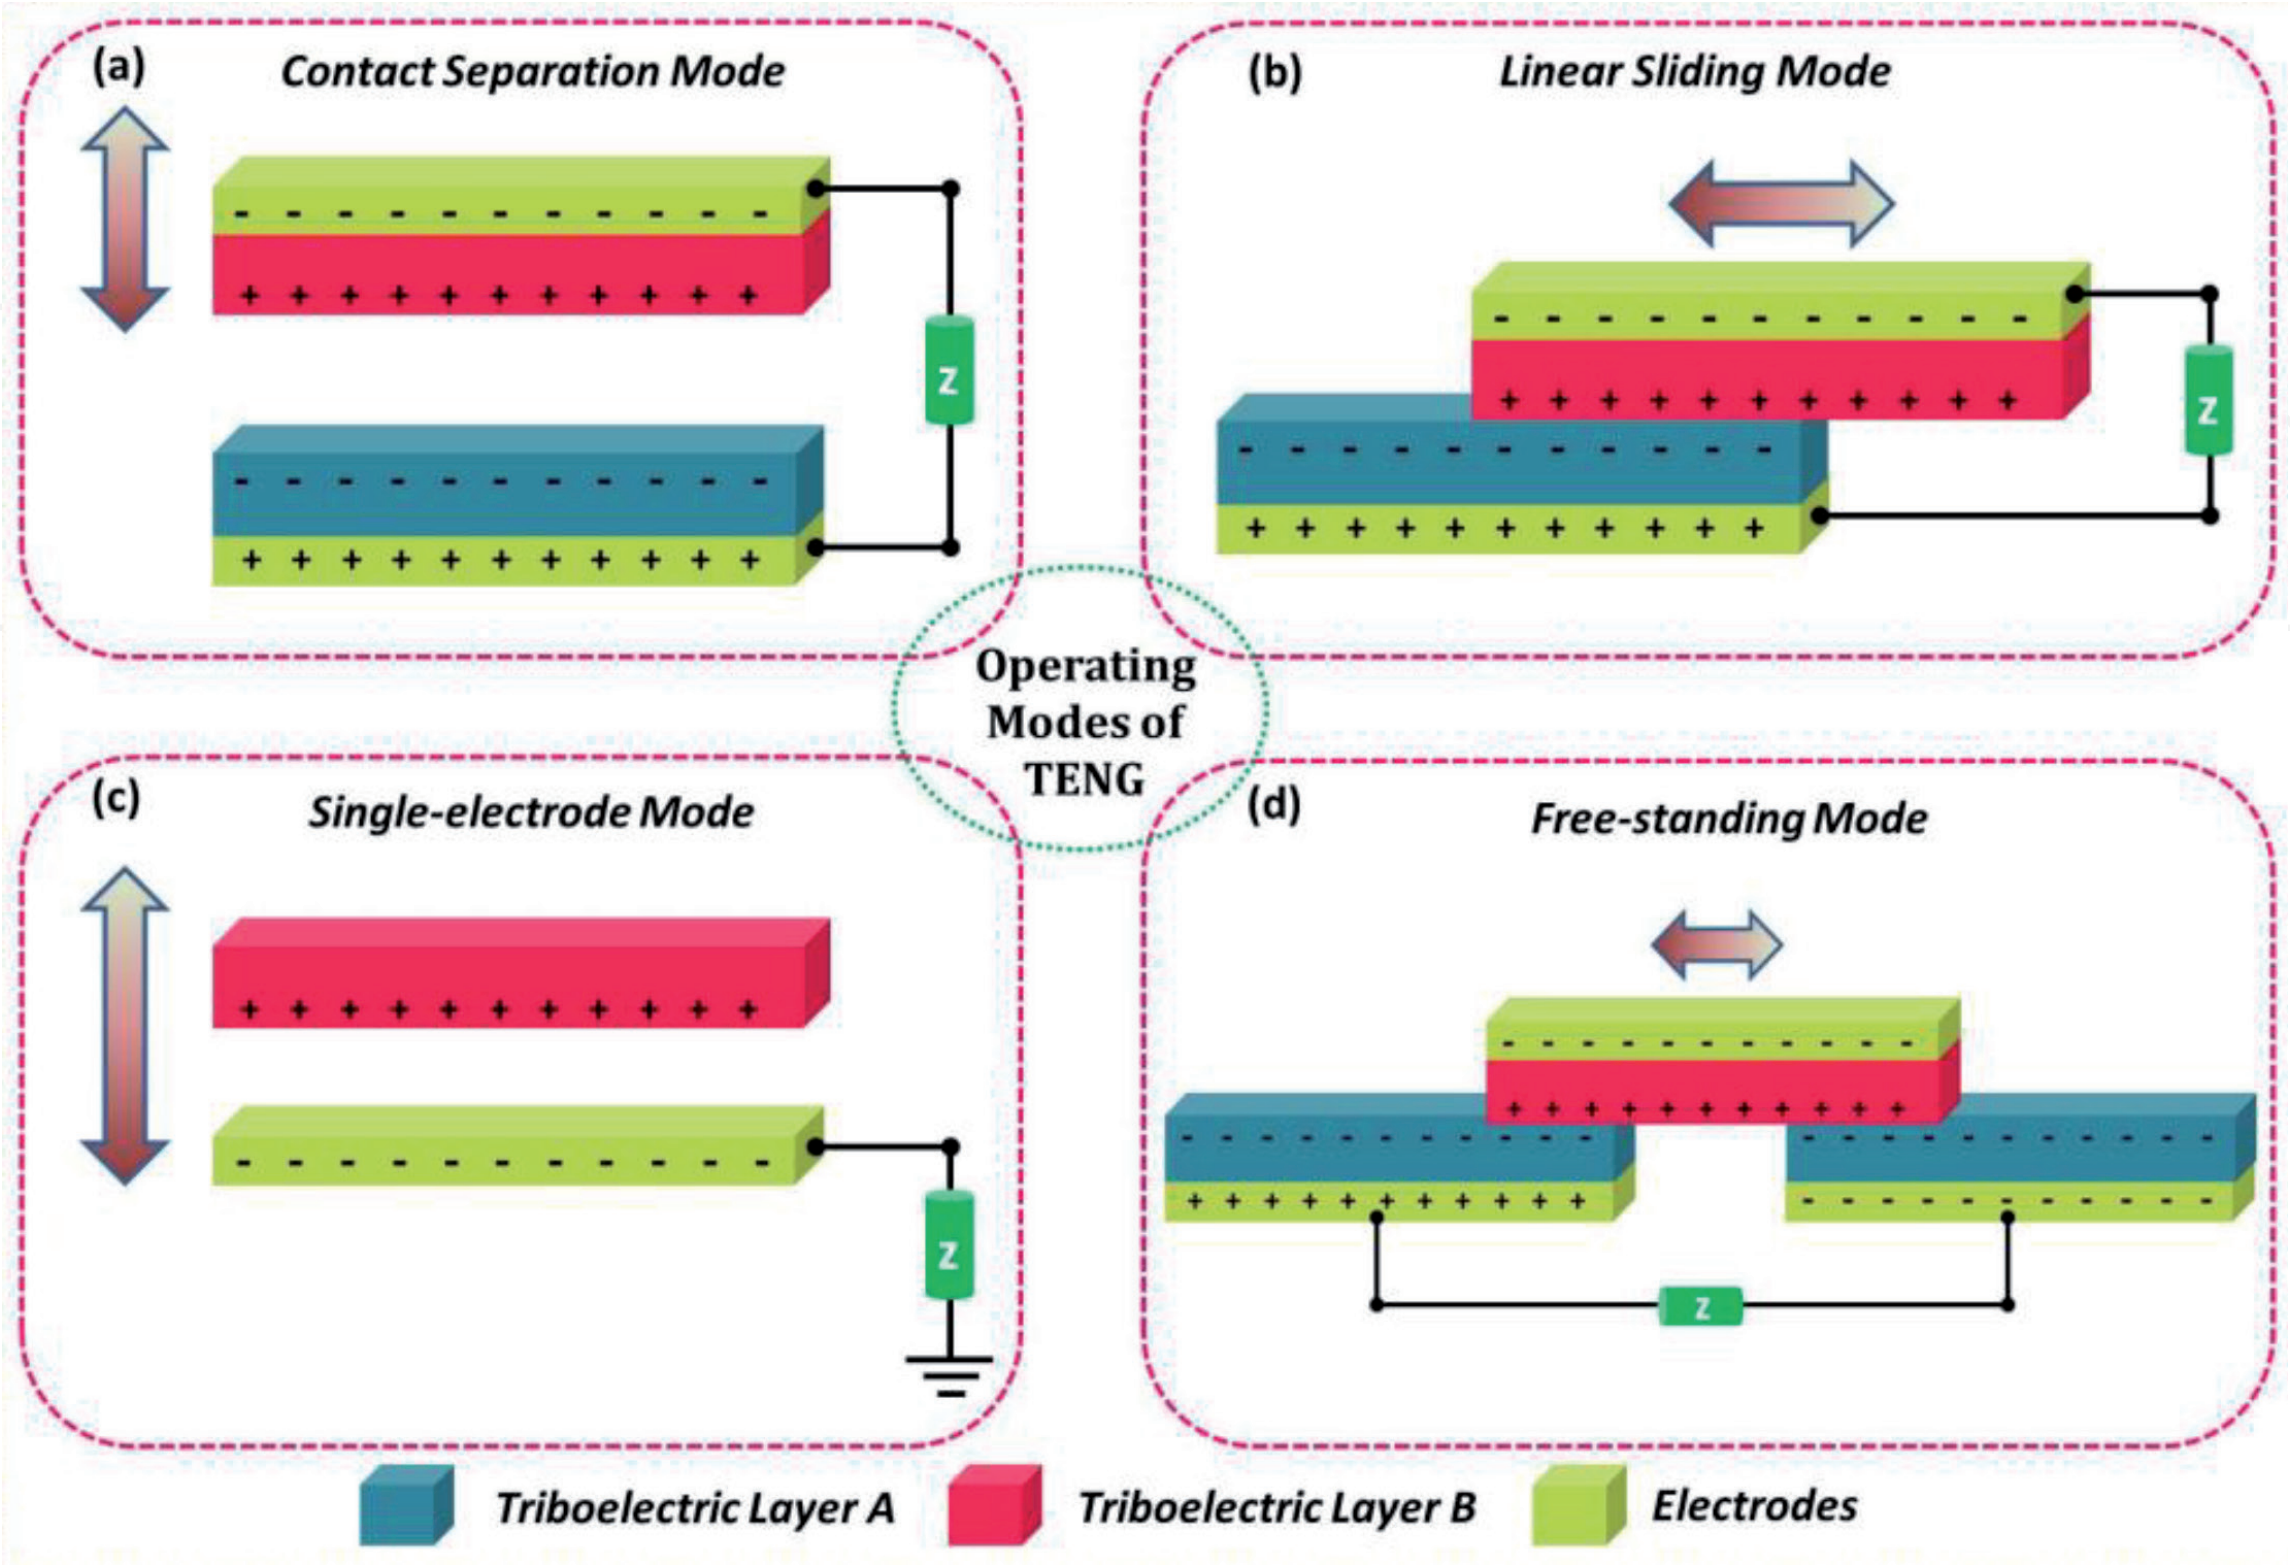

Figure 1.
Schematic representation of the four fundamental operating modes of TENG.

2.2 Linear sliding mode

In the linear sliding mode, the charge generation is by the relative to and from sliding between the layers of TENG. The construction is almost similar to the contact separation mode with electrodes attached to the back of the triboelectric layers, but the displacement is in sideward, as shown in **Figure 1b**. The sliding mode has a low figure-of-merits compared with the vertical contact separation mode due to its protracted displacement in the sliding process. The advantage of this mode is that it can generate more charge density with a highly effective charge generation due to its high contact area. Also, by introducing more grating structures, the output performance can be enhanced. The sliding mode TENG can also be able to operate rotationally with cylindrical grating structures.

2.3 Single-electrode mode

The simplest structure of TENG is the single-electrode mode TENG, but the output performance is too low due to the small charge transfer, making the generated voltage and current to be less, but it is highly suitable for self-powered applications. The advantage of this device is that it overcomes the application limitation due to the contact wire obstructing at both sides in the contact separation mode and sliding mode TENG devices. The basic arrangement of a single-electrode mode TENG is shown in **Figure 1c**.

2.4 Free-standing mode

The free-standing model has one electrode move freely between the two electrodes or triboelectric layers. The electrodes are in a static position, and a triboelectric layer without electrode can move over it. This mode of TENG device has a high figure-of-merits and has demonstrated high output efficiency and electrical output. Also, this type of device can be fabricated easily and integrated into various real-time applications. The necessary arrangement of a single-electrode mode TENG is shown in **Figure 1d**.

3. Progress in TENG

After the invention of TENG in 2012, the field becomes an extensive investigated field with a vast number of researchers working and improving it until today [36]. The first developed TENG device is a contact separation mode device with kapton and polyester as the active layers [7]. Further investigation TENG leads to the invention of other modes in 2013 [37]. The research trend on NGs started moving forward from energy harvesting to self-powered sensing and actuation. The transparent and flexible nanogenerators were fabricated and tested in the later stage with the application in e-skin and tactile sensing. The researchers' then working towards hybridizing the TENG with other energy harvesters such as PENG and EMG for scavenging wind and water wave energy efficiently and also had performed various real-time applications connected to environmental monitoring. Very recently, by adopting these explored TENG design and operation, liquid–solid interface TENGs and liquid–liquid TENGs had introduced for scavenging water droplet energy [38]. There had been a problem in TENGs and its electrical output concerning external factors such as temperature and humidity. Recently, the humidity issues got rectified by introducing a fully packed, waterproof TENG device by our group in 2019. In addition to biodegradable TENGs, an edible TENG made of regular food items

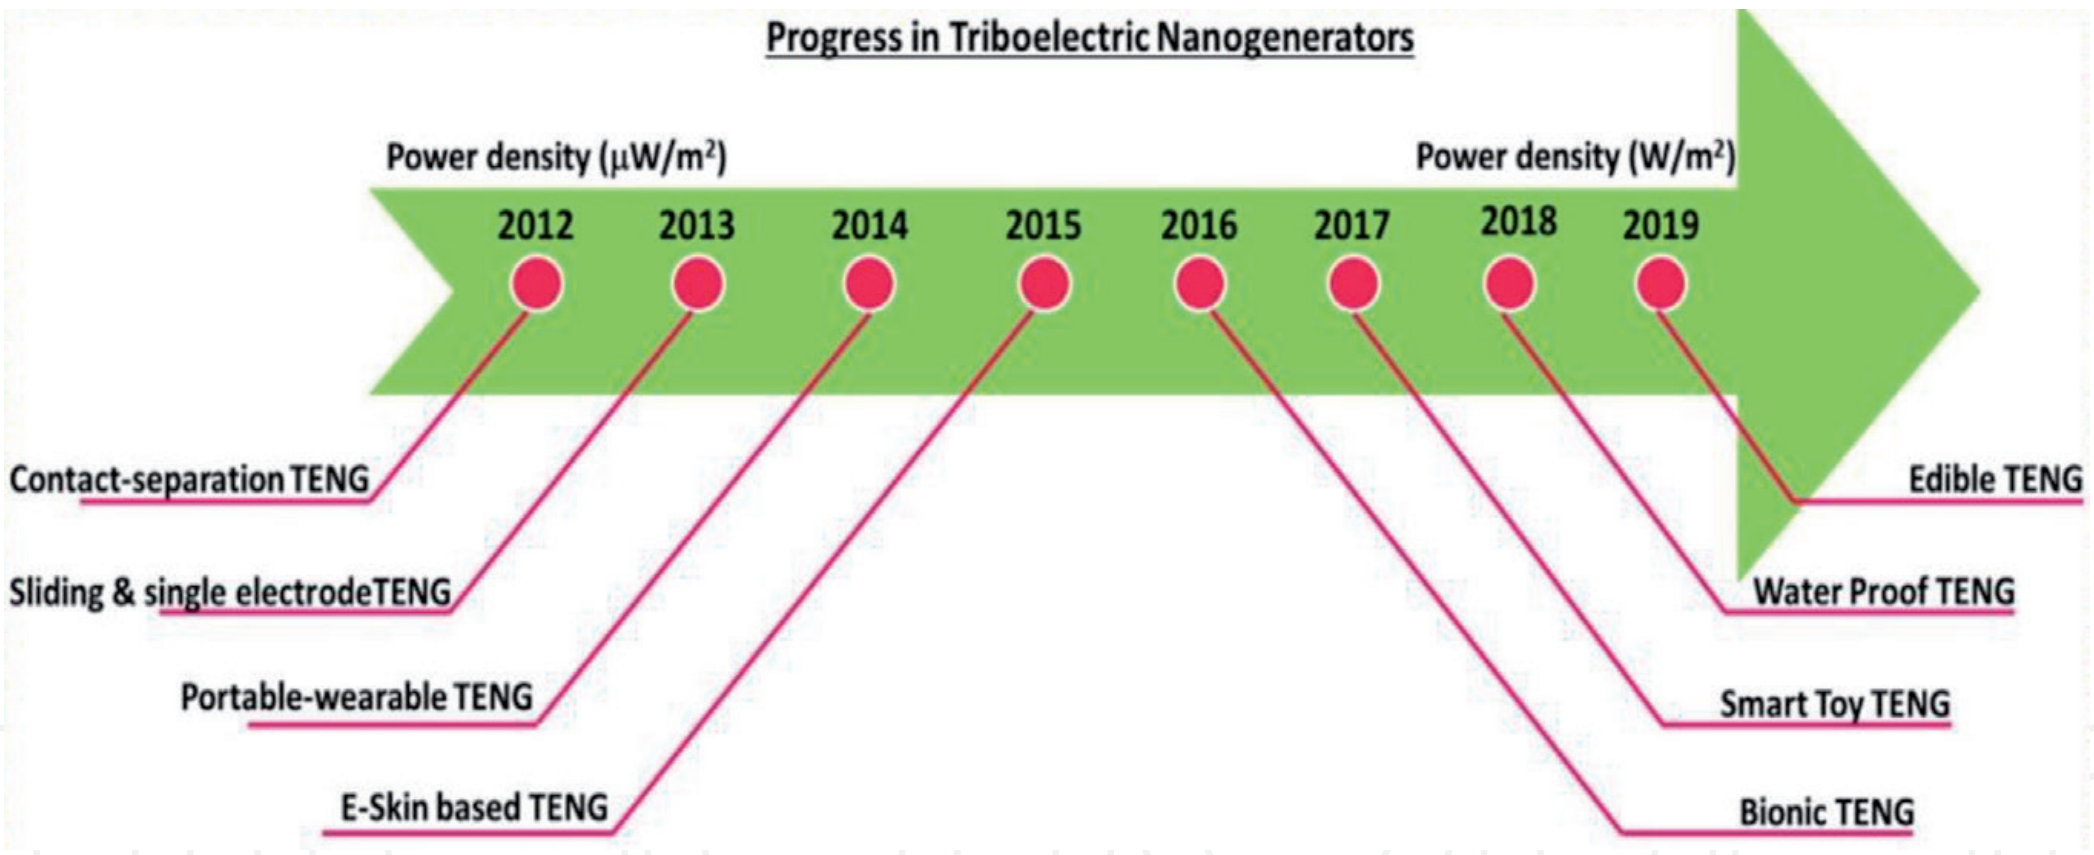

Figure 2.
Design and development of TENGs from its origin to date, with various device structures, applications, and performances.

was designed and fabricated by our group and demonstrated powering low-power electronic devices. Also, the first developed TENG device has a power density in the range of micro watts, and today, the device had reached the power density in watts. The increasing power density shows that the TENGs are reliable energy harvester and self-powered sensors which can able to commercialize shortly and to have a high possibility to replace batteries. **Figure 2** shows the road map, explaining the advancement of TENGs for various applications.

4. Fabrication of TENG device

The fabrication of a TENG device requires precise handling of the arrangement of triboelectric layers and electrodes. The improvement in the design of the TENG device is improving day-by-day. The triboelectric layer with a high surface roughness delivers high electrical output. The phenomenon is that the rough surfaces increase the contact points of the TENG device. Each micro/nano scale roughness interacts with the other triboelectric layer during its mechanical actuation. Therefore, the contact point multiplies the generated output as compared with the flat surface where the contact point is single. There are various approaches to creating surface roughness of the triboelectric layers, such as inductively coupled plasma etching, wet etching, lithographic technique, and casting. These techniques involve various advantages as well as disadvantages. The high-end lithographic and plasma etching techniques involve high-cost instruments and skilled operator, which is a disadvantage. There are various reports on simply creating surface roughness using cost-effective techniques such as using sandpaper as a mold. The sandpaper with more roughness as a mold for fabricating roughness created triboelectric layer, and the polymers such as PDMS and other silicon elastomer-based polymers poured on it, and with heat treatment, the polymer solution is then cured to form a polymeric film with microscale surface roughness. The other cost-effective technique reported is the surface modification of a used acrylonitrile butadiene styrene (ABS) polymer petri dish. The surface modification is done through wet etching using acetone as an etchant. The technique involves less time and a simple preparation process.

The ABS polymer petri dish is first washed with water and dipped in a beaker full of acetone for 90 s, as shown in **Figure 3a**, and the petri dish dried in an air atmosphere at room temperature. By this time, acetone etches the surface of the petri dish, creating micro-roughness on its surface, as shown in **Figure 3b**. The PDMS polymer is poured into the petri dish and cured in a hot air oven to get a polymeric film.

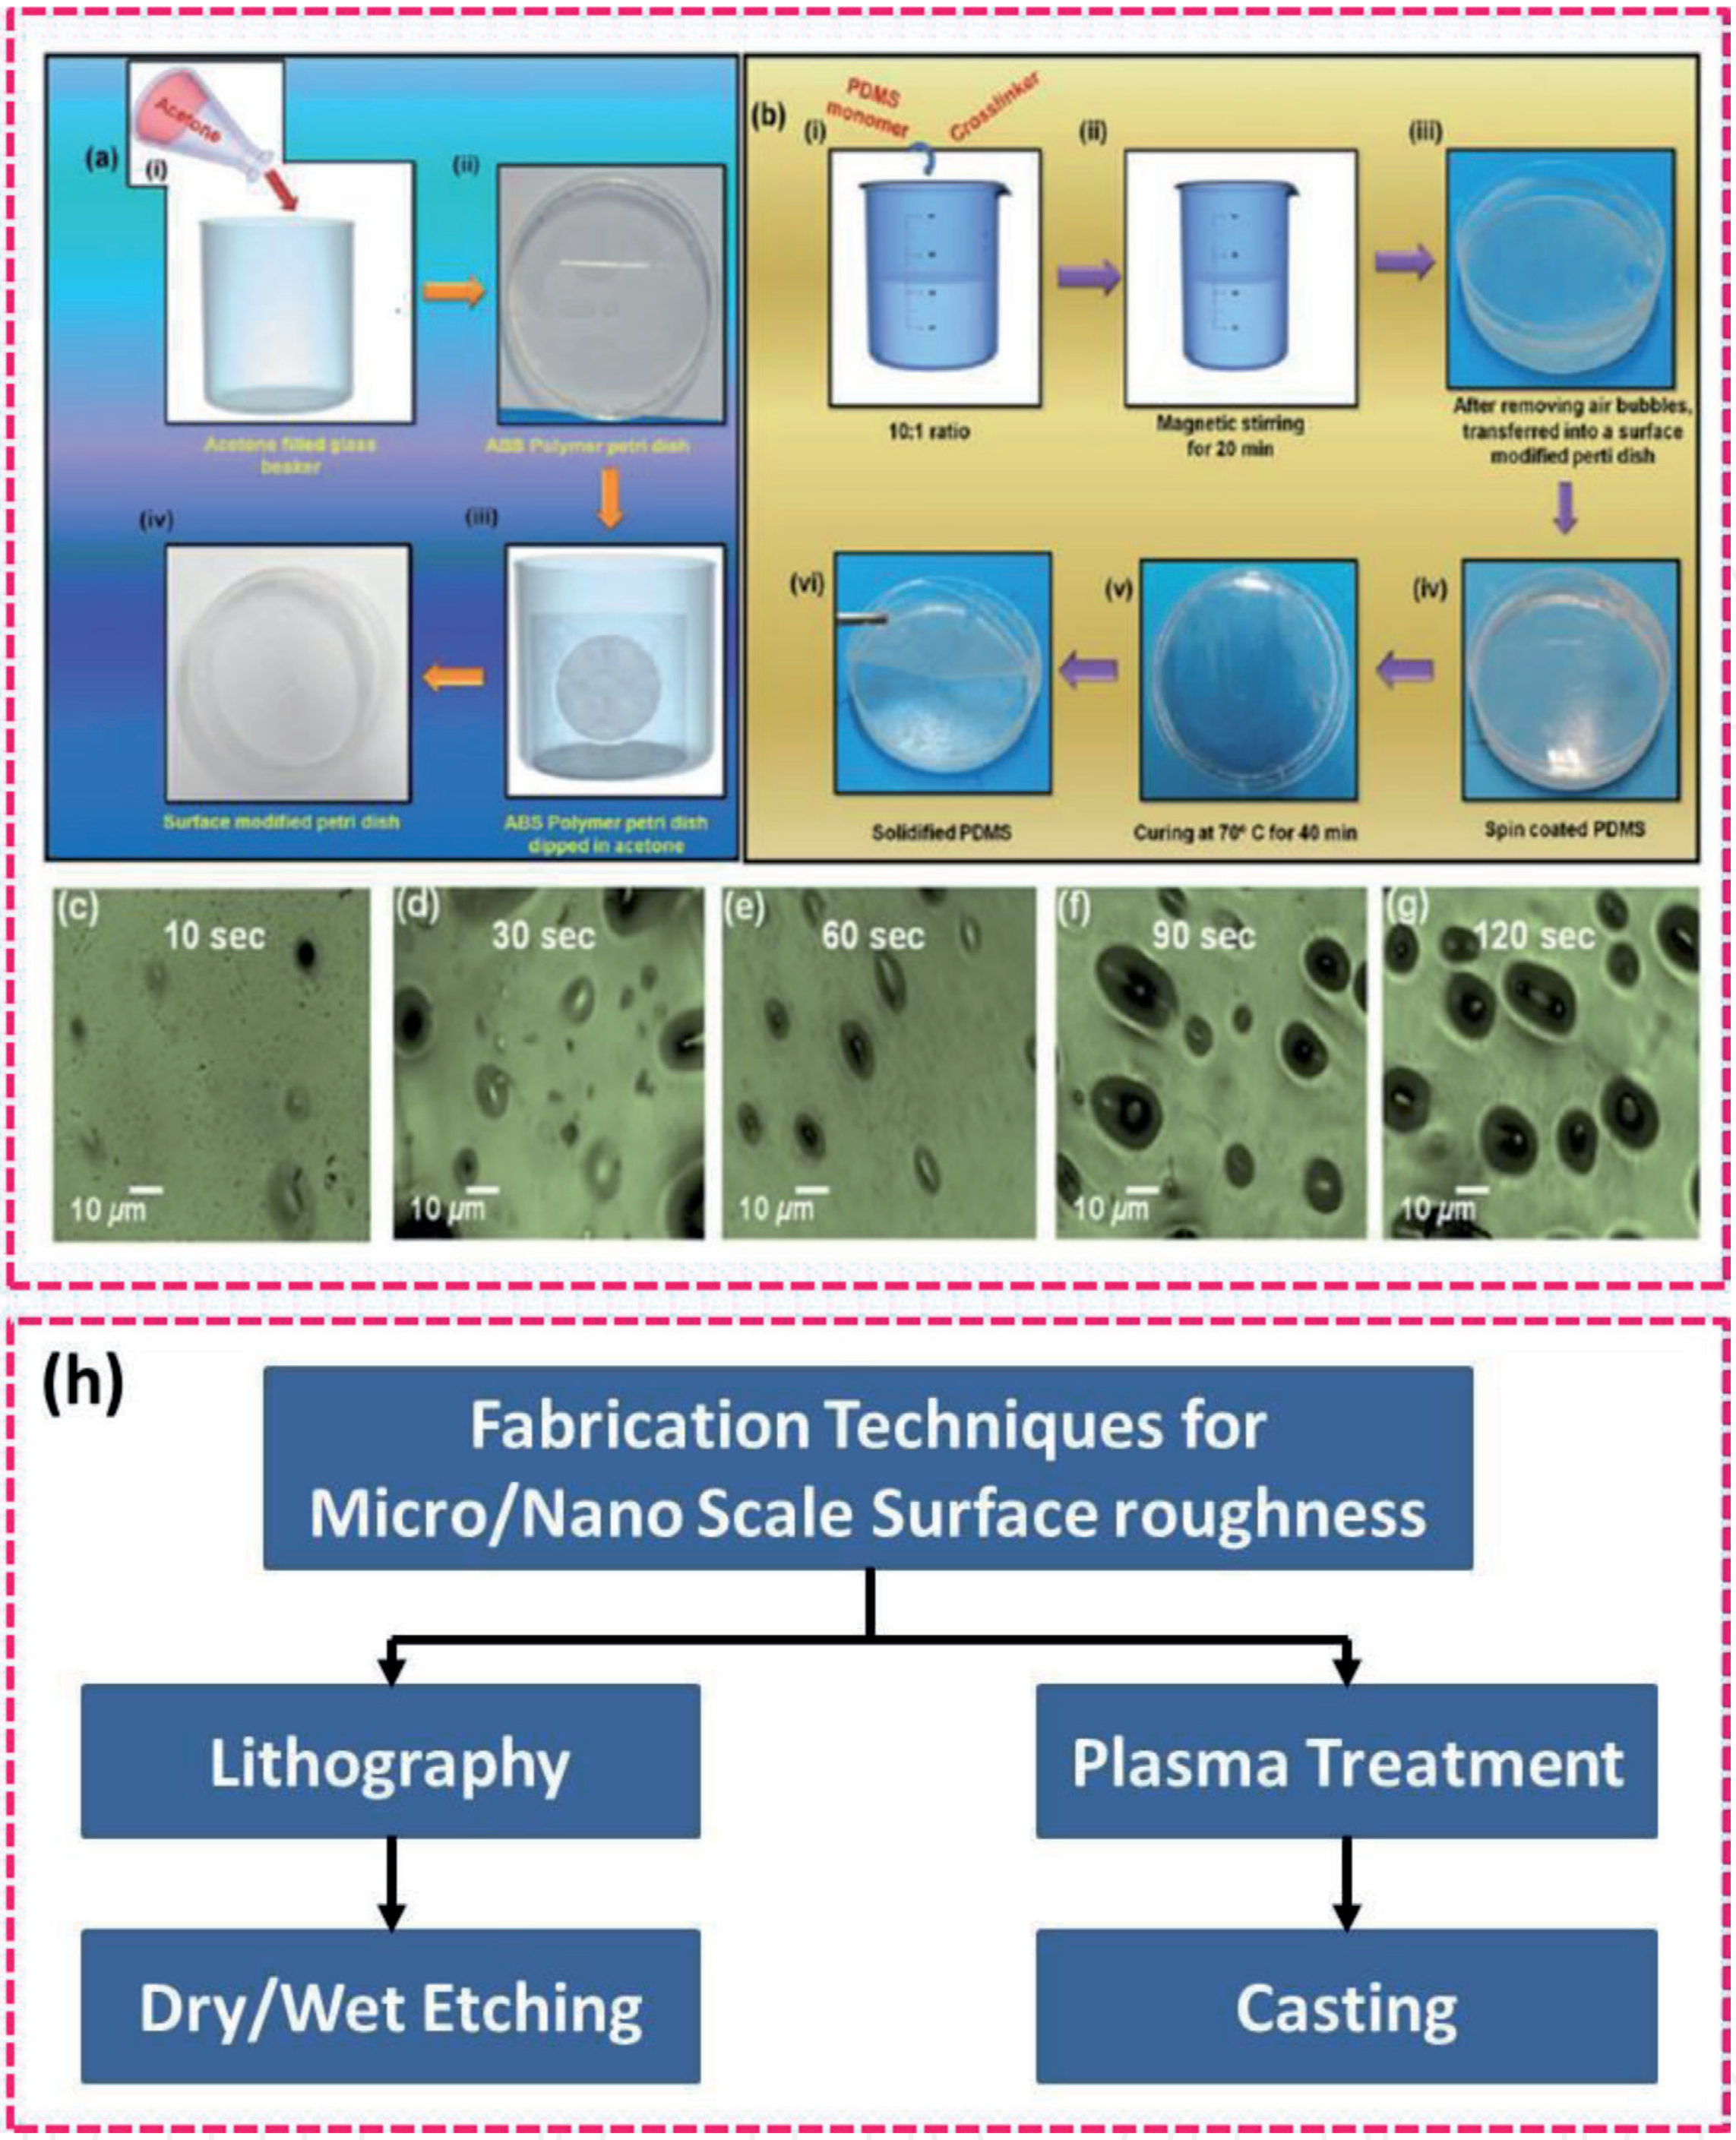

Figure 3.
(a, b) Wet etching of an ABS polymer petri dish using acetone as an etchant and fabrication of mold. The PDMS monomer is then poured on the surface-etched mold and cured to form a roughness patterned PDMS film. (c–g) FE-SEM morphology showing the surface roughness of PDMS film cured in a petri dish with different acetone treated time and their corresponding surface roughness. (h) Fabrication techniques for micro/nanoscale surface roughness [39].

Figure 3c–g shows the FE-SEM morphology of the surface of the PDMS polymer film made using roughness created petri dish mold. The petri dish with acetone treatment for a period of 90 s shows good roughness. **Figure 3h** shows the fabrication techniques involved in the fabrication of different micro or nanoscale surface roughness.

5. TENGs as a biomechanical energy harvester

The primary purpose of a TENG device is that it can harvest mechanical energy from the environment. The mechanical energy can be in any form ranging from vibration, vehicle motion, and human body motion. To scavenge the biomechanical energy and use effectively for a variety of applications, an H-TENG and SS-TENG devices report the fabrication of wearable TENG and its performance to applications. **Figure 4** shows the H-TENG device and its electrical performances with the application of an emergency exit system. The H-TENG device made up of polymeric materials by collecting the polymeric waste materials from the house garbage bin, as shown in **Figure 4a**. The positive material is cooking aluminum foil, and the harmful triboelectric materials are random plastics, and the spacer material is the utensil cleaning sponge. The entire TENG device made of household waste shows its easy fabrication and competitive cost development process. The layer-by-layer schematic of H-TENG is shown in **Figure 4b**. The statistics of plastic wastes generated and creating adverse effect to the environment is shown in **Figure 4c**. The device works on vertical contact separation mode, as shown in **Figure 4d**. The device successfully used for scavenging waste mechanical energy from the human finger, palm, hand, and leg motions, as shown in **Figure 4e** with their corresponding electrical response. The electrical output of the H-TENG device made of various polymers was measured in the laboratory using a linear motor, and their corresponding voltage and current responses are shown in **Figure 4f**. The devices were constantly powering at a maximum of 20 V/300 nA response. At last, the fabricated H-TENG device was used for an emergency exit LED lighting system, indicating the exit direction, as shown in **Figure 4g**.

In a similar approach, an SS-TENG device fabricated for scavenging biomechanical energy by placing it on the seating chair. The whole process of SS-TENG from the schematic, electrical response and applications are shown in **Figure 5**. The device consists of interdigitated electrodes (IDE) made of aluminum is attached to the bottom side of a Kapton film. The kapton film acts as a negative triboelectric layer, and the contact materials were bus cards, polyethylene cover, jeans cloth,

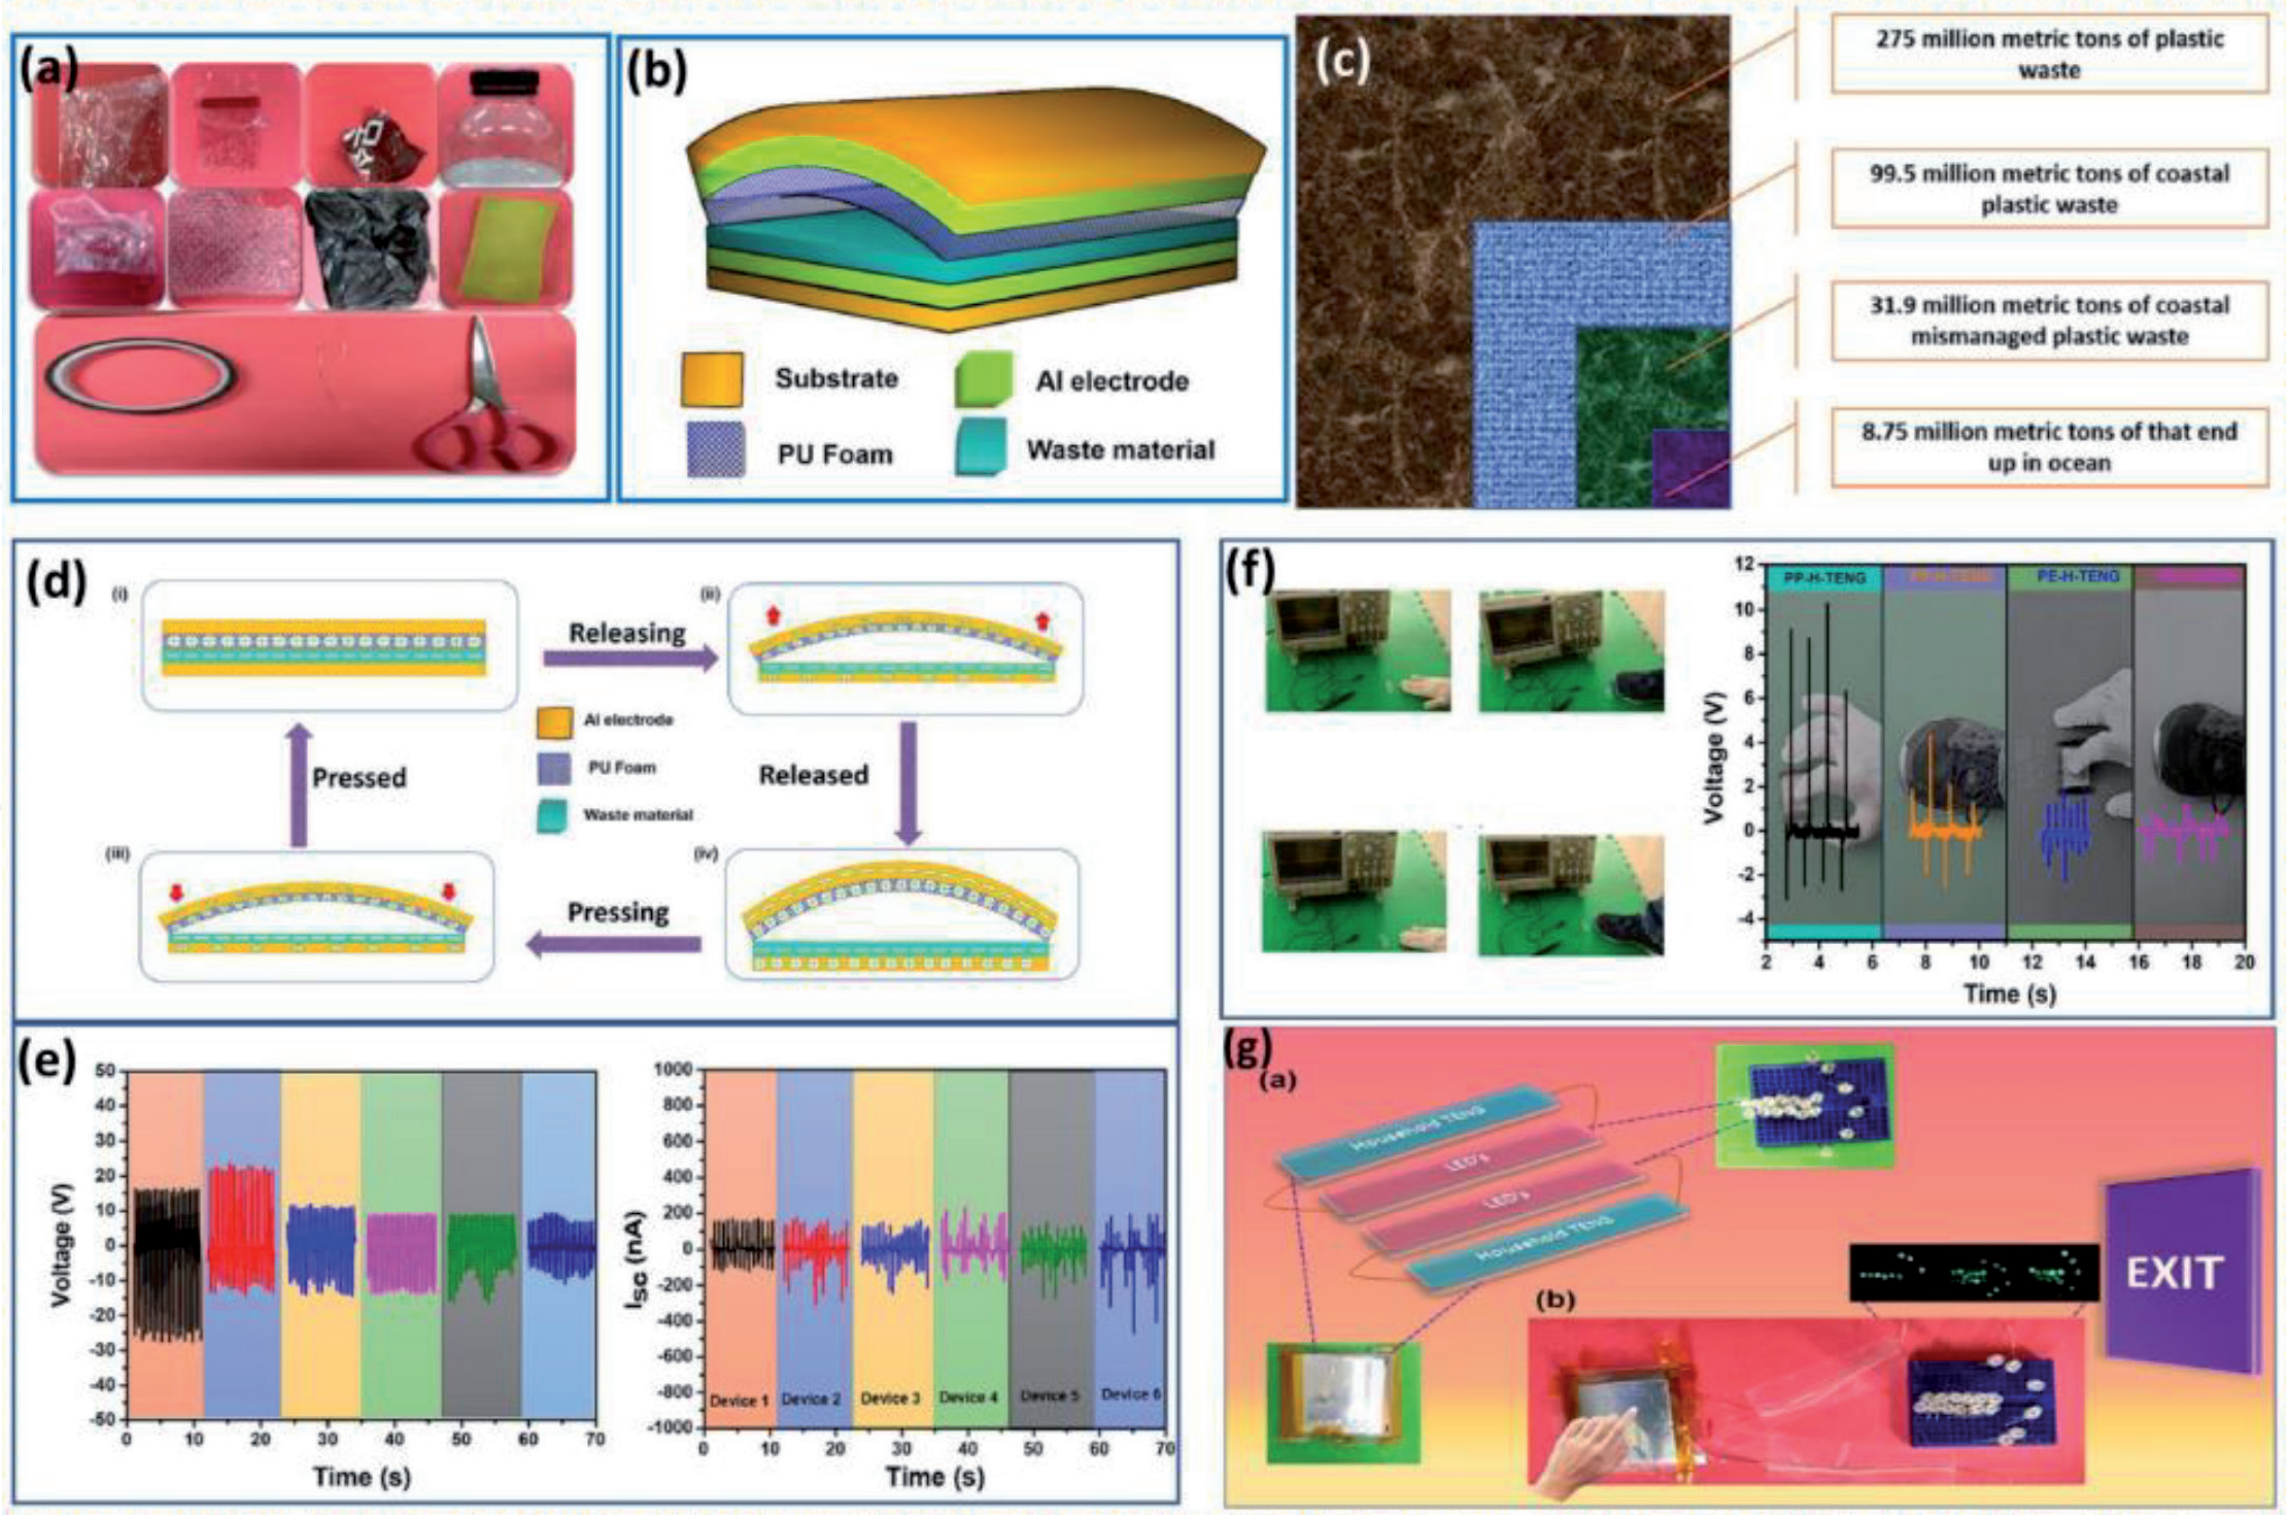

Figure 4.
(a) Fabrication materials of TENG device using recycled waste polymer wrappers from household things. (b) Schematic of the household H-TENG device. (c) Statistics of generated plastic waste all over the world. (d) Contact-separation working mechanism of H-TENG device. (e) Scavenging waste mechanical energy from H-TENG device. (f) Voltage and current response of the H-TENG devices made with different type of polymers. (g) Applications of H-TENG device showing the emergency exit with LED indication [40].

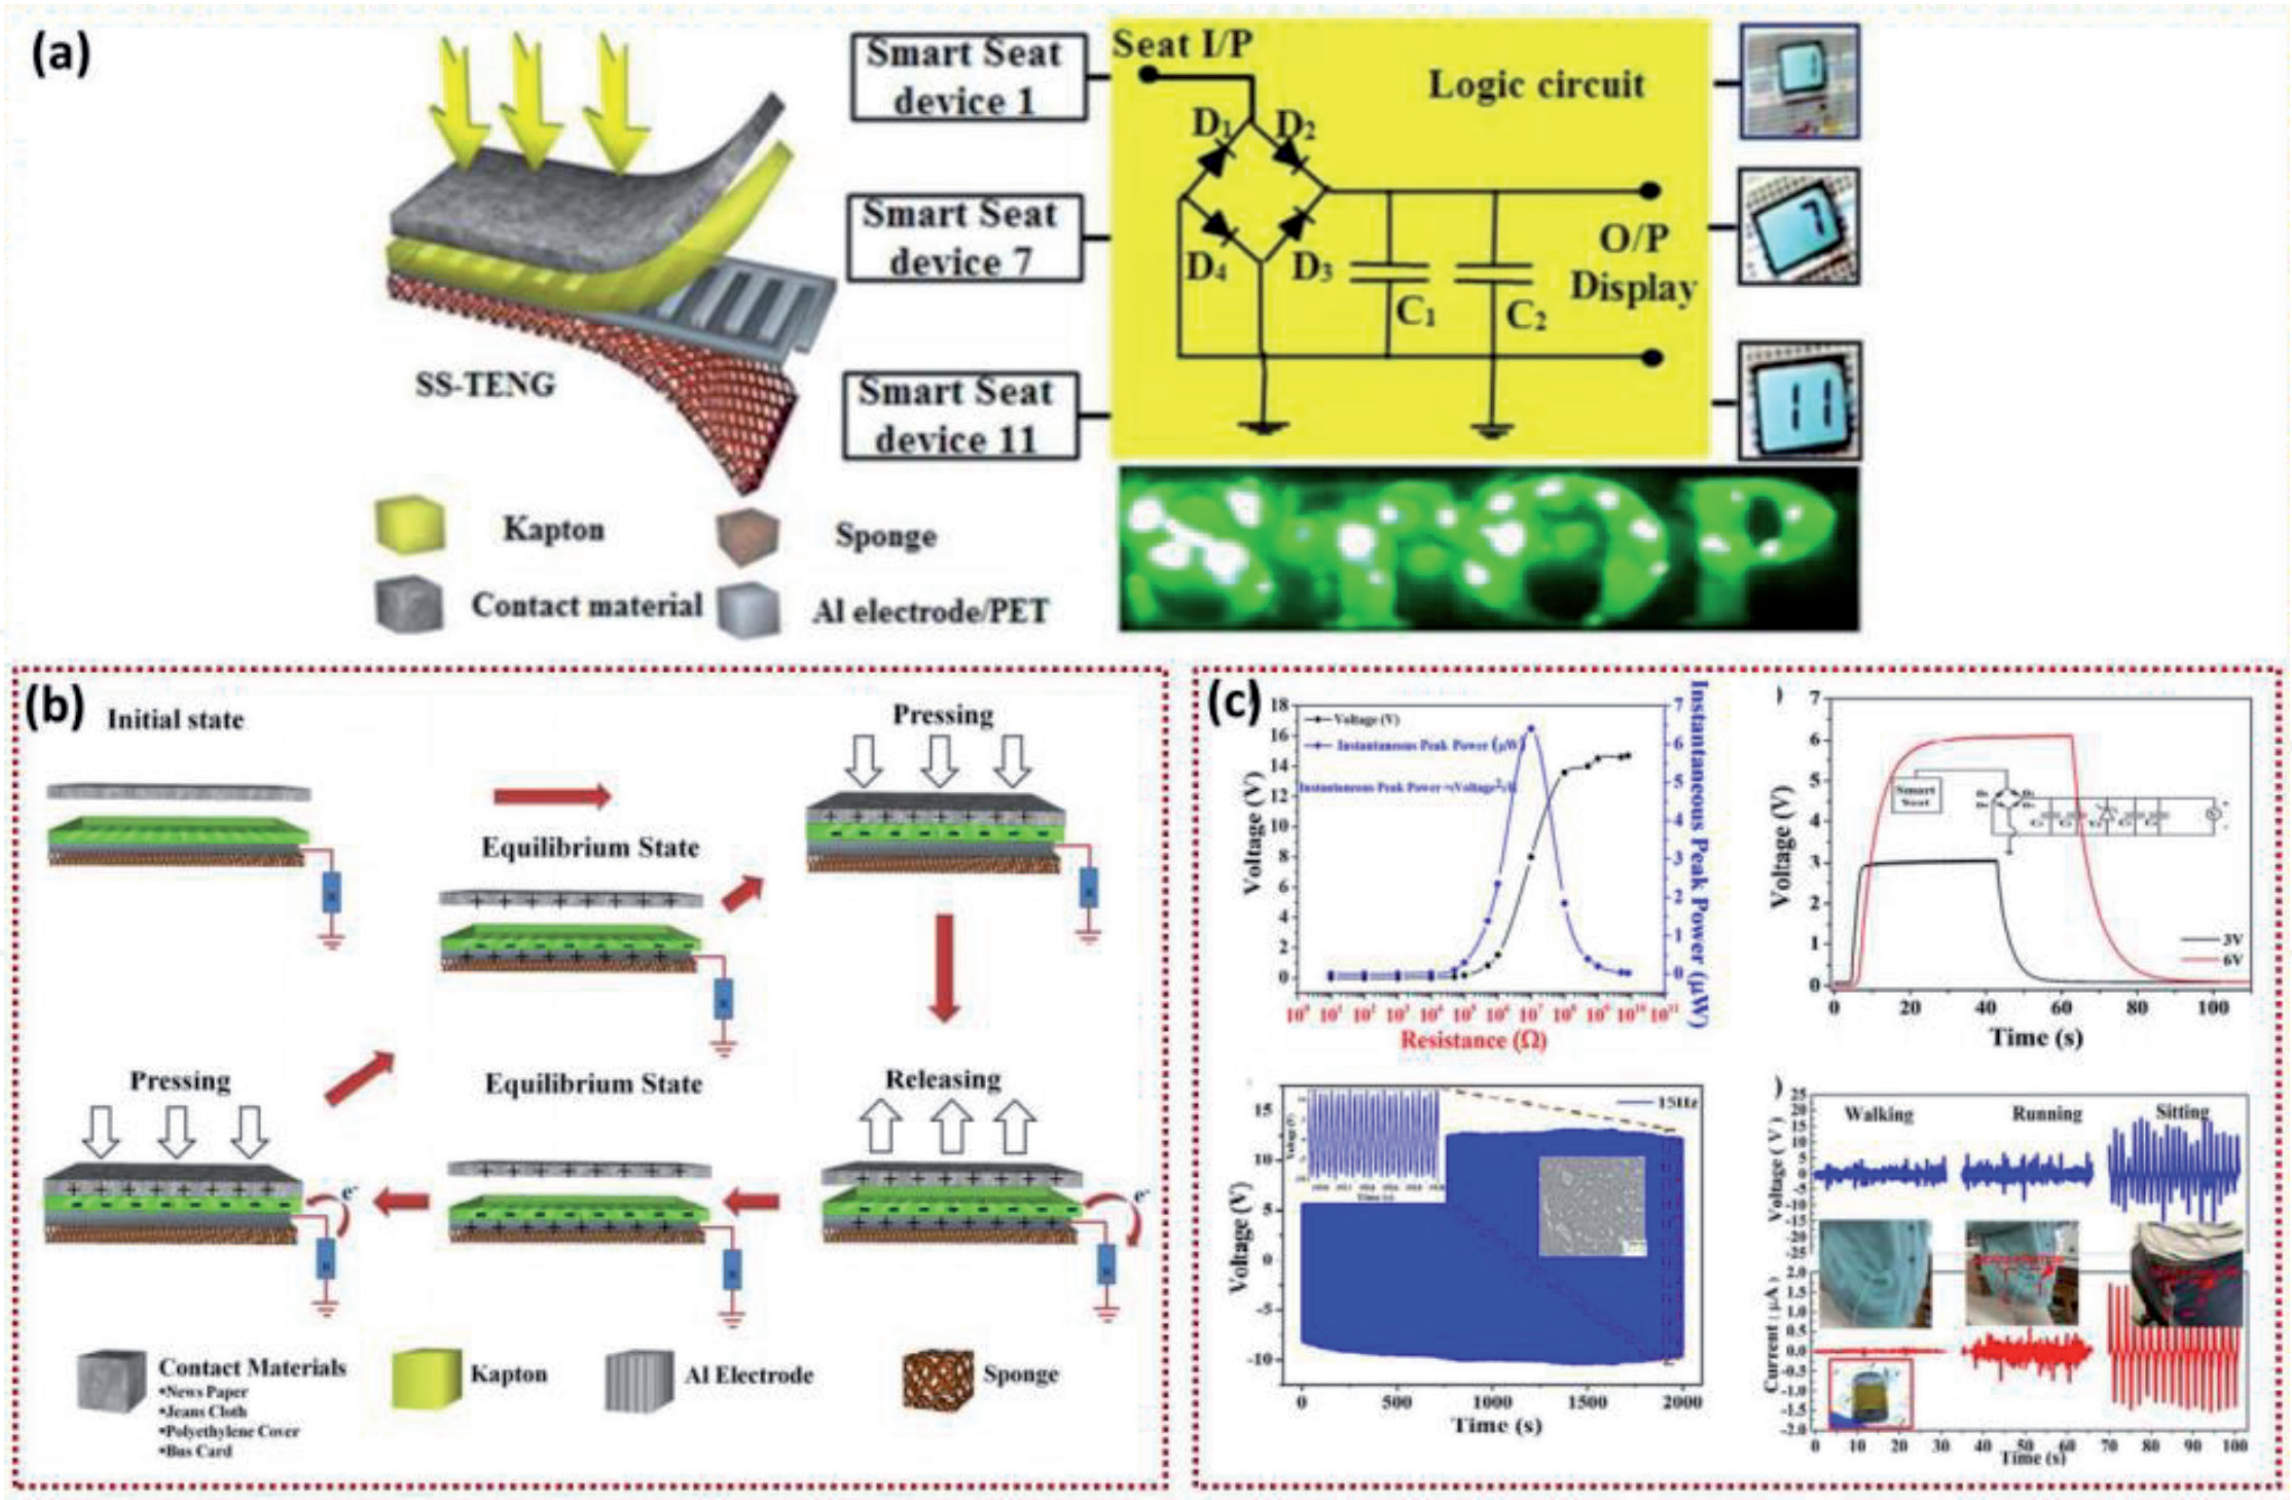

Figure 5.
(a) Schematic of SS-TENG device showing different layers and the logic circuit used for powering electronic displays and LEDs. (b) Working mechanism of SS-TENG device operating with single-electrode mode. (c) Electrical response of SS-TENG and its application as a smart seat [41].

and newspaper. The schematic of the SS-TENG device is shown in **Figure 5a**. The SS-TENG device works on a single-electrode mode triboelectrification. The working mechanism of SS-TENG device with single-electrode mode configuration is shown in **Figure 5b**. **Figure 5c** shows the electrical output response of the device showing a maximum power of 6.5 μW at 10 MΩ resistance. The device also has high stability power continuously for 2000 s without variation in the electrical response. The device is then placed in the pant pocket and measured the electrical response under walking, running, and sitting mechanical motions.

6. TENG for the portable-wearable power source

Besides scavenging biomechanical energy, TENGs can also use as a portable-wearable power sources. By making a design suitable for a portable and wearable process utilizing the appropriate working mode, TENGs can then be used for the mentioned applications. Many researchers have been working on textile-based nanogenerators for wearable applications. These devices use bio-compatible materials as triboelectric layers with the content of fabrics and making it suitable for wearable applications. The advancement in the wearable TENGs can be able to use as a wearable sensor as well as be used as a health monitoring device also. The chapter discusses a smart mobile pouch TENG (SMP-TENG) showing the portable quality of the TENG device. Along with that, a smart backpack TENG (SBP-TENG) demonstrates the energy harvesting and the wearable part.

The SMP-TENG works on the wearable part with the sliding mode. The polymeric layer made of kapton was deposited with the IDE electrode and attached in the mobile phone, which interacts with the triboelectric layer (contact materials) on the mobile pouch. The contact materials tested here are polyester, jeans, cotton, and nylon. **Figure 6a** shows the schematic of the SMP-TENG device with IDE electrode and contact materials. The working mechanism of SMP-TENG is sliding mode, with the contact materials slides over the kapton layer, as shown in **Figure 6b**. **Figure 6c** shows the electrical response of the device with contact materials. Among the four different contact materials, nylon generates a high electrical output of 150 V and 305 μA. Also, the SMP-TENG device was used to transfer the generated electrical output wirelessly using transmitter and receiver antennas.

Similarly, an SBP-TENG device also fabricated with the free-standing triboelectric made and attached to the commercial backpack. The free-standing layer here is the fabric that we wear every day. The device performance got tested with various fabric materials such as polyethylene, jeans, cloth, cotton, paper, and wool. A multi-unit SBP-TENG was constructed and attached continuously in the backpack as four units. The four devices connected in parallel electrical connection. **Figure 7a** shows the four TENG units connected in parallel, and the inset shows the backpack with TENG devices attached on the backside.

Figure 7b shows the electrical response of the device concerning the number of units connected in parallel. The voltage remains constant, and the current of the devices increases every fold with the addition of devices in parallel connection. **Figure 7c**,**d** shows the capacitor charging performance to increase in the TENG device under a parallel connection. The charging performance also increases, which is due to the high current with the increase in the number of devices. The electrical response for the weight of the bag is shown in **Figure 7e**. When the weight of the bag increases, the motion of the bag would be restricted; therefore, the electrical output of the device would decrease. The LED is flashed, as shown in **Figure 7f** and **g**, with the help of a capacitor and a switch. Whenever the bag moves, the capacitor gets charges due to the actuation of the TENG device; during the emergency times, the switch would be operated to give a flashlight.

Figure 7f shows the capacitor charging and discharging with the switch ON and OFF. The electrical response of the device under various contact materials is given in **Figure 7h** and **i**, where the wool as contact materials shows high output with the voltage of 250 V peak-to-peak and the current of 12 μA. **Figure 7j** and **k** shows the voltage and current response of wool material with the peak pattern. The force analysis of SBP-TENG at different weights of the backpack and their respective electrical responses are shown in **Figure 7l** and **m**. Finally, the real-time electrical response is shown in **Figure 7n** with the backpack worn by a person, and

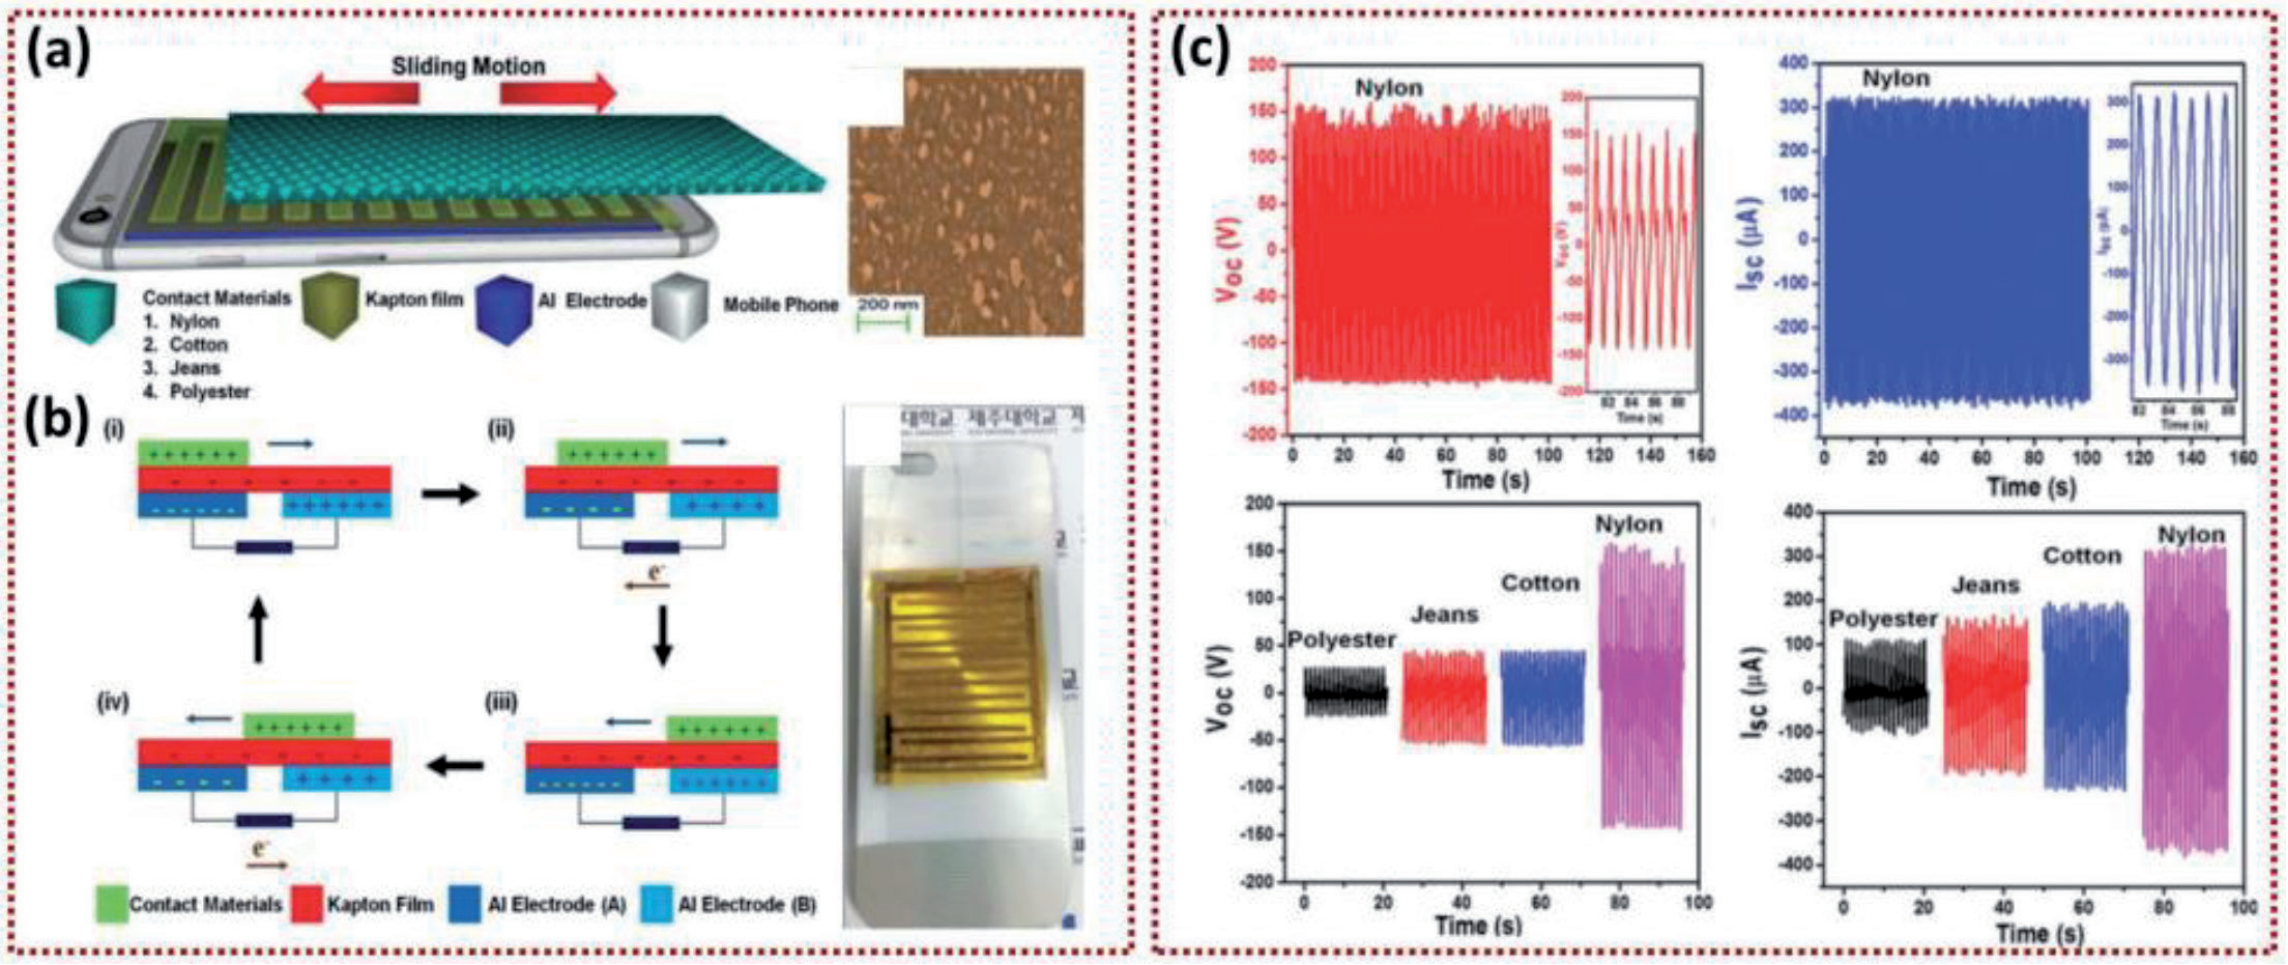

Figure 6.
(a) Schematic of a smart mobile pouch TENG device. (b) Working mechanism of SMP-TENG device operating in a free-standing triboelectrification mode. (c) Electrical response of SMP-TENG using various contact materials [42].

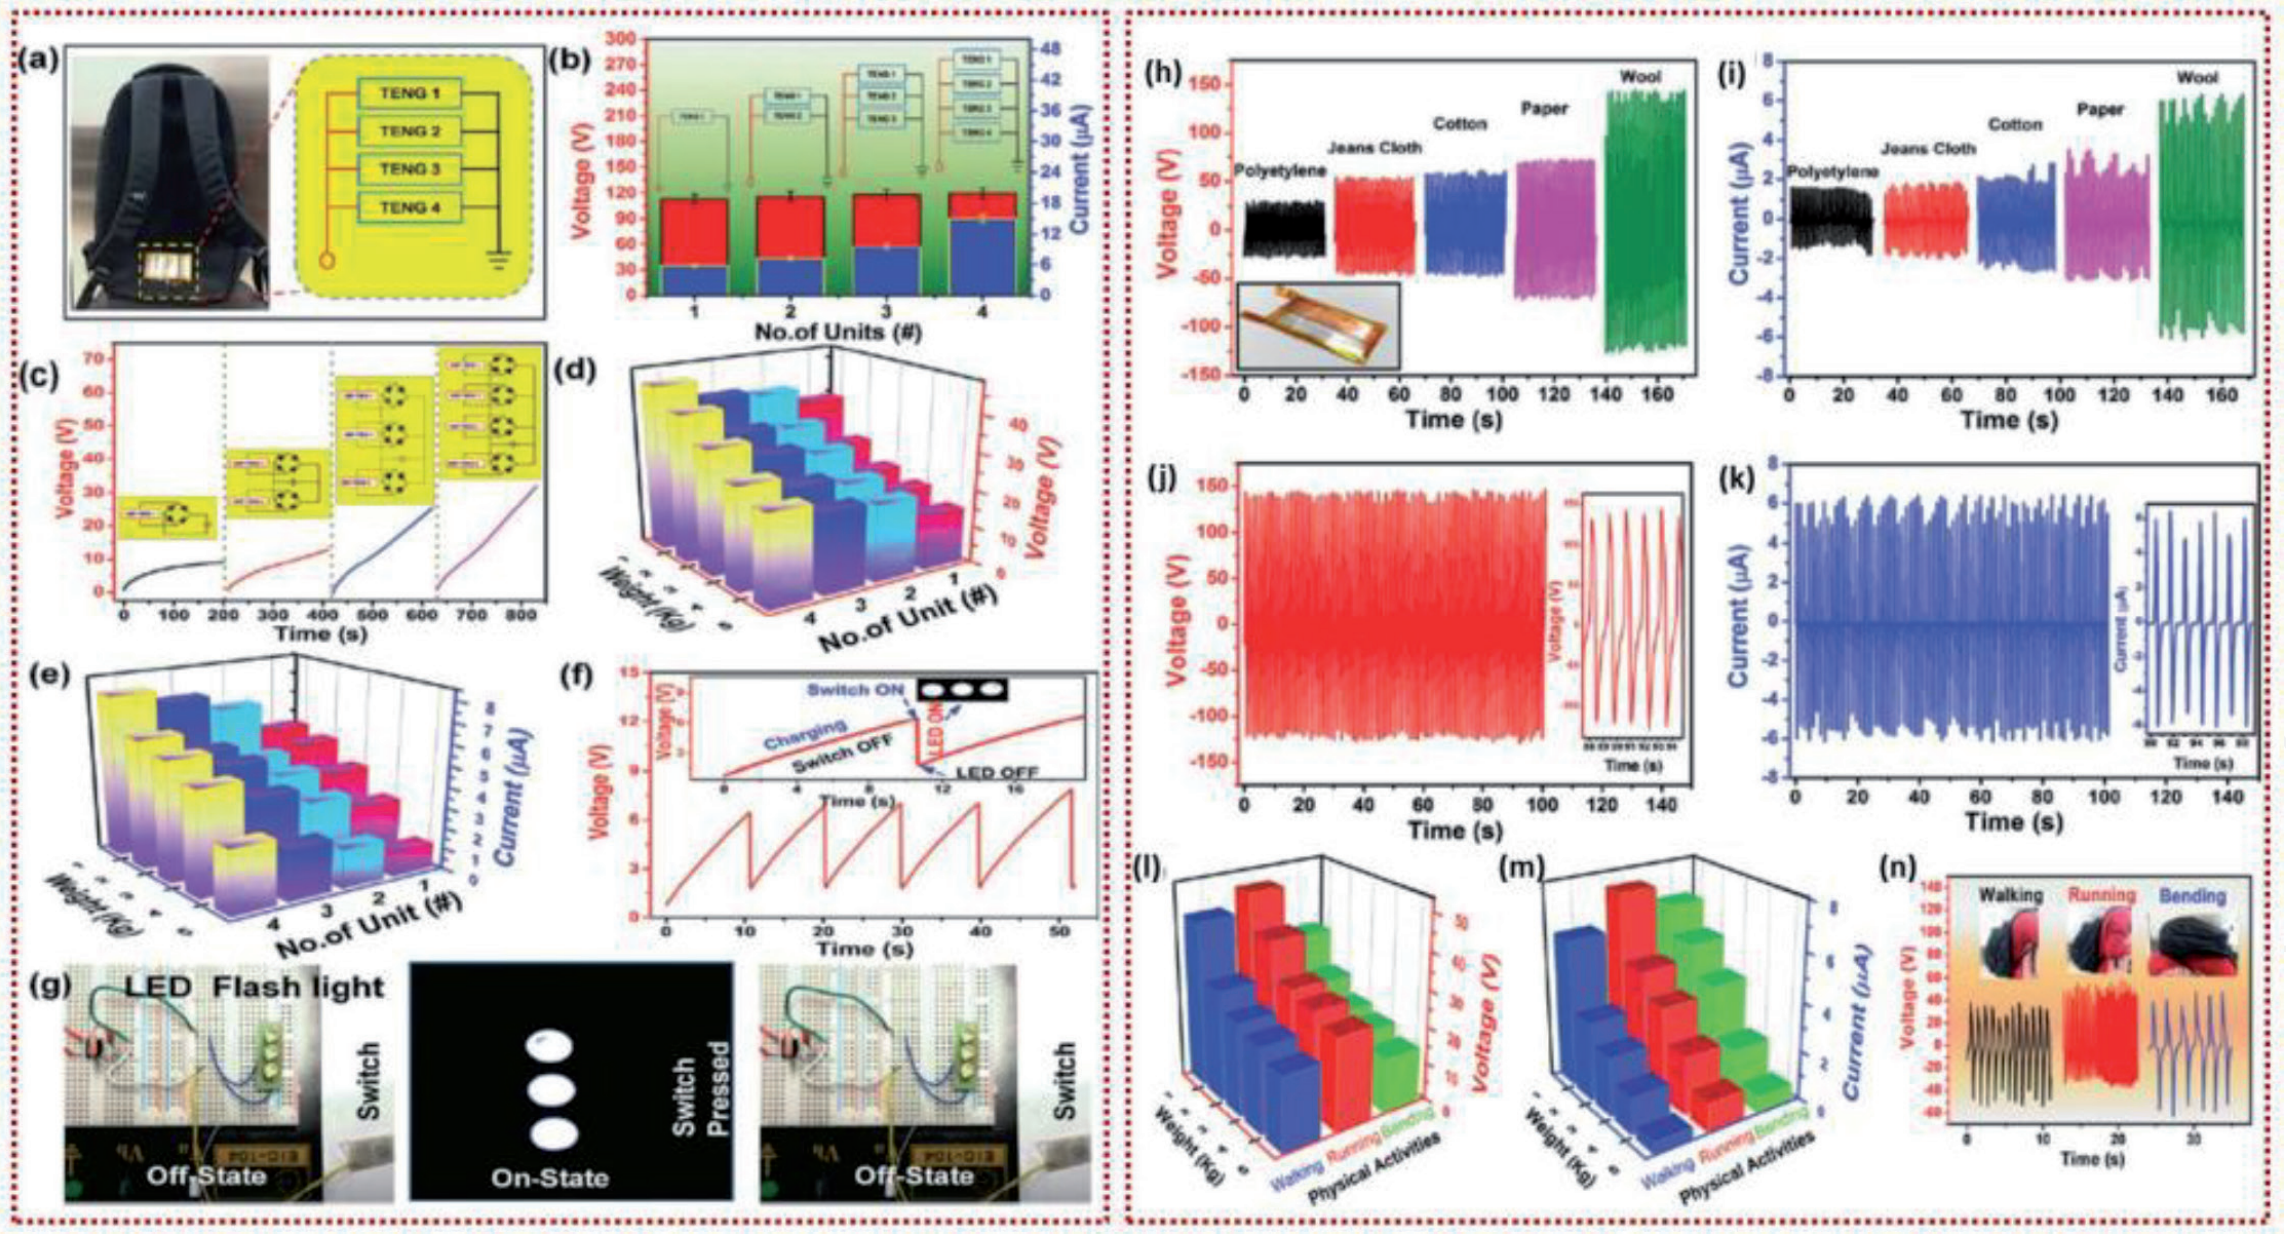

Figure 7.
(a–e) Electrical response of SBP-TENG device showing its electrical response under parallel connections with four units. (f) Cyclic stability study by charging and discharging a 1 μF capacitor. (g) Emergency LED flash using a switch and a capacitor. (h and i) Electrical response of SBP-TENG with various contact materials and the maximum response obtained with wool. (j and k) Voltage and current responses of SBP-TENG with wool. (l–n) The electrical response of SBP-TENG under biomechanical motions such as walking, running, and bending [39].

the electrical response was monitored under various biomechanical motions such as walking, running, and bending. The devices show pleasant repose under the different mechanical motions proving that the SBP-TENG is a promising candidate for scavenging biomechanical energy and for being used under emergencies.

7. Smart toy TENG

Very recently, researchers were taken a step towards the easy commercialization of TENG in a new way by making it a direct commercial product. TENGs have made as a toy which can make the children not to get addicted to electronic gadgets. The researchers have shown that the TENG could be made as a toy and sell it as a commercial product. As an idea, TENGs packed with various toys such as clapping toys, duck toys, puzzles, and computer mouse. The clapping toy makes a clapping sound, in which the contact and separation triboelectric layers were introduced between the clapping layers of the clapping toys.

The generated electric power was used to lit up green LEDs, as shown in **Figure 8a**. **Figure 8b** shows the puzzle TENG. A free-standing device made of PDMS and aluminum was attached to the puzzle board. The puzzle pieces have the other contact material, and the positions are kept different in each piece. The right piece can match with the other triboelectric layer, which placed on the exact matching area on the puzzle board. Whenever the correct piece matches, the liquid crystal display (LCD) shows "C" indicating "correct" in its display. The smart duck toy usually makes noise upon pressing its middle part. The similar concept used here by placing a TENG device placed in the middle of the duck toy connected with two LEDs in the eye portion, as shown in **Figure 8c**. The smart computer mouse uses a sliding mode triboelectrification with IDE electrodes attached to the bottom of the mouse and slides over various contact materials used in the mouse pad. This device glows a few LEDs, lit up an LCD, and charges a Li-ion battery. The improvement of

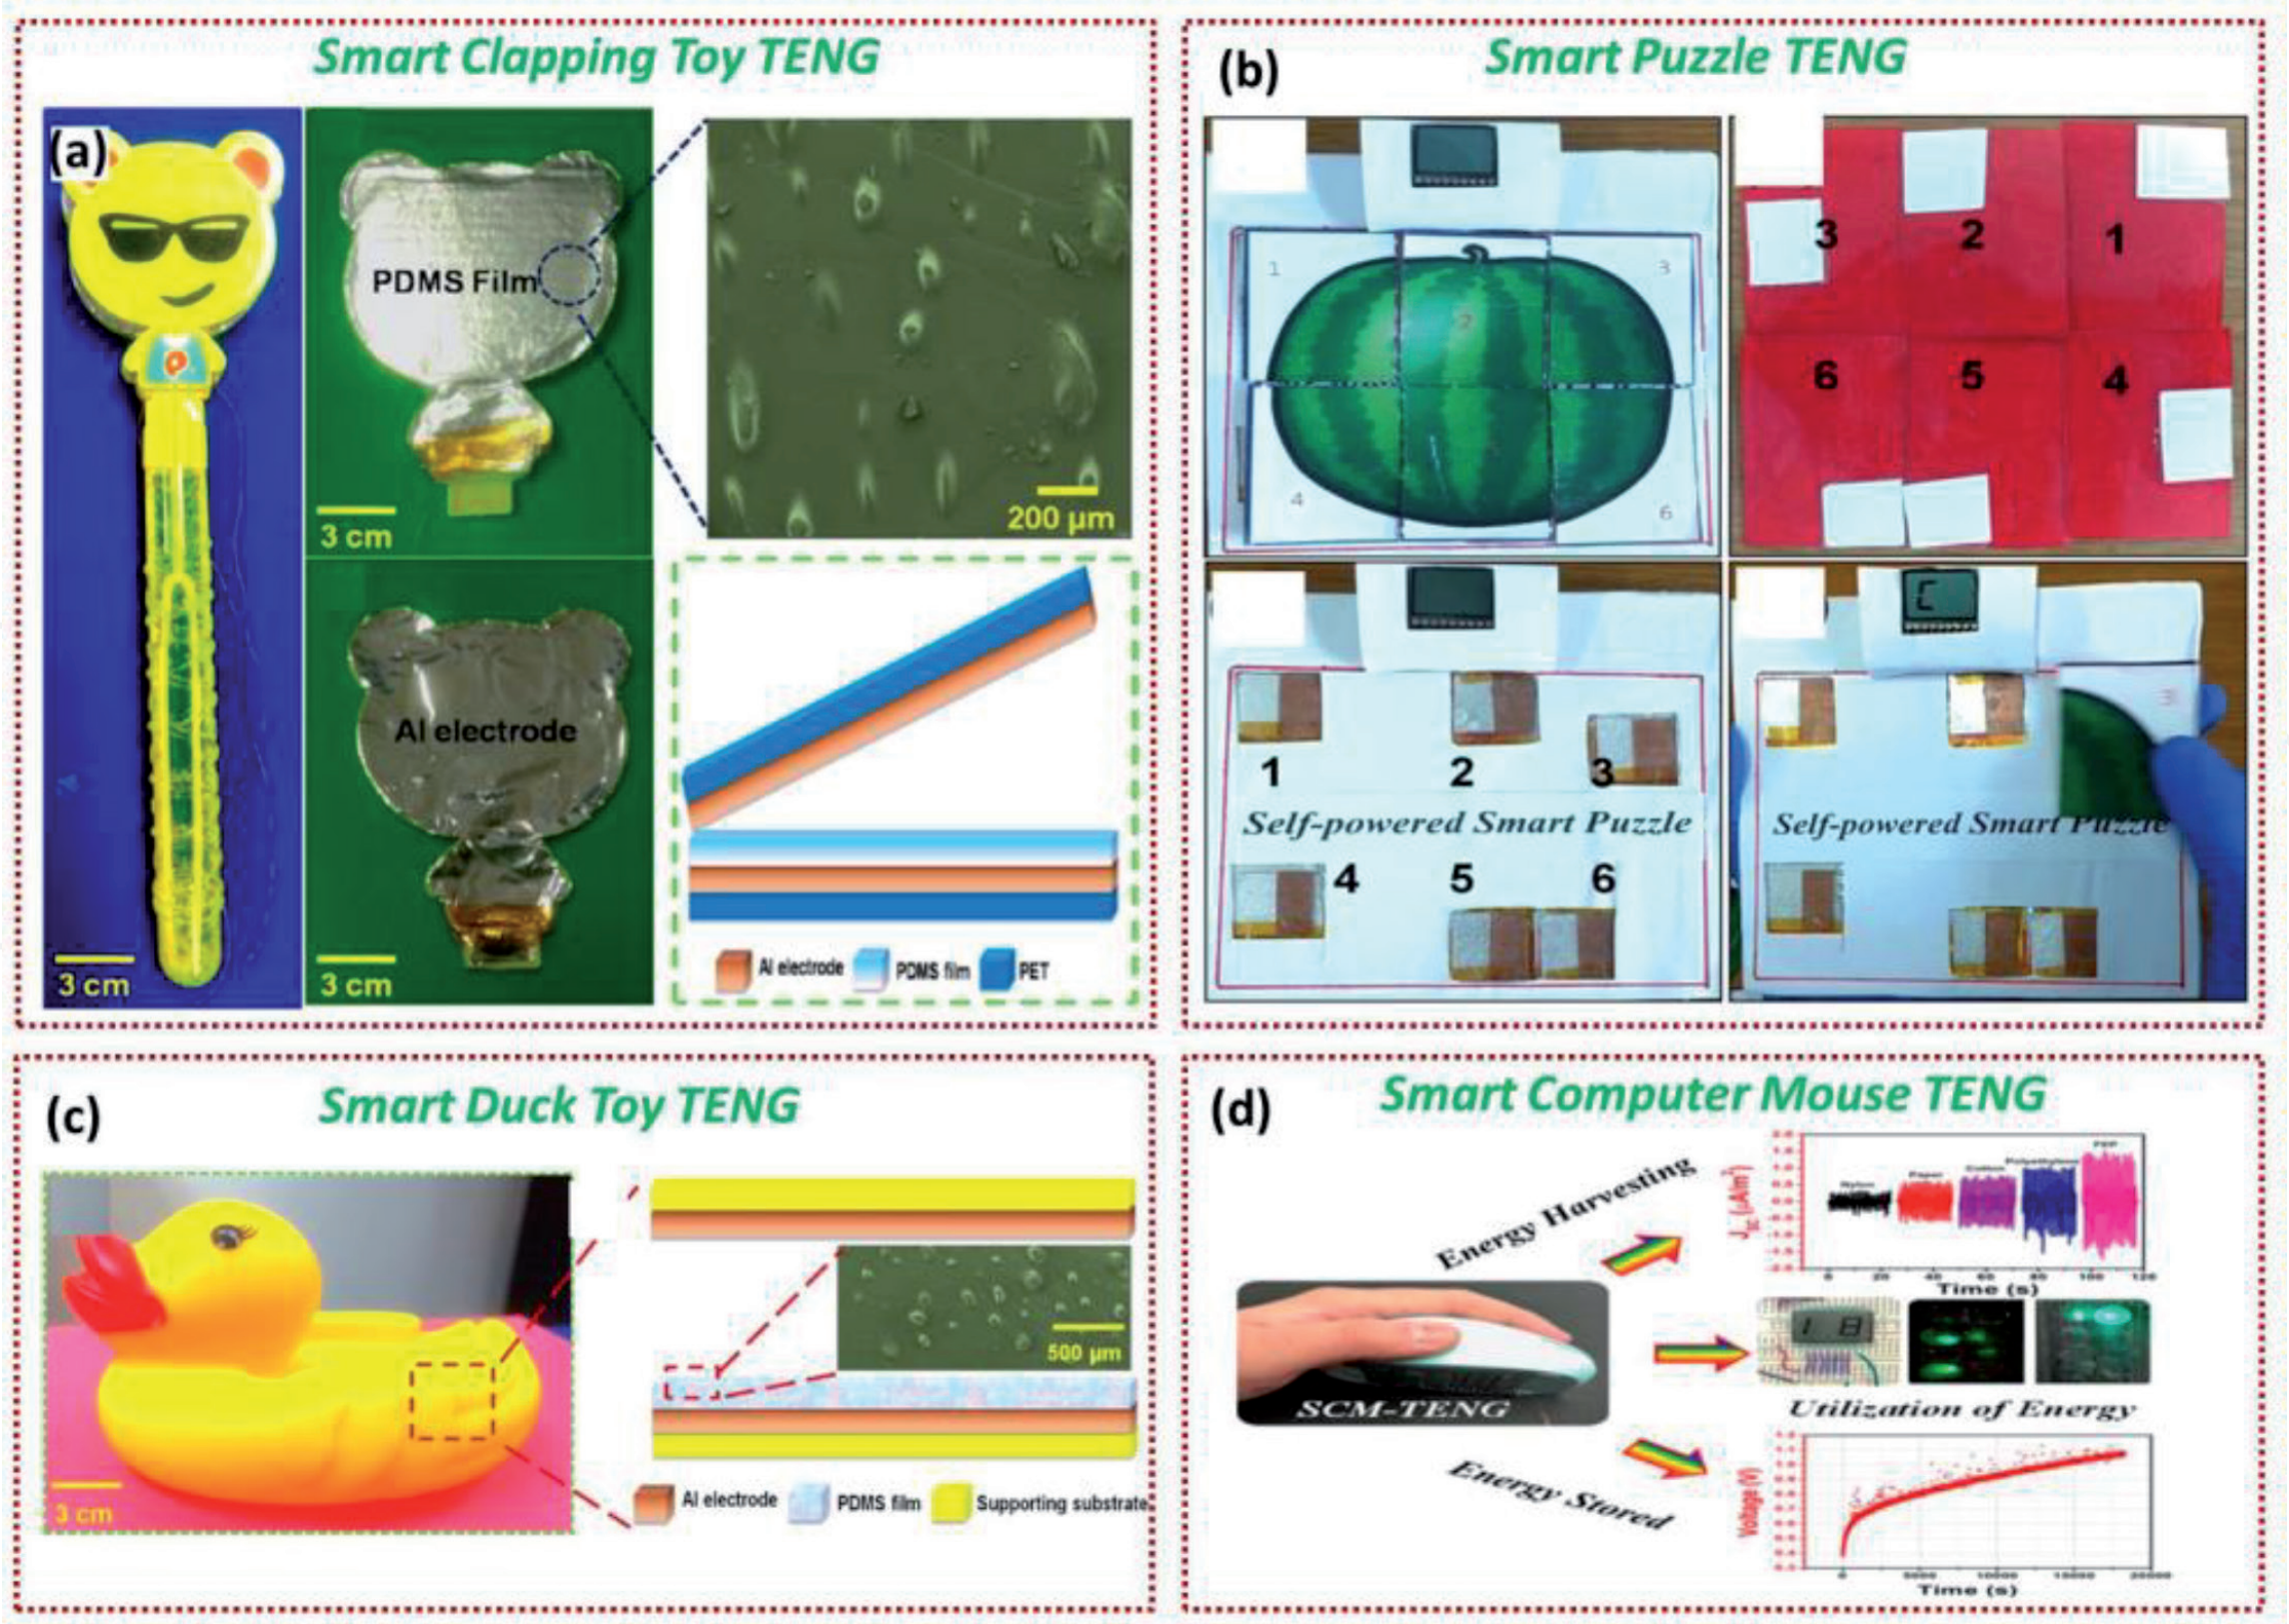

Figure 8.
(a) Schematic and device fabrication of a smart clapping toy TENG. (b) Schematic and operation of a smart puzzle TENG. (c) Schematic of a smart toy TENG. (d) Schematic and electrical response of smart mouse TENG [43, 44].

the device makes the mouse work without battery power source: the schematic and electrical response of the smart mouse TENG as shown in **Figure 8d**.

8. Edible TENG

Biodegradable and edible TENGs have recently been fabricated using edible materials. This approach utilizes the TENGs for implantable applications without being toxic to the human body and the environment. In general, TENG devices made of triboelectric materials, which are either polymer or metals. They usually create pollution in various ways depends on the toxicity levels and properties of the materials used. This section of the book shows an edible TENG made of laver (seaweed) as a triboelectric layer and an edible silver foil as an electrode. The triboelectric layer and electrode were attached to a rice sheet, which acts as a substrate for the active layer. **Figure 9a–e** shows the step-by-step fabrication process of an edible TENG device with its various layers. The TENG operated under a single-electrode mode and contacted day-to-day usage materials such as paper, tissue paper, polyvinyl chloride (PVC), and fluorinated ethylene propylene (FEP). The toxicity level and biocompatibility of the edible TENG device tested with 3-(4,5-dimethylthiazol-2-yl)-2,5-diphenyl tetrazolium bromide (MTT) assay, cell imaging, and 4′,6-diamidino-2-phenylindole (DAPI). The results prove that the triboelectric layer is biocompatible and allows the cells to grow on it. The cell growth that verifies under a confocal microscope and the imaging shows a blue color pattern in **Figure 9f**. **Figure 9g** demonstrates the real-time application of powering various electronic components such as a hygrometer, wristwatch, and LEDs using a capacitor and a switch. The electrical response and stability of the edible TENG device

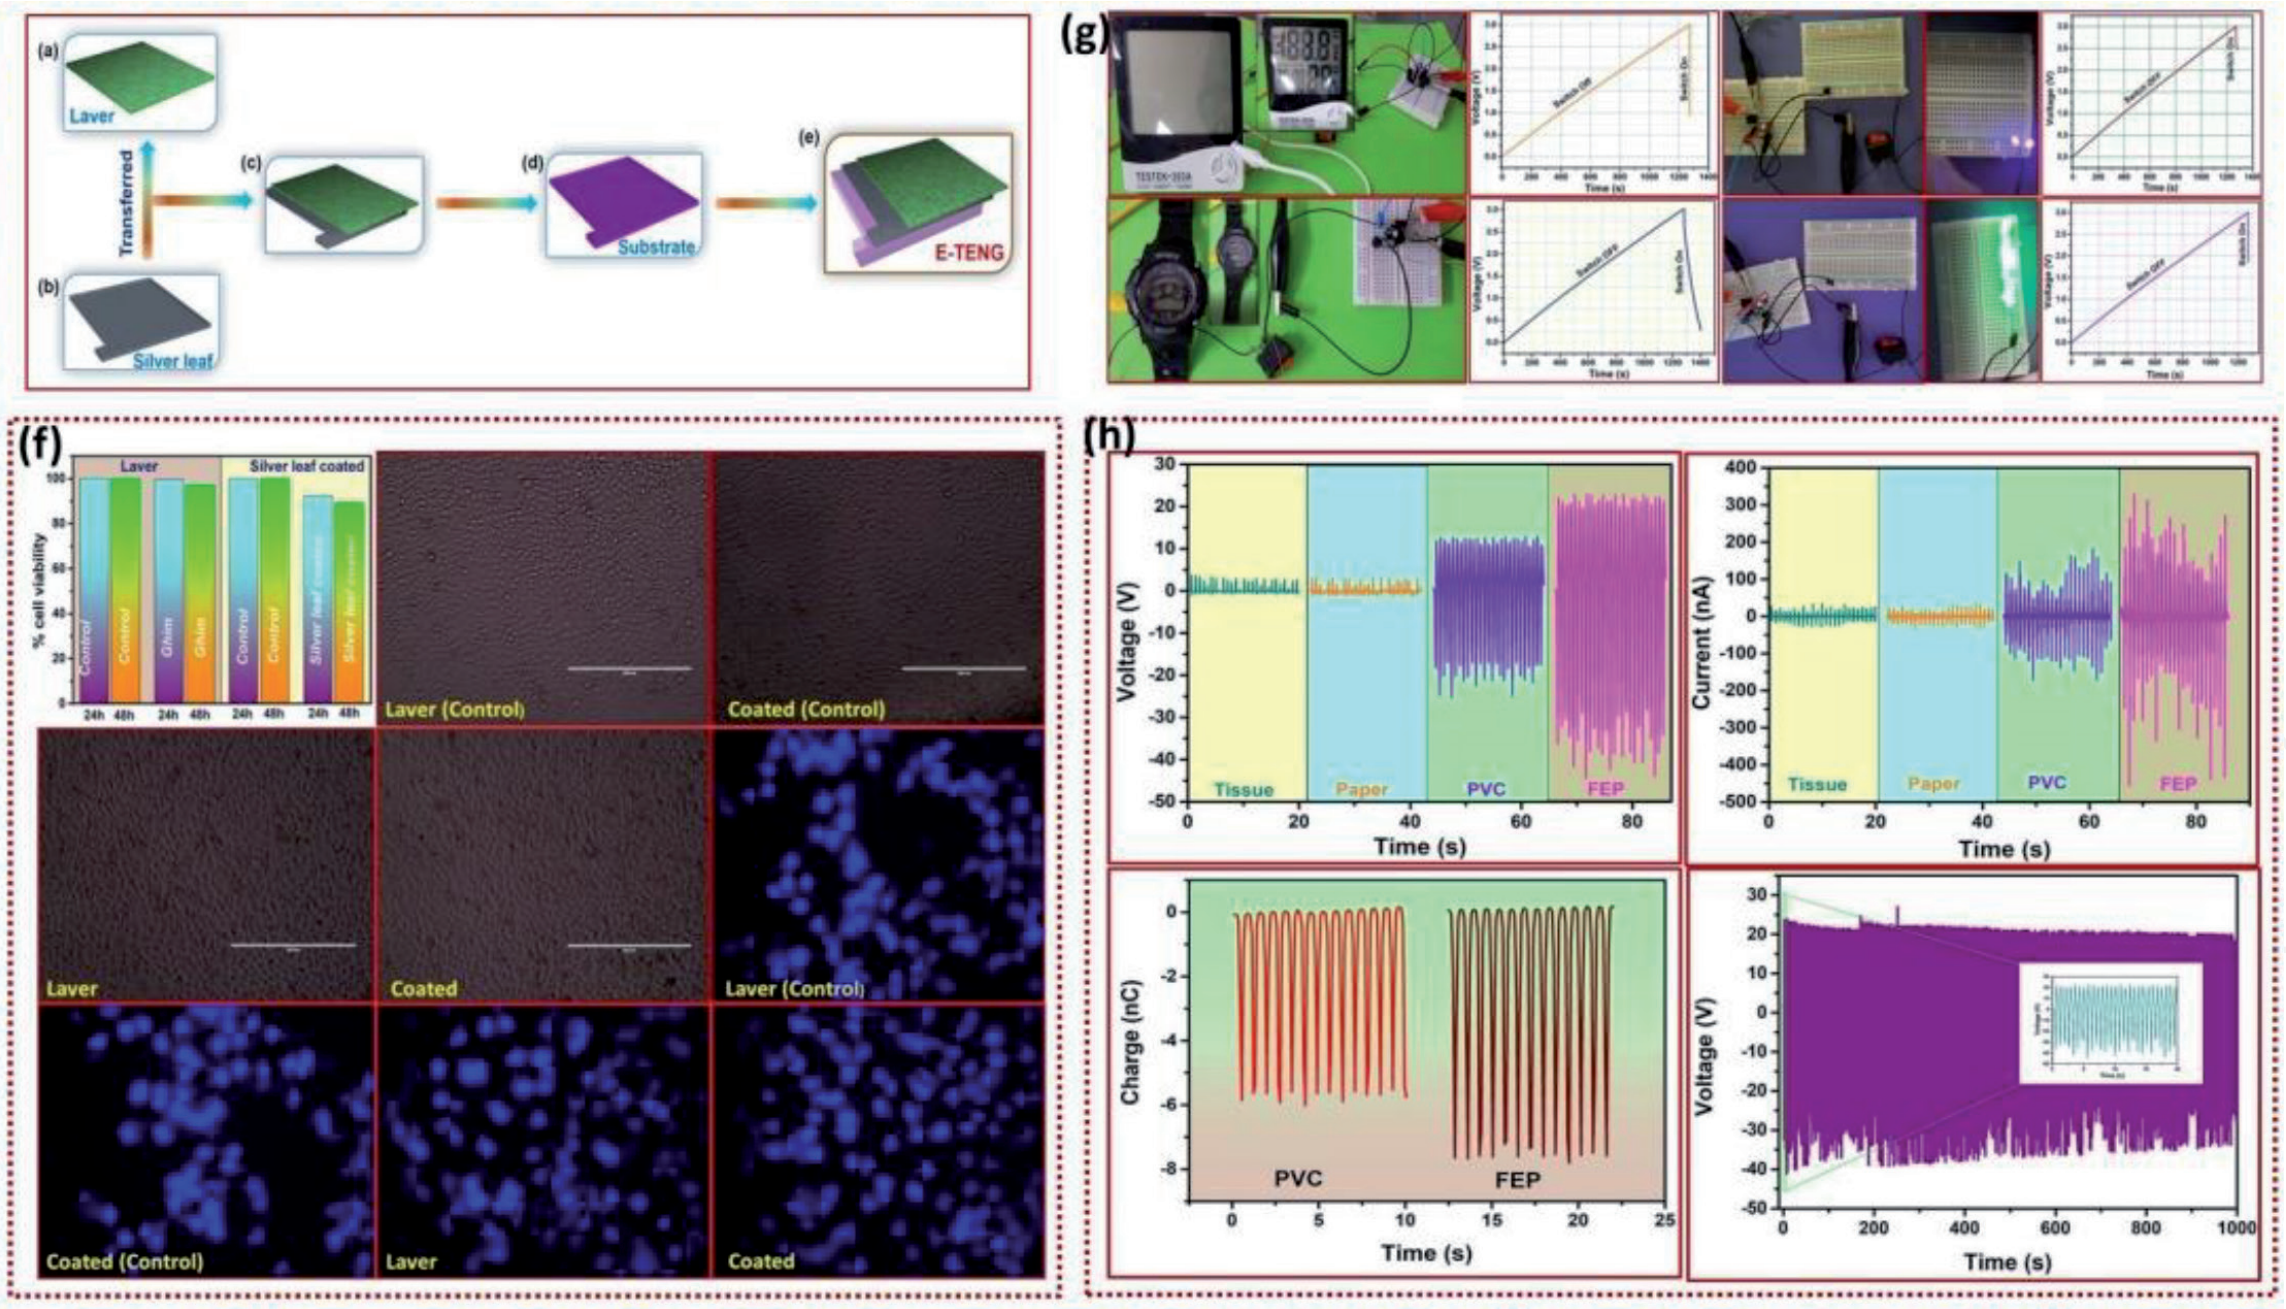

Figure 9.
(a–e) Fabrication of edible TENG device using laver as triboelectric layer and silver foil as an electrode with a rice sheet as a substrate. (f) MTT assay and cell viability test. (g) Powering up various electronic devices. (h) Electrical response analysis and stability test of the edible TENG device [45].

are shown in **Figure 9h** with the maximum output response, with its interaction with FEP. The results prove that the edible TENG is highly suitable for implantable devices and also in the applications related to biomedical electronics.

9. Fully packed-water proof TENG

There are several drawbacks of TENG devices overcome by introducing various solutions, techniques, and fabrication designs. The major drawback that TENGs are facing from the day of its invention is that its electrical performance had affected under humidity. Recently, this issue had overcome by introducing a fully packed, waterproof TENG (WP-TENG) device where it can work even underwater as well as in high humidity. **Figure 9** shows the schematic of a fully packed WP-TENG and its electrical response. The device made of nickel foam as a positive triboelectric layer, and roughness created PDMS as a negative triboelectric layer, as shown in **Figure 10a**, and the FE-SEM shows the layers in microscale in **Figure 10b–d**. The device was packed on either side with a polymer casing and sealed using a pouch laminator, as shown in **Figure 10e**. The device is extremely lightweight and weighs around 1.9 g, which is shown in **Figure 10f**. The waterproof ability of the device is tested by dipping the device underwater and is shown in **Figure 10g**. The device shows an excellent electrical response of 80 V and a maximum instantaneous power density of 4 mW/m^2. The water resistance capability of the device is shown in **Figure 10j** in which the device submerged into the water for a period of 24 h, and the corresponding response in between the intervals is measured. The response was stable for the entire time without affecting its performance. The electrical response and performance of the device are shown in **Figure 10h–j**. The electrical response to humidity is measured using a homemade humidity chamber, and the device was tested with the application of various percentages of relative humidity. The output is stable from 0% RH to 90% RH. **Figure 10k–m** shows the electrical response of humidity studies and the

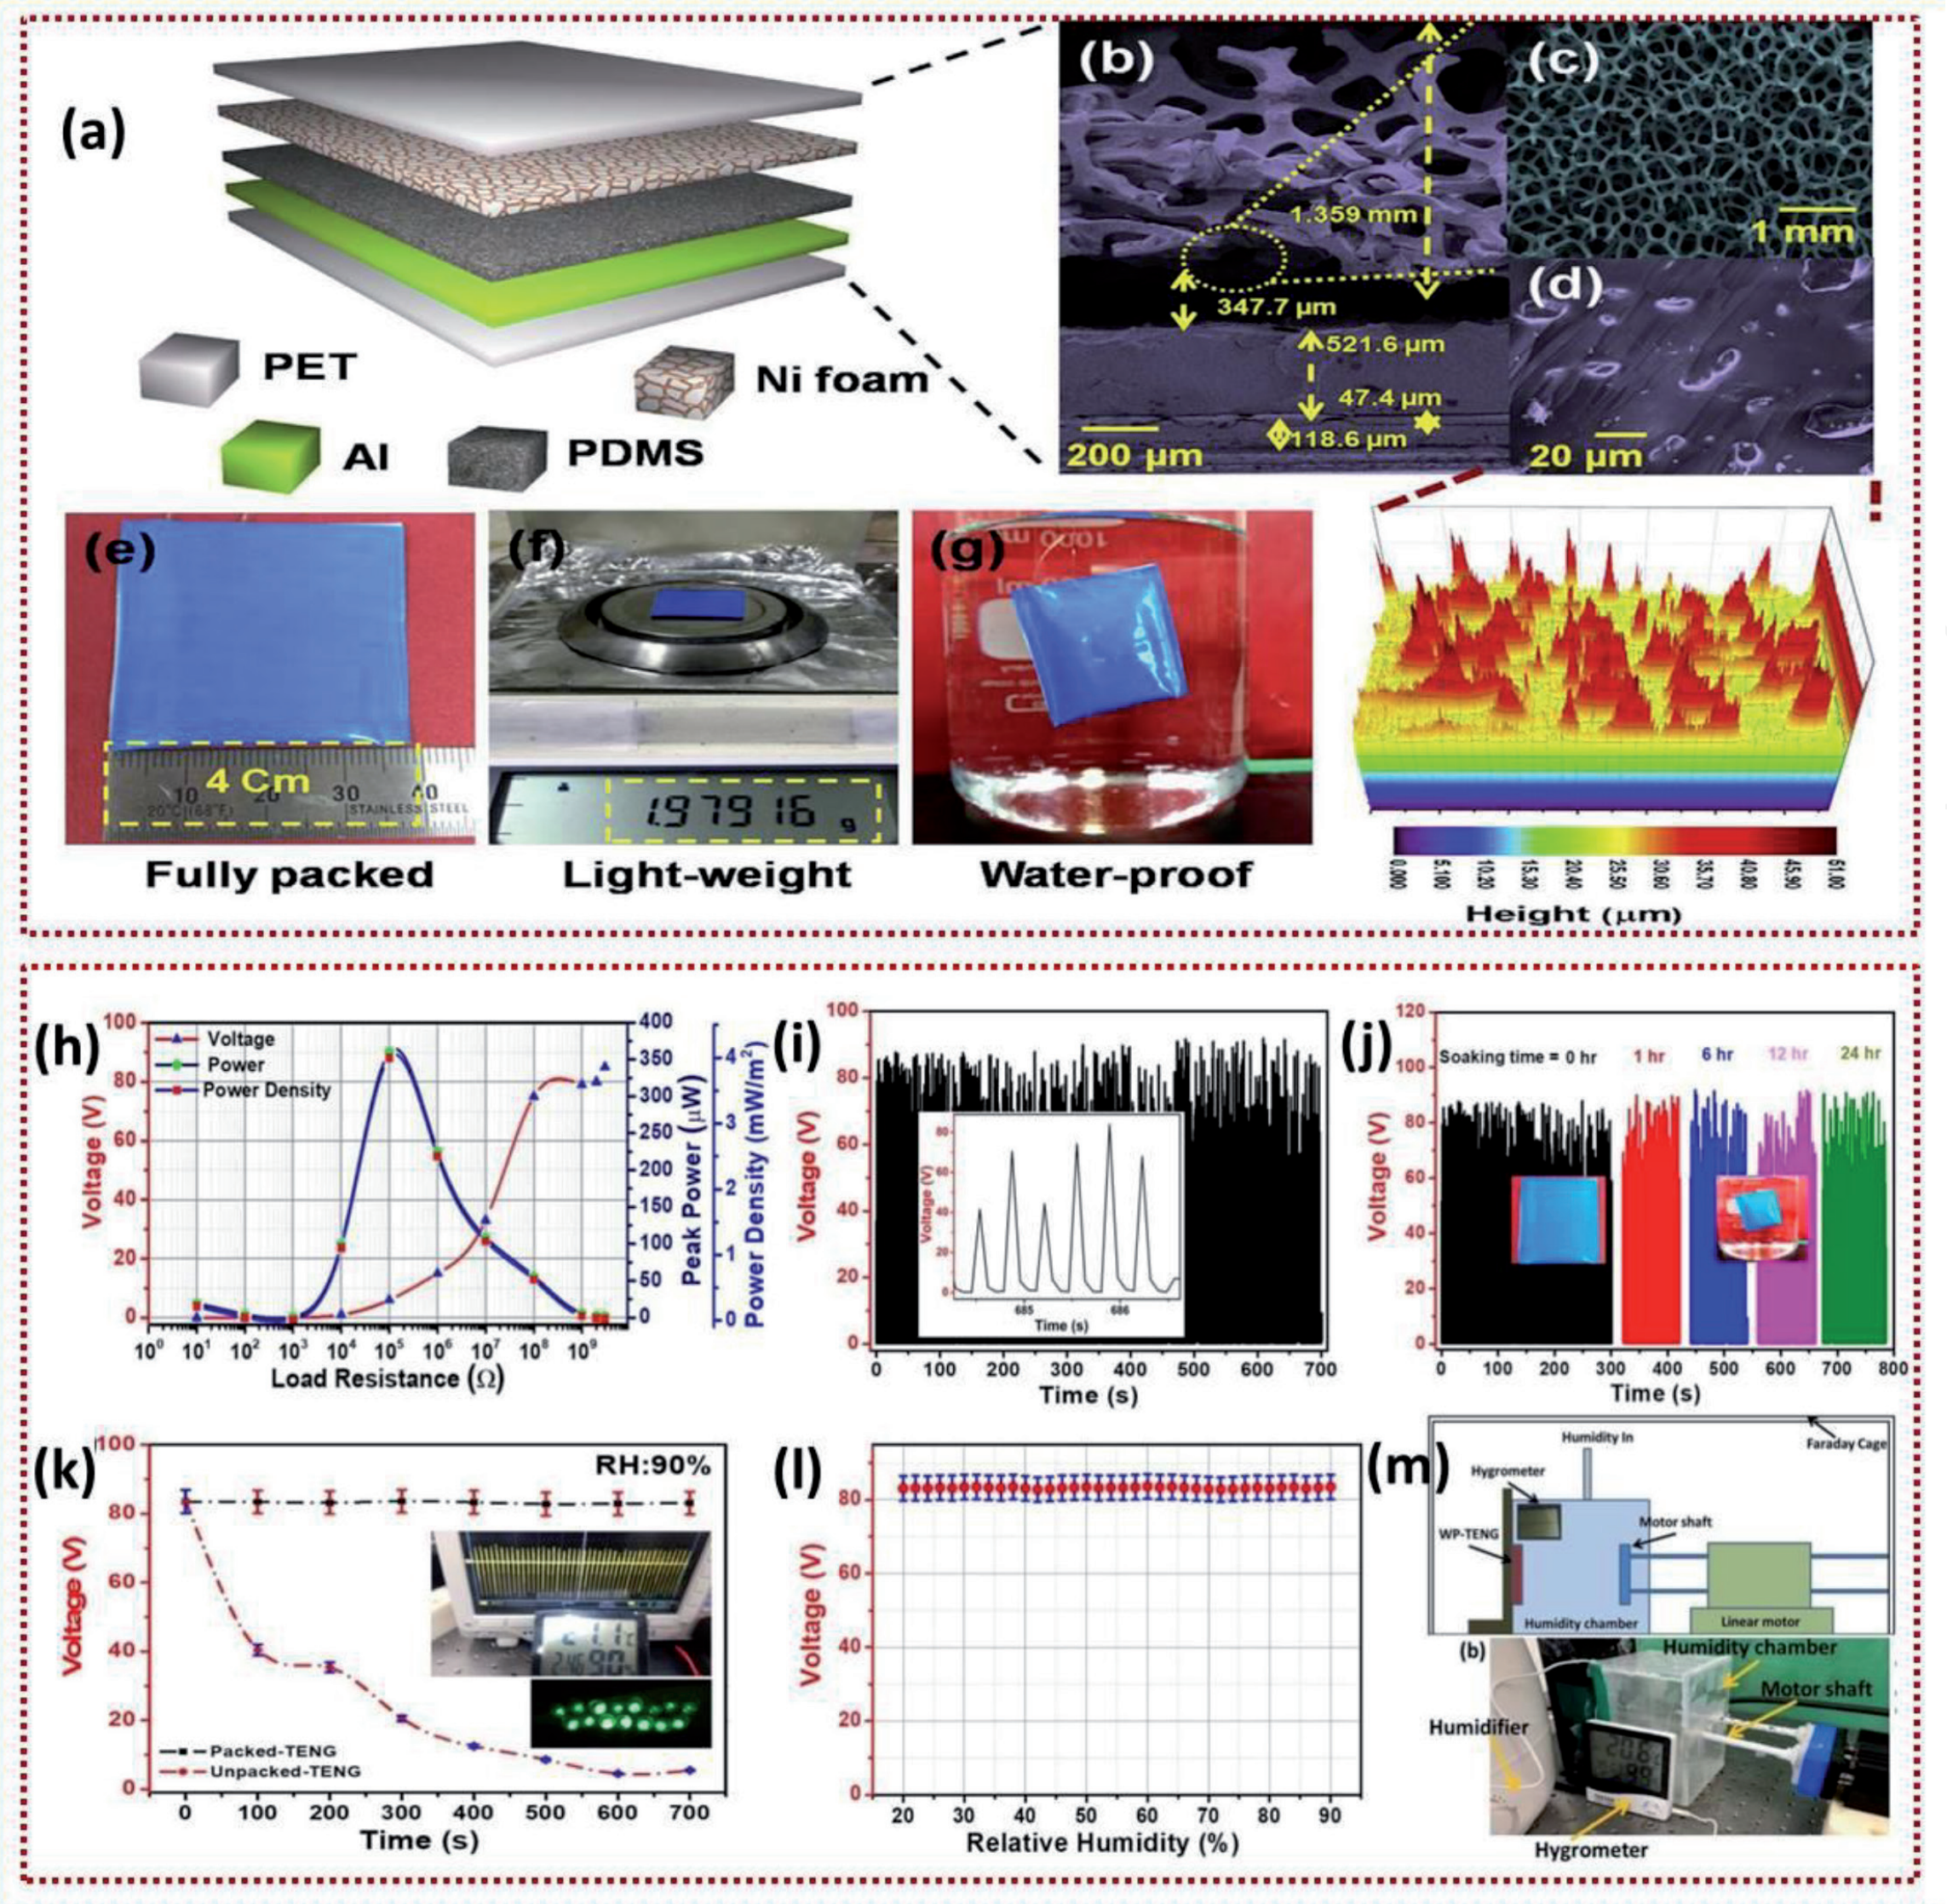

Figure 10.
(a) Schematic and layers of waterproof TENG device. (b–d) FESEM image showing the cross-section of WP-TENG device with both the layers, morphology of nickel foam and roughness PDMS. (e) Fully packed device. (f) Lightweight device weight. (g) Waterproof capability. (h) Load resistance vs. power density analysis. (i) Rectified voltage. (j) Water-resistant analysis with different time duration (k and l) humidity with output analysis. (m) Homemade humidity chamber for the analysis [34].

homemade chamber used. This study of WP-TENG shows that the device is capable of using in harsh and humid weather and environmental conditions.

10. Conclusions

In summary, the development of TENG as a sustainable, portable, and wearable power source focuses on the trend of miniaturization, energy harvesting, and self-powered electronics. The rapid advancement of energy harvesting using nanogenerators brought the possibility to power electronic devices from the waste mechanical energy in the environment. The development of TENG has reached to the bulk and scalable fabrication and started to get commercialized. Further advancement in TENG as flexible construction would be easier to harvest day-to-day mechanical energy from human motions. The construction of TENGs as a flexible power source would pave the way towards a more reliable and sustainable power source and the possibility to replace the battery shortly.

Acknowledgements

This work was supported by the Basic Science Research Program through the National Research Foundation of Korea (NRF) grant funded by the Korean Government (MSIT) (2018R1A4A1025998, 2019R1A2C3009747).

Conflict of interest

The authors declare no conflict of interest.

Author details

Venkateswaran Vivekananthan[1], Arunkumar Chandrasekhar[2], Nagamalleswara Rao Alluri[1], Yuvasree Purusothaman[1], Gaurav Khandelwal[1] and Sang-Jae Kim[1]*

1 Nanomaterials and Systems Lab, Major of Mechatronics Engineering, Faculty of Applied Energy Systems, Jeju, South Korea

2 Department of Sensors and Biomedical Engineering, Vellore Institute of Technology, India

*Address all correspondence to: kimsangj@jejunu.ac.kr

References

[1] Zhao C, Feng H, Zhang L, Li Z, Zou Y, Tan P, et al. Highly efficient In vivo cancer therapy by an implantable magnet triboelectric nanogenerator. Advanced Functional Materials. 2019;**29**(41):1808640

[2] Zheng Q, Shi B, Fan F, Wang X, Yan L, Yuan W, et al. In vivo powering of pacemaker by breathing-driven implanted triboelectric nanogenerator. Advanced Materials. 2014;**26**(33):5851-5856

[3] Moreno S, Baniasadi M, Mohammed S, Mejia I, Chen Y, Quevedo-Lopez MA, et al. Biocompatible collagen films as substrates for flexible implantable electronics. Advanced Electronic Materials. 2015;**1**(9):1500154

[4] Zheng Q, Zhang H, Shi B, Xue X, Liu Z, Jin Y, et al. In vivo self-powered wireless cardiac monitoring via implantable triboelectric nanogenerator. ACS Nano. 2016;**10**(7):6510-6518

[5] Vivekananthan V, Alluri NR, Chandrasekhar A, Purusothaman Y, Gupta A, Kim S-J. Zero-power consuming intruder identification system by enhanced piezoelectricity of $K_{0.5}Na_{0.5}NbO_3$ using substitutional doping of BTO NPs. Journal of Materials Chemistry C. 2019;**7**:7563-7571

[6] Park K-I, Son JH, Hwang G-T, Jeong CK, Ryu J, Koo M, et al. Highly-efficient, flexible piezoelectric PZT thin film nanogenerator on plastic substrates. Advanced Materials. 2014;**26**(16):2514-2520

[7] Fan F-R, Tian Z-Q, Lin WZ. Flexible triboelectric generator. Nano Energy. 2012;**1**(2):328-334

[8] Lee S, Hinchet R, Lee Y, Yang Y, Lin Z-H, Ardila G, et al. Ultrathin nanogenerators as self-powered/active skin sensors for tracking eye ball motion. Advanced Functional Materials. 2014;**24**(8):1163-1168

[9] Song P, Kuang S, Panwar N, Yang G, Tng DJH, Tjin SC, et al. A self-powered implantable drug-delivery system using biokinetic energy. Advanced Materials. 2017;**29**(11):1605668

[10] Vivekananthan V, Kim WJ, Alluri NR, Purusothaman Y, Abisegapriyan KS, Kim S-J. A sliding mode contact electrification based triboelectric-electromagnetic hybrid generator for small-scale biomechanical energy harvesting. Micro and Nano Systems Letters. 2019;**7**(1):14

[11] Wang ZL, Song J. Piezoelectric nanogenerators based on zinc oxide nanowire arrays. Science. 2006;**312**(5771):242-246

[12] Vivekananthan V, Alluri NR, Purusothaman Y, Chandrasekhar A, Kim S-J. A flexible, planar energy harvesting device for scavenging road side waste mechanical energy via the synergistic piezoelectric response of $K_{0.5}Na_{0.5}NbO_3$-$BaTiO_3$/PVDF composite films. Nanoscale. 2017;**9**(39):15122-15130

[13] Vivekananthan V, Chandrasekhar A, Alluri NR, Purusothaman Y, Joong Kim W, Kang C-N, et al. A flexible piezoelectric composite nanogenerator based on doping enhanced lead-free nanoparticles. Materials Letters. 2019;**249**:73-76

[14] Maria Joseph Raj NP, Alluri NR, Vivekananthan V, Chandrasekhar A, Khandelwal G, Kim S-J. Sustainable yarn type-piezoelectric energy harvester as an eco-friendly, cost-effective battery-free breath sensor. Applied Energy. 2018;**228**:1767-1776

[15] Alluri NR, Vivekananthan V, Chandrasekhar A, Kim S-J. Adaptable

piezoelectric hemispherical composite strips using a scalable groove technique for a self-powered muscle monitoring system. Nanoscale. 2018;**10**(3):907-913

[16] Chandrasekhar A, Vivekananthan V, Khandelwal G, Kim S-J. A Sustainable Human-Machine Interactive Triboelectric Nanogenerator towards a Smart Computer Mouse. United states: ACS Sustainable Chemistry & Engineering; 2019;7:7177-7182

[17] Yang Y, Guo W, Pradel KC, Zhu G, Zhou Y, Zhang Y, et al. Pyroelectric nanogenerators for harvesting thermoelectric energy. Nano Letters. 2012;**12**(6):2833-2838

[18] Bowen CR, Taylor J, LeBoulbar E, Zabek D, Chauhan A, Vaish R. Pyroelectric materials and devicesforenergyharvestingapplications. Energy & Environmental Science. 2014;**7**(12):3836-3856

[19] Alluri NR, Selvarajan S, Chandrasekhar A, Balasubramaniam S, Jeong JH, Kim S-J. Self powered pH sensor using piezoelectric composite worm structures derived by ionotropic gelation approach. Sensors and Actuators B: Chemical. 2016;**237**:534-544

[20] Selvarajan S, Alluri NR, Chandrasekhar A, Kim S-J. $BaTiO_3$ nanoparticles as biomaterial film for self-powered glucose sensor application. Sensors and Actuators B: Chemical. 2016;**234**:395-403

[21] Dey G, Venkateswarulu M, Vivekananthan V, Pramanik A, Krishnan V, Koner RR. Sub-picomolar recognition of Cr^{3+} through bioinspired organic–inorganic ensemble utilization. ACS Sensors. 2016;**1**(6):663-669

[22] Vivekananthan V, Alluri NR, Purusothaman Y, Chandrasekhar A, Selvarajan S, Kim S-J. Biocompatible collagen nanofibrils: An approach for sustainable energy harvesting and battery-free humidity sensor applications. ACS Applied Materials & Interfaces. 2018;**10**(22):18650-18656

[23] Chang T-H, Peng Y-W, Chen C-H, Chang T-W, Wu J-M, Hwang J-C, et al. Protein-based contact electrification and its uses for mechanical energy harvesting and humidity detecting. Nano Energy. 2016;**21**:238-246

[24] Maria Joseph Raj NP, Alluri NR, Chandrasekhar A, Khandelwal G, Kim S-J. Self-powered ferroelectric NTC thermistor based on bismuth titanate. Nano Energy. 2019;**62**:329-337

[25] Alluri NR, Chandrasekhar A, Kim S-J. Exalted electric output via piezoelectric–triboelectric coupling/sustainable butterfly wing structure type multiunit hybrid nanogenerator. ACS Sustainable Chemistry & Engineering. 2018;**6**(2):1919-1933

[26] Chandrasekhar A, Alluri NR, Saravanakumar B, Selvarajan S, Kim S-J. A microcrystalline cellulose ingrained polydimethylsiloxane triboelectric nanogenerator as a self-powered locomotion detector. Journal of Materials Chemistry C. 2017;**5**(7):1810-1815

[27] Purusothaman Y, Alluri NR, Chandrasekhar A, Vivekananthan V, Kim S-J. Direct In situ hybridized interfacial quantification to stimulate highly flexile self-powered photodetector. The Journal of Physical Chemistry C. 2018;**122**(23):12177-12184

[28] Purusothaman Y, Alluri NR, Chandrasekhar A, Vivekananthan V, Kim SJ. Regulation of charge carrier dynamics in ZnO microarchitecture-based UV/visible photodetector via photonic-strain induced effects. Small. 2018;**14**(11):1703044

[29] Wang L, Liu S, Wang Z, Zhou Y, Qin Y, Wang ZL. Piezotronic effect

enhanced photocatalysis in strained anisotropic ZnO/TiO(2) nanoplatelets via thermal stress. ACS Nano. 2016;**10**(2):2636-2643

[30] Wang S, Wang ZL, Yang Y. A one-structure-based hybridized nanogenerator for scavenging mechanical and thermal energies by triboelectric-piezoelectric-pyroelectric effects. Advanced Materials. 2016;**28**(15):2881-2887

[31] Wang H, Zhu Q, Ding Z, Li Z, Zheng H, Fu J, et al. A fully-packaged ship-shaped hybrid nanogenerator for blue energy harvesting toward seawater self-desalination and self-powered positioning. Nano Energy. 2019;**57**:616-624

[32] Vivekananthan V, Chandrasekhar A, Alluri NR, Purusothaman Y, Khandelwal G, Pandey R, et al. Fe_2O_3 magnetic particles derived triboelectric-electromagnetic hybrid generator for zero-power consuming seismic detection. Nano Energy. 2019;**64**:103926

[33] Zheng Q, Zou Y, Zhang Y, Liu Z, Shi B, Wang X, et al. Biodegradable triboelectric nanogenerator as a life-time designed implantable power source. Science Advances. 2016;**2**(3):e1501478

[34] Chandrasekhar A, Vivekananthan V, Khandelwal G, Kim SJ. A fully packed water-proof, humidity resistant triboelectric nanogenerator for transmitting Morse code. Nano Energy. 2019;**60**:850-856

[35] Purusothaman Y, Alluri NR, Chandrasekhar A, Venkateswaran V, Kim S-J. Piezophototronic gated optofluidic logic computations empowering intrinsic reconfigurable switches. Nature Communications. 2019;**10**(1):4381

[36] Shi Q, He T, Lee C. More than energy harvesting–combining triboelectric nanogenerator and flexible electronics technology for enabling novel micro−/nano-systems. Nano Energy. 2019;**57**:851-871

[37] Yang Y, Zhou YS, Zhang H, Liu Y, Lee S, Wang ZL. A single-electrode based triboelectric nanogenerator as self-powered tracking system. Advanced Materials. 2013;**25**(45):6594-6601

[38] Nie J, Wang Z, Ren Z, Li S, Chen X, Lin WZ. Power generation from the interaction of a liquid droplet and a liquid membrane. Nature Communications. 2019;**10**(1):2264

[39] Chandrasekhar A, Alluri NR, Vivekananthan V, Purusothaman Y, Kim S-J. A sustainable freestanding biomechanical energy harvesting smart backpack as a portable-wearable power source. Journal of Materials Chemistry C. 2017;**5**(6):1488-1493

[40] Khandelwal G, Chandrasekhar A, Alluri NR, Vivekananthan V, Maria Joseph Raj NP, Kim S-J. Trash to energy: A facile, robust and cheap approach for mitigating environment pollutant using household triboelectric nanogenerator. Applied Energy. 2018;**219**:338-349

[41] Chandrasekhar A, Alluri NR, Saravanakumar B, Selvarajan S, Kim S-J. Human interactive triboelectric nanogenerator as a self-powered smart seat. ACS Applied Materials & Interfaces. 2016;**8**(15):9692-9699

[42] Chandrasekhar A, Alluri NR, Sudhakaran MSP, Mok YS, Kim S-J. A smart mobile pouch as a biomechanical energy harvester towards self-powered smart wireless power transfer applications. Nanoscale. 2017;**9**(28):9818-9824

[43] Chandrasekhar A, Khandelwal G, Alluri NR, Vivekananthan V, Kim S-J. Battery-free electronic smart toys: A step toward the commercialization of sustainable triboelectric

nanogenerators. ACS Sustainable Chemistry & Engineering. 2018;**6**(5):6110-6116

[44] Chandrasekhar A, Alluri NR, Vivekananthan V, Park JH, Kim S-J. Sustainable biomechanical energy scavenger toward self-reliant kids' interactive battery-free smart puzzle. ACS Sustainable Chemistry & Engineering. 2017;**5**(8):7310-7316

[45] Khandelwal G, Minocha T, Yadav SK, Chandrasekhar A, Maria Joseph Raj NP, Gupta SC, et al. All edible materials derived biocompatible and biodegradable triboelectric nanogenerator. Nano Energy. 2019;**65**:104016