

Thermal analysis, X-ray diffraction, spectroscopy studies and magnetic properties of the new compound $Tl_2HAsO_4 \cdot Te(OH)_6$.

I. Bechibani¹, H. litaiem^{1*}, S. Garcia-Granda², M. Dammak¹, L. Ktari¹.

¹Inorganic Chemistry Laboratory, University of Sfax, Faculty of Sciences of Sfax, Tunisia.

E-mail address: ikrambechibani@yahoo.fr; litaiemh@yahoo.fr; meddammak@yahoo.fr;

ktarililia@yahoo.fr;

²Physical and Analytical Chemistry Laboratory, Faculty of Chemistry, University of Oviedo, Spain.

E-mail address: sgg@uniovi.es

ABSTRACT:

The $Tl_2HAsO_4 \cdot Te(OH)_6$ (TlAsTe) compound crystallizes in the triclinic system P1 with unit cell parameters: $a = 7.100(10)$ Å, $b = 7.281(13)$ Å, $c = 8.383(11)$ Å, $\alpha = 76.91(1)^\circ$, $\beta = 87.16(1)^\circ$, $\gamma = 66.96(2)^\circ$, $Z = 2$ and $V = 388.19(1)$ Å³. This new structure can be described as a lamellar one with the atomic arrangement being built by planes of $Te(OH)_6$ octahedra alternating with planes of arsenate tetrahedra. Raman and infrared spectra recorded at room temperature confirm the presence of AsO_4^{3-} and TeO_6^{2-} groups and characterize the hydrogen bonds present in the crystal lattice. Differential scanning calorimetry (DSC) shows the presence of three-phase transitions at 396 K, 408 K and 430 K present in the title compound. Typical thermal analyses, such as differential thermal analysis (DTA) and thermogravimetry (TG-DTG) show that the decomposition of this material starts at about $T = 445$ K. Magnetization curve of $Tl_2HAsO_4 \cdot Te(OH)_6$ substance have revealed a diamagnetic response overall temperature range studied.

Keywords: X ray-diffraction; IR; Raman; DSC; Crystal structure.

*Corresponding Author Tel: +(216)22371409

E-mail address: litaiemh@yahoo.fr

Council for Innovative Research

Peer Review Research Publishing System

Journal: Journal of Advances in Chemistry

Vol. 7, No. 3

editor@cirworld.com

www.cirjac.com, member.cirworld.com

1. INTRODUCTION:

A large number of telluric salts with general formula $M_2AO_4.Te(OH)_6$, where M is a monovalent cations and (A = As, S, Se...), undergo several structural phase transitions and interesting physical properties [1-6]. In order to expand upon the emergent chemistry of template tellurate a new compound using the arsenate group $HAsO_4^{2-}$ has been synthesized. Thus, the presence of the hydrogen atom in this ionic group can differentiate this new tellurate to other previously studied and give new insights on the addition compound based on tellurate. Therefore, there is a great interest to create and study the new family of arsenates tellurates.

In this paper, we present and discuss the results of our investigation concerning the (TlAsTe) material by X-ray diffraction, IR and Raman studies, thermal analysis (DSC, DTA, DTG and TG) and magnetic properties.

2. EXPERIMENTAL:

Colorless and transparent single crystals of $Tl_2HAsO_4.Te(OH)_6$ were prepared by slow evaporation at room temperature from a mixture solution of telluric acid H_6TeO_6 , thallium carbonate Tl_2CO_3 and arsenic acid H_3AsO_4 in the stoichiometric ratio reaction.



The formula of this material was determined by chemical analysis and confirmed by structural refinement. The structure was solved by using the SUPERFLIP program [7] and completed by the Fourier synthesis performed using SHELXL-97 program [8]. The structure graphics were created by the Diamond program [9]. The masses of samples used in TG, DTG and DTA measurements were 9.035 mg. Differential scanning calorimetry (DSC) measurements were carried out by means of a Mettler Toledo DSC model DSC821 with samples placed inside platinum crucibles, at a heating rate of 5K/min.

Infrared absorption spectra of suspension of crystalline in KBr have been recorded using Jasco-FT-IR-420 spectrophotometer in the $(4000-500) \text{ cm}^{-1}$ frequency range. Raman spectra of polycrystalline samples sealed in glass tubes have been recorded on a Labrama HR 800 instrument using 632.81 nm radiations from a physics argon ion laser.

The details of data collection and refinement for the title compound are summarized in Table 1. The final positions and equivalent isotropic atomic displacement parameters for the new compound are given in Table 2 and Table 3.

3. RESULTS AND DISCUSSION:

3.1. Calorimetric study:

A typical result of the calorimetric study of the $Tl_2HAsO_4.Te(OH)_6$ compound is presented in Figure 1. The superposition of TG-DTA and DTG curves are showing in Figure 2. According to these figures, the (TlAsTe) material presents three-phase transitions at $T= 408 \text{ K}$, with a shoulder at $T= 396 \text{ K}$, and an endothermic peak at $T= 430 \text{ K}$, also we can deduce that the decomposition of this material starts at about $T= 445 \text{ K}$. In fact, the first mass loss of 4.5 % may be corresponding to the release of two water molecules per chemical formula. Thus, in the temperature range 400 K - 500 K the telluric acid $Te(OH)_6$ decomposes to disengage the water molecule and give the orthotelluric acid H_2TeO_4 [6, 30].

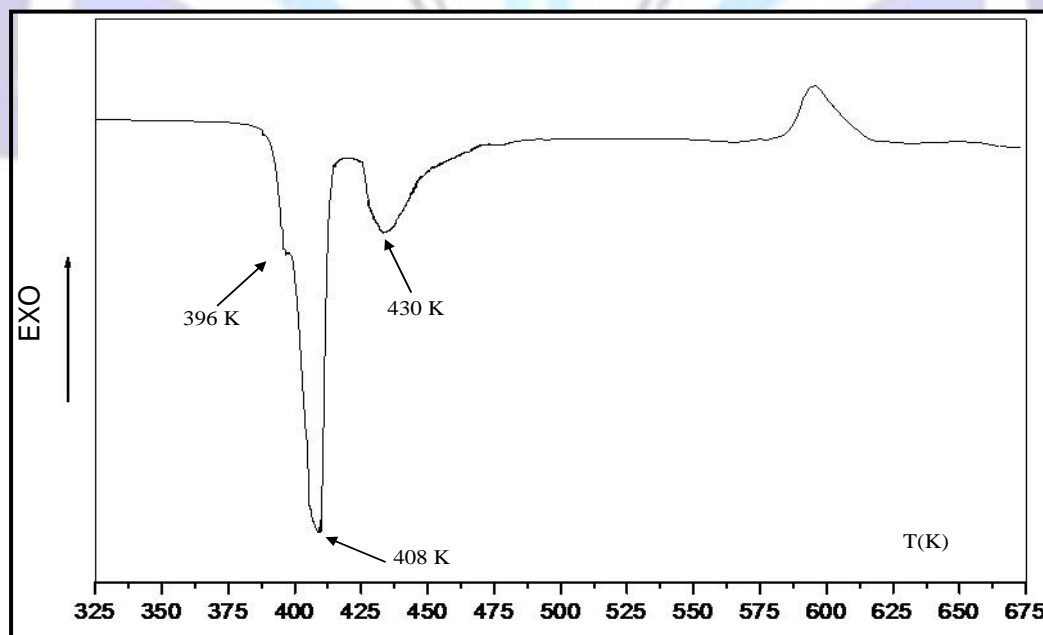


Fig 1. DSC heating curve of $Tl_2HAsO_4.Te(OH)_6$ material.



By comparison with the $\text{Ti}_2\text{SeO}_4\text{Te}(\text{OH})_6$ (TlSeTe) material that exhibits three endothermic peaks at 373, 395 and 437 K. The first peak at 373 K was attributed to a structural phase transition. Whereas, the second peak, at about 395 K, was assimilated to a ferroelectric paraelectric phase transition. The third peak detected at 437 K was assigned to ionic protonic conduction type [10]. We can estimate that the first and the second peaks can be assimilated to an order-disorder phase transitions. The third peak detected at $T = 430$ K may be of ionic protonic conduction type. The calculated transition enthalpies, for the first transition at $T_1 = 408$ K and for the third anomaly at $T_3 = 430$ K are respectively $\Delta H_1 = 937.26 \text{ Jg}^{-1}$ and $\Delta H_3 = 400.38 \text{ Jg}^{-1}$ [1, 2, 10].

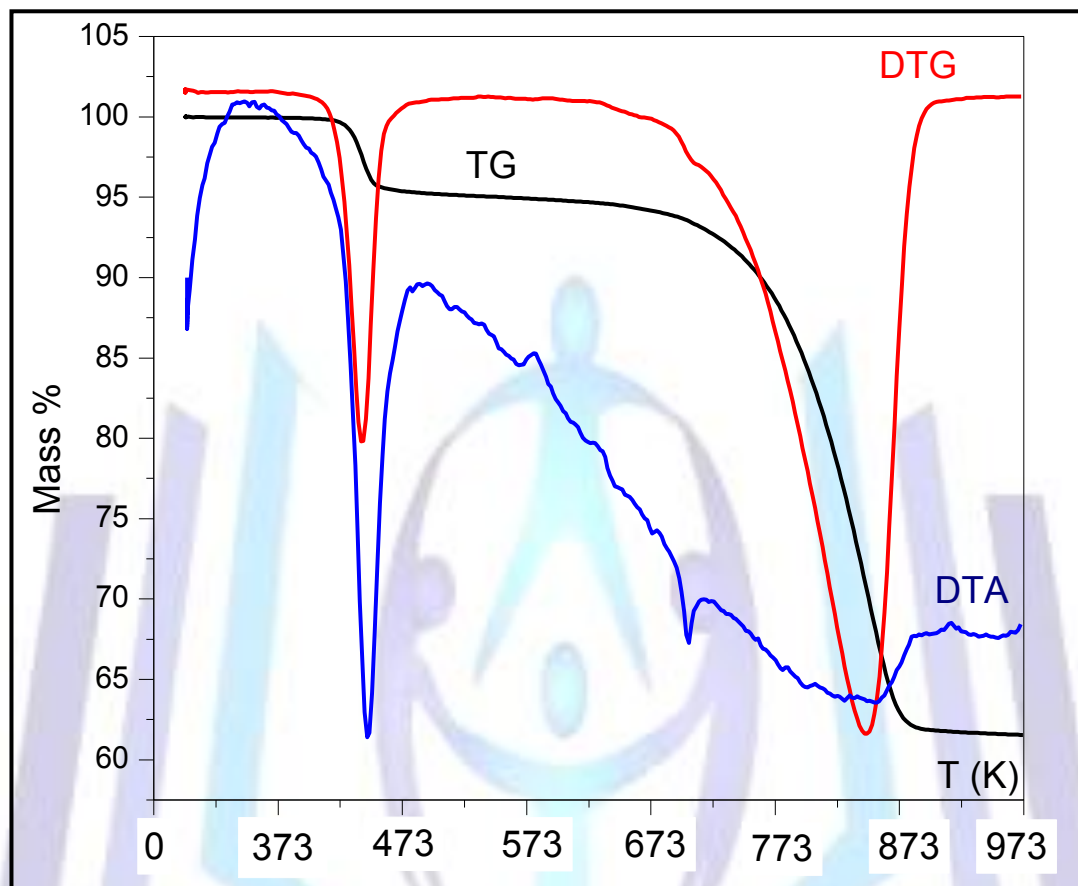


Fig 2. TG-DTA, and DTG heating curve of $\text{Ti}_2\text{HAsO}_4\text{Te}(\text{OH})_6$ compound.

3.2. Structural study:

At room temperature, the structure of (TlAsTe) is triclinic with unit cell parameters are $a = 7.100(10) \text{ \AA}$, $b = 7.281(13) \text{ \AA}$, $c = 8.383(11) \text{ \AA}$, $\alpha = 76.91(1)^\circ$, $\beta = 87.16(1)^\circ$, $\gamma = 66.96(2)^\circ$, $Z = 2$ and $V = 388.19(1) \text{ \AA}^3$. While the (TlSeTe) crystallizes in the monoclinic system $P2_1/c$ with unit cell parameters are $a = 12.358(3) \text{ \AA}$, $b = 7.231(1) \text{ \AA}$, $c = 11.986(2) \text{ \AA}$, $\beta = 111.09(2)^\circ$, $Z = 4$ and $V = 999.6(4) \text{ \AA}^3$ [10]. The volume of the asymmetric unit for the (TlSeTe) is slightly higher due to the differences on anion sizes. The projections of the (TlAsTe) on the ab and ac planes (Figure 3 and Figure 4) show that the structure seems to be a lamellar one. In fact, we observe two AsO_4 tetrahedra layers and one TeO_6 octahedra layer, alternating with Ti^+ cations, connected by $\text{O-H}\dots\text{O}$ hydrogen bonds. Besides, we can describe our structure as chain of planes of different polyhedra linked by $\text{O-H}\dots\text{O}$ hydrogen bond and planes of Ti^+ cations. The sets of these planes are connected by electrostatic actions of the Ti^+ cations as shown in Figure 4 and Figure 5.

Table 1. Main crystallographic features X-ray diffraction parameters of $\text{Ti}_2\text{HAsO}_4\cdot\text{Te}(\text{OH})_6$.

Crystal data	
Formula	$\text{Ti}_2\text{HAsO}_4\cdot\text{Te}(\text{OH})_6$
Crystal system	Triclinic
Space group	$\bar{P}1$
a (Å)	7.100(10)
b (Å)	7.281(13)
c (Å)	8.383(11)
α (°)	76.91(1)
β (°)	87.16(1)
γ (°)	66.96(2)
V (Å ³)	388.19(1)
Z	2
Formula weight (g mol ⁻¹)	778.32
μ (mm ⁻¹)	49.419
ρ_{cal} (g cm ⁻³)	6.761
T(K)	293(2)
Experimental details	
Diffractometer	Agilent diffraction Xcalibur Gemini RCCD
Min/Max Brag angle (°)	3.44 / 31.14
Index ranges	-9 ≤ h ≤ 8 -10 ≤ k ≤ 9, -10 ≤ l ≤ 12
Parameters refined	110
Reflections unique	3219
Reflections observed: $F_0 > 4\sigma(F_0)$	2223
$R_1 = [F^2 > 4\sigma(F)^2]$	0.069
$WR_2 (F^2)$	0.077
R(int)	0.082
$\Delta\rho$ max (eÅ ⁻³)	5.771
$\Delta\rho$ min (eÅ ⁻³)	-6.022


Table 2. Fractional atomic coordinates and equivalent isotropic displacement parameters (U_{iso} for H atoms) for $Tl_2HASO_4 \cdot Te(OH)_6$.

Atoms	X	Y	Z	U_{iso} /équiv
Tl ₁	0.397(11)	0.262(11)	0.011(9)	0.024(3)
Tl ₂	0.847(11)	0.385(12)	0.373(9)	0.027(3)
Te	0.500	0.000	0.500	0.010(3)
As	0.162(2)	0.714(2)	0.174(18)	0.011(4)
O ₁	0.458(2)	0.275(18)	0.495(15)	0.018(2)
O ₂	0.642(2)	0.010(19)	0.299(16)	0.021(3)
O ₃	0.248(2)	0.102(19)	0.374(16)	0.019(2)
O ₂₁	0.200(2)	0.929(2)	0.148(17)	0.026(3)
O ₂₂	0.386(18)	0.508(18)	0.198(17)	0.021(3)
O ₂₃	0.004(2)	0.686(2)	0.324(16)	0.027(3)
O ₂₄	0.057(2)	0.714(2)	-0.011(17)	0.025(3)
H ₁	0.40(4)	0.37(3)	0.44(3)	0.050
H ₂	0.71(4)	0.05(5)	0.22(3)	0.050
H ₃	0.25(5)	0.05(5)	0.30(3)	0.050
H ₂₄	-0.03(4)	0.82(3)	-0.04(4)	0.050

Table 3. Anisotropic displacement parameters of $Tl_2HASO_4 \cdot Te(OH)_6$ compound

Atoms	U_{11}	U_{22}	U_{33}	U_{23}	U_{13}	U_{12}
Tl ₁	0.0222(4)	0.0233(4)	0.0288(4)	-0.0084(3)	0.0027(3)	-0.0070(3)
Tl ₂	0.0222(4)	0.0334(5)	0.0232(4)	-0.006(3)	0.0007(3)	-0.0065(3)
Te	0.0088(6)	0.0075(6)	0.0084(6)	0.0031(4)	-0.0024(4)	0.0007(4)
As	0.0104(7)	0.0080(6)	0.0101(7)	0.0006(5)	-0.0004(5)	0.0010(5)
O ₁	0.027(6)	0.007(5)	0.014(5)	-0.001(4)	-0.003(5)	-0.001(4)
O ₂	0.019(6)	0.013(5)	0.018(6)	0.003(4)	0.009(5)	0.002(4)
O ₃	0.022(6)	0.015(5)	0.021(6)	-0.002(4)	-0.008(5)	-0.010(5)
O ₂₁	0.027(7)	0.026(7)	0.024(7)	-0.009(6)	-0.010(5)	-0.005(5)
O ₂₂	0.012(5)	0.010(5)	0.030(7)	0.005(4)	-0.006(5)	0.003(5)
O ₂₃	0.022(6)	0.025(6)	0.018(6)	0.004(5)	0.009(5)	-0.001(5)
O ₂₄	0.036(8)	0.020(6)	0.020(6)	-0.010(6)	-0.007(5)	-0.004(5)

The anisotropic displacement exponent takes the form: $\text{Exp} [-2\pi^2 \sum_i \sum_j U_{ij} h_i h_j a_i a_j^*]$.

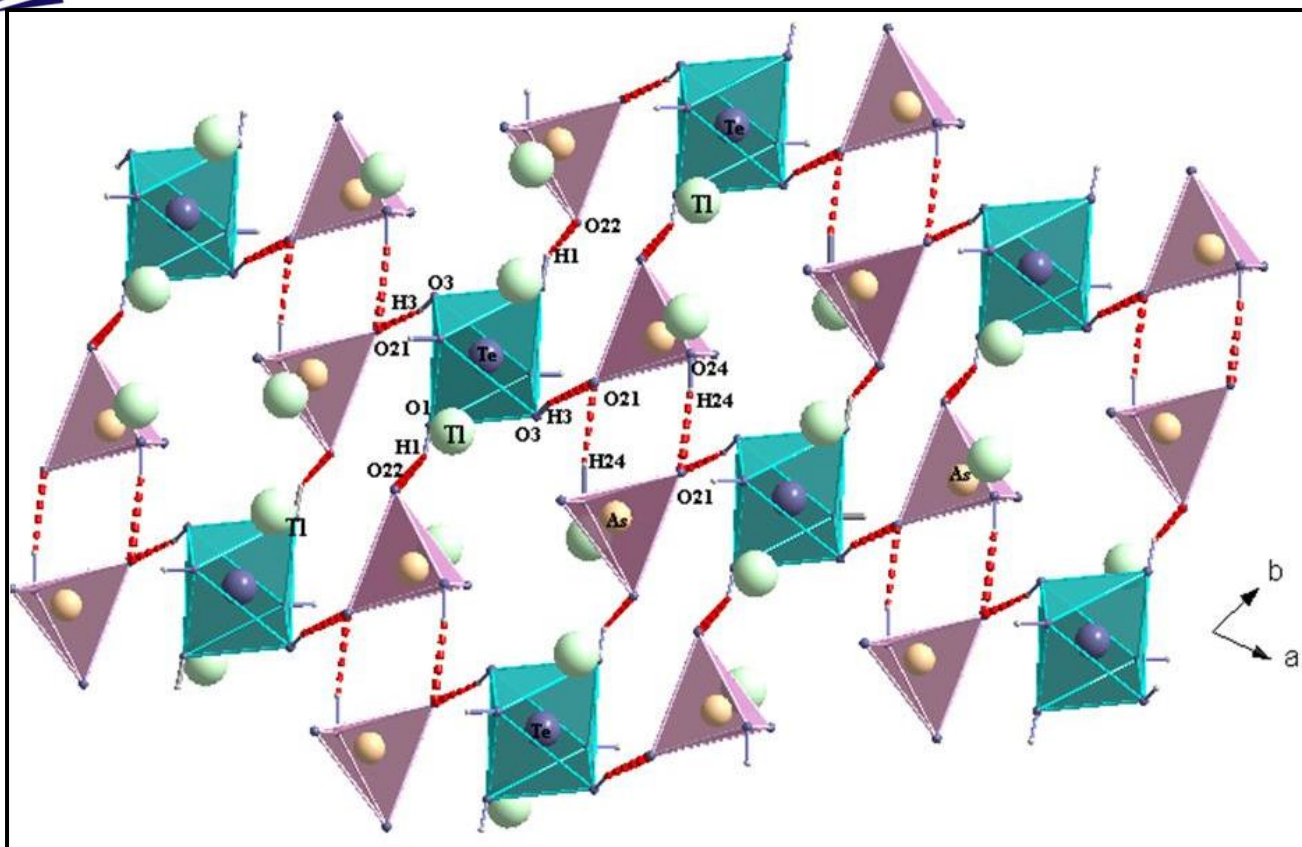


Fig 3: Hydrogen bonds in $Tl_2HAsO_4 \cdot Te(OH)_6$ material.

The Te atom in the $(TlAsTe)$ structure occupies a general position, with Te-O bond length varies between 1.900(12) Å and 1.918(12) Å, forming angles values range from 88.17(5)° to 91.83(5)°. Whilst in the cubic system $F4_132$, the $Te(OH)_6$ structure shows Te-O bond length equal to 1.917 Å with the O-Te-O angles varying from 88.3(1)° to 93.6(1)° [11]. In the $Tl_2SeO_4 \cdot Te(OH)_6$, the Te-O bond length ranging from 1.892(6) Å to 1.937(3) Å, the O-Te-O varies from 87.3(3)° to 92.7(7)° [10]. Whereas in the $Tl_2SO_4 \cdot Te(OH)_6$ structure, the Te-O bond lengths are between 1.912(6) Å and 1.941(6) Å, the O-Te-O ranging from 87.9(4)° to 94.1(4)° [12]. The structural result shows that the TeO_6 octahedra, in this new structure, is more regular than those found in $Tl_2SeO_4 \cdot Te(OH)_6$ and $Tl_2SO_4 \cdot Te(OH)_6$ structures.

In the tetrahedral group, the As-O distances vary from 1.674(14) Å to 1.751(14) Å. The O-As-O angles are between 103.61(7)° and 113.00(7)°. From these values, we can observe an important deformation of these groups compared with those in the $Rb_2HAsO_4 \cdot Te(OH)_6$ where As-O distances are between 1.661(14) Å and 1.725(15) Å, and the O-As-O angles are between 104.69(7)° and 113.72(8)° [6]. The deformation may be due to the difference between the cations bulk. Whereas, in the H_3AsO_4 the bond length As-O varying from 1.66 Å to 1.71 Å [13].

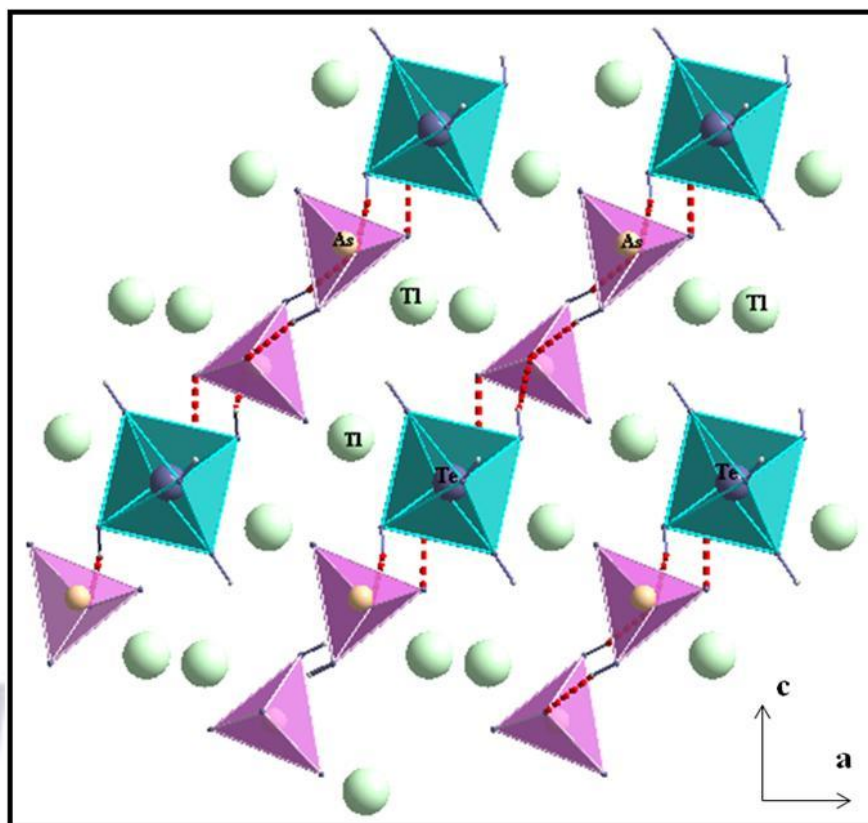


Fig 4: Arrangement of polyhedra layers of $Ti_2HAsO_4 \cdot Te(OH)_6$ in the ac plane.

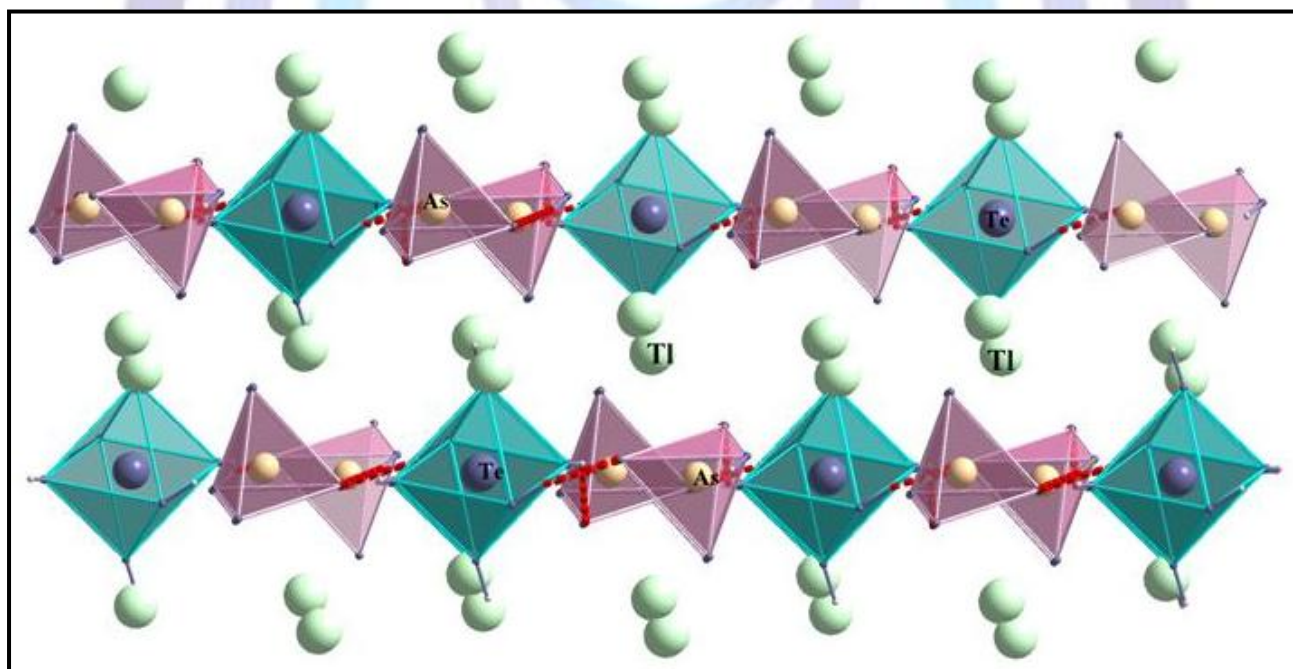


Fig 5: Arrangement of polyhedra planes and cations planes in the $Ti_2HAsO_4 \cdot Te(OH)_6$ material.

In $TiAsTe$ structure the Ti^{+} cations occupies two independent positions. According to Figure 6 both Ti^{+} cations are coordinated by eight oxygen atoms similarly to those in $Ti_2SeO_4 \cdot Te(OH)_6$ structure. The TiO_8 dodecahedra are considerably distorted, being the $Ti-O$ distances ranging between 2.603(18) Å and 3.734(15) Å. The bond lengths and the bond angles are listed in Table 4.


 Table 4. Main inter atomic distances (Å) and bond angles (°) in the $\text{TI}_2\text{HASO}_4\cdot\text{Te}(\text{OH})_6$ material.

Tellurate groups	
Te-O distances (Å)	
Te-O ₁	1.900(12)
Te-O ₁ ^a	1.900(12)
Te-O ₂	1.918(12)
Te-O ₂ ^a	1.918(12)
Te-O ₃	1.913(12)
Te-O ₃ ^a	1.913(12)
O-Te-O angles(°)	
O ₁ -Te-O ₃ ^a	91.83(5)
O ₁ -Te-O ₃	88.17(5)
O ₁ -Te-O ₂	90.63(5)
O ₁ -Te-O ₂ ^a	89.37(5)
O ₃ -Te-O ₂ ^a	91.03(6)
O ₃ -Te-O ₂	88.97(6)
Arseniate groups	
As-O distances (Å)	
As-O ₂₁	1.674(14)
As-O ₂₂	1.675(11)
As-O ₂₃	1.678(13)
As-O ₂₄	1.751(14)
O-As-O angles (°)	
O ₂₁ -As-O ₂₂	110.92(7)
O ₂₁ -As-O ₂₃	113.00 (7)
O ₂₁ -As-O ₂₄	107.33(7)
O ₂₂ -As-O ₂₃	112.32(7)
O ₂₂ -As-O ₂₄	103.61(7)
O ₂₃ -As-O ₂₄	109.09(8)
Thallium coordination (Å)	
Tl₁	Tl₂
O ₂₄ 3.160(14)	O ₂ 3.734(15)
O ₂₄ 3.208(16)	O ₂₄ 3.257 (16)
O ₂₂ 2.931(17)	O ₃ ^b 2.780(17)
O ₂₁ 3.040(17)	O ₂₅ ^c 2.760(17)
O ₂ 2.850(16)	O ₂₅ ^d 2.665(15)
O ₃ 3.281(16)	O ₁ 2.973(15)
O ₂₁ 3.230(16)	O ₁ 3.233(16)
O ₂₂ 2.603(18)	O ₂₂ 3.359(17)

 Symmetry code : (a) $-x+1, -y, -z+1$; (b) $x-1, y, z$; (c) $x+1, y, z$; (d) $-x+1, -y+1, -z+1$.

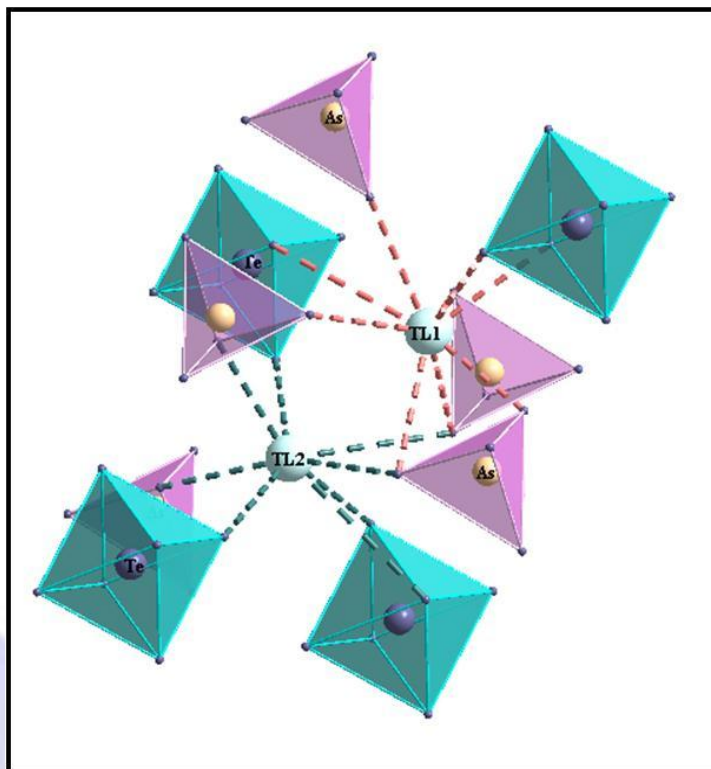


Fig 6: Thallium coordination.

The $Tl_2HASO_4.Te(OH)_6$ structure is stabilized thanks to hydrogen bonds assured by protons belonging to hydroxide groups linked on the one hand the octahedra on tetrahedra groups. On the other hand, they assured the connectivity between the nearest tetrahedra with $O_{24}-H_{24}...O_{21}$ hydrogen bond. According to Figure 3 and Figure 4, we can deduce that the (TlAsTe) structure is a succession of two planes of tetrahedra then one plane of octahedral linked with strong O-H...O hydrogen bond related to the Brown theory [14]. In fact, the O...O bonds varying from 2.561 Å to 2.623 Å. The O-H...O angles ranging from 141.10° to 170°. These values are different to those found in $Rb_2HASO_4.Te(OH)_6$ material where the O...O bonds range from 2.471 Å to 2.685 Å. The O-H...O angles are between 114.32° [6] and 170.17°.

Table 5. Geometrical characterization of hydrogen bonds in the $Tl_2HASO_4.Te(OH)_6$ compound.

O...O (Å)	O-H (Å)	O...H (Å)	O-H...O (°)
$O_{24}...O_{21} = 2.561$	$O_{24}-H_{24} = 0.769(5)$	$O_{21}...H_{24} = 1.801$	$O_{24}-H_{24}...O_{21} = 170$
$O_1...O_{22} = 2.623$	$O_1-H_1 = 0.739(3)$	$O_{22}...H_1 = 2.007$	$O_1-H_1...O_{22} = 141.10$
$O_3...O_{21} = 2.601$	$O_3-H_3 = 0.823(12)$	$O_{21}...H_3 = 1.786$	$O_3-H_3...O_{21} = 166.89$

3.3. Vibrational studies:

In the present investigation, IR and Raman spectroscopic studies of $Tl_2HASO_4.Te(OH)_6$ have been performed and analyzed in order to confirm the presence and the independence of the two anions (AsO_4^{3-} and TeO_6^{6-}). These two analyses give more importance to hydrogen bonds in the new crystal lattice. Raman and infrared spectra of $Tl_2HASO_4.Te(OH)_6$, at room temperature, are shown in Figure 7 and Figure 8, respectively. The observed Raman and IR bands are given in Table 6.

3.3.1 Interpretation of Raman spectrum:

According to the literature of the addition compounds based on tellurate and materials stable due to the hydrogen bonds, we could interpret the different peaks observed in Figure 7.

In fact, the bands which appear at 60 cm^{-1} , 77 cm^{-1} and 96 cm^{-1} are attributed to the lattice mode. While the peaks at 153, 184 and 234 cm^{-1} are probably assigned to hydrogen bonding $\nu(O-H...O)$ [3, 15].

The intense and narrow peak at 634 cm^{-1} is assigned to $\nu_1(\text{TeO}_6)$ [16], while in the others tellurates alkaline, this vibration mode appears at peak with frequency superior than 634 cm^{-1} . Thus, in the $\text{Rb}_2\text{HAsO}_4\cdot\text{Te}(\text{OH})_6$, the $\nu_1(\text{TeO}_6)$ observed at 673 cm^{-1} [6]. The shoulder detected at 606 cm^{-1} is attributed to $\nu_2(\text{TeO}_6)$ [17, 18]. However, the peak at 396 cm^{-1} is assimilated to $\nu_4(\text{TeO}_6)$ [18]. In addition the peak detected at 375 cm^{-1} is attributed to $\nu_5(\text{TeO}_6)$ [17-19]. Whereas the band which appears at 290 cm^{-1} is attributed to $\nu_6(\text{TeO}_6)$ [16]. Vibrational analysis for the isolated AsO_4^{3-} anion with point group Td leads to four modes: $A_1(\nu_1)$, $E(\nu_2)$, $2F_2(\nu_3$ and $\nu_4)$. The ν_1 mode is the totally symmetric stretching vibrational mode of the AsO_4^{3-} anion, ν_2 is the doubly degenerate bending mode, ν_3 and ν_4 are the triply degenerate stretching mode and bending mode respectively. In the free AsO_4^{3-} anion, they are found at 837 , 349 , 878 , and 463 cm^{-1} , respectively. Based on this interpretation and examining the Raman spectra, we can note that A_1 band may shift to different wave numbers and the doubly degenerate E and triply degenerate F modes may give rise to several new A_1 , B_1 , and/or E vibrations [20, 21]. In fact, we can assimilate the band which appears at 721 cm^{-1} to $\nu_1(\text{AsO}_4)$. While the three peaks observed at 797 cm^{-1} , 806 cm^{-1} and 823 cm^{-1} are relating to the triply degenerate bending and stretching mode $\nu_3(\text{AsO}_4)$ [20, 21]. The two regions ($300\text{-}350\text{ cm}^{-1}$ and $400\text{-}450\text{ cm}^{-1}$) are assigned respectively to doubling degenerate bending mode $\nu_2(\text{AsO}_4)$ and $\nu_4(\text{AsO}_4)$ [22]. Thus, the peaks observed at 320 cm^{-1} and 341 cm^{-1} are attributed to $\nu_2(\text{AsO}_4)$. Whilst the band appears at 410 cm^{-1} is assimilated to $\nu_4(\text{AsO}_4)$.

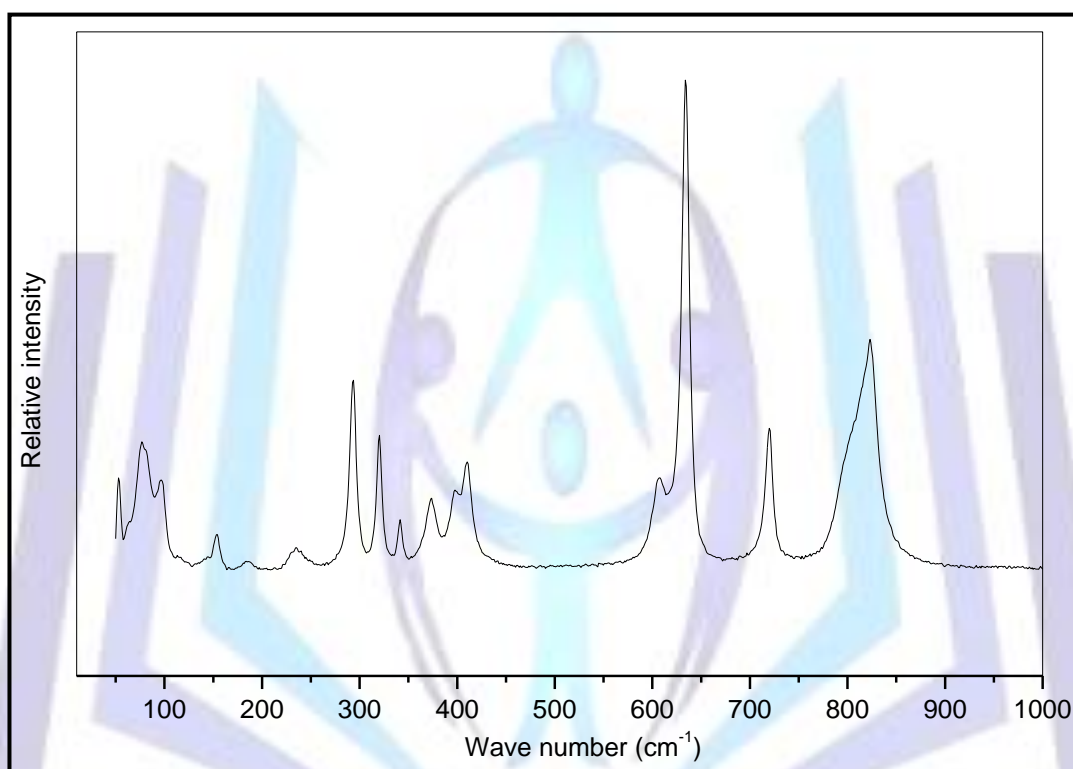


Fig 7: Raman spectra at room temperature of $\text{Ti}_2\text{HAsO}_4\cdot\text{Te}(\text{OH})_6$ compound.

3.3.2 Interpretation of IR spectrum:

In order to confirm the results got by the Raman spectra and to gain more information on the strong O-H...O hydrogen bond in this new structure, we have undertaken the IR study, at room temperature, in the frequency range ($4000\text{--}500\text{ cm}^{-1}$).

The band appeared at 634 cm^{-1} is attributed to $\nu_1(\text{TeO}_6)$ [16]. The peak detected at 1037 cm^{-1} is associated to the stretching bond δ (Te-OH) [3, 20].

In addition, the IR peak observed at 713 cm^{-1} is associated to the vibration mode $\nu_1\text{ AsO}_4^{3-}$. Whilst the three peaks observed at 798 cm^{-1} , 857 cm^{-1} and 897 cm^{-1} are related to the vibration mode $\nu_3\text{ AsO}_4^{3-}$ [20, 21].

The δ (As-O...H) bending vibration mode appears in the region between 1222 cm^{-1} and 1312 cm^{-1} [15, 23, 24]. While the peaks detected at 1567 cm^{-1} and 1689 cm^{-1} are assigned to the presence of the As-O...H free and the presence of strong hydrogen bonds [25].

The peaks observed in the region being from 2300 to 2836 cm^{-1} may be assigned to the asymmetric and symmetric stretching vibrations of the O-H group of strong hydrogen bond [23, 26, 27].

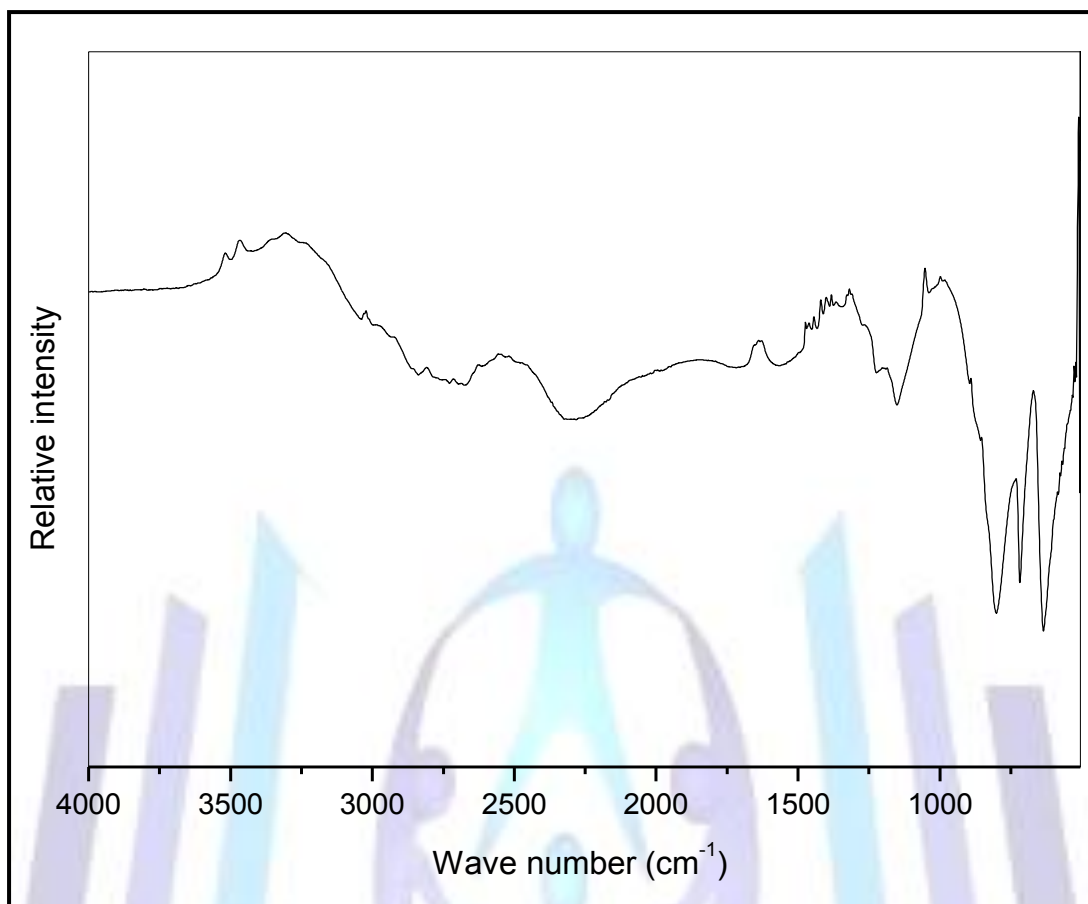


Fig 8: IR spectrum at room temperature of $\text{TI}_2\text{HASO}_4 \cdot \text{Te}(\text{OH})_6$ compound.

Table 6. Infrared and Raman frequencies for $\text{TI}_2\text{HASO}_4 \cdot \text{Te}(\text{OH})_6$ material.

IR (cm^{-1})	Raman (cm^{-1})	Assignment
-	60	} Lattice mode
-	77	
-	96	
-	153	} $\nu(\text{O-H}\dots\text{O})$
-	184	
-	234	
-	290	$\nu_6(\text{TeO}_6)$
-	320	} $\nu_2(\text{AsO}_4)$
-	341	
-	375	$\nu_5(\text{TeO}_6)$
-	396	$\nu_4(\text{TeO}_6)$
-	410	$\nu_4(\text{AsO}_4)$
634	634	$\nu_1(\text{TeO}_6)$
-	606	$\nu_2(\text{TeO}_6)$



713	721	$\nu_1(\text{AsO}_4)$
798 } 857 } 897 }	797 } 806 } 823 }	$\nu_3(\text{AsO}_4)$
1037		$\delta(\text{Te-OH})$
1222 } 1257 } 1312 }	-	$\delta(\text{As-O...H})$
1567 } 1689 }	-	As-O...H free and the strong hydrogen bonds.
2300 } 2670 } 2800 }	-	$\nu(\text{OH})$

4. MAGNETIC PROPERTIES.

The crystals of $\text{Ti}_2\text{HAsO}_4 \cdot \text{Te}(\text{OH})_6$ substances are massive enough to reach a magnetic response that could be higher than the signal detection for VSM option ($>10^{-6}$ emu). Therefore, we have crushed the crystal with agate mortar and pestle in order to obtain a powder specimen. Flattened monocrystal had mounted on a quartz paddle-shaped sample holder and fixed with vacuum grease and PTFE tape. Powder materials had compressed inside a polypropylene powder holder that fit in a brass through-shaped sample holder. These materials have been supplied by Quantum Design Company [28]. Previously, the mass of all samples have been accurate determinate by a Sartorius balance (model CP225D).

Specific sequences have design in order to carry out the magnetic characterization at each composition: isothermal magnetization curves (for example, $M(H, T=300 \text{ K}).\text{seq}$), thermal variation of magnetization at fixed magnetic field (e.g., $M(H=1\text{kOe}, T).\text{seq}$). For diamagnetic substance a single-valued function between both magnitudes is observed and at regular temperatures and magnetic fields is given by the linear relation: $\sigma = \chi_m H$.

Diamagnetic substance: $\text{Ti}_2\text{HAsO}_4 \cdot \text{Te}(\text{OH})_6$.

A thorough study, as an example for a diamagnetic material, was carried out over the $\text{Ti}_2\text{HAsO}_4 \cdot \text{Te}(\text{OH})_6$ sample, where there is not a magnetic ion on its composition. It is worth noting that this sample have been mounted on paddle-shape sample holder which produces a lower level of noise in the measurement, will lead more accurate determination on magnetization (Table 7).

Table 7. Mass susceptibilities at T=300 K for $\text{Ti}_2\text{HAsO}_4 \cdot \text{Te}(\text{OH})_6$ substance.

Substance	m (kg)	A (u)	χ_m (m^3/kg)
$\text{Ti}_2\text{HAsO}_4 \cdot \text{Te}(\text{OH})_6$	1.215×10^{-5}	777.30	$-6.892(8) \times 10^{-9}$

The Figure 9 shows the variation of χ_m with temperature derived from temperature-dependence of σ at applied magnetic field of $\mu_0 H = 14 \text{ T}$. A remarkable peak is observed around 50 K that can ascribe to oxygen trapped by the Teflon tape used to wrap the sample [29].

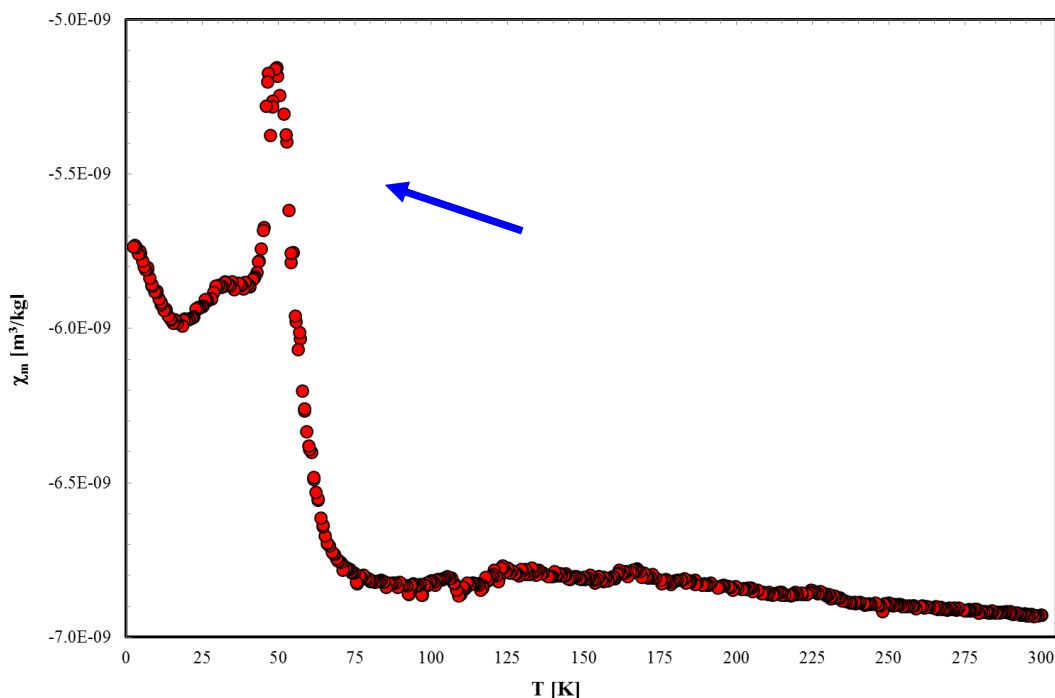


Fig 9: Temperature-dependence of the mass susceptibility, χ_m , for $Ti_2HAsO_4 \cdot Te(OH)_6$ substance. The blue arrow points out the paramagnetic contamination due to oxygen migrated from PTFE tape.

In this way, above this temperature χ_m is almost constant; whereas below it, paramagnetic oxygen contamination produces a slight increase on the value of χ_m measured. Paramagnetic contribution, from oxygen migrating from the PTFE tape, is even clearly visible if an observer compares the isothermal magnetization curves at 300 and 2 K (Figure 10). The difference between both curves has roughly the shape of a Brillouin function, which is a feature of paramagnetic substances at low temperature and/or high applied magnetic field and which should be produced by the presence of the paramagnetic oxygen.

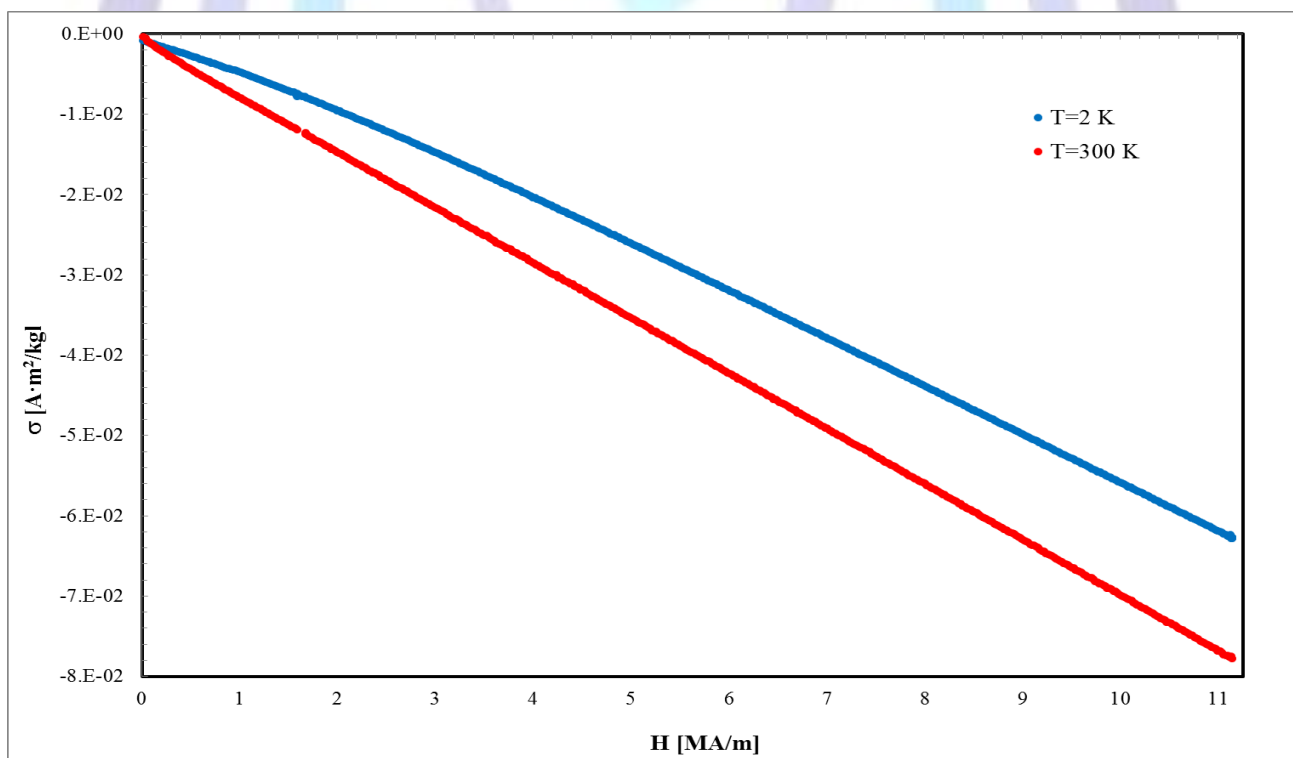


Fig 10: Isothermal magnetic curves of $Ti_2HAsO_4 \cdot Te(OH)_6$ substance measured at 2 y 300K.



5. CONCLUSION:

In the present work, the single crystal of the compound $Tl_2HASO_4 \cdot Te(OH)_6$ synthesized by slow evaporation, at room temperature, has been studied. It crystallizes in the triclinic system PT.

The cohesion of this structure is assured by the strong hydrogen bond and the electrostatic actions of the Tl^+ cations. The Raman study shows that the bending and stretching mode $\nu_3(AsO_4)$ is triply degenerate while the bending mode $\nu_2(AsO_4)$ is doubly degenerate. The magnetic characterization of the thallium hydrogen arsenate tellurate shows that the $(TlAsTe)$ behaves as diamagnetic material.

ACKNOWLEDGMENTS

This work is supported by the minister of Higher Education and Research of Tunisia. All the authors would like to express their thanks to Dr. H. Khemakhem for his help in the spectroscopies Raman measurements.

REFERENCES:

- [1] Litaïem, H., Dammak, M., Mhiri, T., and Cousson, A. J. *Alloys Comp*, 396 (2005) 34.
- [2] Dammak, M., Litaïem, H., and Mhiri, T. J. *Alloys Comp*, 416 (2006) 228.
- [3] Dammak, M., Khemakhem, H., Mhiri, T., Kolsi, A.W., and Daoud, A. J. *Alloys Comp*, 280 (1998) 107.
- [4] Dammak, M., Khemakhem, H., and Mhiri, T. J. *Phys. Chem. Solids*, 62 (2001) 2069.
- [5] Khemakhem, H. *Ferroelectric* 234 (1999) 47.
- [6] Bechibani, I., Litaïem, H., Ktari, L., Lhoste, J., and Dammak, M. *J. Mol. Struct*, 1045 (2013) 199.
- [7] Palatinus, L., and Chapuis, G. SUPERFLIP, program for the solution of crystal structures, *J. of Appl. Cryst.*, 40 (2007) 786.
- [8] Sheldrick, G. M. SHELXL 97, program for the solution of crystal structures, univ. of Göttingen (Germany) (1997).
- [9] Brandenburg, K., and Berndt, M. DIAMOND, Version 2.1.b, Crystal impact Gb R Bonn, Germany (1999).
- [10] Ktari, L., Abdelhedi, M., Bouhleb, N., Dammak, M., and Cousson, A. J. *Mater. Res. Bull.* 44 (2009) 1792.
- [11] Mullica, D. F., Korp, J. D., Milligan, W. O., Beall, G. W., and Bernal, I. *Acta Crystallogr.*, B36 (1980) 2565.
- [12] Zilber, R., Durif, A., and Averbouch-Pouchet, M.T. *Acta Crystallogr.*, B38 (1982) 1554.
- [13] Lee, C., and Harrison, W. T. A. J. *Acta Crystallogr.*, C 63 (2007) 308.
- [14] Brown, L. D. J. of *Acta Crystallogr.*, A 32 (1976) 24.
- [15] Naili, H., Mhiri, T., and Jaud, J. J. *Solid State Chem*, 16 (2001) 161.
- [16] Ktari, L., Dammak, M., Hadrich, A., Cousson, A., Nierlich, M., Romain F., and Mhiri, T. *J. Solid State Sci* 6 (2004) 1393.
- [17] Dammak, M., Khemakhem, H., Mhiri, T., Kolsi, A.W., and Daoud, A. J. *Solid State Chem*, 145 (1999) 612.
- [18] Litaïem, H., Dammak, M., Ktari, L., Kammoun, S., and Mhiri, T. J. *Phase transitions* vol 77, N 11 (2004) 929.
- [19] Chabchoub, N., Khemakhem, H., and Von der mühl, R. J. *Alloys Comp*, 386 (2005) 319.
- [20] Frost, R. L., Sejkora, C. J., Plasil, J., Reddy, B. J., and Keeffe, E. C. *Spectrochimica Acta Part A* 78 (2011) 494.
- [21] Jrifi, A., El Jazouli, A., Chaminade, J. P., and Couzi, M. *Powder Diffraction* 24, 3 (2009) 200.
- [22] Frost, R. L. *Spectra Chimica Acta.*, A71 (2009) 1788.
- [23] Amri, M., Zouari, N., Mhiri, T., and Gravereau, P. J. *Alloys Comp*, 477 (2009) 68.
- [24] Amri, M., Zouari, N., Mhiri, T., Pechev, S., Gravereau, P., and Von Der Mühl, R. J. *Phys. Chem. Solids*, 68 (2007) 1281.
- [25] Bortun, A. I., Bortun, L. N., Clear field Trobajo, A. C., and Garcia, J. R. J. *Mater. Res. Bull*, Vol 33, 4 (1998) 583.
- [26] Hadrich, A., Lautie, A., and Mhiri, T. J. *Raman Spectroscopy*, 31 (2000) 587.
- [27] Hadzi, D., and Bratos, S. *The hydrogen bond, recent development in theory and experiments*, North Holland, Amsterdam, Tome 2 (1977) 588.
- [28] VSM sample mounting techniques, Quantum Design Application Note 1096-306.
- [29] Ard W.B., Shields H., and Gordy W., *J. Chem. Phys*, 23 (1955) 1727.
- [30] Fabry, J., Loub, J., and Feltl, L. J. *Thermal Analysis*, 24 (1982) 95.