



Green Synthesis of Silver Nanoparticles using *Strobilanthes flaccidifolius* Nees. Leaf Extract and its Antibacterial Activity

^aSujata D. Wangkheirakpam, ^bWangkheirakpam Radhapiyari Devi, ^bChingakham B Singh and ^aWarjeet S. Laitonjam*

^aChemistry Department, Manipur University
Canchipur -795003, Imphal, Manipur, India

^bDepartment of Biotechnology,
Institute of Bioresources and Sustainable Development
Imphal-795001, Manipur

*warjeetlaitonjam@yahoo.co.in, warjeet@yahoo.com

ABSTRACT

The leaf extract of *Strobilanthes flaccidifolius* Nees. was used for the synthesis of silver nanoparticles through a green technique of synthesis. The nanoparticles was characterized by UV-VIS spectroscopy which proves the formation silver nanoparticles. FTIR (Fourier Transmission infra red spectroscopy) study was carried out to assess the biomolecule as indigo precursors, Energy dispersion X-ray analysis(EDX) data further proves it. EPR (Electron paramagnetic resonance technique) shows the free radical in silver neutral state and XRD(X-ray diffraction technique) also reports silver neutral formation. The morphology and the shape of the silver nanoparticles were determined by Scanning electron microscopy(SEM) and Tunneling electron microscopy (TEM). The nanoparticles adopted spherical morphology and the size ranging from 6nm to 54.11nm and average size was determined as 12.15 ± 5.3 nm. The nanoparticles had antimicrobial activity.

Keywords

Green synthesis; *Strobilanthes flaccidifolius* Nees. Silver nanoparticles; Indigo precursors; Antimicrobial activity.

Council for Innovative Research

Peer Review Research Publishing System

Journal: Journal of Advances in Chemistry

Vol. 8, No. 1

editor@cirworld.com

www.cirworld.com, member.cirworld.com



1. INTRODUCTION

One of the most active areas of research in modern materials science is the field of nanotechnology. The synthesis of gold nanoparticles inside life plants in alfalfa roots demonstrated for the first time by Gardea-Torresday et al. [1]. Silver nanoparticles were synthesized from the same plant inside the plant [2]. Many other work on biosynthesis from plants were carried out in *Aloe vera*, *Cinnamon camphora*, *Capsicum annum* L, *Medicago sativa*, *Brassica juncea*, *B. chicory* and *Cymbopogon flexuosus* [3]. Mude et al. studied the extracellular synthesis of *in vitro* generated extract of *Carica papaya* for the synthesis of AgNPs. The formation of silver nanoparticles were reported when aqueous silver ions (AgNO_3 1mM) was reacted with callus extract [4]. Song and Kim studied the extracellular synthesis of metallic AgNO_3 using five plant leaf extracts, viz Pine, Persimmon, *Gingko*, *Magnolia* and *Plantanus*. Stable AgNO_3 nanoparticles ranging from 5-500 nm were formed by treating aqueous AgNO_3 with the plant extracts acting as reducing agents [5]. Further polysaccharides (heparin, hyaluronic acid, chitosan, cellulose, starch, dextrose and alginic acid) and pure phytochemicals (aloin A, apiin, aloesin and guavanoic acid) were used to synthesis nanoparticles which had properties like the parent polysaccharides or phytochemicals [6]. The methanol and aqueous extracts of fruits of *Pseudocydonia sinensis* were used for synthesizing silver nanoparticles. The nanoparticles were characterized by Energy dispersive X-ray analysis, X-ray diffraction, Tunneling electron microscopy, FTIR and UV-VIS spectroscopy. The nanoparticles were found antimicrobial activity against *Bacillus subtilis*, *Candida albicans*, *Escherichia coli*, *Staphylococcus aureus* and *Saccharomyces cerevicae*. MTT assay showed cell inhibition and cytotoxic activity [7]. Stable, poly shaped silver, and gold nanoparticles were synthesized using leaf extract of *Lonicera japonica* [8]. Studies on improvement of the bioavailability of curcumin by PLGA nanoparticles in rats; were carried out [9]. Different sized silver nanoparticles were synthesized by simply varying reaction conditions with leaf extract of *Bauhinia variegata* [10]. Biomimetic synthesis of silver nanoparticles by aqueous extract of *Azadirachta indica* leaves was carried out [11]. Green synthesis of nanoparticles using leaf and seed extract of *Syzygium cumini* L. [12], *Capsicum annum* L. extract [13] were tested. *Germanium* leaf assisted biosynthesis of silver nanoparticles was also studied [14]. Efficacy of silver nanoparticles against *Sitophilus oryzae* was studied [15] and in other research too. Antibacterial property of silver nanoparticles using *Artocarpus heterophyllus* Lam. seed extract, *Tribulus terrestris* and *Cryphonectria* sp. were investigated [16-18]. Cytotoxic effect of plant mediated silver nanoparticles using *Morinda citrifolia* root extract was performed [19]. It was seen that the antimicrobial and cytotoxic properties varied with the property of the capping of different plants. Silver nanoparticles were synthesized with different techniques using the extracts of *Coleus aromaticus*, carob, myrrh, Pine cone, banana peel, *Mimusops elengi*, *Cochlospermum gossypium*, *Eucalyptus chapmaniana*, *Hibiscus cannabinus*, *Iresine herbstii*, *Ocimum sanctum*, *Prosopis juliflora* and *Ocimum tenuiflorum* and all the nanoparticles exhibited antimicrobial activity [20-33]. The aim of study is the silver nanoparticle of *Strobilanthes flaccidifolius* Nees. and its antimicrobial activity.

2. MATERIALS AND METHODS

2.1 Plant material and preparation of extract

The freshly leaves weighing 5g were collected in separate beakers. Then it was thoroughly rinsed with distilled water. The sample was heated in 200 mL of solution of 50% ethanol in water on a steam bath till appearance of brown coloration. This brown colored extract was cooled to room temperature and filtered using Whatman filter paper (no.42). This extract was taken as the stock solution.

2.2 Synthesis

Volume of stock solution (40 mL) was made to double by addition of distilled water. The solution was treated with AgNO_3 solution (20 mL) and warmed on steam bath for approximately 10min till reddish brown colour precipitate was observed, allowed to cool at room temperature. The silver nanoparticles were collected by centrifugation process for 10 min at 150000 rpm, washed with distilled water and dried at 30°C in a closed oven [34].

2.3. Characterization of nanoparticles

2.3.1. FTIR analysis

FTIR data was recorded on a Shimadzu FTIR instruments. The sample was made into KBr pellet and the spectra were recorded. The FTIR data of both the raw extract as well as the silver nanoparticles formed was recorded.

2.3.2. UV-VIS analysis

For UV spectra the raw extract was diluted with 50% ethanol and 0.03 M AgNO_3 in the ratio of 4:1. The solution was heated on a water bath for 5min. It was allowed to stand and the absorption was recorded in a Shimadzu UV-VIS spectrophotometer. Further four fold dilution was performed before recording the spectra. For comparison and confirmation of formation of silver nanoparticles, the spectrum of the raw extract was also recorded along with the solution of the nanoparticles.

2.3.3. XRD analysis

The XRD of the sample was loaded on a PAN analytical XPERT-PRO instrument. The spectra were recorded from 20 to 80, 2 theta with step size [$^{\circ}2\theta$.] of 0.0500. Anode Material was Cu, K-Alpha1 [\AA]:1.54060. Generator settings were at 30 mA, 40 kV with scan step time [s] was 2.0000, and divergence slit size was 0.9570 and receiving slit size [mm]: was 0.2000. The Bragg-Brentano focusing geometry was used. The pattern was compared with the patterns of International Centre of Diffraction Data (ICDD) database nearest matching pattern was found with silver with XPERT HIGHSCORE.

2.3.4. SEM analysis

SEM images were recorded on FEI-QUANTA-250 electron microscope. The compound was adsorbed on a carbon sheet and loaded on the microscope. The sizes of particles were measured with the software IMAGE J and the average was calculated.

2.3.5. EPR analysis

Electron paramagnetic resonance (EPR) was recorded for free radical analysis on JEOL JES-FA200 ESR spectrometer with X-band microwave unit.

2.3.6. EDX analysis

The EDX analysis was performed on an EDAX Energy Dispersion X-ray spectrometer. The identification of the elemental constituents and estimation of the quantities were done without standard.

2.3.7. TEM analysis

For TEM analysis the compound was dispersed in ethylene glycol and measured with JEOL JEM-2100. The sizes of particles were measured with the software IMAGE J.

2.4. Antimicrobial assay

The antimicrobial activity was assessed by agar well diffusion method using 20ml of sterile Nutrient agar (NA) (Hi-Media) for testing the bacterial against *Proteus mirabilis*, *Klebsiella pneumoniae*, *Escherichia coli*, *Salmonella paratyphi* and *Pseudomonas aeruginosa* [35]. The sample was diluted in 5mg/ml in DMSO. The dilutions of the sample concentration were deposited 20 μ l on the inoculated well and left for 10 min at room temperature for the extract diffusion. Negative control was AgNO₃ solution. Ciprofloxacin (Hi-Media) for bacteria were served as positive control. The plates were inoculated with bacteria were incubated at 37°C for 24 hr. The experiment was repeated four times and the average results were recorded. The antimicrobial activity was determined by measuring the diameter of the inhibition zone around the well. The susceptibility of microbial was determined by minimum inhibitory concentration determination method [36]. The minimum inhibitory concentrations (MICs) of the sample were determined by serial dilution against the microorganisms. The minimum concentrations at which no visible growth were observed were defined as the MICs, which were expressed in mg/ml. The antimicrobial tests were calculated as a mean of three replicates and the SD was calculated using the software SPSS, version 10 (SPSS, Richmond, USA).

3 RESULTS AND DISCUSSION

3.1 Synthesis

Synthesis was performed with the introduction of AgNO₃ into the raw extract.

3.2 UV-VIS analysis

When the raw extract was treated with 0.03 M AgNO₃ in the ratio of 4:1 and treating as described in the method and recording the spectra at different intervals of time a band started appearing at 450 nm after keeping for 10min which corresponded to the surface Plasmon resonance band of noble metal silver. After 30min band started flattening as illustrated in figure1 [37].

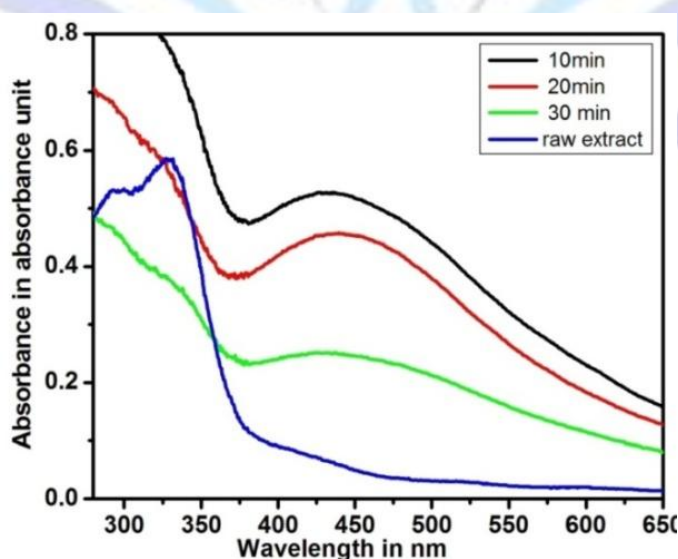


Figure 1. UV spectrum of silver nanoparticles composite of *S. flaccidifolius* at different interval of time

3.3. FTIR analysis

FTIR measurements were carried out to identify the possible biomolecules responsible for reduction, capping and efficient stabilization of the Ag nanoparticles. The representative FTIR spectra of the *S. flaccidifolius* stabilized the silver nanoparticles (Figure 2) showing significant in their respective vibrational spectra where the crude methanol extract of *S. flaccidifolius* extract consisted of mainly the glucosides indican and isatan B which were indigo precursors [38]. Figure 2 showed the presence of three bands at 3300 to 2900 cm^{-1} , 1708 cm^{-1} , 1606 cm^{-1} and 1589 cm^{-1} . The IR bands at 3300 cm^{-1} to 2900 cm^{-1} correspond to OH and small band at 3080 corresponds to NH stretchings. The IR bands at 1708 cm^{-1} and 1606 cm^{-1} were characteristic of carbonyl group whereas the band at 1589 cm^{-1} was characteristic of NH group respectively [39]. Band at 1508 cm^{-1} disappeared in the case of nanoparticles. Band at 761 cm^{-1} is because of NH wagging. These structural changes indicated that the reduction and stabilization of silver nanoparticles proceed via the coordination between N of the indigo precursors and silver ions. The FTIR studies had confirmed the fact that the hydroxyl and N form indigo precursors had the stronger ability to bind metal indicating that the glycosides could possibly form a layer covering the metal nanoparticles (i.e. capping of silver nanoparticles) to prevent agglomeration and thereby stabilized the medium.

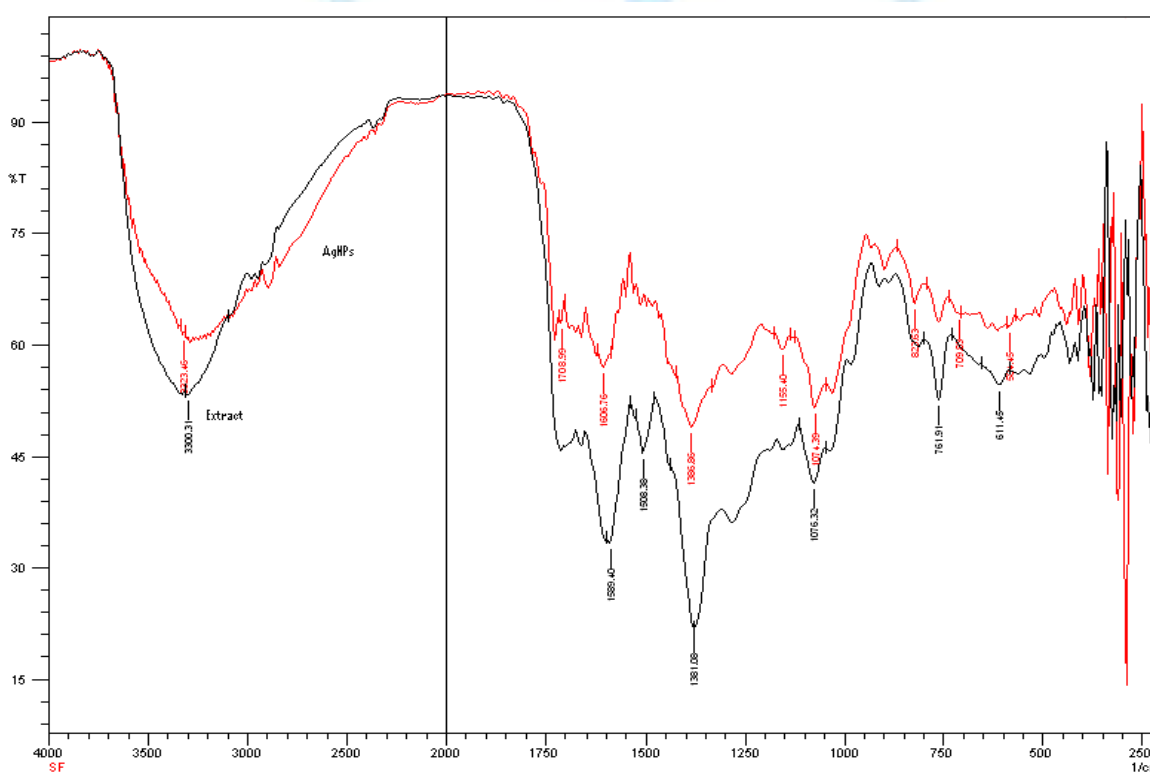


Figure 2. IR spectrum of crude extract and silver nanoparticles composite of *S. flaccidifolius*

3.4. X-ray diffraction analysis

The XRD pattern of the Ag nanoparticles prepared using *S. flaccidifolius* extract showed a number of strong Bragg reflections at 38.2 , 44.3 , 64.4 and 77.3 (Figure 3) which corresponded to the $(1\ 1\ 1)$, $(2\ 0\ 0)$, $(2\ 2\ 0)$ and $(3\ 1\ 1)$ facets of the face centered cubic crystal structure, respectively [40]. No diffraction peaks corresponding to the precursor (AgNO_3) and/or bi-products (such as silver oxide) were observed, which confirmed that only metallic Ag was formed by *S. flaccidifolius* extract reaction.

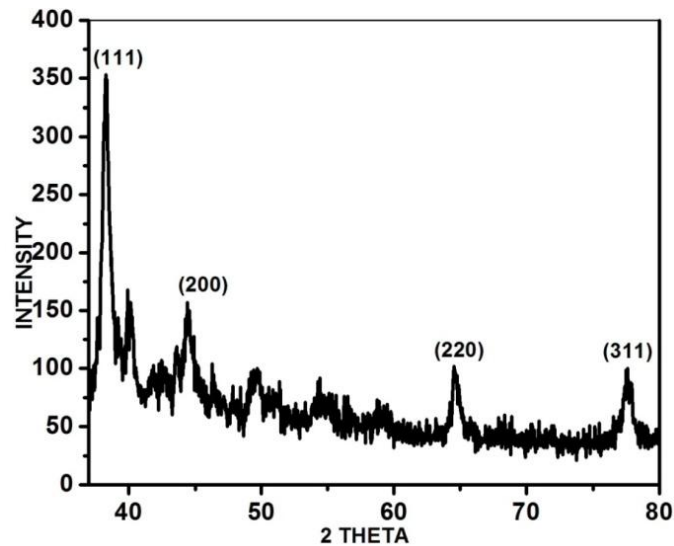


Figure 3. Powder XRD pattern of silver nanoparticles composite of *S. flaccidifolius*

Scanning Electron Microscopy (SEM) provided particle size analysis from the individual nanoparticles which was adopted spherical morphology (Figure 4) [41].

3.5. Scanning Electron Microscopy

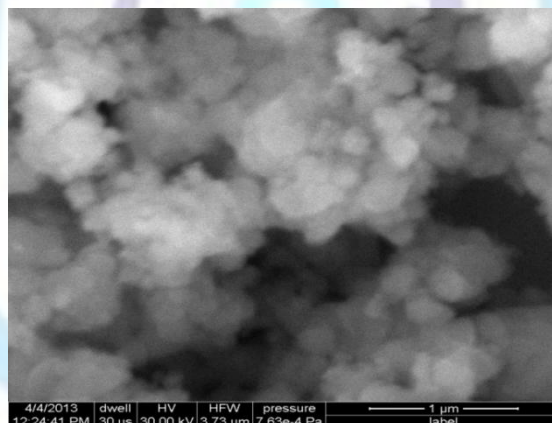


Figure 4. SEM images of AgNPs composite of *S. flaccidifolius*

3.6. EDX identification and estimation

The scanning SEM-EDX mapping images of the nanoparticles synthesized at different temperatures showed the presence of estimated elements (silver, carbon, oxygen, Nitrogen and Silver) (Figure 5). It also confirmed the formation of silver nanoparticles with the capping that reported earlier of indigo precursors and the formation of silver nanoparticles [42].

Label A: 2

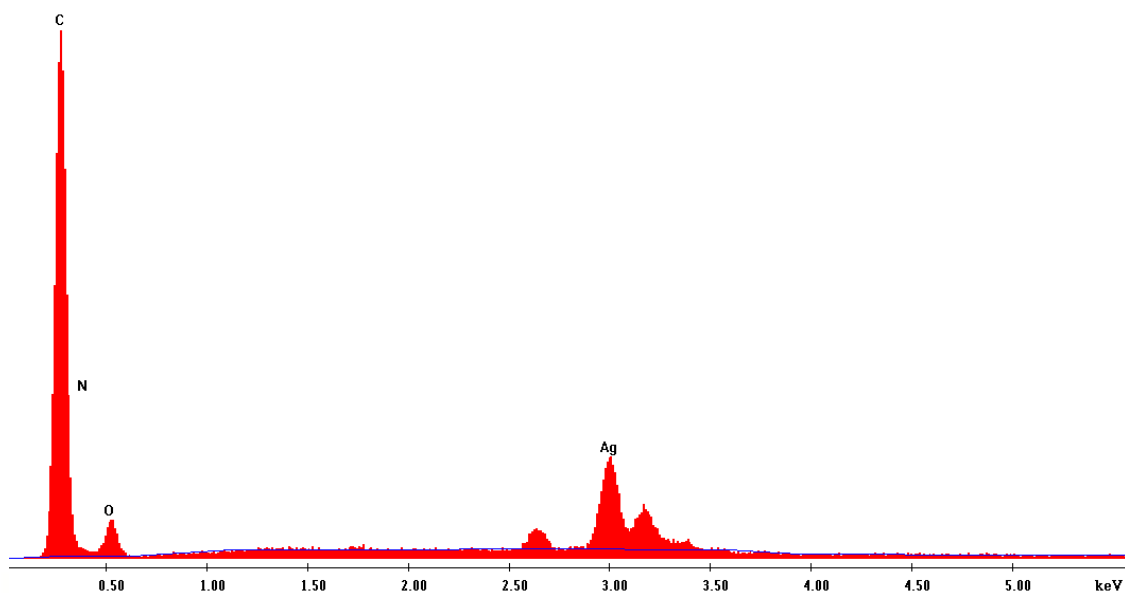


Figure 5. EDX spectrum of AgNPs composite of *S. flaccidifolius*

3.7. EPR analysis

The EPR signal showed the presence of lone pair indicating of the silver in neutral d^9 (Ag⁰) state which was absent in the d^8 (Ag⁺) state (Figure 6). This further proves the formation of silver nanoparticles.

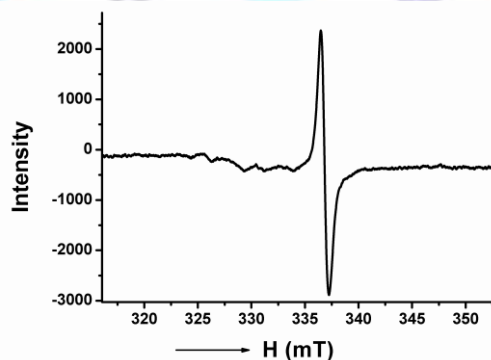


Figure 6. EPR spectrum of nano composite of *S. flaccidifolius*

3.8. Transmission electron microscopy

Spherical shaped particles were showed by TEM of the size ranging from 6nm to 54.11nm (Figure 7a). The average size was 12.15 ± 5.3 nm in TEM image (Figure 7c). The SAED (Selected Area Electron Diffraction) pattern showed the miller planes of silver metal and additional peaks of the organic capping (Figure 7b) that proved the crystalline nature of the compound. The inter planar distance from the adjacent lattice fringes in HR-TEM image of one particle was 2.36Å which corresponded to face centre cubic of Ag (Figure 7d).

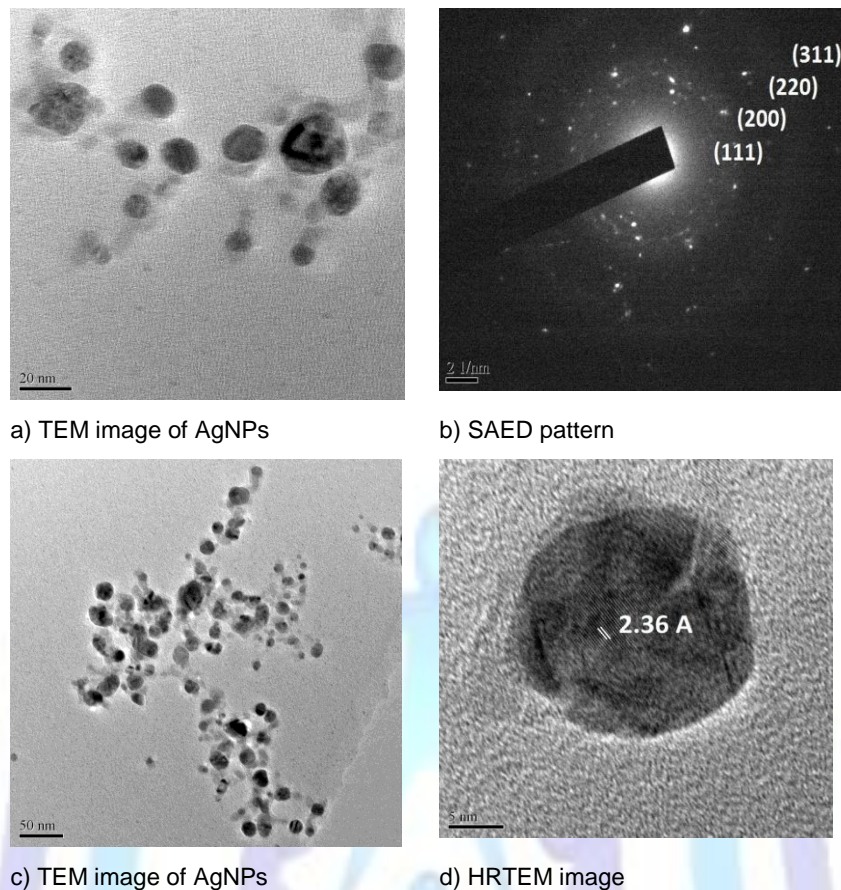


Figure 7. TEM images of AgNPs composite of *S. flaccidifolius*

3.9. Antimicrobial activity

Antimicrobial effects of synthesized silver nanoparticles using *S. flaccidifolius* were tested against human pathogens gram negative bacteria. The result showed inhibitory action when compared to silver nanoparticles at high level of zone of inhibition against *P. aeruginosa*. Moderate level of inhibitory activity was observed for *P. mirabilis*, *K. pneumonia*, *E. coli* and *S. paratyphi*. *P. aeruginosa* (MIC = 0.00122070312 mg/ml) was found to be the most susceptible bacterial pathogen (Table 1). Crude silver blend shows potent activity than the purified silver nanoparticles, implies the bioactivity of combined plant and silver nanoparticles conjugate [43]. Exact antimicrobial effect of silver nanoparticles was still unclear, suggesting three different possible mechanism of action, involving first silver ions attach to the bacterial cell membrane and caused plasmolysis (cytoplasm of bacteria separated from bacterial cell wall), inhibited the bacterial cell membrane synthesis [44]. Secondly, AgNPs could strongly interact with sulphur-phosphorus containing compounds present inside (DNA, proteins) and outside (membrane proteins) of bacterial cell, affecting respiratory chain reaction, cell division and finally lead to cell death [45]. Finally, AgNPs released silver ions that will penetrate into the cell wall, causing condensation of DNA damage and also by affecting the protein synthesis [46]. Overall results showed the involvement of the phenomena of synthesized particles leading to the damage to pathogens or killing the pathogens. Raut et al. [47] investigated the antibacterial activity of photosynthesized silver nanoparticles against *E. coli*, *P. aeruginosa* and *K. pneumoniae*. Similarly, Kim et al. [48] reported antimicrobial activity of silver nanoparticles against *E. coli* and *S. aureus*. Kotakadi et al. [49] showed antibacterial activity of silver nanoparticles against *E. coli*. Sathishkumar et al. [50] inhibited antimicrobial activity of phyto-synthesis of silver nanoscale particles against *E. coli*, *P. aeruginosa* and *K. Pneumonia*.

**Table 1** Inhibitory action of silver nanoparticles synthesized using the leaf extract of *S. flaccidifolius* against human pathogenic bacteria.

Microorganism	Conc. (5mg/ml)	Zone of inhibition (mm)		MIC (mg/ml)
		Silver nanoparticles	Ciprofloxacin (100µg/ml)	Silver nanoparticles
<i>Proteus mirabilis</i>	5	26±0.06	16±0.11	0.009765625
	2.5	24±0.31		
	1.25	20±0.4		
	0.625	18±0.21		
<i>Klebsiella pneumoniae</i>	5	26±0.08	17±0.09	0.009765625
	2.5	24±0.12		
	1.25	20±0.22		
	0.625	18±0.05		
<i>Escherichia coli</i>	5	20±0.14	19±0.21	0.01953125
	2.5	18±0.11		
	1.25	16±0.24		
	0.625	14±0.15		
<i>Salmonella paratyphi</i>	5	26±0.8	19±0.11	<0.009765625
	2.5	22±0.4		
	1.25	20±0.41		
	0.625	18±0.02		
<i>Pseudomonas aeruginosa</i>	5	34±0.14	20±0.08	0.00122070312
	2.5	30±0.22		
	1.25	28±0.41		
	0.625	24±0.24		

4. CONCLUSION

The silver nanoparticles were synthesized with green technique using the extract of *S. flaccidifolius* as the reductant and the stabiliser. The formation of AgNPs was confirmed by IR, UV, EPR, EDX and XRD technique and size was characterized by SEM and HRTEM. The antimicrobial activity of the silver nanoparticles shows much potent inhibitory activity against clinically isolated pathogens. Hence the plant mediated synthesized nanoparticles can be used as good therapeutic agent against human pathogens and also for the successful development of drug delivery in near future.

ACKNOWLEDGEMENT

The authors acknowledge SAIF NEHU, Physics department Manipur University for TEM, SEM, EDX and Powder XRD data. Wangkheirakpam Sujata thank UGC, New Delhi for BSR Fellowship and for financial support.

REFERENCES

- [1] J.L. Gardea-Torresdey, E. Gombez, J.G. Parsons, J. Peralta-Videa, P. Santiago, K.J. Torresdey, S E. Troiani, J.S. Yacaman, Nano. Lett. 2 (2002) 19-26.
- [2] J.L. Gardea-Torresdey, E. Gomez, J.S. Yacaman, J.G. Parsons, J. Peralta-Videa, H E. Troiani, Langmuir. 19(2003)1357-1361.
- [3] S.R. Bonde, D.P., Rathod, A.P. Ingle, R.B., Ade, A.K., Gade, M..K. Rai. Nano science Methods 1(2012) 25-36.
- [4] N. Mude, A. Ingle, A. Gade, M. Rai, J Plant Biochem. Biotechnol. 18(2009)83-86.
- [5] J.Y Song, and B.S. Kim, Bioprocess Biosyst. Eng. 32 (2009) 79-84.
- [6] Y.Park, Y.N. Hong, A. Weyers, Y.S. Kim, R.J. Linhardt, IET Nanotechnology (5) 3 (2011)69-78.



- [7] P.C. Nagajyothi, T.V.M. Sreekanth, D.L. Kap, Synthesis and Reactivity in Inorganic, Metal-Organic and Nano-Metal chemistry 42(2012)1339-1344.
- [8] K.Vineet, K.Y. Sudhesh. Int J Green Nanotechnology 3 (2011)281-291.
- [9] X. Xiaoxia, T. Qing, Z. Yina, Z.Fengyi, G.Miao, W., Ying, W. Hui, Z. Qian, Y. Shuqin, J. Agric. Food Chem. 59(2011)9280-9289.
- [10] V. Kumar, S.K. Yadav, I E T. Nanobiological 6(2011)1-8.
- [11] A. Tripathy, A.M. Raichur, N. Chandrasekharan, T.C. Prathna, A. Mukherjee, J nanoparticle Res 12(2010)237-246.
- [12] V. Kumar, SK. Yadav, Int J Green Nanotech. 3(2011)281-291.
- [13] S. Li, Y. Shen, A. Xie, nX. Yu, L. Qiu, L. Zhang, Q. Zhang, Green Chemistry 9(2007) 852-858.
- [14] S.S. Shankar, A. Ahmad, M. Sastry, Biotechnol Prog. 19(2003)1627-1631.
- [15] A. Z. Abduz, A. Bagavan, C. Kamaraj, G. Elango, R. A., J Biopest. 5(2012)95 - 102.
- [16] B.J. Umesh, A.B. Vishwas, Industrial crops and products. 46(2013)132-137.
- [17] V. Gopinath, D. MubarakAli, S. Priyadarshini, N. M. Priyadharsshinia, N. Thajuddin, P. Velusamy, Colloids and Surfaces B: Biointerfaces 96 (2012) 69– 74.
- [18] A. D. Mudasir, I. Avinash, R. Mahendra, Nanomedicine: Nanotechnology, Biology, and Medicine 9 (2013) 105–110.
- [19] T.Y. Suman, S.R. Radhika Rajasree, A. Kanchana, S. Beena Elizabeth. Colloids and Surfaces B: Biointerfaces 106 (2013) 74– 78.
- [20] V. Mahendran, A. Gurusam .Appl Nanosci. 3(2013)217-223.
- [21] A.M.Awwad, M.S. Nida and O.A. Amany. International J of Industrial Chemistry (2013) 4:29 .
- [22] I. M. El-Sherbiny, S. Ehab and M R. Fikry, J of Nanostructure in Chemistry (2013)3:8.
- [23] V. Palanivel, L. Sang-Myung, I. Mahudunan, L. Kui-Jae, O. Byung-Taek . Appl Microbiol Biotechnol. 97(2013)361-368.
- [24] B. Ashok , J. Bhagyashree , R. K. Ameeta, Z. Smita. Colloids and Surfaces A: Physicochem. Eng. Aspects 368 (2010) 58–63.
- [25] L. Anh-Tuan, P.T. Huy, P D Tam, T Q Huy, D C Phung, A.A. Kudrinskiy , Yu A. Krutyakov. Current Applied Physics 10 (2010) 910–916.
- [26] P. Prakash, P. Gnanaprakasam, R. Emmanuel, S. Arokiyaraj, M. Saravanan Colloids and Surfaces B: Biointerfaces 108 (2013) 255–259.
- [27] J. K. Aruna, R.B. Sashidhar , J. Arunachalam^a Carbohydrate Polymers 82 (2010) 670–679.
- [28] G. M. Sulaiman, W. H. Mohammed, T. R. Marzoog, A. A. Amir Al-Amiery, A.A.H. Kadhum, A. B. Mohamad, Asian Pac J Trop Biomed; 3(2013)58-63.
- [29] M.R. Bindhu, M. Umadevi, Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy 101 (2013) 184–190.
- [30] C. Dipankar, S. Murugan, Colloids and Surfaces B: Biointerfaces 98 (2012) 112–119.
- [31] Y. Subba Rao , Venkata S. Kotakadi, T.N.V.K.V. Prasad , A.V. Reddy , D.V.R. Sai Gopal, Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy 103 (2013) 156–159.
- [32] K. Raja, A. Saravanakumar, R. Vijayakumar. Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy 97 (2012) 490–494.
- [33] S. P. Rupali, R. K. Mangesh, S. K. Sanjay. Spectrochimica Acta Part A 91 (2012) 234–238
- [34] A.K. Jha, K. Prasad, Int J Green Nanotechnology: Physics and Chemistry, 1(2010) 110-117.
- [35] D.S. Reeves, I. Phillips, J.D. Williams, Laboratory methods in antimicrobial chemotherapy. Longman group Ltd, Edinburgh (1979)pp. 20.
- [36] K.R. Cheruiyot, D. Olila, D Kateregga, Afri Health Sci, 9(2009)S42 – S46
- [37] E. Rodriguez-Leon, R. Iniguez-Palomares, R. E. Navarro, R. Herrera-Urbina, J Tanori, C Iniguez-Palomares. A. Maldonado. Nanoscale Research Letters (2013) 8:318
- [38] L.S. Warjeet, W. D. Sujata. Int J Plant Physiol and Biochem.,;3(2011)108-116.
- [39] M. Roni, K. Murugan, C. Panneerselvam, J. Subramaniam, H. Jiang-Shiou Parasitol Res 112 (2013)981–990 .
- [40] M. F. Zayed, W. H. Eisa , A.A. Shabaka. Spectrochimica Acta Part A: Molecular and Biomolecular



Spectroscopy 98 (2012) 423–428.

- [41] V.Gopinath , D. MubarakAli, S. Priyadarshini , N. M. Priyadharsshini , N. Thajuddin , P. Velusamy. *Colloids and Surfaces B: Biointerfaces* 96 (2012) 69–74.
- [42] Y. R. Subba, S. K.Venkata, T.N.V.KV.Prasad, A.V. Reddy, D.V.R. Sai Gopal *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy* 103 (2013) 156–159.
- [43] D. MubarakAli, N. Thajuddin, K. Jeganathan, M. Gunasekaran, *Colloids Surf. B: Biointerfaces* 85 (2011) 360–365.
- [44] J.R. Morones, J.L. Elechiguerra, A. Camacho, K. Holt, B. Juan Kouri, J.T. Ramrez, M.J. Yacaman, *Nanotechnology* 16 (2005) 2346–2353.
- [45] H.Y. Song, K.K. Ko, I.H. Oh, B.T. Lee, *Eur. Cells Mater.* 11 (2006) 58.
- [46] Q.L. Feng, J. Wu, G.Q. Chen, F.Z. Cui, T.N. Kim, J.O. Kim, *J. Biomed. Mater. Res.* 52 (2000) 662–668.
- [47] W. Rout Rajesh, R. Lakkakula Jaya, S. Kolekar Niranjana, D. Mendhulkar Vijay, B. Kashid Sahebrao, *Curr. Nanosci.* 5 (2009) 112–117.
- [48] J.S. Kim, E. Kuk, K.N. Yu, J.H. Kim, S.J. Park, H.J. Lee, S.H. Kim, Y.K. Park, Y.H. Park, C.Y. Hwang, Y.K. Kim, Y.S. Lee, D.H. Jeong, M.H. Cho, *Nanomed.: Nanotechnol. Biol.* 3 (2007) 95–101.
- [49] V. S. Kotakadi, Y. Subba Rao, Susmila Aparna Gaddam, T.N.V.K.V. Prasad, A. Varada Reddy, D.V.R. Sai Gopal, *Colloids and Surfaces B: Biointerfaces* 105 (2013) 194– 198.
- [50] G. Sathishkumar, C. Gobinath, K. Karpagam, V. Hemamalini, K. Premkumar, S. Sivaramakrishnan, *Colloids and Surfaces B: Biointerfaces* 95 (2012) 235– 240.

