



THE UNIVERSITY *of* EDINBURGH

Edinburgh Research Explorer

From scaffold to structure: the synthetic production of cell derived extracellular matrix for liver tissue engineering

Citation for published version:

Grant, R, Hay, D & Callanan, A 2018, 'From scaffold to structure: the synthetic production of cell derived extracellular matrix for liver tissue engineering', *Biomedical Physics & Engineering Express*.
<https://doi.org/10.1088/2057-1976/aacbe1>

Digital Object Identifier (DOI):

[10.1088/2057-1976/aacbe1](https://doi.org/10.1088/2057-1976/aacbe1)

Link:

[Link to publication record in Edinburgh Research Explorer](#)

Document Version:

Peer reviewed version

Published In:

Biomedical Physics & Engineering Express

Publisher Rights Statement:

As the Version of Record of this article is going to be / has been published on a gold open access basis under a CC BY 3.0 licence, this Accepted Manuscript is available for reuse under a CC BY 3.0 licence immediately.

General rights

Copyright for the publications made accessible via the Edinburgh Research Explorer is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy

The University of Edinburgh has made every reasonable effort to ensure that Edinburgh Research Explorer content complies with UK legislation. If you believe that the public display of this file breaches copyright please contact openaccess@ed.ac.uk providing details, and we will remove access to the work immediately and investigate your claim.



ACCEPTED MANUSCRIPT • OPEN ACCESS

From scaffold to structure: the synthetic production of cell derived extracellular matrix for liver tissue engineering

To cite this article before publication: Rhiannon Grant *et al* 2018 *Biomed. Phys. Eng. Express* in press <https://doi.org/10.1088/2057-1976/aacbe1>

Manuscript version: Accepted Manuscript

Accepted Manuscript is “the version of the article accepted for publication including all changes made as a result of the peer review process, and which may also include the addition to the article by IOP Publishing of a header, an article ID, a cover sheet and/or an ‘Accepted Manuscript’ watermark, but excluding any other editing, typesetting or other changes made by IOP Publishing and/or its licensors”

This Accepted Manuscript is © 2018 IOP Publishing Ltd.

As the Version of Record of this article is going to be / has been published on a gold open access basis under a CC BY 3.0 licence, this Accepted Manuscript is available for reuse under a CC BY 3.0 licence immediately.

Everyone is permitted to use all or part of the original content in this article, provided that they adhere to all the terms of the licence <https://creativecommons.org/licences/by/3.0>

Although reasonable endeavours have been taken to obtain all necessary permissions from third parties to include their copyrighted content within this article, their full citation and copyright line may not be present in this Accepted Manuscript version. Before using any content from this article, please refer to the Version of Record on IOPscience once published for full citation and copyright details, as permissions may be required. All third party content is fully copyright protected and is not published on a gold open access basis under a CC BY licence, unless that is specifically stated in the figure caption in the Version of Record.

View the [article online](#) for updates and enhancements.

1
2
3 **From scaffold to structure: the synthetic production of cell derived extracellular**
4 **matrix for liver tissue engineering**
5
6

7
8 Rhiannon Grant MSc, David Hay PhD, Anthony Callanan PhD
9

10 Institute for Bioengineering, School of Engineering, University of Edinburgh, King's Buildings,
11
12 Mayfield Road, Edinburgh, EH9 3JL
13
14

15
16 Corresponding author; anthony.callanan@ed.ac.uk
17
18
19

20 **Rhiannon Grant MSc**
21

22 **Email** rhiannon.grant@ed.ac.uk
23

24 **Telephone** +44 (0)1316517077
25

26 **Fax** +44 (0)131 650 6554
27
28

29
30 **David C Hay PhD**
31

32 **Email** davehay@talktalk.net
33

34 **Telephone** +44 (0)1316519500
35

36 **Fax** +44 (0)131 651 9501
37
38

39
40 **Anthony Callanan PhD**
41


42 **Email** anthony.callanan@ed.ac.uk
43

44 **Telephone** +44 (0)1316507355
45

46 **Fax** +44 (0)131 650 6554
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Abstract

Liver transplant is the only curative treatment option for patients with end-stage liver failure, however there are few donor livers available for transplant. Tissue engineering of a human liver would potentially solve the problem of escalating donor shortages. A major challenge presents itself in the form of the hepatic extracellular matrix (ECM); a finely controlled *in vivo* niche which supports hepatocytes and plays a critical role in the development of liver disease. Polymers and decellularized tissues each provide some of the necessary biological cues for the hepatocytes, however, neither alone has proved sufficient. Equally, the ability to fine tune the microenvironment using bioactive molecules presents researchers with the opportunity to create personalised niches for hepatocytes, representing both normal and diseased phenotypes. This study combines cell derived ECM with a fibronectin vector and electrospun scaffolding techniques to produce a platform for creating customisable ECM microenvironments for hepatocytes (Abstract image). The resulting poly-L-lactic acid-extracellular matrix (PLA-ECM) scaffolds were validated using HepG2 hepatocytes.

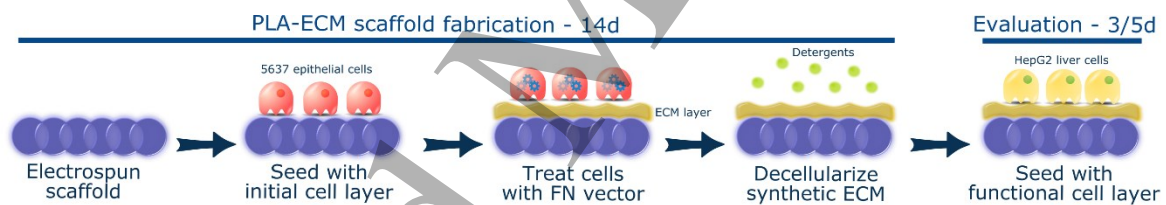

Abstract image. Methodology used to biofunctionalize electrospun scaffolds with synthetically derived ECM.

As expected, statistically significant mechanical differences were observed between the synthetically derived ECM (SD-ECM) scaffolds and normal ECM (N-ECM) scaffolds, confirming that the ECM has been altered by the fibronectin producing vector. The PLA-ECM scaffolds maintained hepatocyte growth and function and influence the gene expression of key hepatic genes. Furthermore, immunohistochemistry showed SD and N-ECMs differed in ratios of Collagen I, Laminin and Fibronectin.

Our results demonstrate that hybrid PLA-ECM scaffolds and the synthetic production of ECM provide a viable, translatable platform for customising microenvironments for hepatocytes.

1
2
3 This technology offers a potential solution to current obstacles in regenerative medicine,
4
5 disease modelling and whole organ tissue engineering.
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Accepted Manuscript

Introduction

In the US alone, as of August 20th 2017, the Organ Procurement and Transplantation Network (OPTN) estimates 14,158 patients are waiting for a donor liver. With a lack of viable new pharmaceuticals, liver transplant remains the sole treatment option for end-stage disease patients¹. Liver disease is an increasing burden on the health of the Western world, with both incidence and mortality increasing rapidly since 1970². Demand for donor livers far outstrips supply, and the incidence of liver disease shows no signs of slowing down³.

Tissue engineers seek to solve this problem by engineering liver 'organoids'; laboratory created organs which can function as a liver *in vivo*⁴⁻⁷. The 3D environment exerts extensive influence on the behaviour and function of hepatocytes^{6,8}. With this in mind, tissue engineers employ scaffold manufacturing technologies to create structures which encompass key characteristics of the native 3D ECM⁹⁻¹⁴. Several different methods of creating a scaffold are in use, and they can be made from a myriad of substances; both natural and synthetic¹⁵, and enhanced with bio-decoration methods⁸. There has been particular focus on decellularization, which provides an ECM bioscaffold with the 3D site-specific vasculature required for hepatocyte function upon their repopulation of the organ¹⁶. Decellularized organs have been repopulated with hepatocytes and endothelial cells which subsequently survive and exhibit some level of function, clearly demonstrating the importance of the ECM in supporting hepatocyte survival and phenotype¹⁷⁻²¹. However, decellularization requires a human or animal source of whole, undamaged organs and while research is showing great promise, the field is fragmented and to date no scaffold has been created which allows hepatocytes to function as well as *in vivo*^{22,23}.

Synthetic biology and genetic engineering are vital tools for tissue engineers and have been used to alter gene expression, enhance intracellular imaging and study fundamental processes in hepatocytes²⁴⁻²⁶. Recently, synthetic biology tools have been successfully employed to direct both stem cell lineage and fate in 3D constructs^{27,28}, in the manipulation of biofilms for cell culture²⁹ and in the production of therapeutic proteins in *in vivo* systems^{30,31}

demonstrating the ability of synthetic biology techniques to manipulate 3D environments and thus their potential benefit to the field of tissue engineering. Groundbreaking CRISPR³²⁻³⁴ and minicircle vector³⁵⁻³⁷ technologies have made the idea of therapeutic gene editing in humans a viable reality, however concerns exist regarding the safety and subsequently, the translatability of such tools with regards to patient treatment. Heavily publicised and tragic events such as the 1999 death of 18 year old Jesse Gelsinger³⁸ and the 2002 clinical trial in which four children developed leukaemia following gene therapy for their Severe Combined Immune Deficiency disease³⁹ have led to obvious worries regarding the safety of gene therapies. The inflammatory and immune modulating effects of damage-associated molecular patterns (DAMPs) such as foreign DNA fragments⁴⁰ are well documented, however clinical use of decellularized ECM in exogenic and allogenic form has demonstrated great promise, giving no immune response and showing regenerative potential. This paves the way for using synthetic biology to tissue engineer the ideal ECM environment. The ideal ECM would utilise synthetic biology and genetic technologies to their utmost, considerable, potential but remove any risk from the tools used; such as the genetically modified cells themselves.

Table 1; Advantages of a combinatorial approach to tissue engineering of liver environments.

<u>Polymer scaffolds</u>	<u>Decellularized tissues</u>	<u>Vector technology</u>	<u>Combinatorial approach</u>
✓ Reproducible	✓ Provides biochemical cues of ECM	✓ Customizable protein profile	✓ Mechanically & proteomically customizable
✓ Mechanically customizable	✓ Vasculature exists within tissue	✓ Rapid production of desired proteins	✓ Cell lines used - donors avoided
✗ Does not provide complex biochemical cues of ECM	✗ Limited donors & donor safety	✗ Vector safety concerns	✓ Vectors removed - safety concerns abated

With the potential of synthetic biology for manipulation of protein production in mind, we set out to address this problem; developing a novel bio-active hybrid scaffold which possesses the potential for customization of the ECM microenvironment. To date, no bioengineers have combined the promising fields of scaffold manufacture, decellularized tissue and synthetic biology. Here we report the first use of a sacrificial, transfected cell line to bio-functionalise an electrospun polymer scaffold for liver tissue engineering. We have successfully decellularized the bio-functionalised scaffold, and validated the platform using cells representative of the liver, HepG2s.

Materials and Methods

Electrospinning

A 10% wt/vol solution of poly-L-lactic acid (Goodman) and hexafluoroisopropanol (Manchester Organics) was dissolved overnight at room temperature with agitation. Solutions were placed into a 10ml syringe and pumped using syringe pump EP-H11 (Harvard Apparatus) into the EC-DIG electrospinning system (IME technologies) via a 27G bore needle under the following parameters;

Table 2; Electrospinning parameters

Volume per hour	Total volume	Mandrel:needle distance	Positive charge	Negative charge	Mandrel rotation	Needle movement
0.5ml	10ml	14 cm	16kV	-3kV	250rpm	100mm/s

The mandrel was coated in non-stick aluminium foil for collecting the electrospun fibres. The sheets of electrospun fibres were allowed to dry overnight in a fume hood when the electrospinning session was completed. The average fibre size was 1.48 μ m as calculated by ImageJ plugin 'DiameterJ'⁴¹.

Scaffold Preparation

10mm discs of scaffold were cut from the dry fibre sheet. The scaffolds were soaked in 70% isopropyl alcohol for 10 minutes, rinsed three times in phosphate buffered saline for 15

1
2
3 minutes each and allowed to dry completely at room temperature. Scaffolds were placed into
4 an antibiotic/antimycotic treatment solution of Dulbeccos Minimal Essential Media
5 supplemented with 100U/ml penicillin, 100µg/ml streptomycin, 0.25µg/ml Fungizone®
6
7 (amphotericin B) Anti-Anti solution (Gibco) for 1 hour.
8
9
10

11 12 **Initial Layer Cell Seeding and Culture**

13
14
15 Scaffolds were removed from the antibiotic/antimycotic treatment solution and rinsed three
16 times for 15 minutes each in complete media; Dulbeccos Minimal Essential Media
17 supplemented with 10% foetal bovine serum, 2mM L-glutamine, 100U/ml penicillin and
18 100µg/ml streptomycin (Gibco). They were then placed into a fresh 48 well tissue culture plate.
19
20
21
22

23
24 5637 human urinary bladder epithelials (ATCC) were cultured and expanded as per supplier
25 recommendations, using the media described above. Cells for scaffold seeding were
26 trypsinized using 0.25% Trypsin-EDTA (Gibco) from tissue culture flasks and counted using
27 the trypan blue exclusion method. 1×10^5 cells at passage 23 were suspended in 100µl of
28 complete media and seeded directly on to the scaffolds. The cells were allowed to incubate in
29 this small volume on the scaffolds for 2 hours, before an additional 400µl of complete media
30 was added.
31
32
33
34
35
36
37
38

39 Media was changed after 24 hours using standard methods and subsequently changed every
40 48 hours. Controls were scaffold only, i.e. not seeded with an initial cell layer and a 'normal'
41 initial layer i.e. untransfected cells. Initial layers of cells were cultured for 7 days at 37°C and
42 5% CO₂ in a humidified incubator.
43
44
45
46
47

48 **Fibronectin Vector**

49
50
51 Vectors were obtained from the DNASU plasmid repository. In brief, the human fibronectin
52 gene (FN1) was placed into a retroviral expression vector, PJ1520. The insert sequence was
53 verified by sequence analysis and restriction enzyme digest by DNASU. The vector was
54 obtained in DH5-alpha T1 phage resistance *Escheria coli* glycerol stock. We cultured the E.
55 coli under selective conditions; 100µg/ml ampicillin, 34µg/ml chloramphenicol and 7%wt/vol
56
57
58
59
60

1
2
3 sucrose in LB media. Plasmid extractions were performed using Cambridge Bioscience's
4 Zyppy™ plasmid extraction kit following manufacturer's methods.
5
6

7 8 **Transfections** 9

10 Transfections were performed using Invitrogen Lipofectamine 3000®. Following titration
11 experiments, a concentration of 1µg plasmid DNA and 0.75µL lipofectamine reagent per
12 scaffold was chosen. The initial layer of 5637 epithelials was cultured on the scaffolds under
13 standard conditions for 7 days. Transfection was performed on the 7th day. Scaffold-cell
14 constructs were then placed into selective media containing 150µg/ml puromycin. The cell-
15 scaffold constructs were cultured under selection for a further 7 days to allow production of
16 the vector derived fibronectin before being decellularized.
17
18
19
20
21
22
23
24

25 26 **Decellularization** 27

28 Decellularization was performed under sterile conditions at room temperature (19 - 22°C) and
29 with agitation. Scaffolds were placed into 50ml falcon tubes and placed on a rotator at 20RPM.
30 Scaffolds were washed with phosphate buffered saline (PBS) for 15 minutes and then rinsed
31 in 10mM tris buffered saline (TBS) for 15 minutes.
32
33
34
35
36

37 The scaffolds were submerged in a 0.1% vol/vol Triton X-100 (Sigma-Aldrich) 1.5M potassium
38 chloride (Acros Organics) 50mM TBS for 4 hours. They were rinsed for 15 minutes in 10mM
39 TBS before being submerged in fresh 10mM TBS overnight.
40
41
42
43
44

45 Scaffolds were given a final rinse in 10mM TBS for 15 minutes before being incubated in
46 complete media for 15 minutes and then transferred to new 48 well plates for seeding.
47
48
49

50 **Functional layer Cell Seeding and Culture** 51

52 HepG2 cells were trypsinized using standard methods from tissue culture flasks and counted
53 using the trypan blue exclusion method. 1×10^5 cells at passage 17 were suspended in 100µl
54 of complete media and seeded directly on to the scaffolds. The cells were allowed to incubate
55
56
57
58
59
60

1
2
3 in this small volume on the scaffolds for 2 hours, before an additional 400µl of complete media
4 was added.
5
6

7
8 Media was changed after 24 hours and changed every 48 hours after the initial 24 hour
9 adherence and recovery period. This functional layer (FL) of cells was cultured using standard
10 methods for either 3 or 5 days at 37°C and 5% CO₂ in a humidified incubator.
11
12
13

14 **Live/Dead[®] Viability/Cytotoxicity assay**

15
16 To determine cellular viability, cell/scaffold constructs were incubated with 10µm calcein and
17 2µm ethidium ho-modimer-1 (Ethd-1) for 30 minutes as part of the two colour live/dead assay
18 (Molecular Probes). Calcein is actively converted to calcein-AM in living cells, which then
19 appear green when excited during fluorescence microscopy. Ethd-1 only accumulates in dead
20 cells, which subsequently appear red. The method allows differentiation between dead and
21 viable cells. The scaffolds were rinsed three times in CaCl₂/MgCl₂ free PBS to remove excess
22 dye and placed onto a standard microscope slide with a 25mm glass coverslip (VWR). All
23 images were captured using a Zeiss Axio Imager fluorescent microscope (COIL, University of
24 Edinburgh) at 40x magnification and post processed using ImageJ.
25
26
27
28
29
30
31
32
33
34
35

36 **CellTiter-Blue[®] Cell viability assay**

37
38 The assay was performed according to manufacturer's instruction (Promega). For each
39 condition group, n = 5. Importantly, cell/scaffolds constructs were moved into fresh 48 well
40 plates to prevent reading activity from tissue culture plastic bound cells. Measurements were
41 read in a Modulus™ II microplate reader at an excitation wavelength of 525 nm and emission
42 wavelength of 580-640 nm and reported as fluorescence.
43
44
45
46
47
48
49
50

51 **Albumin quantification**

52
53 A bromocresol green (BCG) albumin assay (Sigma) was used to quantify serum albumin
54 produced by the HepG2 functional cell layer over 24 hours at 3 and 5 day timepoints. The
55
56
57
58
59
60

1
2
3 assay was performed according to manufacturer's instructions and results read at an
4 absorbance of 620 nm in a Modulus™ II microplate reader.
5
6

7 **Picogreen® DNA quantification**

8
9
10 The Quant-IT™ Picogreen® dsDNA assay kit (Life Technologies™) was employed to establish
11 the efficiency of the decellularization method in removing cellular material and to estimate cell
12 number on the cell/scaffold constructs. The assay was performed according to manufacturer
13 instructions. In brief, constructs (n = 5) were digested in a solution of CaCl₂ and MgCl₂ free
14 PBS (Sigma), containing 2.5 U/ml papain extract (Sigma) 5 mM cysteine-HCl (Sigma)
15 and 5 mM EDTA (Sigma) and incubated for 48 hours at 60°C. Picogreen solution was added
16 to the digests and fluorescent intensity measurements read in a Modulus™ II microplate
17 reader at an excitation wavelength of 480 nm and emission wavelength of 510-570 nm. A
18 standard λ dsDNA curve of graded known concentrations was used to calibrate fluorescence
19 intensity vs dsDNA concentration.
20
21
22
23
24
25
26
27
28
29
30
31

32 **Sectioning and staining**

33
34
35 The samples were rinsed three times in PBS (Gibco) for 15 minutes each, then fixed in 4%
36 v/v formalin buffered in saline for 15 minutes at room temperature. After rinsing with fresh
37 PBS, constructs were embedded in low melting temperature polyester wax (Electron
38 Microscopy Supplies) using methods adapted from Steele et al. (2014). In brief, samples are
39 dehydrated through 70-100% ethanol, then incubated in 50:50 ethanol:wax overnight at 45°C
40 overnight with agitation. The samples were moved into 100% wax for 3 hours at 45°C and
41 then fresh 100% wax for 1 hour at 45°C. Samples were embedded and allowed 72 hours to
42 fully cure before sectioning. Immunohistochemical staining was undertaken using antibodies
43 for Collagen I (Strattech), Laminin (Strattech) and Fibronectin (Sigma). All images were
44 captured using a Zeiss Axio Imager system (Centre Optical Instrumentation Laboratory,
45 University of Edinburgh) at 40x magnification and post processed using ImageJ.
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Scanning Electron Microscopy

SEM was used to characterise the scaffold architecture. Samples were rinsed three times in PBS for 15 minutes each, then fixed in 2.5% v/v glutaraldehyde (Fisher Scientific) in 0.1M phosphate buffer (PB) (pH 7.4) at 4°C overnight. They were then rinsed three times in 0.1M PB before being post-fixed in 1% v/v osmium tetroxide (Electron Microscopy Supplies) buffered with 0.1M PB. Samples were again rinsed three times in 0.1M PB and dehydrated through an ethanol gradient (30-100%). They were dried by placing them in hexamethyldisilazane (HDMS, Sigma) which was allowed to evaporate off at room temperature overnight. We mounted the samples onto SEM chucks using double sided carbon tape and coated them with a thin layer of gold and palladium alloy (Polaron Sputtercoater).

All images were captured at 5 kV using a Hitach S-4700 SEM (BioSEM, University of Edinburgh).

Mechanical Testing

Nanoindentation experiments were undertaken to establish the dynamic properties of scaffolds and decellularized ECM/scaffold constructs using the Keysight/Agilent 5200 nano indenter testing system.

Scaffolds and constructs were subject to indentation by a DCM II actuator flat-ended cylindrical punch ($D = 100\mu\text{m}$) using a max load of 1g-f. All nanoindentation experiments were carried out on fresh, hydrated (suspended in PBS), unfixed samples in a stainless steel well chuck. A total of 36 indentations were carried out on each sample, 50nm apart. Indent sites were selected using the high precision X-Y stage within the testing system (Agilent). Poissons ratio was assumed to be 0.5 for each sample^{42,43}. Allowable drift rate was 0.1nm/s. A NanoSuite (Keysight Technologies) test method "G-Series DCM CSM Flat Punch Complex Modulus" was used for all testing^{44,45}.

Gene Expression analysis

RNA was extracted from constructs using standard Trizol (Fisher Scientific) methods and purified using Qiagen's RNeasy spin column system. cDNA was synthesised using the Promega's ImProm-II™ Reverse Transcription System.

Quantitative real-time polymerase chain reaction (qRT-PCR) was performed using the LightCycler® 480 Instrument II (Roche Life Science) and Sensifast™ SYBR® High-ROX (Bioline) system. Results were normalized to HepG2s of the same passage number grown on tissue culture plastic and compared to the housekeeping gene Glyceraldehyde-3-Phosphate Dehydrogenase (GAPDH). Analysis was performed using the $2^{-[\Delta\Delta Ct]}$ method^{46,47}, $n = 5$. Albumin (Alb), Cytochrome P450 Family 1 Subfamily A Polypeptide 1 (Cyp1A1), Cytochrome P450 Family 1 Subfamily A Polypeptide 2 (Cyp1A2), Cytochrome P450 Family 3 Subfamily A Polypeptide 4 (Cyp3A4), Collagen Type I alpha 1 (Col1A1), Collagen Type 4 alpha 1 (Col4A1) and Fibronectin Type 1 (FN1) were investigated, forward and reverse primers (Sigma) are detailed in Supplementary Table 1.

Statistical Analysis

One-way ANOVAs with Fishers, Games-Howell and Tukey⁴⁸⁻⁵⁰ post-hoc testing were performed using Minitab 17 Statistical Software and graphs generated using Origin software (OriginLab, Northampton, MA). Error bars indicate standard deviation. A minimum of $n = 3$ and max of $n = 6$ was used for all analysis.

Results

Cell attachment and survival on scaffolds

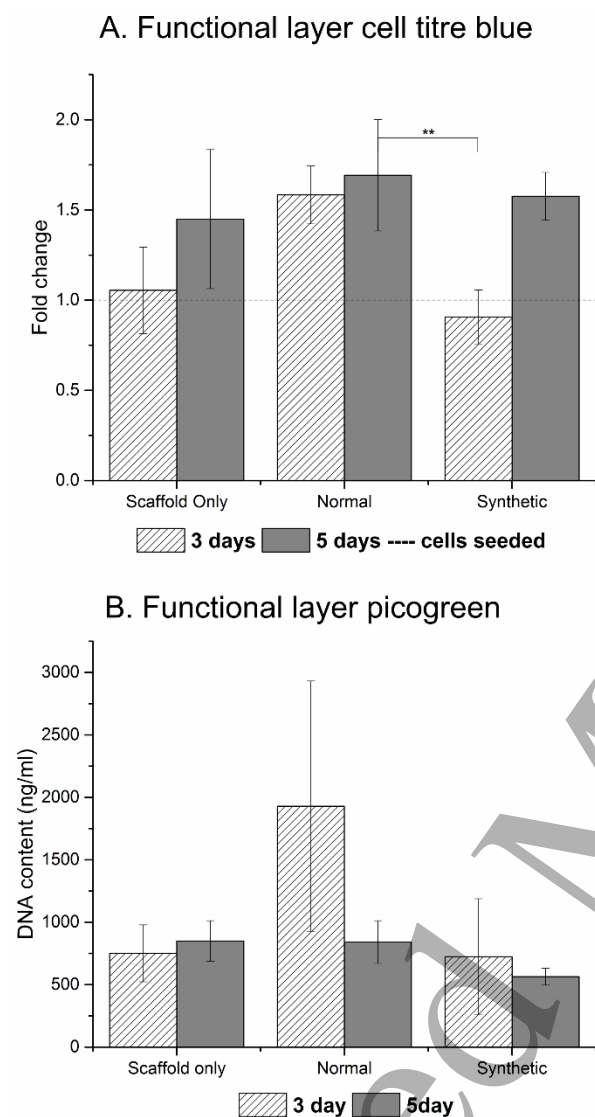


Figure 1. Cell titre blue assay indicating metabolic activity (A) and DNA quantitation of the functional layer (B). One way ANOVA with Games Howell post hoc testing, ** = p value <0.01.

When compared to normal ECM derived from untransfected cells (N-ECM) and the scaffold alone (SO), a lower number of HepG2s adhered to the synthetically derived vector driven (SD-ECM) scaffold-ECM constructs (Fig. 1). According to the CellTiter-Blue[®] results (Fig. 1A), the SD ECM layer maintained the growth of the HepG2s between days 3 and 5. However, this result is not concurrent with the Picogreen[®] DNA quantitation (Fig. 1B). This is most likely due to different data extraction methods and validation methods in the Picogreen and CellTiter-Blue assays. Both assays possess depth dependencies with regards to their efficiency and effectiveness in extracting data from fibrous scaffold constructs. Additionally, the assays were validated using 2D monolayer cell cultures. This

would explain high standard deviations in the Picogreen[®] DNA quantitation dataset and slight different trends observed between the assays. These findings are corroborated by our recent published work of cells on electrospun scaffolds¹⁴. Live/Dead[®] Viability/Cytotoxicity images (Fig. 2) demonstrate the metabolic viability of the functional HepG2 cell layer (FL), and that at day 5 the cells appear to be confluent and living, with low levels of cell death in each condition.

Mechanical characterisation of scaffolds

Reassuringly, both storage (G') and loss (G'') modulus demonstrate significant differences between the three conditions (Fig. 3). Fibronectin is known to influence both the mechanical profile of the ECM^{51,52} and influence the maintenance and structure of other vital ECM proteins, such as collagen⁵³. Equally, cells are known to respond to the mechanical and topographical influence a scaffold exerts⁵⁴.

Testing was performed at frequencies experienced by the human liver in vivo⁵⁵. Storage modulus (G') ranged from 22.92 ± 9.14 to 12.29 ± 0.14 MPa and loss modulus (G'') from 2.45 ± 0.93 to 0.15 ± 0.02 MPa at the frequencies detailed in supplementary tables 2 and 3.

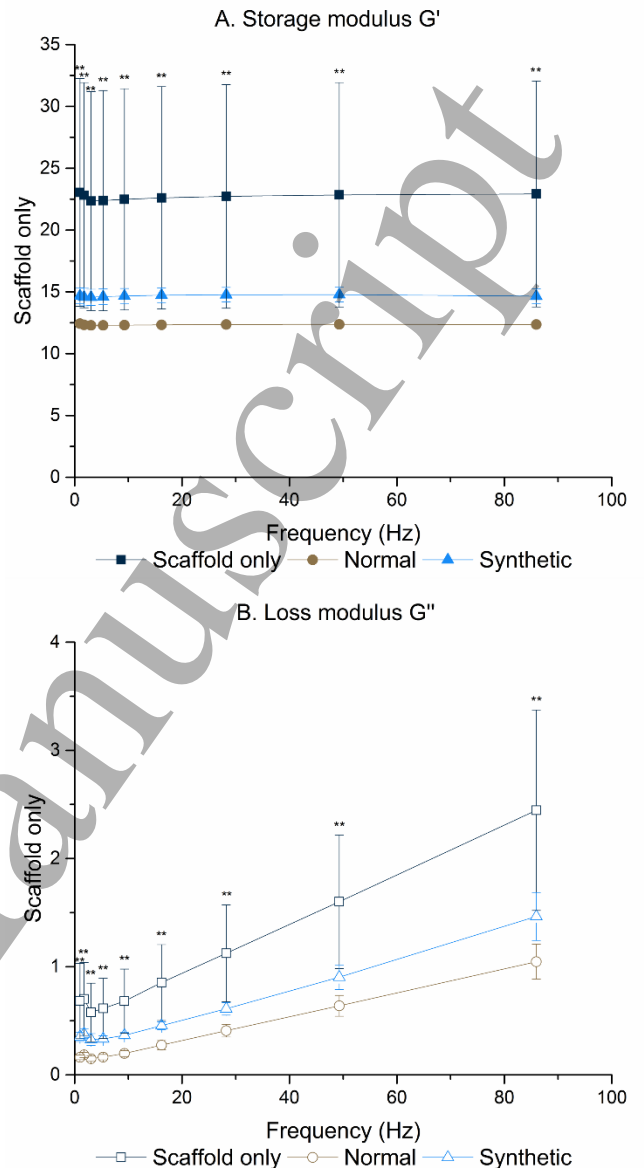
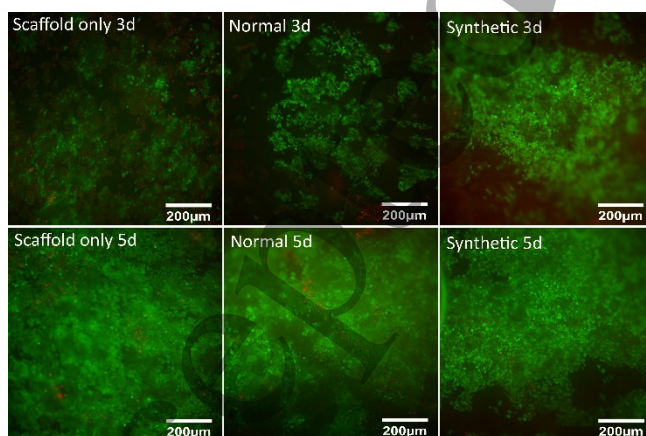


Figure 3. Significant mechanical differences were observed between all scaffold conditions. One way ANOVA with Games Howell post hoc testing, ** = p value < 0.01 .

Figure 2. Live Dead imaging demonstrating the living functional layer present at each time point, with minimal cell death.

Biochemical characterisation of the hybrid polymer-ECM scaffolds

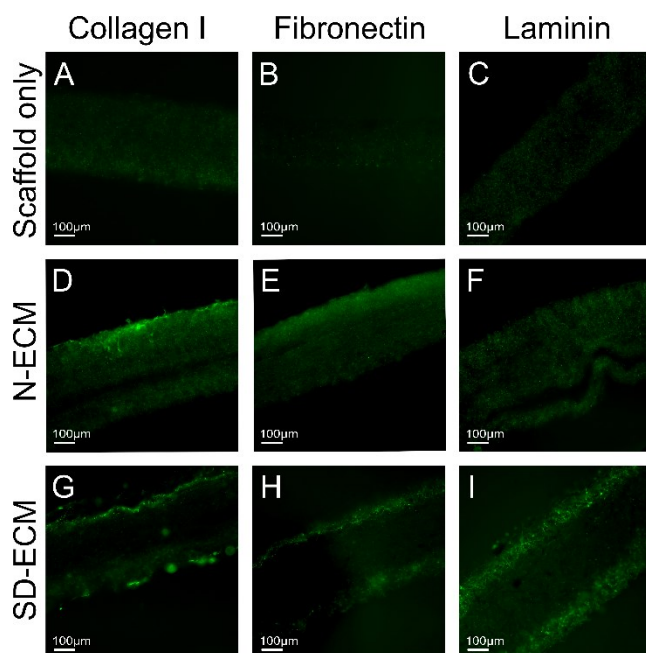


Figure 4. IHC staining showing the retention of major liver ECM proteins Collagen I (D, G), Fibronectin (E, H) and Laminin (F, I) following decellularization. Additionally, SO condition shows no positive staining as expected (A, B, C).

Differences in the biochemical profile of the different ECMs were demonstrated by immunohistochemistry performed on decellularized hybrid scaffold sections (Fig. 4). Hepatic cells are very responsive to extracellular matrix proteins; particularly Collagen I, Laminin and Fibronectin^{56–58}.

Fibronectin is ubiquitous in healthy liver^{59,60}, and antibody staining reveals altered levels of fibronectin in the synthetically derived ECM, as expected due to the introduction of the fibronectin vector (Fig. 4H). ECM proteins do not exist in

isolation, and fibronectin is known to influence the generation and laydown of other ECM proteins including collagen I and laminin^{53,61}, as evidenced in Fig. 4G and 4I when compared to N-ECM. The N-ECM is collagen I rich (Fig. 4D) with some fibronectin and laminin also present (Fig. 4E & 4F). Of note is that the SD-ECM appears to be concentrated on the outer layers of the electrospun scaffold. This could be due to the transfected cells being in fewer number than those which were not transfected (N-ECM), so they did not penetrate the scaffold to the same extent.

Gene expression of HepG2s in response to hybrid polymer-ECM scaffolds

Genes associated with both liver function and ECM production were assayed for gene expression (Fig. 5). Albumin expression, a marker of appropriate liver cell differentiation and function, appears upregulated between day 3 and day 5 in each condition, confirming appropriate development of the cells. At day 5, expression is significantly upregulated in comparison to HepG2s grown on tissue culture plastic (TCP) on the SD-ECM constructs; with

the highest levels of expression observed in SO and SD-ECM conditions. Additionally, albumin mRNA expression is downregulated in comparison to TCP at day 3 in all conditions (Fig. 5A). Cytochrome P450s (Cyp) are a family of enzymes involved in metabolism of xenobiotics and toxic compounds in the liver⁶²⁻⁶⁴. Cyp1A1 mRNA expression is significantly altered in comparison to TCP (Fig. 5B); upregulated at day 3 and downregulated at day 5. Cyp1A2 mRNA expression is consistently significantly downregulated in all but one condition; day 3 N-ECM (Fig. 5C). Cyp3A4 mRNA expression is upregulated in every condition, with a significant upregulation observed in response to SD-ECM (Fig. 5D).

In addition, we assayed for three ECM genes important for normal liver composition^{59,65}; Fibronectin (Fig. 5E), Collagen I (Fig. 5F) and Collagen IV (Fig. 5G). Considering the plastic nature of ECM, these genes are of interest with regards to ongoing modification of the tissue microenvironment despite hepatocytes not being the main producers of ECM proteins in the liver^{59,66}.

Collagen I is consistently upregulated, with significant upregulation observed at day 5 on SD-ECM. Equally, Fibronectin mRNA expression is significantly upregulated on day 5 SD-ECM constructs, though downregulated at day 3 on SO and N-ECM constructs. Collagen IV mRNA expression is consistently upregulated in each condition, with significant changes observed in all but day 3 N-ECM and SD-ECM. While such


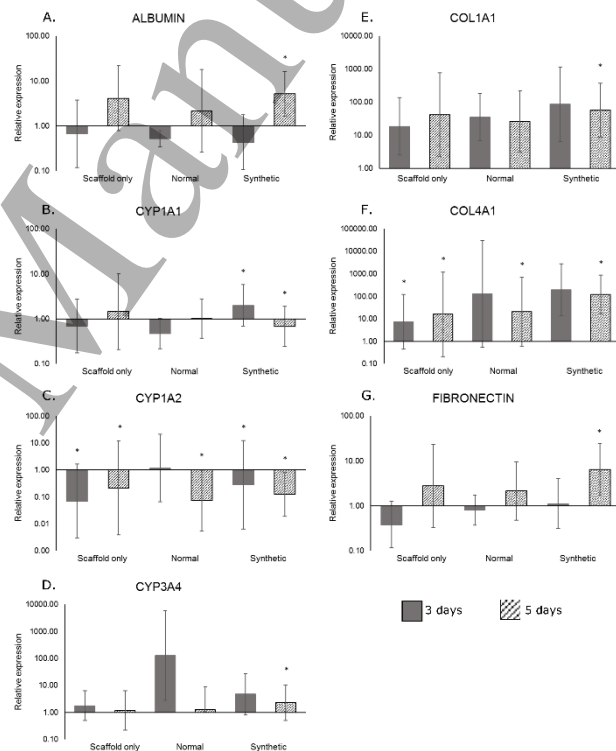


Figure 5. Q-PCR results showing significant changes in expression of major liver genes when compared to TCP, Albumin (A), CYP1A1 (B), CYP1A2 (C), CYP3A4 (D) and ECM genes Col 1A1 (E), Col 4A1 (F) and Fibronectin (G) between the hybrid scaffolds and tissue culture plastic. (A, C, D, E, F, G) = One way ANOVA with Games Howell post hoc testing, * = p value < 0.05. (B) = One way ANOVA with Tukey post hoc testing, * = p value < 0.05.

alterations in gene expression are promising, we refrain from further assumption regarding cell response without further proteomic and functional analyses.

Albumin production

Albumin levels are indicative of hepatocyte health and response to the microenvironment⁵⁷. Each condition results in differing levels of albumin production, with significant differences in protein levels observed between SO and SD-ECM at both 3 days and 5 days (Fig. 6), indicating that the N-ECM encouraged albumin production more than SD-ECM.

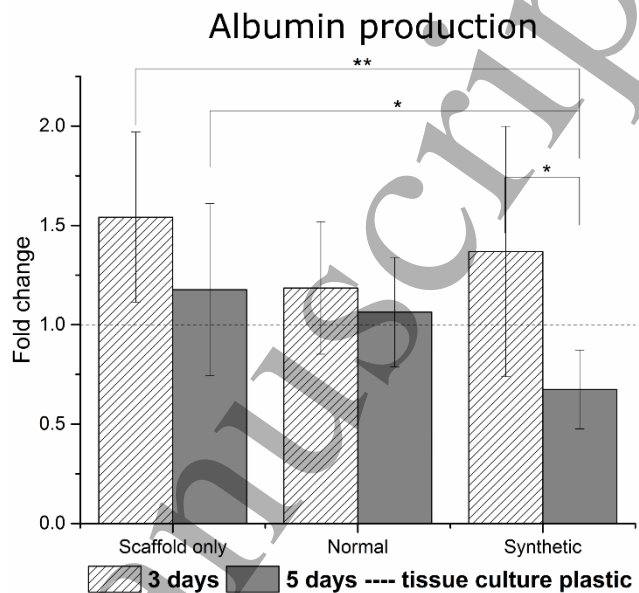


Confirmation of decellularization

Decellularization was confirmed using Picogreen® DNA quantitation (Fig. 7G)

Figure 6. Albumin production between conditions, showing significant changes between SO and SD-ECM conditions at both time points. One way ANOVA with Games Howell post hoc testing, * = p value <0.05. ** = p value <0.01.

and histological staining (Fig. 7A-F). A tenfold reduction in DNA combined with visual confirmation of an absence of DAPI nuclear staining and Phalloidin-514 actin staining on

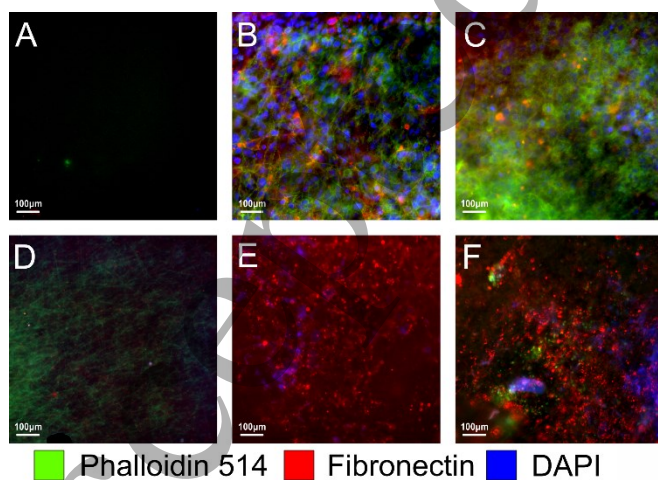

G. Picogreen post-decellularization

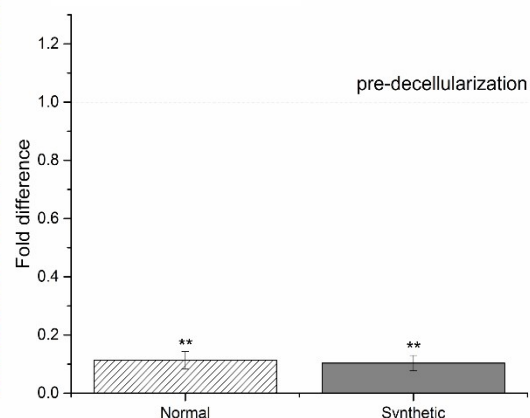


Figure 7. Effectively decellularized constructs, with minimum remnant DNA detected by IHC (E,F) or picogreen (G). Scaffolds pre-decellularization shown in (A), (B) and (C). One way ANOVA with Games Howell post hoc testing, ** = p value <0.05. Scaffold only (A, D), N-ECM (B,E) and SD-ECM (C, F)

1
2
3 decellularized constructs, plus the presence of fibronectin antibody staining on both the N-
4 ECM and SD-ECM decellularized constructs (Fig. 7E&F) provides evidence of efficient
5 decellularization methods, and that synthetically derived fibronectin is present on the hybrid
6 scaffolds.
7
8
9

10 11 12 **Discussion**

13
14
15 The extracellular matrix provides a microenvironment for cells which is not yet fully
16 understood, nor replicable by existing manufacturing methods ^{16,67-69}. By manipulating human
17 cells to produce a customizable blend of ECM components, and combining this with replicable
18 electrospun scaffolds and decellularization methods we overcome the shortage of donor
19 derived ECM bioscaffolds and the issues regarding animal-sourced biomaterials ^{16,70}.
20 Additionally, this platform has the potential to be used to model not only 'healthy' ECM
21 microenvironments, but also those of disease and developing states.
22
23
24
25
26
27
28

29
30 By using fibrous electrospun scaffolds we mimic the morphology of healthy fibrillary collagen
31 ^{10,11,71,72}. PLA was used to fabricate the scaffolds, chosen for its compatibility with hepatocytes
32 ⁵⁶ and its use in multiple types of medical device due to its predictable biodegradation rate and
33 mechanical properties ^{73,74}.
34
35
36
37
38

39
40 Fibronectin was chosen as our protein to synthetically overexpress due to its vital role in the
41 liver ^{51,75} and its interaction with other ECM components such as collagen and laminin ^{52,53}.
42 Fibronectin is a large dimeric adhesive glycoprotein which exists in both cellular and plasma
43 forms, with roles in regenerating tissues, embryonic development and regulation of cell
44 behaviours such as adhesion and migration ⁷⁶. The role of fibronectin in the liver is still unclear,
45 with inhibition of fibronectin production or deposition improving fibrosis outcomes ^{77,78}.
46 However its vital role in the hepatic ECM is demonstrated by mutant mice who were
47 specifically null in only the liver for both plasma and cellular fibronectin. The fibronectin-null
48 livers not only develop highly disorganized/diffuse collagenous ECM networks, but when
49 fibrogenesis was induced the null livers experienced more extensive fibrosis; thought to be
50
51
52
53
54
55
56
57
58
59
60

1
2
3 due to fibronectins role in regulating TGF- β 1 bioavailability ⁷⁵. Additionally, homozygous
4 fibronectin null mutants display early embryonic lethality, while heterozygotes (with 50% of the
5 normal plasma fibronectin levels) appear normal; suggesting a dose dependent role for
6 fibronectin in development ⁷⁹.
7
8
9

10
11
12 As an initial assessment of these novel hybrid scaffolds we investigated the attachment and
13 function of a commonly used liver cell line, HepG2s, when cultured on the synthetically derived
14 hybrid scaffolds versus a wild type 'normal' hybrid scaffold and the scaffold alone. The HepG2
15 cell line was derived from the hepatocarcinoma of a 15 year old Caucasian male. They are
16 often used because they are virus free, possess liver specific functions such as ammonia
17 metabolism and albumin synthesis and secrete some growth factors ⁸⁰. We analysed cell
18 attachment and viability, albumin production and gene expression of both liver function genes
19 and ECM genes at 3 and 5 day time points. Additionally, we validated our decellularization
20 method and performed both immunohistochemical and raman spectrum analyses (data not
21 shown) of the hybrid scaffold-ECM constructs upon which the HepG2s were seeded.
22
23
24
25
26
27
28
29
30
31
32

33
34 Our results indicate not only that synthetically derived ECMs provide a viable method of
35 biofunctionalising electrospun polymer scaffolds, but that the composition of the synthetically
36 derived ECM-polymer hybrid scaffolds influences liver cells. That albumin production is
37 significantly altered between SO and SD-ECM conditions, but not N-ECM conditions supports
38 this assertion. Gene expression of key hepatic genes was altered on day 5 of SD-ECM
39 conditions in every gene tested, whereas SO and N-ECM conditions only influence CYP1A2
40 and COL4A1 expression; demonstrating that the composition of the ECM is highly influential
41 in tissue engineering. This in turn leads to questions regarding donor-donor variability of
42 current decellularization work and its influence upon hepatic behaviour and a need for more
43 reproducible hepatic microenvironments that this platform provides.
44
45
46
47
48
49
50
51
52
53
54

55
56 The researchers responsible recognise that, while this study forms a robust initial proof of
57 principle regarding the exploitation of synthetic biology for scaffold manufacture, and has
58 produced a novel hybrid synthetically derived ECM- polymer scaffold with great potential for
59
60

1
2
3 liver tissue engineering, further work is required to analyse results and increase translatability.
4
5 Vector technologies and synthetic biology present obvious concerns with regards to patient
6
7 safety^{30,81}, and care should be taken to ensure all bacterial/ viral constructs are removed from
8
9 the ECM layer. Detergent based methods used to strip the ECM of cells can be detrimental to
10
11 the bioscaffold^{70,82}, disrupting native tissue ultrastructure, decreasing glycosaminoglycan
12
13 (GAG) content and reducing collagen integrity^{83,84} as well as disrupting lipid-lipid, lipid-protein
14
15 and protein-protein interactions⁸⁵. Care should be taken to optimise this procedure in the
16
17 future. HepG2s provide a convenient method of initial viability testing of the scaffolds, but they
18
19 are derived from a carcinoma and as such criticism of their clinical relevance is well placed.
20
21 Further studies will utilise primary or stem cell derived hepatocytes to combat such criticism.
22
23 Additionally, recognition of the value of further proteomic and functional assays (such as
24
25 ELISAs and Alkaline Phosphatase quantitation) in analysing the function of hepatocytes will
26
27 be vital for expanding this work, however at this time these were deemed unnecessary
28
29 considering the obvious critiques of the use of the HepG2 cell line. Further, the importance of
30
31 ensuring decellularization agents are removed from the constructs should not be
32
33 underestimated, due to their influence upon cells and ECM^{21,70}. While such criticisms are
34
35 important to consider, this work clearly demonstrates the potential of synthetic biology for the
36
37 design of bespoke ECMs and provides a robust initial platform upon which further, improved
38
39 studies can be built.
40
41
42
43

44 **Conclusion**

45
46 This study demonstrates a novel method of creating a biologically bespoke hybrid ECM-
47
48 polymer scaffold; utilising clinically translatable electrospun scaffold technologies and
49
50 synthetic biology methods both easily modified to fulfil Good Manufacturing Practice (GMP)
51
52 guidelines. In order to achieve this, a sacrificial ECM-producing cell layer was transfected
53
54 using a protein producing fibronectin vector on an electrospun scaffold, biofunctionalizing the
55
56 scaffold with a biologically bespoke ECM. Scaffolds with wild type untransfected cells and no
57
58 initial cell layer at all were used as controls. This sacrificial cell layer was successfully removed
59
60

1
2
3 with a detergent based method and the hybrid synthetically derived ECM-polymer scaffolds
4 seeded with HepG2 liver cells for validation. Results were validated using multiple well
5 characterized methods, including mechanical quantitation, Q-PCR and
6 immunohistochemistry. The synthetically derived PLA-ECM scaffolds exert biological
7 influence upon liver cells, manipulating their microenvironment and resulting in alterations in
8 gene expression profile, protein synthesis and cell attachment and survival. Such data
9 demonstrates promise as a unique method of creating biologically bespoke ECMs and
10 exerting influence upon cell populations both *in vivo* and *in vitro*.
11
12
13
14
15
16
17
18
19

20 These novel scaffolds exhibit great promise both as an implantable patient treatment for liver
21 tissue engineering, for adaptation to other tissues and as a useful tool for development of 3D
22 liver cell culture platforms with potential for both *in vivo* cell analysis and novel pharmaceutical
23 research.
24
25
26
27
28

29 **Acknowledgements**

30
31
32 The authors would like to thank Prof Alistair Elfick for use of lab facilities (IBioE, University of
33 Edinburgh). We would also like to thank Steve Mitchell (BioSEM) and Dr David Kelly (COIL)
34 (University of Edinburgh). This work is funded by an Engineering & Physical Sciences
35 Research Council [EPSRC] doctoral training partnership studentship, UK Regenerative
36 Medicine Platform II [RMP II] grant MR/L022974/1 and MRC computational and chemical
37 biology of the stem cell niche grant (CCBN) MR/L012766/1.
38
39
40
41
42
43
44
45

46 **Author disclosure**

47
48 The authors declare no competing interests.
49
50

- 51 1. British Association for the Study of the Liver & British Society of Gastroenterology. A
52 Time to Act: Improving Liver Health and Outcomes in Liver Disease. *Natl. Plan Liver*
53 *Serv. UK* 1–52 (2009).
- 54 2. Williams, R. *et al.* Implementation of the Lancet Standing Commission on Liver
55 Disease in the UK. *Lancet* **386**, 2098–2111 (2015).
- 56 3. Wang, H. *et al.* Global, regional, and national life expectancy, all-cause mortality, and
57 cause-specific mortality for 249 causes of death, 1980–2015: a systematic analysis
58 for the Global Burden of Disease Study 2015. *Lancet* **388**, 1459–1544 (2016).
59
60

- 1
 - 2
 - 3
 4. Huch, M. *et al.* Long-term culture of genome-stable bipotent stem cells from adult human liver. *Cell* **160**, 299–312 (2015).
 - 5
 - 6
 - 7
 - 8
 - 9
 - 10
 - 11
 - 12
 - 13
 - 14
 - 15
 - 16
 - 17
 - 18
 - 19
 - 20
 - 21
 - 22
 - 23
 - 24
 - 25
 - 26
 - 27
 - 28
 - 29
 - 30
 - 31
 - 32
 - 33
 - 34
 - 35
 - 36
 - 37
 - 38
 - 39
 - 40
 - 41
 - 42
 - 43
 - 44
 - 45
 - 46
 - 47
 - 48
 - 49
 - 50
 - 51
 - 52
 - 53
 - 54
 - 55
 - 56
 - 57
 - 58
 - 59
 - 60
4. Huch, M. *et al.* Long-term culture of genome-stable bipotent stem cells from adult human liver. *Cell* **160**, 299–312 (2015).
 5. Ye, J., Shirakigawa, N. & Ijima, H. Hybrid organoids consisting of extracellular matrix gel particles and hepatocytes for transplantation. *J. Biosci. Bioeng.* (2015). doi:10.1016/j.jbiosc.2015.01.004
 6. Takebe, T. *et al.* Vascularized and complex organ buds from diverse tissues via mesenchymal cell-driven condensation. *Cell Stem Cell* **16**, 556–565 (2015).
 7. Banaeiyan, A. A. *et al.* Design and fabrication of a scalable liver-lobule-on-a-chip microphysiological platform. *Biofabrication* **9**, (2017).
 8. Grant, R., Hay, D. & Callanan, A. A Drug-Induced Hybrid Electrospun Poly-Caprolactone: Cell-Derived Extracellular Matrix Scaffold for Liver Tissue Engineering. *Tissue Eng. Part A* **23**, 650–662 (2017).
 9. Nichol, J. W. *et al.* Cell-laden microengineered gelatin methacrylate hydrogels. *Biomaterials* **31**, 5536–44 (2010).
 10. McCullen, S. D., Autefage, H., Callanan, A., Gentleman, E. & Stevens, M. M. Anisotropic Fibrous Scaffolds for Articular Cartilage Regeneration. *Tissue Eng. Part A* **18**, 2073–2083 (2012).
 11. Accardi, M. A. *et al.* Effects of fiber orientation on the frictional properties and damage of regenerative articular cartilage surfaces. *Tissue Eng. Part A* **19**, 2300–10 (2013).
 12. Steele, J. A. M. *et al.* Combinatorial scaffold morphologies for zonal articular cartilage engineering. *Acta Biomater.* **10**, 2065–2075 (2014).
 13. Noszczyk, B. H. *et al.* Biocompatibility of electrospun human albumin: a pilot study. *Biofabrication* **7**, 15011 (2015).
 14. Grant, R., Hay, D. & Callanan, A. A drug induced hybrid electrospun PCL - cell derived ECM scaffold for liver tissue engineering. *Tissue Eng. Part A* ten.TEA.2016.0419 (2017). doi:10.1089/ten.TEA.2016.0419
 15. Naderi, H., Matin, M. M. & Bahrami, A. R. Review paper: critical issues in tissue engineering: biomaterials, cell sources, angiogenesis, and drug delivery systems. *J. Biomater. Appl.* **26**, 383–417 (2011).
 16. He, M. & Callanan, A. Comparison of methods for whole organ decellularisation in tissue engineering of bio-artificial organs. *Tissue Eng. Part B Rev.* **19**, (2012).
 17. De Kock, J. *et al.* Simple and quick method for whole-liver decellularization: A novel in vitro three-dimensional bioengineering tool? *Arch. Toxicol.* **85**, 607–612 (2011).
 18. Baptista, P. M. *et al.* The use of whole organ decellularization for the generation of a vascularized liver organoid. *Hepatology* **53**, 604–617 (2011).
 19. Barakat, O. *et al.* Use of decellularized porcine liver for engineering humanized liver organ. *J. Surg. Res.* **173**, e11–e25 (2012).
 20. Wu, Q. *et al.* Optimizing Perfusion-Decellularization Methods of Porcine Livers for Clinical-Scale Whole-Organ Bioengineering. *Biomed Res. Int.* **2015**, 1–9 (2015).
 21. Zhou, P. *et al.* Decellularization and Recellularization of Rat Livers With Hepatocytes and Endothelial Progenitor Cells. *Artif. Organs* n/a-n/a (2016). doi:10.1111/aor.12645
 22. Faulk, D. M., Wildemann, J. D. & Badylak, S. F. Decellularization and Cell Seeding of Whole Liver Biologic Scaffolds Composed of Extracellular Matrix. *J. Clin. Exp.*

- 1
2
3 *Hepatol.* **5**, 69–80 (2015).
- 4
- 5 23. Kogel, J. Van Der, Bussink, J., Coxon, A., Polverino, A. & M, P. Fluid flow regulation
6 of revascularization and cellular organization in a bioengineered liver platform. *Tissue*
7 *Eng. Part C Methods* 1–22 (2016).
- 8
- 9 24. Hazama, K., Asayama, S. & Kawakami, H. Up-Regulation of Gene Expression by
10 Transfection to Hepatocyte Spheroids. *Mol. Pharm.* (2012).
- 11
- 12 25. Lee, M. H. *et al.* Hepatocyte-Targeting Single Galactose-Appended Naphthalimide: A
13 Tool for Intracellular Thiol Imaging in Vivo. *J. Am. Chem. Soc.* **134**, 1316–1322
14 (2012).
- 15
- 16 26. Lu, C., Xu, W., Zhang, F., Shao, J. & Zheng, S. Nrf2 Knockdown Disrupts the
17 Protective Effect of Curcumin on Alcohol-Induced Hepatocyte Necroptosis. *Mol.*
18 *Pharm.* **13**, 4043–4053 (2016).
- 19
- 20 27. Narsinh, K. H. *et al.* Generation of adult human induced pluripotent stem cells using
21 nonviral minicircle DNA vectors. *Nat. Protoc.* **6**, 78–88 (2010).
- 22
- 23 28. Cachat, E. *et al.* 2- and 3-Dimensional Synthetic Large-Scale De Novo Patterning By
24 Mammalian Cells Through Phase Separation. *Sci. Rep.* **6**, 20664 (2016).
- 25
- 26 29. Chen, A. Y., Zhong, C. & Lu, T. K. Engineering Living Functional Materials. *ACS*
27 *Synth. Biol.* **4**, 8–11 (2015).
- 28
- 29 30. Zhou, D. *et al.* Highly branched poly(β -amino ester)s for skin gene therapy. *J. Control.*
30 *Release* (2016). doi:10.1016/j.jconrel.2016.06.014
- 31
- 32 31. Cutlar, L. *et al.* A Non-Viral Gene Therapy for Treatment of Recessive Dystrophic
33 Epidermolysis Bullosa. *Exp. Dermatol.* 818–820 (2016).
- 34
- 35 32. Deltcheva, E. *et al.* CRISPR RNA maturation by trans-encoded small RNA and host
36 factor RNase III. *Nature* **471**, 602–609 (2011).
- 37
- 38 33. Jinek, M. *et al.* A Programmable Dual-RNA-Guided DNA Endonuclease in Adaptive
39 Bacterial Immunity. *Science (80-.)*. **337**, 816–821 (2012).
- 40
- 41 34. Fonfara, I., Richter, H., Bratovič, M., Le Rhun, A. & Charpentier, E. The CRISPR-
42 associated DNA-cleaving enzyme Cpf1 also processes precursor CRISPR RNA
43 CRISPR–Cas systems that provide defence against mobile genetic elements in
44 bacteria and archaea have evolved a variety of mechanisms to target and cleave RNA
45 or DNA. *Nature* **532**, 517–523 (2016).
- 46
- 47 35. Kay, M. A., He, C.-Y. & Chen, Z.-Y. A robust system for production of minicircle DNA
48 vectors. *Nat. Biotechnol.* **28**, 1287–1289 (2010).
- 49
- 50 36. Yi, H. *et al.* A New Strategy to Deliver Synthetic Protein Drugs: Self-reproducible
51 Biologics Using Minicircles. *Sci. Rep.* **4**, 5961 (2014).
- 52
- 53 37. Munye, M. M. *et al.* Minicircle DNA Provides Enhanced and Prolonged Transgene
54 Expression Following Airway Gene Transfer. *Sci. Rep.* **6**, 23125 (2016).
- 55
- 56 38. Sibbald, B. Death but one unintended consequence of gene-therapy trial. *CMAJ* **164**,
57 1612 (2001).
- 58
- 59 39. Romero, Z., Toscano, M., Unciti, J., Molina, I. & Martin, F. Safer Vectors for Gene
60 Therapy of Primary Immunodeficiencies. *Curr. Gene Ther.* **9**, 291–305 (2009).
- 60 40. Pisetsky, D. S. The origin and properties of extracellular DNA: from PAMP to DAMP.
Clin. Immunol. **144**, 32–40 (2012).

- 1
 - 2
 - 3
 - 4
 - 5
 - 6
 - 7
 - 8
 - 9
 - 10
 - 11
 - 12
 - 13
 - 14
 - 15
 - 16
 - 17
 - 18
 - 19
 - 20
 - 21
 - 22
 - 23
 - 24
 - 25
 - 26
 - 27
 - 28
 - 29
 - 30
 - 31
 - 32
 - 33
 - 34
 - 35
 - 36
 - 37
 - 38
 - 39
 - 40
 - 41
 - 42
 - 43
 - 44
 - 45
 - 46
 - 47
 - 48
 - 49
 - 50
 - 51
 - 52
 - 53
 - 54
 - 55
 - 56
 - 57
 - 58
 - 59
 - 60
41. Hotaling, N. a., Bharti, K., Kriel, H. & Simon, C. G. DiameterJ: A validated open source nanofiber diameter measurement tool. *Biomaterials* **61**, 327–338 (2015).
42. Lakes, R. Foam Structures with a Negative Poisson's Ratio. *Science (New York, N.Y.)* **235**, 1038–1040 (1987).
43. Greaves, G. N., Greer, A. L., Lakes, R. S. & Rouxel, T. Poisson's ratio and modern materials. *Nat. Mater.* **10**, 823–37 (2011).
44. Oliver, W. C. & Pharr, G. M. An improved technique for determining hardness and elastic modulus using load and displacement sensing indentation experiments. *Journal of Materials Research* **7**, 1564–1583 (2011).
45. Akhtar, R. *et al.* Nanoindentation of histological specimens: Mapping the elastic properties of soft tissues. *J. Mater. Res.* **24**, 638–646 (2009).
46. Livak, K. J. & Schmittgen, T. D. Analysis of relative gene expression data using real-time quantitative PCR and the 2- $\Delta\Delta$ CT method. *Methods* **25**, 402–408 (2001).
47. Callanan, A., Davis, N. F., McGloughlin, T. M. & Walsh, M. T. Development of a rotational cell-seeding system for tubularized extracellular matrix (ECM) scaffolds in vascular surgery. *J. Biomed. Mater. Res. Part B Appl. Biomater.* **102**, 781–788 (2014).
48. Bartlett, M. S. Properties of Sufficiency and Statistical Tests. *Proc. R. Soc. A Math. Phys. Eng. Sci.* **160**, 268–282 (1937).
49. Meier, U. A note on the power of Fisher's least significant difference procedure. *Pharm. Stat.* **5**, 253–263 (2006).
50. McHugh, M. L. Multiple comparison analysis testing in ANOVA. *Biochem. Medica* 203–209 (2011). doi:10.11613/BM.2011.029
51. Klaas, M. *et al.* The alterations in the extracellular matrix composition guide the repair of damaged liver tissue. *Sci. Rep.* **6**, 27398 (2016).
52. Kubow, K. E. *et al.* Mechanical forces regulate the interactions of fibronectin and collagen I in extracellular matrix. *Nat. Commun.* **6**, 8026 (2015).
53. Sottile, J. & Hocking, D. C. Fibronectin Polymerization Regulates the Composition and Stability of Extracellular Matrix Fibrils and Cell-Matrix Adhesions. *Mol. Biol. Cell* **14**, 3546–3559 (2002).
54. Discher, D. E., Janmey, P. & Wang, Y.-L. Tissue cells feel and respond to the stiffness of their substrate. *Science* **310**, 1139–43 (2005).
55. Klatt, D. *et al.* Viscoelastic properties of liver measured by oscillatory rheometry and multifrequency magnetic resonance elastography. *Biorheology* **47**, 133–141 (2010).
56. Torok, E. *et al.* Primary Human Hepatocytes on Biodegradable Poly(L-Lactic acid) Matrices: A Promising Model for Improving Transplantation Efficiency With Tissue Engineering. *Liver Transplant.* **13**, 465–466 (2011).
57. Loneker, A. E., Faulk, D. M., Hussey, G. S., D'Amore, A. & Badylak, S. F. Solubilized liver extracellular matrix maintains primary rat hepatocyte phenotype in-vitro. *J. Biomed. Mater. Res. A* 1–9 (2015).
58. Gao, R. *et al.* Hepatocyte Culture in Autologous Decellularized Spleen Matrix. *Organogenesis* (2015).
59. Martinez-Hernandez, A. & Amenta, P. S. The hepatic extracellular matrix I. Components and distribution in normal liver. *Virchows Arch. A Pathol. Anat.*

- 1
2
3 *Histopathol.* **423**, 1–11 (1993).
4
5 60. Cameron, K. *et al.* Recombinant Laminins Drive the Differentiation and Self-
6 Organization of hESC-Derived Hepatocytes. *Stem Cell Reports* **5**, 1–13 (2015).
7
8 61. Pankov, R. & Yamada, K. M. Fibronectin at a glance. *J. Cell Sci.* **115**, 3861–3863
9 (2002).
10
11 62. Seliskar, M. & Rozman, D. Mammalian cytochromes P450-Importance of tissue
12 specificity. *Biochim. Biophys. Acta - Gen. Subj.* **1770**, 458–466 (2007).
13
14 63. Medine, C. N. *et al.* Developing high-fidelity hepatotoxicity models from pluripotent
15 stem cells. *Stem Cells Transl. Med.* **2**, 505–9 (2013).
16
17 64. Palakkan, A. A. *et al.* Polarisation and functional characterisation of hepatocytes
18 derived from human embryonic and mesenchymal stem cells. *Biomed. reports* **3**,
19 626–636 (2015).
20
21 65. Saad, B. *et al.* Crude liver membrane fractions and extracellular matrix components
22 as substrata regulate differentially the preservation and inducibility of cytochrome P-
23 450 isoenzymes in cultured rat hepatocytes. *Eur J Biochem* **213**, 805–814 (1993).
24
25 66. Badylak, S. F. The extracellular matrix as a scaffold for tissue reconstruction. *Semin.*
26 *Cell Dev. Biol.* **13**, 377–383 (2002).
27
28 67. Badylak, S. F., Dziki, J. L., Sicari, B. M., Ambrosio, F. & Boninger, M. L. Mechanisms
29 by which acellular biologic scaffolds promote functional skeletal muscle restoration.
30 *Biomaterials* **103**, 128–136 (2016).
31
32 68. Meng, F. W., Slivka, P. F., Dearth, C. L. & Badylak, S. F. Solubilized extracellular
33 matrix from brain and urinary bladder elicits distinct functional and phenotypic
34 responses in macrophages. *Biomaterials* **46**, 131–40 (2015).
35
36 69. Davis, N. F., Coakley, D. N., Callanan, A., Flood, H. D. & McGloughlin, T. M.
37 Evaluation of xenogenic extracellular matrices as adjuvant scaffolds for the treatment
38 of stress urinary incontinence. *Int. Urogynecol. J.* **24**, 2105–10 (2013).
39
40 70. He, M., Callanan, A., Lagaras, K., Steele, J. A. M. & Stevens, M. M. Optimization of
41 SDS exposure on preservation of ECM characteristics in whole organ
42 decellularization of rat kidneys. *J. Biomed. Mater. Res. Part B Appl. Biomater.* 1–9
43 (2016).
44
45 71. Burton, T. P., Corcoran, A. & Callanan, A. The effect of electrospun polycaprolactone
46 scaffold morphology on human kidney epithelial cells. *Biomed. Mater* **13**, (2018).
47
48 72. Burton, T. P., Corcoran, A. & Callanan, A. The effect of electrospun polycaprolactone
49 scaffold morphology on human kidney epithelial cells. *Biomed. Mater.* **13**, 15006
50 (2017).
51
52 73. Casasola, R., Thomas, N. L., Trybala, A. & Georgiadou, S. Electrospun poly lactic
53 acid (PLA) fibres: Effect of different solvent systems on fibre morphology and
54 diameter. *Polym. (United Kingdom)* **55**, 4728–4737 (2014).
55
56 74. Rafael Auras, Lim, L.-T., Selke, S. E. M. & Tsuji, H. *Poly(Lactic Acid): Synthesis,*
57 *Structures, Properties, Processing, and Applications.* (2010).
58
59 75. Iwasaki, A. *et al.* Molecular mechanism responsible for fibronectin-controlled
60 alterations in matrix stiffness in advanced chronic liver fibrogenesis. *J. Biol. Chem.*
291, 72–88 (2016).
61
62 76. Zollinger, A. J. & Smith, M. L. Fibronectin, the extracellular glue. *Matrix Biol.* (2016).

1
2
3 doi:10.1016/j.matbio.2016.07.011
4

- 5 77. Kawelke, N. *et al.* Fibronectin protects from excessive liver fibrosis by modulating the
6 availability of and responsiveness of stellate cells to active TGF- β . *PLoS One* **6**,
7 e28181 (2011).
8
9 78. Altrock, E. *et al.* Inhibition of fibronectin deposition improves experimental liver
10 fibrosis. *J. Hepatol.* **62**, 625–633 (2015).
11
12 79. George, E. L., Georges-Labouesse, E. N., Patel-King, R. S., Rayburn, H. & Hynes, R.
13 O. Defects in mesoderm, neural tube and vascular development in mouse embryos
14 lacking fibronectin. *Development* **119**, 1079–1091 (1993).
15
16 80. Costantini, S., Di Bernardo, G., Cammarota, M., Castello, G. & Colonna, G. Gene
17 expression signature of human HepG2 cell line. *Gene* **518**, 335–45 (2013).
18
19 81. Gorell, E., Nguyen, N., Lane, A. & Siprashvili, Z. Gene therapy for skin diseases. *Cold*
20 *Spring Harb Perspect Med* **4**, a015149 (2014).
21
22 82. Peloso, A. *et al.* Current achievements and future perspectives in whole-organ
23 bioengineering. *Stem Cell Res. Ther.* **6**, (2015).
24
25 83. Woods, T. & Gratzner, P. F. Effectiveness of three extraction techniques in the
26 development of a decellularized bone-anterior cruciate ligament-bone graft.
27 *Biomaterials* **26**, 7339–7349 (2005).
28
29 84. Funamoto, S. *et al.* The use of high-hydrostatic pressure treatment to decellularize
30 blood vessels. *Biomaterials* **31**, 3590–3595 (2010).
31
32 85. Cebotari, S. *et al.* Detergent decellularization of heart valves for tissue engineering:
33 Toxicological effects of residual detergents on human endothelial cells. *Artif. Organs*
34 **34**, 206–210 (2010).
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60