



THE UNIVERSITY *of* EDINBURGH

Edinburgh Research Explorer

Photo-Controlled One-Pot Strategy for the Synthesis of Asymmetric Three-Arm Star Polymers

Citation for published version:

Zhang, Y, Bradley, M & Geng, J 2019, 'Photo-Controlled One-Pot Strategy for the Synthesis of Asymmetric Three-Arm Star Polymers', *Polymer chemistry*. <https://doi.org/10.1039/C9PY00774A>

Digital Object Identifier (DOI):

[10.1039/C9PY00774A](https://doi.org/10.1039/C9PY00774A)

Link:

[Link to publication record in Edinburgh Research Explorer](#)

Document Version:

Peer reviewed version

Published In:

Polymer chemistry

General rights

Copyright for the publications made accessible via the Edinburgh Research Explorer is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy

The University of Edinburgh has made every reasonable effort to ensure that Edinburgh Research Explorer content complies with UK legislation. If you believe that the public display of this file breaches copyright please contact openaccess@ed.ac.uk providing details, and we will remove access to the work immediately and investigate your claim.



COMMUNICATION

Photo-Controlled One-Pot Strategy for the Synthesis of Asymmetric Three-Arm Star Polymers

Yichuan Zhang,^a Mark Bradley^a and Jin Geng^{*a, b}

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

A rapid photo-controlled one-pot strategy for the synthesis of asymmetric star polymers was developed using two different wavelengths of light to allow spatial and temporal control of the synthesis of the star polymers with controlled structures and narrow polydispersities. Several asymmetric star structures were successfully synthesised and the simultaneous photo-induced ATRP and RAFT polymerisation was demonstrated using this procedure.

Introduction

Block-copolymers with various architectures that include conventional linear forms as well as stars, combs and rings have attracted great interests in material science and biological sciences. Star-shape block-copolymers having either chemically different arms (also known as miktoarm stars) or arms with the same composition have attracted increasing attention over the past two decades owing to their distinct architectures and unique physical and chemical properties in both bulk and solution.^{1, 2} For instance, the phase boundaries of star polymers are different from the linear analogues resulting in dissimilar self-assembly behaviours^{3, 4} and viscosities⁵. The high chain end functionality density gives the opportunity for high degrees of chemical modifications of the polymers,⁶ that contribute to potential applications such as nano/macro materials^{7, 8} morphology modifiers,⁹ catalysis,¹⁰ emulsifiers¹¹ and drug delivery carriers¹². Much effort has focused on the design and development of new star polymers, however complicated synthesis routes and the time consuming isolation processes resulting in many limitations.

The 'arm first' approach is widely used in the synthesis of star polymers, which starts from an end functionalised linear polymer followed by a coupling reaction with a multifunctional reagent.^{6, 13} In comparison to the 'core first' strategy, which

utilise a multifunctional initiating motif (the core) upon which are grown multiple polymer chains,¹⁴ the 'arm first' approach avoids the tedious synthesis of complicated initiator cores, and therefore offers a more straightforward way of producing the target star polymers. However, it is still challenging to synthesise well defined asymmetric miktoarm star polymers because of the limited efficiency of core-arm coupling reaction and the complexity of isolation of intermediates/products from the macromolecular mixture.⁵

Reactions with high yield, minimal side product profiles and high reaction rates that form robust products are required for the coupling chemistry for the synthesis of star polymers. Active functionalities such as active esters,¹⁵ epoxides,¹⁶ isocyanates,¹⁷ chlorotriazines,¹⁸ maleimides,¹⁹ thiols²⁰ and azides²¹ have been utilised for polymer-polymer and polymer-small molecule conjugations. In comparison to these conjugation reactions, strained alkene-tetrazine inverse electron-demand Diels-Alder (IEDDA) chemistry benefit from being catalyst-free, and offer high selectivity, rapid reaction rates and the generation of robust adducts.²²⁻²⁴

Pauses and terminations of polymerisations are often required to achieve a desired structure or molecular weight star and there is thus a growing interest in being able to controllably induce/initiate reactions by external stimuli, *e.g.* potential, light and mechanical forces.²⁵ Light is one of the most favoured energy sources for the temporal and spatial control of reactions, because of the straightforward nature of the processes, the mild reaction conditions and minimised side reactions.²⁶ One such example is photoinduced electron transfer (PET) polymerisation, which is able to precisely control the molecular weight and polydispersity of the synthesized polymers,²⁷⁻²⁹ while tolerating molecular oxygen and offering compatibility to many functional monomers.^{26, 28}

Herein we report new methods for the rapid synthesis of asymmetric miktoarm star polymers through a one-pot tandem strategy combining photo-controlled tetrazine formation chemistry, norbornene-tetrazine IEDDA chemistry and PET-atom transfer radical polymerisation (ATRP) with precise spatial

^{a, b}EaSTCHEM School of Chemistry, University of Edinburgh, United Kingdom

^bShenzhen Institutes of Advanced Technology, Chinese Academy of Sciences, Shenzhen, P. R. China. E-mail: jin.geng@siat.ac.cn

[†]Electronic Supplementary Information (ESI) available: See DOI: 10.1039/x0xx00000x

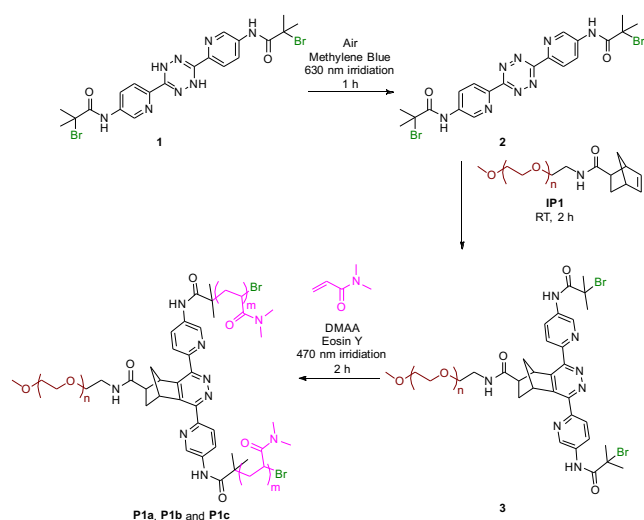


Fig. 1 One-pot synthesis of Star polymer **P1a**, **P1b** and **P1c**. Dihydro-tetrazine **1** was oxidised to give tetrazine **2**, which was subsequently coupled to the macro-initiator precursor **IP1** to generate the macro-initiator **3**. DMAA was then polymerised to give the asymmetric star polymers **P1a**, **P1b** and **P1c** ([DMAA]:[**3**] = 1000:1, 200:1 and 2000:1, respectively).

and temporal control using different wavelength light. A bromine functionalised dihydro-tetrazine ATRP initiator precursor was photo-oxidised aided by a photosensitiser to give a bromine functionalised tetrazine,³⁰ which was subsequently coupled to a norbornene-terminated polyethylene glycol (PEG) resulting in a macro-ATRP initiator, and was polymerised with an acrylamide monomer via a metal free PET-ATRP process to give the desired asymmetric star polymer. The whole process was conducted at ambient temperature in presence of air without the need of any intermediate isolation steps.

Results and discussion

The macro-initiator precursor, ω -norbornene-PEG **IP1** was synthesised by coupling an amine functionalised PEG and a norbornene carboxylic acid (see ESI, Fig. S10). The dihydro-tetrazine precursor **1** was synthesised in two-steps in which the diaminopyridyl dihydro-tetrazine **S1** was synthesised from amino pyridine-carbonitrile according to the previous method³⁰ with the α -bromoisobutryl group introduced through an acid bromide-amine coupling chemistry (see ESI, Fig. S11). The dihydro-tetrazine was oxidised using *i*-pentyl nitrite, to give tetrazine **2** for comparison (see ESI, Fig. S11).³¹

In the one-pot system, reagents dihydro-tetrazine **1** (2.1 mM), methylene blue (0.4 mM), 1,4-diazabicyclo[2.2.2]octane (DABCO) (34.0 mM), Eosin Y (0.2 mM), an acrylamide monomer (1000 mM), and macro-initiator precursor **IP1** (2.0 mM) were combined. The tetrazine formation reaction and the PET-ATRP were initiated independently using two different light sources (at 630 nm and 470 nm, respectively, Fig. 1).

Methylene blue was used as a photosensitiser that catalysed the oxidation of the dihydro-tetrazine with DABCO used as a singlet oxygen quencher. Eosin Y was used as the photo-catalyst for the polymerisation reaction due to its high efficiency while giving polymers with low polydispersities.³² In addition, during

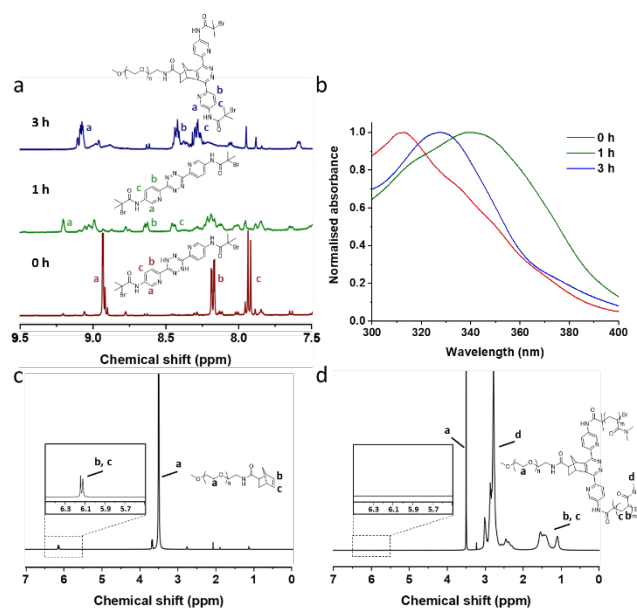


Fig. 2 (a) ^1H NMR spectra of the one-pot reaction mixture after 1h (showing the aromatic region, from 7.5 ppm to 9.5 ppm, d_6 -DMSO). Red, $t=0$ h, before oxidation (dihydro-tetrazine **1**); Green, $t=1$ h (generation of tetrazine **2** with 1 h irradiation at 630 nm); Blue, $t=3$ h (generating **3** by further incubation for 2 h). (b) UV-*vis* spectra of the reaction mixture. Red, $t=0$ h; Green, $t=1$ h; Blue, $t=3$ h. (c) and (d) ^1H NMR spectra (d_6 -DMSO) of macro-initiator precursor **IP1** and star polymers **P1b** (isolated by dialysis, MWCO = 3,500).

the polymerisation, DABCO also acted as an electron donor to accelerate the PET reaction.³³

To evaluate this chemistry as a potentially “one-pot process” each step was initially optimised (see ESI, Table S1). Thus the photo-catalysed oxidation of dihydro-tetrazine and the subsequent norbornene-tetrazine IEDDA chemistry was investigated using ^1H NMR and UV-*vis* spectroscopy (Fig. 2). Molecular oxygen was efficiently activated by methylene blue and 630 nm irradiation ($4.0\text{mW}/\text{cm}^2$) with oxidation of the dihydro-tetrazine **1** to the corresponding tetrazine **2**. The reaction was followed by both ^1H NMR and UV-*vis* analysis (Fig. 2a and 2b) and the tetrazine **2** was identical to that generated using more conventional oxidation routes (see NMR data in ESI, experimental). The non-specific oxidation of the dihydro-tetrazine was minimised using DABCO, which has an agreement with previous studies (ESI, Fig. S6).³⁰

The PET-ATRP progress of *N,N*-dimethylacrylamide (DMAA) on macro-ATRP initiator **3** was investigated using ^1H NMR and

Table 1 Characterisation of the asymmetric star polymers.

[DMAA] / [IP1]	Time (h)	Conversion ^a (%)	M_n^b (kDa)	\bar{D}^b
200/1	2	90	47	1.48
1000/1	2	84	173	1.47
2000/1	2	85	323	1.93
200/1	18	96	64	1.68
1000/1	18	86	249	1.58
2000/1	18	89	391	2.36

^a: determined by ^1H NMR; ^b: determined by GPC (eluting with DMF with 1% LiBr at 60 °C, calibrated with PMMA standards).

Table 2 Characterisation of the asymmetric star polymers using **IP1** ($M_n = 16$ kDa, $\bar{D} = 1.21$), **IP2** ($M_n = 58$ kDa, $\bar{D} = 1.80$) and **IP3** as initiator precursors.

Polymer entry	Macro-initiator precursor	[DMAA] / [macro-initiator precursor]	Conversion ^a (%)	M_n^b (kDa)	\bar{D}^b
P1a	IP1	200/1	90	47	1.48
P1b	IP1	1000/1	84	173	1.47
P1c	IP1	2000/1	85	323	1.93
P2a	IP2	200/1	88	223	1.94
P2b	IP2	1000/1	92	340	1.98
P2c	IP2	2000/1	95	381	2.64
P3a	IP3	200/1	99	24	1.28
P3b	IP3	1000/1	99	164	1.26
P3c	IP3	2000/1	99	208	1.59

^a: determined by $^1\text{H NMR}$; ^b: determined by GPC (eluting with DMF with 1% LiBr at 60 °C, calibrated with PMMA standards).

GPC. Photoinduced polymerisation of DMAA was initiated by illumination at 470 nm ($4.0\text{mW}/\text{cm}^2$) to give asymmetric star polymers (see Fig. 1). We observed that longer irradiation times gave slightly higher conversions and higher molecular weight with polydispersities also increasing (Table 1), attributed to additional chain transfer.³⁴ The resulting polymers, e.g. **P1a** ($\bar{D} = 1.48$) and **P1b** ($\bar{D} = 1.47$) showed moderate increases in molecular weight from the initiator precursor **IP1** ($\bar{D} = 1.21$), although longer polymers e.g. **P1c** ($\bar{D} = 1.93$) gave significant increases.^{35, 36} No polymerisation occurred in the absence of either Eosin Y or the ATRP initiator thus indicating that the photocatalyst Eosin Y did not directly generate free radicals, but undergoes a redox process with the bromine moiety on the initiator as previously reported.³⁷

We observed that polymerisation was only initiated following consumption of the tetrazine **2** and reaction with the

norbornenes, indicating that the tetrazine inhibited the polymerisation process. To confirm this, the commercially available tetrazine, 3,6-di-2-pyridyl-1,2,4,5-tetrazine was added to the reaction mixture consisting of the macro-initiator **3**, DMAA, Eosin Y and DABCO. After illumination at 470 nm for 1 h no polymerisation was observed (ESI, Fig. S8). However, after the full degradation of tetrazines, the polymerisation can be initiated and reached over 80% conversion within 2 h supporting the hypothesis that tetrazines inhibit PET polymerisation, thus providing a powerful switch-on process for controlling chemistry.

In order to further evaluate the one-pot strategy, two other initiator precursors (**IP2** and **IP3**) were synthesised (ESI, Fig. S12 and S13). Using the same procedure as described above, we synthesised three groups of star polymers **P1a**, **P1b** and **P1c** (A_2-B); **P2a**, **P2b** and **P2c** (A_2-B-A_2); **P3a**, **P2b** and **P3c** ($A-A'_2$) (Fig. 2

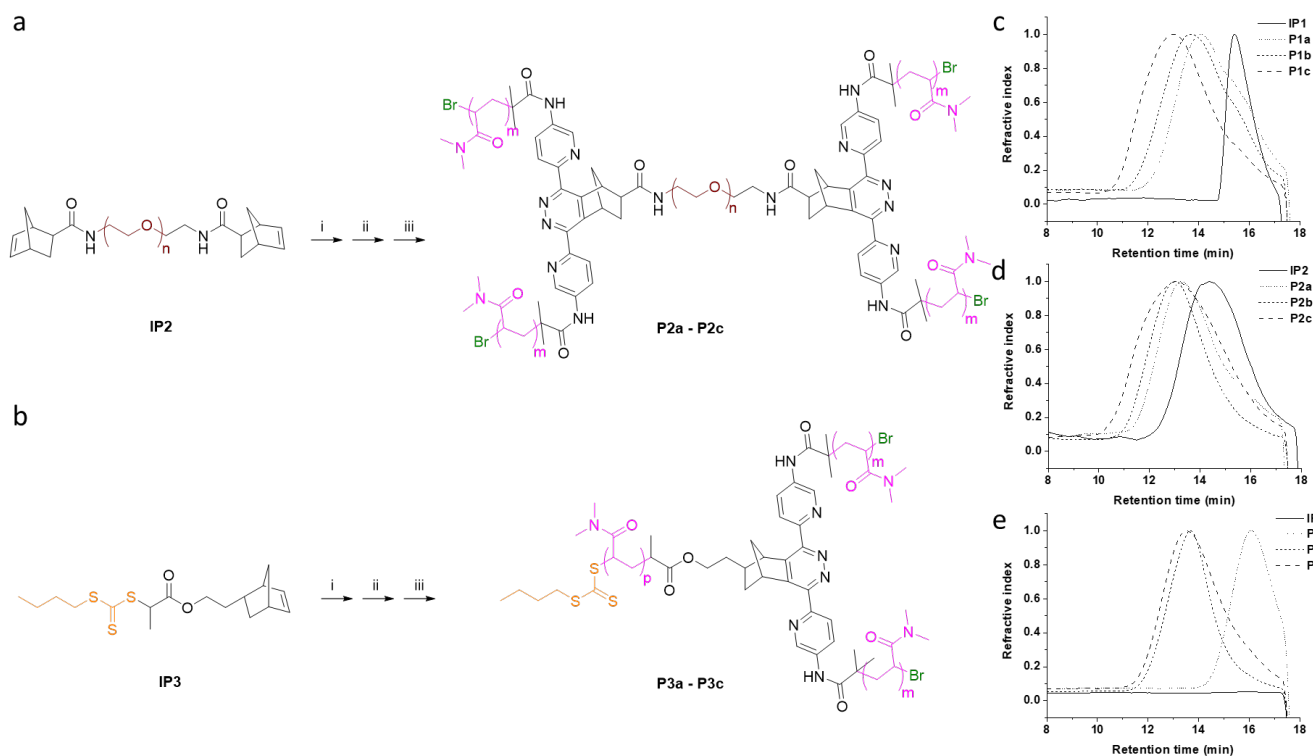


Fig. 3 Synthesis of star polymers from different (macro) initiators. (a) and (b) Synthesis of the asymmetric star polymers **P2a-P2c** and **P3a-P3c** from initiator precursors **IP2** and **IP3**: i) 1, air, Methylene Blue, 630 nm irradiation, 1 h; ii) RT, 2 h; iii) DMAA, Eosin Y, 470 nm irradiation, 2 h. GPC traces of the initiator precursors: (c) **IP1**, (d) **IP2** and (e) **IP3** and their corresponding star polymers.

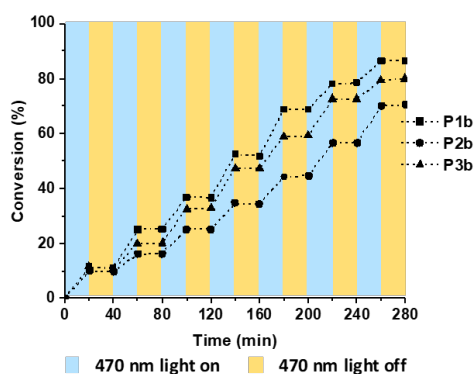


Fig. 4 Plot of monomer conversion versus time. The polymer propagation was controlled by 470 nm light cycling (blue regions = on) and (yellow regions = off). Monomer conversions were quantified by ^1H NMR.

and 3). The photo-induced oxidation and the norbornene-tetrazine IEDDA reactions were complete within 3 h, while the monomer conversion of the polymerisations exceeded 80% after the 2 h photopolymerisation. The polydispersities of the star polymers were inherited from the macro-initiator precursors (**IP1-IP3**) and were nearly unchanged (Table 2).

After purification by dialysis (MWCO = 7 kDa), a small shoulder in GPC traces (15.8 min) in low mass region of the star polymers **P1a** and **P1b** was observed, which could be due to the non-initiated macro-initiators (Fig. 3c).³⁸ To get high quality star polymers, the mixture can be further purified by fractional precipitation³⁹ or SEC column chromatography, although it was not conducted in the current study.

The norbornenyl functionalised trithiocarbonate RAFT chain transfer agent **IP3** was synthesised (see ESI, Fig. S13) in order to conduct simultaneous PET-ATRP and PET-RAFT polymerisations. As previously reported, the reactivity of ATRP and RAFT polymerisation are similar when carried out under the same reaction conditions, giving polymers with similar sizes and polydispersities.⁴⁰ In this study, simultaneous initiation of both polymerisations resulted in A-A'₂ structured star polymers (**P3a**, **P3b** and **P3c**) with the desired molecular weights and narrow dispersities (Table 2).

In general, to minimise the polydispersity and control the molecular weight of polymers, the conversions need to be precisely controlled.³⁶ The photo-induced approach has been employed to allow a remote control of the polymerisation where the reaction can be switched “on” and “off” with and without illumination.^{37, 41} In this study, we also demonstrated that the polymerisation can be conducted as “pause” and “resume” manners with the switches of light (Fig. 4). The polymerisation conversion increased steadily during this process, indicating a well-controlled polymerisation progress.

The compatibility of this approach was further evaluated using two additional monomers (methyl methacrylate and 2-(diethylamino)ethyl acrylate) which gave well-defined stars with ^1H NMR showing identical resonances for different arm compositions and GPC showing narrow dispersities (see ESI, Fig. S9 and Table S2).

Conclusions

A rapid, photo-controlled, asymmetric star polymer synthetic method was developed using the combination of tetrazine-norbornene chemistry and photo-induced polymerisation. This one-pot synthesis simplifies current asymmetric star polymer synthesis strategy, giving well-defined polymers within five hours. The use of two different wavelengths light allows each reaction to be controlled and initiated individually, allowing several well-defined asymmetric star polymers to be synthesised utilising this approach.

The possibility of the synthesis of star polymers with different end functionalities via simultaneous PET-ATRP and PET-RAFT polymerisation were also demonstrated. The resulting terminated ω -bromine and the thiocarbonylthio could be further functionalised independently providing opportunities to generate heterogeneously end-functionalised star polymers.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We thank European Research Council (Advanced Grant ADREEM ERC-2013-340469) for funding.

References

- N. Hadjichristidis, M. Pitsikalis, S. Pispas and H. Iatrou, *Chem. Rev.*, 2001, **101** (12), 3747-3792.
- A. Blencowe, J. F. Tan, T. K. Goh and G. G. Qiao, *Polymer*, 2009, **50** (1), 5-32.
- S. Junnila, N. Houbenov, A. Karatzas, N. Hadjichristidis, A. Hirao, H. Iatrou and O. Ikkala, *Macromolecules*, 2012, **45** (6), 2850-2856.
- N. Hadjichristidis, H. Iatrou, S. Behal, J. Chludzinski, M. Disko, R. Garner, K. Liang, D. Lohse and S. Milner, *Macromolecules*, 1993, **26** (21), 5812-5815.
- T. Higashihara, S. Ito, S. Fukuta, T. Koganezawa, M. Ueda, T. Ishizone and A. Hirao, *Macromolecules*, 2014, **48** (1), 245-255.
- X. Zhang, J. Xia and K. Matyjaszewski, *Macromolecules*, 2000, **33** (7), 2340-2345.
- X. Fan, K. Y. Win, Z. Hu, X. J. Loh and Z. Li, *Macromol. Rapid Commun.*, 2018, **40** (5), 1800217.
- S. Ito, R. Goseki, T. Ishizone and A. Hirao, *Eur. Polym. J.*, 2013, **49** (9), 2545-2566.
- R. Phinjaroenphan, Y. Y. Kim, B. J. Ree, T. Isono, J. Lee, S. Rugmai, H. Kim, S. Maensiri, T. Kakuchi and T. Satoh, *Macromolecules*, 2015, **48** (16), 5816-5833.
- Y. Chi, S. T. Scroggins and J. M. Fréchet, *J. Am. Chem. Soc.*, 2008, **130** (20), 6322-6323.
- Q. Qiu, G. Liu and Z. An, *Chem. Commun.*, 2011, **47** (47), 12685-12687.
- D. E. Discher and A. Eisenberg, *Science*, 2002, **297** (5583), 967-973.

13. M. Morton, T. Helminiak, S. Gadkary and F. Bueche, *J. Polym. Sci.*, 1962, **57** (165), 471-482.
14. K. Matyjaszewski, P. J. Miller, J. Pyun, G. Kickelbick and S. Diamanti, *Macromolecules*, 1999, **32** (20), 6526-6535.
15. A. Das and P. Theato, *Chem. Rev.*, 2015, **116** (3), 1434-1495.
16. D. C. McLeod and N. V. Tsarevsky, *J. Polym. Sci., Part A: Polym. Chem.*, 2016, **54** (8), 1132-1144.
17. J. D. Flores, J. Shin, C. E. Hoyle and C. L. McCormick, *Polym. Chem.*, 2010, **1** (2), 213-220.
18. C. A. Figg, T. Kubo and B. S. Sumerlin, *ACS Macro Lett.*, 2015, **4** (10), 1114-1118.
19. M. P. Robin, M. W. Jones, D. M. Haddleton and R. K. O'Reilly, *ACS Macro Lett.*, 2011, **1** (1), 222-226.
20. C. E. Hoyle, A. B. Lowe and C. N. Bowman, *Chem. Soc. Rev.*, 2010, **39** (4), 1355-1387.
21. V. Coessens, Y. Nakagawa and K. Matyjaszewski, *Polym. Bulletin*, 1998, **40** (2-3), 135-142.
22. C. S. McKay and M. Finn, *Chem. Biol.*, 2014, **21** (9), 1075-1101.
23. K. Neumann, S. Jain, J. Geng and M. Bradley, *Chem. Commun.*, 2016, **52** (75), 11223-11226.
24. S. Jain, K. Neumann, Y. Zhang, J. Geng and M. Bradley, *Macromolecules*, 2016, **49** (15), 5438-5443.
25. F. A. Leibfarth, K. M. Mattson, B. P. Fors, H. A. Collins and C. J. Hawker, *Angew. Chem. Int. Ed.*, 2013, **52** (1), 199-210.
26. G. Li, W. Feng, N. Corrigan, C. Boyer, X. Wang and J. Xu, *Polym. Chem.*, 2018, **9** (20), 2733-2745.
27. J. Xu, K. Jung, A. Atme, S. Shanmugam and C. Boyer, *J. Am. Chem. Soc.*, 2014, **136** (14), 5508-5519.
28. J. Wang, M. Rivero, A. Muñoz Bonilla, J. Sanchez-Marcos, W. Xue, G. Chen, W. Zhang and X. Zhu, *ACS Macro Lett.*, 2016, **5**, 1278-1282.
29. H. Ma, R. H. Davis and C. N. Bowman, *Macromolecules*, 2000, **33** (2), 331-335.
30. H. Zhang, W. S. Trout, S. Liu, G. A. Andrade, D. A. Hudson, S. L. Scinto, K. T. Dicker, Y. Li, N. Lazouski and J. Rosenthal, *J. Am. Chem. Soc.*, 2016, **138** (18), 5978-5983.
31. J. Yuasa, A. Mitsui and T. Kawai, *Chem. Commun.*, 2011, **47** (20), 5807-5809.
32. H. J. Avens and C. N. Bowman, *J. Polym. Sci., Part A: Polym. Chem.*, 2009, **47** (22), 6083-6094.
33. J. Xu, S. Shanmugam, H. T. Duong and C. Boyer, *Polym. Chem.*, 2015, **6** (31), 5615-5624.
34. J. Qiu, T. Pintauer, S. G. Gaynor, K. Matyjaszewski, B. Charleux and J.-P. Vairon, *Macromolecules*, 2000, **33** (20), 7310-7320.
35. K. Matyjaszewski, *Current Opinion in Solid State and Materials Science*, 1996, **1** (6), 769-776.
36. K. Matyjaszewski and J. Xia, *Chem. Rev.*, 2001, **101** (9), 2921-2990.
37. X. Liu, L. Zhang, Z. Cheng and X. Zhu, *Polym. Chem.*, 2016, **7** (3), 689-700.
38. R. Francis, B. Lepoittevin, D. Taton and Y. Gnanou, *Macromolecules*, 2002, **35** (24), 9001-9008.
39. T. Higashihara, R. Faust, K. Inoue and A. Hirao, *Macromolecules*, 2008, **41** (15), 5616-5625.
40. R. N. Kwak, Yungwan and K. Matyjaszewski, *Macromolecules*, 2008, **41** (13), 4585-4596.
41. N. D. Dolinski, Z. A. Page, E. H. Discekici, D. Meis, I. H. Lee, G. R. Jones, R. Whitfield, X. Pan, B. G. McCarthy and S. Shanmugam, *J. Polym. Sci., Part A: Polym. Chem.*, 2019, **57**, 268-273.