

OPEN ACCESS


Interaction of low energy carbon ions with tungsten surface

To cite this article: G Langer *et al* 2014 *J. Phys.: Conf. Ser.* **488** 132009

View the [article online](#) for updates and enhancements.

Related content

- [Conformational changes to plasmid DNA induced by low energy carbon ions](#)
C A Hunniford, D J Timson, R J H Davies *et al.*
- [Effects of low energy carbon ions on plasmid DNA](#)
C A Hunniford, D J Timson, R J H Davies *et al.*
- [Thermal Desorption of Carbon Monoxide Adsorbed on Tungsten Surface](#)
Nobuyuki Hayashi and Kuntatsu Lyo

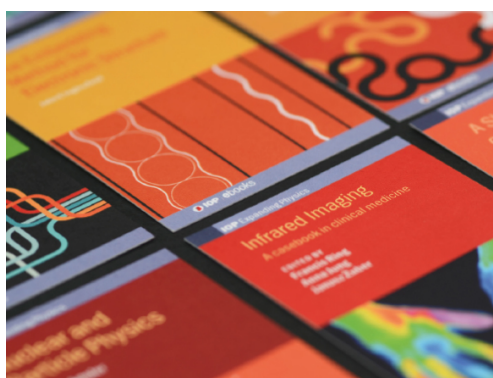

IOP | ebooks™

Bringing together innovative digital publishing with leading authors from the global scientific community.

Start exploring the collection—download the first chapter of every title for free.

Interaction of low energy carbon ions with tungsten surface

G. Langer^a, G. Erdélyi^a, A. Csik^b, D. Tskhakaya^c, D. Coster^d, and K. Tókesi^{b1}

^aUniversity of Debrecen, Department of Solid State Physics, Debrecen, Hungary, EU

^bInstitute for Nuclear Research, Hungarian Academy of Sciences (ATOMKI), Debrecen, Hungary, EU

^cInstitute for Theoretical Physics University of Innsbruck, Innsbruck, Austria, EU

^dMax-Planck-Institut für Plasmaphysik, Garching, Germany, EU

Synopsis We performed measurements using low energy carbon ions (200 eV and 1000 eV) as projectile and tungsten surface as target. The main aim of our work was to get data for the sputtering yields in this projectile and target combination. Surprisingly, instead of the weight loss of the target material, we obtained weight gain. We also observed an interesting energy dependent feature of the process.

In our work we used the experimental set up shown schematically in fig.1 [1]. Measurements were performed in the plasma chamber of a Secondary Neutral Mass Spectrometer (SNMS), (model SPECS INA-X). The sputtering ion beam was extracted from a radio-frequency CH₄ gas-plasma. The plasma was sustained at a pressure of 1×10^{-3} mbar and at an RF power of ~ 150 W. Using the mass spectrometer, we identified the main ionic species of the plasma as H⁺ and CH_x⁺ (x=0-4) ions, which are the products of the dissociation of CH₄. The predominant (80%) ion component of the plasma was the CH₃⁺ ion. The experimental sample configuration within the plasma chamber is also shown in Fig.1. A circular shielding aperture (diameter: 11 mm) was mounted in front of the plane of the sputtered tungsten plate. The sample was placed just below this aperture; the sample-plasma distance was 1.5 mm. The specimen is electrically insulated from the shielding aperture, which is at the same potential as the walls of the plasma container. When the sample is negatively biased with respect to the plasma, an ion current is extracted (~ 1 mA), which impinges at normal incidence onto the sample surface (~ 1 cm²). During the sputtering, the temperature of the sample did not exceed the temperature of 100° C. The tungsten plate was weighed on Sartorius M3P electronic microbalance before and after bombardment in order to determine the mass change. After sputtering, a weight increase was detected at both ion energies. At 200 eV for 40 minutes and at 1000 eV for 20 minutes sputter time, the weight surplus was 65 μ g and 75 μ g, respectively [2]. According to the SNMS investigations, the weight increase was caused by a gradually deposited carbon layer on the surface of tungsten plate. The carbon film was transparent (diamond like) at the ion energy of 200

eV. In contrast to this finding, at 1keV projectile energy, a graphite-like, not transparent film was observed on the tungsten surface.

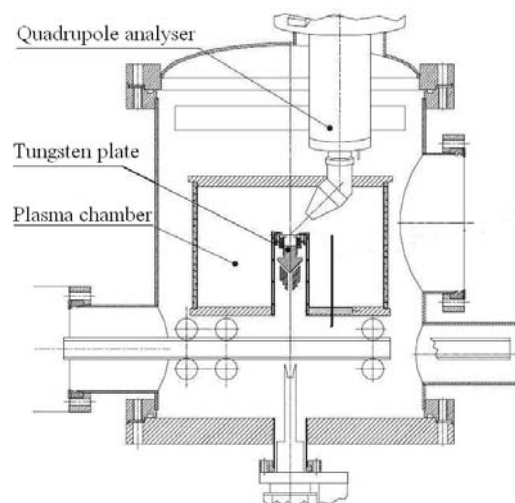


Fig.1. Schematic diagram of the experimental set up.

Acknowledgements

This work, supported by the European Communities under the contract of Association between EURATOM-HAS, was carried out within the framework of the Task Force on Integrated Tokamak Modelling of the European Fusion Development Agreement. The work was also supported by the Hungarian Scientific Research Fund OTKA No. NN103279.

References

- [1] Z. Somogyvári *et al.* 2012 *Vacuum* **86** 1979
- [2] E. Hechtel *et al* 1981 *J.Nuc. Mat.* **104** 333

E-mail: tokesi@atomki.mta.hu



Content from this work may be used under the terms of the [Creative Commons Attribution 3.0 licence](https://creativecommons.org/licenses/by/3.0/). Any further distribution of this work must maintain attribution to the author(s) and the title of the work, journal citation and DOI.