

IOP Conference Series: Materials Science and Engineering

PAPER • OPEN ACCESS

An enhanced power harvesting from woven textile using piezoelectric materials

To cite this article: N Chakhchaoui *et al* 2020 *IOP Conf. Ser.: Mater. Sci. Eng.* **827** 012046

View the [article online](#) for updates and enhancements.

An enhanced power harvesting from woven textile using piezoelectric materials

N Chakhchaoui^{1,2,6}, H Jaouani², R Farhan³, A Eddiai³, M Meddad⁴, O Cherkaoui², L Van Langenhove⁵

¹ BGIM Laboratory, Higher Normal School (ENS), Hassan II University, Casablanca, Morocco

² REMTEX Laboratory, Higher School of Textile and Clothing Industries (ESITH), Casablanca Morocco

³ Laboratory of Physics of Condensed Matter (LPMC), Faculty of Sciences Ben M'Sik Hassan II University, Casablanca, Morocco

⁴ LAS Laboratory of Setif, Mohamed el Bachir el Ibrahimi BBA University, Algeria

⁵ Ghent University, Department of Textiles, Technologiepark 907, 9052 Zwijnaarde, Belgium

⁶ Author to whom any correspondence should be addressed

nabil.chakhchaoui@esith.com

Abstract. The field of power harvesting has experienced significant growth over the past few years due to the ever-increasing desire to produce portable and wireless electronics with extended lifespans. The present work aims to introduce an approach to harvesting electrical energy from a mechanically excited piezoelectric element and investigates a power analytical model generated by a smart structure of type polyvinylidene fluoride (PVDF) that can be stuck onto fabrics and flexible substrates. Moreover, we report the effects of various substrates and investigates the sticking of these substrates on the characterization of the piezoelectric material.

Keywords: Power harvesting, Wireless electronics, Piezoelectric energy, Technical textile, PVDF

1. Introduction

Over the past decade, the number of wireless sensors and portable electronics carried by individuals had a rapid increase [1, 2]. Each of these devices is typically powered using a traditional electrochemical battery. However, the use of batteries involves many drawbacks, such as limited energy storage capability, potential damage to environment and a limited life time, which have limited further development and applications of wearable electronics. To overcome this issue, many efforts have been focused on wearable energy harvesters, allowing the conversion of ambient energy surrounding the system to a usable electrical energy [3, 4] such as the mechanical energy dissipated from human motion [5, 6], including electromagnetic [7], electrostatic [8], thermoelectric [9], and piezoelectric harvesters [10]. Compared with electromagnetic, electrostatic and thermoelectric methods, the piezoelectric approach to power harvesting provides several advantages including: higher energy density, the ability to be fabricated in custom shapes and higher flexibility of being integrated into a system.

The focus here is on piezoelectric materials, which accumulate electrical charge in response to applied mechanical stress. Representative piezoelectric materials can be categorized into piezoceramics and piezopolymers. However, PZT (lead zirconate-titanate) is a commonly used piezoelectric ceramic. On the other hand, the piezopolymer commonly used is polyvinylidene fluoride (PVDF). Compared with rigid, brittle, and heavy PZT [11,12], PVDF is particularly interesting due to its low cost, considerable



flexibility, durability, good stability and easy integration into elements such as clothes and shoes [13]. Recently, a great amount of researches have been conducted to develop simple and efficient energy harvesting devices from vibration by using piezoelectric materials based on smart textiles which harbor potential in various applications such as energy harvesting, sensing and actuation [14]. Smart Textiles are defined as textile products, such as woven, knitted or non-woven structures made from fibers, filaments or yarns, which are able to sense and respond to changes in their environment [15]. Furthermore, recent developments in the field have led to the design of a number of mechanisms that can be used for harvesting electrical energy, from a variety of textiles substrates including textile plus an interface layer such as Kapton and Alumina, and so on [16]. In addition, *Almusallam. A, et al* [17] presented an experimental study on clamping effect on the piezoelectric responses of screen-printed low temperature PZT/polymer films on flexible substrates. Later, *Almusallam. A, et al* [18] made a series of studies about the use of a flexible piezoelectric nano-composite films for kinetic energy harvesting from textiles. In this context, the study has shown a piezoelectric patch that could recharge a small device within few hours when excited by a kneepad located on the knee due to walking [19].

This paper has investigated the development of novel energy harvesting systems, which are a clean and durable solution, based on the thin film PVDF sticking on flexible substrates such as fabrics. The smart structure shows greater piezoelectric and dielectric properties compared to our previous work [19]. These properties are explored and discussed in this paper.

2. General theory of kinetic energy harvesting

2.1 Standard approach to energy harvesting

The simplest method to recover energy is to directly connect the electrical circuit to the piezoelectric elements. This device is shown in figure 1(a) where the resistance R represents the input impedance of the supplied electric circuit. In this case, the load voltage is alternative. The waveforms associated with this technique are shown in figure 1(b), and in this case, a permanent sinusoidal stress has been performed.

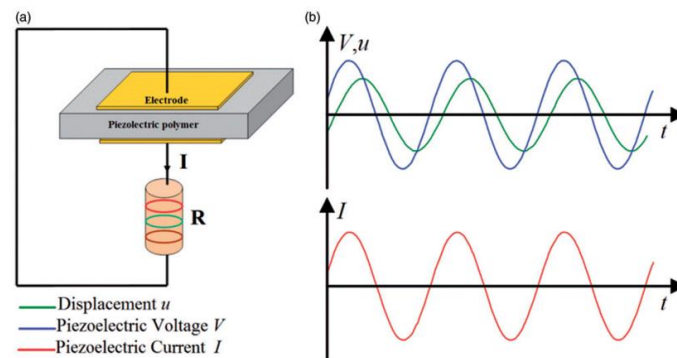


Figure 1. Standard approach Alternating Current (AC) to energy harvesting: (a) standard network and (b) standard waveforms.

2.2 Analytical and modelling of power harvesting system

As one of the important vibration-based energy harvesting methods, piezoelectric conversion has received much attention because of the simple structure of piezoelectric converter and the ease of application characteristic of piezoelectric materials. There are two types of piezoelectric effects that can be used for technological applications: the direct piezoelectric effect that describes the ability of a given material to convert mechanical strain into electricity. On the other hand, the converse effect, which is the ability to convert an applied electrical solicitation into mechanical energy.

Two equations are used to depict the piezoelectric nature of a material and they have been considered from *Jaffe and Cook* [5]. Equations (1) and (2) are defined as the piezoelectric constitutive equations:

$$S_{\alpha} = s_{\alpha\beta} \cdot T_{\beta} + d_{i\alpha} \cdot E_i \quad (1)$$

$$D_i = d_{i\alpha} \cdot T_{\alpha} + \varepsilon_{ij} \cdot E_j \quad (2)$$

$$\alpha = \beta = 1, 2, \dots, 6 \quad i, j = 1, 2$$

The first equation defines the mechanical response of the material, while the second equation defines the electrical response. Where S is the strain, T is the stress, E is the electric field, D is the electric displacement, d is the piezoelectric electromechanical coupling coefficient, s is the compliance, which relates stress and strain at constant electric field, ϵ is the dielectric permittivity, which indicates the charge stored in the capacitive element of the piezoelectric material at constant stress, and the subscripts represent the direction of each property.

$$S_1 = s_{11} \cdot T_1 + s_{12} \cdot T_2 + s_{13} \cdot T_3 + d_{31} \cdot E_3 \quad (3)$$

$$S_3 = s_{13} \cdot (T_1 + T_2) + s_{33} \cdot T_3 + d_{33} \cdot E_3 \quad (4)$$

$$D_3 = d_{31} \cdot (T_1 + T_2) + d_{33} \cdot T_3 + \epsilon_{33} \cdot E_3 \quad (5)$$

When placed on an isotropic substrate (the fabric plus interface layer), the lateral strain is the same in each direction $S_1 = S_2$ and the stress $T_1 = T_2 = T$, equation (1) can be re-written as

$$S_1 = (s_{11} + s_{12}) \cdot T_2 + s_{13} \cdot T_3 + d_{31} \cdot E_3 \quad (6)$$

Thus, the value of S_1 and S_2 must be determined as a function of T_3 using Hooke's law

$$S_1 = S_3 = \left(-\frac{\nu_{sub}}{\gamma_{sub}}\right) \cdot T_3 \quad (7)$$

Also, the mechanical compliance matrix parameters were calculated using the following equations

$$s_{11} = \frac{1}{\gamma_{piez}}; \quad s_{12} = -\frac{\nu_{piez}}{\gamma_{piez}}; \quad s_{13} = -\frac{\nu_{piez}}{\gamma_{piez}} \quad (8)$$

Relating the strain and the ratio of the generated charge to the applied force and combining with equations (4), (5) and (6) gives

$$\left(-\frac{\nu_{sub}}{\gamma_{sub}}\right) \cdot T_3 = \frac{1-\nu_{piez}}{\gamma_{piez}} \cdot T - \frac{\nu_{piez}}{\gamma_{piez}} \cdot T_3 + d_{31} \cdot E_3$$

It is possible to express the T stress as a function T_3 and E_3 , given by

$$T = \frac{\gamma_{piez}}{1-\nu_{piez}} \cdot \frac{\nu_{piez} \cdot \gamma_{sub} - \nu_{sub} \cdot \gamma_{piez}}{\gamma_{piez} \cdot \gamma_{sub}} \cdot T_3 - \frac{\gamma_{piez}}{1-\nu_{piez}} \cdot d_{31} \cdot E_3 \quad (9)$$

Hence the expression of the electric displacement D ; Substituting equation 7 into 3 and rearranging it results in

$$D_3 = d_{33} \cdot \left(\frac{-2 \cdot \gamma_{piez}}{1-\nu_{piez}} \cdot \frac{\nu_{piez} \cdot \gamma_{sub} - \nu_{sub} \cdot \gamma_{piez}}{\gamma_{piez} \cdot \gamma_{sub}} + 1\right) \cdot T_3 + \left(\epsilon_{33} - \frac{2 \cdot \gamma_{piez} \cdot \nu_{piez}^2 \cdot d_{33}^2}{1-\nu_{piez}}\right) \cdot E_3 \quad (10)$$

The current supplied in the polymer in the case of transverse mechanical stress is expressed in the form

$$I = A \cdot \frac{\partial D}{\partial t} = A \cdot \left\{ d_{33} \cdot \left(\frac{-2 \cdot \gamma_{piez}}{1-\nu_{piez}} \cdot \frac{\nu_{piez} \cdot \gamma_{sub} - \nu_{sub} \cdot \gamma_{piez}}{\gamma_{piez} \cdot \gamma_{sub}} + 1\right) \cdot \frac{\partial T_3}{\partial t} + \left(\epsilon_{33} - \frac{2 \cdot \gamma_{piez} \cdot \nu_{piez}^2 \cdot d_{33}^2}{1-\nu_{piez}}\right) \cdot \frac{\partial E_3}{\partial t} \right\} \quad (11)$$

A is the active surface of the polymer.

$\frac{\partial T_3}{\partial t}$ and $\frac{\partial E_3}{\partial t}$ are the time derivatives of the electrical field and strain, respectively.

$$\alpha = d_{33} \cdot \left(\frac{-2 \cdot \gamma_{piez}}{1 - \nu_{piez}} \cdot \frac{\nu_{piez} \cdot \gamma_{sub} - \nu_{sub} \cdot \gamma_{piez}}{\gamma_{piez} \cdot \gamma_{sub}} + 1 \right)$$

$$\beta = \varepsilon_{33} - \frac{2 \cdot \gamma_{piez} \cdot \nu_{piez}^2 \cdot d_{33}^2}{1 - \nu_{piez}}$$

The electric field E is equal to the alternating electric field E_R across the resistor: $E = E_R$. The voltage output of the system across the load resistance is defined by the term figure 1

$$E_R = -\frac{R \cdot I}{t_p}$$

Where I is the current which crosses the load R , e is the thickness of the polymer film. So:

$$E = E_R = -\frac{R \cdot I}{t_p} \quad (12)$$

The general expression the current I is

$$I = A \cdot \alpha \cdot \frac{\partial T_3}{\partial t} - \frac{A \cdot \beta \cdot R}{t_p} \cdot \frac{\partial I}{\partial t} \quad (13)$$

In the frequency domain, the current is expressed in the form

$$I = j \cdot \omega \cdot A \cdot \left(\alpha \cdot T_3 - \frac{\beta \cdot R}{t_p} \cdot I \right) \quad (14)$$

$$I = \frac{j \cdot \omega \cdot A \cdot \alpha \cdot T_3}{1 + j \cdot \omega \cdot A \cdot \frac{\beta \cdot R}{t_p}} \quad (15)$$

In the case of a resistive load connected in series with the piezoelectric polymer working in piezoelectric mode, the objective is to take the expression of the power dissipated in the resistive load, on the basis of the equation that links the power, current, and load $P = R \cdot I^2$.

The power dissipated in the resistor R is expressed by the equation

$$P = \frac{R \cdot (\omega \cdot A \cdot \alpha \cdot T_3)^2}{1 + \left(\omega \cdot A \cdot \frac{\beta \cdot R}{t_p} \right)^2} \quad (16)$$

3. Simulation results and discussion

3.1 Flexible textile substrate

A smart structure of type PVDF was stuck on three different substrates, Kermel and thick woven fabric (Polyester 65%–Cotton 35%) and Cotton 100%. The Kapton substrate was used commonly as reference substrate material for investigating the dielectric and piezoelectric properties of the composite. However, this material is used as a substrate for flexible electronic devices. The PVDF polymer layer was sandwiched between two silver electrodes that were used to enable film poling and perform study of the different parameters. The investigated textiles substrates are polyester-cotton, cotton, and polyamide-imide (Kermel) were plain weave, 65% polyester with a warp and weft.

3.2 Design mode study

This section focuses on the effect of substrates parameters textiles in order to increase the power recovered by the PVDF polymer film. The optimization of these substrates is implemented in order to ensure good performance of this electroactive polymer for energy harvesting.

The theoretical results are presented with an analysis of the 33-mode for the piezoelectric generator to verify the validity of the model developed for application in textile.

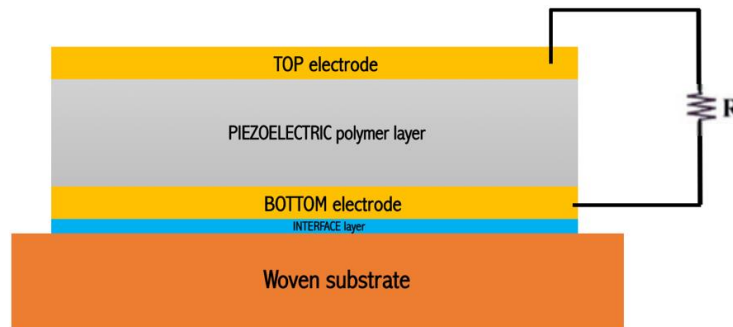


Figure 2. The smart structure stuck on woven fabric.

3.3 Effect of substrats on energy harvesting under compressive force

Figure 3 shows the theoretical results obtained with piezoelectric polymer PVDF film stucked on substrats (cotton; polyster/cotton; kermel) having a thickness of 500 μm , the frequency 6 Hz, and the applied force 80 N. The theoretical results show that the harvested power increases while increasing the resistance load, up to an optimal value in which the power decreases.

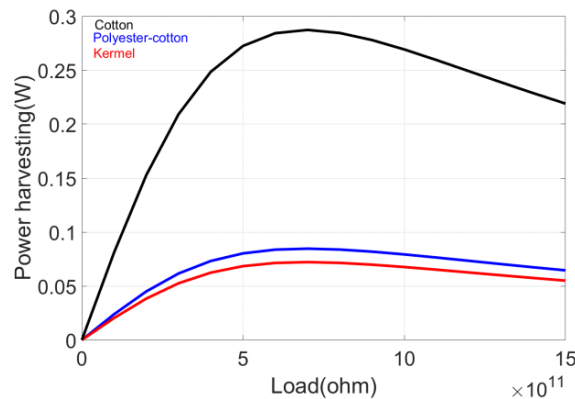


Figure 3. The power harvested as a function of resistive load for cotton, polyester-cotton and Kermel substrates when applying force $F=80\text{N}$ at 6Hz.

4. Conclusion

Textile substrate bears one of the most promising form factors for future electronic applications due to its wide degree of freedom in shapes with flexible and stretchable characteristics. This work investigates the energy harvesting performance of PVDF polymer material stuck on woven-fabric substrates. Clearly the energy harvesting performance is fundamentally linked to the piezoelectric properties of the stuck film. The theoretical investigations confirmed an increase on the power harvesting values by 258mW, 96mW and 95mW for the cotton, Polyester-cotton and kermel substrates, respectively.

References

- [1] Patel S, Park H, Bonato P, Chan L, Rodgers M A 2012 review of wearable sensors and systems with application in rehabilitation *Journal of Neuroeng. Rehabil* **9** 1–17
- [2] Meddad M, Eddiai A, Cherif A, Hajjaji A and Boughaleb Y 2014 Model of piezoelectric self-powered supply for wearable devices *Superlattices and Microstructures* **71** 105-116
- [3] Park J, Lee S, and Kwak B M 2012 Design optimization of piezoelectric energy harvester subject to tip excitation *Journal of Mechanical Science and Technology* **26** 137-143
- [4] Priya S 2007 Advances in energy harvesting using low profile piezoelectric transducers *Journal of electroceramics* **19** 167-184
- [5] Starner T 1996 Human-powered wearable computing *IBM systems Journal* **35** 618-629
- [6] Silva H R, Afonso J A, Morim P C, Oliveira P M, Correia J H and Rocha L A 2007 Wireless

- hydrotherapy smart-suit network for posture monitoring in 2007 IEEE International Symposium on Industrial Electronics (pp. 2713-2717) IEEE
- [7] Saha C R, O'donnell T, Wang N and McCloskey P 2008 Electromagnetic generator for harvesting energy from human motion *Sensors and Actuators A: Physical* **147** 248-253
- [8] Kornbluh R D, Pelrine R, Pei Q, Heydt R, Stanford S, Oh S and Eckerle J 2002, July Electroelastomers: applications of dielectric elastomer transducers for actuation, generation, and smart structures *Smart Structures and Materials* **4698** 254-270
- [9] Ramadass Y K and Chandrakasan A P 2010 A battery-less thermoelectric energy harvesting interface circuit with 35 mV startup voltage *IEEE Journal of Solid-State Circuits* **46** 333-41
- [10] Pozzi M and Zhu M 2012 Characterization of a rotary piezoelectric energy harvester based on plucking excitation for knee-joint wearable applications *Smart Materials and Structures* **21** 055004
- [11] Shenck N S and Paradiso J A 2001 Energy scavenging with shoe-mounted piezoelectrics *IEEE micro* 30-42
- [12] Almusallam A, Yang K, Zhu D, Torah R N, Komolafe A, Tudor and Beeby S P 2015 Clamping effect on the piezoelectric responses of screen-printed low temperature PZT/Polymer films on flexible substrates *Smart Materials and Structures* **24** 115030
- [13] Kymissis, J, Kendall C, Paradiso J and Gershenfeld N 1998, October Parasitic power harvesting in shoes In *Digest of Papers Second International Symposium on Wearable Computers (Cat. No. 98EX215)* 132-139 IEEE
- [14] Tognetti A, Lorussi F, Bartalesi R, Quaglini S, Tesconi M, Zupone G, de Rossi D 2005 Wearable kinesthetic system for capturing and classifying upper limb gesture in post-stroke rehabilitation *J. NeuroEng. Rehabil.* **2** 1-16
- [15] Ma R, Lee J, Choi D, Moon H and Baik S 2014 Knitted fabrics made from highly conductive stretchable fibers *Nano letters* **14** 1944-1951
- [16] R N Torah S P 2004 Experimental investigation into the effect of substrate clamping on the piezoelectric behaviour of thick-film PZT elements *physics d applied physics* **37** 1074-1078
- [17] Almusallam A, Yang K, Zhu D, Torah R N, Komolafe A, Tudor J and Beeby S P 2015 Clamping effect on the piezoelectric responses of screen-printed low temperature PZT/Polymer films on flexible substrates *Smart Materials and Structures* **24** 115030
- [18] Almusallam A, Luo Z, Komolafe A, Yang K, Robinson A, Torah R and Beeby S 2017 Flexible piezoelectric nano-composite films for kinetic energy harvesting from textiles *Nano Energy* **33** 146-156
- [19] Chakhchaoui N, Ennamiri H, Hajjaji A, Eddiai A, Meddad M and Boughaleb Y 2017 Theoretical modeling of piezoelectric energy harvesting in the system using technical textile as a support *Polymers for Advanced Technologies* **28** 1170-1178