

Accepted Article

Title: Metal-organic Framework-Activated Carbon Composite Materials for the Removal of Ammonia from Contaminated Airstreams.

Authors: Lauren Nicole McHugh, Angela Terracina, Paul Stewart Wheatley, Gianpiero Buscarino, Martin William Smith, and Russell Edward Morris

This manuscript has been accepted after peer review and appears as an Accepted Article online prior to editing, proofing, and formal publication of the final Version of Record (VoR). This work is currently citable by using the Digital Object Identifier (DOI) given below. The VoR will be published online in Early View as soon as possible and may be different to this Accepted Article as a result of editing. Readers should obtain the VoR from the journal website shown below when it is published to ensure accuracy of information. The authors are responsible for the content of this Accepted Article.

To be cited as: *Angew. Chem. Int. Ed.* 10.1002/anie.201905779
Angew. Chem. 10.1002/ange.201905779

Link to VoR: <http://dx.doi.org/10.1002/anie.201905779>
<http://dx.doi.org/10.1002/ange.201905779>

COMMUNICATION

Metal-organic Framework-Activated Carbon Composite Materials for the Removal of Ammonia from Contaminated Airstreams

Lauren McHugh,^[a] Angela Terracina,^[b] Paul Wheatley,^[a] Gianpiero Buscarino,^[b] Martin Smith,^[c] and Russell Morris^[a]

Abstract: Metal-organic frameworks (MOFs) are a class of porous materials that show promise in the removal of Toxic Industrial Chemicals (TICs) from contaminated airstreams, though their development for this application has so far been hindered by issues of water stability and the wide availability and low cost of traditionally used activated carbons. Here a series of three MOF-activated carbon composite materials with different MOF to carbon ratios are prepared by growing STAM-17-OEt crystals inside the commercially available BPL activated carbon. The composite materials display excellent water stability and increased uptake of ammonia gas when compared to unimpregnated carbon. Such properties make these composites very promising in the fields of air purification and personal protective equipment.


Metal-organic frameworks (MOFs) are a class of porous, microcrystalline materials that over the last few years have shown potential as adsorbent materials for applications ranging from drug delivery,^[1] to gas separation and adsorption.^[2] One area where MOFs are of interest is in the removal of toxic industrial chemicals (TICs) such as ammonia and hydrogen sulfide from airstreams,^[3,4] and research is currently underway into the possibility of incorporating MOFs into personal protective equipment, such as respirator canisters.^[5]

One of the main issues regarding the potential use of MOFs in personal protective equipment is the hydrolytic stability of the frameworks (due to exposure to the humidity always present in breathable air).^[6] Another key problem is the physical form of MOFs in that they typically form fine powders, which a wearer cannot breathe through. This may be addressed by adopting form-altering techniques such as pelletization,^[7] though this leads to increased synthetic and engineering costs compared to cheaper, currently used adsorptive materials such as activated carbon. One compromise may be to combine a MOF and activated carbon into a composite material that exhibits positive characteristics from both materials. The growth of MOFs within activated carbons in order to improve the mechanostability of

MOFs was reported by Casco,^[8] and was further developed by Aurbach to impart electrical conductivity into an otherwise non-conducting MOF.^[9] MOFs are chemically good choices for the adsorption of smaller molecules such as ammonia and hydrogen sulfide, due to the strong and selective interactions formed between the framework and the target chemicals. Activated carbons conversely excel in the physisorption of larger molecules such as nerve agents due to their greater porosity and larger pore diameters.^[10] By tuning the weight proportion of MOF incorporated into the materials, it is reasonable to suggest that the composites may be tailored to remove specific gases or a broader range of contaminants.

We recently reported the structure of STAM-17-OEt and highlighted its exceptional hydrolytic stability and ability to remove ammonia from both dry and humid airstreams.^[11] In this study, we report the synthesis of three novel MOF-carbon composite materials containing STAM-17-OEt and BPL activated carbon. BPL is an unimpregnated coal-based carbon, which is representative of activated carbons that have been used to prepare impregnated carbons such as those often used in respiratory protection.

As shown schematically in Scheme 1, the synthesis of MOF-activated carbon composite materials is an in-situ process. This procedure leads to black granular materials that appear similar to unimpregnated carbon samples to the naked eye.

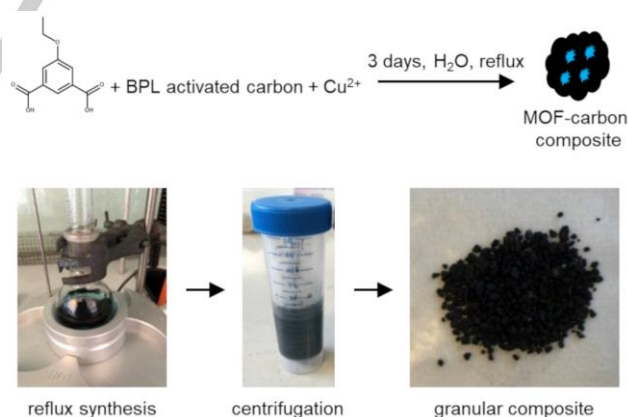

Scheme 1. Synthesis of STAM-17-OEt@BPL composite materials.

The granular form of the STAM-17-OEt@BPL composites addresses a key issue in the preparation of functional filtration materials, where typically unusable powdered MOF samples have been manufactured into a more useable form by incorporation into a granular activated carbon.

Three weight percentages of STAM-17-OEt@BPL are presented here, with 77%, 51% and 39% w/w MOF loading and henceforth

- [a] Miss. L. N. McHugh, Dr. P. S. Wheatley, Prof. R. E. Morris
School of Chemistry
University of St Andrews
St Andrews, KY16 9ST, UK
E-mail: lm83@st-andrews.ac.uk
- [b] Miss. A. Terracina, Dr. G. Buscarino
Dipartimento di Fisica e Chimica
Università degli Studi di Palermo
Palermo, 3690123, Italy
- [c] Mr. M. W. Smith
CBR Division
Dstl Porton Down
Salisbury, SP4 0JQ, UK

Supporting information for this article is given via a link at the end of the document.

COMMUNICATION

named STAM-17-OEt@BPL_1, STAM-17-OEt@BPL_2 and STAM-17-OEt@BPL_3 respectively. The loadings are expressed in weight percentage of MOF, based on an assumed 100% yield of STAM-17-OEt, for example, where 77% loading signifies that each gram of carbon has 0.77 g of MOF added.

Powder X-ray diffraction (PXRD) (Figure 1) confirms the presence of the parent MOF (STAM-17-OEt) in the composite materials, since some of the crystallinity associated with STAM-17-OEt may be observed along with amorphous character arising from the carbon. MOF may be observed at all three MOF loadings, where the sample containing the highest weight percentage of MOF, i.e. STAM-17-OEt@BPL_1, displays the greatest intensity. STAM-17-OEt@BPL_3 shows considerably less intensity due to the significantly lower quantity of MOF incorporation.

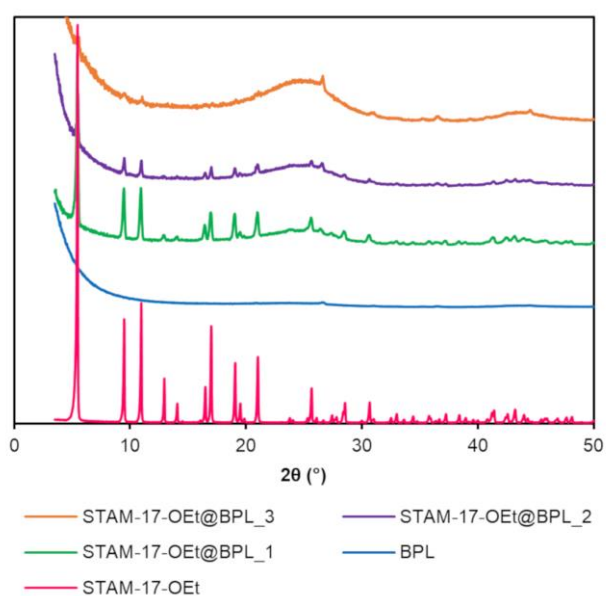


Figure 1. Powder X-ray diffraction patterns of the original MOF, unimpregnated BPL activated carbon and the three composites with varying weight percentages of MOF incorporation.

Scanning electron microscopy (SEM) images (Figure 2a,b) display the overall morphology of the unimpregnated BPL carbon and STAM-17-OEt respectively. The large voids of $\sim 50 \mu\text{m}$ in BPL carbon are clearly visible and allow synthesis of smaller MOF crystals within the carbon. STAM-17-OEt crystals have hexagonal morphology and are usually observed as stacked hexagons with typically $\sim 20 \mu\text{m}$ diameter.^[11] SEM images and associated copper elemental mapping images of STAM-17-OEt@BPL_1 (Figure 2c,d), STAM-17-OEt@BPL_2 (Figure 2e,f) and STAM-17-OEt@BPL_3 (Figure 2g,h) verify the fairly even distribution of copper throughout the carbon. Some areas of more concentrated copper are visible on the surface of the materials, and this is especially true of the samples with higher MOF loading, suggesting that a small amount of STAM-17-OEt has crystallised on the outside of the carbon particles. No discrete MOF particles

were observed however, further signifying that STAM-17-OEt is largely confined inside the carbon particles.

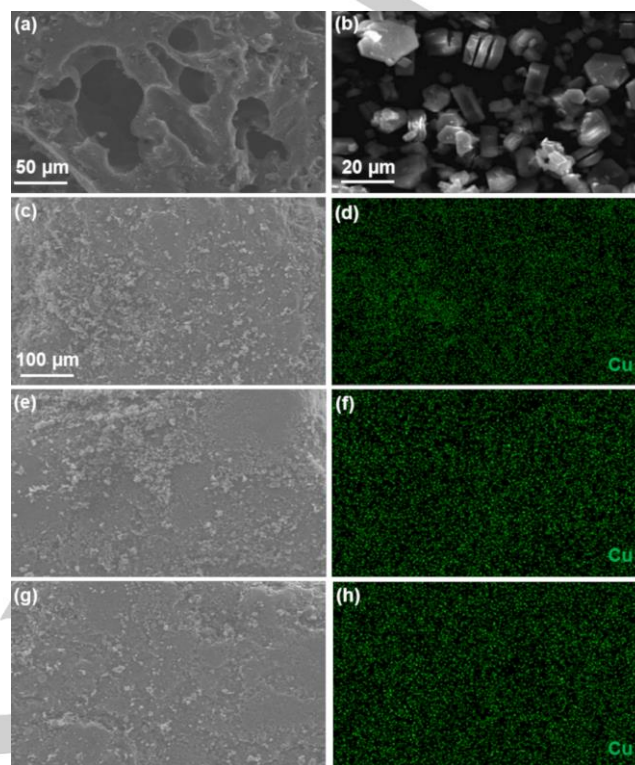


Figure 2. SEM images of: a,b) BPL activated carbon and STAM-17-OEt respectively; SEM image and copper elemental mapping image of: c,d) STAM-17-OEt@BPL_1; e-f) STAM-17-OEt@BPL_2; g,h) STAM-17-OEt@BPL_3.

Nitrogen BET (Brunauer Emmett-Teller) adsorption measurements were performed to investigate the effect of MOF incorporation on carbon porosity. BPL activated carbon has a wide pore size distribution, with both micro and mesopores and a measured surface area of $1209 \text{ m}^2/\text{g}$, which is comparable to the literature value of $1200 \text{ m}^2/\text{g}$.^[12] STAM-17-OEt, like other MOFs, is microporous, though has a surprisingly low surface area of $58 \text{ m}^2/\text{g}$.^[11] The low porosity in STAM-17-OEt is due to its switchable structure, where upon activation, the pores in STAM-17-OEt become constricted by the change in the coordination environment of the copper paddlewheels. This constriction consequently impacts the porosity, though the low surface area observed for STAM-17-OEt is not representative of the material's overall gas adsorption capability. A significant drop in the porosity of the carbon upon incorporation of the MOF would provide further evidence that STAM-17-OEt is inside the carbon, due to partial pore-blocking by STAM-17-OEt crystals. The surface areas of the composites do fall in-between those of the MOF and carbon alone, where the higher the MOF content, the lower the surface area (Table 1). The greatest loss of porosity is observed in the highest loading sample: STAM-17-OEt@BPL_1, with a percentage decrease of 90% compared to unimpregnated BPL activated carbon.

COMMUNICATION


Table 1. BET surface areas of STAM-17-OEt, BPL activated carbon and the three STAM-17-OEt@BPL composites.

Material	BET Surface Area [m ² /g]
STAM-17-OEt	58(1)
STAM-17-OEt@BPL_1	116(1)
STAM-17-OEt@BPL_2	188(2)
STAM-17-OEt@BPL_3	323(2)
BPL activated carbon	1209(7)

Dynamic vapour sorption (DVS) studies using either cyclohexane or water vapours were performed on the materials. Cyclohexane is known to adsorb on the carbon but not the MOF (due to its relatively small pore size) and while water vapour adsorbs on both, the resulting isotherms are very different in shape. In either case, pre-activated samples were exposed to increasing levels of relative pressure and the associated uptake was measured at each point. Comparison of the adsorption branches in the water isotherms (Figure 3a) shows that BPL, STAM-17-OEt and a physical mixture of the two components equivalent to the highest composite carbon:MOF ratio of 1.00:0.77 weighted average all show a similar mass uptake (ca. 15% w/w) at approximately 55% relative humidity (RH). A lower water uptake of ~12% for STAM-17-OEt@BPL_1 is observed at the same level of RH, suggesting that the MOF is 'inside' the composite and therefore the pores, rather than outside as seen in the physical mixture. The shape of the STAM-17-OEt@BPL_1 isotherm is closer to BPL than STAM-17-OEt, though the total water uptake after exposure to 95% RH is closer to that of STAM-17-OEt, showing that the composites show adsorption characteristics arising from both materials.

Adsorption isotherms of cyclohexane are shown in Figure 3b. This molecule has been used as a model physisorbed chemical which is often used to assess the performance of respirator canisters.^[13] It has an atomic radius of ~5.8 Å,^[14] and the microporous nature of STAM-17-OEt prevents significant uptake of cyclohexane. The abundance of larger micro- and mesopores found in BPL activated carbon however, leads to a much greater uptake than in the MOF. The isotherms show that in the composite materials some of the carbon is still accessible to cyclohexane, even at the highest MOF loading in STAM-17-OEt@BPL_1, showing that the transport pores are not simply being 'plugged' with MOF.

A water adsorption-desorption cycling experiment was employed to investigate hydrolytic stability, where a pre-activated sample was exposed to 90% RH in a series of 8 hour cycles.^[15] The maximum water uptake (Figure 3c) remains consistent throughout the cycling experiments, suggesting that the composite is stable even in very harsh conditions. Such hydrolytic stability is undoubtedly imperative in this context due to the moisture always present in breathable air.

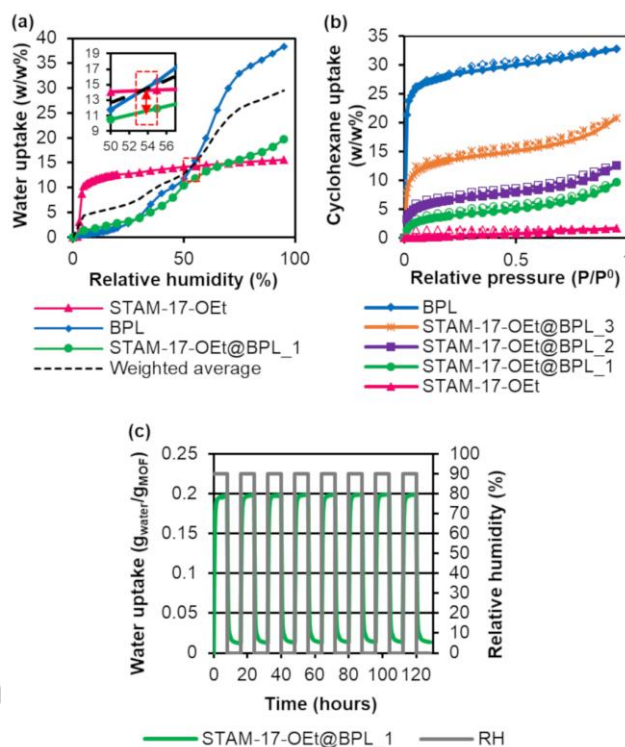**Figure 3.** a) Adsorption branches of water isotherms displaying the shape difference and decrease in water uptake in the isotherm of STAM-17-OEt@BPL_1; b) Cyclohexane isotherms of composites; c) Water sorption-desorption cycling plot of STAM-17-OEt@BPL_1.

In order to investigate the TIC gas adsorption capacity of the materials, micro breakthrough experiments were undertaken, using ammonia as the challenge gas. The resulting micro breakthrough curves (Figure 4a) show that BPL carbon alone is fairly ineffective in the removal of ammonia – with an ammonia uptake percentage of 0.43% based on sample weight. STAM-17-OEt performs significantly better, adsorbing 4.33% based on the weight of sample. The highest loading MOF-carbon sample STAM-17-OEt@BPL_1 adsorbs 1.78% based on the weight of sample, which is almost halfway between the values for unimpregnated BPL carbon and STAM-17-OEt. The trend across the series may be observed in Figure 4b, where increasing MOF loading in the composites leads to an overall increase in the uptake of ammonia. Comparison of the ammonia uptakes with the loadings of MOF on the composites suggest that ca. 55-60% of the MOF is available for ammonia removal. This indicates that some of the MOF is either not accessible to the ammonia, or becomes inaccessible as a result of the ongoing reaction between ammonia and MOF.

Activated carbon has low effectiveness in removing smaller molecules such as ammonia from airstreams, as it lacks the strong and selective interactions formed between the metals in MOFs and the gases themselves. STAM-17-OEt forms strong and favourable interactions and this makes it much better for the adsorption of gases such as ammonia. This is in contrast to what was observed in cyclohexane adsorption, where higher MOF

COMMUNICATION

loading leads to a decrease in cyclohexane uptake. This relationship leads to the postulation that by controlling the amount of MOF in the pores, we can tailor the performance of the composites accordingly.

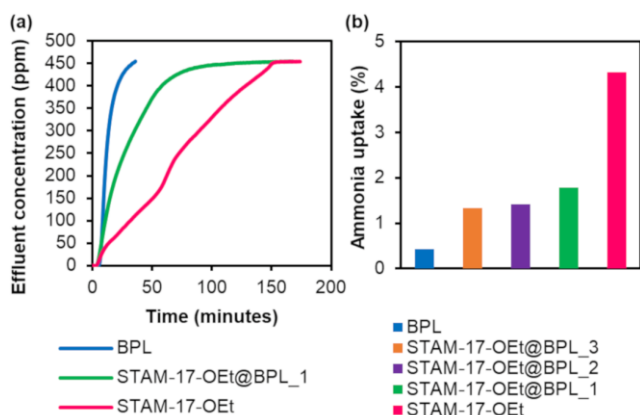


Figure 4. a) Ammonia micro breakthrough curves of BPL activated carbon, STAM-17-OEt and STAM-17-OEt@BPL₁; b) Ammonia uptake across the STAM-17-OEt@BPL series.

Electron paramagnetic resonance (EPR) spectra of activated STAM-17-OEt and the STAM-17-OEt@BPL materials were acquired at $T = 77\text{ K}$ and 300 K . The spectra were normalized by all instrumental parameters and the estimated mass of STAM-17-OEt present in each sample (Figure 5a,b) and normalized by the amplitude of the main peak (Figure 5c,d). The EPR spectra of activated STAM-17-OEt at 77 K (Figure 5a,c), show signals at 25 mT , 480 mT and 600 mT due to a triplet centre arising from the exchange coupling between the two spins ($S = 1/2$) from Cu^{2+} ions within the paddle-wheel. The signal at 330 mT is from Cu^{2+} monomers, which are defects formed during synthesis and the large and unresolved signal observed at 300 K (Figure 5b,d) applies to the triplet centres. The appearance of a single symmetric line for such $S = 1$ centres, rather than the expected multi peak resonance, is due to the exchange interaction between near magnetic paddle-wheels. The strength of this interaction intensifies with increasing temperature as a consequence of the population of the $S = 1$ (triplet) state and it is significant at room temperature. The EPR spectra of STAM-17-OEt@BPL samples are very different. The peaks corresponding to the triplet centres in STAM-17-OEt are no longer present and only a single resonance at both temperatures with similar features is observed. This narrower resonance, centred at $\sim 340\text{ mT}$, shows a fine structure comprising a multiplet of four lines, originating from the hyperfine interaction between the electron spin $S = 1/2$ of the Cu^{2+} ion and its nuclear spin $I_{\text{Cu}} = 3/2$. This multiplet was also present in pristine STAM-17-OEt, but was much less evident. Significant changes were also observed in the EPR spectra of a similar MOF in another hybrid system, where HKUST-1 was confined within mesostructured silica.^[16] The changes in the spectra were attributed to the significantly reduced number of neighbouring paramagnetic centres due to the typically widely spaced pores. The almost total disappearance of the resonances concerning the

triplet centres at 77 K suggests a stronger change in the electronic environment of the paddle-wheels with respect to the cited case and it appears that the signals observed at both 77 and 300 K in the STAM-17-OEt@BPL spectra arise from decoupled copper ions. A similar change in the magnetic properties of MOFs upon incorporation into an activated carbon matrix was observed for HKUST-1.^[9] The reasons of this apparent decoupling are still unclear, but appear to be closely linked to the nature of MOF growth inside a porous carbon matrix.

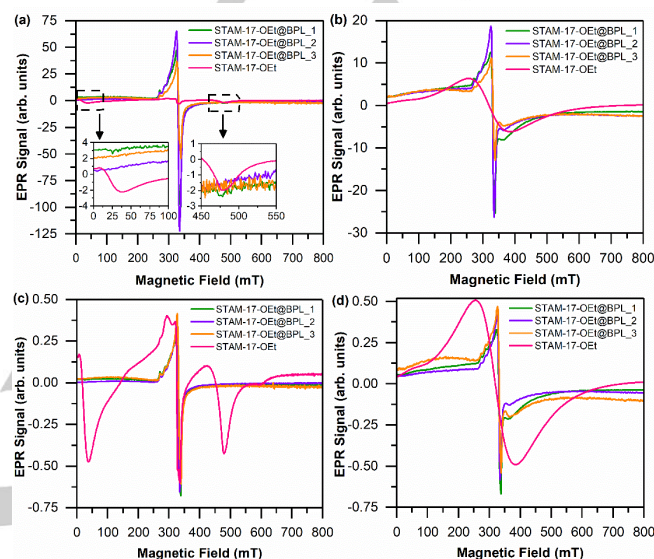


Figure 5. a,b) EPR spectra normalized by the estimated mass of STAM-17-OEt in each sample at 77 K and 300 K respectively; c,d) EPR spectra normalized by the peak-to-peak amplitude of the central resonance line at 77 K and 300 K respectively.

In conclusion, this manuscript shows the synthesis of MOF-carbon composite materials, where STAM-17-OEt has been incorporated into the commercially available BPL activated carbon at a series of loadings. SEM, water adsorption, cyclohexane uptake and EPR suggest that the MOF is formed within the pores of BPL carbon and water adsorption-desorption cycling highlights the hydrolytic stability of the composites. Microbreakthrough experiments show that the MOF-carbon composite materials increase the quantities of ammonia removed from contaminated airstreams compared with the carbon, and cyclohexane uptake shows that the composites can adsorb significantly more cyclohexane than the MOF alone. The granular form of the STAM-17-OEt@BPL composites also overcomes a major hurdle in the engineering of materials used in personal protective equipment, whereby a powdered MOF has been manufactured into a form that can potentially be used inside a filter. These findings suggest that MOF-carbon composites are exciting materials for use in air purification and by altering the loading of MOF within the composites, the materials may be tailored to remove a broader range of contaminants than the individual components alone.

COMMUNICATION

Acknowledgements

L.N.M and R.E.M wish to acknowledge the financial support from the EPSRC industrial CASE award (grant EP/N50936X/1).

A.T and G.B would like to thank the financial support from the Fondo per il finanziamento delle attività base di ricerca (grant PJ-RIC-FFABR_2017).

Keywords: porous materials • metal-organic frameworks • activated carbons • gas adsorption • water stability


- [1] a) A. C. McKinlay, R. E. Morris, P. Horcajada, G. Férey, R. Gref, P. Couvreur, C. Serre, *Angew. Chem. Int. Ed.* 2010, 49, 6260; b) I. A. Lázaro, R. S. Forgan, *Coord. Chem. Rev.* 2018, 380, 230
- [2] a) R-B. Lin, S. Xiang, H. Xing, W. Zhou, B. Chen, *Coord. Chem. Rev.* 2019, 378, 87; b) K. Sumida, D. L. Rogov, J. A. Mason, T. M. McDonald, E. D. Bloch, Z. R. Herm, T-H. Bae, J. R. Long, *Chem. Rev.* 2012, 112, 724.
- [3] a) G. W. Peterson, G. W. Wagner, A. Balboa, J. Mahle, T. Sewell, C. J. Karwacki, *J. Phys. Chem. C.* 2009, 113, 13906; b) E. Barea, C. Montoro, J. A. R. Navarro, *Chem. Soc. Rev.* 2014, 43, 5149.
- [4] a) L. Hamon, C. Serre, T. Devic, T. Loiseau, F. Millange, G. Férey, G. De Weireld, *J. Am. Chem. Soc.*, 2009, 131, 8775; b) J. Antonio Zárate, E. Sánchez-González, T. Jurado-Vázquez, A. Gutiérrez-Alejandre, E. González-Zamora, I. Castillo, G. Maurin, I. A. Ibarra, *Chem. Comm.* 2019, 55, 3049.
- [5] M. Jacoby, *Chem. Eng. News.* 2014, 92, 34-38.
- [6] a) N C. Burtch, H. Jasuja, K. S. Walton, *Chem. Rev.*, 2014, 114, 10575; b) M. Todaro, G. Buscarino, L. Sciortino, A. Alessi, F. Messina, M. Taddei, M. Ranocchiarri, M. Cannas, F. M. Gelardi, *J. Phys. Chem. C.*, 2016, 120, 12879.
- [7] S. Hindocha, S. Poulston, *Faraday Discuss.*, 2017, 201, 113.
- [8] M. E. Casco, J. Fernández-Catalá, M. Martínez-Escandell, F. Rodríguez-Reinoso, E. V. Ramos-Fernández, J. Silvestre-Albero, *Chem. Comm.*, 2015, 51, 14191.
- [9] O. Fleker, A. Borenstein, R. Lavi, L. Benisvy, S. Ruthstein, D. Aurbach, *Langmuir*, 2016, 32, 4935.
- [10] a) R. Osovsky, D. Kaplan, I. Nir, H. Rotter, S. Elisha, I. Columbus, *Environ. Sci. Technol.* 2014, 48, 10912; b) D. Kaplan, L. Shmueli, I. Nir, D. Waysbort, I. Columbus, *Clean*, 2007, 35, 172.
- [11] L. N. McHugh, M. J. McPherson, L. J. McCormick, S. A. Morris, P. S. Wheatley, S. J. Teat, D. McKay, D. M. Dawson, C. E. F. Sansome, S. E. Ashbrook, C. A. Stone, M. W. Smith, R. E. Morris, *Nat. Chem.*, 2018, 10, 1096.
- [12] B. P. Russell, M. D. Levan, *Carbon*, 1994, 32, 845.
- [13] CEN European Normalization Committee, European Norm EN 14387, Respiratory Protective device - gas filters and combined filters - Requirements, testing, marking (BSI British standards, London 2004).
- [14] F. D. Magalhães, R. L. Laurence, W. C. Conner, *J. Phys. Chem. B.*, 1998, 102, 2317.
- [15] J. R. Álvarez, E. Sánchez-González, E. Pérez, E. Schneider-Revueltas, A. Martínez, A. Tejeda-Cruz, A. Islas-Jácome, E. González-Zamora, I. A. Ibarra, *Dalton Trans.* 2017, 46, 9192.
- [16] M. Mazaj, T. Čendak, G. Buscarino, M. Todaro, N. Zabukovec Logar, *J. Mat. Chem. A.*, 2017, 5, 22305.

COMMUNICATION

Entry for the Table of Contents

COMMUNICATION

A new series of MOF-activated carbon composite materials are synthesised, using the copper MOF: STAM-17-OEt and commercially available BPL activated carbon. STAM-17-OEt is grown inside BPL carbon at three loadings to provide a series of granular materials that display excellent gas adsorption properties and water stability.

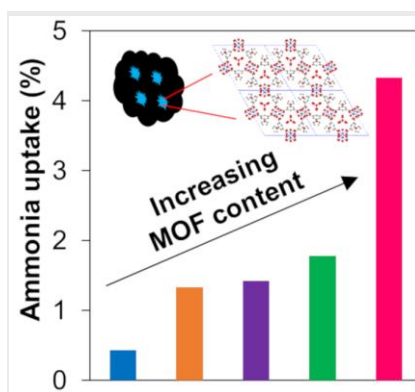

Lauren McHugh*, Angela Terracina,
Paul Wheatley, Gianpiero Buscarino,
Martin Smith, Russell Morris

Page No. – Page No.

**Metal-organic Framework-Activated
Carbon Composite Materials for the
Removal of Ammonia from
Contaminated Airstreams**

Accepted Manuscript