

MATHEMATICAL MODELING OF LEACHING PROCESS OF RED MUD IN ORDER TO OBTAIN THE KINETICS PARAMETERS

E. M. Magalhães,
K. L. M. dos Passos,
B. M. Viegas,
E. N. Macêdo,
and J. A. S. Souza

Universidade Federal do Pará
Faculdade de Engenharia Química
Bairro Guamá CP. 19011, Belém, Pará, Brasil
magalhaes@ufpa.br

Received: September 08, 2015

Revised: October 08, 2015

Accepted: November 09, 2015

ABSTRACT

The use of the waste of the Bayer process, red mud, is due to its chemical and mineralogical composition that shows a material rich in oxides of iron, titanium and aluminum. Some studies conducted show that this waste can be applied as a source of alternative raw material for concentration and subsequent recovery of titanium compounds from an iron leaching process, which is present in higher amounts, about 30% by weight. To obtain a greater understanding about the leaching kinetics, the information of the kinetic data of this process is very important. In this context, the main objective of this work is the development of a mathematical model that is able to fit the experimental data (conversion / extraction iron, titanium and aluminum) of the leaching process by which is possible to obtain the main kinetic parameters such as the activation energy and the velocity of chemical reactions as well as the controlling step of the process. The development of the mathematical model was based on the model of core decreasing. The obtained model system of ordinary differential equations was able to fit the experimental data obtained from the leaching process, enabling the determination of the controlling step, the rate constants and the activation energies of the leaching process.

Keywords: red mud, kinetics parameters, leaching

NOMENCLATURE

a_p	Is the area of a particle of red mud, m
b	Is the coefficient stoichiometric
d	Is the coefficient stoichiometric
C_A	Is the concentration of A, mol/liter
D_{ef}	Effective diffusion coefficient, $m^2 \cdot s^{-1}$
K_m	Coefficient of mass transfer, $m \cdot s^{-1}$
N_A	The flow of the reagent in the liquid film, $mol/(m^2 \cdot s)$
N_{B0}	The initial moles of iron
N_{C0}	The initial moles of titanium
N_{D0}	The initial moles of aluminum
q_A	The reaction rate, mol/s
R	Radius of a sphere, m
R_T	The total resistance based on the resistance of the sum in the liquid film, the diffusion process resistance and resistance to chemical reaction
r_c	Core radius unreacted, m.
r_B	Particle radius B (Fe_2O_3), m
r_C	Particle radius C (TiO_2), m
r_D	Particle radius D (Al_2O_3), m
r_p	Particle radius, m
S_i	Sum of areas, m^2
$C_{A\infty}$	Is the concentration of A away from of the liquid film, mol/L.
C_A	Is the concentration of A on the particle surface, mol/L.
S_B	Surface area of B, m^2
S_C	Surface area of C, m^2

S_D	Surface area of D, m^2
V_B	The volume B, m^3
τ	The time required to complete reaction of a particle, s.
X_B	Fractional conversion of reactant B, %.
X_C	Fractional conversion of reactant C, %.
X_D	Fractional conversion of reactant D, %.
E	Activation energy, KJ/mol

Greek symbols

α	relationship between the numbers of initial moles of iron, titanium and aluminum to the volume of the reaction
ρ_B	Density of B, mol/m^3
ρ_C	Density of C, mol/m^3
ρ_c	Density of D, mol/m^3

Subscripts

S	The particle surface
p	Surface of the core unreacted
∞	Distant location of the liquid film

INTRODUCTION

The industrial unit Alumina do Norte do Brazil S/A (Hydro- ALUNORTE), located in the state of Pará, created to produce and market alumina, aluminum oxide, Al_2O_3 , together with miner Rio do Norte S/A (MRN) aluminum Brasileiro S/A

(ALBRAS) and Hydroelectric Tucuruí complete cycle of aluminum production in the state, and although the production of aluminum has a great socio-economic importance to the state, it generates a large amount of solid residue called red mud (LV), thereby causing environmental impacts. According to Magalhães (2012), some studies indicate that the red mud can be used as a source of raw material for the concentration and recovery of valuable metals such as titanium, thereby making it a raw material for the production thereof.

One theory for the uncatalyzed reactions of particles surrounded by a fluid which react with may be treated considering two ideal models simple: progressive conversion model and model without reaction in the core (Balarini, 2009). For the progressive conversion model assumes that reactant fluid enters and reacts in the particle at all times, most likely with different velocities and in different places. Thus, the solid reactant is converted continuously and progressively within the particle. In the model without reaction in the core is assumed that the reaction occurs primarily on the outer surface of the particle. The reaction zone then moves toward the center of the solid and may leave material for the behind completely converted and inert solid (ash), so that at any instant, there is a core of unreacted material which decrease in size during the reaction. However, the outline of this unreacted core does not always have a definite form but, nevertheless, there is evidence that, in most cases, the model without reaction in the core is closer of real particles than progressive conversion model (Levenspiel, 1999).

In this context, based on the unreacted core model, was performed a kinetic study of reaction solid-liquid (leaching) between the red mud and sulfuric acid solutions in order to extract iron, titanium concentration aiming in the red mud, and to a greater understanding of how to process the extraction of iron oxide, was carried out mathematical modeling of the extraction process, in order of obtain a model which would fit the experimental data, and capable of allowing the obtention of kinetic parameters such as: activation energy, rate constant for the reaction, well how the controller stage of the extraction process.

MATHEMATICAL MODELING OF LEACHING PROCESS RED MUD

According to the unreacted core model the stages main of a process of extracting metals from a mineral matrix can be described as follows: Stage 1 - Diffusion of the reactant fluid A through the layer surrounding the particle to the surface of the solid. Stage 2 - penetration and diffusion of A through the ash layer to the surface of the unreacted core. Stage 3 - Reaction of the fluid A with the solid in the reaction surface. Stage 4 - Diffusion of the fluid B product through the ashes back to the outer surface of the solid. Stage 5 - Diffusion of B through of the layer of

fluid back for into the solution. Main Assumptions of the mathematical model, are:

- The mathematical modeling is performed considering that the red mud particles are all spherical;

- Considering the leaching process as a reaction system solid-fluid, the mathematical model is developed based on the unreacted core model, then the mathematical modeling is performed using the following stages: Flow of reactant A in the liquid film; Flow of the reactant A in the region $r_c < r < R$; Reaction of the reagent A on the surface of r_c , where r_c is the radius of the core of the unreacted particle and R is the radius of the particle;

- It is considered that only the iron oxide is being extracted from red mud;

- The variables main affecting the extraction process are temperature and concentration of sulfuric acid;

- The extraction process is governed by the third stage, ie, the reaction of the fluid A (H_2SO_4) with red mud particles in the reaction surface.

Development Of The Mathematical Model

The flow of reagent A in the liquid film may be given under the definition of a mass transfer coefficient (similar to Newton's law of cooling). For the case in question the mass flow of A to the surface is given by:

$$N_{A_{z-p}} = K_m (C_{A\infty} - C_{A_s}) \quad (1)$$

where $N_{A_{z-p}}$ is the flow of the reagent away from of the liquid film, mol/(m².s), K_m is the coefficient of mass transfer in the liquid film, m.s⁻¹, $C_{A\infty}$ is the concentration of A away from of the liquid film, mol/L, and C_{A_s} is the concentration of A on the particle surface. mol/L. For the case in question, ie, particles red mud were all considered with spherical shape, and as the flow is variable for the spherical geometries, we will opt to work, for all cases, derived from Eq. (1) in terms of rate, thus, Eq.(1), becomes:

$$q_{A_{z-p}} = a_p \times N_{A_{z-p}} = 4\pi R^2 K_m (C_{A\infty} - C_{A_s}) \quad (2)$$

where $q_{A_{z-p}}$ is the taxa of reaction away from of the liquid film, mol/s, R is the radius of a sphere, m, and a_p is the area of a particle of red mud. m².

The rate on the region $r_c < r < R$ can be obtained according to the Fick's law of diffusion:

$$q_{A_p} = \frac{4\pi D_{ef}}{\left(\frac{1}{r_c} - \frac{1}{R}\right)} \times (C_{A_s} - C_{A_c}) \quad (3)$$

where q_{A_p} is the surface reaction rate, D_{ef} is the diffusion coefficient, $m^2.s^{-1}$, r_c is the core radius unreacted, m , and C_{A_c} is the concentration of the acid on the surface.

The reactions which occur on the surface r_c are the reaction between iron (Fe_2O_3) and sulfuric acid solution, well as, may happen the acid reaction with titanium (TiO_2) and aluminum (Al_2O_3). The total rate of consumption of the reagent A at the surface r_c can be written as follows:

$$-\frac{1}{Si} \frac{dN_{A_{TOTAL}}}{dt} = R_{A_{TOTAL}}^* \quad (4)$$

$$= K_1 \frac{S_B}{Si} C_A|_{r_B} + K_2 \frac{S_C}{Si} C_A|_{r_C} + K_3 \frac{S_D}{Si} C_A|_{r_D}$$

where K_1 , K_2 and K_3 are the kinetic constants of iron, titanium and aluminum, respectively, m/s , S_B , S_C and S_D are the surfaces area B, C and D, respectively, m^2 , $C_A|_{r_B} \approx C_A|_{r_C} \approx C_A|_{r_D} \approx C_A|\bar{r}$ are the concentrations of A of the unreacted core and Si is the total area, m^2 .

Consequently the Equation of the rate for the consumer in the r_c surface, takes the following form:

$$q_{A_{TOTAL}} = 4\pi\bar{r}^2 (K_1 \xi_B + K_2 \xi_C + K_3 \xi_D) C_{A\bar{r}} \quad (5)$$

$$\text{where } \xi_B = \left(\frac{r_B}{\bar{r}}\right)^2; \xi_C = \left(\frac{r_C}{\bar{r}}\right)^2; \xi_D = \left(\frac{r_D}{\bar{r}}\right)^2$$

Making an analogy electrical with mass transfer process with chemical reaction (processes in series), we can find, derived from Eq. (5), the total resistance, \mathbb{R}_T^* , based on the liquid film in the process of diffusion and chemical reaction, is written as:

$$\mathbb{R}_T^* = \frac{1}{k_m} + \frac{\left(1 - \left(\frac{\bar{r}}{r_p}\right)\right) r_p}{\left(\frac{\bar{r}}{r_p}\right) D_{ef}} + \frac{1}{\left(\frac{\bar{r}}{r_p}\right)^2 (\xi k_1 + \xi k_2 + \xi k_3)} \quad (6)$$

$$\text{where } \bar{r} = \frac{(r_B + r_C + r_D)}{3} \text{ and } r_p \text{ is the radius of}$$

particle. In this case, the rate, q_A , can be given by the equation below:

$$q_{A_{TOTAL}} = \frac{C_{A\infty}}{\mathbb{R}_T^*} = U_A C_{A\infty} \quad (7)$$

$$\text{where } U_A = \frac{4\pi r_p^2}{\mathbb{R}_T^*}. \text{ The substituting Eq. (7) into}$$

Eq. (5) is written as:

$$C_{A\bar{r}} \approx \frac{C_{A\infty}}{\left(\frac{\bar{r}}{r_p}\right)^2 \mathbb{R}_T^* (K_1 \xi_B + K_2 \xi_C + K_3 \xi_D)} \quad (8)$$

According Balarini (2009), the chemical stage is usually more sensitive to temperature than the physical stage, therefore, experiments at different temperatures can easily distinguish between gray or diffusion layer on one side, and chemical reaction on the other hand, as driver stage. In this case, \mathbb{R}_T^* will be represented by the last term of the Eq. (6).

$$\mathbb{R}_T^* = \frac{1}{\left(\frac{\bar{r}}{r_p}\right)^2 (K_1 \xi_B + K_2 \xi_C + K_3 \xi_D)} \quad (9)$$

It is known that $C_{A\infty}$ in the Eq. (8) varies with time, Bayrak (2005) in his study of natural magnesite dissolution kinetics of gluconic acid solutions affirms that this concentration can be represented as follows:

$$C_i = C_{i0} \left(1 - \sum_i \frac{N_{i0}}{Vb} X_i\right) \quad (10)$$

Based on Balarini (2009) and adapting to the case in question, the Eq. (10) takes the following form:

$$C_{A\bar{r}} = C_{A\infty} \approx C_{A(0)} (1 - \alpha_0 X_B - \alpha_1 X_C - \alpha_2 X_D) \quad (11)$$

where, $\alpha_0 = N_{B_0} / (VC_{A_0} b)$; $\alpha_1 = N_{C_0} / (VC_{A_0} b)$ and X_i is the fraction of a particular component, X_B , X_C and X_D , %, N_{B_0} the initial moles of iron, N_{C_0} the initial moles of aluminum, b the stoichiometric coefficient of iron and V the reaction volume, m^3 .

The mathematical models are usually given in terms of extraction of the metals of interest (conversion), in this case, the reaction rate for the components B, C and D are represented as follow:

$$\frac{dx_B}{dt} = \tilde{C}_1 (1 - x_B)^{\frac{2}{3}} (1 - \alpha_0 x_B - \alpha_1 x_C - \alpha_2 x_D) \quad (12)$$

$$\frac{dx_C}{dt} = \tilde{C}_2 (1 - x_C)^{\frac{2}{3}} (1 - \alpha_0 x_B - \alpha_1 x_C - \alpha_2 x_D) \quad (13)$$

$$\frac{dx_D}{dt} = \tilde{C}_3 (1-x_D)^{\frac{2}{3}} (1-\alpha_0 x_B - \alpha_1 x_C - \alpha_2 x_D) \quad (14)$$

$$t = 0 \Rightarrow x_B = x_C = x_D = 0$$

where $C_1 = \frac{3bCA\infty(0)K_1}{\rho_B r_p}$; $\tilde{C}_2 = \frac{3dCA\infty(0)K_2}{\rho_C r_p}$

and $\tilde{C}_3 = \frac{3bCA\infty(0)K_3}{\rho_D r_p}$

where ρ_B , ρ_C and ρ_D are molar density of iron, titanium and aluminum, respectively, mol/m³.

To solve the mathematical model represented by Eqs. (12), (13) and (14) was built a code in FORTRAN language in 2003, where we used the IMSL routine IVPAG that is appropriate for solving of ordinary systems ordinary differential equations with nature "stiff". This code was run on a Pentium Intel (R) Core (TM) Quad 2.66 GHz platform. Also for the solution of the system of values K_1 , K_2 and K_3 were estimated, to subsequently obtain \tilde{C}_1 , \tilde{C}_2 and \tilde{C}_3 and consequently values of the $X_B(t)$, $X_C(t)$ and $X_D(t)$ were obtained.

After this process the estimated, theoretical values of K_1 , K_2 and K_3 were fitted with the experimental data for later obtaining the Arrhenius parameters. We used experimental data obtained from the leaching process at 900°C calcined red mud order to extraction and / or concentration of titanium present in the waste to feed the developed mathematical model. The leaching process was conducted at the temperatures 60, 80 and 90 °C using as a leaching agent in the sulfuric acid concentrations of 20 and 30%.

RESULTS AND DISCUSSION

Effect of the temperature and concentration in the reaction constant K_1 and K_2

In the Table 1 can be observed values of the speed constant K_1 of reaction of the red mud calcined at 900 °C (LV900). In this Table 1, it can be observed (for both acid concentrations studied) which reaction constant increases with temperature, as expected.

Table 1. Behavior of K_1 with the concentration and temperature of leaching (LV-900).

Temperature (K)	K_1 20% (m/s)	K_1 30% (m/s)
333.16	1.76E-10	1.23E-09
353.16	9.48E-09	6.32E-09
363.16	2.07E-08	9.48E-09

The behavior of the reaction constant K_1 with acid concentration can be analyzed as follows:

i) For T = 333.16 K, K_1 decreases with

concentration;

ii) For T = 353.16 K, K_1 decreases with concentration;

iii) For T = 363.16 K, K_1 decreases with concentration.

In this case the red mud calcined at 900 °C sodium participated of the reactions of calcination and formed a glassy phase. Thus, it is suggested that the mechanism of reaction suffer interference of the following factors that reduce the rate of reaction with increasing concentrations of acid, such factors are: a) the common ion effect, and b) the ionic dissociation of sulfuric acid which is reduced drastically with increasing concentration, (VOGEL, 1989).

Table 2 shows the results speed constant K_2 of reaction, which has similar behavior to K_1 .

Table 2. Behavior of K_1 with the concentration and temperature of leaching (LV-900).

Temperature (K)	K_2 20% (m/s)	K_2 30% (m/s)
333.16	4.32E-10	2.28E-10
353.16	7.20E-10	4.92E-10
363.16	8.88E-10	6.84E-10

In the Figures (1) and (2) for the iron and titanium are shown respectively in curves $\ln K_1$ and $\ln K_2$ versus $1/T$ based on the Arrhenius equation for the red mud in the two acid concentrations studied.

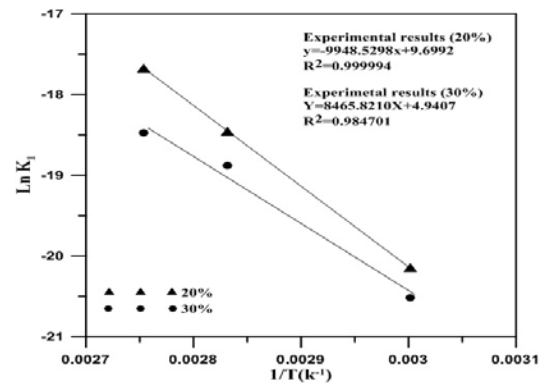


Figure 1. Obtaining the kinetics parameters of the Arrhenius equation of the iron oxide.

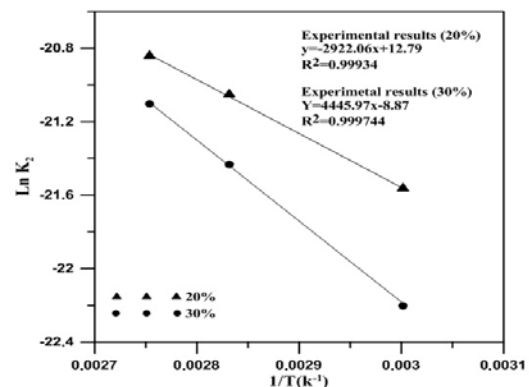


Figure 2. Obtaining the kinetics parameters of the Arrhenius equation of the titanium oxide.

From Figures 1 and 2 it was possible to obtain the kinetic parameters of activation energy and frequency factor.

Table 3 shows the values of parameters kinetics the Arrhenius equation for the iron obtained from Figure 1. The value of activation energy shows that for the reaction with iron oxide leaching kinetics is controlled by the chemical reaction.

Table 3. Kinetics parameters of the Arrhenius equation for iron .

% de H ₂ SO ₄	E (KJ/mol)	K ₀ (m/s)
20	82.71	16305.2
30	70.38	139.06

Table 4 it is noted that for the reaction with the titanium oxide the activation energy values are below of 25 KJ/mol for concentration of 20% sulfuric acid, suggests that the mass transport is the controlling step in the process.

Table 4. Kinetics parameters of the Arrhenius equation for titanium.

% de H ₂ SO ₄	E (KJ/mol)	K ₀ (m/s)
20	24.29	2.79E-06
30	36.96	14.29E-05

CONCLUSIONS

In this work, was developed a mathematical model based on total resistance to mass transfer in the leaching process. This model has been constructed taking into consideration the resistance at the liquid film, the resistance in the region of ash and resistance due to chemical reaction at the surface of the unreacted core.

An analytical solution for the model was determined considering that iron is prevalent in the extraction process and that the reaction rate controls the leaching process. The model then was fit to experimental data in order to determine the kinetic constants and the parameters of the Arrhenius law for each concentration studied.

For the case of red mud calcined at 900 °C the sodium was consumed, and thus, it is suggested that the reaction mechanism only suffer interference of the common ion effect and ionic dissociation of sulfuric acid.

The results of activation energy for the reaction with the iron exceeds 40 KJ/mol, which according to the literature, the values above this shows that the chemical reaction is the step of controlling the process. For reactions with titanium oxide was observed that the values for the activation energy is less than 25 KJ/mol for the 20% concentration sulfuric acid, according to propose Prosser (1996), mass transport is step control process of leaching.

REFERENCES

- Balarini, J. C., 2009, Kinetic Study Ustulado of Votorantim Metais Zinco: Catalytic Mechanism not Associated with the Characterization and Determination of Residence Times, Doctoral Thesis, School of Engineering, Minas Gerais, MG, Brazil.
- Bayrak, B., 2005, Investigation of Dissolution Kinetics Natural Magnesite in Gluconic Acid Solutions, Journal of Chemical Engineering, Vol. 117, No. 1, pp. 109-115.
- Bhatnagar, S, S., and Sundara Rao, A. L., 1945, Pilot Plant for the Recovery of Titanium Dioxide from Bauxite Sludge, Journal of Scientific and Industrial Research, Vol. 4, pp. 378-381.
- Levenspiel, O., 2000, *Engineering of Chemical reactions*, Edgar Blucher Book.
- Magalhães, E, M, 2012, Estudo da Extração de Compostos de Ferro da Lama Vermelha Visando a Extração e/ou Recuperação de Compostos de Titânio, Doctoral Thesis, PRODERNA/ITEC, Belém, PA. (*in Portuguese*)
- Kasliwal, P, and Sai, P. S. T., 1999, Enrichment of Titanium Dioxide in Red Mud: a Kinetic Study, Hydrometallurgy, Vol. 53, pp. 73-87.
- Vogel, A, I., 1989, *Quantitative Chemical Analysis*, Textbook.