
Effect of Cu Doping on the Anatase-to-Rutile Phase Transition in TiO₂ Photocatalysts: Theory and Experiments

Ciara Byrne ^{a,b}, Lorraine Moran ^c, Daphne Hermosilla ^d, Noemí Merayo ^c, Ángeles Blanco ^c, Stephen Rhatigan ^f, Steven Hinder ^g, Priyanka Ganguly ^{a,b}, Michael Nolan ^{f,†}, and Suresh C. Pillai ^{a,b,†}

^a *Nanotechnology and Bio-engineering Research Group, Department of Environmental Science, Institute of Technology Sligo, Sligo, Ireland*

^b *Centre for Precision Engineering, Materials and Manufacturing Research (PEM), Institute of Technology Sligo, Sligo, Ireland.*

^c *Department of Life Sciences, Institute of Technology Sligo, Sligo, Ireland*

^d *University of Valladolid, E.U. Ingenierías Agrarias de Soria, Campus Duques de Soria, 42005 Soria, Spain.*

^e *Complutense University of Madrid, FCC Químicas, Ciudad Universitaria s/n, 28040 Madrid, Spain.*

^f *Tyndall National Institute, University College Cork, Lee Maltings, Dyke Parade, Cork, Ireland*

^g *The Surface Analysis Laboratory, Faculty of Engineering and Physical Sciences, University of Surrey, Guildford, Surrey, GU2 7XH, United Kingdom*

† Corresponding authors E-mail address: michael.nolan@tyndall.ie; pillai.suresh@itsligo.ie

Abstract

This paper presents a study of the effect of copper doping of TiO₂ (0, 2, 4 & 8 mol. % Cu) calcined at various temperatures on the anatase-rutile phase transition temperature and the resulting photocatalytic properties. The 0% Cu (control) sample remains 100% anatase till 500°C, contained 34.3% anatase at 600°C and transitioned to 100% rutile by 650°C. All copper doped samples maintained 100 % anatase up to 600°C. With 2% Cu doping, anatase fully transformed to rutile at 650°C, at higher Cu contents of 4% & 8% mixed phased samples, with 27.3% anatase and 74.3% anatase respectively, are present at 650°C. All samples had fully transformed to rutile by 700°C. 0%, 4% and 8% Cu were evaluated for photocatalytic degradation of 1, 4 dioxane. Without any catalyst, 15.8 % of the 1,4 dioxane degraded upon irradiation with light for 4 hours. Cu doped TiO₂ shows poor photocatalytic degradation ability compared to the control samples. Density functional theory (DFT) studies of Cu-doped rutile and anatase show formation of charge compensating oxygen vacancies and a Cu²⁺ oxidation state. The high cost of formation of reducing oxygen vacancies with Cu doping is proposed as the origin of the enhanced temperature stability of anatase. XPS and DFT show that Cu and Ti cations are reduced to Cu⁺ and Ti³⁺. Cu 3d states are present in the valence to conduction band energy gap upon doping. We propose that the poor photocatalytic activity of Cu-doped TiO₂, arises from the charge recombination at defect sites that result from incorporation of copper into TiO₂.

Keywords: TiO₂, doping, DFT, oxygen vacancy, photocatalysis

1. Introduction

Titanium dioxide (TiO₂) was first commercially used during the 20th century for applications that include pigments in paint, UV blockers, batteries and food colouring. Since 1972, when the

production of hydrogen with TiO₂ under illumination was first reported [23] the use of TiO₂ as a photocatalyst has gained significant interest.[47] There are numerous reasons why TiO₂ remains the most researched photocatalyst. These include ease of preparation, strong oxidising ability, long term stability, nontoxicity, high refractive index, high dielectric constant and low cost.[26, 55, 65, 71, 73] The potential for use of TiO₂ in energy and environmental applications is another reason why TiO₂ continues to be examined. Of particular importance are hydrogen production, CO₂ reduction, solar cells, self-cleaning coatings and degradation of organic compounds (e.g. phenol) in water.[4, 55, 65, 73] The large band gap (3.2 eV for anatase) is partly responsible for its use as a photocatalyst.[77] The band gap has a direct impact on the rate of electron-hole recombination during photocatalysis and titania has a relatively slow recombination rate compared to most photocatalysts.[26]

TiO₂ is naturally present in three main phases: anatase (tetragonal, a=b=3.785Å, c=9.54Å), brookite (orthorhombic, a=5.143Å, b=5.456Å, c=9.182Å) and rutile (a=b=4.593Å, c=2.959Å). [7, 12, 19, 29, 58] The thermodynamically metastable phases, anatase and brookite, transition irrevocably into the stable rutile phase at high temperatures.[26] Generally this takes place in the range of 600-700°C in pure synthetic TiO₂. Of these TiO₂ phases, anatase is considered to be the most photocatalytically active phase. It can however only be activated by UV light, which accounts for *ca.* only 4% of the solar spectrum.[9] In order to stabilise the anatase phase at elevated temperatures and to utilise UV and visible light for photocatalysis, chemical modifiers and dopants can be used. These include anion dopants, e.g. carbon, [5, 17, 20, 30, 60] nitrogen, [9, 21, 24, 56] sulphur [58, 75] and fluorine[11, 57], or metal dopants, e.g. iron, [32, 75] silver, [35, 53] chromium[33] and manganese [1, 28].

Copper has been previously investigated as a potential dopant in TiO₂ but to date a detailed systematic analysis of the effect of Cu doping on the phase stability of TiO₂ is lacking.[77] In an important contribution, Yoong *et al.* examined Cu-doped Degussa P25 TiO₂ for different weight% of Cu (0, 2, 5, 10, 15 %) at three temperatures (300, 400, 500°C).[77] However, the highest temperature in this work is below the anatase-rutile phase transition. Hence there is no comprehensive understanding of the effect of copper doping on the anatase-rutile phase transition in TiO₂. Unravelling the role of Cu in this phase transition will clearly be beneficial in stabilising the more photoactive anatase phase of TiO₂ at higher temperatures.

Therefore, the aim of this paper is to present a systematic and detailed study of the impact of copper doping of titanium dioxide on the temperature of the anatase to rutile phase transition, composition and the resulting photocatalytic activity. We have prepared copper doped titania with four different Cu concentrations, namely 0, 2, 4 and 8 mol. % Cu and these were calcined between 400-1000°C. Density functional theory (DFT) studies of Cu doping of bulk rutile and anatase were carried out to explore the effect of doping on the cation oxidation states, oxygen vacancy formation and any changes to the electronic structure of rutile and anatase after doping. X-ray diffraction (XRD) analysis and Raman spectroscopy were used for determining the phase composition of each sample. X-ray photoelectron spectroscopy (XPS) was used for identifying the bonding that was present in samples.

2. Materials & Methods

2.1 Chemicals & Reagents

Titanium tetraisopropoxide (97%), copper sulphate pentahydrate ($\geq 98.0\%$) and isopropanol ($\geq 99.5\%$) were purchased from Sigma-Aldrich and were used without further treatment. 1,4-dioxane was purchased from Merck.

2.2 Preparation of nanomaterials

2.2.1 Preparation of TiO_2

46.16 mL of titanium isopropoxide (TTIP) was added to 200 mL of isopropanol (IPA). This solution was stirred for 15 min. To this solution 200 mL of deionised water was added. This mixture was stirred for another 30 min. The resulting gel was dried in the oven set at 100°C for 12 hrs. The resulting powder was annealed at 400°C , 500°C , 600°C , 650°C , 700°C and 800°C , at a ramp rate of $10^\circ\text{C}/\text{min}$ and held at the target temperature for 2 hrs.

2.2.2 Preparation of copper doped materials

For a 2% copper sample, 45.24 mL of TTIP was added to 200 mL of IPA and was stirred for 15 min (Solution A). 0.8705 g of copper sulphate (CuSO_4) was added to 200 mL of deionised water, this was stirred for 15 min (Solution B). Solution B was added to Solution A and this was stirred for 30 min. The resulting gel was dried in the oven at 100°C for 12 hrs. The resulting powder was annealed at 440°C , 500°C , 600°C , 650°C , 700°C and 800°C , at a ramp rate of $10^\circ\text{C}/\text{min}$ and was held for 2 hrs. This method was repeated for the 4% and 8% copper samples by altering the amount of TTIP and CuSO_4 (4% - 44.32 mL and 1.7375 g; 8% - 42.47 mL and 3.5075 g).

2.3 Characterisation

All samples were analysed with X-ray Diffraction (XRD). The diffractograms were produced using a Siemens D500 X-ray powder diffractometer, using $\text{Cu K}\alpha$ radiation ($\lambda = 0.15418 \text{ nm}$). The diffraction range examined was between $2\theta = 10^\circ - 80^\circ$. To determine the fraction of rutile in the samples, the Spurr equation was used (eq. 1). [67]

$$F_R = \frac{1}{1 + 0.8 \left[\frac{I_A(101)}{I_R(110)} \right]} \quad (\text{eq. 1})$$

where F_R is the quantity of rutile in mixed sample and $I_A(101)$ and $I_R(110)$ are the intensities of the main anatase and rutile peaks.

The crystallinity of the samples were calculated using the XRD spectra and the Scherrer equation (eq. 2). [62]

$$\Phi = \frac{K\lambda}{\beta \cos\theta} \quad (\text{eq. 2})$$

where Φ is the crystallite size, K is the shape factor, λ is the X-ray wavelength, β is the full line width at the half-maximum height of the main intensity peak and θ is the Bragg angle.

The Horiba Jobin Yvan LabRAM HR 800 with a grating of 300gr/mm was used for Raman analysis. A 660nm solid state diode laser standard bandwidth version with double edge filter upgrade was the laser used. The acquisition time was 3 seconds. When focusing onto the sample a X50 lens was used.

A ThermoFisher Scientific Instruments (East Grinstead, UK) K-Alpha⁺ spectrometer was utilised in obtaining XPS spectra, with a monochromated Al K α X-ray source ($h\nu = 1486.6$ eV) and ~ 400 μm radius was used as an x-ray spot. The survey spectra and a high-resolution core level spectrum for all elements was obtained using a Pass Energy of 200 eV and 50 eV, respectively. The C1s peak (285) was used as a charge reference to account for charging effects during acquisition. The non-linear (Shirley) background was removed from the high resolution, core level spectra before calculating the quantitative surface chemical analyses. The manufacturers Avantage software was used which incorporates the appropriate sensitivity factors and corrects for the electron energy analyser transmission function.

The surface morphology of the samples was analysed using the Siemens TM1000 Scanning Electron Microscopy with Energy Dispersive X-Ray Analyser (SEM-EDX).

In order to determine the surface area of the samples the Brunauer–Emmett–Teller method (BET) was used. The samples were first degassed for an hour at 300°C. The adsorption isotherms were acquired at -196.15°C.

The following analyses were made according to the standard methods for the examination of water and wastewater (APHA 2005). Total organic carbon (TOC) was measured by the combustion-infrared method using a multi N/C^o 3100 TOC/TN analyser (Analytik Jena AG, Jena, Germany), which performed the catalytic combustion on cerium oxide at 850°C.

1,4-Dioxane was quantified using gas–liquid chromatography (GLC) on a 7980A instrument (Agilent Technologies Inc., Palo Alto, CA) equipped with a flame ionization detector. The temperatures of the injector and the detector were 310°C and 280°C, respectively. Samples (2 μL) were injected using the pulsed-split mode (split ratio 5:1) and analysed in a TRB-FFAP (Teknokroma, Sant Cugat del Vallès, Spain) fused silica column (30 m x 0.25 mm internal diameter x 0.25 μm film thickness) with He (43 psi) as carrier gas, and the following temperature programme: 80°C to 240°C at a 15°C/min ramp rate, after a 9 min initial hold. Peaks were identified according to relative retention time figures provided by commercial standards. Quantification was performed according to peak area, corrected with the response factors calculated for each compound using 1-butanol (60 ppm) as internal standard, and the GC-ChemStation software Rev.B.04.02 (96) from Agilent.

2.4 Photocatalysis

Experiments were performed with a synthetic solution of 1,4-dioxane (75 mg/L) that was kept stirred during the experiment using a magnetic device. The corresponding doped-TiO₂ catalyst was added to the suspension with a concentration of 1 g/L. The photocatalytic reaction was performed for duration of 240 minutes. Samples were withdrawn from the solution every 30 min. The source of UV light was a solar simulator supplied by Newport (Irvine, USA) equipped with a Xenon lamp (300 W). A correction filter (ASTM E490-73a) provides the simulated solar spectrum under ideal conditions. A total photon flux of $6.8 \cdot 10^{19}$ photon $\cdot\text{s}^{-1}$ was calculated to flow inside the photochemical reactor, as described by Liang et al. (2011). Light intensity between 200 to 400 nm resulted of 150 W $\cdot\text{m}^{-2}$ at 3

cm from the light source, which was the distance between the sample surface and the lamp. Light intensity was recorded using a radiometer (UV-Elektronik, UV-VIS Radiometer RM-21, Ettlingen, Germany).

The light intensity recorded on the irradiated liquid surface in $W \cdot m^{-2}$ ($J \cdot s^{-1} \cdot m^{-2}$) was converted to kJ/L taking into account the volume of the solution (50 mL) and the irradiated surface (0.0104 cm^{-2}) in order to normalize the data. Blank experiments either performed without adding the catalyst, without switching the UV lamp on, or using no dopant concentration were performed. All experiments were repeated three times.

2.5 Density Functional Theory Computations

Calculations were performed using the VASP5.2 [37, 38] code with projector augmented wave [3, 39] (PAW) potentials to account for the core-valence interaction and a kinetic energy cut-off of 400 eV. Cu was substitutionally doped onto a Ti site in rutile ($2 \times 2 \times 3$) and anatase ($2 \times 2 \times 2$) supercells. This gives dopant percentages of 4.2 % and 3.1 % for rutile and anatase respectively, which are consistent with the experimental concentrations of Cu in TiO_2 . [8, 10, 79] The k-point sampling used a Monkhorst-Pack ($4 \times 4 \times 2$) grid for both bulk polymorphs. Structures were relaxed until forces were less than $0.01 \text{ eV } \text{Å}^{-1}$.

Calculations were performed taking into account spin polarisation and no symmetry constraints were imposed. In the initial DFT + U calculations, $U = 4.5 \text{ eV}$ was applied to the Ti 3d states and $U = 7 \text{ eV}$ was applied to the Cu 3d states, arising from the inability of DFT to describe consistently the Cu^{2+} oxidation state of Cu and $U = 7 \text{ eV}$. [51, 52] These choices for U are based on previous studies. [6, 36, 46, 49, 50] The starting geometries were manually distorted from the symmetric bulk geometry in order to examine relaxation to distorted geometries which can be compared with undistorted geometries. To study the charge compensation that arises as a result of the difference in the Cu^{2+} and Ti^{4+} oxidation states, one oxygen ion was removed from different sites of the most stable Cu-doped structures and the energy of formation was calculated via:

$$E^{vac} = E(Cu_xTi_{1-x}O_{2-y}) + 1/2E(O_2) - E(Cu_xTi_{1-x}O_2) \text{ (eq. 3)}$$

where $E(Cu_xTi_{1-x}O_{2-y})$ is the total energy of Cu doped TiO_2 with a charge compensating oxygen vacancy and $E(Cu_xTi_{1-x}O_2)$ is the total energy of Cu-doped TiO_2 . The formation energy is referenced to half the total energy of O_2 . A similar formula is used to compute the formation energy of the subsequent reducing oxygen vacancy.

Given that copper ions can take a 2+ oxidation state these calculations were therefore performed with 1 and 3 unpaired spins which takes into account the electron deficit due to substitutional doping of Cu^{2+} for Ti^{4+} and the d^9 configuration of Cu^{2+} . The oxidation states of the Cu dopant and lattice Ti and O ions were determined from Bader charge analysis [27] and spin magnetisations and these values are quoted in the results.

3. Results and Discussion

3.1 X-ray Diffraction (XRD) Characterisation

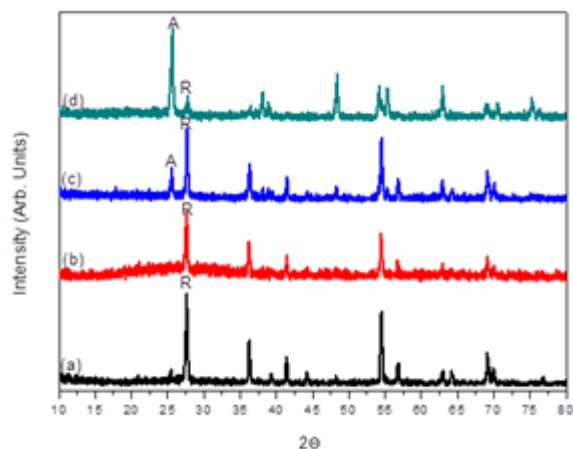


Figure 1: XRD of (a) 0% Cu-TiO₂ (b) 2% Cu-TiO₂ (c) 4% Cu-TiO₂ (d) 8% Cu-TiO₂ after calcining to 650°C. A = anatase and R = Rutile

X-ray Diffraction (XRD) was used to determine the effect of copper on the anatase to rutile transition temperature in TiO₂. The intensities of the main anatase and rutile peaks (101 and 110 respectively) were used in the Spurr equation (eq. 1) for calculating the % anatase and % rutile present in each sample. There were no peaks present relating to copper metal (which appear at approx. $2\theta = 43, 50$ and 74°), [72] the only peaks that were present were those for titanium dioxide. All samples were 100% anatase phase at 400°C and 500°C. At 600°C, the control (0%) was 34.3% anatase and 65.7% rutile while the copper doped samples remained 100% anatase (figure S1). At all temperatures above 650°C, the 0% and 2% Cu-TiO₂ samples contained 100% rutile. However, at the same temperature the 4% and 8% Cu-TiO₂ had 27.3% anatase and 74.3% of anatase respectively (figure 1). All samples were 100% rutile phase at temperatures above 700°C (figure S2). Figure 2 shows the composition profile of the samples prepared.

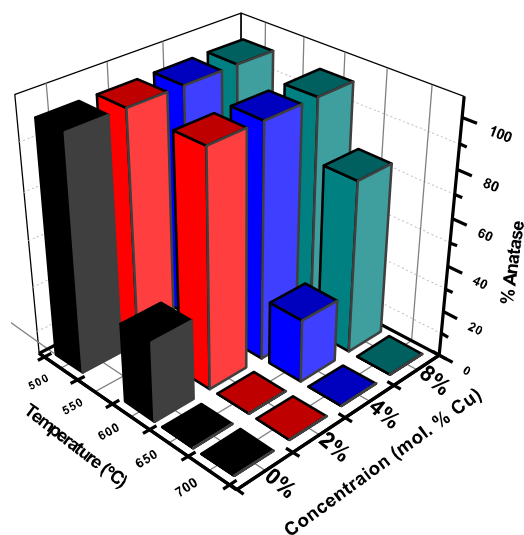


Figure 2: Percentage of the anatase phase in Cu-doped TiO₂ samples

XRD was also used to determine the crystallinity of all samples (Table 1) using the Scherrer equation (eq. 2). [62] Generally as the temperature increases so does the crystallinity. The origin of this is due to the samples converting from the anatase phase (with a smaller crystalline size) to the rutile phase. At 400°C, 500°C and 600°C all doped samples show a smaller crystalline size compared to the undoped sample, indicating that at these temperatures Cu doping stabilises the anatase phase. The 8% Cu sample has lowest crystalline size in the range of 400-700°C,

Table 1: Crystalline size (in nm) of all samples calcined at 400°C, 500°C, 600°C, 650°C, 700°C and 800°C.

	0% Cu	2% Cu	4% Cu	8% Cu
400°C	7.06	6.15	5.75	5.07
500°C	10.11	8.98	6.77	5.49
600°C	17.73 (A) 19.88 (R)	15.46	14.02	14.07
650°C	24.87	25.03	23.65 (A) 26.14 (R)	21.10 (A) 22.70 (R)
700°C	27.12	28.45	26.09	24.09
800°C	33.94	31.36	29.20	25.18

3.2 Raman Spectroscopy

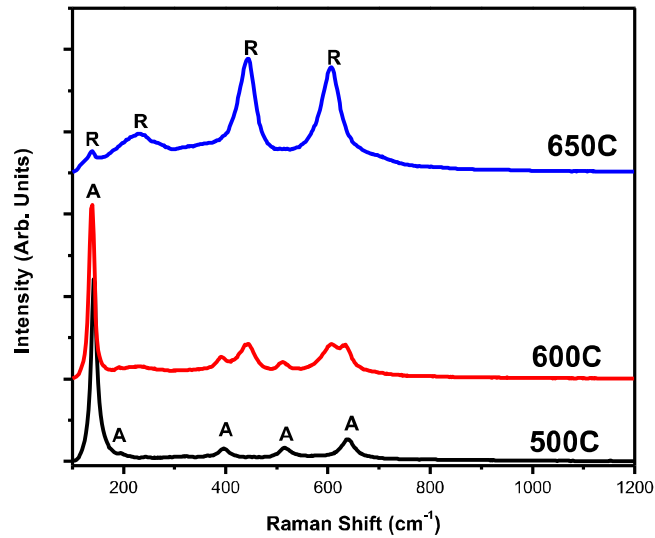


Figure 3: Raman spectra of 0% Cu-doped TiO₂.

The anatase to rutile transition of Cu-TiO₂ was further examined using Raman spectroscopy. A typical Raman spectrum shows characteristic modes at different wavenumbers corresponding to Raman shifts.[17, 18, 59] The active modes for anatase are A_{1g} , $2B_{1g}$ and $3E_g$ at 147, 197, 396, 516 and 638cm⁻¹. [2, 17, 18, 54, 59, 70] For rutile the Raman active modes are A_{1g} , B_{1g} , B_{2g} and $3E_g$ at 144, 238, 446, 612 and 827cm⁻¹. [2, 17, 18, 54, 59, 70] Raman spectra showed the presence of the titania peaks and did not show the occurrence of copper/copper oxides or other impurities. The Raman results are consistent with the data from XRD analysis. If we consider the example of 0% Cu-doping of TiO₂, then samples calcined at 500°C exhibited 100% anatase phase (figure 3), while 0% Cu-TiO₂

calcined at 600°C illustrated a mixed phase profile (figure 3). The peaks for 100% rutile phase can be observed for the 0% Cu-TiO₂ sample when calcined at 650°C (figure 3). The Raman spectra of 8% Cu-TiO₂ are shown in figure S3.

3.3 X-ray photoelectron spectroscopy (XPS)

The X-ray Photoelectron spectroscopy (XPS) measurements were performed to analyse the elemental composition and metal oxidation states of each sample. XPS analysis was performed on all samples that were treated at 600°C, 650°C and 700°C. Figure 4(a) illustrates the survey spectrum for the example of samples with 8% Cu-doping and which were calcined at 600°C, 650°C and 700°C. The survey spectrum indicates the presence of Titanium, Oxygen, Copper and Sulphur. C1s peaks (at binding energies (BE) of 284.9-285.0 eV) are present in all samples. These peaks can be attributed to adventitious carbon (C-C, C=C and/or C-H bonds) which arise due to contamination during synthesis and calcination.[16, 18, 19] The concentrations of the elements present in the Cu-doped TiO₂ materials are tabulated in Table S1. Sulphur is present at *ca.* 4 at.% in the 8% Cu material calcined at 600°C, Table S1. The presence of sulphur in Cu-doped TiO₂ at this concentration is mostly likely due to the release of sulphur dioxide from the Cu precursor (CuSO₄) during the calcination process. [66] However, the amount of Sulphur reduces to below 1 at.% in the composites calcined at 700°C (Table S1), which is also evident from the Sulphur 2p spectrum in figure 4(e).

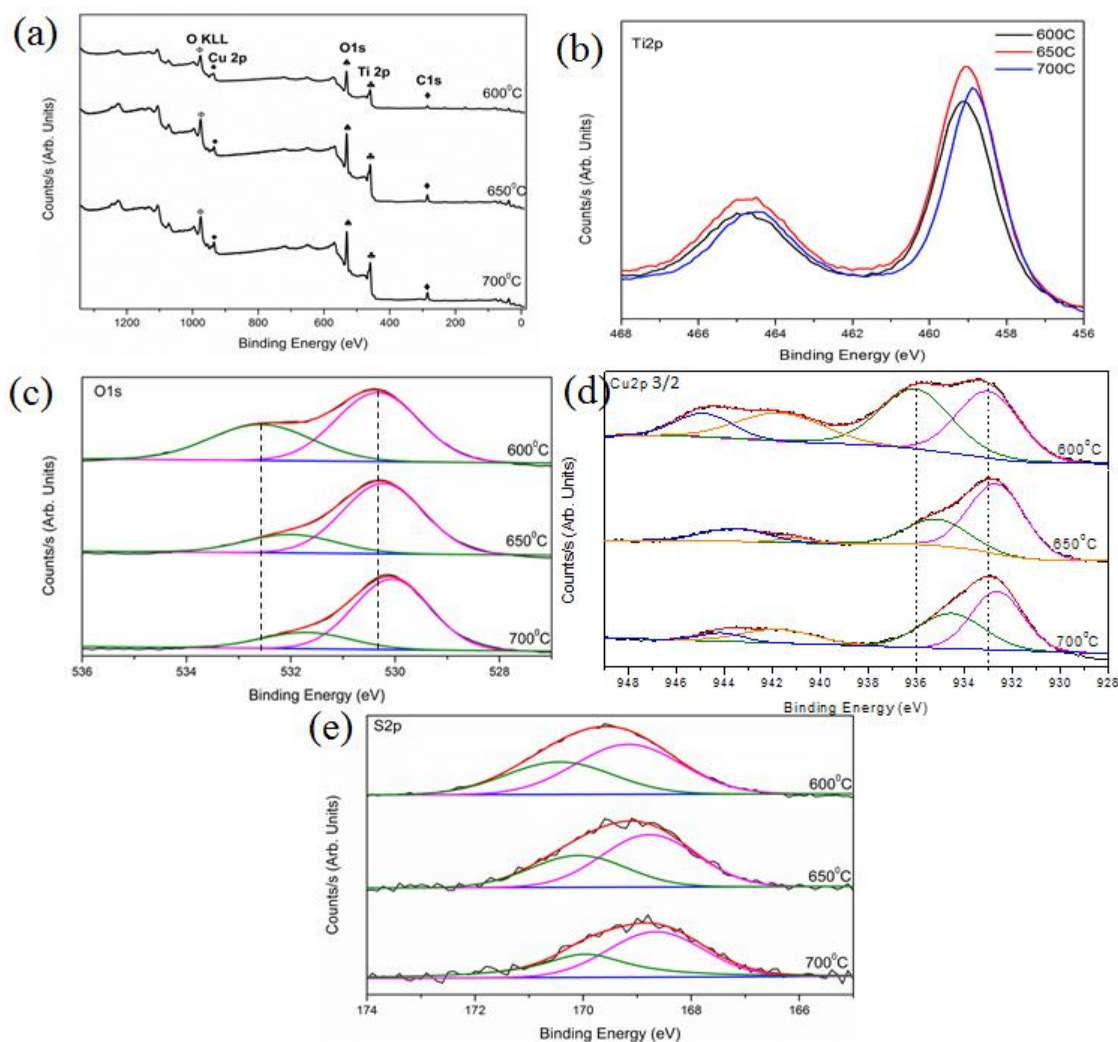


Figure 4: XPS spectra for the example of 8% Cu-TiO₂ that was calcined at 600°C, 650°C and 700°C, Part (a) shows the survey spectrum, (b) shows the Ti2p BE region, (c) shows the O1s BE region, (d) shows the Cu2p_{3/2} BE region and (e) shows the S2p BE region.

There is a similar decrease in the binding energy of the O1s peak (BE = 530.4-530.1 eV), shown in figure 4(c) and Tables S2 and S3. This slight decrease in the O1s BE further indicates the formation of oxygen vacancies. [2, 15, 19] The formation of oxygen vacancies (as determined from the O1s and Ti2p_{3/2} peaks) signifies that the anatase phase is beginning the transformation to the rutile phase. [2, 5, 15, 19, 76] The second dominant peak in the O1s spectra at 532.6 eV in Cu-TiO₂ calcined at 600°C shows a shift to 531.7 eV, when calcined at 700°C. These peaks are assigned to oxygen in the sulphate and oxygen bound to Cu (as Cu²⁺) respectively. [25]

As XPS is significantly more sensitive than XRD and Raman to minute compositional changes such changes can be detected from XPS analysis, i.e. any copper oxides that may form can be detected in XPS but not in XRD and Raman spectra.[58, 81] Figure 4(d) shows the Cu2p_{3/2} spectra of 8% Cu-TiO₂ samples calcined at 600°C, 650°C and 700°C. The sample calcined at 600°C exhibits a broad asymmetric curve from 930 eV to 937 eV. The deconvolution of this curve gave 2 prominent peaks at 933.1 eV and 936 eV corresponding to Cu²⁺ in CuO and CuSO₄ respectively. Calcining at higher temperatures of 650°C and 700°C resulted in slight shift in these peaks. At 700°C the peaks were observed at 932.6 eV and 934.1 eV corresponding to Cu¹⁺ and Cu²⁺ oxidation states, respectively. Hence, XPS results revealed the presence of copper in two oxidation states. Moreover, two satellite peaks of Cu2p_{3/2} that correspond to the Cu²⁺ oxidation state are observed at 941 eV and 944 eV; the peak intensities gradually decreased as the calcination temperature increased. [41, 44, 64, 69] The S2p (figure 4 (e)) XPS spectrum shows two sub-component peaks at 170.1 eV and 168.8 eV, these are attributed to S2p_{1/2} and S2p_{3/2} respectively and these binding energies suggest the presence of sulphur in S⁶⁺ state. [34]

3.4 Effect of Cu Doping and Temperature on Surface Area

BET analysis was performed in order to determine the surface area and porosity of the sample. Table 2 shows the surface area and the porosity for the control (0% Cu) and the example of 8% Cu-TiO₂, which shows the highest anatase-rutile transition temperature. The surface area for the control is significantly smaller than that of the 8% copper sample calcined at 500°C (both 100% anatase) and 600°C (0 Cu% = 34.3% anatase; 8 Cu% =100% anatase). After calcining at 700°C (where both samples are 100% rutile) the two samples have similar surface areas. There are small differences in the pore volumes of the different samples. For example in pure TiO₂ these range from 24 -26 Å and for 8% Cu-TiO₂ these range from 26 -27 Å (Table 2).

Table 2: Surface area and porosity of 0% and 8% Cu-TiO₂ calcined at 500°C, 600°C & 700°C

Sample	Surface area (m ² /g)	Pore volume (Å)
0% Cu-TiO ₂ 500°C	57.4	26.5
0% Cu-TiO ₂ 600°C	6.6	26.5
0% Cu-TiO ₂ 700°C	3.5	24.4
8% Cu-TiO ₂ 500°C	83.2	27.8
8% Cu-TiO ₂ 600°C	21.2	26.9
8% Cu-TiO ₂ 700°C	3.9	26.7

3.5 Scanning Electron Microscopy- Energy Dispersive X-Ray Analyser (SEM-EDX)

The morphology and elemental composition were examined using Scanning Electron Microscopy with an Energy Dispersive X-Ray Analyser (SEM-EDX). No specific shapes were able to be determined due to the agglomeration of the samples, as a result of the high calcination temperatures. Examples of SEM-EDX results are shown in the supplementary information (figure S4 & S5).

3.6 Density Functional Theory Simulations

3.6.1 Atomic and Electronic Structure of Cu-Doped TiO₂

The local atomic structure that results from substituting Cu on a Ti site in Cu-doped bulk rutile and anatase TiO₂ (see figure S6), is distorted about the dopant site. Replacing a Ti⁴⁺ cation with a Cu²⁺ cation results in a deficiency of two electrons and formation of two oxygen holes. Two energy minima are found. The first is in which the local atomic structure is distorted symmetrically about the dopant with the distortion arising from ionic radius differences between copper and titanium. The second is an asymmetric distortion to the geometry.

In the first solution the four equatorial dopant-O distances are equal (2.014 Å (1.956 Å)) for rutile (anatase)) as are the two apical dopant-O distances (1.998 Å (2.002 Å)) for rutile (anatase)). In undoped rutile (anatase), the equatorial/apical Ti-O distances are 1.96/2.00 Å (1.93/1.98 Å). Upon doping, the equatorial and apical Cu-O distances are larger than the equivalent Ti-O distances in undoped TiO₂. The symmetric structure is consistent with delocalisation of the oxygen holes and the result for rutile are similar to those previously reported.[14] Figures 5 (a) and 5 (c) show that with DFT, the oxygen holes formed upon Cu doping are delocalised over all oxygen ions in rutile and more localised in anatase, but still notably delocalised.

The asymmetric solution, with a geometry distortion about the dopant shows non-uniform dopant-O distances. For rutile, there is one elongated Cu-O distance, consistent with a longer bond between Cu and an oxygen hole polaron. This has also been observed in In-doped rutile TiO₂[31] and Li-doped MgO[51] and ZnO[13] among other materials. [52, 61, 63, 68] That the effect is less strong in Cu-doped TiO₂ can be attributed to the presence of a second hole which is less localised, being distributed over oxygen ions neighbouring the dopant as shown by the spin density plot in figure 5 (b). This diminishes the Coulombic attraction and lengthens the cation-O bonds.[69] We find that a solution starting with two fully localised holes relaxes to the partially localised hole distribution just described.

In the case of anatase, the polaron is not bonded directly to the dopant and sits at an equatorial site of a neighbouring Ti (yellow sphere in figure 5 (d)). The polaron induces a significant extension of the Ti-O distance of between 0.07 and 0.1 Å when compared to undoped TiO₂. The second polaron is also partially localised over oxygens near the dopant.

The asymmetric polaronic solution is more stable by 0.5 eV and 0.2 eV in rutile and anatase within the present DFT + U computational set-up. The asymmetric solution is not stable with DFT, consistent with previous work showing that only symmetric solutions are stable with DFT. [31]

The identity of the polaron is further confirmed through the calculated Bader atomic charges and the spin magnetisations. For a polaronic oxygen the computed Bader charge is reduced from 7.4

electrons (lattice O^{2-}) to 6.7 (6.9) electrons for Cu-doped rutile (anatase). The calculated spin magnetisations are 0.85 (0.71) μ_B in rutile (anatase). In rutile, the other five oxygen ions neighbouring the dopant have spin magnetisations in the range of 0.16 to 0.22 μ_B . Similarly, in anatase, five of the six oxygen ions neighbouring the dopant have spin magnetisations in the range of 0.12 to 0.17 μ_B , with a value of 0.33 μ_B on a sixth oxygen, namely lower apical oxygen bonded to the dopant in figure 5(d). The Bader charges of the Cu dopant are 9.6 electrons for rutile and 9.7 electrons for anatase, consistent with the Cu^{2+} oxidation state. [43]

Figures 5 (b) and 5 (d) display the electronic density of states (EDOS) projected onto the Ti and Cu 3d states and the O 2p states. The PEDOS plots show qualitatively similar behaviour for both doped phases. The DFT calculations, with the delocalised symmetric solution, have states associated with the oxygen holes positioned just above the valence band, crossing the Fermi level. For anatase case, in which the polaron is partially localised over oxygen ions near the dopant, even without the +U correction, an O 2p state appears in the gap, just above the VB. These results concur with previous *ab initio* studies of rutile [14] and anatase. [80]

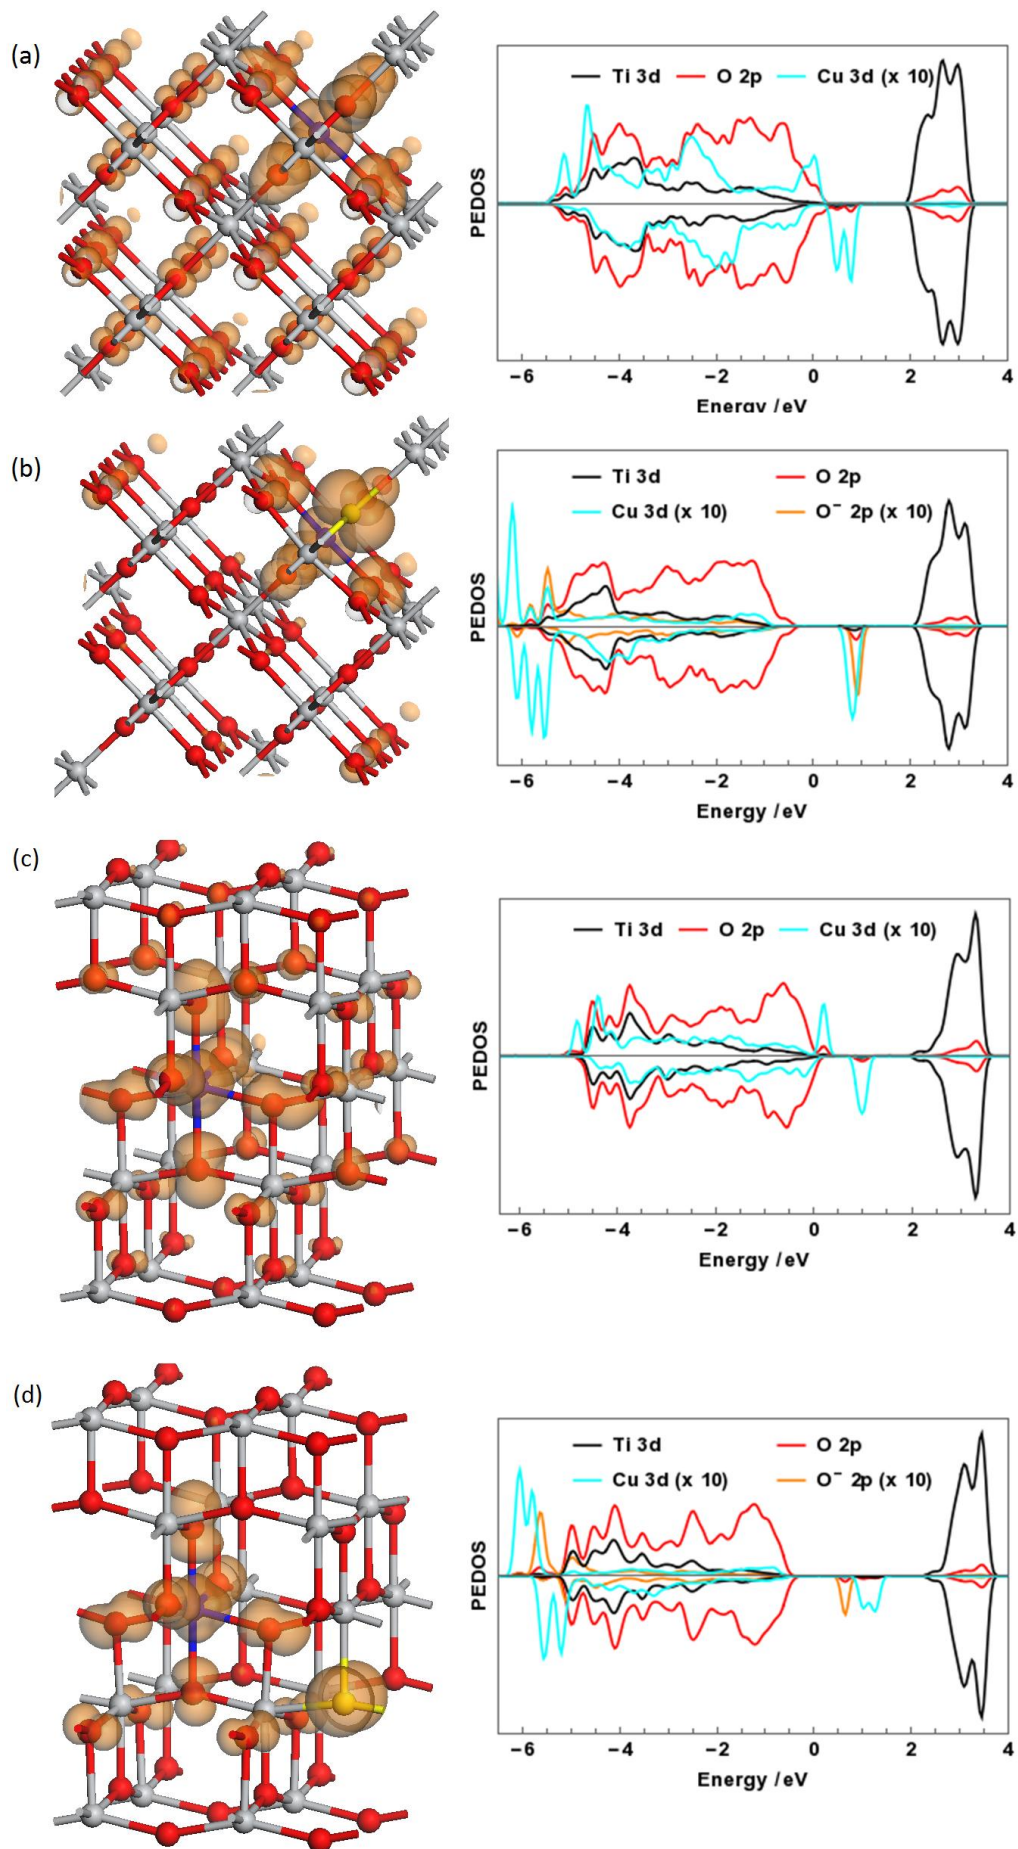


Figure 5: Spin density and EDOS plots for Cu-doped rutile TiO₂ for (a) DFT and (b) DFT + U and Cu-doped anatase TiO₂ for (c) DFT and (d) DFT+U. Cu is represented in blue with yellow marking the position of the oxygen polarons. The spin isosurfaces are set to 0.02 electrons Å⁻¹.

Applying the +U correction to the O 2p, Ti 3d and Cu 3d states, proved necessary to obtain a properly localised polaron description [51, 52, 61] and the PEDOS plots consequently display the typical empty oxygen hole polaron state in the middle of the valence to conduction band energy gap. The onsite Coulomb interaction pushes the defect state into the middle of the gap as opposed to an unoccupied continuum state at the top of the valence band. Considering the Cu 3d states, with DFT the empty Cu 3d states lie just above the valence band edge, while with the +U correction on the Cu 3d states there is clear shift of these states into the energy gap. Examining the position of the empty Cu 3d states, one could conclude that the TiO₂ energy gap could be reduced by up to 0.5 eV upon Cu doping.

The charge compensation mechanism for doping of TiO₂ with lower valence cation dopants is the formation of oxygen vacancies. Therefore, given the 2+ oxidation state of Cu, one neutral oxygen species per Cu is removed from different sites in Cu-doped rutile and anatase. The most stable site for a compensating oxygen vacancy was determined and both apical and equatorial oxygen sites yield negative formation energies of -0.08 (-0.71) eV and -0.42 (-1.20) eV in rutile (anatase). The equatorial vacancies are more favourable. This trend corroborates that found in a previous study of the effect of oxygen vacancies on the magnetic moment of Cu-doped rutile TiO₂. [14]

Figure 6 shows the geometry of the charge compensated structures of Cu-doped TiO₂. For rutile and anatase the copper dopant and two neighbouring titanium ions each coordinate to five oxygens. This under-coordination leads to a distortion, with the titanium ions moving off their lattice sites and outwards from the vacancy site along the direction of the missing bond. This distortion is accompanied by a shortened Ti-O bond to the oxygen ion positioned opposite the vacancy. For rutile, this shortened bond is 1.84 Å compared to 2.02 Å for equivalent bonds away from the vacancy site. In anatase, the Ti-O distances are shortened by up to 0.15 Å. The oxygen vacancy has little effect on the remaining Cu-O bonds.

Figure 6 also shows the excess spin density plots and the associated PEDOS for the compensating oxygen vacancy. The same trend is exhibited in the excess spin density plots of both rutile (figure 6(a)) and anatase (figure 6(b)) in that the excess spin is localized on the Cu dopant. The small spin on four neighbouring oxygens arises from covalency in the Cu-O bonds. The fifth oxygen, in both cases, is that positioned at an equatorial site opposite the vacancy. The computed Bader charges for Cu are 9.7 and 9.8 electrons for rutile and anatase, consistent with a Cu²⁺ oxidation state, which is unaffected by the charge compensation process.

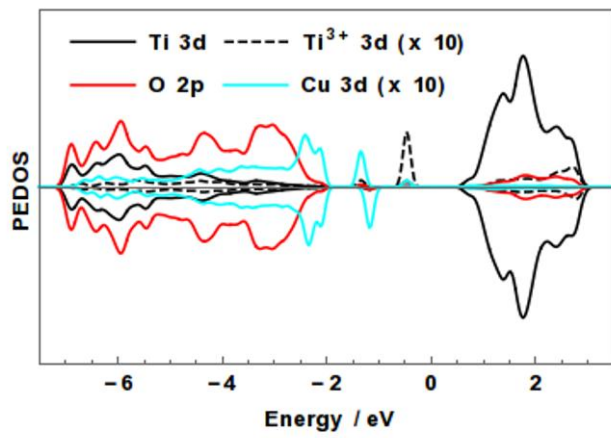
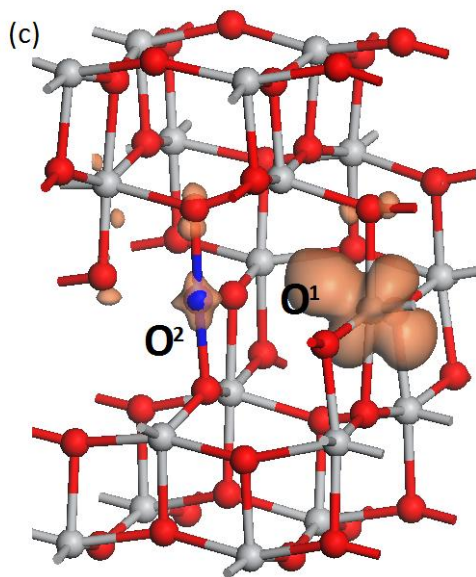
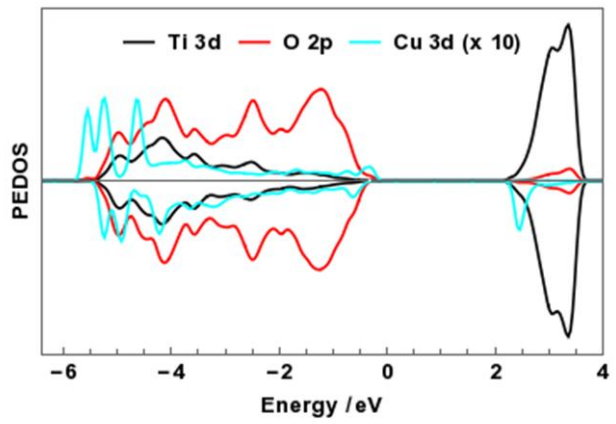
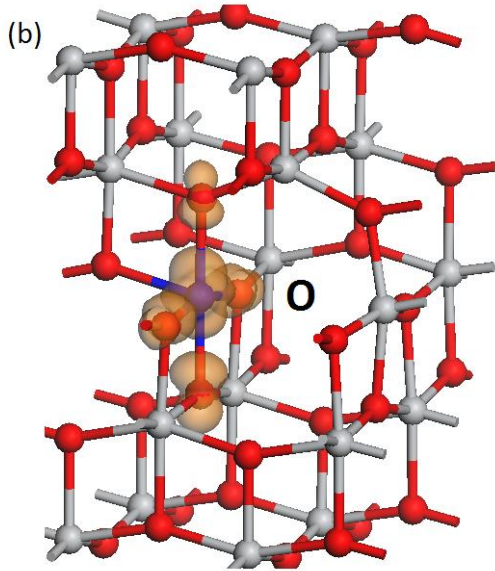
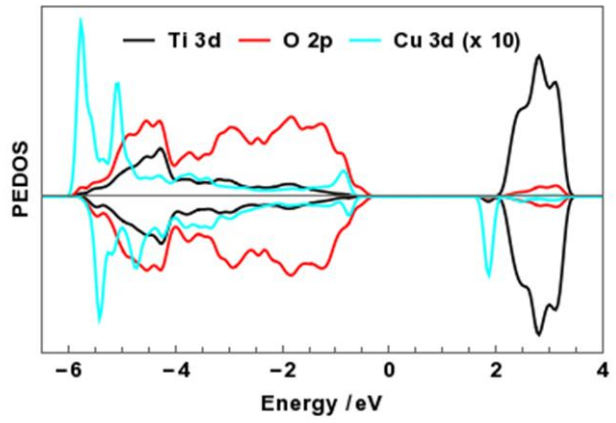
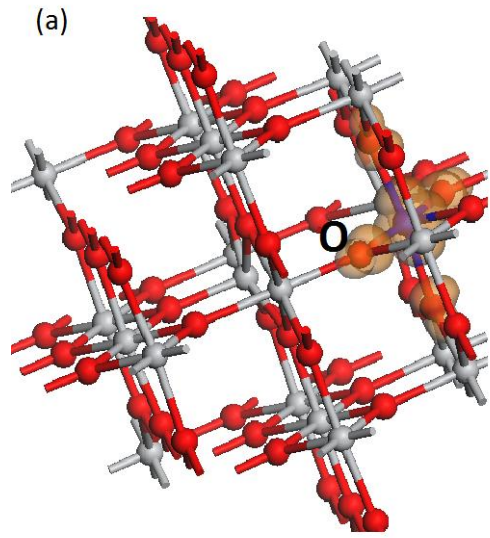


Figure 6: Excess spin density and PEDOS plots of charge compensated Cu-doped (a) rutile and (b) anatase TiO₂. Cu is represented by a blue sphere and the black circle marks the location of the charge compensating oxygen vacancy. (c) Cu-doped anatase with a second, reducing oxygen vacancy, where O¹ and O² indicate the site of the compensating and reducing oxygen vacancies. The spin density isosurface is set to 0.02 electrons Å⁻³.

For both TiO₂ polymorphs, the PEDOS plots are significantly altered upon forming the compensating vacancy. The PEDOS displays a peak attributed to the empty 3d d orbital of the Cu²⁺ oxidation state. For rutile, this peak lies in the gap just below the CB minimum whereas for anatase this peak coincides with the bottom of the CB. For both polymorphs, the charge compensating vacancy thus shifts the Cu 3d states closer to the CB edge of TiO₂. Around the valance band region, Cu-doped anatase shows a filled Cu 3d state above the TiO₂ valence band edge, while for rutile, this state lies below the valence band edge. The empty oxygen hole states disappear after charge compensation.

Thus a small reduction in the band gap at this Cu doping concentration is proposed for rutile and anatase. For rutile, the shift is 0.3 eV and for anatase the proposed band gap decrease is 0.2 eV. Since these results should be regarded with caution given that this DFT+U set-up is not quantitatively describing the band gap of TiO₂, we ran single point hybrid DFT calculations of Cu-doped TiO₂. These use the HSE06 functional, with 25 % Fock exchange and a screening parameter of 0.2 Å⁻¹. The PEDOS in figure 7 for doped anatase shows similar trends as the DFT+U result, despite the differences in the DFT+U and hybrid DFT energy gaps. With no charge compensating oxygen vacancy, the position of Cu 3d and O 2p polaron states are similar to those from DFT+U. With the charge compensating vacancy, the occupied Cu 3d states are similar to those found with DFT+U but the empty Cu 3d states lie above the TiO₂ conduction band edge. This gives a band gap reduction of 0.2 eV, similar to DFT+U. Thus, both DFT approaches appear to suggest that doping with Cu induces only a small, if any, red shift in light absorption.

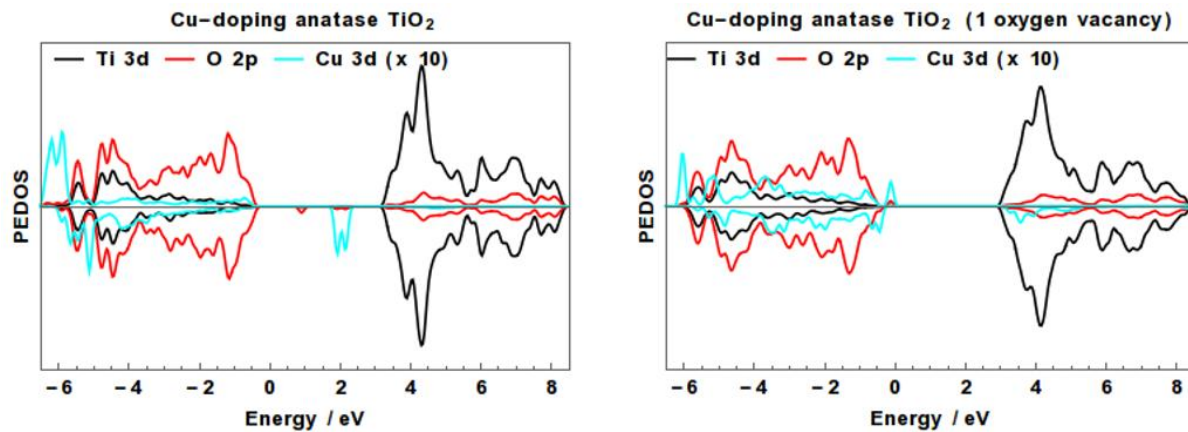


Figure 7: Hybrid DFT PEDOS for Cu-doped TiO₂. Left panel: Cu-doped anatase with no compensating oxygen vacancy, right panel: Cu-doped anatase with the compensating oxygen vacancy.

Finally, the formation of a neutral oxygen vacancy in charge compensated Cu-doped anatase has been studied. This is motivated by the experiments described previously, in which TiO₂ is calcined to over 500°C, at which temperatures the formation of oxygen vacancy defects is likely. We compute a

formation energy of 4.8 eV for the most stable oxygen vacancy site in charge compensated Cu-doped anatase, with the atomic structure, spin density and PEDOS shown in figure 6 (c). We note the high energy cost to form this oxygen vacancy in bulk Cu-doped anatase at 0 K. However, given the elevated temperatures in the experiments, oxygen vacancies will likely be present and we can examine the effect of these vacancies on the electronic properties of Cu-doped anatase. We note that the computed oxygen vacancy formation energy of Cu-doped anatase is higher than that of undoped anatase. This would then inhibit formation of oxygen vacancies and based on the vacancy-promoted mechanism of the anatase-rutile phase transition, Cu doping would then increase the temperature at which the phase transition takes place, consistent with experimental findings.

The computed Bader charge on Cu is 10.4 electrons, with a spin of 0.1 μ_B , which is consistent with reduction to Cu^+ . One Ti cation has a Bader charge of 1.71 electrons and a spin of 0.95 μ_B , which is consistent with a Ti^{3+} cation (all other Ti cations are Ti^{4+} with computed Bader charges of 1.24 electrons). The formation of a neutral oxygen vacancy thus reduces one Ti cation to Ti^{3+} and the Cu dopant to Cu^+ . Comparing with the XPS data, this is consistent with the assignment of reduced Cu^{1+} at elevated temperatures. The decrease in peak intensities of the Cu^{2+} satellites with increasing temperature is also consistent with Cu^{2+} reduction by oxygen vacancy formation. Finally, the PEDOS in figure 6 (c) shows the introduction of occupied Cu^+ states in the TiO_2 valence-conduction band energy gap. These states can enhance charge recombination after excitation that could result in reduced photocatalytic activity; this is discussed in the following section.

3.7 Photocatalytic Analysis

The adsorption of 1,4-dioxane onto the Cu-doped TiO_2 catalyst surface did not exceed 10% in the dark control experiments, where the catalyst was added without applying solar light; as well as in the control trials applying radiation without adding the catalyst (figure 8). Here we examined samples with all Cu concentrations and calcined at 600°C & 650°C.

The highest degradation of 1,4-dioxane was achieved by adding TiO_2 prepared at 500°C without Cu doping. Increasing the temperature to 600 or 650°C limited the extent of 1,4-dioxane degradation (figure 8 and figures S7 and S8). The inclusion of Cu does not, therefore, result in any improvement of the photocatalytic activity of TiO_2 (figure 8, S7 and S8). This is also irrespective of the polymorph of TiO_2 present as a result of Cu-doping and calcination temperature. Thus, while Cu doping can be used to control the stability of anatase TiO_2 , its incorporation has the effect of reducing photocatalytic activity.

This behaviour agrees with previous studies, in which Cu-doping did not always report an improvement of the photocatalytic efficiency of Cu- TiO_2 even being anatase phase [10, 42, 74] This is usually attributed to the recombination of electron-hole at defect centres. This process is favoured by the presence of Cu within the TiO_2 catalyst; as well as to the prevention of photon absorption by TiO_2 due to the presence of Cu. [74] Moreover, Colon et al. [10] reported that deactivation may be caused by the formation of CuO species at the surface of the catalyst. [10] Cu^{2+} , identified by XPS in TiO_2 calcinated at 600 and 650°C, would impact on photocatalytic activity through migration of a photogenerated electron from the conduction band of TiO_2 , which prevents the generation of

OH·.[10] In addition, Lopes et al. reported higher activity of the catalysts with the lowest copper content due to a higher Cu(I)/Cu(0) ratio. [10]

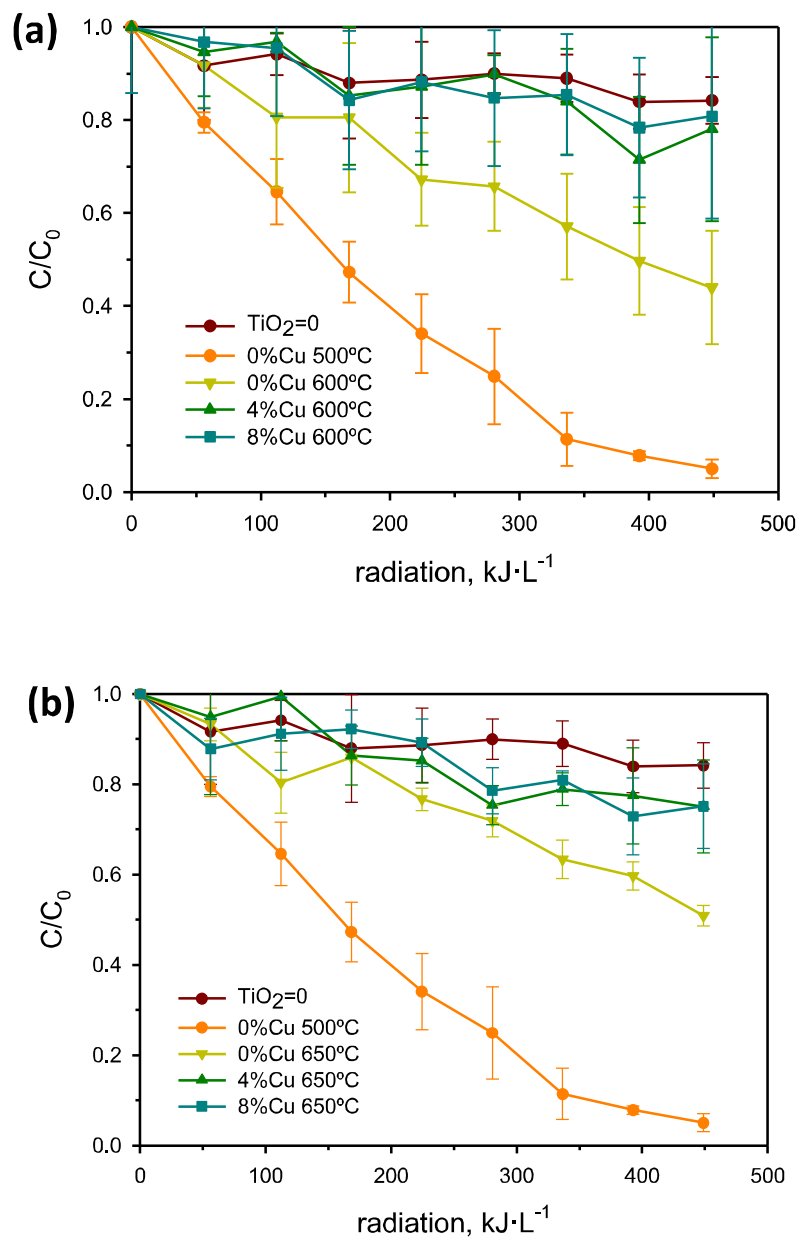


Figure 8: Degradation of 1,4-dioxane by Cu-doped TiO_2 photocatalysis at (a) 600°C and (b) 650°C compared with TiO_2 prepared at 500°C and radiation without catalyst.

In contrast to this study, a number of studies have found an increase of photocatalytic activity when using copper nitrate as the copper precursor. [22, 40, 42, 45, 48, 78] For example, López *et al.* (2009) found that the photodegradation of dichlorophenoxyacetic acid was enhanced with the inclusion of copper, compared with bare titania. They concluded that the increased photocatalytic activity was due to the stabilisation of Cu^+ by TiO_2 . [42] Another example is the study by Fisher *et al.* [77] in which the effect of copper doping (with a copper nitrate precursor) and Cu-N co-doping on TiO_2 were

explored. These authors found that there was improved activity for both all doped samples compared to bare titania when examining the photocatalytic degradation of methylene blue and the inactivation of microbiological materials. [22]

4. Conclusions

Cu-doped TiO₂ was synthesised using a modified sol-gel method to explore the effect of Cu-doping of anatase TiO₂ on the transition to rutile at elevated temperatures. Samples were calcined between 500 and 800°C. We find that in comparison to the control (0% Cu) the copper doped samples improve the stabilisation of anatase at elevated temperatures, thus shifting the transition temperature higher. Doping with 8% Cu was found to be optimum. At 600°C, the control sample (with 0% Cu) contained 34.3% anatase while at the same temperature; all doped samples were 100% anatase. At 650°C, the 4% and 8% Cu-TiO₂ had anatase contents of 27.3% and 74.3% respectively. All samples heated to 700°C were 100% rutile. XPS showed no indication of Ti-Cu binding, only Ti-O binding was present. XPS was also used for determining that the increase in temperature resulted in copper being reduced from Cu²⁺ to Cu¹⁺.

The doping of bulk rutile and anatase TiO₂ with Cu was investigated using different DFT approaches. We have shown that charge compensating oxygen vacancies form to balance the lower +2 oxidation state of Cu. The density of states shows localised peaks near the valence and conduction band edges, arising from the empty Cu 3d state of Cu²⁺. These result in a predicted small red shift in the adsorption edge. While oxygen vacancy formation shows a high computed formation energy compared to undoped anatase, the high temperature calcination will promote oxygen vacancy formation in Cu-doped TiO₂. This inhibits the vacancy-drive transition from anatase to rutile, pushing the transition to higher temperatures. Formation of reducing oxygen vacancies reduces Cu²⁺ to Cu⁺ and Ti⁴⁺ to Ti³⁺ with a localised Cu-derived gap state that can act as a recombination centre and degrade the photocatalytic activity of anatase.

Photocatalysis studies, using 1,4-dioxane, indicated that inclusion of copper induced a significant reduction in the rate of photodegradation. The sample that showed the most photocatalytic activity was the 0% Cu-TiO₂ (100% anatase), which showed a 1,4-dioxane removal of approx. 90% after 450kJL⁻¹ (240 minutes). All copper doped samples showed 1,4-dioxane removal of between 20-40% over the same time and radiation. When we compare these findings to the results from the DFT studies, we propose that the reduction in activity over undoped TiO₂ most likely arises from the presence of the Cu⁺/Cu²⁺-induced defect states described in Section 3.6 which act as traps for charges and thus promote recombination.

Acknowledgements

SR and MN acknowledge support from Science Foundation Ireland (SFI) through the US-Ireland R&D Partnership Program, grant number SFI 14/US/E2915 and the European Commission through the COST Action CM1104 "Reducible Metal Oxides, Structure and Function". We acknowledge access to computing resources at Tyndall provided by SFI and by the SFI and Higher Education Authority funded Irish Centre for High End Computing. CB, LM and SP would like to acknowledge access to Raman Spectroscopy at Centre for Research in Engineering Surface Technology (CREST), FOCAS

Institute, Dublin Institute of Technology, Kevin Street. CB & PG would like to acknowledge the Institute of Technology Sligo President's Bursary for providing financial support. DH would like to acknowledge the Universidad de Valladolid for granting the stay at the Institute of Technology Sligo. DH would also to thank Ministerio de Economía y Competitividad of Spain (research grant number: CTM2016-77948-R) for providing research funding.

References

- [1] R. Arroyo, G. Cordoba, J. Padilla, V. Lara, Influence of manganese ions on the anatase–rutile phase transition of TiO₂ prepared by the sol–gel process, *Materials Letters* 54 (2002) 397-402.
- [2] H. Berger, H. Tang, F. Lévy, Growth and Raman spectroscopic characterization of TiO₂ anatase single crystals, *Journal of crystal growth* 130 (1993) 108-112.
- [3] P.E. Blöchl, Projector augmented-wave method, *Physical Review B* 50 (1994) 17953-17979.
- [4] Y. Boyjoo, H. Sun, J. Liu, V.K. Pareek, S. Wang, A review on photocatalysis for air treatment: From catalyst development to reactor design, *Chemical Engineering Journal* 310 (2017) 537-559.
- [5] C. Byrne, R. Fagan, S. Hinder, D.E. McCormack, S.C. Pillai, New approach of modifying the anatase to rutile transition temperature in TiO₂ photocatalysts, *RSC Advances* 6 (2016) 95232-95238.
- [6] J.J. Carey, M. Nolan, Dissociative adsorption of methane on the Cu and Zn doped (111) surface of CeO₂, *Applied Catalysis B: Environmental* 197 (2016) 324-336.
- [7] O. Carp, C.L. Huisman, A. Reller, Photoinduced reactivity of titanium dioxide, *Progress in Solid State Chemistry* 32 (2004) 33-177.
- [8] R. Chand, E. Obuchi, K. Katoh, H.N. Luitel, K. Nakano, Enhanced photocatalytic activity of TiO₂/SiO₂ by the influence of Cu-doping under reducing calcination atmosphere, *Catalysis Communications* 13 (2011) 49-53.
- [9] H. Choi, M.G. Antoniou, M. Pelaez, A.A. De la Cruz, J.A. Shoemaker, D.D. Dionysiou, Mesoporous nitrogen-doped TiO₂ for the photocatalytic destruction of the cyanobacterial toxin microcystin-LR under visible light irradiation, *Environmental science & technology* 41 (2007) 7530-7535.
- [10] G. Colón, M. Maicu, M.C. Hidalgo, J.A. Navío, Cu-doped TiO₂ systems with improved photocatalytic activity, *Applied Catalysis B: Environmental* 67 (2006) 41-51.
- [11] A. Czoska, S. Livraghi, M. Chiesa, E. Giamello, S. Agnoli, G. Granozzi, E. Finazzi, C.D. Valentin, G. Pacchioni, The nature of defects in fluorine-doped TiO₂, *The Journal of Physical Chemistry C* 112 (2008) 8951-8956.
- [12] R.F. de Farias, C.C. Silva, T.A. Restivo, Thermal study of the anatase-rutile structural transitions in sol-gel synthesized titanium dioxide powders, *Journal of the Serbian Chemical Society* 70 (2005) 675-679.
- [13] M.-H. Du, S.B. Zhang, Impurity-bound small polarons in ZnO: Hybrid density functional calculations, *Physical Review B* 80 (2009) 115217.
- [14] S. Duhalde, M.F. Vignolo, F. Golmar, C. Chilotte, C.E.R. Torres, L.A. Errico, A.F. Cabrera, M. Rentería, F.H. Sánchez, M. Weissmann, Appearance of room-temperature ferromagnetism in Cu-doped $\{\text{TiO}\}_2$ films, *Physical Review B* 72 (2005) 161313.
- [15] D. Dvoranová, V. Brezová, M. Mazúr, M.A. Malati, Investigations of metal-doped titanium dioxide photocatalysts, *Applied Catalysis B, Environmental* 37 (2002) 91-105.

- [16] V. Etacheri, G. Michlits, M.K. Seery, S.J. Hinder, S.C. Pillai, A Highly Efficient TiO₂-x C x Nano-heterojunction Photocatalyst for Visible Light Induced Antibacterial Applications, *ACS applied materials & interfaces* 5 (2013) 1663-1672.
- [17] V. Etacheri, G. Michlits, M.K. Seery, S.J. Hinder, S.C. Pillai, A Highly Efficient TiO₂-x C x Nano-heterojunction Photocatalyst for Visible Light Induced Antibacterial Applications, *ACS applied materials & interfaces* 5 (2013) 1663-1672.
- [18] V. Etacheri, M.K. Seery, S.J. Hinder, S.C. Pillai, Highly Visible Light Active TiO₂- x N x Heterojunction Photocatalysts†, *Chemistry of Materials* 22 (2010) 3843-3853.
- [19] V. Etacheri, M.K. Seery, S.J. Hinder, S.C. Pillai, Oxygen Rich Titania: A Dopant Free, High Temperature Stable, and Visible-Light Active Anatase Photocatalyst, *Advanced Functional Materials* 21 (2011) 3744-3752.
- [20] R. Fagan, D.E. McCormack, D.D. Dionysiou, S.C. Pillai, A review of solar and visible light active TiO₂ photocatalysis for treating bacteria, cyanotoxins and contaminants of emerging concern, *Materials Science in Semiconductor Processing* (2015).
- [21] X. Fang, Z. Zhang, Q. Chen, H. Ji, X. Gao, Dependence of nitrogen doping on TiO₂ precursor annealed under NH₃ flow, *Journal of Solid State Chemistry* 180 (2007) 1325-1332.
- [22] M.B. Fisher, D.A. Keane, P. Fernandez-Ibanez, J. Colreavy, S.J. Hinder, K.G. McGuigan, S.C. Pillai, Nitrogen and copper doped solar light active TiO₂ photocatalysts for water decontamination, *Applied Catalysis B: Environmental* 130 (2013) 8-13.
- [23] A. Fujishima, K. Honda, Photolysis-decomposition of water at the surface of an irradiated semiconductor, *Nature* 238 (1972) 37-38.
- [24] A. Fujishima, X. Zhang, Titanium dioxide photocatalysis: present situation and future approaches, *Comptes Rendus Chimie* 9 (2006) 750-760.
- [25] H. Gao, G. Wang, Y. Luan, K. Chaikittikul, X. Zhang, M. Yang, W. Dong, Z. Shi, A fast synthesis of hierarchical yolk-shell copper hydroxysulfates at room temperature with adjustable sizes, *CrystEngComm* 16 (2014) 2520-2526.
- [26] D.A. Hanaor, C.C. Sorrell, Review of the anatase to rutile phase transformation, *Journal of Materials science* 46 (2011) 855-874.
- [27] G. Henkelman, A. Arnaldsson, H. Jónsson, A fast and robust algorithm for Bader decomposition of charge density, *Computational Materials Science* 36 (2006) 354-360.
- [28] K.C. HEO, C.I. OK, J.W. KIM, B.K. MOON, The effects of manganese ions and their magnetic properties on the anatase-rutile phase transition of nanocrystalline TiO₂: Mn prepared by using the solvothermal method, *Journal of the Korean Physical Society* 47 (2005) 861-865.
- [29] Y. Hu, H.L. Tsai, C.L. Huang, Effect of brookite phase on the anatase-rutile transition in titania nanoparticles, *Journal of the European Ceramic Society* 23 (2003) 691-696.
- [30] H. Irie, Y. Watanabe, K. Hashimoto, Carbon-doped anatase TiO₂ powders as a visible-light sensitive photocatalyst, *Chemistry Letters* 32 (2003) 772-773.
- [31] A. Iwaszuk, M. Nolan, Charge compensation in trivalent cation doped bulk rutile TiO₂, *Journal of Physics: Condensed Matter* 23 (2011) 334207.
- [32] R. Janes, L. Knightley, C. Harding, Structural and spectroscopic studies of iron (III) doped titania powders prepared by sol-gel synthesis and hydrothermal processing, *Dyes and pigments* 62 (2004) 199-212.
- [33] S. Karvinen, The effects of trace elements on the crystal properties of TiO₂, *solid state sciences* 5 (2003) 811-819.
- [34] S. Kelemen, G. George, M. Gorbaty, Direct determination and quantification of sulphur forms in heavy petroleum and coals: 1. The X-ray photoelectron spectroscopy (XPS) approach, *Fuel* 69 (1990) 939-944.
- [35] L. Kőrösi, S. Papp, J. Ménesi, E. Illés, V. Zöllmer, A. Richardt, I. Dékány, Photocatalytic activity of silver-modified titanium dioxide at solid-liquid and solid-gas interfaces, *Colloids and Surfaces A: Physicochemical and Engineering Aspects* 319 (2008) 136-142.

- [36] P.M. Kowalski, M.F. Camellone, N.N. Nair, B. Meyer, D. Marx, Charge Localization Dynamics Induced by Oxygen Vacancies on the $\text{TiO}_2(110)$ Surface, *Physical Review Letters* 105 (2010) 146405.
- [37] G. Kresse, J. Furthmüller, Efficiency of Ab-initio Total Energy Calculations for Metals and Semiconductors using a Plane-wave Basis Set, *Computational Materials Science* 6 (1996) 15-50.
- [38] G. Kresse, J. Furthmüller, Efficient Iterative Schemes for Ab-initio Total-energy Calculations using a Plane-wave Basis Set, *Physical Review B* 54 (1996) 11169.
- [39] G. Kresse, D. Joubert, From ultrasoft pseudopotentials to the projector augmented-wave method, *Physical Review B* 59 (1999) 1758-1775.
- [40] K. Lalitha, G. Sadanandam, V.D. Kumari, M. Subrahmanyam, B. Sreedhar, N.Y. Hebalkar, Highly stabilized and finely dispersed $\text{Cu}_2\text{O}/\text{TiO}_2$: a promising visible sensitive photocatalyst for continuous production of hydrogen from glycerol: water mixtures, *The Journal of Physical Chemistry C* 114 (2010) 22181-22189.
- [41] Y. Liu, P. Bailey, T.C. Noakes, G.E. Thompson, P. Skeldon, M.R. Alexander, Chemical environment of copper at the surface of a CuAl_2 model alloy: XPS, MEIS and TEM analyses, *Surface and interface analysis* 36 (2004) 339-346.
- [42] R. López, R. Gómez, M.E. Llanos, Photophysical and photocatalytic properties of nanosized copper-doped titania sol-gel catalysts, *Catalysis Today* 148 (2009) 103-108.
- [43] Y. Maimaiti, M. Nolan, S.D. Elliott, Reduction mechanisms of the $\text{CuO}(111)$ surface through surface oxygen vacancy formation and hydrogen adsorption, *Physical Chemistry Chemical Physics* 16 (2014) 3036-3046.
- [44] N. McIntyre, S. Sunder, D. Shoesmith, F. Stanchell, Chemical information from XPS—applications to the analysis of electrode surfaces, *Journal of Vacuum Science and Technology* 18 (1981) 714-721.
- [45] M.M. Momeni, Y. Ghayeb, Z. Ghonchehi, Fabrication and characterization of copper doped TiO_2 nanotube arrays by in situ electrochemical method as efficient visible-light photocatalyst, *Ceramics International* 41 (2015) 8735-8741.
- [46] B.J. Morgan, G.W. Watson, A DFT + U description of oxygen vacancies at the TiO_2 rutile (1 1 0) surface, *Surface Science* 601 (2007) 5034-5041.
- [47] M. Ni, M.K. Leung, D.Y. Leung, K. Sumathy, A review and recent developments in photocatalytic water-splitting using TiO_2 for hydrogen production, *Renewable and Sustainable Energy Reviews* 11 (2007) 401-425.
- [48] H. Nishikiori, T. Sato, S. Kubota, N. Tanaka, Y. Shimizu, T. Fujii, Preparation of Cu-doped TiO_2 via refluxing of alkoxide solution and its photocatalytic properties, *Research on Chemical Intermediates* 38 (2012) 595-613.
- [49] M. Nolan, S.D. Elliott, The p-type conduction mechanism in Cu_2O : a first principles study, *Physical Chemistry Chemical Physics* 8 (2006) 5350-5358.
- [50] M. Nolan, S.D. Elliott, J.S. Mulley, R.A. Bennett, M. Basham, P. Mulheran, Electronic structure of point defects in controlled self-doping of the $\text{TiO}_2(110)$ surface: Combined photoemission spectroscopy and density functional theory study, *Physical Review B* 77 (2008) 235424.
- [51] M. Nolan, G.W. Watson, The electronic structure of alkali doped alkaline earth metal oxides: Li doping of MgO studied with DFT-GGA and GGA+U, *Surface science* 586 (2005) 25-37.
- [52] M. Nolan, G.W. Watson, Hole localization in Al doped silica: a DFT+ U description, *The Journal of chemical physics* 125 (2006) 144701.
- [53] N.T. Nolan, M.K. Seery, S.J. Hinder, L.F. Healy, S.C. Pillai, A systematic study of the effect of silver on the chelation of formic acid to a titanium precursor and the resulting effect on the anatase to rutile transformation of TiO_2 , *The Journal of Physical Chemistry C* 114 (2010) 13026-13034.

- [54] T. Ohsaka, F. Izumi, Y. Fujiki, Raman spectrum of anatase, TiO₂, *Journal of Raman spectroscopy* 7 (1978) 321-324.
- [55] A. Okasha, F. Gomaa, H. Elhaes, M. Morsy, S. El-Khodary, A. Fakhry, M. Ibrahim, Spectroscopic analyses of the photocatalytic behavior of nano titanium dioxide, *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy* 136 (2015) 504-509.
- [56] F.E. Oropeza, J. Harmer, R. Egdell, R.G. Palgrave, A critical evaluation of the mode of incorporation of nitrogen in doped anatase photocatalysts, *Physical Chemistry Chemical Physics* 12 (2010) 960-969.
- [57] S.C. Padmanabhan, S.C. Pillai, J. Colreavy, S. Balakrishnan, D.E. McCormack, T.S. Perova, Y. Gun'ko, S.J. Hinder, J.M. Kelly, A simple sol-gel processing for the development of high-temperature stable photoactive anatase titania, *Chemistry of Materials* 19 (2007) 4474-4481.
- [58] P. Periyat, S.C. Pillai, D.E. McCormack, J. Colreavy, S.J. Hinder, Improved high-temperature stability and sun-light-driven photocatalytic activity of sulfur-doped anatase TiO₂, *The Journal of Physical Chemistry C* 112 (2008) 7644-7652.
- [59] S.C. Pillai, P. Periyat, R. George, D.E. McCormack, M.K. Seery, H. Hayden, J. Colreavy, D. Corr, S.J. Hinder, Synthesis of high-temperature stable anatase TiO₂ photocatalyst, *The Journal of Physical Chemistry C* 111 (2007) 1605-1611.
- [60] S. Sakthivel, H. Kisch, Daylight photocatalysis by carbon-modified titanium dioxide, *Angewandte Chemie International Edition* 42 (2003) 4908-4911.
- [61] D.O. Scanlon, A. Walsh, B.J. Morgan, M. Nolan, J. Fearon, G.W. Watson, Surface sensitivity in lithium-doping of MgO: a density functional theory study with correction for on-site Coulomb interactions, *The Journal of Physical Chemistry C* 111 (2007) 7971-7979.
- [62] P. Scherrer, Bestimmung der Grösse und der inneren Struktur von Kolloidteilchen mittels Röntgenstrahlen, *Nachrichten von der Gesellschaft der Wissenschaften zu Göttingen, mathematisch-physikalische Klasse* 1918 (1918) 98-100.
- [63] O.F. Schirmer, O – bound small polarons in oxide materials, *Journal of Physics: Condensed Matter* 18 (2006) R667.
- [64] G. Schön, ESCA studies of Cu, Cu₂O and CuO, *Surface Science* 35 (1973) 96-108.
- [65] N. Shaham-Waldmann, Y. Paz, Away from TiO₂: a critical minireview on the developing of new photocatalysts for degradation of contaminants in water, *Materials Science in Semiconductor Processing* 42 (2016) 72-80.
- [66] R.V. Siriwardane, J.A. Poston Jr, E.P. Fisher, M.-S. Shen, A.L. Miltz, Decomposition of the sulfates of copper, iron (II), iron (III), nickel, and zinc: XPS, SEM, DRIFTS, XRD, and TGA study, *Applied Surface Science* 152 (1999) 219-236.
- [67] R.A. Spurr, H. Myers, Quantitative analysis of anatase-rutile mixtures with an X-ray diffractometer, *Analytical Chemistry* 29 (1957) 760-762.
- [68] A.M. Stoneham, J. Gavartin, A.L. Shluger, A.V. Kimmel, D.M. Ramo, H.M. Rønnow, G. Aeppli, C. Renner, Trapping, self-trapping and the polaron family, *Journal of Physics: Condensed Matter* 19 (2007) 255208.
- [69] B.R. Strohmeier, D.E. Levden, R.S. Field, D.M. Hercules, Surface spectroscopic characterization of CuAl₂O₃ catalysts, *Journal of Catalysis* 94 (1985) 514-530.
- [70] H. Tang, K. Prasad, R. Sanjines, P. Schmid, F. Levy, Electrical and optical properties of TiO₂ anatase thin films, *Journal of applied physics* 75 (1994) 2042-2047.
- [71] H. Tao, X. Liang, Q. Zhang, C.-T. Chang, Enhanced photoactivity of graphene/titanium dioxide nanotubes for removal of Acetaminophen, *Applied Surface Science* 324 (2015) 258-264.
- [72] T. Theivasanthi, M. Alagar, X-ray diffraction studies of copper nanopowder, arXiv preprint arXiv:1003.6068 (2010).
- [73] W.-K. Wang, J.-J. Chen, X. Zhang, Y.-X. Huang, W.-W. Li, H.-Q. Yu, Self-induced synthesis of phase-junction TiO₂ with a tailored rutile to anatase ratio below phase transition temperature, *Scientific reports* 6 (2016) 20491.

- [74] R.S. Wong, J. Feng, X. Hu, P.L. Yue, Discoloration and mineralization of non-biodegradable azo dye orange II by copper-doped TiO₂ nanocatalysts, *Journal of Environmental Science and Health, Part A* 39 (2004) 2583-2595.
- [75] H.M. Yadav, S.V. Otari, V.B. Koli, S.S. Mali, C.K. Hong, S.H. Pawar, S.D. Delekar, Preparation and characterization of copper-doped anatase TiO₂ nanoparticles with visible light photocatalytic antibacterial activity, *Journal of Photochemistry and Photobiology A: Chemistry* 280 (2014) 32-38.
- [76] J. Yang, H. Bai, X. Tan, J. Lian, IR and XPS investigation of visible-light photocatalysis—Nitrogen—carbon-doped TiO₂ film, *Applied Surface Science* 253 (2006) 1988-1994.
- [77] L. Yoong, F.K. Chong, B.K. Dutta, Development of copper-doped TiO₂ photocatalyst for hydrogen production under visible light, *Energy* 34 (2009) 1652-1661.
- [78] L. Yoong, F.K. Chong, B.K. Dutta, Development of copper-doped TiO₂ photocatalyst for hydrogen production under visible light, *Energy* 34 (2009) 1652-1661.
- [79] L.S. Yoong, F.K. Chong, B.K. Dutta, Development of copper-doped TiO₂ photocatalyst for hydrogen production under visible light, *Energy* 34 (2009) 1652-1661.
- [80] H. Zhang, X. Yu, J.A. McLeod, X. Sun, First-principles study of Cu-doping and oxygen vacancy effects on TiO₂ for water splitting, *Chemical Physics Letters* 612 (2014) 106-110.
- [81] S. Zhou, K. Potzger, G. Talut, J. von Borany, W. Skorupa, M. Helm, J. Fassbender, Using x-ray diffraction to identify precipitates in transition metal doped semiconductors, *Journal of Applied Physics* 103 (2008) 07D530.