

Modelling of Experimental Tests of Wooden Specimens from Scots Pine (*Pinus sylvestris*) with the Help of Anisotropic Plasticity Material Model

Modeliranje eksperimentalnih ispitivanja uzoraka izrađenih od drva običnog bora (*Pinus sylvestris*) uz pomoć modela za anizotropno-plastične materijale

Original scientific paper • Izvorni znanstveni rad

Received – prispjelo: 9. 12. 2013.

Accepted – prihvaćeno: 14. 1. 2015.

*UDK: 630*812.702; 674.032.475.442*

doi:10.5552/drind.2015.1362

ABSTRACT • *In order to describe the behaviour of wood when calculating wooden elements and structures with the use of the finite element method, orthotropic material model in combination with non-interactive (maximum stress criterion) or interactive failure criteria (Hoffman and Tsai-Wu criterion) is used. Another option is to use a general anisotropic plasticity material model complemented with a non-interactive failure criterion – maximum stress criterion, which allows to describe wood failure by brittle failure in tension. The presented general material model was used in combination with the idealization of annual rings by cylindrical surface for the modelling of wood specimen tests from Scots pine (*Pinus sylvestris*). The obtained results show good agreement between the results of numerical analysis and experimental testing of wood specimens. The use of the anisotropic material model can also be seen in cases when the level of the applied load is higher than the level when the failure of wooden material occurs.*

Key words: *Scots pine (*Pinus sylvestris*), FEA, numerical modelling, elastic constants, material constants, anisotropic plasticity*

SAŽETAK • *Radi objašnjenja ponašanja drva pri proračunima drvnih elemenata i konstrukcija primjenom metode konačnih elemenata, upotrijebljen je model ortotropnog materijala u kombinaciji s neinteraktivnim kriterijem (kriterij maksimalnog naprezanja) ili interaktivnim kriterijima loma (Hoffmanov i Tsai-wuov kriterij). Druga je mogućnost upotrijebiti opći model za anizotropno-plastične materijale dopunjen neinteraktivnim kriterijem loma – kriterijem maksimalnog naprezanja, koji omogućuje objašnjenje lomljivosti drva pri naprezanju. Predstavljene opći model materijala u kombinaciji s idealizacijom godova kao cilindričnih površina upotrijebljen je za modeli-*

¹ Author is assistant professor at Brno University of Technology, Faculty of Civil Engineering, Institute of Building Structures, Brno, Czech Republic.

¹ Autor je docent Tehnološkog sveučilišta u Brnu, Građevinski fakultet, Zavod za građevinske konstrukcije, Brno, Republika Češka.

ranje uzoraka izrađenih od drva običnog bora (*Pinus sylvestris*). Dobiveni rezultati pokazuju dobru podudarnost rezultata numeričke analize i rezultata eksperimentalnih ispitivanja uzoraka drva. Model anizotropnog materijala primjenjiv je i kada je opterećenje veće od onoga pri kojemu dolazi do loma drvnog materijala.

Ključne riječi: obični bor (*Pinus sylvestris*), FEA, numeričko modeliranje, elastične konstante, materijalne konstante, anizotropna plastičnost

1 INTRODUCTION

1. UVOD

Despite the high abundance of Scots pine (*Pinus sylvestris*) in mild and colder Eurasia climate (Úradníček *et al.*, 2001; 2012a), few literature sources contain information on elastic and material constants of this tree species, which could be used for an analysis with the use of anisotropic plasticity material model. Anisotropic plasticity material model defined by 9 elastic and 18 material constants is described by Moses and Prion (2004) as a general material model, which allows to define different bilinear elasto-plastic behaviour with possible hardening of material in three perpendicular directions, including the definition of different behaviour in these directions in tension, compression, and shear.

Elastic and material constants are predominantly specified for Loblolly pine (*Pinus taeda*) (Bergman *et al.*, 2010; Bodig and Goodman, 1973; Morais *et al.*, 2001; Jeong *et al.*, 2010) and for Douglas fir (*Douglas fir*) (Bergman *et al.*, 2010; Bodig and Goodman, 1973; Winandy, 1994; Nairin, 2007; Kim and Harries, 2010).

Elastic constants for Scots pine (*Pinus sylvestris*), shown by Bodig and Goodman (1973) and Martin and Berger (2001), are based on a special report produced by R. F. S. Hearmon (Hearmon, 1948). Elastic constants for Scots pine used for the modelling of a section of a wooden string staircase and stair joints are also presented by Pousette (2006). Elastic and material constants of Scots pine are shown by Danielsson and Gustafsson (2013), who used these constants for the modelling of a double cantilever beam (DCB) and end-notched beams. According to Danielsson and Gustafsson (2013), the specified constants are in compliance with the values for Norway spruce (*Picea abies*). The values of elastic and material constants of Scots pine are shown in the papers of Matovič (1993) and Požgaj *et al.* (1997; 2004).

For the purpose of the numerical analysis of a prefabricated suspended staircase from Scots pine (Pěňčík, 2013), elastic and material constants of the Scots pine were selected with the use of results presented in the papers of Matovič (1993) and Požgaj *et al.* (1997; 2004). The constants are shown in Table 1, where E is modulus of elasticity in material directions (longitudinal $L - E_L$, radial $R - E_R$ and tangential $T - E_T$), G is shear modulus in material planes (G_{RT} , G_{LT} , G_{LR}), ν Poisson's ratio (ν_{RT} , ν_{LT} , ν_{LR}), f_{Li} , f_{Ri} , f_{Ti} are strengths in tension and f_{Lc} , f_{Rc} , f_{Tc} are strengths in compression in material directions L , R and T , f_{LR} , f_{LT} , f_{RT} are shear strengths in material planes.

The elastic constants (Table 1) were selected taking into account the meeting of criteria presented in relation (1) (Gillis, 1972; Hallai, 2008) and in relation (2) (Xavier, 2007), which express their inter-relation.

$$E_L > E_R > G_{LR} \approx G_{LT} > E_T > G_{RT} \quad (1)$$

$$E_L \gg E_R > E_T, G_{LR} > G_{LT} \gg G_{RT}, \nu_{LR} > \nu_{LT} > \nu_{RT} \quad (2)$$

The verification of elastic and material constants (Table 1) was performed by a numerical modelling of experimental testing with the use of finite element calculation using software ANSYS (ANSYS, 2012a).

2 MATERIAL AND METHODS

2. MATERIJAL I METODE

2.1 Experimental testing

2.1. Eksperimentalno ispitivanje

Wooden specimens made of Scots pine (*Pinus sylvestris*) were prepared in compliance with ČSN EN 408. The dimensions of the cross section – width (b) and height (h) and length (L) of specimens were selected in compliance with the requirements of ČSN EN 408; $b \times h \times L = 25 \times 25 \times 475$ mm. Before the testing, the specimens were conditioned in a standard environment at the temperature of 20 ± 2 °C and relative

Table 1 Elastic and material constants of Scots pine (*Pinus sylvestris*) in MPa

Tablica 1. Elastične konstante i materijalne konstante drva običnog bora (izražene u MPa)

Elastic constant for orthotropic and anisotropic plasticity material model								
<i>Elastične konstante za model ortotropnoga i anizotropnoga plastičnog materijala</i>								
E_L	E_R	E_T	G_{RT}	G_{LT}	G_{LR}	ν_{RT}	ν_{LT}	ν_{LR}
14300	700	545	500	800	1230	0.380	0.040	0.030
Material constant / Materijalne konstante								
f_{Li}	f_{Lc}	f_{Ti}	f_{Tc}	f_{Ri}	f_{Rc}	f_{LR}	f_{LT}	f_{RT}
103.0	48.5	3.5	7.6	5.4	5.2	7.5	7.3	2.3
R_b	E_b	ρ						
86	12800	505						
Adjusted material constant for anisotropic plasticity material model								
<i>Prilagodba materijalnih konstanti za model anizotropnoga plastičnog materijala</i>								
f_{Li}	f_{Lc}	f_{Ti}	f_{Tc}	f_{Ri}	f_{Rc}	f_{LR}	f_{LT}	f_{RT}
101.0	43.0	4.927	5.4	5.4	5.2	7.5	7.3	2.3

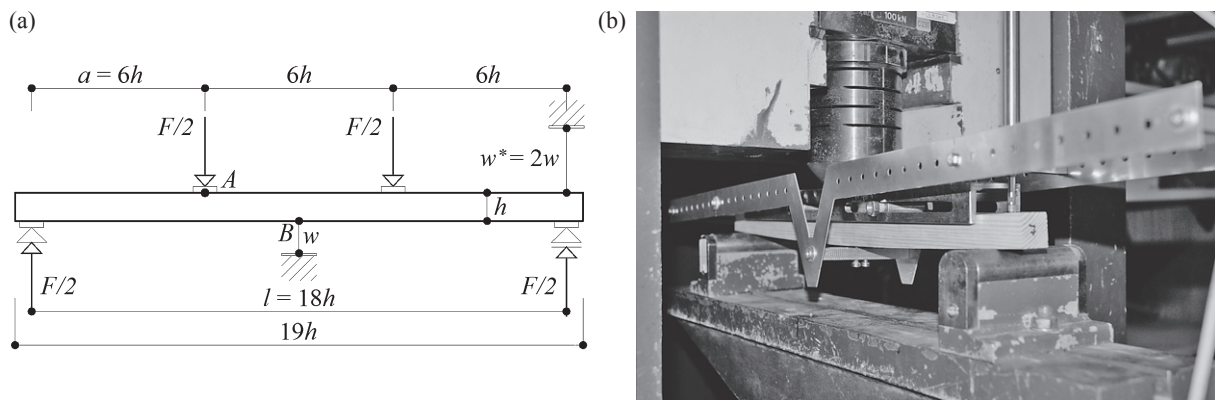


Figure 1 Arrangement of the test in compliance with ČSN EN 408 (a) and specimen No. 7 with a steel V-shape fixture (b)
Slika 1. Skica ispitivanja u skladu s normom ČSN EN 408 (a) i uzorak broj 7 čeličnim učvršćenjem V-oblika (b)

humidity of $65 \pm 2 \%$ until reaching constant weight (Kuklík and Vídeňský, 2005). In total, 10 specimens were prepared.

The specimens were simply supported during the experimental testing. The specimens were loaded by four-point bending (Fig. 1). The distance between supports was 450 mm ($18 \cdot h$). The testing set was complemented with a developed steel V-shape fixture (Fig. 1), which prevented transversal displacement of the tested specimens, while allowing their bending.

For the purpose of the monitoring of vertical displacement w^* (Fig. 1), testing specimens were fitted on the right support at their upper surface, with an inductive standard displacement transducer HBM WA-T/50 mm (HBM, 2012), with the measuring range of 0 – 50 mm and accuracy of 0.001 mm. The vertical displacement w at midspan was converted with the use of the measured vertical displacement w^* ($w = w^*/2$). The load was derived from the mechanical testing press FPZ100. The magnitude of the loading force was recorded by a calibrated resistance load cell. All sensors were connected to an 8-channel measuring data logger HBM Spider 8 (HBM, 2006). The data were recorded with the recording frequency of 2 Hz, i.e. in the time interval of 0.2 s.

2.2 Results of experimental testing

2.2. Rezultati eksperimentalnog ispitivanja

The relation of applied load F on vertical load w (load – displacement diagram $F - w$) for the whole inter-

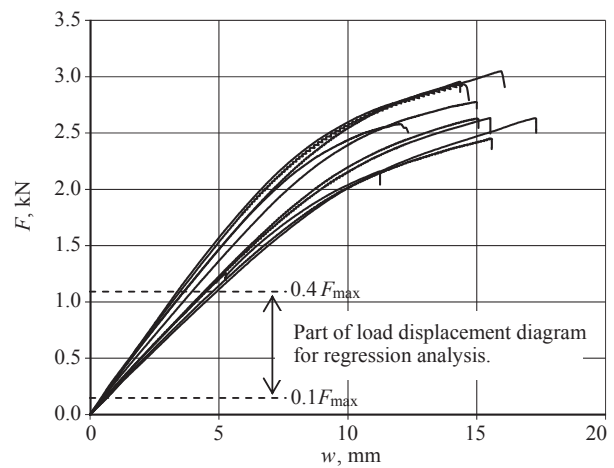


Figure 2 Load displacement diagram ($F - w$) for the whole loading interval

Slika 2. Dijagram opterećenje – pomak ($F - w$) za cijeli interval opterećenja

val of loading and all specimens is shown in Fig. 2. The load displacement diagram for individual specimens is shown in Fig. 5. The average value of limit load F_{max} is 2.693 kN (Table 2). The regression analysis and the determination of modulus of elasticity in bending used the part of graph in the interval $0.1 \cdot F_{max}$ to $0.4 \cdot F_{max}$, i.e. the part with linear relationship between load F and displacement w (Fig. 2) with the value of reliability R^2 higher than 0.99 (Kuklík and Vídeňský, 2005).

Table 2 Experimentally measured values for individual specimens

Tablica 2. Eksperimentalno dobivene vrijednosti za pojedine uzorke

Specimen No. Uzorak br:	m g	ρ kg/m ³	F_{max} kN	w^* mm	w mm	E_b MPa	R_b MPa	w_1 mm	w_2 mm	R^2
1	152.3	513.0	2.643	34.6188	17.3094	10624.0	74.5	1.14592	4.83916	0.9999
2	150.8	508.0	2.458	31.4688	15.7344	11070.0	69.2	1.13983	4.68429	0.9998
3	165.8	558.5	2.979	28.7375	14.3688	15738.0	83.9	0.83749	3.33063	1.0000
4	169.6	571.3	2.579	27.1000	13.5500	14414.0	72.6	0.86025	3.5824	0.9995
5	155.5	523.8	2.777	37.8688	18.9344	13157.6	78.2	0.91057	3.89265	1.0000
6	162.5	547.4	3.062	32.3875	16.1938	14510.4	86.3	0.89047	3.59453	0.9995
7	150.5	506.9	2.171	22.5063	11.2531	11518.3	61.2	1.03163	4.43813	0.9991
8	153.9	518.4	2.936	30.4813	15.2406	14785.6	82.7	0.78059	3.43433	1.0000
9	165.1	556.1	2.639	31.0688	15.5344	11710.7	74.3	1.06821	4.41875	0.9994
10	159.7	537.9	2.684	30.1625	15.0813	11825.1	75.6	1.03245	4.35058	1.0000
Average Prosječno	158.6	534.1	2.693	30.6400	15.3200	12935.4	75.9			

2.3 Evaluation of modulus of elasticity in bending

2.3. Određivanje modula elastičnosti pri savijanju

Modulus of elasticity in bending E_b (MPa) (Table 2) was determined with the use of relation (3) according to ČSN EN 408, where l – free sample length, m, b – width of cross-section, m and h – height of cross-section, m, and a – distance of load from support ($6 \cdot h$), m (Fig. 1). The difference $(F_2 - F_1)$ and $(w_2 - w_1)$ shows the growth of loading and vertical displacement on the linear part of the load – displacement diagram. The values F_1, F_2, w_1 and w_2 were determined with the use of load–displacement diagram in Fig. 2; $F_1 = 0.269$ kN and $F_2 = 1.077$ kN. The measured values are arranged in Table 2, where m – weight, g, F_{max} – limit load, kN, w^* – measured vertical displacement, mm, w – converted vertical displacement at midspan, mm and R^2 – value of reliability.

$$E_b = \frac{l^3 \cdot (F_2 - F_1)}{b \cdot h^3 \cdot (w_2 - w_1)} \cdot \left[\left(\frac{3 \cdot a}{4 \cdot l} \right) - \left(\frac{a}{l} \right)^3 \right] \quad (3)$$

2.4 Evaluation of bending strength

2.4. Određivanje čvrstoće na savijanje

Bending strength R_b (MPa) (Table 2) was determined with the use of the relation (4) according to ČSN EN 408, where b – width of cross-section, m, and h – height of cross-section, m, a – distance of load from support ($6 \cdot h$), m and F_{max} – limit load of specimen.

$$R_b = \frac{3 \cdot F_{max} \cdot a}{b \cdot h^2} \quad (4)$$

2.5 Numerical analysis of experimental testing

2.5. Numerička analiza eksperimentalnog ispitivanja

When modelling wood by the finite element method (Bathe, 2006; Tankut *et al.*, 2014), several approaches to wood modelling can be used. The approaches are based on simplifications of the real natural material. The modelling idealizes the real trunk of generally cone shape as a cylindrical object (Bodig and Jayne, 1993), idealizes annual rings as constant shape, thickness and curvature, local failures (knots, cracks),

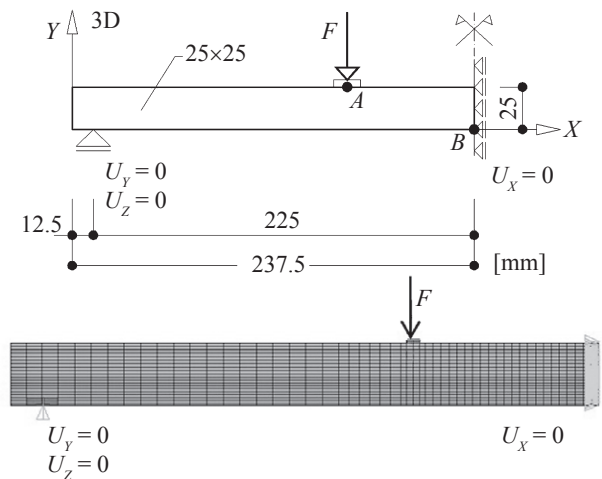


Figure 3 Geometry and 3D numeric model of wooden specimens in the calculation system ANSYS

Slika 3. Geometrijski i numerički 3D model drvnih uzoraka u računalnom sustavu ANSYS

variable structure of material, and differences between earlywood and latewood.

The numerical modelling of experimental testing of specimens idealized annual rings of individual specimens as cylindrical surfaces (Fig. 4) and the behaviour of wood was described with the use of anisotropic plasticity material model (Moses and Prion, 2004). The model was described with elastic and material constants shown in Table 1. The material constants were adjusted in order to meet the conditions of plasticity incompressibility and closed surface plasticity of elliptical shape mentioned by Moses and Prion (2004) and ANSYS (2012a). The material model was complemented with non-interactive failure criterion – maximum stress criterion (Vinson and Sierakowski, 2002), in order to allow the description of wood failure by brittle failure in tension. Neither the hardening of material, nor the limitation concerning the plasticity reserve was considered for compression.

Ten 3D numerical models of specimens were made in the calculation system ANSYS version 14.0 (ANSYS, 2012a). The models were created with the

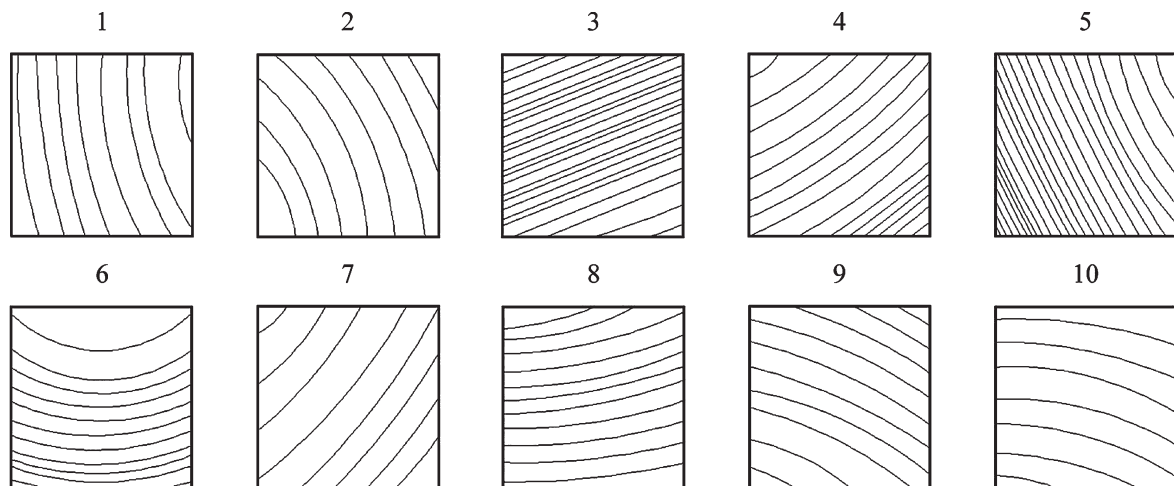


Figure 4 Idealised annual ring characteristics found from the characteristics of annual rings at the specimen front

Slika 4. Idealizirani godovi na poprečnom presjeku uzoraka

use of solid finite elements of SOLID45 and SURF154 type (ANSYS, 2012a).

In order to reduce the time demanding nature of calculations, symmetric boundary conditions were considered (Cook *et al.*, 2001), i.e. specimen halves were modelled of a size of $25 \times 25 \times 237.5$ mm (Fig. 3). In the transversal direction, the line load (line *A*) was distributed on specimens with the use of a distribution board (Fig. 3).

The cross sections of numerical models considered the characteristics of annual rings. The modelling of the characteristics of annual rings was based on one of two front views of specimens. General cone shape of the trunk, as well as the spiral arrangement of grains along the whole length of the trunk, was neglected. The characteristics of annual rings in the front were replaced with cylindrical surfaces, and the specimens were expected to have constant curvature along the length. The cross sections of specimens are shown in Fig. 4.

The calculations were made in steps, taking into account material non-linearity. In addition, the effect of large displacements and rotations of finite elements, i.e. geometric non-linearity, was taken into account.

3 RESULTS AND DISCUSSION

3. REZULTATI I RASPRAVA

3.1 Results of experimental testing

3.1. Rezultati eksperimentalnog ispitivanja

On average, the failure of tested specimens occurred under the force of 2.693 kN (Table 2). The min-

imum force of 2.171 kN at the failure was measured when testing specimen No. 7. In contrast, the maximum force of 3.062 kN at the failure was measured when testing specimen No. 6. The experimentally measured variation strength coefficient at failure is 9.83 %.

The average value of the modulus of elasticity in bending E_b , determined by experimental testing of 10 specimens, is 12935.4 MPa. The measured values of the modulus of elasticity in bending ranged within the interval of 10624.0 MPa (min; specimen No. 1) to 15738.0 MPa (max; specimen No. 3). The experimentally measured variation coefficient of the modulus of elasticity in bending is 14.0 %, which is a lower value than that of 22 % mentioned by Bergman *et al.* (2010) and Jirů (1970).

The average value of bending strength R_b is 75.9 MPa. Minimum and maximum values of bending strength do not correspond to the same samples used for measuring modulus of elasticity in bending. The measured values of bending strength ranged within the interval of 61.2 MPa (min; specimen No. 7) to 86.3 MPa (max; specimen No. 6). The experimentally measured variation coefficient of bending strength is 9.8 %, which is again a lower value than that of 16 % mentioned by Bergman *et al.* (2010) and Jirů (1970).

The value of modulus of elasticity in bending E_b and bending strength R_b depends on the orientation and density of annual rings (Table 2 and Fig. 4). Higher values E_b and R_b were shown by samples with higher density of annual rings and specimens, whose annual rings were convex when looking at the specimen front.

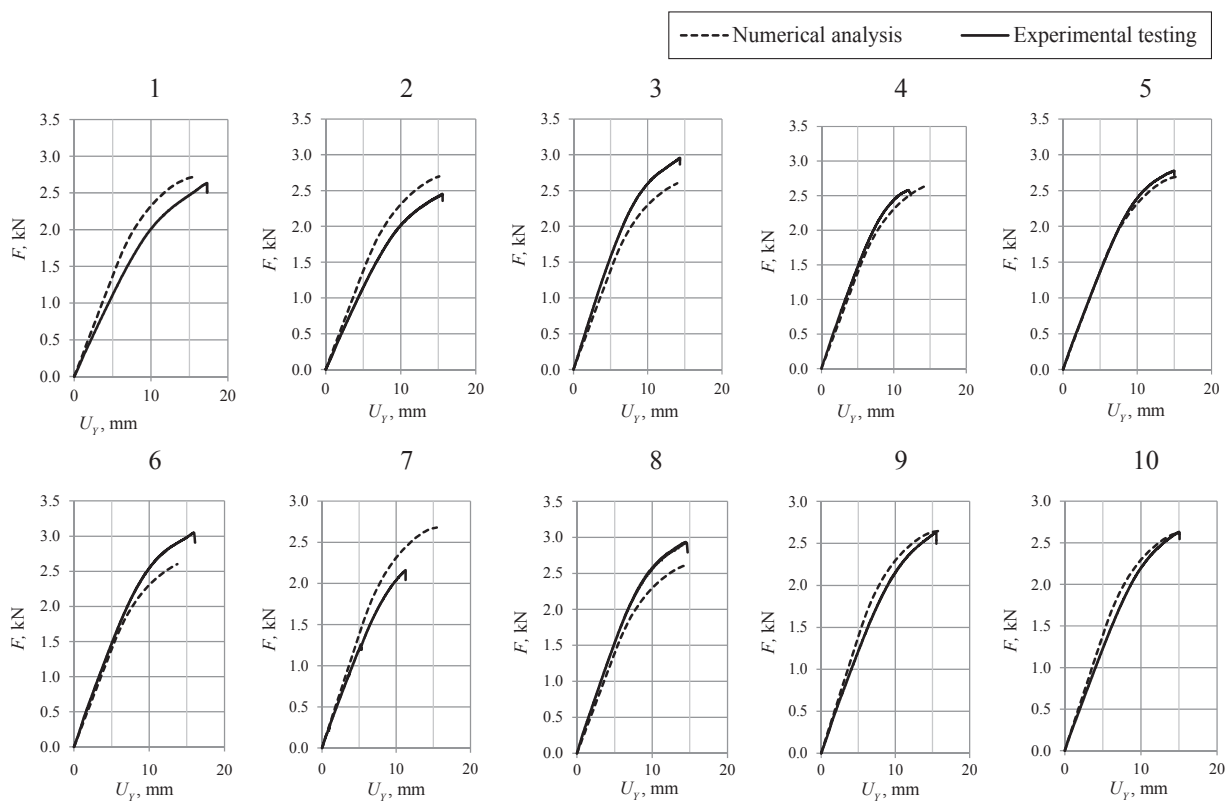


Figure 5 Load displacement diagrams ($F - U_y$) of specimens determined by numerical analysis and experimental testing
Slika 5. Dijagram opterećenje – pomak za ispitivane uzorke određen numeričkom analizom eksperimentalnog ispitivanja

Table 3 Results of experimental measurement of strength at the failure limit F (kN) and vertical displacement U_y at point B at midspan with numerically determined values**Tablica 3.** Rezultati eksperimentalnog mjerenja čvrstoće pri maksimalnom opterećenju F (kN) i vertikalnom pomaku U_y u točki B u sredini raspona s numerički utvrđenim vrijednostima

Specimen No. <i>Uzorak br.</i>	w	F_{max}	U_y	$F_{max,NA}$	w/U_y	$F_{max}/F_{max,NA}$
	mm	kN	mm	kN	%	%
	Experimental testing <i>Eksperimentalni podaci</i>		Numerical analysis <i>Numerička analiza</i>			
1	17.3094	2.643	15.9896	2.723	-8.25	2.91
2	15.7344	2.458	15.1248	2.698	-4.03	8.90
3	14.3688	2.979	13.9851	2.601	-2.74	-14.53
4	13.5500	2.579	14.2121	2.631	4.66	1.98
5	18.9344	2.777	15.4661	2.696	-22.42	-2.99
6	16.1938	3.062	13.7368	2.601	-17.89	-17.74
7	11.2531	2.171	15.4568	2.678	27.20	18.96
8	15.2406	2.936	14.5737	2.610	-4.58	-12.51
9	15.5344	2.639	15.9157	2.647	2.40	0.32
10	15.0813	2.684	14.8208	2.618	-1.76	-2.52
Average	15.3200	2.693	14.9282	2.650	-	-

3.2 Results of numerical analysis of experimental testing

3.2. Rezultati numeričke analize eksperimentalnog ispitivanja

The load curves $F - U_y$ at point B (Fig. 3) are shown in Fig. 5. Very good conformity between experimental tests and numerical analysis was reached with the specimen No. 4, 5, 6, 9 and 10. Regarding the specimen No. 1, 2 and 7, the hardness values of the numerical and material model, respectively, were higher than those of wood specimens. Load curves of specimen No. 3 and 8 are located under the experimentally determined load curves, indicating lower rigidity of the numerical and material model, respectively.

The average strength at the failure limit determined by experimental testing (2.693 kN) differs from the average strength at the failure limit determined by numerical modelling (2.650 kN) by -1.62 % (Table 3). The difference of the average measured vertical displacement at midspan (15.32 mm) and numerically determined values (14.93 mm) is -2.61 %.

4 CONCLUSIONS

4. ZAKLJUČAK

The determined value of average modulus of elasticity in bending E_b 12935.4 MPa by experimental testing differs from the values stated in literature for Scots pine (*Pinus sylvestris*) 12800 MPa (Table 1) by 1.05 %. The average bending strength R_b 75.9 MPa determined with the use of the same group of specimens differs by 11.74 % from the published value of 86.0 MPa. The determined average values E_b and R_b confirm the values of these constants mentioned in the paper of Matovič (1993) and Požgaj *et al.* (1997, 2004). The partial results of experimental testing of specimens show that constants E_b and R_b are dependent on the orientation and density of annual rings.

The use of anisotropic plasticity material model (Moses and Prion, 2004) for wood modelling with elastic and material constants according to Table 1, while

taking into account non-interactive failure criterion and the idealisation of the annual rings characteristics, showed good agreement between the results of numerical analysis and experimental testing of wood specimens. The difference between experimentally and numerically determined results is on average up to 2.7 %. Numerically determined load curves follow the load curves determined by experimental testing. The use of anisotropic plasticity material model can be seen on examples of load test modelling, numerical determination of load bearing capacity, i.e. in cases when the level of the applied loading is higher than the load when the material failure occurs. Otherwise, the above described approach can be replaced by a simpler, orthotropic material model with elastic constants according to Table 1 and interactive failure criteria – Hoffman (Hoffman, 1967) and Tsai-Wu criterion (Tsai and Wu, 1971).

Acknowledgments - Zahvala

This paper has been worked out under the project No. LO1408 “AdMaS UP – Advanced Materials, Structures and Technologies”, supported by Ministry of Education, Youth and Sports under the „National Sustainability Programme I” and under the project FAST-S-15-2757 supported by the IGA, Brno University of Technology, Czech Republic.

5 REFERENCES

5. LITERATURA

1. Bathe, K. J., 2006: Finite element procedures. [New ed.] [S.l.: s.n.].
2. Bergman, R.; Cai, Z.; Carl, Ch. G.; Clausen, C. A.; Di-etenberger, M. A.; Falk, R. H.; Frihart, Ch. R.; Glass, S. V.; Hunt, Ch. G.; Ibach, R. E.; Kretschmann, D. E.; Rammer, R. J.; Ross, R. J.; Stark, N. M., 2010: Wood Handbook, Wood as an Engineering Material (All Chapters). Forest Products Laboratory. Wood handbook – Wood as an engineering material. General Technical Report FPL-GTR-190. Madison, WI: U.S. Department of Agriculture, Forest Service, Forest Products Laboratory.
3. Bodig, J.; Goodman, J. R., 1973: Prediction of Elastic Parameters for Wood. Wood Science, 5(4): 249-264.

4. Bodig, J.; Jayne, B. A., 1993: Mechanics of wood and wood composites. Reprint ed. Malabar, Fla.: Krieger Pub., 1993, xxi, 712 p.
5. Danielsson, H.; Gustafsson, P. J., 2013: A three dimensional plasticity model for perpendicular to grain cohesive fracture in wood. *Engineering Fracture Mechanics*, (98): 137-152.
<http://dx.doi.org/10.1016/j.engfracmech.2012.12.008>
6. Gillis, P. P., 1972: Orthotropic elastic constants of wood. *Wood Science and Technology*, 6(2): 138-156.
<http://dx.doi.org/10.1007/BF00350827>
7. Hallai, J., 2008: Fracture of Orthotropic Materials under Mixed Mode Loading: EM 388F Fracture Mechanics: Term Paper. Austin, Texas: University of Texas at Austin, Department of Aerospace Engineering and Engineering Mechanics, (online).
<http://imechanica.org/files/Julian's%20Term%20Paper.pdf> (Accessed September 28, 2013).
8. Hoffman, O., 1967: The Brittle Strength of Orthotropic Materials. *Journal of Composite Materials*, 1: 200-206.
<http://dx.doi.org/10.1177/002199836700100210>
9. Morais, J. L.; Xavier, J. C.; Dourado, N. M.; Lousada, J. L., 2001: Mechanical behaviour of wood in the orthotropic directions. In: SharePDF.net - Free Download PDF File (online).
<http://sharepdf.net/view/87548/mechanical-behaviour-of-wood-in-the-orthotropic-directions> (Accessed September 24, 2013).
10. Hearmon, R. F. S., 1948: The Elasticity of Wood and Plywood. *Forest Products Research Special Report*, 7(1):1-87.
11. Jeong, G. Y.; Hindman, D. P.; Zink-Sharp, A., 2010: Orthotropic properties of loblolly pine (*Pinus taeda*) strands. *Journal of Materials Science*, 45 (21): 5820-5830.
<http://dx.doi.org/10.1007/s10853-010-4658-2>
12. Jirů, P., 1970: Dřevařská technická příručka – Oddíl první – Dřevo. SNTL – Nakladatelství technické literatury.
13. Kim, Y. J.; Harries, K. A., 2010: Modeling of timber beams strengthened with various CFRP composites. *Engineering Structures*, (32): 3225-3234.
<http://dx.doi.org/10.1016/j.engstruct.2010.06.011>
14. Kuklík, P.; Videňský, J., 2005: Stanovení komplexu fyzikálně-mechanických a fyzikálně-chemických charakteristik. In: *Centre for Integrated Design of Advanced Structures: Uplatnění pokročilých materiálů v integrovaném návrhu konstrukcí*. Prague: CIDEAS, pp. 1-2.
15. Martin, P. A.; Berger, J. R., 2001: Waves in wood: free vibrations of a wooden pole. *Journal of the Mechanics and Physics of Solids*, (49): 1155-1178.
[http://dx.doi.org/10.1016/S0022-5096\(00\)00068-5](http://dx.doi.org/10.1016/S0022-5096(00)00068-5)
16. Matovič, A., 1993: Fyzikální a mechanické vlastnosti dřeva a materiálů na bázi dřeva, Brno: Vysoká škola zemědělská.
17. Morais, J. L.; Xavier, J. C.; Dourado, N. M.; Lousada, J. L., 2001: Mechanical behaviour of wood in the orthotropic directions. In: SharePDF.net - Free Download PDF File (online).
<http://sharepdf.net/view/87548/mechanical-behaviour-of-wood-in-the-orthotropic-directions> (Accessed September 24, 2013)
18. Moses, D. M.; Prion, H. G. L., 2004: Stress and failure analysis of wood composites: a new model. *Composites: Part B: engineering*, (35): 251-261.
<http://dx.doi.org/10.1016/j.compositesb.2003.10.002>
19. Nairn, J. A., 2007: Numerical Modeling of Deformation and Fracture of Wood including Heterogeneity and Anisotropy. COST Action E35 Meeting, Lausanne, Switzerland, 2007 (online).
20. Dostupné: <http://www.cof.orst.edu/cof/wse/faculty/Nairm/papers/NairmCOST.pdf> (Accessed September 24, 2013).
21. Pěncík, J., 2013: Dřevěné segmentové schodiště s jednostranně zavěšenými stupni. Brno, 2013. Habilitation thesis.
22. Pousette, A., 2006: Testing and modeling of the behavior of wooden stairs and stair joints. *Journal of Wood Science*, 52(4): 358-362.
<http://dx.doi.org/10.1007/s10086-005-0778-8>
23. Požgaj, A.; Chovanec, D.; Kurjatko, S.; Babiak, M., 1997: Štruktúra a vlastnosti dreva, Priroda, Bratislava.
24. Tankut, N.; Tankut, A. N.; Zor, M., 2014: Finite Element Analysis of Wood Materials. *Drvna industrija*, 65(2): 159-171.
<http://dx.doi.org/10.5552/drind.2014.1254>
25. Tsai, S. W.; Wu, E. M., 1971: A General Theory of Strength for Anisotropic Materials. *Journal of Composite Materials*, (5): 58-79.
<http://dx.doi.org/10.1177/002199837100500106>
26. Úradníček, L., Maděra, P., Tichá, S., Koblížek, J., 2001: Dřeviny České republiky. 2. ed. Písek: Matice lesnická.
27. Vinson, J. R.; Sierakowski, R., 2002: The behavior of structures composed of composite materials. 2nd ed. Boston: Kluwer Academic Publishers, xiv, 435 p.
<http://dx.doi.org/10.1007/0-306-48414-5>
28. Winandy, J. E., 1994: in *Encyclopedia of agricultural science*, ed. Arntzen, Ch. J., Ritter, E. M. Academic Press, New York, 4: 549-561.
29. Xavier, J., 2007: Identification de la variabilité des rigidités du bois à l'intérieur de l'arbre par la méthode des champs virtuels: application au P. Pinaster dans le plan LR. Paris. Thèse pour obtenir la grade de Docteur. E. N.S.A.M (Ecole Nationale Supérieure des Arts et Métiers). (online). (Accessed September 28, 2013).
30. ***2004: "Fyzikální a mechanické vlastnosti dřeva" (online), Mendel University in Brno, wood.mendelu.cz/cz/sections/Props/?q=node/56. First published 2004 (Accessed Sept. 20, 2013).
31. ***2006: "Spider8 from HBM" (online), HBM Inc., <http://www.hbm.com/fileadmin/mediapool/hbmdoc/technical/b0409.pdf>. First published 2006 (Accessed Sept. 20, 2013).
32. *** ANSYS® Academic Research, Release 14.5, ANSYS, Inc., 2012a.
33. ***2012: "HBM WA T – Inductive displacement transducer (Probe)" (online), HBM Inc.
<http://www.hbm.com/en/menu/products/transducers-sensors/displacement/wa-t/#c71014> (Accessed Sept. 20, 2013).
34. ***2012a: "EUFORGEN: Distribution maps" (online), EUFORGEN.
http://www.euforgen.org/distribution_maps.html (Accessed Sept. 20, 2013).
35. *** ČSN EN 408 (73 1741), 2004: Timber structures - Structural timber and glued laminated timber - Determination of some physical and mechanical properties.

Corresponding address:

Assist. Prof. Ing. JAN PĚNCÍK, Ph. D.

Institute of Building Structures
Faculty of Civil Engineering
Brno University of Technology
CZECH REPUBLIC
e-mail: pencik.j@fce.vutbr.cz