



OPEN

Fabrication of Nb₂O₅ Nanosheets for High-rate Lithium Ion Storage Applications

SUBJECT AREAS:
BATTERIES
MATERIALS CHEMISTRYMeinan Liu¹, Cheng Yan² & Yuegang Zhang¹Received
30 November 2014Accepted
15 January 2015Published
9 February 2015Correspondence and
requests for materials
should be addressed to
Y.G.Z.
(ygzhang2012@
sinano.ac.cn)¹Lab, Suzhou Institute of Nano-Tech and Nano-Bionics, Chinese Academy of Sciences, Suzhou, China, ²School of Chemistry, Physics and Mechanical Engineering, Queensland University of Technology, Brisbane, Australia.

Nb₂O₅ nanosheets are successfully synthesized through a facile hydrothermal reaction and followed heating treatment in air. The structural characterization reveals that the thickness of these sheets is around 50 nm and the length of sheets is 500 ~ 800 nm. Such a unique two dimensional structure enables the nanosheet electrode with superior performance during the charge-discharge process, such as high specific capacity (~184 mAh·g⁻¹) and rate capability. Even at a current density of 1 A·g⁻¹, the nanosheet electrode still exhibits a specific capacity of ~90 mAh·g⁻¹. These results suggest the Nb₂O₅ nanosheet is a promising candidate for high-rate lithium ion storage applications.

Lithium ion batteries are commonly used for consumer electronics, portable electric devices, electric vehicles and other applications¹⁻⁵. However, for high power density applications such as in electric vehicles, it is hindered by the achievement of high-rate capability of electrode materials. Recently, transition metal oxides have been extensively explored as anode replacing graphite due to their higher theoretical capacity and high packing densities, which lead to high volumetric energy densities in devices⁶⁻¹⁰.

Among the different transition metal oxide as anode materials, lithium titanate (Li₄Ti₅O₁₂) and niobium oxide (Nb₂O₅) have received the most study because of the considerable safety advantage that their redox potentials match to the LUMO of the organic liquid-carbonate electrolyte¹¹⁻¹³. Compared with Li₄Ti₅O₁₂ with a specific capacity of 140 mAh·g⁻¹, Nb₂O₅ exhibits a higher capacity (~200 mAh·g⁻¹)^{11,12}. Furthermore, Augustyn and Dunn *et al* found that the crystal structure of orthorhombic Nb₂O₅ permits exceptionally rapid ionic transport since the mostly empty octahedral sites between (001) planes provide natural tunnels for lithium ion transport throughout the *a-b* plane^{14,15}, which makes Nb₂O₅ a promising anode material. However, its intrinsic poor electric conductivity ($\sigma \sim 3 \times 10^{-6} \text{ S}\cdot\text{cm}^{-1}$) and the capacity decay resulted from pulverization during charge-discharge process limit its practical application in lithium ion batteries, and thus it is still challenging to develop efficient but simple ways to enhance the utilization of electroactive Nb₂O₅¹⁵⁻¹⁹.

Building nanostructures with desirable morphology and size is of great importance for addressing this issue¹⁵⁻³¹. For instance, Dunn *et al* developed Nb₂O₅ mesoporous films through a simple solution process, which exhibited high-rate lithium insertion capability¹⁶. Wang and Lu *et al* reported high performance supercapacitors based on nanocomposites of Nb₂O₅ nanocrystals and carbon nanotubes¹⁷. Nb₂O₅-carbon core-shell nanocomposites were fabricated by Li and Ma *et al*, which exhibited high specific capacity and rate capability¹⁸. Nb₂O₅ nanobelts and hollow nanospheres were also been developed with large capacity and high rate capability^{19,20}.

Among these nanostructures, two dimensional structures with nano size in thickness and micro size in length have been considered to be the appropriate morphology for energy storage²²⁻²⁵. Generally, a nano-sized thickness has short ion diffusion path and large surface area; the micro-sized length can lower the internal resistance and facilitate the electron transfer rate as compared with the noncontinuous oxide framework composed of nanoparticles²²⁻²⁵. These merits encourage us to investigate Nb₂O₅ electrode materials with two dimensional structures.

In this work, Nb₂O₅ nanosheets were developed by a two-step hydrothermal reaction and subsequent calcination process. The two dimensional sheet-like structure was composed of thin thickness (~50 nm) and long length (~800 nm), fitting the desirable structure principles as mentioned above. As expected, the nanosheet electrodes exhibited superior capacity (~184 mAh·g⁻¹), much higher than commercial Nb₂O₅ particles (~135 mAh·g⁻¹). Additionally, the samples performed well at high current density (~130 mAh·g⁻¹ at 0.4 A·g⁻¹ and



$\sim 90 \text{ mAh}\cdot\text{g}^{-1}$ at $1 \text{ A}\cdot\text{g}^{-1}$), indicating its high rate capability. These results demonstrate that our samples are promising for the future practical application in lithium ion storage.

Results

Synthesis of intermediate $\text{Nb}_3\text{O}_7\text{F}$ nanosheets. As shown in Fig. 1a, XRD pattern of the as-obtained powders from hydrothermal process can be indexed as an orthorhombic $\text{Nb}_3\text{O}_7\text{F}$ structure (JCPDS Card No. 74-2363). Fig. 1b shows the morphology of the as-prepared $\text{Nb}_3\text{O}_7\text{F}$, displaying two dimensional sheet-like structure. A TEM image of $\text{Nb}_3\text{O}_7\text{F}$ nanosheets after ultrasound treatment is shown in Fig. 1c. It can be observed that these $\text{Nb}_3\text{O}_7\text{F}$ nanosheets are rectangular shape. The nanosheets are almost transparent, suggesting the sheet is very thin. The size of these sheets is around $500 \sim 800 \text{ nm}$. The HRTEM image (Fig. 1d) and SAED pattern (top inset in Fig. 1d) reveal a good single crystalline nature of the $\text{Nb}_3\text{O}_7\text{F}$ nanosheets. The lattice fringes show an interplanar spacing of ca. 0.38 nm and 0.39 nm (Fig. 1d), corresponding to the (010) and (001) planes of the orthorhombic $\text{Nb}_3\text{O}_7\text{F}$, respectively.

We investigated the effect of different hydrothermal conditions on the resultant $\text{Nb}_3\text{O}_7\text{F}$ crystal structure and morphologies. The reaction time has been found playing a crucial role in controlling the nucleation and growth of crystallites during the hydrothermal system. As shown in Fig. 2, XRD patterns of the solids samples prepared at 160°C with different reaction time indicates pronounced changes in crystal structure during the reaction. XRD patterns of the sample obtained in 3 h are different from that of raw materials Nb, suggesting a new crystal phase forms at the expense of Nb in a short period. With prolonging the reaction time to 6 h, a new diffraction peak appears at $2\theta = 22.5^\circ$, which can be indexed as $\text{Nb}_3\text{O}_7\text{F}$. Increasing the reaction time to 8 h, it can be found that the diffraction peak at $2\theta = 36.6^\circ$ almost disappear, indicating the crystal phase

formed in 3 h degrades readily in the subsequent reaction process. All diffraction peaks of the sample prepared with 12 h are indexed to $\text{Nb}_3\text{O}_7\text{F}$ (JCPDS card No. 74-2363). Further prolonging the reaction time to 24 h or 48 h, the XRD patterns are similar, demonstrating the as-obtained samples are pure $\text{Nb}_3\text{O}_7\text{F}$ with the reaction time at and longer than 12 h.

The morphology evolution of $\text{Nb}_3\text{O}_7\text{F}$ with increasing reaction times was also studied. As shown in Fig. 3a, the samples formed in 3 h are particles. With the reaction time prolonging to 6 h, one dimensional rod-like structure can be observed. The diameter of these rods is around 30 nm (Fig. 3b). Further study indicates that these nanorods appear as a metastable intermediate. For instance, XRD results clearly demonstrate that some new diffraction peaks of $\text{Nb}_3\text{O}_7\text{F}$ appear after 8 h of reaction. In addition, this has also been confirmed by SEM observation. With increasing the reaction time to 8 h, some sheets are formed besides those nanorods. The thickness of sheets is around 20 nm and the size is $600 \sim 800 \text{ nm}$. Fig. 3d reveals the presence of a large number of sheets, which indicates that the purity of sheets in the product is increased by prolonging the reaction time. XRD results confirm that the products obtained after reacting 12 h are pure $\text{Nb}_3\text{O}_7\text{F}$. The samples prepared in 24 h are well-crystallized sheets, as shown in Fig. 3e. The thickness of these sheets is around 50 nm , much thicker than that of sheets obtained in 8 h. However, it can be found that most of sheets crack into small pieces with further prolonging the reaction time to 48 h, indicating too long reaction time may damage the perfect sheet-like structure. Therefore, it can be concluded that 24 h is the optimized reaction condition for preparing $\text{Nb}_3\text{O}_7\text{F}$ nanosheets.

Synthesis of Nb_2O_5 nanosheets. Ultrathin Nb_2O_5 nanosheets could be developed by an in-situ heat treatment of $\text{Nb}_3\text{O}_7\text{F}$ nanosheets prepared from optimized reaction condition in air. Fig. 4a shows

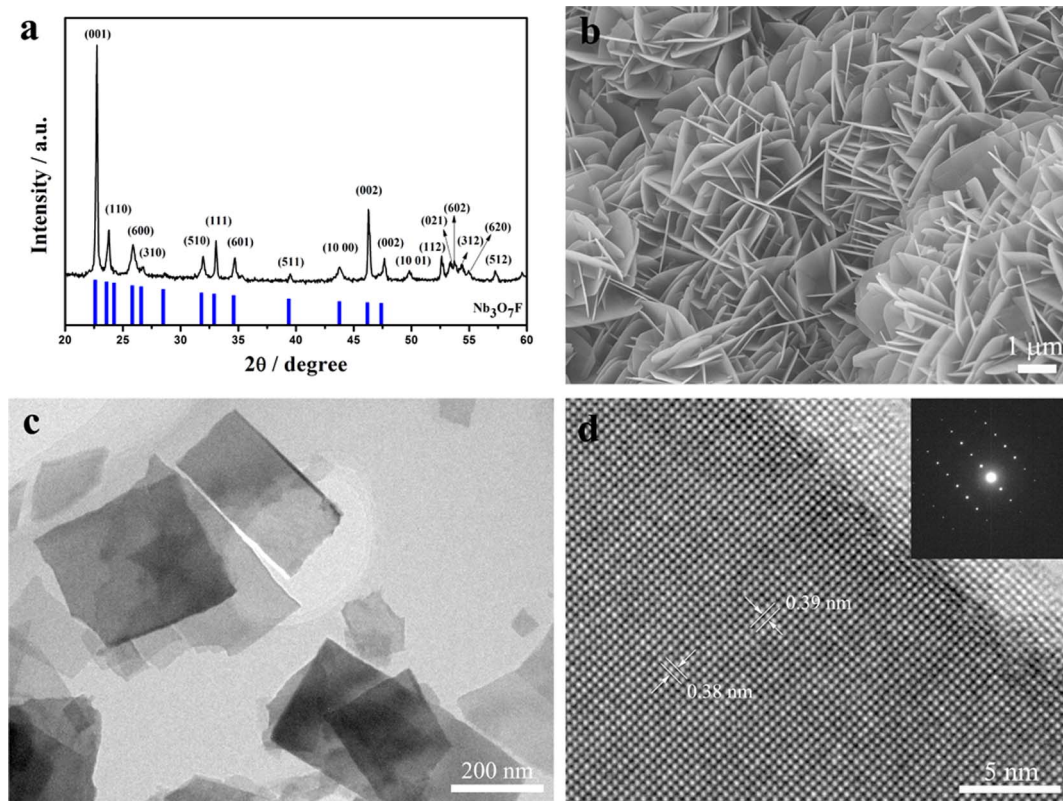


Figure 1 | XRD patterns (a) and SEM images (b) of the $\text{Nb}_3\text{O}_7\text{F}$ prepared at 160°C with 24 h. The standard diffraction peaks of $\text{Nb}_3\text{O}_7\text{F}$ (JCPDF card No. 74-2363) are included as reference. TEM image (c) and HRTEM image (d) of the as-obtained $\text{Nb}_3\text{O}_7\text{F}$ nanosheets. The inset in (d) is the SAED pattern.

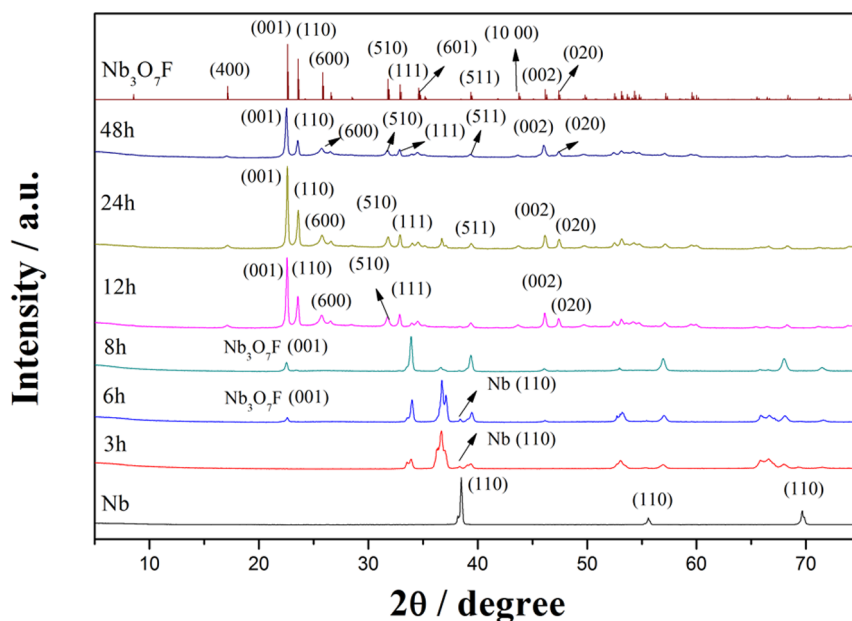


Figure 2 | XRD patterns of Nb foil, precursor $\text{Nb}_3\text{O}_7\text{F}$ and intermediates obtained with different reaction times. The standard diffraction pattern of $\text{Nb}_3\text{O}_7\text{F}$ (JCPDS card No. 74-2363) is shown as a reference.

the XRD pattern of $\text{Nb}_3\text{O}_7\text{F}$ heated at 550°C for 1 h. All diffraction peaks are indexed to orthorhombic Nb_2O_5 (JCPDS card No. 30-0873). From SEM image in Fig. 4b, it can be observed that the sheet-like structure was kept very well after heating treatment. This is also confirmed by the TEM observation, as shown in Fig. 4c. A typical HRTEM image (Fig. 4d) discloses the lattice fringes with a spacing of 0.39 nm, in a good agreement with the spacing of the (001) planes of Nb_2O_5 . The results indicate the (001) planes are perpendicular to nanosheets, which may provide natural tunnels for lithium ion transport throughout the a - b plane¹⁵, and thus favour fast intercalation/de-intercalation reaction.

Electrochemical performance of Nb_2O_5 nanosheets. High-valent Nb_2O_5 is well known to act as electrode material for lithium intercalation ($x\text{Li} + xe^- + \text{Nb}_2\text{O}_5 \rightarrow \text{Li}_x\text{Nb}_2\text{O}_5$). The amount of lithium insertion in $\text{Li}_x\text{Nb}_2\text{O}_5$ varies between $x = 1.6$ to a maximum

capacity of $200 \text{ mAh}\cdot\text{g}^{-1}$ ($x = 2$). Here, the electrochemical properties of lithium ions intercalation (or deintercalation) into (or from) Nb_2O_5 nanosheets are characterized. As shown in Fig. 5a, the CV curves of Nb_2O_5 at a scan speed of 0.5 mV/s in a potential window of 2.5 to 1.0 V (vs. Li^+/Li) present symmetric cathodic and anodic peaks, indicating a reversible lithium intercalation and de-intercalation process. Representative voltage profiles at second cycle is shown in Fig. 5b. The curve shows highly reversible capacities.

Fig. 5c compares the charge storage and Coulombic efficiencies of the electrodes from Nb_2O_5 nanosheets and commercial Nb_2O_5 particles at $0.2 \text{ A}\cdot\text{g}^{-1}$ (1 C). The initial discharge capacity of this nanosheet electrode is $184 \text{ mAh}\cdot\text{g}^{-1}$, which almost reaches the theoretical capacity ($200 \text{ mAh}\cdot\text{g}^{-1}$), while the initial discharge capacity of commercial Nb_2O_5 particles electrode is only $135 \text{ mAh}\cdot\text{g}^{-1}$, much lower than that of nanosheet electrode. The capacity can keep

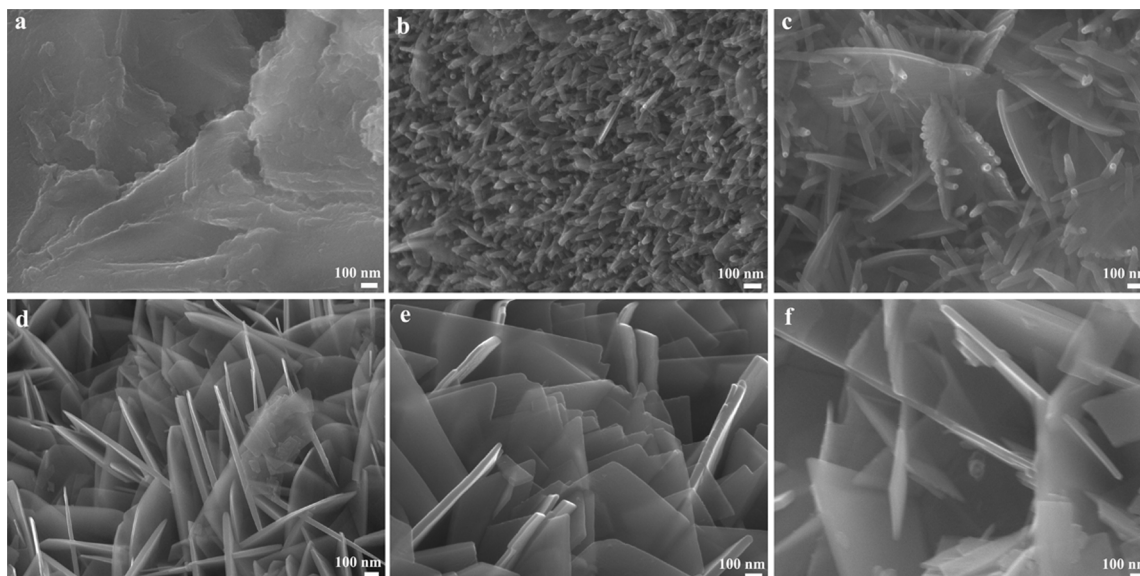


Figure 3 | SEM images of the structure evolution of $\text{Nb}_3\text{O}_7\text{F}$ nanosheets with increasing times: (a) 3 h; (b) 6 h; (c) 8 h; (d) 12 h; (e) 24 h; (f) 48 h.

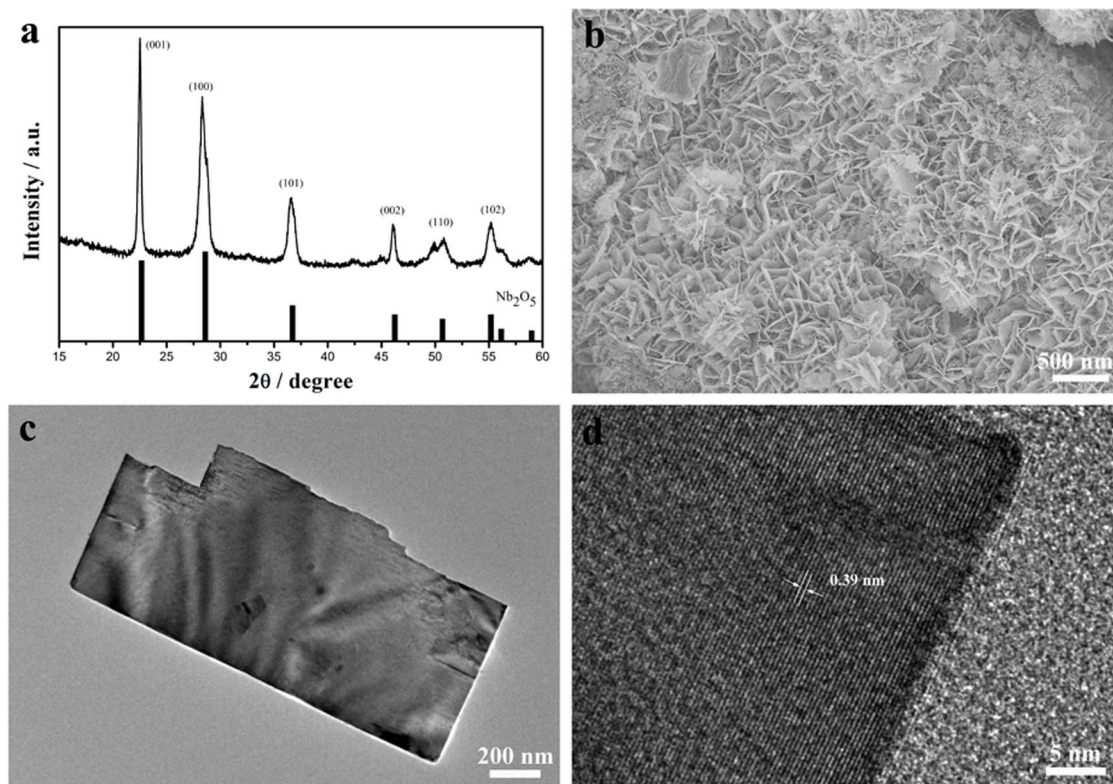


Figure 4 | XRD patterns (a) and SEM image (b) of the as-obtained Nb_2O_5 nanosheets heated at 550°C in air for 1 h. The standard diffraction pattern of Nb_2O_5 (JCPDS card No. 30-0873) is shown as a reference. TEM image (c) and HRTEM image (d) of the as-obtained Nb_2O_5 nanosheets.

$117 \text{ mAh}\cdot\text{g}^{-1}$ and $83 \text{ mAh}\cdot\text{g}^{-1}$ after 100 cycles for the nanosheet and particle electrodes, respectively. Kodama *et al* found that the continuous variation in the valence state from Nb^{5+} to Nb^{4+} takes place in the discharge reaction, as $x\text{Li} + x\text{e}^- + \text{Nb}_2\text{O}_5 \rightarrow \text{Li}_x\text{Nb}_2\text{O}_5$ ($x = 0-2$)²¹. This structural variation during the Li intercalation of the two phases could induce strain, which may influence the structure integ-

rity of nanosheets. The structure change of nanosheets could deteriorate the contact between active materials and conducting additives, and thus lead to the capacity fading. The similar phenomenon was also observed in nanobelt electrodes¹⁹. It should be noted that the Coulombic efficiencies of nearly 100% are achieved for both nanosheet and particle electrodes in this work.

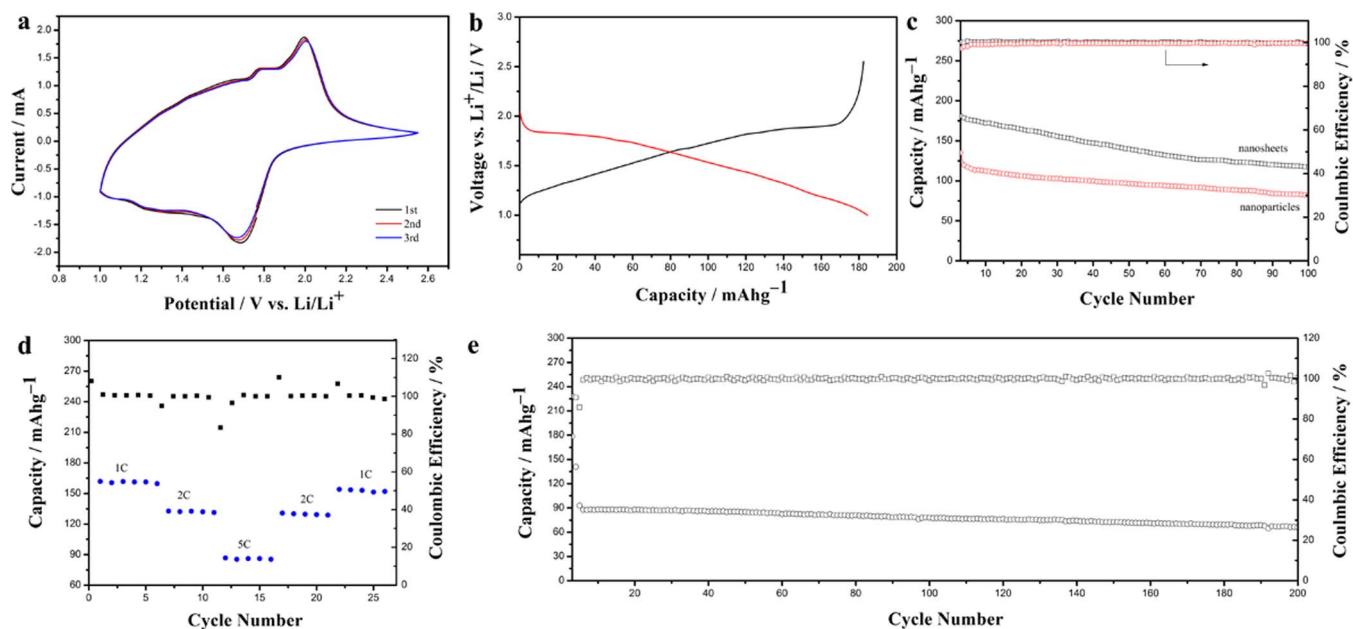


Figure 5 | Electrochemical properties of the Nb_2O_5 nanosheet electrodes. (a) CV curves of Nb_2O_5 nanosheet electrodes; (b) second galvanostatic discharge/charge profiles under 1 C; (c) cycling performance and Coulombic efficiency of the Nb_2O_5 nanosheet and nanoparticle electrodes under 1 C; (d) rate performance of the Nb_2O_5 nanosheet electrodes; (e) cycling performance and Coulombic efficiency of the Nb_2O_5 nanosheet electrodes under 5 C.



To investigate the rate-capability, the electrode was charged and discharged at 1C to 5C. Fig. 5d shows the rate performance of the nanosheet electrodes. As expected, the specific capacity decreases with the increase of current densities. But the good capacity can be switched back to 2C and 1C again. Furthermore, the nanosheet electrode still exhibits a specific capacity of $\sim 90 \text{ mAh}\cdot\text{g}^{-1}$ at 5C, indicates the fast reaction kinetics in the electrodes. Fig. 5e shows the cycling performance of the nanosheet electrode at 5C for 200 cycles. It can be found that the specific capacity is around $90 \text{ mAh}\cdot\text{g}^{-1}$ at the first cycle at 5C and around $70 \text{ mAh}\cdot\text{g}^{-1}$ after 200 cycles, with Coulombic efficiency stabilized at 100%. The capacity decay rate is as low as 0.11%, which is considered very good for metal oxide nanostructures based electrode materials²⁰. The results well demonstrate that Nb_2O_5 nanosheets are promising anode materials for high-rate lithium ion storage applications.

Discussion

Growth mechanism of intermediate $\text{Nb}_3\text{O}_7\text{F}$ nanosheets. Based on XRD and SEM results (in Fig. 2 and Fig. 3), a possible $\text{Nb}_3\text{O}_7\text{F}$ nanosheets growth process is presented here. Firstly, Nb powders are slowly etched to H_2NbF_7 by HF, and then H_2NbF_7 is hydrolyzed into $\text{Nb}_3\text{O}_7\text{F}$. With increasing the hydrothermal reaction time, the $\text{Nb}_3\text{O}_7\text{F}$ concentration in reaction solution was further enhanced, which resulted in the formation of $\text{Nb}_3\text{O}_7\text{F}$ nanosheets. The chemical reaction process in this hydrothermal system is similar to the results reported by other researchers³².

Improving the electrochemical performance of Nb_2O_5 electrodes through constructing 2D microstructures. It is obvious that the specific capacity of Nb_2O_5 nanosheet electrode is much higher than that of Nb_2O_5 particles, as shown in Fig. 5c. The improved electrochemical performance could be related to the following structural features. First, the micro-sized length ($\sim 1 \mu\text{m}$) provides a continued pathway for charge transfer, which makes the redox reaction rate faster. Second, the thin thickness ($\sim 50 \text{ nm}$) increases the specific surface area, which results in the improvement of the contact area between electrode and electrolyte and facilitated the diffusion of electrolyte into the material, leading to more efficient utilization of the active materials. Third, the (001) planes perpendicular to nanosheets allow degenerate pathways with low energy barriers for ion transport, which may also contribute to the improvement of cycling performance¹⁵. As shown in Fig. 5e, it can be found that the capacitance retention of 200th cycle is 78% compared to the first cycle at 5C. The nanosheets exhibit superior cycling stability than those nanobelts reported by Wei *et al.*, which retains only 72% of the initial discharge capacity after 50 charge/discharge cycles at 0.5C¹⁹. The superior performance of nanosheets can be attributed to the unique morphology that these sheets not only provide short Li-ion transport length but also accommodate the volume variation. In addition, Sasidharan *et al.* reported that their hollow nanospheres also exhibit excellent cycle stability²⁰. The capacity retention of 250th cycle is 90% compared to the first cycle²⁰. They attribute this excellent cycle performance to the thin-shell of hollow spheres with 6 nm favoring fast intercalation/deintercalation reaction and void space effectively buffering against the local volume changes during repeated charge/discharge processes²⁰. As a consequence, the performance of nanosheets could be further improved if the thickness could be reduced in future.

In summary, we have successfully synthesized Nb_2O_5 nanosheets from its precursor $\text{Nb}_3\text{O}_7\text{F}$ nanosheets. The nanosheet electrode delivers a superior electrochemical performance with an initial discharge capacity of $184 \text{ mAh}\cdot\text{g}^{-1}$ at $0.2 \text{ A}\cdot\text{g}^{-1}$ current density. Cycling measurement suggest Nb_2O_5 nanosheet electrodes show a high reversible charge/discharge capacity, high rate-capability and excellent cycling stability, making this material a good candidate as

an electrode for high-rate electrochemical energy storage applications.

Methods

Materials Synthesis. Synthesis of Nb_2O_5 nanosheets was performed using the metal Nb powder as the starting materials. In a typical synthesis, 0.15 g Nb metal powder and 0.3 mL HF were added into 30 mL distilled water, then the mixture solution was transferred into a 50 mL Teflon-lined autoclave, and kept it in oven at 160°C for 3 \sim 48 h. The as-prepared precursor was then annealed at 550°C for 1 h in air to obtain Nb_2O_5 nanosheets.

Materials Characterization. The morphologies of precursor and annealed samples were investigated using a field emission scanning electron microscope (FE-SEM, Hitachi S4800) and a field emission transmission electron microscopy (FE-TEM, FEI, Tecnai G2 F20 S-Twin). X-ray diffraction (XRD, Bruker AXS, D8 Advance) was used for crystal structure characterization.

Electrochemical Measurements. The as-obtained Nb_2O_5 nanosheets were mixed with super P and polyvinylidene fluoride (PVDF, $M_w = 560 \text{ K}$) in a weight ratio of 80 (active materials):10 (super P):10 (binder), and 1-Methyl-2-pyrrolidinone (NMP) was added to form a homogenous slurry. The slurry was cast onto aluminum current collector using the doctor blade technique. The cast electrode was dried in a vacuum oven at 100°C for 5 h and punched into 15 mm circular discs. CR2016 coin cells were assembled in an Ar-filled glove box with a lithium metal foil as counter electrode and a porous polypropylene separator (2400, Celgard). The electrolyte consisted of a solution of 1 M LiPF_6 in ethylene carbonate (EC)/dimethyl carbonate (DMC)/diethyl carbonate (DEC) (1 : 1 : 1 by volume).

- Dunn, B., Liu, P. & Meng, S. Nanoscience and Nanotechnology in Next Generation Lithium Batteries. *Nanotech.* **24**, 420201 (2013).
- Stevenson, K., Ozolins, V. & Dunn, B. Electrochemical Energy Storage. *Acc. Chem. Res.* **46**, 1051–1052 (2013).
- Ji, L. *et al.* Graphene Oxide as a Sulfur Immobilizer in High Performance Lithium/Sulfur Cells. *J. Am. Chem. Soc.* **133**, 18522–18525 (2011).
- Song, M., Zhang, Y. & Cairns, E. J. A Long-Life, High-Rate Lithium/Sulfur Cell: A Multifaceted Approach to Enhancing Cell Performance. *Nano Lett.* **13**, 5891–5899 (2013).
- Yu, Y. *et al.* Encapsulation of Sn/carbon Nanoparticles in Bamboo-like Hollow Carbon Nanofibers as an Anode Material in Lithium-Based Batteries. *Angew. Chem. Int. Ed.* **48**, 6485–6489 (2009).
- Luo, J. *et al.* Three-Dimensional Graphene Foam Supported Fe_3O_4 Lithium Battery Anodes with Long Cycle Life and High Rate Capability. *Nano Lett.* **13**, 6136–6143 (2013).
- Hu, L., Wu, F., Lin, C., Khlobystov, A. & Li, L. Graphene-modified LiFePO_4 Cathode for Lithium Ion Battery beyond Theoretical Capacity. *Nat. Commun.* **4**, 1687 (2013).
- Pan, A., Wu, H., Yu, L. & Lou, X. Template-free Synthesis of VO_2 Hollow Microspheres with Various Interiors and Their Conversion into V_2O_5 for Lithium-ion Batteries. *Angew. Chem. Int. Ed.* **52**, 2226–2230 (2013).
- Lou, X., Li, C. & Archer, L. Designed Synthesis of Coaxial SnO_2 @carbon Hollow Nanospheres for Highly Reversible Lithium Storage. *Adv. Mater.* **21**, 2536–2539 (2009).
- Lin, Y., Wei, T., Chien, H. & Lu, S. Manganese Oxide/Carbon Aerogel Composite: an Outstanding Supercapacitor Electrode Material. *Adv. Energy Mater.* **1**, 901–907 (2011).
- Viet, A., Reddy, M., Jose, R., Chowdari, B. & Ramakrishna, S. Nanostructured Nb_2O_5 Polymorphs by Electrospinning for Rechargeable Lithium Batteries. *J. Phys. Chem. C* **114**, 664–671 (2010).
- Jiang, Y., Wang, K., Zhang, H., Wang, J. & Chen, J. Hierarchical $\text{Li}_4\text{T}_i_5\text{O}_{12}/\text{TiO}_2$ Composite Tubes with Regular Structural Imperfection for Lithium Ion Storage. *Scientific Reports* **3**, 3490 (2013).
- Kim, J., Augustyn, V. & Dunn, B. The Effect of Crystallinity on the Rapid Pseudocapacitive Response of Nb_2O_5 . *Adv. Eng. Mater.* **2**, 141–148 (2012).
- Liu, C., Zhou, F. & Ozolins, V. First Principles Study for Lithium Intercalation and Diffusion Behavior in Orthorhombic Nb_2O_5 Electrochemical Supercapacitor. *American Physical Society March Meeting*, Abstr. B26.00003 (2012).
- Augustyn, V. *et al.* High-Rate Electrochemical Energy Storage through Li^+ Intercalation Pseudocapacitance. *Nat. Mater.* **12**, 518–522 (2013).
- Brezesinski, K. *et al.* Pseudocapacitive Contributions to Charge Storage in Highly Ordered Mesoporous Group V Transition Metal Oxides with Iso-Oriented Layered Nanocrystalline Domains. *J. Am. Chem. Soc.* **132**, 6982–6990 (2010).
- Wang, X. *et al.* High-Performance Supercapacitors Based on Nanocomposites of Nb_2O_5 Nanocrystals and Carbon Nanotubes. *Adv. Eng. Mater.* **1**, 1089–1093 (2011).
- Li, G., Wang, X. & Ma, X. Nb_2O_5 -Carbon Core-Shell Nanocomposite as Anode Material for Lithium Ion Battery. *J. Energy Chem.* **22**, 357–362 (2013).
- Wei, M., Wei, K., Ichihara, M. & Zhou, H. Nb_2O_5 Nanobelts: A Lithium Intercalation Host with Large Capacity and High Rate Capability. *Electrochem. Commun.* **10**, 980–983 (2008).



20. Sasidharan, M., Gunawardhana, N., Yoshio, M. & Nakashima, K. Nb₂O₅ Hollow Nanospheres as Anode Materials for Enhanced Performance in Lithium Ion Batteries. *Mater. Res. Bull.* **47**, 2161–2164 (2012).
21. Kodama, R., Terada, Y., Nakai, I., Komaba, S. & Kumagai, N. Electrochemical and In situ XAFS-XRD Investigation of Nb₂O₅ for Rechargeable Lithium Batteries. *J. Electrochem. Soc.* **153**, A583–588 (2006).
22. Zhang, G. & Lou, X. Controlled Growth of NiCo₂O₄ Nanorods and Ultrathin Nanosheets on Carbon Nanofibers for High-Performance Supercapacitors. *Scientific Reports* **3**, 1470 (2013).
23. Yang, Q., Lu, Z., Sun, X. & Liu, J. Ultrathin Co₃O₄ Nanosheet Arrays with High Supercapacitive Performance. *Scientific Reports* **3**, 3537 (2013).
24. Yuan, C. *et al.* Growth of Ultrathin Mesoporous Co₃O₄ Nanosheet Arrays on Ni Foam for High-Performance Electrochemical Capacitors. *Energy Environ. Sci.* **5**, 7883–7887 (2012).
25. Hu, L. *et al.* CoMn₂O₄ Spinel Hierarchical Microspheres Assembled with Porous Nanosheets as Stable Anodes for Lithium-Ion Batteries. *Scientific Reports* **2**, 986 (2012).
26. Li, Q. *et al.* Design and Synthesis of MnO₂/Mn/MnO₂ Sandwich-Structured Nanotube Arrays with High Supercapacitive Performance for Electrochemical Energy Storage. *Nano Lett.* **12**, 3803–3807 (2012).
27. Li, H. *et al.* Amorphous Nickel Hydroxide Nanospheres with Ultrahigh Capacitance and Energy Density as Electrochemical Pseudocapacitor Materials. *Nat. Commun.* **4**, 1894 (2012).
28. Lee, J., Hall, A., Kim, J. & Mallouk, T. A Facile and Template-free Hydrothermal Synthesis of Mn₃O₄ Nanorods on Graphene Sheets for Supercapacitor Electrodes with Long Cycle Stability. *Chem. Mater.* **24**, 1158–1164 (2012).
29. Yang, S. *et al.* Bottom-up Approach toward Single-Crystalline VO₂-Graphene Ribbons as Cathodes for Ultrafast Lithium Storage. *Nano Lett.* **13**, 1596–1601 (2013).
30. Wang, Y., Zhong, Z., Chen, Y., Ng, C. T. & Lin, J. Controllable Synthesis of Co₃O₄ from Nanosize to Microsize with Large-Scale Exposure of Active Crystal Planes and Their Excellent Rate Capability in Supercapacitors Based on the Crystal Plane Effect. *Nano Res.* **4**, 695–704 (2011).
31. Nan, C. *et al.* Size and Shape Control of LiFePO₄ Nanocrystals for Better Lithium Ion Battery Cathode Materials. *Nano Res.* **6**, 469–477 (2013).
32. Wang, Z. *et al.* Template-free Synthesis of 3D Nb₃O₇F Hierarchical Nanostructures and Enhanced Photocatalytic Activities. *Phys. Chem. Chem. Phys.* **15**, 3249–3255 (2013).

Acknowledgments

This work was supported by the National Natural Science Foundation of China (No. 51402345, 2014M551677, No. 21433013, No. 21403287) and Suzhou Science and Technology Development Program (No. ZXG2013002).

Author contributions

M.N.L. designed and conducted the experiment. C.Y. and Y.G.Z. involved in the scientific discussions. M.N.L., C.Y. and Y.G.Z. wrote the manuscript.

Additional information

Competing financial interests: The authors declare no competing financial interests.

How to cite this article: Liu, M., Yan, C. & Zhang, Y. Fabrication of Nb₂O₅ Nanosheets for High-rate Lithium Ion Storage Applications. *Sci. Rep.* **5**, 8326; DOI:10.1038/srep08326 (2015).



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder in order to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>