

Two Dimensional Materials for Military Applications

Doğuş Özkan^{#,*}, M. Cenk Özekinci[@], Zeynep Taşlıçukur Öztürk[#], and Egemen Sulukan[#]

[#]National Defence University, Turkish Naval Academy, Tuzla-İstanbul - 34942, Turkey

[@]National Defence University, Barbaros Naval Science and Engineering Institute, Tuzla-İstanbul - 34942, Turkey

^{*}E-mail: dozkan@dho.edu.tr

ABSTRACT

This paper particularly focuses on 2D materials and their utilization in military applications. 2D and heterostructured 2D materials have great potential for military applications in developing energy storage devices, sensors, electronic devices, and weapon systems. Advanced 2D material-based sensors and detectors provide high awareness and significant opportunities to attain correct data required for planning, optimization, and decision-making, which are the main factors in the command and control processes in the military operations. High capacity sensors and detectors or energy storage can be developed not only by using 2D materials such as graphene, hexagonal boron nitride (hBN), MoS₂, MoSe₂, MXenes; but also by combining 2D materials to obtain heterostructures. Phototransistors, flexible thin-film transistors, IR detectors, electrodes for batteries, organic photovoltaic cells, and organic light-emitting diodes have been being developed from the 2D materials for devices that are used in weapon systems, chemical-biological warfare sensors, and detection systems. Therefore, the utilization of 2D materials is the key factor and the future of advanced sensors, weapon systems, and energy storage devices for military applications.

Keywords: 2D materials; Graphene; Sensors; Heterostructured 2D materials; Decision-making

1. INTRODUCTION

Materials have always been fundamental to engineering in constructing and developing applications¹. Therefore, developing new materials is an important research area for all fields of science^{2,3}. Material researches are shaped into the pertinent application field in which they are targeted or needed. Materials used in the air, land, or sea platforms of the military are produced by pure, alloy, or composite forms of metals and non-metallic substances to enhance military capabilities⁴. The durability of the devices or systems, especially under challenging conditions, is directly related to materials and their appropriate utilization. Durability and effective life-cycle of the weapon systems, military vehicles, and electronic devices highly depends on the strength and development level of the materials in the challenging operating conditions⁵. Advanced materials are the source of new technologies that any army requires for improved situational awareness, command-and-control, communication, and sensing to achieve success in the operation field⁶.

In military operations, systems consisted of advanced materials have a crucial role in the success of the operation and military organization from tactical to strategic level⁷. For example, some advanced materials are used to reflect or absorb radar emissions and infrared waves, providing stealth or deception for detection and tracking systems^{8,9}. Besides,

a variety of materials ranging from nano to macro scale are developed for sensor technologies such as detectors, and electronic card components like chips, microprocessors, and diodes^{10,11}. Specifically, sensors provide the required data to evaluate or optimize the required decision making in military operations^{12,13}. Moreover, advanced electronic devices such as processors or nano/microchips are essential to high-speed data and image processing, computing, and networking, especially to process and optimize big data. The performance of the processors or nano/microchips can be upgraded or novel variants can be developed by using advanced materials. These materials range from nanoscale like 2D materials in one-atom-thickness to macro scales¹⁴. 2D materials have been one of the most popular research fields of advanced materials over the past decade and the well-known 2D materials are graphene, MoS₂, hBN, WS₂, WSe₂. They can also be combined to create new materials with enhanced thermal, electronic, mechanical, or optoelectronic properties that are named heterostructures¹⁵. MXenes are other kinds of 2D materials with higher saturable absorption (SA) than the other 2D materials. Having higher SA (up to 50%) provides increased modulation depth for optical isolator applications¹⁶. This paper mainly focuses on advanced materials, including 2D materials and their utilization in military applications. 2D materials are the future of advanced military systems and 2D material researches are essential to developing novel, long-ranged/high capacity and advanced sensors, weapon systems, and energy storage devices for military applications.

2. BACKGROUND

Owing to their superior electrical, chemical, optical, thermal, structural, and mechanical properties, two-dimensional (2D) materials have been widely studied in the literature for several engineering applications¹⁷ as shown in Fig. 1. The above-stated properties can be exemplified as follows:

- (i) Electrical conductivity: Some 2D materials have high electron carrier capability like a mechanically exfoliated single-layer graphene that has a carrier mobility of 200000 $\text{cm}^2/(\text{V.s})$ ¹⁸.
- (ii) Thermal conductivity: The high thermal conductivity property of the 2D materials is the key factor to develop high performance and efficient energy storage, nanoelectronics, and optoelectronics devices¹⁹. Each 2D material has different lattice thermal conductivity, for example, the thermal conductivity of single-layer MoS_2 is reported to be 84 W/m.K whereas single-layer graphene can present the ultimate thermal conductivity of 4100 W/m.K ²⁰. This is originated from not only electrons but also phonons that account for the total thermal conductivity²¹.
- (iii) Optical properties: Within the 2D materials family, graphene has good optical transparency higher than 90% therefore, it can be used to develop new detector and sensor technologies²².
- (iv) Mechanical properties: 2D materials have high stiffness and strength properties with approximately one atomic thickness, as well as bending flexibility. Single-layer graphene in one atomic thickness has a hundred times higher strength than steel with 1 TPa elastic modulus²³. The van der Waals forces between layers determine the mechanical properties such as shear, friction, and fracture characteristics in multilayer 2D materials²⁴.
- (v) Chemical properties: Chemically inert 2D materials can make chemical absorption on their surface that yields a change in the electrical properties of 2D materials, this change is used to detect chemical or biological molecules information for developing sensor devices²⁵.

2D materials are crystalline materials that consist of a single or a few layers of atoms and are used as superconductors for electronic devices either pure or combined with other 2D materials to improve their desired ability such as thermal and electric conductivity²⁶. Furthermore, some of them have

good mechanical strength that is suitable for friction and wear reduction, which eventually increases the corrosion resistance in tribological systems²⁷. Therefore, 2D materials can be used as solid lubricants for the application in micro and nano-electromechanical systems (MEMS/NEMS), which are used to develop chemical or biological sensors for detection of chemical gasses and biological agents in chemical and biological warfare, identification friend or enemy (FOE) systems, active surfaces, distributed sensor network, micro-robotic electronic disabling systems²⁸.

2D materials have been a strong candidate for optoelectronic device applications such as photodetectors, light-emitting diodes, and photovoltaic devices²⁹. The most widely known and the precursor of the 2D materials are graphene, molybdenum disulfide (MoS_2), and hexagonal boron nitride (hBN) with one atom thickness (named single layer) or more than two layers (referred to as multi-layer)³⁰. Each of them has different properties that can be used in the different application fields; for example, graphene is found to be an excellent electrical conductor whereas hBN is an insulator with a large bandgap. However, contrary to electric conduction, hBN has better tribological properties than graphene, especially in high temperatures³¹. MoS_2 with different electrical, chemical, biological, and mechanical properties than other 2D materials are used in electronics, catalysis, biomedical, and energy-related fields as nanosheets³². Semiconductor MoS_2 can retrieve the weakness of the graphene band gap and is used in optoelectronic applications³³. 2D materials have great potential for military applications to develop energy storage devices, sensors, electronic devices, and armors. 2D materials can be used to develop cathodes having high power density, long-life and shorter start-up time for thermal batteries which are employed for power delivering to electricity supply, electronic and activation systems of guided missiles, torpedos, and rockets³⁴. To date research interest and trends in material science and technology have not only focused on understanding the behavior of these materials at the nanoscale, but also under extreme conditions at the macro-scale³⁵.

3. TWO DIMENSIONAL MATERIALS AND MILITARY APPLICATIONS

3.1 Graphene

Graphene has been the most attractive 2D material since it was discovered by Geim and Novoselov in 2004³⁶ and it has been the pathfinder of the 2D materials researches. Graphene consists of two-dimensional hexagonal lattice carbon atoms bonded with sp^2 covalent bonds³⁷. With superior properties such as chemical inertness, thermal stability, electrical conductivity, oxidation resistance, and mechanical strength, graphene is the most promising 2D material for all application fields³⁸. Graphene can be produced by two main methods that involve mechanically breaking layers of stacked graphite to get a single layer carbon atom, and synthesizing graphene from alternative carbon-containing sources^{39,40}.

In the first method, graphene is obtained via exfoliation of graphite mechanically by using Scotch tape or chemical exfoliation of graphite using as a sacrificial electrode in H_2SO_4 -KOH solutions⁴¹. The second method contains chemical vapor

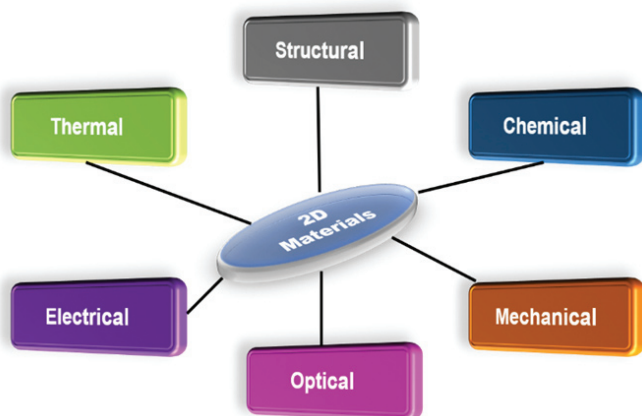


Figure 1. Properties of the two-dimensional (2D) materials.

deposition (CVD) that depends on the thermal decomposition of hydrocarbon and further deposition or accumulation on a substrate either in monolayer or multilayer as a Carbon nanosheet⁴² as shown in Fig. 2. CVD is the most common method for producing large scale graphene on active metals such as *Cu*, *Ni*, *Ru*, *Pt* and *Cu* either at ambient or vacuum pressure. *Cu* is one of the most commonly used substrates for graphene growth on a large scale due to its low diffusion barrier to carbon⁴³. In this method, graphene can be grown using *Ar*, *H₂*, and precursor Carbon sources like methane and acetylene⁴⁴ on copper, nickel in a high-temperature tube furnace (see Fig. 2(a)) at approximately 1000 °C by breaking the *C-H* bonds to form a layer consisted of *C-C* atoms. This layer is then transferred onto any desired surface by polymethyl methacrylate (PMMA)-mediated wet transfer method⁴⁵.

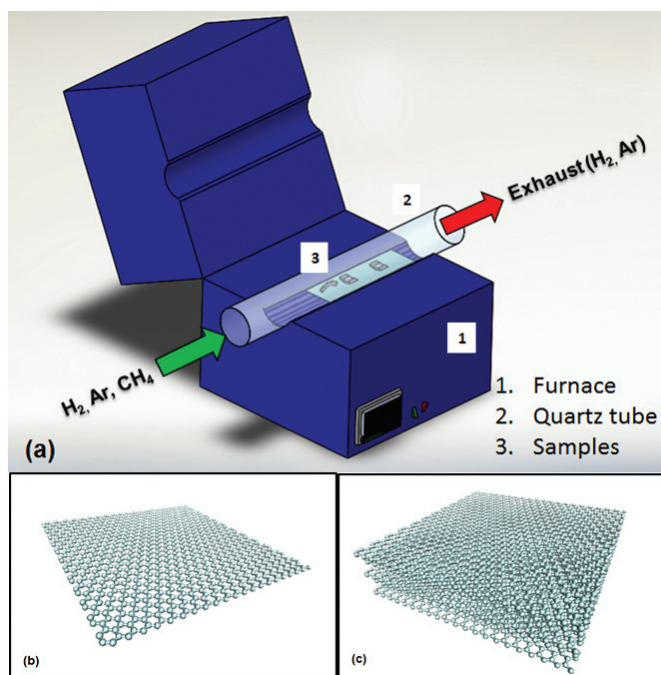


Figure 2. (a) CVD set up for graphene growth, (b) Monolayer graphene nanosheet image, and (c) multilayer graphene nanosheet image.

Molecular beam epitaxy (MBE) is another carbon sourced application of graphene growth. In this application, C_{60} and SiC sources are used to obtain the carbon flux molecular beams for thermally decomposed graphene growth at 1600 °C⁴⁶. Graphene is mostly characterized by Raman analysis using the 532 nm laser wavelength. The typical fingerprint of the graphene is the G and 2D peaks at 1570 and 2670 ± 20 cm^{-1} , respectively as shown in Fig. 3. The intensity ratio of I_G / I_{2D} identifies the layer number of graphene where the ratio increase with layers and $I_G / I_{2D} < 1$ indicates monolayer graphene, $1 < I_G / I_{2D} < 2$ and $I_G / I_{2D} > 3$ show bilayer and multilayer graphene⁴⁷. Fig. 3 shows Raman spectroscopy characterization of a large area of mono and multi-layer graphene that is grown by CVD and then transferred on to the AISI 316 steel surface by wet transfer method using PMMA. In addition to Raman spectroscopy characterization, X-ray diffraction, and X-ray photon spectroscopy are also used to characterize graphene.

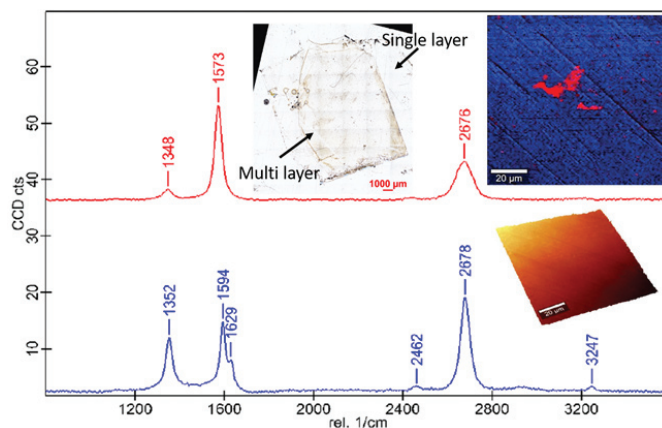


Figure 3. Raman mapping of a larger area monolayer and multilayer CVD grown graphene on a steel surface (Blue area with blue Raman spectrum is monolayer graphene and red area with Raman spectrum shows multilayer graphene on steel surface).

Single-layer graphene that is grown on the *Cu* sample shows no graphitic (002) peak whereas multilayer graphene shows the (002) graphitic peak at 26.5° indicating graphitic lattice spacing of 0.335 nm. *C1s* peak at a binding energy of 284.5 eV is attributed to typical *sp²* hybridized carbon atoms of graphene⁴⁸.

Mechanical characteristics of graphene were identified by AFM nanoindentation, scratching tests, and wear, friction behavior of graphene was evaluated via ball on disk tribometer tests. From the tribological aspect, graphene acts as a strong solid film with higher than 1 TPa reported elastic modulus between the sliding surfaces that reduces the friction and wear of the tribological system⁴⁹. Meanwhile, graphene nanoparticles have been added to the engine oil and tested against base oil in recent studies, where significant friction and wear reduction have been reported⁵⁰. However, there hasn't been any commercial tribological application of graphene in the military yet. Figure 4 demonstrates nanoscale friction force evaluation by atomic force microscopy of mono and multilayer graphene on the steel surface. A significant friction force reduction was observed for graphene at 50 nN loads.

Due to its higher mechanical strength than steel (tensile strength=0.4 GPa) with 130 GPa tensile strength, graphene has the potential to be a light ballistic armor material⁵¹. In the case of the application of multi-layer graphene, on-body armors will increase the mobility of the soldiers in the operation field. On the other hand, recent researches reported that hydrophobic graphene increases the corrosion resistance of the surfaces. Parasai⁵², *et al.* reported that graphene significantly reduces the oxidation of the metals and it is the thinnest corrosion protective coating.

Kousalya⁵, *et al.* reported that synthesized graphene on the copper surface can be an oxidation and corrosion protective coating for refrigeration systems that run in the liquid or liquid-vapor phase of refrigerant. Graphene has not been a commercial corrosion protection application yet due to the difficulty of large scale production and transfers to the desired surface. However, researches on large scale graphene coating or directly graphene growth on metals has still been continuing with different growth

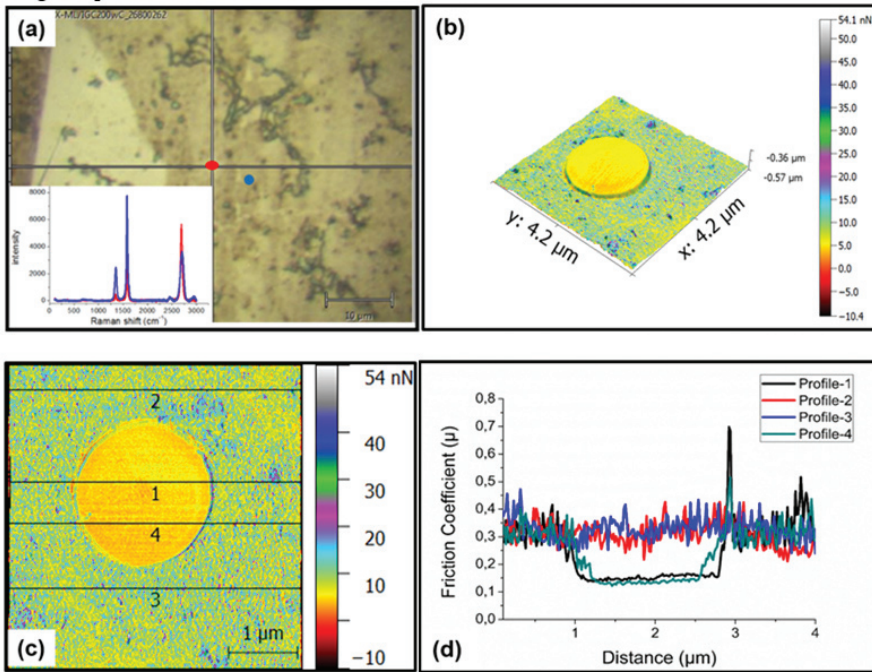


Figure 4. (a) Raman analysis of graphene on the steel surface showing monolayer (red dot and spectra) graphene and multilayer (blue dot and spectra) graphene, (b) friction force measurements of graphene overlaid topography image of graphene, (c) friction force profile extraction, (d) friction coefficients of extracted profiles.

methods⁵⁴. With the high corrosion resistance, graphene can be used to protect critical parts of the mechanical or electronic systems from the corrosion that are used especially in naval operations, e.g. unmanned aerial vehicles (UAV) or air/surface radars, aircraft. Due to its superconductivity, graphene can be used in electric/electronic applications as computer processors, antennas, and solar cells⁵⁵. On the other hand, quantum confinement and edge effects of graphene have been reported to cause photoluminescence (PL). Besides, by using quantum confinement effects, the fabrication size of quantum dots can be controlled to adjust the graphene bandgap and these dots have potential applications in a new generation of detection and microelectronics devices, biomedicine production⁵⁶. Its superior electrical property with low noise makes graphene an excellent sensor candidate that can be used in military applications such as pressure and humidity sensors⁵⁷.

The higher level of electrical conductivity and optical transmittance opens a path to graphene use in screens, liquid crystal displays, organic photovoltaic cells, and organic light-emitting diodes (OLEDs)⁵⁸. Especially, shatter-resistant graphene-made screens and touch panels can be used in military applications in hard operating conditions. A very specific surface area with high conductivity is the desired characteristic to develop electrodes for novel energy storage and batteries. Graphene has a very high specific surface area of 2675 m²/g compared to metals⁵⁹.

Graphene is a supercapacitor material with a specific surface area of 925 m²g⁻¹, the pore size of mainly 3-15 nm, and a specific capacitance of 117 Fg⁻¹ in H₂SO₄ electrolyte⁶⁰. Therefore, graphene is used as an electrode material for lithium-ion batteries enhancing the anode's conductivity in diverse phases of the charge-discharge cycle and capacity⁶¹

of the battery up to 1500 mAhg⁻¹. Therefore, graphene increases battery storage capacity, which means longer battery life for handheld radios used by units in the operation field⁶². Graphene was used to produce infrared (IR) transparent windows that can be used in IR guided missiles. On the other hand, owing to higher than 85 % IR transmittance, graphene is used as an IR sensor/detector for IR cameras or missile detectors as shown in Fig. 5 with desired electromagnetic (EM) shielding properties⁶³.

3.2 Hexagonal Boron Nitride

The two-dimensional hexagonal lattice boron nitride (2D-hBN) has a similar structure as graphene and is named as white graphene which is an electrically insulating, chemically, and thermally stable ceramic material⁶⁴. The bond length of B-N is 1.44

Å in hBN whereas the bond length of C-C is 1.45 Å in graphene as shown in Fig. 6⁶⁵. Single-layer h-BN can be synthesized on Pt and Cu foils via ambient/ low-pressure CVD by using a precursor-like borazine and ammonia-borane at 1000 °C or it can be produced from bulk crystalline h-BN exfoliation⁶⁶. The typical XRD peaks at 2θ = 26.3, 41.4, 43.5, 54.7, and 75.7 are identified as (002), (100), (101), (004), and (110) planes respectively of the hexagonal phase of BN (see Fig. 7(a))⁶⁷. The FT-IR spectrum of hBN

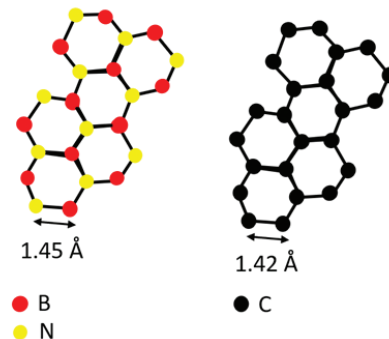


Figure 5. Structure of the IR seeker of the missile.

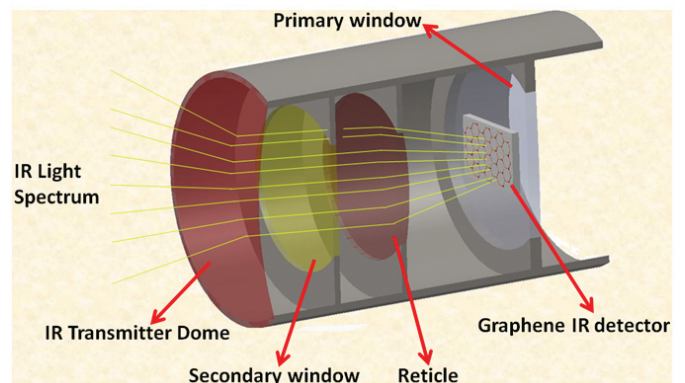


Figure 6. Structure and bond lengths of hBN and graphene.

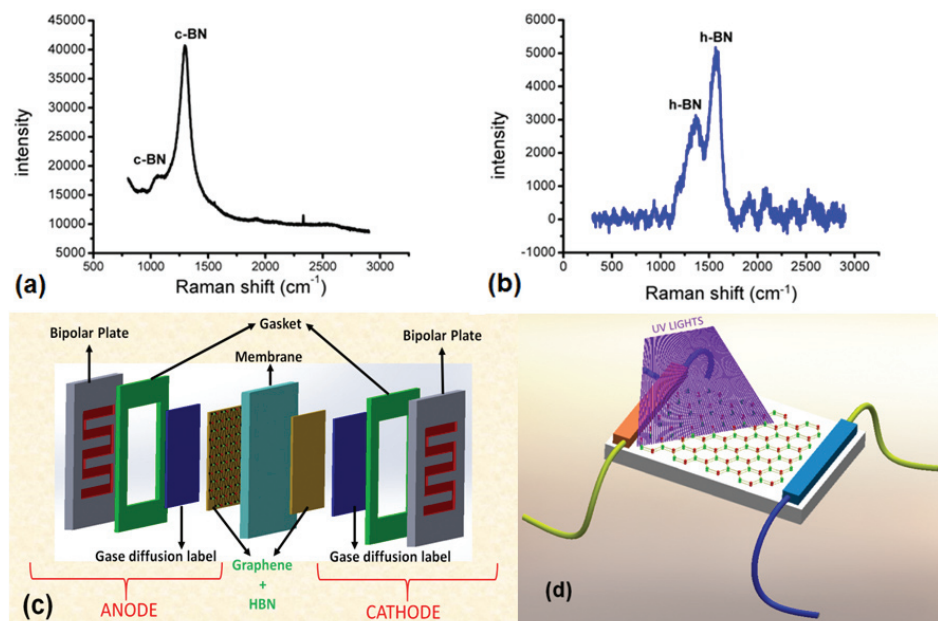


Figure 7. (a) Raman spectra of cBN, (b) Raman spectra of hBN, (c) Graphene-hBN heterostructure fuel cell, and (d) UV-photodetector.

shows two typical peaks at 1380 cm^{-1} and 805 cm^{-1} described as $B-N$ stretching vibration. In the XPS identification, BI_s peak at a binding energy of 190.2 eV is assigned to $B-N$ bonds of hBN⁶⁸.

The 2D hBN is characterized by Raman analysis with the determination of a typical sharp peak at $1360\text{-}1370\text{ cm}^{-1}$ wavelength in Raman spectra as shown in Fig. 7(b)⁶⁹ that arises from the E_{2g} phonon⁷⁰.

When looking at the mechanical properties of the 2D hBN, the tensile strength of the 2D hBN is reported to be $120\text{-}165\text{ GPa}$, and Young's modulus was found to be $0.8\text{-}1 \pm 0.1\text{ TPa}$ by AFM indentation measurements⁷¹. Due to this high mechanical strength and lower friction coefficient, it has been used as a solid lubricant in tribological systems⁷² or added into base oil as a nano additive in which it reduced wear approximately⁷³ 50% . The thermal conductivity of the few-layer 2D hBN nanosheet was measured to be $100\text{-}270\text{ W/m.K}$, which is a good heat spreading material for novel electronic devices⁷⁴. With these findings, it has been reported as a new material candidate against SiO_2 used in transistors⁷⁵. Although 2D hBN is an insulator material, it can be activated by graphene in fuel cells (see Fig. 7(c)) enhancing the cell performance up to 50% ⁷⁶. On the other hand, with the high band edge absorption coefficient, it can be utilized to develop UV photodetectors as shown in Fig. 7(d)⁷⁷.

3.3 Molybdenum Disulfide

The other popular 2D material is molybdenum disulfide (MoS_2) with unique electrical, physicochemical, biological, and mechanical properties⁷⁸. It can be produced by exfoliation of geological MoS_2 crystals, chemical vapor deposition (CVD), metalorganic chemical vapor deposition (MOCVD), and pulsed laser deposition (PLD) and then transferred onto the desired sample⁷⁹. MoS_2

consists of trigonal prismatic structure $S\text{-Mo-S}$ bonds (see Fig. 8(a))⁸⁰ with van der Waals interactions and typical Raman characterization show 2D MoS_2 peaks between $380\text{-}390$ and $400\text{-}410\text{ cm}^{-1}$ at Raman spectra⁸¹.

2D MoS_2 has been used to develop ultra-fast field-effect transistors (FETs), optical devices, and flexible electronic devices⁸². Besides, the hybrid heterostructure MoS_2 combined with graphene showed a good ability to sense gases⁸³. Thus, 2D MoS_2 can be used to produce low-powered, high-performance gas sensors to detect and monitor explosive and chemical gases for land and marine units, especially, in chemical warfare⁸⁴. The 2D MoS_2 has been used to develop phototransistors (see Fig. 8(b)), flexible thin-film transistors, and electrodes for lithium-ion batteries⁸⁵. For the tribological applications, single and multilayer MoS_2 nanosheets were added into a base oil and tested with a ball on the disk tribometer. It was reported that multilayered or two-dimensional MoS_2 nanosheets can be a commercial nano additive for the paraffin oil to improve friction and wear resistance properties⁸⁶. Besides, 2D MoS_2 was reported to be a good solid lubricant for relatively sliding mechanical components⁸⁷.

3.4 MXene 2D Materials

2D transition metal carbides, nitrides or carbonitrides have been introduced as MXene with a chemical formula of $M_n + 1YnTx$, where M is the transition metal (such as $Sc, Ti, Zr, Hf, V, Nb, Ta, Cr, Mo, Mn$), Y is the carbon or nitrogen, T is the functional groups such as $=O$ or $-OH$ ($n=1\text{-}3$). They are produced by extracting the Y element from three-dimensional (3D) MYT phases with acidic chemical reactions⁸⁸. They have great potential to develop photothermal conversion, field-effect transistors, topological insulators, optoelectronic properties, sensors, and hydrogen evolution reactions⁸⁹. Furthermore, they have better saturable absorption (SA is up to 50%) than other 2D materials such as graphene and MoS_2 (SA is up to 20%), which is used to increase modulation depth for optical isolator applications in fiber-based femtosecond lasers. Therefore, they can be used in weapon systems such

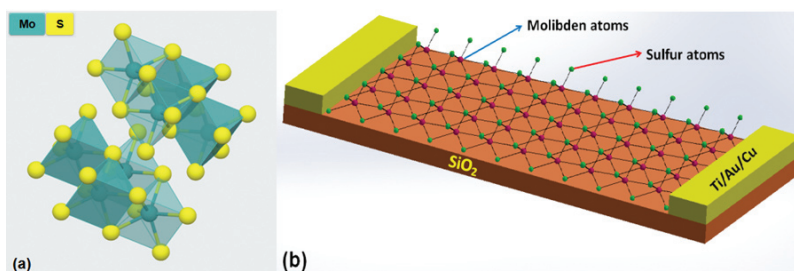


Figure 8. (a) Structure of MoS_2 and (b) Schematic view of the fabricated multi-layer MoS_2 phototransistor.

as FLIR cameras, targeting pods, especially they could be a solution to overheating of the laser power supply of targeting pods that cause missiles to fall into ballistic guidance⁹⁰. Moreover, recent studies have been reported higher effective Young's modulus of 330 ± 30 GPa than 2D MoS₂, GO, r-GO, however, lower than graphene and hBN. This high elasticity suggests protective coatings, membranes, and nanoresonators for military applications⁹¹.

3.5 Heterostructured 2D Materials

Graphene derived from exfoliation of the graphite is the flagship of the 2D materials researches and has also accelerated researches on heterostructure 2D materials which are carried out directly stacking individual monolayers of 2D materials such as WSe₂, MoTe₂, WS₂-MoS₂, WSe₂-SnS₂, hBN-graphene, MoS₂-graphene. The combination of these 2D materials forms heterostructures that enable excellent electron transfer. They also have specific properties that open new paths to novel researches for military applications including transistors, photodetectors, chemical, and biological sensors, and nanoelectromechanical systems. For example, the combination of graphene and black phosphorus provides rich novel light-substance interaction phenomena, like photothermoelectric, and various other optoelectronic effects which have the great potential to develop new IR detectors for military applications⁹². Development of the flexible gas sensor by using MoS₂/graphene heterostructure material was reported by Cho⁹³, *et al.* With this sensor, hazardous/toxic gases can be detected and it has potential usage in chemical gas detection systems for military applications. Heterostructured 2D materials researches on developing energy storage systems have been significant in recent years to replace lithium-ion batteries with a new energy storage technology that has the ultimate fast charge capacity and long effective life⁹⁴. Graphene-based Na⁺, K⁺, Mg²⁺, and Al₃⁺ electrodes are in the scope of this researches. Graphene-based silicene, borophene, phosphorene 2D heterostructures are new electrode candidates for future energy storage devices⁹⁵. The development of new energy storage devices can lead to an upgrade in the diesel-electric submarine propulsion system. Thanks to 2D heterostructure wearable sensing systems, flexible/stretchable electronics devices and novel sensors (pressure, humidity, etc.) could be developed for military applications to be used in infantry units⁹⁶. The Moire patterns (an involvement pattern produced by overlaying similarly structured monolayer materials, but slightly rotated in any direction) are formed by 2D mono-layer van der Waals stacking materials such as MoS₂/MoSe₂ as shown in Fig. 9. These materials with high electron mobility are reported to have great potential for the development of nanodevices⁹⁷. Therefore, the production of vertical or lateral heterostructures from two-dimensional materials opens a gate to quantum-engineered transistors which will be the alternative silicon technology for sensors, electronic devices, and computers⁹⁸.

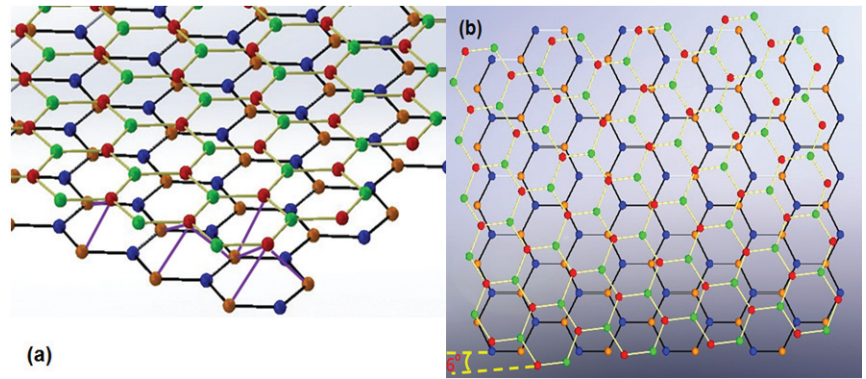


Figure 9. (a) Structure of 2D mono-layer MoS₂/MoSe₂, and (b) Top view of MoS₂/MoSe₂.

Additionally, MXenes/graphene heterostructures have been explored for battery cathodes and their positive effects on capacity compared to functionalized MXenes have been reported⁹⁹.

4. CONCLUSION

Advanced materials are going to be key for the future of the state of the art device developments, where 2D materials have an important role in this development process. Sensors, MEMs, electronic devices that use diodes, chips, transistors; and energy storage systems such as batteries and fuel cells will be more effective by using 2D materials than conventional ones. With the large application field, 2D materials have many advanced technological benefits to the military for critical applications such as thermal batteries for missile systems. Advanced 2D material based sensors and detectors will give a significant opportunity to attain correct data that is needed for planning, optimization, and decision-making which are the main factors in the command and control process in the military operations. Development and commercialization of advanced 2D materials require models including materials and systems. In the material model, the nanostructure is the output of the application field. The system model includes requirements and environment as inputs where performance, costs, safety, reliability, and durability are the outputs. To achieve any product based on advanced 2D materials robust optimization between these models is needed. Therefore, interdisciplinary work must be conducted between the fundamental sciences, and respective engineering fields; i.e. mechanical, electrical, electronic, and industrial engineers in developing advanced 2D materials based systems for military applications.

REFERENCES

1. Shubha, G.N.; Tejaswini, M.L. & Lakshmi, K.P. Advanced material for newer applications. *Mater. Today: Proc.*, 2018, **5**(1), 2541-2546. doi: 10.1016/j.matpr.2017.11.037
2. Krishtop, V.G.; Zhevnenko, D.A.; Gornev, E.G.; Vergeles, S.Y.; Bugaev, Alexander S.; Popov, Vladimir G.; Dudkin, Pavel V.; Kohanovsky, Sergey V. And Krishtop, Tatyana V. Technology and application of electrochemical motion sensors. *Adv. Mater. Proc.*, 2019, **4**(1), 03-09.

- doi: 10.1002/admt.201900251
3. Zhao, G.; Di, W. & Wang, M. Application of advanced materials in petroleum engineering. *Energy Materials*, 2014, 767-773.
doi: 10.1002/9781119027973.ch94
 4. Büch, H.; Rossi, A.; Forti, S.; Convertino, D; Tozzini, Valentina & Coletti, Camilla. Superlubricity of epitaxial monolayer WS₂ on graphene. *Nano Research*, 2018, **11**(11), 5946–956.
doi: 10.1007/s12274-018-2108-7
 5. National Research Council. Opportunities in protection materials science and technology for future army applications. Washington, DC: *The Nat. Acad. Press*, 2011, 20-25.
doi: 10.17226/13157
 6. O'Regan, T. & Perconti, P. 2D electronic materials for army applications. Micro and nanotechnology sensors, systems, and applications VII. *Proc. SPIE*, 2015, 9467, 94670S.
doi: 10.1117/12.2178401
 7. National Research Council. Materials research to meet 21st-century defense Needs. Washington, DC: *The Nat. Acad. Press*, 2003, 13-16.
doi: 10.17226/10631
 8. National Academies of Sciences, Engineering, and medicine. frontiers of materials research: A decadal survey. Washington, DC: *The Nat. Acad. Press*, 2019, 26-30.
doi: 10.17226/25244
 9. National Research Council. High-performance synthetic fibers for composites. Washington, DC: *The Nat. Acad. Press*, 1992, 9-11.
doi: 10.17226/1858
 10. Gogotsi, Y. Energy storage wrapped up. *Nature*, 2014, **509** (7502), 568–569.
doi: 10.1038/509568a
 11. Rogalski, A. Infrared detectors: An overview. *Infrared Phys. Technol.*, 2002, **43**(3–5), 187-210.
doi: 10.1016/S1350-4495(02)00140-8
 12. Reshke, R. Brave new conflicts: Emerging global technologies and trends. *Jad. Pap.*, 2007, **1**, 11-54.
 13. Singh, M.; Khare, S. & Kaushik, B. Performance improvement of electro-optic search and track system for maritime surveillance. *Def. Sci. J.*, 2020, **70**(1), 66-71
doi: 10.14429/dsj.70.13824
 14. Gong, Z.; Jia, X.; Ma, W.; Zhang, B. & Zhang, J. Hierarchical structure graphitic-like/MoS₂ film as superlubricity material. *Appl. Surf. Sci.*, 2017, **413**, 381-386.
doi: 10.1016/j.apsusc.2017.04.057
 15. Guo, J.; Legum, B.; Anasori, B.; Wang, K.; Lelyukh, P.; Gogotsi, Y. & Randall, C.A. Cold sintered ceramic nanocomposites of 2D MXene and Zinc Oxide. *Advanced Materials*, 2018, **30** (32), 1801846.
doi: 10.1002/adma.201801846
 16. Zhu, J.; Ha, E; Zhao, G.; Zhou, Y.; Huang, D.; Yue, G.; Hu, L.; Sun, Ning; Wang, Yong; Lee, L.Y.S.; Xu, Chen; Wong, Kwok-Yin; Astruc, D. & Zhao, P. Recent advance in MXenes: A promising 2D material for catalysis, sensor and chemical adsorption. *Coordin. Chem. Rev.*, 2017, **352**, 306-327.
doi:10.1016/j.ccr.2017.09.012
 17. Kiran, N.U.; Dey, S.; Singh, B.P. & Besra, L. Graphene coating on copper by electrophoretic deposition for corrosion prevention. *Coatings*, 2017, **7**(214), 1-13.
doi: 10.3390/coatings7120214
 18. Kim, J.S., Choi, K., Lee, B., Kim, Y. & Hong, B.Y. Materials for flexible, stretchable electronics: Graphene and 2D materials. *Annu. Rev. Mater. Res.*, 2015, **45** (1), 63–84.
doi: 10.1146/annurev-matsci-070214-020901
 19. Zhu, G.; Liu, J.; Zheng, Q.; Zhang, R.; Li, D.; Banerjee, D. & Cahill, D.G. Tuning thermal conductivity in molybdenum disulfide by electrochemical intercalation. *Nature Communications*, 2016, **7**, 13211.
doi: 10.1038/ncomms13211
 20. Gu, X.; Li, B. & Yang, R. Layer thickness-dependent phonon properties and thermal conductivity of MoS₂. *J. Appl. Phys.*, 2016, **119**(8), 085106.
doi: 10.1063/1.4942827
 21. Peng, B.; Zhang, H.; Shao, H.; Xu, Yuchen; Zhang, Xiangchao & Zhu, H. Low lattice thermal conductivity of stanene. *Scientific Reports*, 2016, **6**(1), 20225.
doi: 10.1038/srep20225
 22. Gao, L. Flexible device applications of 2D semiconductors. *Small*, 2017, **13**(35), 1603994.
doi: 10.1002/smll.201603994
 23. Kim, J. H.; Jeong, J. H.; Kim, N.; Joshi, R. & Lee, G.H. Mechanical properties of two-dimensional materials and their applications. *J. Phys. D: Appl. Phys.*, 2019, **52**, 083001.
doi: 10.1088/1361-6463/aaf465
 24. Androulidakis, C.; Zhang, K.; Robertson, M. & Tawfik, S. Tailoring the mechanical properties of 2D materials and heterostructures. *2D Materials*, 2018, **5**(3), 032005.
doi: 10.1088/2053-1583/aac764
 25. Mannix, A.J.; Kiraly, B.; Hersam, M.C. & Guisinger, N.P. Synthesis and chemistry of elemental 2D materials. *Nat. Rev. Chem.*, 2017, **1**(2), 0014.
doi: 10.1038/s41570-016-0014
 26. Geng, X. & Yi, J. Chapter 6 - The Development of High-temperature superconductors and 2D iron-based superconductors. *In Micro and Nano Technologies. Nano-Sized Multifunct. Mater.*, 2019, 117-144.
doi: 10.1016/B978-0-12-813934-9.00006-2
 27. Yi, M. & Zhang, C. The synthesis of two-dimensional MoS₂ nanosheets with enhanced tribological properties as oil additives. *RSC Advances*, 2018, **8**(17), 9564-9573.
doi: 10.1039/C7RA12897E
 28. Brendley, K.W. & Steeb, R. Military applications of microelectromechanical systems. *Nat. Def. Res. Inst.*, 1993.
 29. Zhang, W.; Wang, Q.; Chen, Y.; Wang, Z. & Wee, T.S.A. Van der Waals stacked 2D layered materials for optoelectronics. *2D Materials*, 2016, **3**(2), 022001.
doi: 10.1088/2053-1583/3/2/022001
 30. Mounet, N.; Gibertini, M.; Schwaller, P.; Campi, D.; Merkys, A.; Marrazzo, A.;Sohier, T.; Castelli, I. E. ;

- Cepellotti, A.; Pizzi, G. & Marzari, N. Two-dimensional materials from high-throughput computational exfoliation of experimentally known compounds. *Nature Nanotechnology*, 2018, **13**(3), 246–252. doi: 10.1038/s41565-017-0035-5
31. Liu, Z.; Gong, Y.; Zhou, W.; Ma, L.; Yu, J.; Idrobo, J. C.; Jung, J.; MacDonald, A.H.; Vajtai, R.; Lou, J. & Ajayan, P. M. Ultrathin high-temperature oxidation-resistant coatings of hexagonal boron nitride. *Nature Communications*, 2013, **4**(1), 2541. doi: 10.1038/ncomms3541
 32. Wang, Z. & Mi, B. Environmental Applications of 2D Molybdenum Disulfide (MoS₂) nanosheets. *Envir. Sci. Technol.*, 2017, **51**(15), 8229–8244. doi: 10.1021/acs.est.7b01466
 33. Zhang, S.; Ma, T.; Erdemir, A. & Li, Q. Tribology of two-dimensional materials: From mechanisms to modulating strategies. *Materials Today*, 2019, **26**, 67–86. doi: 10.1016/j.mattod.2018.12.002
 34. Mensah, T.O.; Wang, B.; Bothun, G.; Winter, J. & Davis, V. Nanotechnology commercialization: Manufacturing processes and products. Wiley, 2018, 169–172, USA. doi: 10.1002/9781119371762
 35. Zagorac D.; Zagora J.; Djukic M.; eJordanov, D.; Rosic, M.; Cebela, M.; Lukovic, J.; Maksimovic, V.; & Matovic, B. Theoretical investigation of structural, mechanical, elastic and vibrational properties of advanced materials under extreme conditions. *Procedia Struct. Integrity*, 2018, **13**, 2005–2010. doi: 10.1016/j.prostr.2018.12.216
 36. Geim, A. & Novoselov, K. The rise of graphene. *Nanosci. Technol.*, 2007, **6**, 183–191. doi: 10.1142/9789814287005_0002
 37. Randviir, E.P.; Brownson, D.A.C. & Banks, C.E. A decade of graphene research: Production, applications, and outlook. *Materials Today*, 2014, **17**(9), 426–32. doi: 10.1016/j.mattod.2014.06.001
 38. Chen, X.; Zhang, L. & Chen, S. Large area CVD growth of graphene. *Synthetic Metals*, 2015, **210**, 95–108. doi: 10.1016/j.synthmet.2015.07.005
 39. Edwards, R. S. & Coleman, K. S. Graphene synthesis: relationship to applications. *Nanoscale*, 2013, **5**(1), 38–51. doi: 10.1039/c2nr32629a
 40. Joshi, S.; Kumar, A. & Zaidi, M. Effect of nanographite on electrical mechanical and wear characteristics of graphite epoxy composites. *Def. Sci. J.*, 2020, **70**(3), 306–312. doi: 10.14429/dsj.70.15357
 41. Englert, J.M.; Röhrli, J.; Schmidt, C.D.; Graupner, R.; Hundhausen, M.; Hauke, F. & Hirsch, A. Soluble Graphene: Generation of aqueous graphene solutions aided by a perylenebisimide-based bolaamphiphile. *Advanced Materials*, 2009, **21**(42), 4265–4269. doi: 10.1002/adma.200901578
 42. Li, Y. & Chopra, N. Progress in large-scale production of graphene. Part 2: Vapor methods. *JOM-J. Min. Met. Mat. S.*, 2014, **67**(1), 44–52. doi: 10.1007/s11837-014-1237-z
 43. Seah, C.M.; Chai, S.P. & Mohamed, A.R. Mechanisms of graphene growth by chemical vapor deposition on transition metals. *Carbon*, 2014, **70**, 1–21. doi: 10.1016/j.carbon.2013.12.073
 44. Reina, A.; Jia, X.T.; Ho, J.; Nezich, D.; Son, H.; Bulovic, V.; Dresselhaus, M.S. & Kong, J. Large area, few-layer graphene films on arbitrary substrates by chemical vapor deposition. *Nano Letters*, 2009, **9**(1), 30–35. doi: 10.1021/nl801827v
 45. Nandanapalli, K.R.; Mudusu, D. & Lee, S. Functionalization of graphene layers and advancements in device applications. *Carbon*, 2019, **152**, 954–985. doi: 10.1016/j.carbon.2019.06.081
 46. Park, J.; Mitchel, W. C.; Grazulis, L.; Smith, H. E.; Eyink, K. G.; Boeckl, J. J. & Hoelscher, J. E. Epitaxial Graphene growth by carbon molecular beam epitaxy (CMBE). *Advanced Materials*, 2010, **22**(37), 4140–145. doi: 10.1002/adma.201000756
 47. Ni, Z.H.; Wang, H.M.; Kasim, J.; Fan, H.M.; Yu, T.; Wu, Y.H.; Feng, Y.P.; Shen, Z.X. Graphene thickness determination using reflection and contrast spectroscopy. *Nano Letters*, 2007, **7**(9), 2758–2763. doi: 10.1021/nl071254m
 48. Choudhury, D.; Das, B.; Sarma, D. D. & Rao, C. N. R. XPS evidence for molecular charge-transfer doping of graphene. *Chem. Phys. Lett.*, 2010, **497**(1–3), 66–69. doi: 10.1016/j.cplett.2010.07.089
 49. Berman, D.; Erdemir, A. & Sumant, A.V. Graphene: A new emerging lubricant. *Materials Today*, 2014, **17**(1), 31–42. doi: 10.1016/j.mattod.2013.12.003
 50. Ali, M. & Xianjun, H. Improving the tribological behavior of internal combustion engines via the addition of nanoparticles to engine oils. *Nanotechnol. Reviews*, 2015, **4**(4), 347–358. doi: 10.1515/ntrev-2015-0031
 51. Reyes, L.; Loganathan, A.; Boesl, B. & Agarwal, A. Effect of 2D boron nitride nanoplate additive on tribological properties of natural oils. *Tribology Letters*, 2016, **64**(3), 41. doi: 10.1007/s11249-016-0778-4
 52. Bordignon, R.; Salvaro, D.; Binder, C.; Klein, Aloisio N.; Drago, Valderes & de Mello, J.D.B. Tribological behaviour of plasma-functionalized graphene as low-viscosity oil additive. *Tribology Letters*, 2018, **66** (3), 114. doi: 10.1007/s11249-018-1065-3
 53. Lee, C.X.; Wei, X.; Kysar, J. W. & Hone, J. Measurement of the elastic properties and intrinsic strength of monolayer graphene. *Science*, 2008, **321**(5887), 385–88. doi: 10.1126/science.1157996
 54. Prasai, D.; Tuberquia, J.C.; Harl, R.R.; Jennings, G.K. & Bolotin, K.I. Graphene: Corrosion-inhibiting coating. *ACS Nano*, 2012, **6**(2), 1102–1108. doi: 10.1021/nn203507y
 55. Kousalya, A.S.; Kumar, A.; Paul, R.; Zemlyanov, D. & Fisher, T.S. Graphene: An effective oxidation barrier coating for liquid and two-phase cooling systems. *Corrosion Science*, 2013, **69**, 5–10. doi: 10.1016/j.corsci.2012.12.014
 56. Wang, G.; Shen X.; Yao, J. & Park J. Graphene nanosheets for enhanced lithium storage in lithium-ion batteries. *Carbon*, 2009, **47**(8), 2049–53.

- doi: 10.1016/j.carbon.2009.03.053
57. Karthick, R. & Chen, F. Free-standing graphene paper for energy application: Progress and future scenarios. *Carbon*, 2019, **150**, 292-310.
doi: 10.1016/j.carbon.2019.05.017
 58. Zhu, S.; Zhang, J.; Qiao, C.; Tang, S.; Li, Y.; Yuan, W.; Li, Bo; Tian, Lu; Liu, Fang; Hu, Rui; Gao, H.; Wei, H.; Zhang, H.; Sun, H. & Yang, B. Strongly green-photoluminescent graphene quantum dots for bioimaging applications. *Chem. Comm.*, 2011, **47**(24), 6858-860.
doi: 10.1039/c1cc11122a
 59. Choi, W.; Lahiri, I.; Seelaboyina, R. & Kang, Y.S. Synthesis of graphene and its applications: A Review. *Crit. Rev. Solid State Mater. Sci.*, 2010, **35**(1), 52-71.
doi: 10.1080/10408430903505036
 60. Neto, C.A.H.; Guinea, F.; Peres, N.M.R.; Novoselov, K.S. & Geim, A.K. The electronic properties of graphene. *Rev. Mod. Phys.*, 2009, **81** (1), 109-162.
doi: 10.1103/RevModPhys.81.109
 61. Cranford, S.W. & Buehler, M.J. Packing efficiency and accessible surface area of crumpled graphene. *Physical Review B*, 2011, **84**(20).
doi: 10.1103/PhysRevB.84.205451
 62. Du, X.; Guo, P.; Song, H. & Chen, X. Graphene nanosheets as electrode material for electric double-layer capacitors. *Electrochimica Acta*, 2010, **55**(16), 4812-4819.
doi: 10.1016/j.electacta.2010.03.047
 63. Wang, G.; Wang, B.; Park, J.; Wang, Y.; Sun, B. & Yao, J. Highly efficient and large-scale synthesis of graphene by electrolytic exfoliation. *Carbon*, 2009, **47**(14), 3242-246.
doi: 10.1016/j.carbon.2009.07.040
 64. Tassin, P.; Koschny, T.; Kafesaki, M.; Soukoulis, C.M. A comparison of graphene, superconductors, and metals as conductors for metamaterials and plasmonics. *Nature Photonics*, 2012, **6**(4), 259-64.
doi: 10.1038/nphoton.2012.27
 65. Han, J.; Wang, X.; Qiu, Y.; Zhu, J. & Hu, P. Infrared-transparent films based on conductive graphene network fabrics for electromagnetic shielding. *Carbon*, 2015, **87**, 206-214.
doi: 10.1016/j.carbon.2015.01.057
 66. Zhang, K.; Feng, Y.; Wang, Y.; Yanga, Z. & Wang, J. Two-dimensional hexagonal boron nitride (2D-hBN): synthesis, properties, and applications. *J. Mater. Chem. C*, 2017, **5**(46), 11992-12022.
doi: 10.1039/C7TC04300G
 67. Li, H.L. & Chen, Y. Atomically thin boron nitride: Unique properties and applications. *Adv. Funct. Mater.*, 2016, **26**(16), 2594-2608.
doi: 10.1002/adfm.201504606
 68. Kim, J.H.; Jeong, J.H.; Kim, N.; Joshi, R. & Lee, G.-H. Mechanical properties of two-dimensional materials and their applications. *J. Phys. D: Appl. Phys.*, 2019, **52**, 083001.
doi: 10.1088/1361-6463/aaf465
 69. Son, M.; Lim, H.; Hong, M. & Choi, H.C. Direct growth of graphene pad on exfoliated hexagonal boron nitride surface. *Nanoscale*, 2011, **3**(8), 3089.
doi: 10.1039/c1nr10504c
 70. Ismach, A.; Chou, H.; Ferrer, D.A.; Wu, Y.; McDonnell, S.; Floresca, H.C.; Covacevich, A.; Pope, C.; Piner, R.; Kim, M.J.; Wallace, R.M.; Colombo, L. & Ruoff, R.S. Toward the controlled synthesis of hexagonal Boron Nitride films. *ACS Nano*, 2012, **6**(7), 6378-385.
doi: 10.1021/nn301940k
 71. Li, X.; Sun, M.; Shan, C.; Chen, Q. & Wei, X. Mechanical properties of 2D materials studied by in situ microscopy techniques. *Adv. Mater. Interfaces*, 2018, **5**(5)1701246.
doi: 10.1002/admi.201701246
 72. Zhi, C.; Bando, Y.; Tang, C.; Kuwahara, H. & Golberg, D. Large-scale fabrication of Boron Nitride Nanosheets and their utilization in polymeric composites with improved thermal and mechanical properties. *Advanced Materials*, 2009, **21**(28), 2889-893.
doi: 10.1002/adma.200900323
 73. Deepika, Li. H.L.; Glushenkov, A.M.; Hait, S.K., Hodgson, P. & Chen, Y. High-efficient production of boron nitride nanosheets via an optimized ball milling process for lubrication in oil. *Scientific Reports*, 2014, **4**(1), 1-6.
doi: 10.1038/srep07288
 74. Lindsay, L. & Broido, D. A. Enhanced thermal conductivity and isotope effect in single-layer hexagonal boron nitride. *Physical Review B*, 2011, **84**(15), 035436.
doi: 10.1103/PhysRevB.84.155421
 75. Huo, C.; Yan, Z.; Song, X. & Zeng, H. 2D materials via liquid exfoliation: a review on fabrication and applications. *Science Bulletin*, 2015, **60**(23), 1994-2000.
doi: 10.1007/s11434-015-0936-3
 76. Balakrishnan, P. & Holmes, S. 2D materials graphene and hBN boost DMFC performance. *Fuel Cells Bull.*, 2017, **4**, 14. doi: 10.1021/acs.est.7b01466
 77. Wang, Z. & Mi, B. Environmental applications of 2D molybdenum disulfide (MoS₂) Nanosheets. *Environ. Sci. Technol.*, 2017, **51**(15), 8229-8244.
doi: 10.1021/acs.est.7b01466
 78. Dumcenco, D.; Ovchinnikov, D.; Marinov, K.; Lazić, P.; Gibertini, M.; Marzari, N.; Sanchez, O.P.; Kung, Yen-Cheng; Krasnozhan, D.; Chen, Ming-Wei; Bertolazzi, S.; Gillet, P.; i-Morral, A.F.; Radenovic, A. & Kis, A. Large-area epitaxial monolayer MoS₂. *ACS Nano*, 2015, **9**(4), 4611-4620.
doi: 10.1021/acsnano.5b01281
 79. Persson, Kristin. Materials Data on MoS₂ by Materials Project. United States, 2020. <https://materialsproject.org/materials/mp-1018809/>, [Accessed on 20 December 2019]. doi: 10.17188/1350454
 80. Lee, C.; Yan, H.; Brus, L.E.; Heinz, T.F.; Hone, J. & Ryu, S. Anomalous lattice vibrations of single- and few-layer MoS₂. *ACS Nano*, 2010, **4**(5), 2695-2700.
doi: 10.1021/nn1003937
 81. Ruzmetov, D.; Zhang, K.; Stan, G.; Kalanyan, B.; Bhimanapati, G.R.; Eichfeld, S.M.; Burke, R. A.; Shah, P. B.; O'Regan, T.P.; Crowne, F.J.; Birdwell, A.G.; Robinson, J.A.; Davydov, A.V.; & Ivanov, T.G. Vertical 2D/3D semiconductor heterostructures based on Epitaxial Molybdenum Disulfide and Gallium Nitride. *ACS Nano*,

- 2016, **10**(3), 3580-3588.
doi: 10.1021/acsnano.5b08008
82. Bag, A. & Lee, N.E. Gas sensing with heterostructures based on two-dimensional nanostructured materials: A review. *J. Mater. Chem. C*, 2019, **7**(43),13367-13383.
doi: 10.1039/C9TC04132J
 83. Cheng, H. H.; Zhao, Y.; Fan, Y. Q.; Xie, X. J.; Qu, L. T. & Shi, G. Q. Graphene-quantum-dot assembled nanotubes: A new platform for efficient Raman enhancement. *ACS Nano*, 2012, **6**, 2237–2244. doi: 10.1021/nm204289t
 84. Mak, K.F.; Lee, C.; Hone, J.; Shan, J. & Heinz, T. F. Atomically thin MoS₂: A new direct-gap semiconductor. *Phys. Rev. Lett.*, 2010, **105**, 136805.
doi: 10.1103/PhysRevLett.105.136805
 85. Yi, M. & Zhang, C. The synthesis of two-dimensional MoS₂ nanosheets with enhanced tribological properties as oil additives. *RSC Advances*, 2018, **8**(17), 9564-9573.
doi: 10.1039/C7RA12897E
 86. Vazirisereshk, M.R.; Martini, A.; Strubbe, D.A.; Baykara, M.Z. Solid Lubrication with MoS₂: A review. *Lubricants*, 2019, **7**(7), 57. doi: 10.3390/lubricants7070057
 87. Zribi, J.; Khalil, L.; Zheng, B.; Avila, J.; Pierucci, D.; Brule, T.; Chaste, J.; Lhuillier, E.; Asensio, M.C.; Pan, A.; & Ouerghi, A. Strong interlayer hybridization in the aligned SnS₂/WSe₂ hetero-bilayer structure. *NPJ 2D Mater. Appl.*, 2019, **3**(1), 27.
doi: 10.1038/s41699-019-0109-3
 88. Zhang, X.; Zhang, Z. & Zhou, Z. MXene-based materials for electrochemical energy storage, *J. Energy Chem.*, 2018, **27**(1), 73-85. doi:10.1016/j.jchem.2017.08.004
 89. Lee, E.; VahidMohammadi, A.; Prorok, B.C.; Yoon, Y.S.; Beidaghi, M. & Kim, D.-J. Room temperature gas sensing of two-dimensional titanium carbide (MXene). *ACS Appl. Mater. Inter.*, 2017, **9** (42), 37184-37190.
doi: 10.1021/acsnano.5b08008
 90. Dong, Y.; Chertopalov, S.; Maleski, K.; Anasori, B.; Hu, L.; Bhattacharya, S.; Rao, A.M.; Gogotsi, Y.; Mochalin, V.N.; Podila, R. Saturable Absorption in 2D Ti₃C₂ MXene thin films for passive photonic diodes, *Advanced Materials*, 2018, **30**(10), 1705714.
doi: 10.1002/adma.201705714
 91. Anasori, B. & Gogotsi, Y. 2D Metal Carbides and Nitrides (MXenes): Structure, properties and applications. Springer International Publishing, Switzerland. 2019, 378-380.
doi: 10.1007/978-3-030-19026-2
 92. Nourbakhsh, A.; Yu, L.; Lin, Y.; Hempel, M.; Shiue, R.-J.; Englund, D. & Palacios, T. Heterogeneous integration of 2D materials and devices on a Si platform. beyond-CMOS technologies for next generation computer design, edited by Topaloglu, R.,O.; Wong, P. H.S. Springer International Publishing, Switzerland, 2019, 43–84.
doi: 10.1007/978-3-319-90385-9_3
 93. Cho, B.; Yoon, J.; Lim, S.K.; Kim, A.R.; Kim, D.-H.; Park, S.-G.; Kwon, J.-D.; Lee, Y.-J.; Lee, B. H.; Ko, H.C. & Hahm, M. G. Chemical sensing of 2D graphene/MoS₂ heterostructure device. *ACS Appl. Mater. Inter.*, 2015, **7**(30), 16775–16780. doi: 10.1021/acsnano.5b08008
 94. Pomerantseva, E. & Gogotsi, Y. Two-dimensional heterostructures for energy storage. *Nature Energy*, 2017, **2**(7), 17089. doi: 10.1038/nenergy.2017.89
 95. Wee, A.T.S.; Hersam, M.C.; Chhowalla, M. & Gogotsi, Y. An update from Flatland. *ACS Nano*, 2016, **10**(9), 8121-23.
doi: 10.1021/acsnano.6b06087
 96. Lee, Y.; Kim, J.; Joo, H.; Raj, M. S.; Ghaffari, R. & Kim, D.-H. Wearable sensing systems with mechanically soft assemblies of nanoscale materials. *Adv. Mater. Technol.*, 2017, **2**(9), 1700053. doi: 10.1002/admt.201700053
 97. Fernández, P.S.; Bissett, M. & Ago, H. Synthesis, structure, and applications of graphene-based 2D heterostructures. *Chem. Soc. Rev.*, 2017, **46** (15), 4572-613.
doi: 10.1039/C7CS00160F
 98. Iannaccone, G.; Bonaccorso, F.; Colombo, L. & Fiori, G. Quantum engineering of transistors based on 2D materials heterostructures. *Nature Nanotechnology*, 2018, **13**(3), 183–191. doi: 10.1038/s41565-018-0082-6
 99. Jiang, X.; Kuklin, A.V.; Baev, A.; Ge, Y.; Agren, H.; Zhang, H.; Prasad, P.N. Two-dimensional MXenes: From morphological to optical, electric, and magnetic properties and applications. *Physics Report*, 2020, **848**, 1-58.
doi: 10.1016/j.physrep.2019.12.006.

CONTRIBUTORS

Dr Doğuş Özkan received his PhD in Mechanical Engineering from Yıldız Technical University, in 2016. Currently, he has been working as an Assistant Professor in the Mechanical Engineering Department of Turkish Naval Academy. His research fields are tribology, coatings, 2D materials, and internal combustion engines.

In the current study, he has written paper, worked on growth and characterization, literature review.

Mr Musa Cenk Özekinci graduated in Automotive Engineering from Cukurova University, Turkey, in 2015. He is currently pursuing his MSc (Mechanical Engineering) in National Defence University, Barbaros Naval Science and Engineering Institute. Presently working as a research assistant in the Department of Mechanical Engineering, at the Turkish Naval Academy. His research area includes coatings and corrosion.

In the current study, he has prepared figures and reviewed the literature, and assisted writing paper.

Dr Zeynep taşlıçukur öztürk received her PhD in Metallurgical and Materials Engineering from Yıldız Technical University in 2010. Currently, she has been working as an Assistant Professor in the Mechanical Engineering Department of Turkish Naval Academy. Her research fields are advanced materials, ceramics technology, synthesis of high tech materials.

In the current study, she has helped in the literature review and discussing the paper.

Dr Egemen Sulukan received BSc in Mechanical Engineering from Turkish Naval Academy in 1997, MSc, and PhD from Marmara University, Turkey in 2004 and 2010, respectively. Presently working as an Associate Professor in the Mechanical Engineering Department of Turkish Naval Academy. His research interests are energy systems analysis and modelling, green technologies, and onboard energy technologies.

In the current study, he has helped in the literature review and discussing the paper.