

We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

5,000

Open access books available

125,000

International authors and editors

140M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities



WEB OF SCIENCE™

Selection of our books indexed in the Book Citation Index
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?
Contact book.department@intechopen.com

Numbers displayed above are based on latest data collected.
For more information visit www.intechopen.com



Supported-Metal Oxide Nanoparticles-Potential Photocatalysts

Vu T. Tan and La The Vinh

Abstract

Recently, nanosized metal oxides play an essential role in the photocatalytic system due to their ability to create charge carriers during the light irradiation. Metal oxide nanoparticles display excellent light absorption properties, outstanding charge transport characteristics, which are suitable in the photocatalytic system for the treatment of wastewater. Most of the photocatalysts found in the literature are in the form of powders. Only a few supported photocatalytic systems have been reported. The advantages of supported photocatalysts, such as that they produce a small pressure drop, have good mechanical stability and are easily separated from the reaction medium, make them superior to conventional powder photocatalysts. In this chapter, the definition of supported-metal oxide nanoparticles as the photocatalyst and their synthesis methodology are detailed discussed.

Keywords: photocatalysis, metal oxides, thin film, semiconductor, substrate

1. General description about photocatalysis

Photocatalysis by semiconductors, such as those indicated above, is a well-established method for degrading organic contaminants in wastewaters. When the photon with energy greater than the band gap of the semiconductor is absorbed by the solid, an electron is excited from the valence band to the conduction band, resulting in an electron-hole pair. These exciting state conduction band electrons and valence band holes have several possible fates [1]:




- a. they can combine and disperse the energy as heat while still in the bulk matrix of the crystal;
- b. they can become trapped in defect traps;
- c. they can migrate to the surface, where they recombine;
- d. they may take part in redox reactions with electron donors or acceptors adsorbed onto the surface, which is the desirable pathway if degradation of organic contaminants is to occur.

In aqueous systems, these adsorbed species will correspond to water molecules, hydroxide ions, and oxygen molecules.

It is clear to know that in semiconductors, the generation of electrons and holes depends on the position of the energy levels. Besides, the redox potential of a donor species on the surface of the photocatalyst needs to be more negative (higher in energy) than the valence band position of the semiconductor to fill the electron vacancies. Similarly, acceptor molecules must have a more positive redox potential (lower in energy) than the conduction band. In view of this, one of the advantages of TiO₂ and ZnO compared to other semiconductors is that their electronic structure is such that it allows both the reduction of protons and the oxidation of water [3]. This phenomenon can be appreciated in the redox potential diagram shown in **Figure 1**. Recently, the use of TiO₂ and ZnO as photocatalysts has been thoroughly investigated.

Numerous conditions of a photocatalyst are required to achieve high photocatalytic efficiency. Firstly, the bandgap of the semiconductor must be higher than the redox potential of the H₂O/OH[•] couple, and the material must be photo-stable. Secondly, the recombination of electron-hole pairs must be minimized. In other words, they need to be kept apart to allow time for the redox reactions to occur. Separation can be achieved by trapping electrons or holes in defects [4] or by using electrically conductive supports [5].

The holes in the photocatalyst valence band can oxidize the adsorbed water or hydroxide ions, while electrons in the conduction band can reduce molecular oxygen to superoxide anions [6]. These processes are summarized in the following equations:



The degradation of organic contaminants is commonly attributed to oxidation by hydroxyl radicals. This process is schematically described in **Figure 2**. This has led to the use of the term “Advanced Oxidation Processes,” although there is evidence that in some systems, reductive pathways also operate [7].

Among *Advanced Oxidation Processes*, the photocatalytic processes are focused on the conversion of highly toxic organic to either less toxic organic compounds or CO₂ and H₂O [8]. When the photocatalytic reaction is implemented in the presence of O₂, the catalyst plays two main roles: to scavenge the photogenerated electrons and to produce active oxygen species [9]. We already know that metal oxides can respond to both UV-light and visible light, depending on the energy band gap of the materials. Newly, the photocatalytic process used visible light is widely employed for environmental cleanup [10].

Recently, many metal oxides (TiO₂, ZnO, SnO₂, and WO₃) have been widely used for the photocatalysis process. This is due to their abundance in nature,

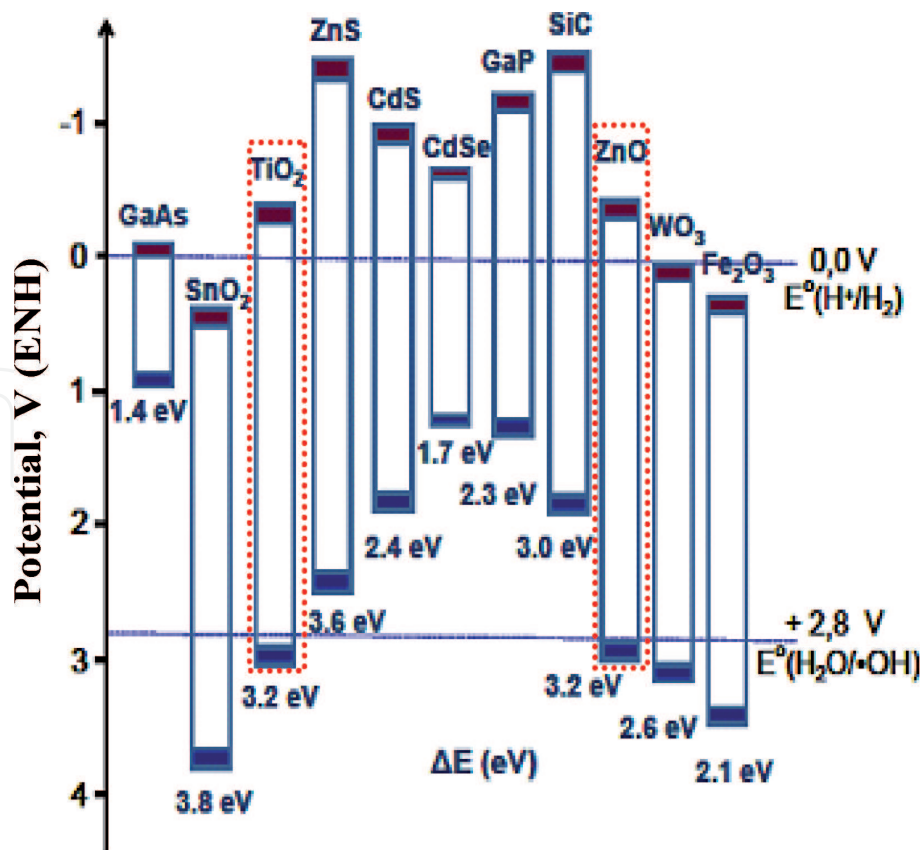


Figure 1.
 Band gaps (eV) and redox potentials for several semiconductors referred to the normal hydrogen electrode (NHE). Reproduced from Ania et al. [2].

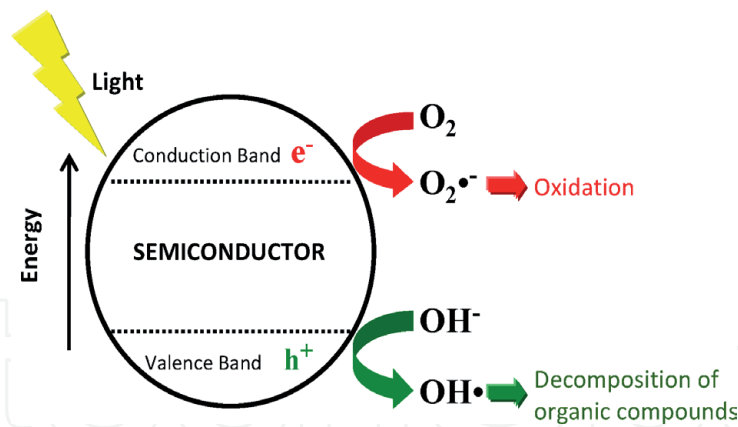


Figure 2.
 Schematic diagram showing the processes involved in semiconductor photocatalysis. Reproduced from Gratzel et al. [3].

stability in many conditions, and the capability to create charge carriers when they were exposed under UV or visible light. The advantageous combination of the electronic structure, light absorption capacities, and excited lifetimes of metal oxides has provided them possible for their application as photocatalyst. The photocatalysis employing metal oxides such as TiO_2 , ZnO , SnO_2 , and WO_3 has demonstrated their efficiency in the degradation of various harmful pollutants into carbon dioxide and water.

The vast majority of the photocatalysts studied are in powder form with all the difficulties in handling and recovering that implies. Consequently, supported photocatalysts are nowadays an important research area.

2. Supported TiO₂ photocatalysts

When the light is irradiated to the surface of the semiconductor, its absorption of photons provokes the photocatalytic reaction at the surface of the catalyst. Among many semiconductor materials, titanium dioxide (TiO₂) nanoparticles have been widely studied for photocatalytic applications over the last two decades [11, 12]. TiO₂ is relatively inexpensive, insoluble in water, and non-toxic. It can provide photogenerated holes with high oxidizing power because of its wide bandgap (3.2 eV) [13].

The common mechanism of the photocatalytic process of TiO₂ material consists of the interfacial redox reactions of the generated holes and electrons when the TiO₂ materials are irradiated by light with appropriate energy (**Figure 3**) [14, 15].

Most of the photocatalysts found in the literature are in the form of powders. Only a few supported photocatalytic systems have been reported, even though they have clear advantages from a practical point of view [16–18]. The most important benefit is that the separation of the supported photocatalysts from the reaction medium is simple, which minimizes the power requirements. In addition, they can be adapted to operate in flow-type continuous reactors [19–21]. Most recently, research was described by Fernández et al. [21]. They reported two methods of deposition of TiO₂ powders on different substrates (glass, quartz, and stainless steel) and evaluated the photocatalytic activities of these supporting materials through the degradation of organic compounds (**Figure 4**).

The authors demonstrated the influence of coating methodology and photocatalytic activities. The results showed that titania deposited on quartz displays a similar photocatalytic activity to that of the powder form. Therefore, the result opens a new feature for a new advantage route to immobilize catalyst for flow reactor or batch reactor. Because filtration step to recover the catalyst always causes many drawbacks in water treatment.

Then some authors [22, 23] developed a new type of supported photocatalyst that consists of mixtures of noble metal nanoparticles and commercially available TiO₂ nanoparticles (P25, Degussa-Evonik) deposited by dip-coating procedure on quartz substrate. The photocatalytic activity of the immobilized catalyst was evaluated by the degradation of malic acid. A comparison of the photocatalytic activity between supported TiO₂ with the powder TiO₂ Degussa P-25 shows slightly lower catalytic activity. This phenomenon could be explained by the total surface exposed of the catalyst to the light during the irradiation. However,

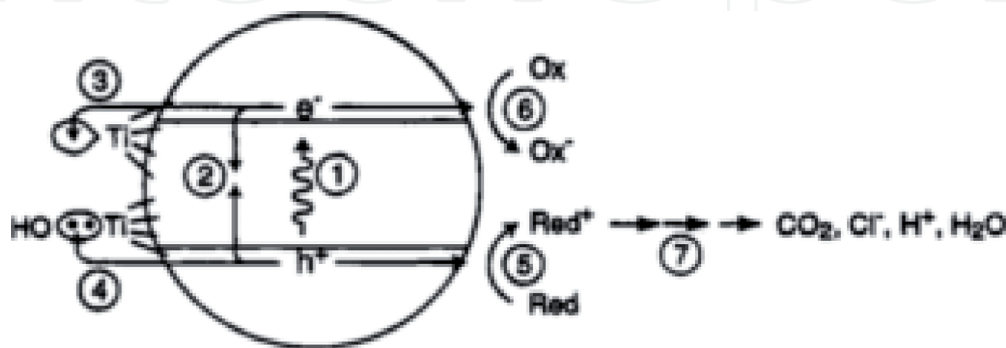


Figure 3.

The mechanism of photocatalysis process of TiO₂. Reproduced from Hoffman et al. [15]. (1) The formation of the electrons and holes by photon absorption. (2) The recombination of the generated electrons and holes. (3) The electron trapping of Ti (IV) at the conduction band to form Ti (III). (4) The hole trapping of titanium group at the valence band. (5) The oxidative pathways at the conduction band. (6) The reductive pathways at the valence band. (7) Photocatalytic oxidation reactions to form harmless compounds.

the result could be compensated by the advantage of eliminating the recovering catalyst after the treatment.

Lately, several works also reported the preparation of thin TiO_2 film on quartz substrates (**Figure 5**) by coating the TiO_2 sol using rotary evaporator [24], by dip-coating [25], by spin coating [26].

Recently, Borges et al. [27] supported commercial TiO_2 (Degussa P25) on glass spheres as a photocatalyst to treat the wastewater (**Figure 6**).

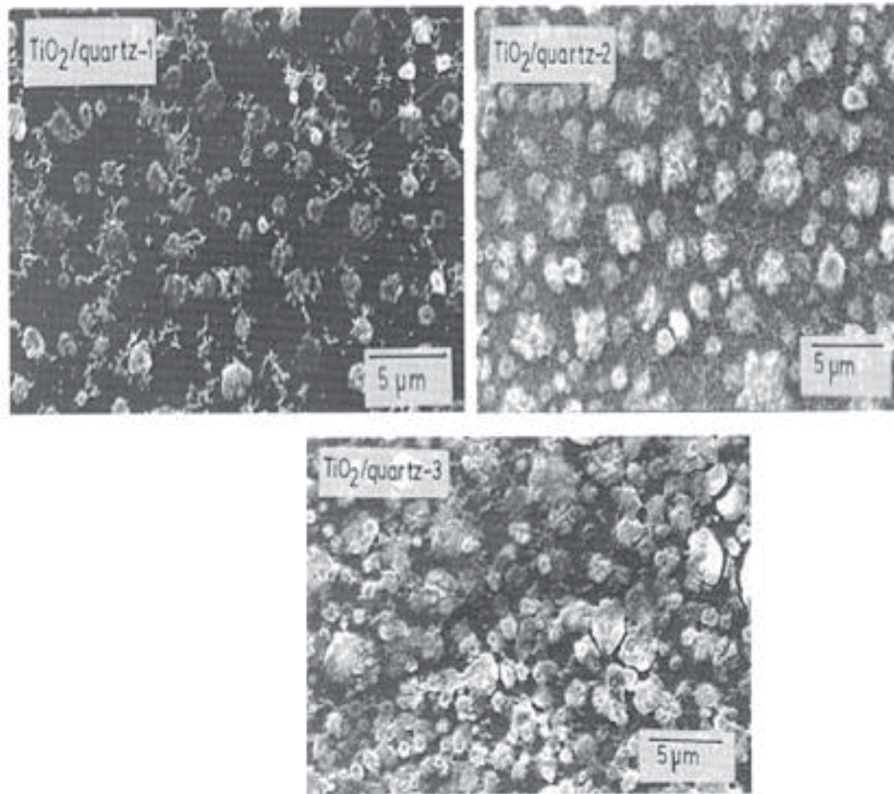


Figure 4.
SEM micrographs for the three $\text{TiO}_2/\text{quartz}$ samples. Reproduced from Hoffman et al. [15].

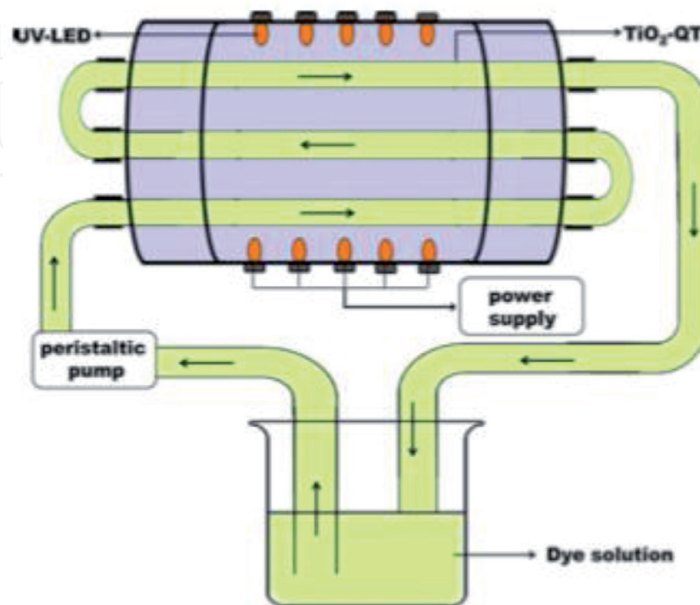


Figure 5.
Schematic representation of photocatalytic reactor using TiO_2 supported on quartz. Reproduced by Natarajan et al. [25].

Figure 7 shows the surface morphology substrate of the glass spheres without TiO_2 particles. **Figure 7b** shows the TiO_2 supported on the substrate and the homogeneous distribution of TiO_2 on the surface of the glass sphere. The authors showed that photocatalytic treatment in photoreactor displays more advantages than in batch system for high volumes of industrial wastewater.

Later, several authors also used poly-vinylidene fluoride (PVDF) dual layer hollow fiber membrane as a support to immobilize TiO_2 to treat pharmaceutical compound in wastewater (**Figure 8**) [28, 29].

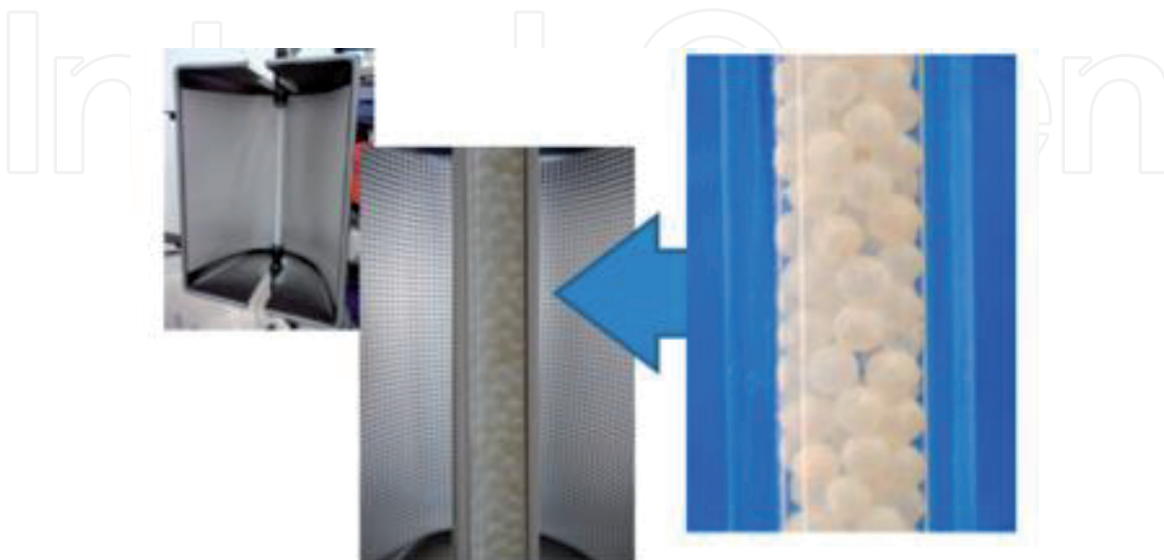


Figure 6. Packed-bed photoreactor system and glass spheres photocatalytic bed in photoreactor. Reproduced by Borges et al. [27].

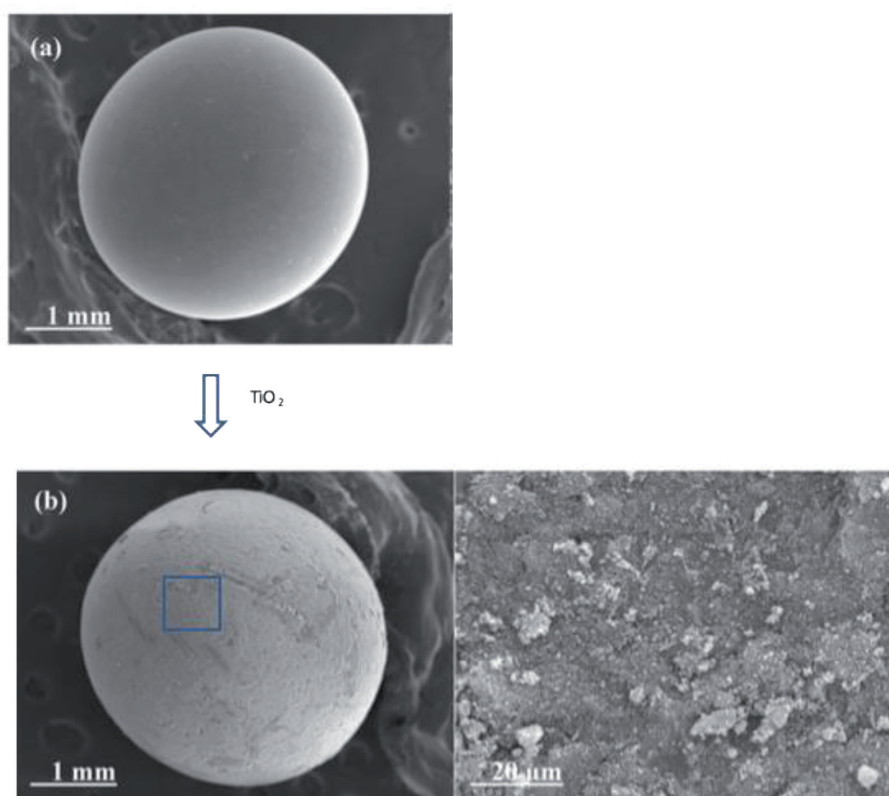


Figure 7. SEM image of the glass sphere (a), SEM image of TiO_2 supported on the glass sphere (b). Reproduced by Borges et al. [27].

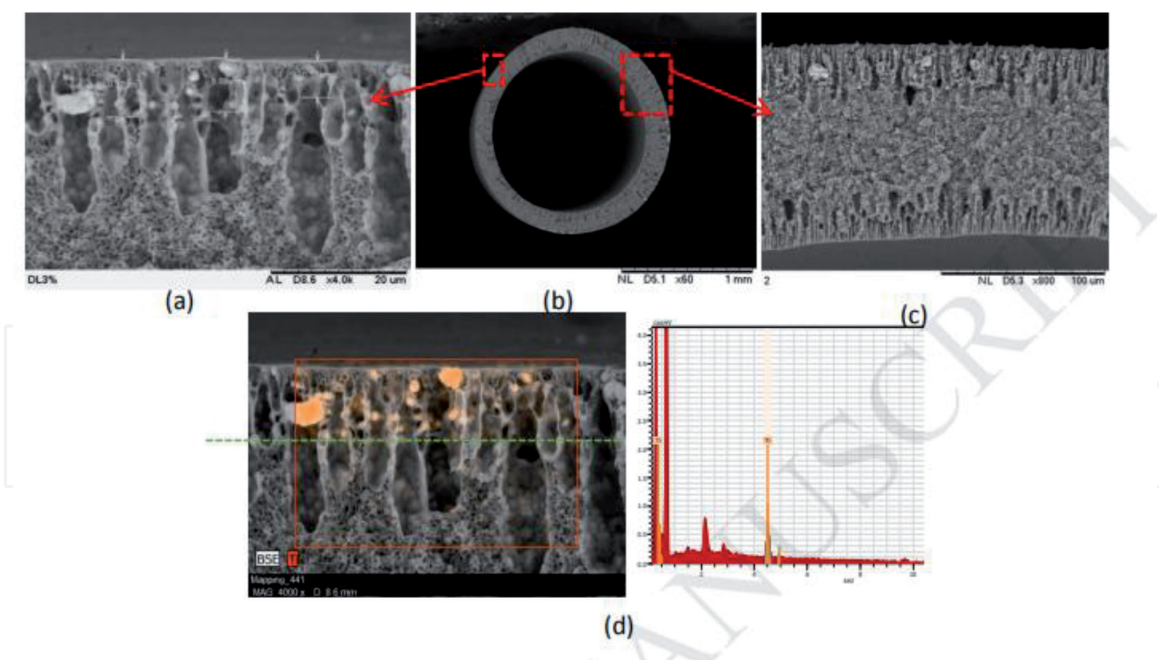


Figure 8. Images of the PVDF membranes: (a) outer surface, (b) full cross section, (c) partial cross section, and (d) EDX images of TiO₂ nanoparticles at the outer layer. Reproduced by Paredes et al. [29].

The author demonstrated that the TiO₂ supported catalyst on PVDF membranes improved the photo-transformation rate of wastewater compounds during the photocatalytic treatment. The author also claimed that the supported catalyst could be easily recycled without any separation systems or catalysis recovery technologies.

It is already to know that TiO₂ is used as a photocatalyst in the ultraviolet light region due to its wide bandgap. To improve its photocatalytic efficiency in the visible light, efforts have been made such as, doping TiO₂ with anionic species (Fluorine, Sulfur, Nitrogen), or combining TiO₂ with other metal oxides. The combination of TiO₂ with other metal oxides can reduce the recombination effect of the electron-hole before they migrate to the surface of the material [30]. In addition, the composite of TiO₂ with other metal oxides can be generated in the surface hydroxyl groups, which can trap holes after the irradiation process, which improve the separation of the electron-holes. In some cases, the composite of TiO₂ with other metal oxides can enhance the crystallinity degree of TiO₂ and increases the specific surface area of the composite which are two important properties for a photocatalyst.

Recently, TiO₂ is widely combined with other metal oxides, such as ZrO₂, SnO₂, WO₃, CeO₂, ZnO, to improve the photocatalytic activity of TiO₂ in the ultraviolet light and improving its photocatalytic efficiency in the visible region.

For example, the composite of mixed oxide ZrO₂-TiO₂ material recently gains a great attention. By combining TiO₂ with ZrO₂, the surface acidity of the composite can be increased, hence improved the reactivity compared to the TiO₂ [31]. In addition, the hydroxyl groups are located on the surface of the catalyst, where the holes are trapped which could improve the efficiency of the degradation of organic pollutant [32]. Therefore, the mixed oxide ZrO₂-TiO₂ has been widely studied for the photodegradation of toxic organic compounds [31–35]. Many researchers also focused on the fabrication of ZrO₂-TiO₂ composite thin film and study its photocatalytic efficiency under ultraviolet or visible irradiation [36–40].

Luo et al. has fabricated the ZrO₂-TiO₂ composite thin film on glass substrate using micro-arc oxidation process and used it for the degradation of rhodamine

B under ultraviolet irradiation [40]. The $\text{ZrO}_2\text{-TiO}_2$ composite thin film consists of three compounds: anatase, rutile, and ZrO_2 phases, results that the generated electron can transfer from rutile to anatase. This phenomenon inhibits the recombination of the generated electron-hole pairs, thus improved the photocatalytic efficiency of the composite. The photodegradation of MB under UV light irradiation shows that the photocatalytic activity of $\text{ZrO}_2\text{-TiO}_2$ composite thin film is three times higher than that of the pure TiO_2 thin film.

Alotaibi et al. have reported the preparation of $\text{ZrO}_2\text{-TiO}_2$ composite thin film on glass substrate using aerosol-assisted chemical vapor deposition [32]. The photocatalytic activity of the fabricated composite thin film was evaluated through the photodegradation of resazurin redox dye under Ultraviolet light irradiation (**Figure 9**). The composite shows an enhancement of photocatalytic activity compared to a pure TiO_2 thin film fabricated by the same condition.

Tungsten oxide (WO_3) is a common dopant in heterogeneous photocatalysis. In the last decade, WO_3 was extensively combined with TiO_2 to improve the photocatalytic activity of TiO_2 in both UV and Visible light. Besides of using the catalyst in the powder form, the preparation of $\text{WO}_3\text{-TiO}_2$ film and its photocatalytic activity was extensively studied [41–44] due to its advantage of the recuperation way. The $\text{WO}_3\text{-TiO}_2$ film has been fabricated by several methodologies such as sol-gel and dip coating [45]; spin-coating [46]; solvothermal method combining magnetron sputtering [47]; or film on pyrex substrates by casting methodology [48].

For example, Fu et al. have fabricated the $\text{WO}_3\text{-TiO}_2$ film on quartz substrate by dip-coating synthesis [42]. The photocatalytic efficiency was evaluated by the degradation of 4-chlorophenol-4 CP, xenobiotic micropollutants, under the irradiation visible light. The result shows that by incorporation of WO_3 into TiO_2 , the $\text{WO}_3\text{-TiO}_2$ film can shift the absorption band from near UV region to the visible region. Under visible light, for the degradation of 4-CP, the prepared composite film demonstrated a higher photocatalytic activity for than that of pure TiO_2 film.

Recently, Adel et al. have prepared the $\text{WO}_3\text{-TiO}_2$ thin film on glass substrate by reactive chemical spraying and tested its photocatalytic activity under visible light. The results show that the photocatalytic thin film can degrade completely dye in textile, wastewater leading to cleaner processes [49].

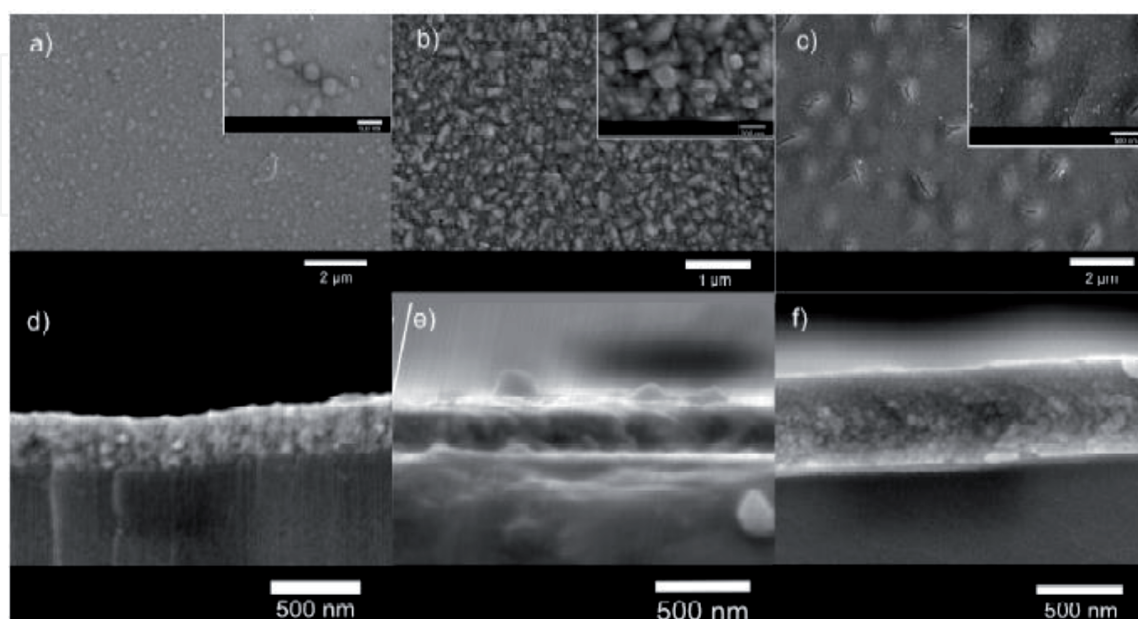








Figure 9. SEM images of the (a) ZrO_2 , (b) TiO_2 and (c) $\text{ZrO}_2\text{-TiO}_2$ composite films with the high magnification. The side on images—(d) ZrO_2 , (e) TiO_2 , and (f) $\text{ZrO}_2\text{-TiO}_2$ composite—shows the film thickness. Reproduced by Alotaibi et al. [32].

Spanu et al. have prepared Pt deposited on WO₃-TiO₂ nanotube arrays on Ti foil by sputtering method in order to improve the photocatalytic activity of the WO₃-TiO₂ system. The photocatalyst was used for the fabrication of H₂ by photocatalysis. The Pt deposited on WO₃-TiO₂ nanotube arrays show highly enhanced photocatalytic H₂ evolution efficiency comparing to other single-photocatalyst system such as (Pt-TiO₂ and WO₃-TiO₂) and pristine TiO₂ nanotubes [50].

3. Supported ZnO photocatalysts

ZnO is a metal oxide with a broad energy band gap (3.37 eV), which is one of the best semiconductors in the last decade. Recently, ZnO is extensively used as a photocatalyst under UV or Visible light irradiation due to its outstanding electrical, mechanical, optical, and non-toxic properties. In addition, the production cost of ZnO is low cost comparing to the fabrication of other semiconductors [51].



The mechanism of photocatalysis process of ZnO to degrade organic compounds under irradiation light can be summarized as follows [52]:



ZnO shares many similar properties with TiO₂, including a similar band gap (see **Figure 1**). There have even been several examples of ZnO displaying a higher photocatalytic activity than TiO₂ [53]. In addition, ZnO exhibits a better quantum efficiency because it can absorb a larger fraction of the solar spectrum than TiO₂ [54] and its price is even lower than that of TiO₂ [55]. Compared to TiO₂, ZnO can be easily supported on different types of substrates by means of low-temperature synthesis methods [56].

We already know that the photocatalytic efficiency of a photocatalyst is evaluated through the photogeneration of electron-hole pairs and their time-life. However, the main limitation of ZnO as a photocatalyst is the rapid recombination rate of photogenerated electron-hole pairs, which decreases the photocatalytic efficiency of ZnO. In addition, the use of ZnO as a photocatalyst is limited by the photocorrosion phenomenon. This process occurs because of the action of UV

radiation. As a consequence, the catalyst is partially dissolved, which gives rise to a dramatic decrease in catalytic activity [57]. The mechanism of this process is represented by the following self-oxidation reactions [58–60]:



where h^+ is the positive holes created by the action of UV radiation. Photocorrosion is the main obstacle to the use of ZnO as an effective photocatalyst. Therefore, significant efforts have been made to reduce the degradation of ZnO.

Beside TiO_2 using as a photocatalyst, Jung et al. [61] studied the synthesis and photocatalytic activity of CuO-ZnO nanowires supported on stainless steel wire meshes (SSWM). They showed that CuO-ZnO structures supported on SSWM exhibit an enhanced photocatalytic activity with respect to catalysts using other supports, such as ITO. This result they attributed to the efficient charge separation of the electron-hole pair favored by the SSWM support [61]. Another advantage of SSWM is its flexibility, which allows the mesh to be easily shaped to the desired configuration.

In general, the procedures used to achieve this involves the deposition onto the ZnO surface of: (a) silver nanoparticles [62–66]; (b) polyaniline monolayers [67], (c) graphitic carbon [68]; (d) Nafion films [69]; (e) AlSi nanoclays [70]; and (f) C_{60} fullerenes which become hybridized with ZnO [59].

Although the above modifications improve the photocatalytic stability of ZnO, some problems persist. For instance, Bessekhoud et al. [71] have reported that the photocatalytic activity of the doped materials is impaired by thermal instability and by an increase in the number of hole/electron recombination centers. Therefore, the development of novel methods that provide effective protection of the ZnO photocatalyst against photocorrosion is required.

An attempt must be made to increase catalytic activity under visible irradiation, since the solar spectrum contains a large fraction of visible light compared to UV radiation. Recently, the photocatalytic activity of ZnO in the visible region has been improved by various techniques, such as: (a) modification of the ZnO surface by non-metal element doping [72]; (b) transition metal doping [73, 74]; (c) the combination of ZnO with another semiconductor [75], etc. Of these methods, the coupling of different semiconductor photocatalysts offers great promise as it increases the charge separation of the electron-hole pairs, resulting in an increase in photocatalytic decolorization efficiency [76].

Recently, ZnO has been combined successfully with TiO_2 [77], CdO [78], CdS [79], and WO_3 [80]. CdO is a good candidate for coupling with ZnO due to its band gap, ~ 2.2 eV [78], so that $\text{Cd}_x\text{Zn}_{1-x}\text{O}$ nanostructures are active in the visible range. In addition, under visible light the excited electrons from the conduction band (CB) of ZnO can be easily transferred to the CB of CdO since the E_{CB} of CdO is lower than the E_{CB} of ZnO. These transferal processes increase the excess of electrons in the conduction band of CdO, which shifts in the Fermi level of CdO [81], increasing its photocatalytic efficiency. To the best of our knowledge, CdO-ZnO has been always synthesized in powder form. The use of CdO-ZnO supported on a target substrate (such as SSWM) as a photocatalyst for dye degradation processes in UV or visible has reported by Vu et al. [82]. They also attempt to demonstrate in parallel that coupling CdO and ZnO may be also an excellent method to avoid photocorrosion.

4. Supported WO₃ photocatalysts

Tungsten oxide (WO₃) is a high-ranking material in photocatalysis [83]. The WO₃ presents in several phases such as monoclinic, orthorhombic, triclinic, cubic, etc., but only the monoclinic phase exhibits the best photocatalytic efficiency. In addition, WO₃ is a material with many advantages, such as harmless, high stability in acidic and oxidative ambient, and its cost fabrication cost is very low compared with other photocatalysts [84].

It has been shown that the band gap energy of WO₃ is varied from 2.5 to 3.0 eV [85, 86], leading WO₃ can be used as a photocatalyst at the visible region. In recent times, there are many studies focused on the improvement strategies of the photocatalytic efficiency of WO₃ [84, 87].

Recently, the researchers have proposed many strategies for the fabrication of WO₃ thin film [88], such as sputtering deposition [89–92], aerosol-assisted chemical vapor deposition [93, 94], sol-gel spin-coating [95, 96], hydrothermal-assisted growth [97, 98], and surfactant-assisted spray pyrolysis [99, 100]. Many works focused on the photocatalytic efficiency of WO₃, especially the studying of WO₃ thin film as a photocatalyst in the visible region [84, 101].

For example, the author fabricated a WO₃ thin film with a thickness 500–600 nm deposited on a quartz substrate by DC reactive magnetron sputtering [102]. The fabricated film WO₃ used for the degradation of CH₃CHO (acetaldehyde) under ultraviolet, standard fluorescence, and visible light. The result shows that WO₃ film fabricated by sputtering can be a good photocatalyst under visible light region.

To improve the separation of photogenerated charged and to increase the photocatalytic activity, many researchers combined other elements with the WO₃ thin film. For example, Higashino et al. have fabricated a layer of WO₃ on the Al-W alloy coatings by selective solution and heat treatment (**Figure 10**). The formed thin film WO₃ exhibits photocatalytic self-cleaning properties under the visible light irradiation [103].

Takashima et al. have taken advantage of the multielectron reduction of Pt to improve the photocatalytic activity of WO₃ thin film on W foil. The author fabricated Pt loaded WO₃ thin film using a reactive DC magnetron sputtering technique or low damage reactive gas flow sputtering [104]. The formed Pt-WO₃ thin film was used to photodegrade CH₃CHO under visible light. The result shows that the fabricated thin film demonstrates excellent photodecomposition rates under visible light.

Another approach to improve the separation of photogenerated charged, C₃N₄ is combined with WO₃ film to form a heterojunction composite WO₃/C₃N₄. The

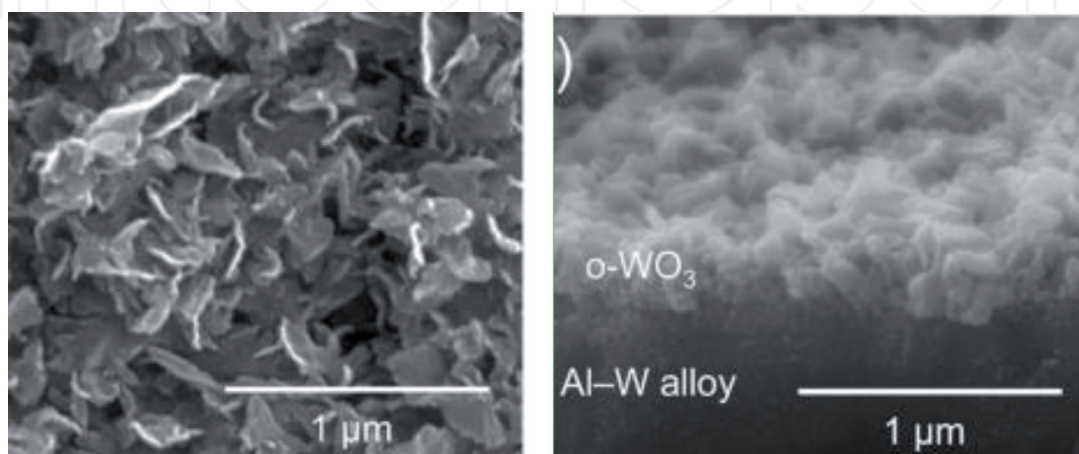


Figure 10. SEM images of the surface and cross-sectional of WO₃. Reproduced by Higashino et al. [103].

fabricated composite was deposited on fluorine-doped tin oxide (FTO) substrate [105]. The photocatalytic activity of the composite was tested by photocatalytic degradation of MB and Cr^{6+} in wastewater under UV illumination.

The supported $\text{WO}_3/\text{C}_3\text{N}_4$ composite presents higher photocatalytic activity on the decoloration of MB and the reduction of Cr^{6+} to Cr^{3+} , compared to the photocatalytic activity of WO_3 thin film.

5. Supported SnO_2 photocatalysts

SnO_2 is an inorganic compound that is exhibiting high optical transparency, excellent thermal and chemical stability, and strong oxidizing properties [106]. The band gap of SnO_2 is quite large, around 3.6 eV, which leads that SnO_2 can be used as a photocatalyst at the UV region. This property makes SnO_2 becoming an excellent photocatalyst for the degradation of many organic compounds.

Recently, SnO_2 played an important role in the photo-oxidation of pollutants and received a lot of attention despite the outstanding properties of this material. However, the vast number of researches used SnO_2 in the powder form as a photocatalyst for the degradation of the toxic organic compound, and the experiments are usually performed using SnO_2 in the powder form. There are only a few works describing the use of supported SnO_2 thin film as a photocatalyst.

In recent times, many methodologies have been applied for the fabrication of SnO_2 thin films such as, sol-gel [107], pulsed plasma deposition [108], pulsed laser deposition [109], reactive evaporation [110], and chemical bath deposition [111] methods.

For example, Jana et al. used the galvanic technique to fabricate SnO_2 thin film on transparent conducting oxide (TCO) [112].

Figure 11 shows the nanoporous flake-like structure, which allows more efficient transport of reactant molecules to the active interfaces and results in a higher photocatalytic activity for degrading methyl orange (MO) dye than that of P25 under UV light [112].

However, the SnO_2 in the powder form presents low photocatalytic activity comparing with other semiconductors due to its wide-band gap, 3.6 eV, and the rapid recombination of the photo-generated electron-hole pairs. Thus, the SnO_2 thin film could present lower photocatalytic efficiency comparing with SnO_2 in the bulk form. Therefore, the SnO_2 thin film is widely combined with other metal ions such as Ni, Co, Fe [113], Cr [114], Zn [115], Sb [116], W [117], or other semiconductors, such as ZnO [118], TiO_2 [119], etc.

For example, the W-doped SnO_2 thin films are fabricated on glass (ITO) substrate by simple chemical deposition techniques [120]. The result showed that the energy band gap is varied by the doping concentration of W, which is in the range of 3.46–3.35 eV. In addition, the UV-Visible absorption and Photoluminescence characterization results demonstrated that W-dopant SnO_2 could narrow the band gap, thus enhancing the photocatalytic efficiency of the W-doped SnO_2 in the visible light (**Figure 12**). The author used the fabricated W-doped SnO_2 for the degradation of Methylene Blue and Rhodamine (RHB) under the visible region. The W-doped SnO_2 thin film presents higher photocatalytic efficiency comparing to the pure SnO_2 thin film in the visible light irradiation.

In recent time, Sr-doped metal oxides have great attention in electronic and optoelectronic applications. Besides, when Sr is combined with SnO_2 , the crystal growth rate of SnO_2 is reduced, making the Sr-doped SnO_2 to have a higher specific surface area. Thus, the combination of Sr with SnO_2 can improve the photocatalytic activity of SnO_2 . For example, Haya et al. have prepared Sr-doped SnO_2 thin film

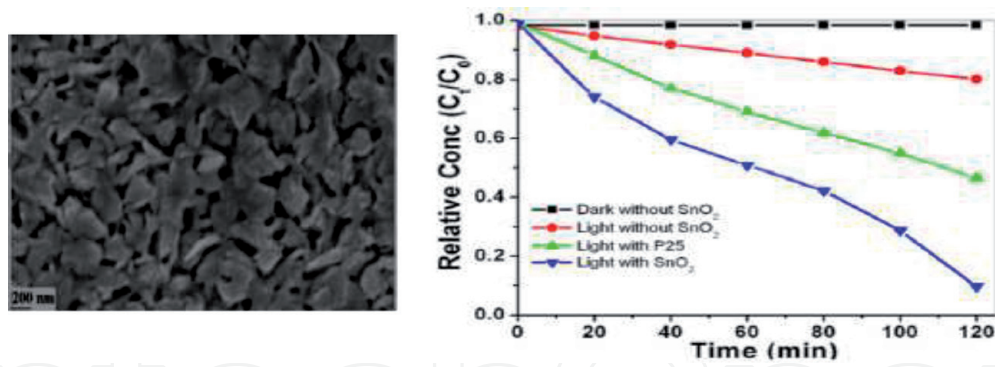


Figure 11. The SnO₂ thin film and the photocatalytic activity of SnO₂ thin film. Reproduced by Jana et al. [112].

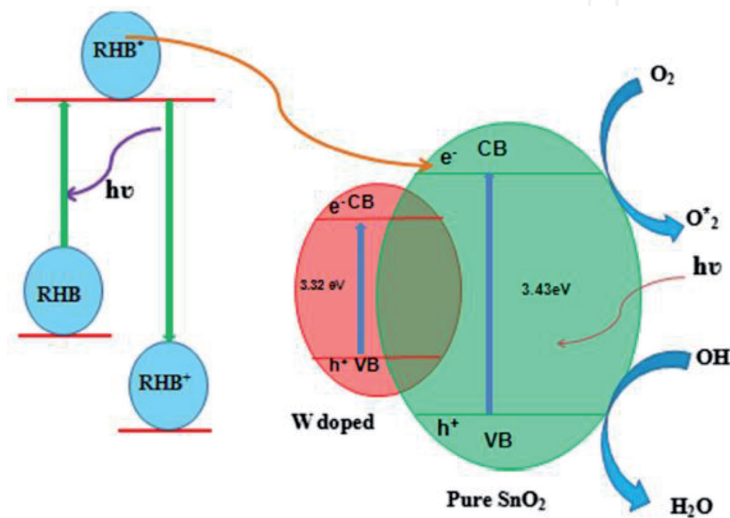


Figure 12. Schematic representation for photocatalytic mechanism of RHB in W-SnO₂ thin films. Reproduced by Vadivel et al. [120].

on glass substrate by simple sol-gel technique and study its photocatalytic activity under UV-irradiation [121]. The doping of Sr makes the SnO₂ thin film to decrease its degree of crystallinity, reducing the particle size and increasing the specific surface area of the thin film. The results show that the Sr-doped (8%) SnO₂ film has higher photocatalytic activity compared to undoped SnO₂ thin film.

In addition, many researchers also combined with other metal elements to improve the photocatalytic activity of SnO₂ thin film such as Cu-doped SnO₂ [122], Fe-doped SnO₂ [123], F- or Sr-doped [124], and Cl-doped SnO₂ [125] on glass substrate.

Recently, to improve the photocatalytic efficiency of SnO₂ thin film, B/Ag/F was doped with the SnO₂-ZnO composite film on glass by the sol-gel route. The fabricated composite thin film was used for the degradation of methyl green and formaldehyde under UV irradiation. The result showed that the synergy of ZnO and tri-doping B/Ag/F had improved the photocatalytic activity of SnO₂ thin film [126]. In addition, Kong et al. also prepared B/Fe co-doped SnO₂-ZnO thin film on glass substrates using the sol-gel technique. The prepared composite thin film improved the lifetime of the photogenerated charge carriers and optical absorption properties. The photocatalytic efficiency of the composite thin film was evaluated through the degradation of organic pollutants such as acid naphthol red and formaldehyde. The B/Fe co-doped SnO₂-ZnO film exhibits the highest photocatalytic activity compared with an undoped or only singly doped SnO₂ thin film [127].

6. Conclusion

In this chapter, an overview of the development of supported catalysts and their prospects from a scientific point of view is presented. We can see that the field has experienced major advances in the last 5 years, especially in the area of supported TiO₂, ZnO, WO₃, SnO₂, and mixed oxides on several types of substrates (SSWM, quartz, glass (ITO)). Based on the literature presented here, we believe that there is still quite a lot that can be achieved in improving the performance of supported catalysts for photocatalytic applications.

IntechOpen

IntechOpen

Author details

Vu T. Tan* and La The Vinh
School of Chemical Engineering, Hanoi University of Science and Technology,
Hanoi, Vietnam

*Address all correspondence to: tan.vuthi@hust.edu.vn

IntechOpen

© 2020 The Author(s). Licensee IntechOpen. This chapter is distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/3.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited. 

References

- [1] Philippopoulos CJ, Nikolaki MD. Photocatalytic Processes on the Oxidation of Organic Compounds in Water. Croatia: New Trends in Technologies; 2010. pp. 89-107. DOI: 10.5772/7588
- [2] Ania CO, Velasco LF, Valdés-Solís T. Photochemical behavior of carbon adsorbents. In: Novel Carbon Adsorbents. Oxford: Elsevier; 2012. pp. 521-547
- [3] Photoelectrochemical Cells. Nature. Available from: <https://www.nature.com/articles/35104607> [Accessed: 17 January 2020]
- [4] Zinc Oxide Nanoparticles with Defects—Ischenko—2005—Advanced Functional Materials—Wiley Online Library. 2005. Available from: <https://onlinelibrary.wiley.com/doi/10.1002/adfm.200500087> [Accessed: 17 January 2020]
- [5] Öztas M, Bedir M. Thickness dependence of structural, electrical and optical properties of sprayed ZnO:Cu films. Thin Solid Films. 2008;**516**(8):1703-1709. DOI: 10.1016/j.tsf.2007.05.018
- [6] Eslami A et al. Photocatalytic degradation of methyl tert-butyl ether (MTBE) in contaminated water by ZnO nanoparticles. Journal of Chemical Technology and Biotechnology. 2008;**83**(11):1447-1453. DOI: 10.1002/jctb.1919
- [7] Environmental Applications of Semiconductor Photocatalysis. Chemical Reviews. 1995;**95**(1):69-96. Available from: <https://pubs.acs.org/doi/abs/10.1021/cr00033a004> [Accessed: 17 January 2020]
- [8] Wang H et al. Semiconductor heterojunction photocatalysts: Design, construction, and photocatalytic performances. Chemical Society Reviews. 2014;**43**(15):5234-5244. DOI: 10.1039/C4CS00126E
- [9] Nosaka Y, Nosaka A. Generation and detection of reactive oxygen species in photocatalysis. Chemical Reviews. 2017;**117**:11302-11336. DOI: 10.1021/acs.chemrev.7b00161
- [10] Byrne C, Subramanian G, Pillai SC. Recent advances in photocatalysis for environmental applications. Journal of Environmental Chemical Engineering. 2018;**6**(3):3531-3555. DOI: 10.1016/j.jece.2017.07.080
- [11] Nakata K, Fujishima A. TiO₂ photocatalysis: Design and applications. Journal of Photochemistry and Photobiology C Photochemistry Reviews. 2012;**13**(3):169-189. DOI: 10.1016/j.jphotochemrev.2012.06.001
- [12] Fujishima A, Rao TN, Tryk DA. Titanium dioxide photocatalysis. Journal of Photochemistry and Photobiology C Photochemistry Reviews. 2000;**1**(1):1-21. DOI: 10.1016/S1389-5567(00)00002-2
- [13] Photocatalytic Degradation of Organic Dyes in the Presence of Titanium Dioxide under UV and Solar Light: Effect of Operational Parameters—Akbal—2005—Environmental Progress. 2005;**24**(3):317-322. Available from: <https://onlinelibrary.wiley.com/doi/abs/10.1002/ep.10092> [Accessed: 17 January 2020]
- [14] Schneider J et al. Understanding TiO₂ photocatalysis: Mechanisms and materials. Chemical Reviews. 2014;**114**(19):9919-9986. DOI: 10.1021/cr5001892
- [15] Hoffmann MR, Martin ST, Choi W, Bahnemann DW. Environmental applications of semiconductor photocatalysis. Chemical Reviews. 1995;**95**(1):69-96. DOI: 10.1021/cr00033a004

- [16] Taoda H. Development of TiO₂ photocatalysts suitable for practical use and their applications in environmental cleanup. *Research on Chemical Intermediates*. 2008;**34**(4):417-426. DOI: 10.1163/156856708784040579
- [17] Wang L, Wang X, Cui S, Fan X, Zu B, Wang C. TiO₂ supported on silica nanolayers derived from vermiculite for efficient photocatalysis. *Catalysis Today*. 2013;**216**:95-103. DOI: 10.1016/j.cattod.2013.06.026
- [18] Singh S, Mahalingam H, Singh PK. Polymer-supported titanium dioxide photocatalysts for environmental remediation: A review. *Applied Catalysis A: General*. 2013;**462-463**:178-195. DOI: 10.1016/j.apcata.2013.04.039
- [19] Enhancement of Photocatalytic Degradation of Methyl Orange by Supported Zinc Oxide Nanorods/ Zinc Stannate (ZnO/ZTO) on Porous Substrates. *Industrial & Engineering Chemistry Research*. 2013;**52**(38):13629-13636. Available from: <https://pubs.acs.org/doi/10.1021/ie4019726> [Accessed: 17 January 2020]
- [20] Photocatalytic Degradation Activity of Titanium Dioxide Sol-Gel Coatings on Stainless Steel Wire Meshes—Science Direct. *Materials Chemistry and Physics*. 2010;**124**(2):1225-1231. Available from: <https://www.sciencedirect.com/science/article/abs/pii/S025405841000684X> [Accessed: 17 January 2020]
- [21] Fernández A et al. Preparation and characterization of TiO₂ photocatalysts supported on various rigid supports (glass, quartz and stainless steel). Comparative studies of photocatalytic activity in water purification. *Applied Catalysis B: Environmental*. 1995;**7**(1):49-63. DOI: 10.1016/0926-3373(95)00026-7
- [22] Characterization and Photocatalytic Activity in Aqueous Medium of TiO₂ and Ag-TiO₂ Coatings on Quartz—Science Direct. *Applied Catalysis B: Environmental*. 1997;**13**:219-228. Available from: <https://www.sciencedirect.com/science/article/abs/pii/S0926337396001075> [Accessed: 17 January 2020]
- [23] Yu J, Xiong J, Cheng B, Liu S. Fabrication and characterization of Ag-TiO₂ multiphase nanocomposite thin films with enhanced photocatalytic activity. *Applied Catalysis B: Environmental*. 2005;**60**(3):211-221. DOI: 10.1016/j.apcatb.2005.03.009
- [24] Photocatalytic Degradation of Phenol in a Fluidized Bed Reactor Utilizing Immobilized TiO₂ Photocatalyst: Characterization and Process Studies—SciAlert Responsive Version. *Journal of Applied Sciences*. 2011;**11**(13). Available from: <https://scialert.net/fulltextmobile/?doi=jas.2011.2320.2326> [Accessed: 17 January 2020]
- [25] Photocatalytic Reactor Based on UV-LED/TiO₂ Coated Quartz Tube for Degradation of Dyes—Science Direct. *Chemical Engineering Journal*. 2011;**178**:40-49. Available from: <https://www.sciencedirect.com/science/article/pii/S1385894711012460> [Accessed: 17 January 2020]
- [26] Hanaor DAH, Triani G, Sorrell CC. Morphology and photocatalytic activity of highly oriented mixed phase titanium dioxide thin films. *Surface and Coating Technology*. 2011;**205**(12):3658-3664. DOI: 10.1016/j.surfcoat.2011.01.007
- [27] Borges ME, García DM, Hernández T, Ruiz-Morales JC, Esparza P. Supported photocatalyst for removal of emerging contaminants from wastewater in a continuous packed-bed photoreactor configuration. *Catalysts*. 2015;**5**(1):77-87. DOI: 10.3390/catal5010077
- [28] Borges ME, Sierra M, Esparza P. Solar photocatalysis at semi-pilot scale:

Wastewater decontamination in a packed-bed photocatalytic reactor system with a visible-solar-light-driven photocatalyst. *Clean Technologies and Environmental Policy*. 2017;**19**(4):1239-1245. DOI: 10.1007/s10098-016-1312-y

[29] Paredes L et al. Application of immobilized TiO₂ on PVDF dual layer hollow fibre membrane to improve the photocatalytic removal of pharmaceuticals in different water matrices. *Applied Catalysis B: Environmental*. 2019;**240**:9-18. DOI: 10.1016/j.apcatb.2018.08.067

[30] Sathasivam S et al. Combinatorial atmospheric pressure CVD of a composite TiO₂/SnO₂ thin film. *Chemical Vapor Deposition*. 2014;**20**:69-79. DOI: 10.1002/cvde.201307081

[31] Kambur A, Pozan G, Boz I. Preparation, characterization and photocatalytic activity of TiO₂-ZrO₂ binary oxide nanoparticles. *Applied Catalysis B: Environmental*. 2012;**s115-116**:149-158. DOI: 10.1016/j.apcatb.2011.12.012

[32] Alotaibi AM, Sathasivam S, Parkin IP. Aerosol assisted chemical vapour deposition of a ZrO₂-TiO₂ composite thin film with enhanced photocatalytic activity. *RSC Advances*. 2015;**5**(83):67944-67950. DOI: 10.1039/C5RA12340B

[33] Poliseti S, Deshpande PA, Madras G. Photocatalytic activity of combustion synthesized ZrO₂ and ZrO₂-TiO₂ mixed oxides. *Industrial and Engineering Chemistry Research*. 2011;**50**(23):12915-12924. DOI: 10.1021/ie200350f

[34] Wang X, Patel RL, Liang X. Significant improvement in TiO₂ photocatalytic activity through controllable ZrO₂ deposition. *RSC Advances*. 2018;**8**(45):25829-25834. DOI: 10.1039/C8RA03423K

[35] Koohestani H, Sadrnezhaad SK. Improvement in TiO₂ photocatalytic

performance by ZrO₂ nanocompositing and immobilizing. *Desalination and Water Treatment*. 2016;**57**(58):28450-28459. DOI: 10.1080/19443994.2016.1183233

[36] Maver K, Štangar UL, Černigoj U, Gross S, Korošec RC. Low-temperature synthesis and characterization of TiO₂ and TiO₂-ZrO₂ photocatalytically active thin films. *Photochemical & Photobiological Sciences*. 2009;**8**(5):657-662. DOI: 10.1039/B817475J

[37] Hernández-Alonso M, Tejedortejedor I, Coronado J, Soria J, Anderson M. Sol-gel preparation of TiO₂-ZrO₂ thin films supported on glass rings: Influence of phase composition on photocatalytic activity. *Thin Solid Films*. 2006;**502**:125-131. DOI: 10.1016/j.tsf.2005.07.256

[38] Linnik O et al. TiO₂/ZrO₂ thin films synthesized by PLD in low pressure N-, C- and/or O-containing gases: Structural, optical and photocatalytic properties. *Digest Journal of Nanomaterials and Biostructures*. 2012;**7**:1343-1352

[39] Hernández-Alonso MD, Tejedortejedor I, Coronado JM, Soria J, Anderson MA. Sol-gel preparation of TiO₂-ZrO₂ thin films supported on glass rings: Influence of phase composition on photocatalytic activity. *Thin Solid Films*. 2006;**502**:125-131. DOI: 10.1016/j.tsf.2005.07.256

[40] Luo Q et al. Preparation and characterization of ZrO₂/TiO₂ composite photocatalytic film by micro-arc oxidation. *Transactions of the Nonferrous Metals Society of China*. 2013;**23**(10):2945-2950. DOI: 10.1016/S1003-6326(13)62818-6

[41] Tatsuma T, Takeda S, Saitoh S, Ohko Y, Fujishima A. Bactericidal effect of energy storage TiO₂-WO₃ Photocatalysis in dark. *Electrochemistry Communications*. 2003;**5**:793-796. DOI: 10.1016/j.elecom.2003.07.003

- [42] Fu L, Cai W, Wang AW, Zheng YH, He L, Fu ZX. Synthesis and photocatalytic properties of TiO₂-WO₃ hybrid film. *Materials and Technologies*. 2015;**30**(5):264-268. DOI: 10.1179/1753555714Y.0000000256
- [43] Kim H-M, Kim D, Kim B. Photoinduced hydrophilicity of TiO₂/WO₃ double layer films. *Surface and Coating Technology*. 2015;**271**:18-21. DOI: 10.1016/j.surfcoat.2015.01.054
- [44] Chen G-S, Cheng C. Searching for the formation of TiO₂ mesoporous films with durable photoactivity by synergy of WO₃ and sodium using a simple sputtering and annealing process. *Applied Catalysis B: Environmental*. 2014;**150-151**:354-362. DOI: 10.1016/j.apcatb.2013.12.017
- [45] Rampaul A, Parkin IP, O'Neill SA, DeSouza J, Mills A, Elliott N. Titania and tungsten doped titania thin films on glass; active photocatalysts. *Polyhedron*. 2003;**22**(1):35-44. DOI: 10.1016/S0277-5387(02)01333-5
- [46] Tatsuma T, Takeda S, Saitoh S, Ohko Y, Fujishima A. Bactericidal effect of an energy storage TiO₂-WO₃ photocatalyst in dark. *Electrochemistry Communications*. 2003;**5**(9):793-796. DOI: 10.1016/j.elecom.2003.07.003
- [47] Tang K et al. Fabrication of WO₃/TiO₂ core-shell nanowire arrays: Structure design and high electrochromic performance. *Electrochimica Acta*. 2020;**330**:135189. DOI: 10.1016/j.electacta.2019.135189
- [48] Tae Kwon Y, Yong Song K, In Lee W, Jin Choi G, Rag Do Y. Photocatalytic behavior of WO₃-loaded TiO₂ in an oxidation reaction. *Journal of Catalysis*. 2000;**191**(1):192-199. DOI: 10.1006/jcat.1999.2776
- [49] Youssef AB, Laamari M, Bousselmi L. TiO₂ and WO₃/TiO₂ thin films for photocatalytic wastewater treatment. *International Journal of Environment and Waste Management*. 2019;**24**:151. DOI: 10.1504/IJEWM.2019.10022371
- [50] Spanu D, Recchia S, Mohajernia S, Schmuki P, Altomare M. Site-selective Pt dewetting on WO₃-coated TiO₂ nanotube arrays: An electron transfer cascade-based H₂ evolution photocatalyst. *Applied Catalysis B: Environmental*. 2018;**237**:198-205. DOI: 10.1016/j.apcatb.2018.05.061
- [51] Ong CB, Ng LY, Mohammad AW. A review of ZnO nanoparticles as solar photocatalysts: Synthesis, mechanisms and applications. *Renewable and Sustainable Energy Reviews*. 2018;**81**:536-551. DOI: 10.1016/j.rser.2017.08.020
- [52] Rajamanickam D, Shanthi M. Photocatalytic degradation of an organic pollutant by zinc oxide-solar process. *Arabian Journal of Chemistry*. 2016;**9**:S1858-S1868. DOI: 10.1016/j.arabjc.2012.05.006
- [53] Lizama C, Freer J, Baeza J, Mansilla HD. Optimized photodegradation of reactive blue 19 on TiO₂ and ZnO suspensions. *Catalysis Today*. 2002;**76**(2):235-246. DOI: 10.1016/S0920-5861(02)00222-5
- [54] Sakthivel S, Neppolian B, Shankar MV, Arabindoo B, Palanichamy M, Murugesan V. Solar photocatalytic degradation of azo dye: Comparison of photocatalytic efficiency of ZnO and TiO₂. *Solar Energy Materials & Solar Cells*. 2003;**77**(1):65-82. DOI: 10.1016/S0927-0248(02)00255-6
- [55] Chiu WS et al. Photocatalytic study of two-dimensional ZnO nanopellets in the decomposition of methylene blue. *Chemical Engineering Journal*. 2010;**158**(2):345-352. DOI: 10.1016/j.cej.2010.01.052
- [56] Vu TT, del Río L, Valdés-Solís T, Marbán G. Tailoring the synthesis of

- stainless steel wire mesh-supported ZnO. *Materials Research Bulletin*. 2012;**47**(6):1577-1586. DOI: 10.1016/j.materresbull.2012.02.017
- [57] Kenanakis G, Giannakoudakis Z, Vernardou D, Savvakis C, Katsarakis N. Photocatalytic degradation of stearic acid by ZnO thin films and nanostructures deposited by different chemical routes. *Catalysis Today*. 2010;**151**(1):34-38. DOI: 10.1016/j.cattod.2010.02.054
- [58] Neppolian B, Choi HC, Sakthivel S, Arabindoo B, Murugesan V. Solar/UV-induced photocatalytic degradation of three commercial textile dyes. *Journal of Hazardous Materials*. 2002;**89**(2):303-317. DOI: 10.1016/S0304-3894(01)00329-6
- [59] Fu H, Xu T, Zhu S, Zhu Y. Photocorrosion inhibition and enhancement of photocatalytic activity for ZnO via hybridization with C60. *Environmental Science & Technology*. 2008;**42**(21):8064-8069. DOI: 10.1021/es801484x
- [60] Photo-induced dissolution of zinc in alkaline solutions—Science Direct. Available from: <https://www.sciencedirect.com/science/article/pii/S0013468699003229> [Accessed: 17 January 2020]
- [61] Fabrication of CuO-ZnO Nanowires on a Stainless Steel Mesh for Highly Efficient Photocatalytic Applications. Available from: https://www.researchgate.net/publication/49754945_Fabrication_of_CuO-ZnO_nanowires_on_a_stainless_steel_mesh_for_highly_efficient_photocatalytic_applications [Accessed: 17 January 2020]
- [62] Ren C et al. Synthesis of Ag/ZnO nanorods array with enhanced photocatalytic performance. *Journal of Hazardous Materials*. 2010;**182**(1):123-129. DOI: 10.1016/j.jhazmat.2010.05.141
- [63] Facile Synthesis of Ag/ZnO Heterostructures Assisted by UV Irradiation: Highly Photocatalytic Property and Enhanced Photostability—Science Direct. Available from: <https://www.sciencedirect.com/science/article/pii/S0025540811002741> [Accessed: 17 January 2020]
- [64] Xie W, Li Y, Sun W, Huang J, Xie H, Zhao X. Surface modification of ZnO with Ag improves its photocatalytic efficiency and photostability. *Journal of Photochemistry and Photobiology A: Chemistry*. 2010;**216**(2):149-155. DOI: 10.1016/j.jphotochem.2010.06.032
- [65] Tian C, Zhang Q, Jiang B, Tian G, Fu H. Glucose-mediated solution–solid route for easy synthesis of Ag/ZnO particles with superior photocatalytic activity and photostability. *Journal of Alloys and Compounds*. 2011;**509**(24):6935-6941. DOI: 10.1016/j.jallcom.2011.04.005
- [66] Han Z, Ren L, Cui Z, Chen C, Pan H, Chen J. Ag/ZnO flower heterostructures as a visible-light driven photocatalyst via surface plasmon resonance. *Applied Catalysis B: Environmental*. 2012;**126**:298-305. DOI: 10.1016/j.apcatb.2012.07.002
- [67] Photocorrosion Inhibition and Photoactivity Enhancement for Zinc Oxide via Hybridization with Monolayer Polyaniline. *The Journal of Physical Chemistry C*. Available from: <https://pubs.acs.org/doi/abs/10.1021/jp810748u> [Accessed: 17 January 2020]
- [68] Photocorrosion Suppression of ZnO Nanoparticles via Hybridization with Graphite-like Carbon and Enhanced Photocatalytic Activity—Google Search. Available from: https://www.google.com/search?q=Photocorrosion+Suppression+of+ZnO+Nanoparticles+via+Hybridization+with+Graphite-like+Carbon+and+Enhanced+Photocatalytic+Activity&rlz=1C1GCEU_esES875ES875&oq=Ph

- otocorrosion+Suppression+of+ZnO+Nanoparticles+via+Hybridization+with+Graphite-like+Carbon+and+Enhanced+Photocatalytic+Activity&aq=chrome..69i57.884j0j4&sourceid=chrome&ie=UTF-8 [Accessed: 17 January 2020]
- [69] Wang J, Liu P, Wang S, Han W, Wang X, Fu X. Nanocrystalline zinc oxide in perfluorinated ionomer membranes: Preparation, characterization, and photocatalytic properties. *Journal of Molecular Catalysis A: Chemical*. 2007;**273**(1):21-25. DOI: 10.1016/j.molcata.2007.03.062
- [70] Suchithra PS, Shadiya CP, Mohamed AP, Velusamy P, Ananthakumar S. One-pot microwave mediated growth of heterostructured ZnO@AlSi as a potential dual-function eco-catalyst for treating hazardous pollutants in water resources. *Applied Catalysis B: Environmental*. 2013;**130-131**:44-53. DOI: 10.1016/j.apcatb.2012.10.010
- [71] Bessekhoud Y, Robert D, Weber J-V, Chaoui N. Effect of alkaline-doped TiO₂ on photocatalytic efficiency. *Journal of Photochemistry and Photobiology A: Chemistry*. 2004;**167**(1):49-57. DOI: 10.1016/j.jphotochem.2003.12.001
- [72] Chen L-C, Tu Y-J, Wang Y-S, Kan R-S, Huang C-M. Characterization and photoreactivity of N-, S-, and C-doped ZnO under UV and visible light illumination. *Journal of Photochemistry and Photobiology A: Chemistry*. 2008;**199**(2):170-178. DOI: 10.1016/j.jphotochem.2008.05.022
- [73] Kaneva NV, Dimitrov DT, Dushkin CD. Effect of nickel doping on the photocatalytic activity of ZnO thin films under UV and visible light. *Applied Surface Science*. 2011;**257**(18):8113-8120. DOI: 10.1016/j.apsusc.2011.04.119
- [74] Cobalt-Doped Zincblende–Wurtzite Mixed-Phase ZnO Photocatalyst Nanoparticles with High Activity in Visible Spectrum—Science Direct. *Applied Catalysis B: Environmental*. 2014;**144**:435-441. Available from: <https://www.sciencedirect.com/science/article/abs/pii/S0926337313004670> [Accessed: 17 January 2020]
- [75] Zhu H-Y, Xiao L, Jiang R, Zeng G-M, Liu L. Efficient decolorization of azo dye solution by visible light-induced photocatalytic process using SnO₂/ZnO heterojunction immobilized in chitosan matrix. *Chemical Engineering Journal*. 2011;**172**(2):746-753. DOI: 10.1016/j.cej.2011.06.053
- [76] Tian H, Ma J, Li K, Li J. Photocatalytic degradation of methyl orange with W-doped TiO₂ synthesized by a hydrothermal method. *Materials Chemistry and Physics*. 2008;**112**(1):47-51. DOI: 10.1016/j.matchemphys.2008.05.005
- [77] Adsorption-Photodegradation of Humic Acid in Water by using ZnO Coupled TiO₂/Bamboo Charcoal Under Visible Light Irradiation—PubMed—NCBI. *Journal of Hazardous Materials*. 2013;**262**:16-24. Available from: <https://www.ncbi.nlm.nih.gov/pubmed/24004575> [Accessed: 17 January 2020]
- [78] ZnO/CdO Composite Nanorods for Photocatalytic Degradation of Methylene Blue under Visible Light—Science Direct. *Materials Chemistry and Physics*. 2011;**125**:277-280. Available from: <https://www.sciencedirect.com/science/article/abs/pii/S0254058410007571> [Accessed: 17 January 2020]
- [79] Pawar RC, Lee CS. Single-step sensitization of reduced graphene oxide sheets and CdS nanoparticles on ZnO nanorods as visible-light photocatalysts. *Applied Catalysis B: Environmental*. 2014;**144**:57-65. DOI: 10.1016/j.apcatb.2013.06.022

- [80] Li D, Haneda H, Ohashi N, Hishita S, Yoshikawa Y. Synthesis of nanosized nitrogen-containing $\text{MO}_x\text{-ZnO}$ ($M = \text{W, V, Fe}$) composite powders by spray pyrolysis and their visible-light-driven photocatalysis in gas-phase acetaldehyde decomposition. *Catalysis Today*. 2004;**93-95**:895-901. DOI: 10.1016/j.cattod.2004.06.099
- [81] Encapsulation of CdO/ZnO NPs in PU Electrospun Nanofibers as Novel Strategy for Effective Immobilization of the Photocatalysts—Science Direct. *Colloids and Surfaces A: Physicochemical and Engineering Aspects*. 2012;**401**:8-16. Available from: <https://www.sciencedirect.com/science/article/abs/pii/S0927775712001148> [Accessed: 17 January 2020]
- [82] Vu T, Rodil A, Marban G, Valdés-Solís T. Nanostructured stainless steel wire mesh-supported $\text{Cd}_x\text{Zn}_{1-x}\text{O}$: A stable photocatalyst under visible and ultraviolet irradiation. *Journal of Environmental Chemical Engineering*. 2014;**2**:1612-1620. DOI: 10.1016/j.jece.2014.06.018
- [83] Janáky C, Rajeshwar K, de Tacconi NR, Chanmanee W, Huda MN. Tungsten-based oxide semiconductors for solar hydrogen generation. *Catalysis Today*. 2013;**199**:53-64. DOI: 10.1016/j.cattod.2012.07.020
- [84] Dong P, Hou G, Xi X, Shao R, Dong F. WO_3 -based photocatalysts: Morphology control, activity enhancement and multifunctional applications. *Environmental Science. Nano*. 2017;**4**(3):539-557. DOI: 10.1039/C6EN00478D
- [85] Johansson M, Niklasson G, Osterlund L. Structural and optical properties of visible active photocatalytic WO_3 thin films prepared by reactive dc magnetron sputtering. *Journal of Materials Research*. 2012;**27**:3130-3140. DOI: 10.1557/jmr.2012.384
- [86] Wicaksana Y, Liu S, Scott J, Amal R. Tungsten trioxide as a visible light photocatalyst for volatile organic carbon removal. *Molecules*. 2014;**19**:17747-17762. DOI: 10.3390/molecules191117747
- [87] Tahir MB, Nabi G, Rafique M, Khalid NR. Nanostructured-based WO_3 photocatalysts: Recent development, activity enhancement, perspectives and applications for wastewater treatment. *International journal of Environmental Science and Technology*. 2017;**14**(11):2519-2542. DOI: 10.1007/s13762-017-1394-z
- [88] Formation of a Photocatalytic WO_3 Surface Layer on Electrodeposited Al-W Alloy Coatings by Selective Dissolution and Heat Treatment. *Scientific Reports*. 2019. Available from: <https://www.nature.com/articles/s41598-019-52178-6> [Accessed: 11 June 2020]
- [89] Valerini D, Hernández S, Di Benedetto F, Russo N, Saracco G, Rizzo A. Sputtered WO_3 films for water splitting applications. *Materials Science in Semiconductor Processing*. 2016;**42**:150-154. DOI: 10.1016/j.mssp.2015.09.013
- [90] Zheng H, Sadek AZ, Latham K, Kalantar-Zadeh K. Nanoporous WO_3 from anodized RF sputtered tungsten thin films. *Electrochemistry Communications*. 2009;**11**(4):768-771. DOI: 10.1016/j.elecom.2009.01.033
- [91] Khatko V et al. Tungsten trioxide sensing layers on highly ordered nanoporous alumina template. *Sensors and Actuators B: Chemical*. 2006;**118**(1):255-262. DOI: 10.1016/j.snb.2006.04.030
- [92] Visible-Light Active Thin-Film WO_3 Photocatalyst with Controlled High-Rate Deposition by Low-Damage Reactive-Gas-Flow Sputtering. *APL Materials*. 2010;**3**(10). Available from: <https://aip.scitation.org/>

doi/10.1063/1.4922942 [Accessed: 11 June 2020]

[93] Kim H, Bonsu RO, O'Donohue C, Korotkov RY, McElwee-White L, Anderson TJ. Aerosol-assisted chemical vapor deposition of tungsten oxide films and nanorods from oxo tungsten(VI) fluoroalkoxide precursors. *ACS Applied Materials & Interfaces*. 2015;7(4):2660-2667. DOI: 10.1021/am507706e

[94] Houweling ZS, Geus JW, Schropp REI. Hot-wire chemical vapor deposition of WO_{3-x} thin films of various oxygen contents. *Materials Chemistry and Physics*. 2013;140(1):89-96. DOI: 10.1016/j.matchemphys.2013.02.072

[95] Au BWC, Chan KY, Pang WL, Lee CL, Mustafa AH. Tungsten oxide (WO_3) films prepared by sol-gel spin-coating technique. *Solid State Phenomena*. 2018;280:71-75. Available from: /SSP.280.71 [Accessed: 11 June 2020]

[96] Kim K-W et al. Various coating methodologies of WO_3 according to the purpose for electrochromic devices. *Nanomaterials*. 2020;10:821-823. DOI: 10.3390/nano10050821

[97] Mathuri S, Margoni MM, Ramamurthi K, Babu RR, Ganesh V. Hydrothermal assisted growth of vertically aligned platelet like structures of WO_3 films on transparent conducting FTO substrate for electrochromic performance. *Applied Surface Science*. 2018;449:77-91. DOI: 10.1016/j.apsusc.2018.01.033

[98] Hydrothermal Formation of Tungsten Trioxide Nanowire Networks on Seed-Free Substrates and Their Properties in Electrochromic Device. Request PDF. Available from: https://www.researchgate.net/publication/262150728_Hydrothermal_Formation_of_Tungsten_Trioxide_Nanowire_Networks_on_Seed-Free_Substrates_and_Their_Properties_in_

Electrochromic_Device [Accessed: 11 June 2020]

[99] Bertus LM et al. Synthesis and characterization of WO_3 thin films by surfactant assisted spray pyrolysis for electrochromic applications. *Materials Chemistry and Physics*. 2013;140(1):49-59. DOI: 10.1016/j.matchemphys.2013.02.047

[100] Mancieru L, Duta A. Synthesis of WO_3 thin films by surfactant mediated spray pyrolysis. *Ceramics International*. 2012;38:2873-2882. DOI: 10.1016/j.ceramint.2011.11.060

[101] Lai CW. WO_3 nanoplates film: Formation and photocatalytic oxidation studies. *Journal of Nanomaterials*. 2015;22:7. Available from: <https://www.hindawi.com/journals/jnm/2015/563587/> [Accessed: 11 June 2020]

[102] Visible Light-Induced Photocatalytic Properties of WO_3 Films Deposited by DC Reactive Magnetron Sputtering. *Journal of Vacuum Science & Technology A*. 2012;30:031503 Available from: <https://avs.scitationo.rg/doi/abs/10.1116/1.3696876?journalCode=jva> [Accessed: 11 June 2020]

[103] Higashino S, Miyake M, Ikenoue T, Hirato T. Formation of a photocatalytic WO_3 surface layer on electrodeposited Al-W alloy coatings by selective dissolution and heat treatment. *Scientific Reports*. 2019;9(1):16008. DOI: 10.1038/s41598-019-52178-6

[104] Takashima J, Oka N, Shigesato Y. Photocatalytic activity of WO_3 films crystallized by postannealing in air. *Japanese Journal of Applied Physics*. 2012;51(5R):055501. DOI: 10.1143/JJAP.51.055501

[105] Cui L et al. Facile preparation of Z-scheme $WO_3/g-C_3N_4$ composite photocatalyst with enhanced photocatalytic performance under visible light. *Applied Surface Science*.

2016;**391**:202-210. DOI: 10.1016/j.apsusc.2016.07.055

[106] Bouras K et al. Optical and structural properties of Nd doped SnO₂ powder fabricated by the sol-gel method. *Journal of Materials Chemistry C*. 2014;**2**(39):8235-8243. DOI: 10.1039/C4TC01202J

[107] Huang Y, Li D, Feng J, Li G, Zhang Q. Transparent conductive tungsten-doped tin oxide thin films synthesized by sol-gel technique on quartz glass substrates. *Journal of Sol-Gel Science and Technology*. 2010;**54**(3):276-281. DOI: 10.1007/s10971-010-2182-0

[108] Huang Y, Zhang Q, Li G. Transparent conductive tungsten-doped tin oxide polycrystalline films prepared on quartz substrates. *Semiconductor Science and Technology*. 2008;**24**(1):015003. DOI: 10.1088/0268-1242/24/1/015003

[109] Nakao S, Yamada N, Hitosugi T, Hirose Y, Shimada T, Hasegawa T. Fabrication of transparent conductive W-doped SnO₂ thin films on glass substrates using anatase TiO₂ seed layers. *Physica Status Solidi C: Current Topics in Solid State Physics*. 2011;**8**(2):543-545. DOI: 10.1002/pssc.201000505

[110] Yadav JB, Patil RB, Puri RK, Puri V. Studies on undoped SnO₂ thin film deposited by chemical reactive evaporation method. *Materials Science and Engineering B*. 2007;**139**(1):69-73. DOI: 10.1016/j.mseb.2007.01.032

[111] Rifai A, Iqbal M, Tapran N, Nuruddin A, Suyatman S, Yulianto B. Synthesis and characterization of SnO₂ thin films by chemical bath deposition. *AIP Conf. Proc.* 2011;**1415**:231-233. DOI: 10.1063/1.3667263

[112] Jana S, Mitra B, Bera P, Sikdar M, Mondal A. Photocatalytic activity of galvanically synthesized nanostructure

SnO₂ thin films. *Journal of Alloys and Compounds*. 2014;**602**:42-48. DOI: 10.1016/j.jallcom.2014.02.182

[113] Soussi L et al. Effect of (Co, Fe, Ni) doping on structural, optical and electrical properties of sprayed SnO₂ thin film. *Surfaces and Interfaces*. 2020;**19**:100467. DOI: 10.1016/j.surfin.2020.100467

[114] Gandhi TI, Ramesh Babu R, Ramamurthi K. Structural, morphological, electrical and optical studies of Cr doped SnO₂ thin films deposited by the spray pyrolysis technique. *Materials Science in Semiconductor Processing*. 2013;**16**(2):472-479. DOI: 10.1016/j.mssp.2012.07.008

[115] Cho Y, Parmar NS, Nahm S, Choi J-W. Full range optical and electrical properties of Zn-doped SnO₂ and oxide/metal/oxide multilayer thin films deposited on flexible PET substrate. *Journal of Alloys and Compounds*. 2017;**694**:217-222. DOI: 10.1016/j.jallcom.2016.09.293

[116] Gupta S, Yadav BC, Dwivedi PK, Das B. Microstructural, optical and electrical investigations of Sb-SnO₂ thin films deposited by spray pyrolysis. *Materials Research Bulletin*. 2013;**48**(9):3315-3322. DOI: 10.1016/j.materresbull.2013.05.001

[117] Wang M et al. Transparent and conductive W-doped SnO₂ thin films fabricated by an aqueous solution process. *Thin Solid Films*. 2013;**544**:419-426. DOI: 10.1016/j.tsf.2013.02.088

[118] Ynineb F et al. Influence of Sn content on properties of ZnO:SnO₂ thin films deposited by ultrasonic spray pyrolysis. *Materials Science in Semiconductor Processing*. 2013;**16**:2021-2027. DOI: 10.1016/j.mssp.2013.07.023

- [119] Medjaldi F, Bouabellou A, Bouachiba Y, Taabouche A, Bouatia K, Serrar H. Study of TiO₂, SnO₂ and nanocomposites TiO₂:SnO₂ thin films prepared by sol-gel method: Successful elaboration of variable–refractive index systems. *Materials Research Express*. 2020;**7**(1):016439. DOI: 10.1088/2053-1591/ab6c0c
- [120] Vadivel S, Rajarajan G. Effect of W doping on structural, optical and photocatalytic activity of SnO₂ nanostructure thin films. *Journal of Materials Science: Materials in Electronics*. 2015;**26**(9):7127-7133. DOI: 10.1007/s10854-015-3335-2
- [121] Haya S, Brahmia O, Halimi O, Sebais M, Boudine B. Sol–gel synthesis of Sr-doped SnO₂ thin films and their photocatalytic properties. *Materials Research Express*. 2017;**4**(10):106406. DOI: 10.1088/2053-1591/aa8deb
- [122] Influence of Cu Doping on Structural, Optical and Photocatalytic Activity of SnO₂ Nanostructure Thin Films. *Materials Chemistry and Physics*. **148**(3):528-532. Available from: <https://www.springerprofessional.de/en/influence-of-cu-doping-on-structural-optical-and-photocatalytic-/3559896> [Accessed: 13 June 2020]
- [123] Nassiri C, Hadri A, Chafi F, Rouchdi M, Fares B, Mzerd A. Structural, optical and electrical properties of Fe doped SnO₂ prepared by spray pyrolysis. *Journal of Materials and Environmental Sciences*. 2017;**8**:420-425
- [124] Thangaraju B. Structural and electrical studies on highly conducting spray deposited fluorine and antimony doped SnO₂ thin films from SnCl₂ precursor. *Thin Solid Films*. 2002;**402**(1):71-78. DOI: 10.1016/S0040-6090(01)01667-4
- [125] Abass AK. Electrical and optical properties of chlorine doped SnO₂ coatings. *Solid State Communications*. 1987;**61**(8):507-510. DOI: 10.1016/0038-1098(87)90502-3
- [126] Han K, Peng X-L, Li F, Yao M-M. SnO₂ composite films for enhanced photocatalytic activities. *Catalysts*. 2018;**8**(10):453. DOI: 10.3390/catal8100453
- [127] Kong X, Li F, Qi Z, Qi L, Yao M. SnO₂-based thin films with excellent photocatalytic performance. *Journal of Materials Science: Materials in Electronics*. 2017;**28**:1-8. DOI: 10.1007/s10854-017-6459-8