



Flotation-separation of toxic metal ions from aqueous solutions using thiosemicarbazide derivatives as chelating agents and oleic acid as a surfactant

Shaban El-Sayed Ghazy*, Gaber Mohamed Abu El-Reash, Ola Ahmed Al-Gammal and Tarek Yousef

Department of Chemistry, Faculty of Science Mansoura University, Mansoura-35516, Egypt

*Corresponding author at: Department of Chemistry, Faculty of Science Mansoura University, Mansoura-35516, Egypt. Tel.: +20502246254; fax: +20502246254. E-mail-address: ghazyse@mans.edu.eg (S.E. Ghazy).

ARTICLE INFORMATION

Received: 27 February 2010
Received in revised form: 10 April 2010
Accepted: 3 May 2010
Online: 30 June 2010

KEYWORDS

Mercury
Manganese
Cadmium
Thiosemicarbazide derivatives
Oleic acid
Natural water

ABSTRACT

A simple and rapid procedure was developed for flotation-separation of toxic metal ions namely Hg^{2+} , Mn^{2+} and Cd^{2+} from aqueous solutions. Thiosemicarbazide derivatives such as: 1-(amino-*N*-phenylmethanethio)-4-(pyridine-2-yl)thiosemicarbazide (H_2PPS), *N*-phenyl-2-(pyridine-2-ylcarbamothioyl)hydrazinecarboxamide (H_2PBO), 1-(amino(thioformyl)-*N*-phenylform)-4-(pyridine-2-yl)thiosemicarbazide (H_2APO), and 1-(amino-*N*-(pyridine-3-yl) methanethio)-4-(pyridine-2-yl)thiosemicarbazide (H_2PPY) have been used as organic chelating agents and oleic acid (HOL) as a surfactant. The different parameters affecting the flotation process namely, metal ion, ligands and surfactant concentrations, foreign ions (which are normally present in fresh and saline waters), pH and temperature are examined. About 100% of mercury, cadmium and manganese ions float at room temperature ($\sim 25^\circ\text{C}$), at a metal:ligand ratio of 1:2 and at pH ~ 5 . The procedure was successfully applied to recover Hg^{2+} , Mn^{2+} and Cd^{2+} ions spiked into some water samples. The flotation mechanism is suggested based on some physical and chemical studies on the ligands and metal-complexes isolated from the floated layers.

1. Introduction

Toxic metal pollution is spreading throughout the world with the expansion of industrial activities [1]. These metals, which find many useful applications in our lives, are very harmful if they are discharged into natural water resources and may finally pose serious health hazards [2-4]. In other words, toxic metals which are of great environmental concern must be removed [5-7]. Industrial wastewater contains high levels of toxic metals and in order to avoid water pollution, treatment is needed before its disposal.

Mercury is considered to be a serious toxic metal pollutant [8]. Hg induced toxicity is related to differences in species, chemical form, specimen size and temperature, as well as other factors [9]. Hg^{2+} can be methylated to $(\text{CH}_3)_2\text{Hg}$ and CH_3Hg^+ . Therefore, the longer the divalent inorganic mercurials remain in the environment, the more problematic the lipophilicity of the product-organic alkylmercury salt. Since the majority (often 100%) of Hg in muscles is CH_3Hg^+ species [9], little safety margin exists.

Cadmium, a heavy metal with limited biological function, is widely distributed in the aquatic environment as a result of natural and anthropogenic activities. Discharges containing cadmium are strictly controlled due to the highly toxic nature of this element and its tendency to accumulate in the tissues of living organisms. The harmful effects of cadmium include a number of chronic and acute disorders such as renal damage, emphysema, hypertension, high blood pressure, kidney damage and destruction of red blood cells [8,10].

Manganese is an essential metal ion for life. It is a cofactor for a wide variety of enzymes, including the oxygen evolving complex, several kinases, phosphatases, synthetases and oxido-

reductases [11]. Mn is an essential metal found in a variety of biological tissues and is necessary for normal functioning of a variety of physiological processes including amino acid, lipid, protein and carbohydrate metabolism [12]. It is also widely employed in industry (e.g. ferro-alloy plants), in agriculture (fertilizers and pesticides) and it has recently been introduced as an antiknock agent in unleaded gasoline. However, exposure to Mn may lead to accumulation in the basal ganglia of the brain, where it may have its neurotoxic effects [13]. Therefore, from the viewpoints of environmental chemistry, geochemistry and marine biology, it is important to establish a rapid and simple method for removing Hg^{2+} , Cd^{2+} and Mn^{2+} ions from water.

Numerous techniques for the separation, removal and control of metal toxicants have been reported [8,14-16]. Although adsorption has been well established as a technology for removing toxic compounds from wastes or wastewaters, the process may face filter-blocking problems [16]. Also, sedimentation is a relatively slow process when dealing with biological materials that are usually of low density. Flotation as a separation process has recently received a considerable interest owing to its simplicity, rapidity, economy, good separation yields ($R > 95\%$) at small concentrations (10^{-6} - 10^{-2} mol L^{-1}), and a large possibility of application for species having different nature and structure, flexibility and friability of equipment and processing for recovery purposes [17]. It is believed that this process will soon be incorporated as a clean technology to treat both water and wastewater [18]. Therefore, the flotation technique was used in this investigation.

Ion flotation involves the removal of surface-inactive ions (colligend) from aqueous solutions by adding surfactants which act as collectors. The subsequent passage of gas bubbles

through the solution transfers the surface-active ions to the top [19]. Compared to other separation methods, ion flotation has advantages in its ease of operation and low costs. It shows particular promise for treating large volumes of dilute aqueous solutions [20].

Precipitate flotation is a foam separation process used to remove surface inactive substances from aqueous dispersions. The component to be removed is precipitated before the addition of a surfactant (collector). This may be accomplished by adding any substance that forms an insoluble compound. Since the surfactant needs only to react with ions on the surface, small amounts of collector is required [10]. Moreover, in this process the separation is obtained at the interface of the bulk and foam phases without the assistance from the extended phase, having the advantage of producing dry foam of small volume and thus allowing the use of compact equipment [10].

Electroflotation (ECF) technology could potentially present an alternative method for the removal of metals originating from products or machines facilities. ECF uses small bubbles obtained through aqueous solution electrolysis to float particles of a given size to the top. During the process, a cloud or blanket of finely dispersed gas bubbles is created with the help of two metallic electrodes (cathode/anode). The fine bubbles rise and attach to insoluble contaminant particles like metals or other organic substances. Part of the electrolytic products in the form of free radicals might also react with soluble organic matter and may cause considerable transformation. Several minutes into the process, coagulation begins which subsequently leads to the formation of a foamy layer that float to the top of the reaction vessel [21].

Although some work has been carried out for the flotation of Hg^{2+} [8,10,14,22-28]; Cd^{2+} [8,10,29-37] and Mn^{2+} [17,32,38-43] from aqueous solutions, wastes and natural waters, no attention has been paid towards the use of thiosemicarbazide derivatives in this respect. Therefore, the objective of the present work was to extend the application of flotation technique to separate Hg^{2+} , Cd^{2+} and Mn^{2+} ions from aqueous solutions using (H_2PPS), (H_2PBO), (H_2APO), (H_2PPY) and oleic acid surfactant (HOL) under the recommended conditions.

2. Experimental

2.1. Reagents

Unless otherwise stated, all the chemicals used were of analytical grade and were used without further purification. Oleic acid (HOL) surfactant was used directly as received. Its stock solution 6.36×10^{-2} mol L^{-1} , was prepared from food grade with specific gravity 0.895 (J. T. Baker Chemical Co.) by dispersing 20 ml in one liter of kerosene. Mercuric chloride (HgCl_2), manganese chloride (MnCl_2) and cadmium chloride (CdCl_2) stock solutions, 1×10^{-2} mol L^{-1} , each, were prepared by dissolving the calculated amounts in double distilled water. The stock solutions of the ligands H_2PPS , H_2PBO , H_2APO and H_2PPY , 1×10^{-2} mol L^{-1} , each, were prepared in dioxane. The solids of these ligands were prepared by slowly adding phenyl isothiocyanate, phenylisocyanate, benzoylisothiocyanate and 2-pyridylisothiocyanate in absolute ethanol. The mixtures were refluxed on a water bath for a fixed time (30-120 min) depending on the reaction mixture. The products obtained were crystallized several times from absolute ethanol and dried in a vacuum desiccator over anhydrous CaCl_2 . The purity and properties of the ligands (Table 1) was checked by elemental analysis (Table 2) and IR (Table 3).

2.2. Apparatus

The flotation cell was a tube of 16 mm inner diameter and 290 mm in length with a quick fit stopper at the top and a

stopcock at the bottom [44]. There are no instruments on the market for these techniques and because of the simplicity of the necessary devices, they are tailored according to the task in hand. Moreover, the following instruments are available in our Chemistry Department. The infrared spectra of the ligands, and their metal complexes were recorded on Mattson 5000 FTIR Spectrophotometer using KBr disc method. Spectrophotometric measurements were performed using a Unicam UV-2100 spectrophotometer. The pH measurements were carried out using Hanna Instrument 8519 digital pH meter.

2.3. Procedure

A suitable aliquot containing a known amount of Hg^{2+} , Mn^{2+} or Cd^{2+} specified for each investigation, was mixed with one of the thiosemicarbazide derivatives. The solution pH was adjusted with HNO_3 and/or NaOH to the required value. The solution was then transferred to the flotation cell and the total volume was made up to 10 ml with double distilled water. The cell was shaken well for 5 min to ensure complete complexation. To this, 2 mL of HOL (with known concentration) were added. The cell was then inverted upside down twenty times by hand. After 5 min standing for complete flotation, the concentration of the investigated metal ions in the mother liquors was determined spectrophotometrically using dithizone method at 485 nm (for Hg^{2+}), potassium periodate oxidant in acidic medium at 528 nm (for Mn^{2+}) and dithizone method at 520 nm (for Cd^{2+}) [45].

The floatability (F %) of each M^{2+} ion was calculated according to the relation :

$$F \% = (C_i - C_f) / C_i \times 100 \quad (1)$$

where C_i and C_f denote the initial and the final concentrations of M^{2+} ion in the mother liquor, respectively.

3. Results and Discussion

Several experiments were carried out to investigate the floatability of Hg^{2+} , Mn^{2+} and Cd^{2+} ions using only HOL as a surfactant. The floatability of M^{2+} ions does not exceed 40%. Therefore, an enhancement of the process was required. Trials were made using some thiosemicarbazide derivatives as chelating agents. A number of reports concerning thiosemicarbazides and their metal complexes were established owing to their chemical and biological activities [46]. Really, an important number of thiosemicarbazides possess cardiostatic efficacy and substantial *in vivo* activity against various human tumor lines [47]. Encouraging flotation results were attained using (H_2PPS), (H_2PBO), (H_2APO) and (H_2PPY) for Hg^{2+} ions; (H_2PPS) and (H_2APO) for Mn^{2+} ions and (H_2PPY) for Cd^{2+} ions flotation.

3.1. Effect of pH

pH is an important factor influencing flotation process since it affects not only the degree of ionization of metal ions, chelating agents and surfactants but also the speciation of the heavy metal ions in solution. The metal ions in aqueous solution are converted to different insoluble hydrolysis products due to changes in pH. Several experiments were carried out to investigate the floatability of 2×10^{-4} mol L^{-1} of Hg^{2+} , Mn^{2+} and Cd^{2+} ions vs. solution pH using 4×10^{-4} mol L^{-1} of each thiosemicarbazide derivative and 1×10^{-3} mol L^{-1} HOL. The results obtained are plotted in Fig. 1 (A, B, and C). It can be seen that, maximal floatability of Hg^{2+} ions (~100%) were attained in the pH ranges of 4-6, 4-8, 3-10 and 4-9 using (H_2PPS), (H_2PBO), (H_2APO) and (H_2PPY), respectively (Figure 1A). Moreover, maximal floatability (~100%) of Mn^{2+} (Figure 1B) and Cd^{2+} (Figure 1C) ions were attained in the pH ranges of 2-6 using (H_2PPS) and (H_2APO) and of 4-7 using (H_2APO), respectively.

Table 1. Physical properties of the prepared ligands.

Compound	Color	Solvent	M.p.(°C)	Yield(%)	Formula
H ₂ PPS	yellow	Dioxane,DMF	180	78	C ₁₃ H ₁₃ N ₅ S ₂
H ₂ PBO	yellow	Dioxane,DMF	270	81	C ₁₃ H ₁₃ N ₅ SO
H ₂ APO	white	Dioxane,DMF	182	79	C ₁₄ H ₁₃ N ₅ S ₂ O
H ₂ PPY	yellow	Dioxane,DMF	310	82	C ₁₂ H ₁₂ N ₆ S ₂

Table 2. Chemical analysis of the prepared ligands.

Compound	Mol. Wt.	% Calc. (Found)				
		C	H	N	O	S
C ₁₃ H ₁₃ N ₅ S ₂ (H ₂ PPS)	303.41	51.46 (51.13)	4.32 (4.25)	23.08 (22.96)	-	21.14 (21.11)
C ₁₃ H ₁₃ N ₅ OS (H ₂ PBO)	287.34	54.34 (54.15)	4.56 (4.45)	24.37 (23.98)	5.57 (5.40)	11.16 (11.11)
C ₁₄ H ₁₃ N ₅ OS ₂ (H ₂ APO)	331.42	50.74 (50.35)	3.95 (3.47)	21.13 (21.78)	4.83 (4.80)	19.35 (19.31)
C ₁₂ H ₁₂ N ₆ S ₂ (H ₂ PPY)	304.06	47.35 (47.02)	3.97 (4.05)	27.61 (27.86)	-	21.07 (21.31)

Table 3. Assignment of important bands in the infrared spectra of the prepared ligands.

Compound	$\nu(\text{C}=\text{S})$	$\nu(\text{NH})$ a, a'	$\nu(\text{NH})$ b, c	$\nu(\text{C}=\text{N})$ py	$\nu(\text{C}=\text{C})$	$\nu(\text{C}=\text{O})$
H ₂ PPS	1223,755,850	3099	3160	1569	1598	-
H ₂ PBO	1247,775,800	3170, 3104	3220	1641	1600	1672
H ₂ APO	1243,701,865	3158, 3100	3239	1542	1604	1675
H ₂ PPY	1218,900,750	3174	3234	1562	1604	-

This facilitates the application of some of the investigated thiosemicarbazide derivatives for the separation of Hg²⁺, Mn²⁺ and Cd²⁺ ions from acidic, neutral and alkaline mediums. The common pH range in which all the thiosemicarbazide derivatives gave maximal flotation of the investigated metal ions was found to be in the range of 4-6. Hence, pH ~5 was fixed for further experiments for the flotation-separation of Hg²⁺, Mn²⁺ and Cd²⁺ ions.

3.2. Effect of metal ion and ligand concentrations

Attempts were carried out to float different concentrations of Hg²⁺, Mn²⁺ and Cd²⁺ ions using 4×10⁻⁴ mol L⁻¹ of each thiosemicarbazide derivative and 1×10⁻³ mol L⁻¹ HOL at pH ~5. The results obtained (Figure 2A, 2B, and 2C) show that the maximum flotation efficiency (~100%) of these metal ions were obtained for all the investigated thiosemicarbazide derivatives whenever the ratio of (M:L) is 1:1 for some thiosemicarbazides or 1:2 for others. Moreover, when the ratio is smaller than 1:2, all the chelating agents gave quantitative separation of Hg²⁺, Mn²⁺ and Cd²⁺ ions which may be attributed to the presence of sufficient amounts of thiosemicarbazide derivatives to bind all the investigated metal ions. At high metal ion concentration more than the ratio of 1:1, the flotation begins to decrease.

Another series of experiments were conducted to investigate the collecting ability of (H₂PPS), (H₂PBO), (H₂APO) and (H₂PPY) towards Hg²⁺, Mn²⁺ and Cd²⁺ ions using different concentrations of thiosemicarbazide derivatives and 1×10⁻³ mol L⁻¹ HOL at pH ~5. The data presented in Figure 3 (A, B and C) show that, the floatability of metal ions increases abruptly reaching its maximum value (~100%) at M:L ratio of (1:1). Moreover, excess ligands have no adverse effect on the flotation process, thus facilitating the separation of Hg²⁺, Mn²⁺ and Cd²⁺ ions from unknown matrices; 4×10⁻⁴ mol L⁻¹ of each thiosemicarbazide derivative was used throughout.

3.3. Effect of surfactant concentration

Trials were carried out to float Hg²⁺, Mn²⁺ and Cd²⁺ ions with HOL only, but the recovery does not exceed 40%, as shown in curve b (Figure 4A). Therefore, another series of experiments were performed to float 2×10⁻⁴ mol L⁻¹ of Hg²⁺, Mn²⁺ and Cd²⁺ ions in the presence of 4×10⁻⁴ mol L⁻¹ of each thiosemicarbazide derivative and different concentrations of HOL at pH ~5. The results depicted in Figure 4 (A, B, and C) show that in the HOL concentration range of 1×10⁻³-6×10⁻² mol L⁻¹, complete flotation of Hg²⁺, Mn²⁺ and Cd²⁺ ions was achieved, below which the flotation decreases. This may be attributed to the presence of insufficient amounts of surfactant required for complete flotation.

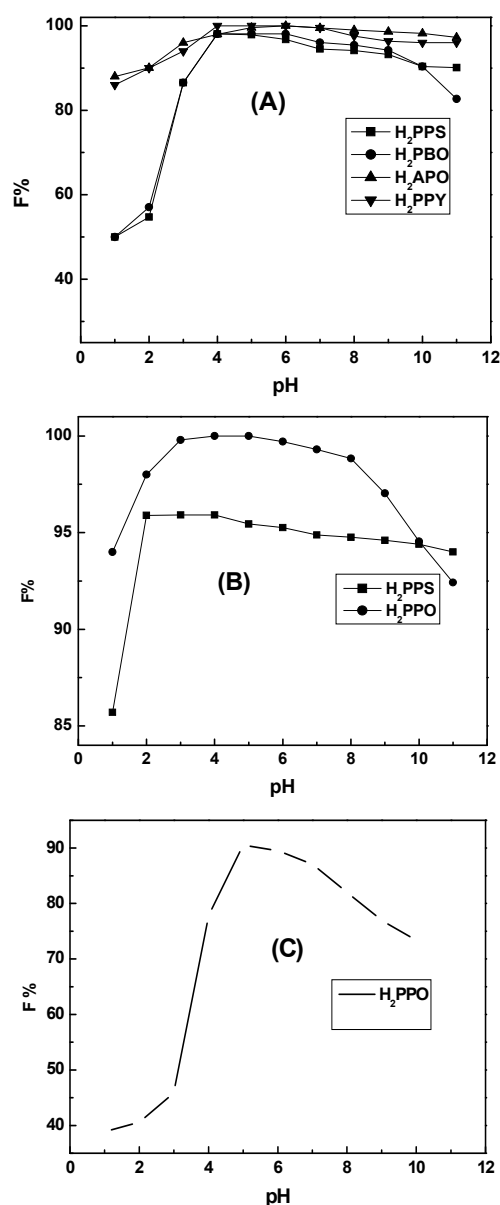


Figure 1. Effect of pH on the floatability of 2×10⁻⁴ mol L⁻¹ (A) Hg²⁺ ions; (B) Mn²⁺ ions and (C) Cd²⁺ ions using 4×10⁻⁴ mol L⁻¹ of each thiosemicarbazide derivative and 1×10⁻³ mol L⁻¹ HOL.

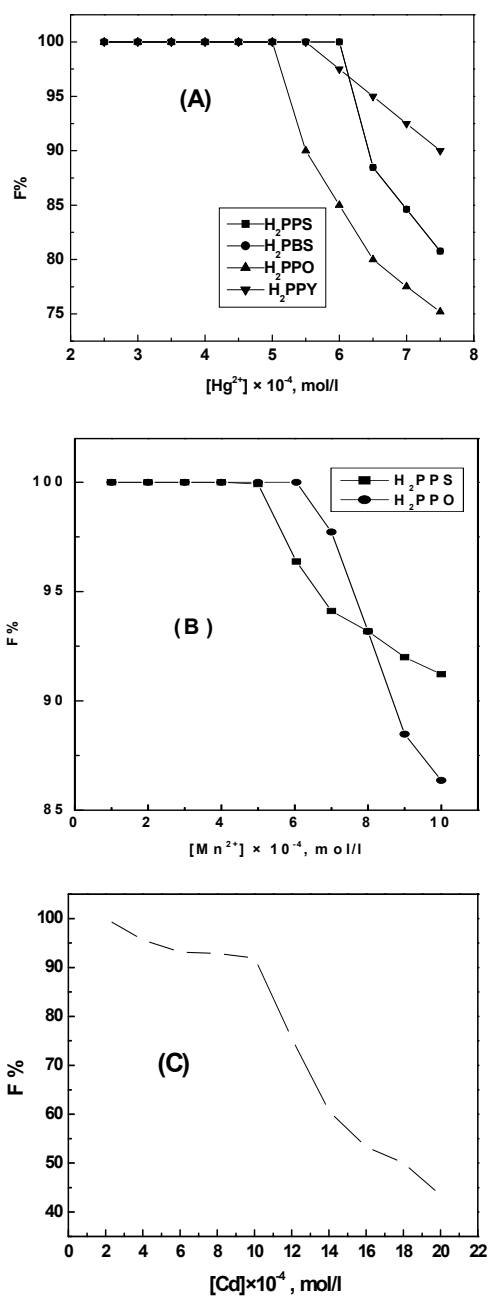


Figure 2. Floatability of different concentrations of (A) Hg²⁺ ions; (B) Mn²⁺ ions and (C) Cd²⁺ ions using 4×10⁻⁴ mol L⁻¹ of each thiosemicarbazide derivative and 1×10⁻³ mol L⁻¹ HOL at pH ~5.

At higher surfactant concentration the incomplete flotation of Hg²⁺, Mn²⁺ and Cd²⁺ ions may be due to the fact that the surfactant changes the state of the particles, M-thiosemicarbazide precipitates, from coagulation precipitation through coagulation flotation to re-dispersion with an increase in the amount of HOL added [48]. Moreover, the poor flotation at high surfactant concentration is caused by the formation on the air bubble surface of a stable, hydrated envelope of surfactant or, by forming a hydrate micelle coating on the solid surface [49]. As a result, the hydrophobicity of this surface was not satisfactory for flotation. Therefore, a concentration of 1×10⁻³ mol L⁻¹ of HOL was fixed throughout.

3.4. Effect of temperature

Under the recommended conditions, a series of experiments was conducted to float Hg²⁺, Mn²⁺ and Cd²⁺ ions at a wide range of temperatures. In order to do this, a solution of Hg²⁺, Mn²⁺ or Cd²⁺ ions, the thiosemicarbazide derivative and another containing HOL was either heated or cooled to the same temperature in a water bath. The HOL solution was quickly poured into Hg²⁺, Mn²⁺ or Cd²⁺ solution. The mixture was introduced into the flotation cell jacketed with 1 cm thick fiberglass insulation. The flotation procedure was then followed. The obtained results (Table 4) clarified that only H₂PPS, H₂PBO and H₂APO showed maximum flotation (~100%) of Hg²⁺ ions in the range of 5- 85°C, while H₂PPY gave its maximum flotation in the temperature range of 25-65°C. Moreover, the maximum separation (~100%) of Mn²⁺ and Cd²⁺ ions were achieved at 5°C to 65°C using H₂PPS and H₂APO for Mn²⁺ and H₂APO for Cd²⁺ ion. Therefore, 25°C is common between the four ligands and was used throughout.

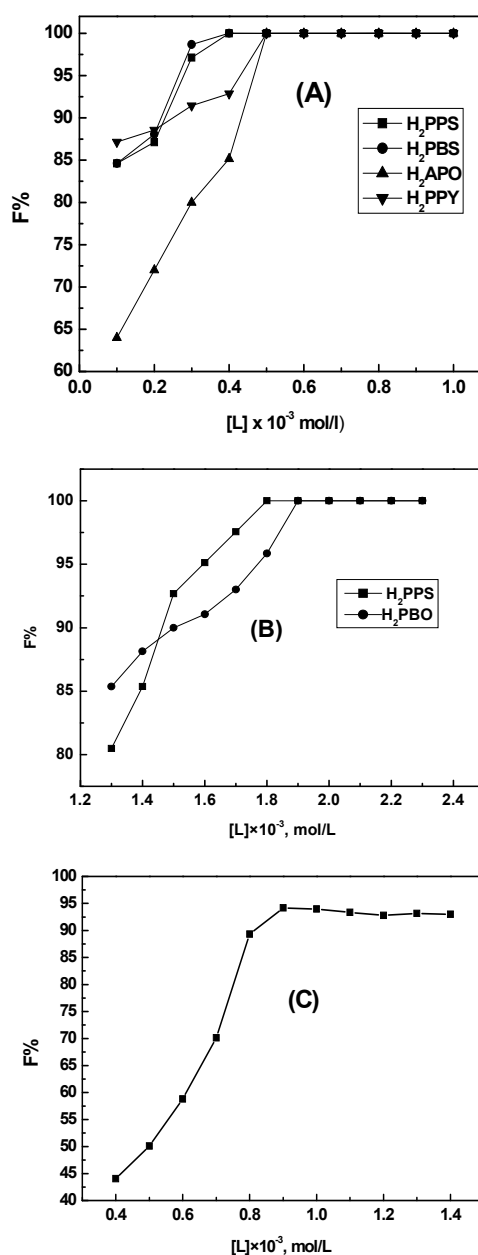


Figure 3. Floatability of 2×10⁻⁴ mol L⁻¹ (A) Hg²⁺ ions; (B) Mn²⁺ ions and (C) Cd²⁺ ions using different concentrations of each thiosemicarbazide derivative and 1×10⁻³ mol L⁻¹ HOL at pH ~5.

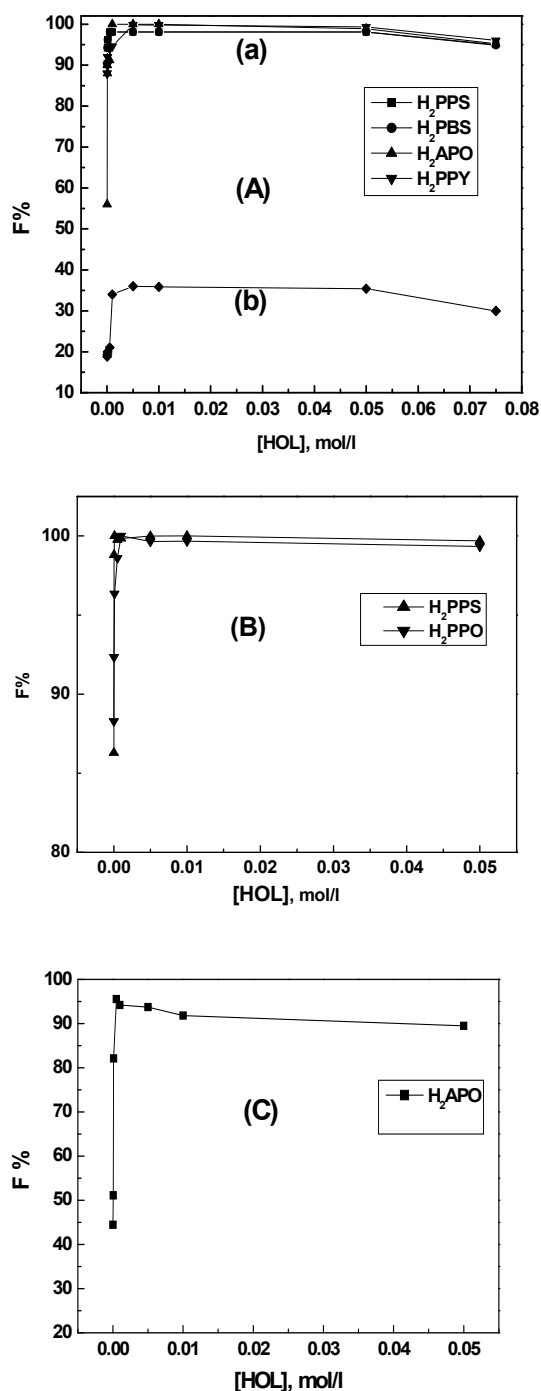


Figure 4. Floatability of 2×10^{-4} mol L⁻¹ (A) Hg²⁺ ions in the absence (b) and presence (a) of HOL; (B) Mn²⁺ ions and (C) Cd²⁺ ions using different concentrations of HOL and 2×10^{-4} mol L⁻¹ of each thiosemicarbazide derivative at pH ~5.

The decrease in separation upon raising the temperature may be due to the increase in the solubility of the precipitate and the instability of the foam giving rise to partial dissolution of the precipitate and insufficient foam consistency to hold up the precipitate [27]. Since this parameter has an important and variable influence on the flotation process, it is very interesting to study each particular case, especially for large temperature variations [50].

3.5. Effect of foreign ions

In order to assess the applicability of the proposed method to recover Hg²⁺, Mn²⁺ and Cd²⁺ ions added to water samples, the

effect of some foreign ions on the floatability of the investigated metal ions was carried out. These foreign ions were selected on the basis that they are normally present in fresh and saline waters. Solutions containing various amounts of foreign ions, Hg²⁺, Mn²⁺ and Cd²⁺ ions and each of the ligands were subjected to the described flotation procedure. The tolerable amounts of each ion, giving a maximum error of ± 2 % in the floatability, are summarized in Table 5. As can be seen, all of the investigated foreign ions with relatively high concentrations (in comparison with that of Hg²⁺, Mn²⁺ and Cd²⁺ ions) have no adverse effect on the flotation of the investigated metal ions. Therefore, the recommended procedure may find its applications on water samples.

3.6. Flotation of metal ions from different volumes

Under the recommended conditions of the proposed procedure, the floatabilities of 2×10^{-4} mol L⁻¹ of Hg²⁺, Mn²⁺ and Cd²⁺ ions from different volumes of aqueous solutions (10 to 2000 mL) in the presence of 4×10^{-4} mol L⁻¹ of each thiosemicarbazide derivative and 1×10^{-3} mol L⁻¹ HOL at pH ~5 were carried out. The obtained results showed that about 100% of the analytes were floated from the volumes of 10 to 1500 mL above which the floatability slightly decreased.


3.7. Application

In order to evaluate the capability of the flotation method for the flotation of Hg²⁺, Mn²⁺ and Cd²⁺ ions from water, various types of water samples were selected (i.e. soft, fresh and hard water). The selection of these samples was done in a way to provide a wide variety of sample matrices, characterized by different types of interferences. Solutions of pre-filtered water samples (10 mL, each) containing Hg²⁺, Mn²⁺ and Cd²⁺ ions with a concentration of 5 or 10 mg L⁻¹ were floated under the recommended conditions. The data obtained are given in Table 6. It is clear that satisfactory flotation results of Hg²⁺, Mn²⁺ and Cd²⁺ ions were obtained.

4. Flotation mechanism

The mechanism of the flotation of metal-thiosemicarbazide precipitates is suggested depending on the following:

Hg²⁺, Mn²⁺ and Cd²⁺ ions react with the investigated thiosemicarbazide derivatives in a M:L ratio of 1:1 and 1:2 to give the complexes MHL⁺ and M(HL)₂ according to the following equations:



These equations were confirmed by elemental analyses of C, H, N, O and S. These complexes have many sites containing electronegative atoms, such as oxygen, sulfur and nitrogen in the form of C = O, C = S, NH and C = N, functional groups as shown in Table 3, capable of forming hydrogen bonds.

The nature of the chemical species of oleic acid in the solution is determined by pH as the degree of dissociation is governed by pH [51]. Oleic acid begins to dissociate at pH > 5.2 [48] and the percentage of different forms of oleic acid are determined by IR analysis and the data are reported [52]. As a representative example the percentage of different forms of oleic acid determined by IR analysis at pH 9 (adjusted by NaOH) are: 13.2% oleic acid, 68.2% oleate and 18.2% sodium oleate [52]. The IR spectra of oleic acid with changing pH indicated that at 1300 – 1800 cm⁻¹, there are bands characteristic of the groups CO₂H, CO₂⁻ and CO₂⁻ contained with Na [52]. These data agree with those reported [49] that the C = O stretching band of oleic acid at 1705 cm⁻¹ is shifted on ionization to bands in the range of

Table 4. Floatability of 2×10^{-4} mol L⁻¹ of Hg²⁺, Mn²⁺ and Cd²⁺ ions at different temperatures using 4×10^{-4} mol L⁻¹ of each thiosemicarbazide derivative and 1×10^{-3} mol L⁻¹ HOL at pH ~5.

Temperature, °C	Hg ²⁺ Floatability, (%)				Mn ²⁺ Floatability, (%)		Cd ²⁺ Floatability, (%)
	H ₂ PPS	H ₂ PBO	H ₂ APO	H ₂ PPY	H ₂ PPS	H ₂ APO	H ₂ APO
5	99.0	99.0	99.1	80.0	99.0	99.1	99.1
10	99.2	99.6	99.2	83.7	99.2	99.2	99.2
25	100.0	100.0	100.0	100.0	100.0	100.0	100.0
35	100.0	100.0	99.3	100.00	100.0	99.3	99.3
45	99.9	99.9	99.9	99.9	99.9	99.9	99.9
55	99.8	99.7	99.8	99.6	99.8	99.8	99.8
65	99.9	99.8	99.5	97.9	99.9	99.5	99.5
75	99.7	99.7	99.7	53.9	99.7	99.7	99.7
85	99.9	99.5	99.5	80.3	99.9	99.5	99.5

Table 5. Floatability of 2×10^{-4} mol L⁻¹ of Hg²⁺, Mn²⁺ and Cd²⁺ ions in the presence of some selected foreign ions using 4×10^{-4} mol L⁻¹ of each thiosemicarbazide derivative and 1×10^{-3} mol L⁻¹ HOL at pH ~5.




Foreign ion ^a	[Foreign ion] mg L ⁻¹ ; Hg ²⁺ Floatability, (%)				[Foreign ion] mg L ⁻¹ ; Mn ²⁺ Floatability, (%)		[Foreign ion] mg L ⁻¹ ; Cd ²⁺ Floatability, (%)
	H ₂ PPS	H ₂ PBO	H ₂ APO	H ₂ PPY	H ₂ PPS	H ₂ APO	H ₂ APO
Na ⁺	[20]; 100	[5]; 99.9	[5]; 99.5	[70]; 100.0	[5]; 99.0	[5]; 99.1	[5]; 99.1
K ⁺	[50]; 99.9	[15]; 99.9	[5]; 99.3	[50]; 99.9	[5]; 99.2	[5]; 99.2	[5]; 99.2
Mg ²⁺	[50]; 99.9	[20]; 100.0	[5]; 99.1	[5]; 98.9	[5]; 100.0	[5]; 100.0	[5]; 100.0
Ca ²⁺	[20]; 99.8	[15]; 100.0	[10]; 98.7	[20]; 99.0	[10]; 100.0	[5]; 99.3	[20]; 99.3
Cl ⁻	[15]; 99.7	[8]; 98.8	[8]; 98.8	[108]; 100.0	[16]; 99.9	[8]; 99.9	[8]; 99.9
SO ₄ ²⁻	[10]; 99.5	[10]; 99.0	[5]; 98.9	[50]; 100.0	[10]; 99.8	[5]; 99.8	[5]; 99.8
HCO ₃ ⁻	[30]; 99.5	[20]; 99.5	[20]; 99.2	[10]; 98.6	[20]; 99.9	[10]; 99.5	[20]; 99.5
CH ₃ COO ⁻	[50]; 99.7	[30]; 99.9	[5]; 98.5	[5]; 98.0	[50]; 99.7	[10]; 99.7	[20]; 99.7

^a The cations are added in the form of their chloride while the anions are added as their sodium salts.

Table 6. Floatability of Hg²⁺, Mn²⁺ and Cd²⁺ ions added to some selected water samples using 4×10^{-4} mol L⁻¹ of each thiosemicarbazide derivative and 1×10^{-3} mol L⁻¹ HOL at pH ~5.

Water sample, (Location)	[M ²⁺], (mg L ⁻¹)	Hg ²⁺ Floatability, (%)				Mn ²⁺ Floatability, (%)		Cd ²⁺ Floatability, (%)
		H ₂ PPS	H ₂ PBO	H ₂ APO	H ₂ PPY	H ₂ PPS	H ₂ APO	H ₂ APO
Distilled water	5	100.0	98.5	98.6	97.3	99.0	99.1	99.1
	10	100.0	99.3	99.2	99.0	99.7	99.9	100.0
Drinking water (Mansoura City)	5	97.5	96.0	94.5	94.5	99.2	99.2	99.2
	10	99.0	98.8	97.0	98.0	99.8	99.8	99.7
Nile water (Mansoura City)	5	97.5	97.0	94.5	100.0	100.0	100.0	100.0
	10	99.3	99.0	97.1	100.0	100.0	99.9	100.0
Sea water (Gamasa)	5	93.8	92.5	91.5	85.8	100.0	99.3	99.3
	10	95.0	95.0	95.3	89.1	100.0	99.8	99.9
Sea water (Ras El-Barr)	5	87.5	98.5	81.5	93.0	99.9	99.9	99.9
	10	89.0	99.5	84.3	94.9	100.0	100.0	100.0
Lake water (Manzalah)	5	77.5	78.5	87.3	100.0	99.8	99.8	99.8
	10	88.9	83.7	89.9	100.0	100.0	100.0	99.9
Underground water (Cinbellaween City)	5	91.3	92.8	85.7	84.3	99.9	99.5	99.5
	10	93.0	94.8	88.0	87.0	100.0	99.8	99.9

1520-1540 cm⁻¹ for sodium oleate. Therefore, oleic acid can interact with other systems, through hydrogen bonding, either in its un-dissociated (R-COOH) or dissociated (R-COO⁻) forms depending on the pH of the medium and according to the following:



This view was checked by carrying out infrared analyses. The infrared spectra of the isolated complexes from the float layers (after good washing) have no absorption bands corresponding to oleic acid. This means that oleic acid may combine with metal-thiosemicarbazide chelates through weak bonds (hydrogen bonds) depending on the solution pH [53].

The combination of oleic acid surfactant with the metal thiosemicarbazides gives hydrophobic aggregates that float with the aid of air bubbles (created inside the flotation cell by slight shaking) to the surface of the solution [53].

5. Conclusions

This investigation presents thiosemicarbazide derivatives as organic chelates (which are not pollutant for water media and may have biological importance) for the separation of about 100% of Hg²⁺, Mn²⁺ and Cd²⁺ ions. This is accomplished by using the simple, rapid and inexpensive flotation technique. This

technique is expected to be soon incorporated as a clean technology to treat water and wastewater. The procedure is free from interferences, is not affected by raising the temperature up to 65°C (which enables its application to hot wastewater treatment without the need for cooling) making the process economical. It is also successfully applied to the recovery of Hg²⁺, Mn²⁺ and Cd²⁺ ions spiked into different environmental water samples. The flotation mechanism is based on the formation of hydrogen bonding between oleic acid surfactant and mercury-thiosemicarbazide complexes.

References

- [1]. Sittling, M. Hand Book of Toxic and Hazardous Chemicals, Noyes Publications, Park Ridge, NJ, 1981.
- [2]. Kadirvelu, K.; Thamaraislvi, K.; Namasivayam, C. *Sep. Purif. Technol.* **2001**, *24*, 497-505.
- [3]. Hasar, H. J. *Hazard. Mater.* **2003**, *97*, 49-57.
- [4]. Al-Asheh, S.; Duvnjak Z. *Sep. Sci. Technol.* **1997**, *33*, 1303-1329.
- [5]. Gksungure, Y.; Uren, S.; Güvenc, U. *Bioresource Technol.* **2005**, *96*, 103-109.
- [6]. Kim, J. S.; Akeprathumchia, S.; Wickrasinghe, S. J. *Member. Sci.* **2001**, *182*, 161-172.
- [7]. Blöcher, C.; Dorda, J.; Mavrov, V.; Chmiel, H.; Lazaridis, N. K.; Matis, K. A. *Water Res.* **2003**, *37*, 4018-4026.
- [8]. Ghazy, S. E. *Sep. Sci. Technol.* **1995**, *30*, 933-947.
- [9]. Sorensen, E. M. B. *Metal Poisoning in Fish*, CRC Press Inc, Boca Raton, Florida, 1991.
- [10]. Ghazy, S. E.; Mostafa G.A. E. *Canadian J. Anal. Sci. Spect.* **2008**, *53*, 28-35.
- [11]. Chubar, N.; Carvalho, J. R.; Correia, M. J. N. *Colloids and Surfaces A*, **2003**, *230*, 57-65.
- [12]. Aschner, M.; Erikson, K. M.; Dorman, D. C. J. *Crit. Rev. Toxicol.* **2005**, *35*, 1-32.

- [13]. Quintanar, L. *Inorg. Chim. Acta* **2008**, *361*, 875-884.
- [14]. Mizuike, A. *Fresenius' J. Anal. Chem.* **1986**, *324*, 672-677.
- [15]. Leyden, D. E.; Wegscheider, W. *Anal. Chem.* **1981**, *53*, 1059A-1065A.
- [16]. Zouboulis, A. I.; Lazaridis, N. K.; Zamboulis, D. *Sep. Sci. Technol.* **1994**, *29*, 385-400.
- [17]. Stoica, L.; Dinculescu, M.; Plapcianu, C.G. *Water Res.* **1998**, *32*, 3021-3030.
- [18]. Rubio, J.; Souza, M. L.; Smith, R. W. *Minerals Eng.*, **2002**, *15*, 139-155.
- [19]. Doyle, F. M. *Int. J. Miner. Process.* **2003**, *72*, 387-399.
- [20]. Doyle, F. M.; Liu, Z. J. *Colloid Interface Sci.* **2003**, *258*, 396-403.
- [21]. Cora, M. G.; Hung, Y-T. *Int. J. Environ. Eng.* **2009**, *1*, 3-19.
- [22]. Kidkoro, T.; Matusi, K.; Ishiwata, S.; Sasaki, T. *Bull. Chem. Soc. Jpn.* **1988**, *61*, 1505-1508.
- [23]. Kabil, M. A. *Fresenius J. Anal. Chem.* **1994**, *348*, 246-247.
- [24]. Voyce, D.; Zeitlin, H. *Anal. Chim. Acta* **1974**, *69*, 27-34.
- [25]. Feng, X.; Ryan, D.E. *Intern. J. Environ. Anal. Chem.* **1985**, *19*, 273-280.
- [26]. Ghazy, S. E.; Rakha, T.H.; El-Kady, E. M.; El-Asmy, A. A. *Indian J. Chem. Technol.* **2000**, *7*, 178-182.
- [27]. Clarke, A. N.; Wilson, D. J. *Sep. Purif. Reviews* **1978**, *7*, 55 - 98.
- [28]. Mathew, L.; Reddy, M. L.; Prasada Rao, T.; Iyer, C.S.P.; Damodaran, A.D. *Microchimica Acta* **1997**, *127*, 125-128.
- [29]. Ghazy, S. E. *Sep. Sci. Technol.* **1994**, *29*, 935-941.
- [30]. Ghazy, S. E.; Kabil, M. A.; Shallaby, A. M.; Ammar, N. S. *Indian J. Chem. Technol.* **2001**, *8*, 211-218.
- [31]. Akl, M. A.; Khalifa, M. E.; Ghazy, S. E.; Hassanien, M. M. *Anal. Sci.* **2002**, *18*, 1235-1240.
- [32]. Pavlovska, G.; Čundiva, K.; Stafilov, T.; Zendelovska, D. *Sep. Sci. Technol.* **2003**, *38*, 1111-1124.
- [33]. Ulewicz, M.; Walkowiak, W.; Krystyna Brandt, K.; Porwolik-Czomperlik, I. *Sep. Sci. Technol.* **2003**, *38*, 633-645.
- [34]. Jurkiewicz, K. *Colloids and Surfaces A* **2006**, *276*, 207-212.
- [35]. Scorzelli, I. B.; Fragomeni, A. L.; Torem, M.L. *Minerals Eng.* **1999**, *12*, 905-917.
- [36]. Matis, K. A.; Zouboulis, A. I. *Biotechnol. Bioeng.* **2004**, *44*, 354-360.
- [37]. Ulewicz, M.; Walkowiak, W.; Bartsch, R. A. *Sep. Purif. Technol.* **2006**, *48*, 264-269.
- [38]. Hiraide, M.; Ito, T.; Baba, M.; Kawaguchi, H.; Mizuike, A. *Anal. Chem.* **1980**, *52*, 804-807.
- [39]. Mumallah, N. A.; Wilson, D. J. *Sep. Sci. Technol.* **1981**, *16*, 213-228.
- [40]. Zendelovska, D.; Čundeva, K.; Stafilov, T. *Microchimica Acta* **2000**, *135*, 1436-5073.
- [41]. Tuzen, M.; Soylak, M. J. *Hazardous Materials* **2009**, *162*, 724-729.
- [42]. Gregory, O. J.; Barnett, S. M.; Deluise, F. J. *Sep. Sci. Technol.* **1980**, *15*, 1499-1512.
- [43]. Moruzzi, R.; Reali, M. A. P.; Patrizzi, L. J. A Different View of Removing Iron and Manganese Complexes Using Dissolved Air Flotation, In Young Researchers, 2004, Edited by Lens. P.; Stuetz, R. IWA Publishing, London, UK, pp. 259-266.
- [44]. Ghazy, S. E.; Kabil, M. A. *Bull. Chem. Soc. Jpn.* **1994**, *67*, 474-478.
- [45]. Marczenko, Z. Separation and Spectrophotometric Determination of Elements, John Wiley & Sons, New York, Toronto 1986.
- [46]. Mohsen, A.; Omar, M. E.; Labouta, I. M.; Kasem, M. G.; Boudais, J. J. *Pharm. Sci.* **1983**, *72*, 1226-1228.
- [47]. West, D. X.; Swearingen, J. K.; El-Swaf, A. K. *Trans. Met. Chem.* **2004**, *29*, 80-83.
- [48]. Ghazy, S. E.; Samra, S. E.; Mahdy, A. M.; El-Morsy, S. M. *Anal. Sci.* **2006**, *22*, 377-382.
- [49]. Klassen, V. I.; Mokrousov, V. A. An Introduction to the Theory of Flotation, Butterworths, London, 1963.
- [50]. Caballero, M.; Cela, R.; Perez-Bustamante, J. A. *Talanta* **1990**, *37*, 275-300.
- [51]. Ramachandra, R. S. Surface Chemistry of Froth Flotation, Vol. 2 Reagents and Mechanisms, 2nd ed., Kluwer Academic/Plenum Publishers, New York, 1982.
- [52]. Pol'kin, S. I.; Berger, G. S.; Revazashavili, I. B.; Shchepkina, M. M. *Izv. Vyssh. Ucheb. Zaved., Tsvet. Met.*, **1968**, *11*, 6-11.
- [53]. Ghazy, S. E.; Mostafa, H. A.; El-Farra, S. A.; Fouda, A. S. *Indian J. Chem. Technol.* **2004**, *11*, 787-792.