



Cruz-González, O.L., Rodríguez-Ramos, R., Otero, J.A., Ramirez Torres, A. , Penta, R. and Lebon, F. (2020) On the effective behavior of viscoelastic composites in three dimensions. *International Journal of Engineering Science*, 157, 103377. (doi: [10.1016/j.ijengsci.2020.103377](https://doi.org/10.1016/j.ijengsci.2020.103377))

The material cannot be used for any other purpose without further permission of the publisher and is for private use only.

There may be differences between this version and the published version. You are advised to consult the publisher's version if you wish to cite from it.

<http://eprints.gla.ac.uk/225777/>

Deposited on 29 October 2020

Enlighten – Research publications by members of the University of  
Glasgow

<http://eprints.gla.ac.uk>

## On the effective behavior of viscoelastic composites in three dimensions

O.L. Cruz-González<sup>a</sup>, R. Rodríguez-Ramos<sup>b,\*</sup>, J. A. Otero<sup>c</sup>,  
A. Ramírez-Torres<sup>d</sup>, R. Penta<sup>e</sup>, F. Lebon<sup>a</sup>

<sup>a</sup>*Aix Marseille Univ, CNRS, Centrale Marseille, LMA UMR 7031, Marseille, France.*

<sup>b</sup>*Facultad de Matemática y Computación, Universidad de La Habana, San Lázaro y L, Vedado, La Habana. CP 10400. Cuba.*

*Present address: Escuela de Ingeniería y Ciencias, Tecnológico de Monterrey, Campus Puebla Atlixcáyotl 5718, Reserva Territorial Atlixcáyotl, 72453 Puebla, Mexico.*

<sup>c</sup>*Escuela de Ingeniería y Ciencias, Tecnológico de Monterrey, Campus Estado de México, EM CP 52926 Atizapán de Zaragoza, Mexico.*

<sup>d</sup>*Dipartimento di Scienze Matematiche "G. L. Lagrange", Politecnico di Torino, 10129 Turin, Italy.*

<sup>e</sup>*School of Mathematics and Statistics, Mathematics and Statistics Building, University of Glasgow, University Place, Glasgow G12 8QQ, UK.*

---

### Abstract

We address the calculation of the effective properties of non-aging linear viscoelastic composite materials. This is done by solving the microscale periodic local problems obtained via the Asymptotic Homogenization Method (AHM) by means of finite element three-dimensional simulations. The work comprises the investigation of the effective creep and relaxation behavior for a variety of fiber and inclusion reinforced structures (e.g. polymeric matrix composites). As starting point, we **consider** the elastic-viscoelastic correspondence principle and the Laplace-Carson transform. Then, a classical asymptotic homogenization approach for composites with discontinuous material properties and perfect contact at the interface between the constituents is performed. **In particular, we** reach to the stress jump conditions

---

\*Corresponding author

*Email address:* [reinaldo@matcom.uh.cu](mailto:reinaldo@matcom.uh.cu) (R. Rodríguez-Ramos)

## On the effective behavior of viscoelastic composites in three dimensions

---

### Abstract

We address the calculation of the effective properties of non-aging linear viscoelastic composite materials. This is done by solving the microscale periodic local problems obtained via the Asymptotic Homogenization Method (AHM) by means of finite element three-dimensional simulations. The work comprises the investigation of the effective creep and relaxation behavior for a variety of fiber and inclusion reinforced structures (e.g. polymeric matrix composites). As starting point, we consider the elastic-viscoelastic correspondence principle and the Laplace-Carson transform. Then, a classical asymptotic homogenization approach for composites with discontinuous material properties and perfect contact at the interface between the constituents is performed. In particular, we reach to the stress jump conditions from local problems and obtain the corresponding interface loads. Furthermore, we solve numerically the local problems in the Laplace-Carson domain, and compute the effective coefficients. Moreover, the inversion to the original temporal space is also carried out. Finally, we compare our results with those obtained from different homogenization approaches, such as the Finite-Volume Direct Averaging Micromechanics (FVDAM) and the Locally Exact Homogenization Theory (LEHT).

*Keywords:* Viscoelasticity, composite materials, fibrous and inclusion reinforcement, asymptotic homogenization method, computational study

---

## 1. Introduction

The study of creep and relaxation in viscoelastic heterogeneous materials, in which the phases generally involve both instant elastic and time-dependent viscous behavior, has gone some way towards enhancing our understanding of these kinds of composites. Several examples of man-made materials consist of viscoelastic constituents and are designed with practical purposes (see [1, 2]). Others are found in nature such as biological tissues (see [3, 4, 5, 6]). From the point of view of modeling and manufacturing, the high cost associated to experimental evaluations of the effective viscoelastic properties of composites motivates the development of predictive modeling techniques.

Recently, several studies have addressed the problem of modeling viscoelastic composites. For instance, in [7], the calculation of the effective viscoelastic properties of a short fiber reinforced composite is studied, wherein the orientation distribution of the fibers varies from perfectly aligned to randomly oriented ones. Moreover, in [8], the overall properties of viscoelastic porous materials obtained by infilling of pores with either a viscoelastic solid or fluid are investigated. In [9], the Authors studied materials containing multiple inhomogeneities of oblate shape. In particular, they use this framework to model the viscoelastic properties of blood. In these three works, the viscoelastic properties are expressed in terms of the fraction-exponential operators of Scott Blair–Rabotnov [10]. On the other hand, in [11], a nonlocal higher-order refined magneto-electro-viscoelastic beam model for vibration analysis of smart nanostructures is considered. Moreover, a RVE-based Finite Element algorithm for evaluating the effective viscoelastic creep behaviors of aligned short fiber composites is developed in [12]. Furthermore,

in [13], the higher-order zigzag theory is used to analyze the hygrothermo-mechanical behavior of viscoelastic composite laminated plates. In addition, a thermodynamic framework for viscoelastic polymers undergoing microstructural changes is studied in [14], and an approach for predicting the five independent viscoelastic constants of a unidirectional carbon fibre epoxy resin composite is experimentally validated in [15]. Besides, in [16], the two-scale asymptotic homogenization method is extended to the viscoelastic case and analytical closed form expressions, in Laplace-Carson space, for the effective coefficients of fibrous viscoelastic composites with square and hexagonal cells are reported. In [17], the effects of viscoelasticity as well as geometrical imperfections on the mechanics of carbon nanotubes with large deformations are analysed via a modified nonlocal elasticity model. Finally, in [18] and [19], the Authors use an artificial neural network to model the viscoelastic properties of a thermoset vinyl ester nanocomposite and predict the load-displacement curve in a long bone, respectively.

The AHM has proved to be advantageous in the description of the coarse scale mechanics of composite materials. Many studies have dealt with the theoretical bases of the method, see e.g., [20, 21, 22, 23, 24]. In general, the AHM permits to obtain an effective characterization of the heterogeneous system or phenomenon under study by encoding the information available at the microscale into the so-called effective coefficients. This, in turn, reduces dramatically the computational complexity of the resulting boundary problems. However, the main disadvantage of AHM is that the analytical solution of the local problems has been derived for only a few composite structures (see [25, 26, 27]). For instance, in [28] and [29], the Authors report a set of formulae for laminated and fiber reinforced viscoelastic composites, respectively. Therefore, in order to handle complex microstructures, numer-

ical approaches based on the finite element method (FEM) offer a potential alternative to solve the local problems.

The aim of this work is to apply a semi-analytical technique that combines the theoretical strengths of the AHM with numerical computations based on FEM. The novelty of this study lies in the computations of the effective properties of non-aging linear viscoelastic composites in three dimensions. This is done via suitable generalization of the theoretical and computational platform presented in [30, 31] for linear elastic composites. To the best of our knowledge, there are no studies addressing numerical computations of the properties of viscoelastic composites by varying the microstructure within the periodic cell.

In addition, the manuscript presents some differences with respect to previous works of some of the authors ([16, 29, 30]) and with others in the literature ([32, 33, 34, 35]). Specifically, the numerical solution of the local problem is tackled by means of the finite element software COMSOL Multiphysics<sup>®</sup> and LiveLink<sup>™</sup> for Matlab<sup>®</sup> scripting, and the solution's convergence is analyzed through three types of mesh discretization. We compute the effective coefficients for several types of fiber and inclusion reinforced structures with isotropic components and perfect contact at the interfaces. In particular, Maxwell's model, four parameter model, as well as Prony's series are employed to describe the viscoelastic effects in the sub-phases and the results are tabulated in Sub-section 4.5.

The manuscript is organized as follows. In Section 2, we give a brief overview of the linear viscoelastic heterogeneous problem. In Section 3, we describe the mathematical and computational methodology. In Section 4, we compare our numerical results with different methods existing in the literature. By doing this, we offer an alternative way to compute the effective

coefficients of non-aging linear viscoelastic composites.

## 2. Linear viscoelastic heterogeneous problem

Let us denote by  $\Omega \in \mathbb{R}^3$  a linear, viscoelastic composite material with well-separated length scales  $\ell$  and  $L$ . Particularly,  $\ell$  refers to the characteristic length scale of the microstructure, while  $L$  is the characteristic length of the composite medium (see Fig.1). Then, we introduce the dimensionless, scaling parameter

$$\varepsilon := \frac{\ell}{L} \ll 1. \quad (1)$$

Moreover, by denoting with  $x$  the macroscopic, or slow, variable, and using Eq. (1), we define the microscopic, or fast, variable  $y$  as

$$y := \frac{x}{\varepsilon}. \quad (2)$$

The heterogeneous material  $\Omega$  is assumed to be a two-phase composite where  $\bar{\Omega} = \bar{\Omega}_1^\varepsilon \cup \bar{\Omega}_2^\varepsilon$  and  $\bar{\Omega}_1^\varepsilon \cap \bar{\Omega}_2^\varepsilon = \Omega_1^\varepsilon \cap \bar{\Omega}_2^\varepsilon = \emptyset$ . In particular, we consider  $\Omega_2^\varepsilon = \cup_{i=1}^N \Omega_{2,i}^\varepsilon$ , where  $N$  represents the number of inclusions, and the interface between  $\Omega_1^\varepsilon$  and  $\Omega_2^\varepsilon$  is denoted by  $\Gamma^\varepsilon$  (see Fig.1 (b)). Furthermore,  $Y$  stands for the unitary periodic cell and its constituents,  $Y_1$  and  $Y_2$ , satisfy the constraint  $\bar{Y} = \bar{Y}_1 \cup \bar{Y}_2$  and  $\bar{Y}_1 \cap Y_2 = Y_1 \cap \bar{Y}_2 = \emptyset$ . Finally,  $\Gamma_Y$  represents the interface between  $Y_1$  and  $Y_2$  (see Fig.1 (c)).

We remark that in the remainder of this work, the notation  $\phi^\varepsilon(x, t) = \phi(x, y, t)$  is considered, where  $\phi$  is assumed to be periodic in  $y$ .

### 2.1. Statement of the problem

Here, we consider that the constitutive response of the constituents of  $\Omega$  to be linear viscoelastic. Then, the balance of linear momentum, neglecting

inertial terms, reads

$$\nabla \cdot \boldsymbol{\sigma}^\varepsilon(x, t) = \mathbf{0} \quad \text{in } (\Omega \setminus \Gamma^\varepsilon) \times \mathbb{R}, \quad (3a)$$

$$\llbracket \mathbf{u}^\varepsilon(x, t) \rrbracket = \mathbf{0} \quad \text{on } \Gamma^\varepsilon \times \mathbb{R}, \quad (3b)$$

$$\llbracket \boldsymbol{\sigma}^\varepsilon(x, t) \cdot \mathbf{n}^{(y)} \rrbracket = \mathbf{0} \quad \text{on } \Gamma^\varepsilon \times \mathbb{R}. \quad (3c)$$

Boundary conditions on  $\partial\Omega \times \mathbb{R}$ ,

$$\mathbf{u}^\varepsilon(x, t) = \bar{\mathbf{u}}, \quad (3d)$$

$$\boldsymbol{\sigma}^\varepsilon(x, t) \cdot \mathbf{n} = \bar{\mathbf{S}}. \quad (3e)$$

Initial condition in  $\Omega \times \{0\}$ ,

$$\mathbf{u}^\varepsilon(x, t) = \mathbf{0}. \quad (3f)$$

In equations (3a)-(3f),  $\boldsymbol{\sigma}^\varepsilon$  represents the second-order stress tensor and it is given by the expression, [36]

$$\boldsymbol{\sigma}^\varepsilon(x, t) = \int_0^t \mathcal{R}^\varepsilon(x, t - \tau) : \frac{\partial \boldsymbol{\xi}(\mathbf{u}^\varepsilon(x, \tau))}{\partial \tau} d\tau, \quad (4)$$

where the term  $\mathbf{u}^\varepsilon$  stands for the displacement field and  $\mathcal{R}^\varepsilon$  refers to the relaxation modulus, which is assumed to be a smooth function of  $x$  in  $(\Omega \setminus \Gamma^\varepsilon) \times \mathbb{R}$ . In general, however, we consider discontinuous material properties on  $\Gamma^\varepsilon \times \mathbb{R}$ . Moreover, the symmetry properties  $\mathcal{R}_{ijkl}^\varepsilon = \mathcal{R}_{jikl}^\varepsilon = \mathcal{R}_{ijlk}^\varepsilon = \mathcal{R}_{klij}^\varepsilon$  hold true. Furthermore,  $\boldsymbol{\xi}$  represents the second-order strain tensor and is defined by the formula

$$\boldsymbol{\xi}(\mathbf{u}^\varepsilon(x, t)) := \frac{1}{2} (\nabla \mathbf{u}^\varepsilon(x, t) + (\nabla \mathbf{u}^\varepsilon(x, t))^T). \quad (5)$$

We notice that in equations (3b)-(3c), we impose continuity conditions for displacements and tractions on  $\Gamma^\varepsilon$ , in which the term  $\mathbf{n}^{(y)}$  stands for the outward unit vector to the surface  $\Gamma^\varepsilon$  and the operator  $\llbracket \phi^\varepsilon \rrbracket$  denotes the “jump” of  $\phi^\varepsilon$  across the interface between the constituents.



Since the scale-dependent constitutive law (4) corresponds to a non-aging linear viscoelastic material, we can employ the elastic-viscoelastic correspondence principle (see [37, 38] for further details) and state the problem (3a)-(3f) in the Laplace-Carson space. Before doing this, we introduce the Laplace-Carson transform, for all real numbers  $t \geq 0$ , of  $\phi^\varepsilon$  namely, [36]

$$\hat{\phi}^\varepsilon(x, p) := p \int_0^\infty e^{-pt} \phi^\varepsilon(x, t) dt,$$

where the “hat” symbol denotes the Laplace-Carson transform of  $\phi^\varepsilon$  and  $p$  represents the variable in the Laplace-Carson space.

Then, taking into account the above considerations, we rewrite the system (3a)-(3f) in the Laplace-Carson space, as follows

$$\nabla \cdot \left[ \hat{\mathcal{R}}^\varepsilon(x, p) : \boldsymbol{\xi}(\hat{\mathbf{u}}^\varepsilon(x, p)) \right] = \mathbf{0} \quad \text{in } (\Omega \setminus \Gamma^\varepsilon) \times [0, +\infty), \quad (6a)$$

$$\llbracket \hat{\mathbf{u}}^\varepsilon(x, p) \rrbracket = \mathbf{0} \quad \text{on } \Gamma^\varepsilon \times [0, +\infty), \quad (6b)$$

$$\llbracket \hat{\mathcal{R}}^\varepsilon(x, p) : \boldsymbol{\xi}(\hat{\mathbf{u}}^\varepsilon(x, p)) \cdot \mathbf{n}^{(y)} \rrbracket = \mathbf{0} \quad \text{on } \Gamma^\varepsilon \times [0, +\infty). \quad (6c)$$

Boundary conditions on  $\partial\Omega \times [0, +\infty)$ ,

$$\hat{\mathbf{u}}^\varepsilon(x, p) = \bar{\mathbf{u}}, \quad (6d)$$

$$\hat{\mathcal{R}}^\varepsilon(x, p) : \boldsymbol{\xi}(\hat{\mathbf{u}}^\varepsilon(x, p)) \cdot \mathbf{n} = \bar{\mathbf{S}}. \quad (6e)$$

Initial condition in  $\Omega \times \{0\}$ ,

$$\hat{\mathbf{u}}^\varepsilon(x, p) = \mathbf{0}. \quad (6f)$$

### 3. Description of the semi-analytical technique

In this section, we describe the semi-analytical technique adopted in this work. Specifically, we highlight the main results of the AHM, and show the procedure for the computation of the effective properties of the composite.

It is worth to recall that, in this study, we adapt the methodology described in [30, 31] to our purposes, and extend the results to the case of non-aging, linear viscoelastic composite materials.

### 3.1. Two-scale asymptotic homogenization approach

We notice that, according to the chain rule and Equation (2), the following relation is obtained

$$\frac{\partial \hat{\phi}_i^\varepsilon(x, p)}{\partial x_j} = \frac{\partial \hat{\phi}_i(x, y, p)}{\partial x_j} + \frac{1}{\varepsilon} \frac{\partial \hat{\phi}_i(x, y, p)}{\partial y_j}. \quad (7)$$

Therefore, Equation (5) becomes,

$$\xi_{kl}(\hat{\phi}^\varepsilon(x, p)) = \xi_{kl}(\hat{\phi}(x, y, p)) + \frac{1}{\varepsilon} \xi_{kl}^{(y)}(\hat{\phi}(x, y, p)), \quad (8)$$

with

$$\xi_{kl}^{(y)}(\hat{\phi}(x, y, p)) = \frac{1}{2} \left( \frac{\partial \hat{\phi}_k(x, y, p)}{\partial y_l} + \frac{\partial \hat{\phi}_l(x, y, p)}{\partial y_k} \right). \quad (9)$$

Now, we propose the solution of the heterogeneous problem (6a)-(6f) as a formal multi-scale expansion of the displacement  $\hat{\mathbf{u}}^\varepsilon$  in powers of  $\varepsilon$ , [22, 39]

$$\hat{\mathbf{u}}^\varepsilon(x, p) = \sum_{i=0}^{+\infty} \varepsilon^i \hat{\mathbf{u}}^{(i)}(x, y, p). \quad (10)$$

After replacing (10) into (6a)-(6f) and using the relations (7) and (8), the procedure follows by grouping the resulting equations in powers of the smallness parameter  $\varepsilon$ . Specifically, by performing some algebraic manipulations, we reach the following sequence of problems, (we refer the reader to [16, 28] for further details)

**Problem for  $\varepsilon^{-2}$**

$$\frac{\partial}{\partial y_j} \left[ \hat{\mathcal{R}}_{ijkl}(y, p) \xi_{kl}^{(y)}(\hat{\mathbf{u}}^{(0)}(x, y, p)) \right] = 0 \quad \text{in } (Y \setminus \Gamma_Y) \times [0, +\infty), \quad (11a)$$

$$\left[ \hat{u}_i^{(0)}(x, y, p) \right] = 0 \quad \text{on } \Gamma_Y \times [0, +\infty), \quad (11b)$$

$$\left[ \hat{\mathcal{R}}_{ijkl}(y, p) \xi_{kl}^{(y)}(\hat{\mathbf{u}}^{(0)}(x, y, p)) n_j^{(y)} \right] = 0 \quad \text{on } \Gamma_Y \times [0, +\infty). \quad (11c)$$

Initial condition in  $Y \times \{0\}$ ,

$$\hat{u}_i^{(0)}(x, y, p) = 0. \quad (11d)$$

Since the right hand side of (11a) is zero, the problem can be solved using the solvability condition reported in [22, 40], wherein  $\hat{\mathbf{u}}^{(0)}$  is a solution of (11a)-(11c) if and only if it is constant in relation to the variable  $y$ , i.e.

$$\hat{\mathbf{u}}^{(0)}(x, y, p) = \hat{\mathbf{v}}(x, p), \quad (12)$$

where  $\hat{\mathbf{v}}$  is a smooth function.

**Problem for  $\varepsilon^{-1}$**

$$\begin{aligned} \frac{\partial}{\partial y_j} \left[ \hat{\mathcal{R}}_{ijkl}(y, p) (\xi_{kl}^{(y)}(\hat{\mathbf{u}}^{(1)}(x, y, p)) \right. \\ \left. + \xi_{kl}(\hat{\mathbf{u}}^{(0)}(x, y, p))) \right] = 0 \quad \text{in } (Y \setminus \Gamma_Y) \times [0, +\infty), \end{aligned} \quad (13a)$$

$$\left[ \hat{u}_i^{(1)}(x, y, p) \right] = 0 \quad \text{on } \Gamma_Y \times [0, +\infty), \quad (13b)$$

$$\begin{aligned} \left[ \hat{\mathcal{R}}_{ijkl}(y, p) (\xi_{kl}^{(y)}(\hat{\mathbf{u}}^{(1)}(x, y, p)) \right. \\ \left. + \xi_{kl}(\hat{\mathbf{u}}^{(0)}(x, y, p))) n_j^{(y)} \right] = 0 \quad \text{on } \Gamma_Y \times [0, +\infty). \end{aligned} \quad (13c)$$

Initial condition in  $Y \times \{0\}$ ,

$$\hat{u}_i^{(1)}(x, y, p) = 0. \quad (13d)$$

The solvability condition also applies in this case, ensuring the existence and uniqueness, up to a  $y$ -constant function, of the solution to the problem (13a)-(13d). An expression for the aforementioned solution can be derived by means of the method of separation of variables, namely [22, 40]

$$\hat{u}_m^{(1)}(x, y, p) = \hat{\chi}_{klm}(y, p) \xi_{kl}(\hat{\mathbf{v}}(x, p)), \quad (14)$$

where the third order tensor  $\hat{\chi}_{klm}$ , which is periodic in  $y$ , is the solution of the following problem referred to as the  $\varepsilon$ -local problem,

$$\frac{\partial}{\partial y_j} \left[ \hat{\mathcal{R}}_{ijpq}(y, p) \xi_{pq}^{(y)}(\hat{\mathbf{X}}_{kl}(y, p)) + \hat{\mathcal{R}}_{ijkl}(y, p) \right] = 0 \quad \text{in } (Y \setminus \Gamma_Y) \times [0, +\infty), \quad (15a)$$

$$\llbracket \hat{\chi}_{klm}(x, y, p) \rrbracket = 0 \quad \text{on } \Gamma_Y \times [0, +\infty), \quad (15b)$$

$$\llbracket (\hat{\mathcal{R}}_{ijpq}(y, p) \xi_{pq}^{(y)}(\hat{\mathbf{X}}_{kl}(y, p)) + \hat{\mathcal{R}}_{ijkl}(y, p) n_j^{(y)}) \rrbracket = 0 \quad \text{on } \Gamma_Y \times [0, +\infty). \quad (15c)$$

Initial condition in  $Y \times \{0\}$ ,

$$\hat{\chi}_{klm}(y, p) = 0. \quad (15d)$$

with,

$$\xi_{pq}^{(y)}(\hat{\mathbf{X}}_{kl}(y, p)) := \frac{1}{2} \left( \frac{\partial \hat{\chi}_{klp}(y, p)}{\partial y_q} + \frac{\partial \hat{\chi}_{klq}(y, p)}{\partial y_p} \right). \quad (16)$$

According to the problem (15a)-(15d), a further condition is required to obtain uniqueness of the solution, for instance, by requiring that  $\langle \hat{\chi}_{klm} \rangle_y = 0$  [30, 31] or alternately, by fixing the value of  $\hat{\chi}_{klm}$  at one point of the reference cell  $Y$ . Here, the notation  $\langle \phi \rangle_y$  stands for the cell average operator and is defined as,

$$\langle \phi \rangle_y := \frac{1}{|Y|} \int_Y \phi \, dy, \quad (17)$$

where  $|Y|$  represents the volume of the periodic cell  $Y$ .

**Problem for  $\varepsilon^0$**

Now, by considering relation (14), the homogenized problem can be written in the form

$$\hat{\mathcal{R}}_{ijkl}^{(*)}(p) \frac{\partial}{\partial x_j} \xi_{kl}(\hat{\mathbf{v}}(x, p)) = 0 \quad \text{in } \Omega^h \times [0, +\infty). \quad (18a)$$

Boundary conditions on  $\partial\Omega^h \times [0, +\infty)$ ,

$$\hat{v}_i(x, p) = \bar{u}_i, \quad (18b)$$

$$\hat{\mathcal{R}}_{ijkl}^{(*)}(p)\xi_{kl}(\hat{\mathbf{v}}(x, p))n_j = \bar{S}_i. \quad (18c)$$

Initial condition in  $\Omega^h \times \{0\}$ ,

$$\hat{v}_i(x, p) = 0. \quad (18d)$$

In equation (18a),  $\hat{\mathcal{R}}^{(*)}$  represents the effective relaxation modulus in the Laplace-Carson space and is defined through the expression

$$\hat{\mathcal{R}}_{ijkl}^{(*)}(p) := \left\langle \hat{\mathcal{R}}_{ijkl}(y, p) + \hat{\mathcal{R}}_{ijpq}(y, p)\xi_{pq}^{(y)}(\hat{\mathbf{x}}_{kl}(y, p)) \right\rangle_y. \quad (19)$$

### 3.2. Computational approach

In this section, we report some of the main aspects of the computational approach used in this work. In particular, for simplicity in our computations, we assume a  $y$ -constant expression for the relaxation modulus ( $\hat{\mathcal{R}}_{ijkl}$ ) in each phase of the periodic cell, i.e.

$$\hat{\mathcal{R}}_{ijpq}(y, p) = \begin{cases} \hat{\mathcal{R}}_{ijpq}^{(1)}(p), & \text{if } y \in Y_1, \\ \hat{\mathcal{R}}_{ijpq}^{(2)}(p), & \text{if } y \in Y_2, \end{cases} \quad (20)$$

where the superscripts (1) and (2) indicate the matrix and the inclusion phases, respectively (see Fig. 1). Therefore, the local problem (15a)-(15d) can be rewritten as,

$$\frac{\partial}{\partial y_j} \left[ \hat{\mathcal{R}}_{ijpq}^{(1)}(p)\xi_{pq}^{(y)}(\hat{\mathbf{x}}_{kl}^{(1)}(y, p)) \right] = 0 \quad \text{in } Y_1 \times [0, +\infty), \quad (21a)$$

$$\frac{\partial}{\partial y_j} \left[ \hat{\mathcal{R}}_{ijpq}^{(2)}(p)\xi_{pq}^{(y)}(\hat{\mathbf{x}}_{kl}^{(2)}(y, p)) \right] = 0 \quad \text{in } Y_2 \times [0, +\infty), \quad (21b)$$

$$\hat{\mathbf{x}}_{klm}^{(1)}(y, p) = \hat{\mathbf{x}}_{klm}^{(2)}(y, p) \quad \text{on } \Gamma_Y \times [0, +\infty), \quad (21c)$$

$$\left( \hat{\mathcal{R}}_{ijpq}^{(1)}(p)\xi_{pq}^{(y)}(\hat{\mathbf{x}}_{kl}^{(1)}(y, p)) \right) n_j^{(y)} - \left( \hat{\mathcal{R}}_{ijpq}^{(2)}(p)\xi_{pq}^{(y)}(\hat{\mathbf{x}}_{kl}^{(2)}(y, p)) \right) n_j^{(y)}$$

$$= \left( \hat{\mathcal{R}}_{ijkl}^{(2)}(p) - \hat{\mathcal{R}}_{ijkl}^{(1)}(p) \right) n_j^{(y)} \quad \text{on } \Gamma_Y \times [0, +\infty). \quad (21d)$$

Initial condition in  $Y \times \{0\}$ ,

$$\hat{\chi}_{klm}(y, p) = 0. \quad (21e)$$

We notice that, in equation (21d), the interface loads  $\mathbf{f}_{kl}^{(y)} := \left( \hat{\mathcal{R}}_{ijkl}^{(2)} - \hat{\mathcal{R}}_{ijkl}^{(1)} \right) n_j^{(y)}$  represent the driving forces leading to nontrivial solutions of the six elastic-type local problems  $((k, l), k \geq l)$  when discontinuities in the coefficients (20), between the matrix and inclusions, arise (see [30, 31]).

Now, in order to compute the numerical solution of the six elastic-type local problems (21a)-(21e) and the effective viscoelastic properties of the given composite material, we employ a combination of the finite element software COMSOL Multiphysics<sup>®</sup> with LiveLink<sup>™</sup> for Matlab<sup>®</sup> scripting. [The procedure can be summarized as follows:](#)

- (I) [To define](#) the geometry of the periodic cell  $Y$ , introduce the parameters, set the properties of the materials and implement the six elastic-type local problems (21a)-(21e) in COMSOL Multiphysics<sup>®</sup>. In this first step, the scheme proposed in [30] is adapted for our purposes.
- (II) [To integrate into a Matlab script](#) the codes for working with LiveLink<sup>™</sup> for Matlab<sup>®</sup>, the viscoelastic material properties and the algorithm for the numerical inversion of the Laplace-Carson transform.
- (III) [To solve, for every value of  \$p\$ , the](#) set of elastic local problems (21a)-(21e) in Laplace-Carson space and to calculate the effective relaxation modulus  $\hat{\mathcal{R}}^{(*)}$  using (19), updating in each iteration the corresponding parameters and the properties of the materials.
- (IV) [To invert](#) to the original time domain. The function INVLAP, developed in [41] is used for this purpose. The algorithm needs to calculate

40 points in Laplace-Carson’s space in order to find one point for the effective coefficient in the time domain.

For completeness of the analysis in the calculation of the effective creep compliance  $\mathcal{J}^{(*)}$ , the mathematical relationship between both magnitudes  $\mathcal{R}^{(*)}$  and  $\mathcal{J}^{(*)}$  is presented in Laplace-Carson space as follows,

$$\hat{\mathcal{R}}_{ijmn}^{(*)}(p)\hat{\mathcal{J}}_{mnkl}^{(*)}(p) = I_{ijkl}, \quad (22)$$

where  $I$  is the fourth order identity tensor [42]. We notice that expression (22) is used to compute  $\mathcal{J}^{(*)}$  once  $\hat{\mathcal{R}}^{(*)}$  is known.

#### 4. Numerical results and discussion

In this section, we compute the effective properties of a composite for several periodic cell configurations, report the results of our computations and compare them with other approaches found in the literature. By doing this, we validate the methodology described in Section 3 and highlight its major advantages. We notice that in the remainder of this manuscript the acronym PM stands for present model.

To start with, in Sub-section 4.1 we address the instant elastic response of a composite material reinforced with long circular fibers aligned along the axis  $Ox_3$  (see Fig. 9 (a)), and we study the solution’s convergence through three types of mesh discretization. Moreover, in Sub-section 4.2, we compute the effective relaxation modulus and the effective creep compliance for unidirectionally-reinforced glass/epoxy composites. Specifically, the four parameter model is employed to describe the viscoelastic polymeric matrix. In Sub-section 4.3, we compute the effective relaxation modulus for viscoelastic composites reinforced with spherical inclusions. In this case, the

matrix viscoelastic properties are expressed in terms of a Maxwell’s model. In Sub-section 4.4, we consider three different inclusion shapes for the calculation of the effective relaxation modulus. Here, the Prony’s series are used to describe both viscoelastic constituents. Finally, in Sub-section 4.5, we take into account all the inclusions shapes displayed in Fig. 9 for the computation of the effective relaxation modulus.

#### 4.1. Instant elastic response

We start our analysis by considering a composite with periodically distributed and non-overlapping long fibers with circular cross-sections and perfectly bonded to the matrix (see Fig. 9 (a)). Besides, we assume that the both constituents of the heterogeneous material are linear elastic and isotropic. We notice that, by referring to equation (4), the instant elastic response of the composite can be obtained by considering  $t = 0$ . In this limit case, the composite describe a linear elastic material, and  $\mathcal{R}_{ijkl}^{(*)}$  will represents the effective elastic tensor.

In the present context, we determine the instant elastic effective response in a wide range of volume fractions, and assume that  $\nu_1 = 0.39$ ,  $\nu_2 = 0.2$ . Particularly, we focus on the porous ( $\mu_2 = 0$ ) and moderate contrast ( $\mu_2/\mu_1 = 6$ ) cases. We notice that the notation  $\nu_1(\nu_2)$  stands for Poisson’s ratio and  $\mu_1(\mu_2)$  for the shear modulus of the matrix (fibers). The values of these parameters have been obtained from [43].

It is worth to remark that, here, we keep track of the solution’s convergence through three types of mesh discretization for the periodic cells (see Fig. 2). In particular, the mesh of the periodic cell  $Y$  is built such that, first, we create surface meshes of free triangular type for the interface  $\Gamma_Y$ , and then, the latter are extended into a three-dimensional mesh of free tetrahe-



dral type, which covers the whole periodic cell (see Fig. 2). The increasing mesh refinements are described in Table 1. We notice that the mesh on the interface between the matrix and the inclusion is more refined to better capture the boundary loads contribution. The mesh statistic outlines that, for instance, the number of tetrahedra subvolumes for a volume fractions of 0.3 are 1015 (Mesh A), 8460 (Mesh B) and 37 067 (Mesh C), respectively.

-	Element Size	
	Interface ( $\Gamma_Y$ )	Remaining ( $Y \setminus \Gamma_Y$ )
Mesh A	Coarser	Extremely Coarse
Mesh B	Fine	Coarse
Mesh C	Finer	Fine

Table 1: Mesh discretization of the unit cells.

The values of the normalized effective elastic coefficients, denoted by  $(\mathcal{R}_{11}^{(*)} - \mathcal{R}_{12}^{(*)})/2\mu_0$ ,  $\mathcal{R}_{55}^{(*)}/\mu_0$ ,  $\mathcal{R}_{13}^{(*)}/\mathcal{R}_{13}^{(1)}$  and  $\mathcal{R}_{33}^{(*)}/\mathcal{R}_{33}^{(1)}$ , as functions of the volume fraction ( $V_f$ ), are reported in Fig. 3 (a)-(d) for both porous and moderate contrast cases. [These figures display the results obtained by the present model \(PM\), for each of the meshes A, B and C, with respect to the volume fraction. Moreover, in Fig. 3 we compare with different sets of simple, closed-form and approximate formulae given by Kantor and Bergman \(K&B\), Luciano and Barbero \(L&B\), non-interacting Maxwell’s approximations \(\*non-int\*\) and exact periodic solutions \(RUC\) \[43\].](#)

[A closer look at the data in Fig. 3 \(a\)-\(d\) reveals that there is good agreement in the comparisons between PM and RUC and no significant differences are found in relation to K&B and L&B. The most notable discrepancy arises from the data corresponding to the \*non-int\* approach in Fig.](#)

3 (a), nonetheless the remaining coefficients are consistent within the comparisons. Additionally, we note the three types of mesh discretizations are barely distinguishable.

The relative errors with respect to  $RUC$ , for both porous and moderate contrast of the three mesh discretizations are shown in Fig. 3 (e)-(h). The results provide further evidence of the good correlation between  $PM$  and  $RUC$ . A remarkable pattern is that with the increased mesh refinement the relative error is improved, however, even with the coarser mesh (Mesh A) the maximum observed error is less than 3%, highlighting the good convergence of the present model.

Then, based on the good performance of the three mesh discretizations and the execution time, the remaining calculations are performed using Mesh B (see Fig. 2).

#### 4.2. Viscoelastic response: four-parameter model

Now, the potential of PM in the calculation of the effective relaxation modulus and the effective creep compliance for unidirectionally-reinforced glass/epoxy composites (see Fig. 9 (a)) is shown. Particularly, the linear isotropic constituents of the heterogeneous structure are elastic glass fibers embedded into a viscoelastic polymeric matrix. The latter is described using the four-parameter model or Burger's model (see [44]), where the expression of the creep compliance is given as follows,

$$J(t) = \frac{1}{E_0} + \frac{1}{E_1} \left( 1 - \exp\left(-\frac{E_1}{\eta_1} t\right) \right) + \frac{t}{\eta_2}. \quad (23)$$

The material constants for this model are  $E_0 = 3.27$  GPa,  $E_1 = 1.8$  GPa,  $\eta_1 = 300$  GPa · h and  $\eta_2 = 8000$  GPa · h, where  $E$  and  $\eta$  represent the elastic modulus of spring and the constitutive parameter of dashpot, respectively.

Furthermore, the matrix Poisson's ratio is assumed to be  $\nu_1 = 0.38$ , and the mechanical properties of the fibers are  $E_2 = 68.77$  GPa and  $\nu_2 = 0.21$ . The data has been taken from [45, 33].

In Fig. 4, we compare the results of PM with those obtained by the Locally exact homogenization theory (LEHT) reported in [46, 32], the finite-volume direct averaging micromechanics theory (FVDAM 2D) proposed in [45], and the three-dimensional FVDAM developed in [33]. These results correlate fairly well in the comparison against LEHT and FVDAM for three fiber volume fractions 20%, 30% and 40%. Additionally, Fig. 5 shows the relative errors of PM with respect to both FVDAM and LEHT. We can notice that the maximum error is less than 1%.

Finally, in Fig. 6 we report the values of the effective creep compliance  $\mathcal{J}^{(*)}$  and compare them with those resulting from FVDAM 2D. The data for FVDAM 2D were collected from Fig. 12 of [45] by using the free software G3Data.

#### 4.3. Viscoelastic response: Maxwell's model

We now consider a spherical reinforced composite with repeating unit cell of the type shown in Fig. 9 (h), and analyze the overall viscoelastic behavior under the assumption of isotropic phases. In particular, the spherical inclusions are assumed to be linear elastic with Young's modulus and Poisson's ratio being  $E_2 = 168.4$  GPa and  $\nu_2 = 0.443$ , respectively, whereas the matrix is described as a linear viscoelastic constituent and the Maxwell's model (see [38, 44]) is used to simulate its properties, namely

$$S(t) = \frac{1}{E_0} + \frac{t}{\eta_0}. \quad (24)$$

In the above equation,  $E_0 = 4.082$  GPa and  $\eta_0 = 159.81$  GPa · min. Moreover, the matrix Poisson's ratio is  $\nu_1 = 0.311$ . The input data can be found

in [33].

As illustrated in Fig. 7 (a)-(c), there is a good agreement between PM, FVDAM and FEM in the calculation of the effective relaxation moduli using three different volume fractions (10%, 20%, 30%). Moreover, due to low relative errors in relation to FVDAM (see Fig. 7 (d)-(f)), we can confirm the complete consistence between PM and FVDAM. In contrast, as time passes, much higher values for the relative errors with respect to FEM are reported. A possible explanation for this is tackled in [33], wherein it is suggested that the values of the effective relaxation moduli become small after 50min.

#### 4.4. Viscoelastic response: Prony's series

In this section, we take inspiration from [47] and consider three different inclusion shapes for the calculation of the effective relaxation modulus i.e. fibrous, spherical and ellipsoidal (see Fig. 9 (a),(h) and (i), respectively). Moreover, both constituents are assumed isotropic and linear viscoelastic.

The shear and bulk relaxation functions  $G(t)$  and  $K(t)$  can be computed in terms of Prony's series as follows,

$$G(t) = G_\infty + \sum_{i=1}^{N_G} G_i \exp\left(-\frac{t}{\xi_i^{(G)}}\right), \quad (25a)$$

$$K(t) = K_\infty + \sum_{j=1}^{N_K} K_j \exp\left(-\frac{t}{\xi_j^{(K)}}\right), \quad (25b)$$

where  $N_G$  and  $N_K$  are the number of terms for the corresponding modulus,  $\xi_i^{(G)}$  and  $\xi_j^{(K)}$  stand for the corresponding relaxation times,  $G_\infty$  and  $K_\infty$  denote the asymptotic moduli and,  $G_i$  and  $K_j$  represent the shear elastic modulus and bulk elastic modulus, respectively. Furthermore, by applying Laplace-Carson transform to equations (25a)-(25b) the following expressions

Stiff material					Soft material				
Relaxation times (s)	Shear moduli (GPa)	Bulk moduli (GPa)	Asymptotic moduli (GPa)		Relaxation times (s)	Shear moduli (GPa)	Bulk moduli (GPa)	Asymptotic moduli (GPa)	
$\xi_i^{(G)}$	$\xi_j^{(K)}$	$G_i$	$K_j$	$G_\infty = 100$	$\xi_i^{(G)}$	$\xi_j^{(K)}$	$G_i$	$K_j$	$G_\infty = 3.162$
3	10000	3.162	40000	$K_\infty = 8000$	0.032	100	2.512	3000	$K_\infty = 200$
10		17.1783			0.100	316.228	10	100	
32		100			0.316		56.234		
100		316.228			1		316.228		
316		1000			3.162		1000		
1000		5623.413			10		199.526		
3162		10000			31.623		50.119		
10000		562.341			100		19.953		
31623		141.254			316.228		12.589		
100000		56.234			1000		2.512		
316228		17.783			3162.278		1.698		
1000000		5.623			10000		1.202		
3162278		3.162			31622.777		1.148		
10000000		1.778			100000		1.096		

Table 2: Input data for Prony's series (see Table 1 of [47]).

are obtained

$$G(s) = G_\infty + \sum_{i=1}^{N_G} \frac{sG_i}{\xi_i^{(G)} + s}, \quad (26a)$$

$$K(s) = K_\infty + \sum_{j=1}^{N_K} \frac{sK_j}{\xi_j^{(K)} + s}. \quad (26b)$$

The parameters for the viscoelastic constituents used in the computations are reported in Table 2. In particular, we consider the fiber as the stiff material and the matrix as the soft one.

In Fig. 8 (a)-(b), we display the effective relaxation moduli  $\mathcal{R}_{12}^{(*)}$  and  $\mathcal{R}_{44}^{(*)}$  considering PM and the asymptotic homogenization method (AHM) developed in [16, 29]. The formulae for AHM involve two orders of truncation in the calculation of the effective properties, which are denoted by AHMT1 and AHMT2, respectively (see [48]). We notice that the curves in Fig. 8 (a)-(b) show similar trends to those reported in Fig. 1 and 2 of [47] except for an order of 10. This apparent lack of correlation can be attributed to

the assumed dimensions in relation to shear, bulk and asymptotic modulus summarized in Table 2. We take all this magnitudes with GPa dimension and pointed out this possible limitation in the paper [47].

Now, in order to support our results, we perform a numerical experiment only for the case of a fiber reinforced composite. That is, we consider the fiber's volumetric fraction equal to zero, so that the heterogeneous material is reduced to the homogeneous matrix with the properties of the soft material in Table 2. **In this respect**, the coefficients  $\mathcal{R}_{12}^{(*)}$  and  $\mathcal{R}_{44}^{(*)}$  for  $t = 0$  can be obtained from (25a)-(25b) as,

$$G(0) = G_\infty + \sum_{i=1}^{N_G} G_i = 1677.979 \quad (27a)$$

$$K(0) = K_\infty + \sum_{j=1}^{N_K} K_j = 3300 \quad (27b)$$

$$\mathcal{R}_{44}^{(*)}(0) = G(0) = 1677.979 \quad (27c)$$

$$\mathcal{R}_{12}^{(*)}(0) = K(0) - \frac{2}{3}G(0) = 2181.347 \quad (27d)$$

In particular, Fig. 8 (c)-(d) highlights the values of the effective coefficients  $\mathcal{R}_{12}^{(*)}$  and  $\mathcal{R}_{44}^{(*)}$  for  $t = 0.01$  when the fiber's volumetric fraction is equal to zero. As predicted, they are very close to those calculated in equations (27c)-(27d) for  $t = 0$  and provide positive evidence in support of the present study.

#### 4.5. Tabulation of results for different inclusions shapes

We conclude **our discussion** by presenting a tabulation of the effective relaxation modulus through three different numerical tests (see Table 3, 4 and 5). In particular, each case refers to one of the models analyzed in Sections 4.2, 4.3 and 4.4 which describe the viscoelastic behavior of the

constituents, i.e. four parameter model, Maxwell's model and Prony's series, respectively. Specifically, we closely examine, for fixed values of time, some of the numerical results shown in Fig. 4, 7 and 8. Besides, we go further and perform the computations for all the inclusions shapes displayed in Fig. 9. Regarding the geometrical details, we consider a unit periodic cell. Moreover, we notice that the aspect ratio for the ellipsoidal inclusion is  $b = c = \frac{4}{5}a$  and for the elliptical fibers  $b = \frac{4}{5}a$ , where  $a$  is the largest semi axis. It is worth mentioning that these computations used Mesh B and the fibers are considered aligned along  $Ox_3$ .

TIME (min)	$\mathcal{R}_{ij}^{(*)}$ (V.F.)	Maxwell's model								
		<i>LCF</i>	<i>LEF</i>	<i>LRF</i>	<i>LSF</i>	<i>Two LSF</i>	<i>Three LSF</i>	<i>CI</i>	<i>SI</i>	<i>EI</i>
0.01	$\mathcal{R}_{11}^{(*)}$ (10%)	6.5782	6.7394	6.6068	6.6782	6.5821	13.3268	7.0848	6.8205	7.0177
	$\mathcal{R}_{12}^{(*)}$ (10%)	2.8986	2.8982	2.9290	2.8526	2.9972	3.6123	2.8709	2.9171	2.9199
	$\mathcal{R}_{44}^{(*)}$ (10%)	1.8818	1.8242	1.9176	1.9148	2.3344	2.0521	1.9040	1.8720	1.8504
	$\mathcal{R}_{11}^{(*)}$ (20%)	7.7657	8.2663	7.8575	8.0175	7.6637	22.9399	9.0257	8.4137	9.1976
	$\mathcal{R}_{12}^{(*)}$ (20%)	3.2669	3.2625	3.3423	3.1343	3.5389	5.7337	3.1548	3.2878	3.2896
	$\mathcal{R}_{44}^{(*)}$ (20%)	2.2842	2.1369	2.3830	2.3534	4.2381	3.0749	2.2788	2.2249	2.1643
	$\mathcal{R}_{11}^{(*)}$ (30%)	9.3610	10.6932	9.6522	9.8140	8.9964	34.6365	11.6231	10.7037	14.2783
	$\mathcal{R}_{12}^{(*)}$ (30%)	3.6610	3.6501	3.8094	3.3992	4.2584	9.0923	3.4451	3.6813	3.7241
	$\mathcal{R}_{44}^{(*)}$ (30%)	2.7962	2.4992	3.0373	2.9006	7.7179	4.9077	2.7188	2.6699	2.5231
50	$\mathcal{R}_{11}^{(*)}$ (10%)	1.4305	1.4693	1.4376	1.4587	1.4346	8.4110	1.5724	1.4910	1.5416
	$\mathcal{R}_{12}^{(*)}$ (10%)	0.6246	0.6244	0.6318	0.6095	0.6459	1.2403	0.6078	0.6272	0.6271
	$\mathcal{R}_{44}^{(*)}$ (10%)	0.4136	0.3990	0.4238	0.4230	0.8066	0.5932	0.4217	0.4111	0.4056
	$\mathcal{R}_{11}^{(*)}$ (20%)	1.7012	1.8250	1.7246	1.7747	1.6832	17.5080	2.0687	1.8697	2.0849
	$\mathcal{R}_{12}^{(*)}$ (20%)	0.6983	0.6965	0.7158	0.6538	0.7593	2.9414	0.6402	0.6966	0.6928
	$\mathcal{R}_{44}^{(*)}$ (20%)	0.5105	0.4726	0.5395	0.5306	2.4171	1.3995	0.5130	0.4952	0.4796
	$\mathcal{R}_{11}^{(*)}$ (30%)	2.0726	2.4163	2.1495	2.2109	1.9914	28.6057	2.7635	2.4421	3.6273
	$\mathcal{R}_{12}^{(*)}$ (30%)	0.7697	0.7633	0.8020	0.6785	0.9108	5.7818	0.6504	0.7547	0.7350
	$\mathcal{R}_{44}^{(*)}$ (30%)	0.6368	0.5589	0.7104	0.6681	5.7110	3.0512	0.6213	0.6042	0.5656
150	$\mathcal{R}_{11}^{(*)}$ (10%)	0.1439	0.1485	0.1448	0.1481	0.1451	7.1801	0.1649	0.1514	0.1578
	$\mathcal{R}_{12}^{(*)}$ (10%)	0.0620	0.0619	0.0628	0.0594	0.0640	0.6516	0.0578	0.0619	0.0618
	$\mathcal{R}_{44}^{(*)}$ (10%)	0.0423	0.0405	0.0438	0.0437	0.4135	0.2212	0.0439	0.0420	0.0413
	$\mathcal{R}_{11}^{(*)}$ (20%)	0.1732	0.1881	0.1761	0.1844	0.1725	16.1373	0.2302	0.1950	0.2250
	$\mathcal{R}_{12}^{(*)}$ (20%)	0.0683	0.0680	0.0702	0.0605	0.0744	2.2496	0.0546	0.0669	0.0656
	$\mathcal{R}_{44}^{(*)}$ (20%)	0.0536	0.0488	0.0579	0.0566	1.9354	0.9668	0.0548	0.0517	0.0497
	$\mathcal{R}_{11}^{(*)}$ (30%)	0.2146	0.2586	0.2248	0.2370	0.2068	27.0712	0.3285	0.2663	0.4798
	$\mathcal{R}_{12}^{(*)}$ (30%)	0.0730	0.0715	0.0760	0.0563	0.0885	4.9615	0.0433	0.0674	0.0574
	$\mathcal{R}_{44}^{(*)}$ (30%)	0.0688	0.0587	0.0804	0.0736	5.1674	2.5659	0.0679	0.0647	0.0597

Table 3: The input data for the sub-phases are the same as Section 4.3.



The four-parameter model (Burgers model)										
TIME (hrs)	$\mathcal{R}_{ij}^{(*)}$	<i>LCF</i>	<i>LEF</i>	<i>LRF</i>	<i>LS</i>	<i>Two LSF</i>	<i>Three LSF</i>	<i>CI</i>	<i>SI</i>	<i>EI</i>
0.01	$\mathcal{R}_{22}^{(*)}$ (10%)	6.9280	6.8556	6.9408	7.0033	10.3621	9.3053	7.2770	7.0949	7.0470
	$\mathcal{R}_{44}^{(*)}$ (10%)	1.4236	1.3823	1.4481	1.4462	1.6315	1.4867	1.4416	1.4238	1.4088
	$\mathcal{R}_{66}^{(*)}$ (10%)	1.3701	1.3652	1.4097	1.3652	1.3926	1.4860	1.4416	1.4238	1.4306
	$\mathcal{R}_{22}^{(*)}$ (20%)	7.9713	7.7699	8.0122	8.1660	15.2759	13.0746	8.8627	8.4295	8.2657
	$\mathcal{R}_{44}^{(*)}$ (20%)	1.7177	1.6128	1.7847	1.7648	2.5510	1.9982	1.7160	1.6865	1.6442
	$\mathcal{R}_{66}^{(*)}$ (20%)	1.5665	1.5561	1.6536	1.5568	1.6254	1.9984	1.7160	1.6865	1.7071
	$\mathcal{R}_{22}^{(*)}$ (30%)	9.3467	8.9045	9.4856	9.7073	20.8178	17.4240	10.9678	10.3008	9.8516
	$\mathcal{R}_{44}^{(*)}$ (30%)	2.0884	1.8788	2.2494	2.1589	4.1179	2.8360	2.0357	2.0120	1.9096
	$\mathcal{R}_{66}^{(*)}$ (30%)	1.7921	1.7722	1.9535	1.7775	1.8954	2.8353	2.0357	2.0118	2.0878
100	$\mathcal{R}_{22}^{(*)}$ (10%)	3.2059	3.1673	3.2145	3.2509	6.9821	5.8175	3.4141	3.2980	3.2716
	$\mathcal{R}_{44}^{(*)}$ (10%)	0.6589	0.6377	0.6726	0.6716	0.8409	0.7273	0.6706	0.6590	0.6512
	$\mathcal{R}_{66}^{(*)}$ (10%)	0.6315	0.6290	0.6547	0.6294	0.6475	0.7268	0.6706	0.6590	0.6625
	$\mathcal{R}_{22}^{(*)}$ (20%)	3.7383	3.6285	3.7659	3.8580	11.8724	9.4425	4.2871	3.9976	3.9039
	$\mathcal{R}_{44}^{(*)}$ (20%)	0.8042	0.7497	0.8426	0.8310	1.6098	1.1235	0.8071	0.7880	0.7660
	$\mathcal{R}_{66}^{(*)}$ (20%)	0.7262	0.7209	0.7778	0.7219	0.7655	1.1238	0.8072	0.7880	0.7989
	$\mathcal{R}_{22}^{(*)}$ (30%)	4.4583	4.2105	4.5513	4.6886	17.4378	13.6729	5.4964	5.0246	4.7535
	$\mathcal{R}_{44}^{(*)}$ (30%)	0.9906	0.8802	1.0853	1.0315	3.0636	1.8531	0.9674	0.9510	0.8968
	$\mathcal{R}_{66}^{(*)}$ (30%)	0.8358	0.8257	0.9345	0.8293	0.9009	1.8522	0.9675	0.9509	0.9934
600	$\mathcal{R}_{22}^{(*)}$ (10%)	2.2114	2.1846	2.2174	2.2430	6.0825	4.8869	2.3576	2.2751	2.2568
	$\mathcal{R}_{44}^{(*)}$ (10%)	0.4545	0.4398	0.4640	0.4633	0.6258	0.5230	0.4628	0.4546	0.4492
	$\mathcal{R}_{66}^{(*)}$ (10%)	0.4355	0.4338	0.4519	0.4341	0.4478	0.5226	0.4628	0.4545	0.4570
	$\mathcal{R}_{22}^{(*)}$ (20%)	2.5791	2.5031	2.5985	2.6636	10.9497	8.4549	2.9666	2.7593	2.6941
	$\mathcal{R}_{44}^{(*)}$ (20%)	0.5549	0.5172	0.5815	0.5735	1.3449	0.8837	0.5572	0.5437	0.5284
	$\mathcal{R}_{66}^{(*)}$ (20%)	0.5009	0.4972	0.5372	0.4980	0.5297	0.8841	0.5572	0.5436	0.5512
	$\mathcal{R}_{22}^{(*)}$ (30%)	3.0773	2.9053	3.1427	3.2405	16.5020	12.6307	3.8148	3.4727	3.2830
	$\mathcal{R}_{44}^{(*)}$ (30%)	0.6836	0.6072	0.7497	0.7122	2.7572	1.5785	0.6680	0.6563	0.6188
	$\mathcal{R}_{66}^{(*)}$ (30%)	0.5765	0.5696	0.6462	0.5721	0.6231	1.5775	0.6680	0.6562	0.6858

Table 4: The input data for the sub-phases are the same as Section 4.2.

Prony's series											
TIME (s)	$\mathcal{R}_{ij}^{(*)}$	<i>LCF</i>	<i>LEF</i>	<i>LRF</i>	<i>LSF</i>	<i>Two LSF</i>	<i>Three LSF</i>	<i>CI</i>	<i>SI</i>	<i>EI</i>	
0.01	$\mathcal{R}_{11}^{(*)}$ (10%)	6330.9686	6463.9069	6353.2006	6395.5246	6319.6010	7922.7994	6679.2780	6529.3003	6677.3653	
	$\mathcal{R}_{12}^{(*)}$ (10%)	2471.7239	2472.4374	2496.2939	2450.4499	2500.0625	2624.5756	2479.4462	2493.5456	2496.7699	
	$\mathcal{R}_{14}^{(*)}$ (10%)	1970.2266	1923.0107	1994.0628	1992.2400	2125.9549	2000.0913	1977.5356	1959.6305	1941.9464	
	$\mathcal{R}_{11}^{(*)}$ (20%)	7354.3096	7744.2020	7421.8783	7506.3527	7241.6860	10784.4328	8167.4082	7850.5967	8376.1987	
	$\mathcal{R}_{12}^{(*)}$ (20%)	2779.1465	2779.3829	2839.1636	2719.1023	2862.4893	3271.4743	2780.4459	2820.5936	2828.9589	
	$\mathcal{R}_{14}^{(*)}$ (20%)	2332.3499	2214.6194	2395.7865	2377.3201	2884.3603	2467.2618	2311.3543	2281.1879	2232.2256	
	$\mathcal{R}_{11}^{(*)}$ (30%)	8675.7725	9625.4785	8873.7830	8931.4620	8348.5790	14134.7816	10038.2104	9611.7325	11428.1469	
	$\mathcal{R}_{12}^{(*)}$ (30%)	3117.5790	3115.7507	3234.0979	3006.9721	3312.1272	4171.26466	3126.8903	3194.9530	3258.5255	
	$\mathcal{R}_{14}^{(*)}$ (30%)	2776.2291	2546.1982	2922.0911	2841.4458	4010.3548	3135.0835	2697.1986	2671.6363	2557.2173	
	14.5	$\mathcal{R}_{11}^{(*)}$ (10%)	3420.2613	3444.4360	3421.1834	3450.3520	3440.0138	5265.4117	3528.1570	3452.4691	3481.5114
		$\mathcal{R}_{12}^{(*)}$ (10%)	3080.4828	3082.1377	3090.7180	3060.7676	3022.6373	3132.2673	3056.9273	3083.1828	3082.7123
		$\mathcal{R}_{14}^{(*)}$ (10%)	159.6480	153.5738	164.3080	163.9929	273.9138	210.6148	167.4352	164.0731	162.0413
$\mathcal{R}_{11}^{(*)}$ (20%)		3882.0742	3967.2178	3883.6528	3974.8329	3913.4023	7949.9654	4219.6897	3993.3174	4143.3180	
$\mathcal{R}_{12}^{(*)}$ (20%)		3399.6095	3401.0045	3426.0061	3330.2289	3259.6196	3659.07117	3306.1255	3395.9505	3386.8793	
$\mathcal{R}_{14}^{(*)}$ (20%)		198.8048	182.9519	212.0436	207.9328	740.7131	440.8431	205.7879	200.7157	194.7131	
$\mathcal{R}_{11}^{(*)}$ (30%)		4503.7518	4774.3710	4517.7570	4713.3316	4526.0909	11138.8076	5246.4682	4795.6902	5887.4423	
$\mathcal{R}_{12}^{(*)}$ (30%)		3761.2571	3754.4058	3818.5060	3594.4532	3532.8398	4417.5313	3542.4684	3730.6670	3686.6281	
$\mathcal{R}_{14}^{(*)}$ (30%)		250.4889	217.6392	284.2823	264.9639	1682.9608	905.1975	250.6470	247.2180	231.4440	
60		$\mathcal{R}_{11}^{(*)}$ (10%)	2203.2138	2211.4122	2205.1478	2213.7889	2211.8782	4027.5795	2237.2881	2212.8662	2221.0832
		$\mathcal{R}_{12}^{(*)}$ (10%)	2100.5041	2102.6491	2105.0875	2096.0546	2060.8204	2169.8632	2094.4675	2102.6113	2102.6042
		$\mathcal{R}_{14}^{(*)}$ (10%)	49.0575	47.3497	50.3364	50.2619	150.6666	96.3096	51.0229	49.9909	49.4189
	$\mathcal{R}_{11}^{(*)}$ (20%)	2481.3152	2508.8586	2485.4144	2515.6742	2497.1469	6536.0159	2594.9182	2513.5329	2554.2208	
	$\mathcal{R}_{12}^{(*)}$ (20%)	2340.9156	2345.3027	2351.5403	2321.8900	2237.5040	2634.8713	2309.0240	2342.6406	2338.7861	
	$\mathcal{R}_{14}^{(*)}$ (20%)	60.3727	55.9703	63.9319	62.8304	568.5508	298.0519	62.0211	60.4567	58.7335	
	$\mathcal{R}_{11}^{(*)}$ (30%)	2844.1822	2932.0577	2855.1898	2932.8775	2871.3467	9527.5119	3136.2394	2927.9989	3402.6565	
	$\mathcal{R}_{12}^{(*)}$ (30%)	2633.4308	2639.9065	2657.7396	2574.2137	2444.0244	3326.9868	2536.3056	2624.1038	2602.0840	
	$\mathcal{R}_{14}^{(*)}$ (30%)	75.0864	66.0692	83.9259	78.9781	1449.0097	725.3000	74.9251	73.6305	69.2229	

Table 5: The input data for the sub-phases are the same as Section 4.4.

## 5. Conclusions

In this paper, we use a semi-analytical technique that naturally appear as a combination of the two-scale asymptotic homogenization method and a three dimensional computational study, [by means of the finite element software COMSOL Multiphysics<sup>®</sup>](#). [Particularly, the methodology is framed to the investigation of the effective creep and relaxation behavior of non-aging linear viscoelastic composite materials. The results derived from the AHM's procedure are based on the elastic-viscoelastic correspondence principle and the Laplace-Carson transform, and comprised the local and homogenized problem, and the expression for the effective coefficients.](#) Moreover, the stress jump conditions and the corresponding interface loads for composites with discontinuous material properties and perfect contact at the interfaces as well as significantly details of the three dimensional computational study are provided.

The strength of our work lies in achieving accurate results for the calculation of the effective properties of composite materials reinforced with several types of inclusions. [This is evidenced by the good correlation and low relative errors in the comparisons with others methods reported in the literature. In this respect, an study of the solution's convergence through three different mesh discretizations for the particular case of linear elastic composites is performed. In the computational simulations, we describe the viscoelastic behavior of the constituents by having recourse to Maxwell's model, four parameter model and Prony's series.](#)

[One of the limitations of this work is related to the computational time involved to pass from the Laplace-Carson space to the time domain. One way to deal with this issue can be through parallel computing. This concern](#)

is part of our current investigations.

Finally, we take the occasion to notice that our work can be adapted to model biological and bioinspired materials with hierarchical structure, e.g. bones [49, 50, 51]. Furthermore, the present framework can also be suitable for the study of the effective behavior of piezoelectric–polymeric composites (see [52, 53]).

Future developments of the present work include the consideration of imperfect contact conditions (see [54, 55]) and the extension to ageing viscoelastic composite materials (see [56, 57]).

## References

- [1] Liu, X. and Tang, T. and Yu, W. and Pipes, R. B., Multiscale modeling of viscoelastic behaviors of textile composites, *International Journal of Engineering Science* 130 (2018) 175–186. doi:10.1016/j.ijengsci.2018.06.003.
- [2] Dastjerdi, S. and Akgöz, B. and Civalek, Ö., On the effect of viscoelasticity on behavior of gyroscopes, *International Journal of Engineering Science* 149 (2020) 103236. doi:10.1016/j.ijengsci.2020.103236.
- [3] D. Malhotra, S. Pan, L. Rüther, T. Goudoulas, G. Schlippe, W. Voss, N. Germann, Linear viscoelastic and microstructural properties of native male human skin and in vitro 3d reconstructed skin models, *Journal of the Mechanical Behavior of Biomedical Materials* 90 (2019) 644–654. doi:10.1016/j.jmbbm.2018.11.013.
- [4] Kumar, N. and Khader, S. M. A. and Pai, R. and Khan, S.H. and Kyriacou, P.A., Fluid structure interaction study of stenosed carotid

artery considering the effects of blood pressure, *International Journal of Engineering Science* 154 (2020) 103341. doi:10.1016/j.ijengsci.2020.103341.

- [5] Carpenter, H. J. and Gholipour, A. and Ghayesh, M. H. and Zander, A. C. and Psaltis, P. J., A review on the biomechanics of coronary arteries, *International Journal of Engineering Science* 147 (2020) 103201. doi:10.1016/j.ijengsci.2019.103201.
- [6] Gholipour, A. and Ghayesh, M. H. and Zander, A. C. and Psaltis, P. J., In vivo based biomechanics of right and left coronary arteries, *International Journal of Engineering Science* 154 (2020) 103281. doi:10.1016/j.ijengsci.2020.103281.
- [7] Sevostianov, I. and Levin, V. and Radi, E., Effective viscoelastic properties of short-fiber reinforced composites, *International Journal of Engineering Science* 100 (2016) 61–73. doi:10.1016/j.ijengsci.2015.10.008.
- [8] E. Vilchevskaya, V. Levin, S. Seyedkavoosi, I. Sevostianov, Replacement relations for a viscoelastic material containing multiple inhomogeneities, *International Journal of Engineering Science* 136 (2019) 26–37. doi:10.1016/j.ijengsci.2018.12.006.
- [9] Smirnov, A. and Vilchevskaya, E. and Sevostianov, I., Evaluation of the effective viscoelastic properties of a material containing multiple oblate inhomogeneities using fraction-exponential operators, *International Journal of Engineering Science* 144 (2019) 103124. doi:10.1016/j.ijengsci.2019.103124.

- [10] Sevostianov, I. and Mogilevskaya, S. G. and Kushch, V. I., Maxwell's methodology of estimating effective properties: Alive and well, *International Journal of Engineering Science* 140 (2019) 35–88. doi:10.1016/j.ijengsci.2019.05.001.
- [11] Ebrahimi, F. and Barati, M. R. , A nonlocal higher-order refined magneto-electro-viscoelastic beam model for dynamic analysis of smart nanostructures, *International Journal of Engineering Science* 107 (2016) 183–196. doi:10.1016/j.ijengsci.2016.08.001.
- [12] Z. Wang, D. E. Smith, Numerical analysis on viscoelastic creep responses of aligned short fiber reinforced composites, *Composite Structures* 229 (2019) 111394. doi:10.1016/j.compstruct.2019.111394.
- [13] S.-N. Nguyen, J. Lee, J.-W. Han, M. Cho, A coupled hygrothermo-mechanical viscoelastic analysis of multilayered composite plates for long-term creep behaviors, *Composite Structures* 242 (2020) 112030. doi:10.1016/j.compstruct.2020.112030.
- [14] Song, R. and Muliana, A. and Rajagopal, K., A thermodynamically consistent model for viscoelastic polymers undergoing microstructural changes, *International Journal of Engineering Science* 142 (2019) 106–124. doi:10.1016/j.ijengsci.2019.05.009.
- [15] Hine, P. J. and Gusev, A. A., Validating a micromechanical modelling scheme for predicting the five independent viscoelastic constants of unidirectional carbon fibre composites, *International Journal of Engineering Science* 144 (2019) 103133. doi:10.1016/j.ijengsci.2019.103133.

- [16] R. Rodríguez-Ramos, J. A. Otero, O. L. Cruz-González, R. Guinovart-Díaz, J. Bravo-Castillero, F. J. Sabina, P. Padilla, F. Lebon, I. Sevostianov, Computation of the relaxation effective moduli for fibrous viscoelastic composites using the asymptotic homogenization method, *International Journal of Solids and Structures* 190 (2020) 281–290. doi:10.1016/j.ijsolstr.2019.11.014.
- [17] Farajpour, A. and Ghayesh, M. H. and Farokhi, H., Nonlocal nonlinear mechanics of imperfect carbon nanotubes, *International Journal of Engineering Science* 142 (2019) 201–215. doi:10.1016/j.ijengsci.2019.03.003.
- [18] Omari, M. A. and Almagableh, A. and Sevostianov, I. and Ashhab, M. S. and Yaseen, A. B., Modeling of the viscoelastic properties of thermoset vinyl ester nanocomposite using artificial neural network, *International Journal of Engineering Science* 150 (2020) 103242. doi:10.1016/j.ijengsci.2020.103242.
- [19] Rahmanpanah, H. and Mouloudi, S. and Burvill, C. and Gohari, S. and Davies, H. M. S., Prediction of load-displacement curve in a complex structure using artificial neural networks: A study on a long bone, *International Journal of Engineering Science* 154 (2020) 103319. doi:10.1016/j.ijengsci.2020.103319.
- [20] A. Bensoussan, G. Papanicolau, J.-L. Lions, *Asymptotic Analysis for Periodic Structures*, 1st Edition, Vol. 5, North-Holland, 1978.
- [21] E. Sanchez-Palencia, *Non-Homogeneous Media and Vibration Theory*, Lecture Notes in Physics, Springer-Verlag, 1980. doi:10.1007/3-540-10000-8.

- [22] N. S. Bakhvalov, G. Panasenko, Homogenisation: Averaging Processes in Periodic Media: Mathematical Problems in the Mechanics of Composite Materials, Mathematics and its Applications, Kluwer Academic Publishers, 1989. doi:10.1007/978-94-009-2247-1.
- [23] G. Allaire, M. Briane, Multiscale convergence and reiterated homogenisation, Proceedings of the Royal Society of Edinburgh Section A Mathematics 126 (2) (1996) 297–342. doi:10.1017/S0308210500022757.
- [24] J. L. Auriault, C. Boutin, C. Geindreau, Homogenization of Coupled Phenomena in Heterogenous Media, ISTE, 2009. doi:10.1002/9780470612033.
- [25] Guinovart-Díaz, R. and López-Realpozo, J. C. and Rodríguez-Ramos, R. and Bravo-Castillero, J. and Ramírez, M. and Camacho-Montes, H. and Sabina, F. J., Influence of parallelogram cells in the axial behaviour of fibrous composite, International Journal of Engineering Science 49 (1) (2011) 75 – 84. doi:10.1016/j.ijengsci.2010.06.024.
- [26] N. Willoughby, W. J. Parnell, A. L. Hazel, I. D. Abrahams, Homogenization methods to approximate the effective response of random fibre-reinforced composites, International Journal of Solids and Structures 49 (13) (2012) 1421–1433. doi:10.1016/j.ijsolstr.2012.02.010.
- [27] A. L. Kalamkarov, I. V. Andrianov, P. M. C. L. Pacheco, M. A. Savi, G. A. Starushenko, Asymptotic analysis of fiber-reinforced composites of hexagonal structure, Journal of Multiscale Modelling 07 (03) (2016) 1650006. doi:10.1142/S1756973716500062.
- [28] O. L. Cruz-González, A. Ramírez-Torres, R. Rodríguez-Ramos,



- R. Penta, J. Bravo-Castillero, R. Guinovart-Díaz, J. Merodio, F. J. Sabina, F. Lebon, A hierarchical asymptotic homogenization approach for viscoelastic composites, *Mechanics of Advanced Materials and Structures* 0 (0) (2020) 1–12. doi:10.1080/15376494.2020.1722872.
- [29] J. A. Otero, R. Rodríguez-Ramos, R. Guinovart-Díaz, O. L. Cruz-González, F. J. Sabina, H. Berger, T. Böhlke, Asymptotic and numerical homogenization methods applied to fibrous viscoelastic composites using Prony’s series, *Acta Mechanica* (2020). doi:10.1007/s00707-020-02671-1.
- [30] R. Penta, A. Gerisch, Investigation of the potential of asymptotic homogenization for elastic composites via a three-dimensional computational study, *Computing and Visualization in Science* 17 (2016). doi:10.1007/s00791-015-0257-8.
- [31] R. Penta, A. Gerisch, The asymptotic homogenization elasticity tensor properties for composites with material discontinuities, *Continuum Mechanics and Thermodynamics* 29 (1) (2017) 187–206. doi:10.1007/s00161-016-0526-x.
- [32] G. Wang, M.-J. Pindera, Locally-exact homogenization of viscoelastic unidirectional composites, *Mechanics of Materials* 103 (2016) 95–109. doi:10.1016/j.mechmat.2016.09.009.
- [33] Q. Chen, G. Wang, X. Chen, J. Geng, Finite-volume homogenization of elastic/viscoelastic periodic materials, *Composite Structures* 182 (2017) 457–470. doi:10.1016/j.compstruct.2017.09.044.
- [34] Q. Li, W. Chen, S. Liu, J. Wang, A novel implementation of asymptotic

- homogenization for viscoelastic composites with periodic microstructures, *Composite Structures* 208 (2019) 276–286. doi:10.1016/j.compstruct.2018.09.056.
- [35] Y. Chen, P. Yang, Y. Zhou, Z. Guo, L. Dong, E. P. Busso, A micromechanics-based constitutive model for linear viscoelastic particle-reinforced composites, *Mechanics of Materials* 140 (2020) 103228. doi:10.1016/j.mechmat.2019.103228.
- [36] R. M. Christensen, *Theory of Viscoelasticity - 2nd Edition An Introduction*, Academic Press, Cambridge, MA, 1982.
- [37] S. Maghous, G. J. Creus, Periodic homogenization in thermoviscoelasticity: case of multilayered media with ageing, *International Journal of Solids and Structures* 40 (4) (2003) 851–870. doi:10.1016/S0020-7683(02)00549-8.
- [38] R. Lakes, *Viscoelastic Materials*, Cambridge University Press, 2009. doi:10.1017/CB09780511626722.
- [39] [Cioranescu, D. and Donato, P., An introduction to homogenization, Oxford University Press, 1999.](#)
- [40] L. Persson, L. Persson, N. Svanstedt, J. Wyller, *The Homogenization Method. An Introduction.*, Studentlitteratur, 1993.
- [41] Juraj, Numerical inversion of laplace transforms in matlab (2020).  
URL <https://www.mathworks.com/matlabcentral/fileexchange/32824-numerical-inversion-of-laplace-transforms-in-matlab>
- [42] Z. Hashin, *Theory of fiber reinforced materials*, NASA contractor report. NASA CR-1974, 1972.

- [43] S. Mogilevskaya, V. Kushch, D. Nikolskiy, Evaluation of some approximate estimates for the effective tetragonal elastic moduli of two-phase fiber-reinforced composites, *Journal of Composite Materials* 48 (19) (2014) 2349–2362. doi:10.1177/0021998313498103.
- [44] F. Mainardi, G. Spada, Creep, relaxation and viscosity properties for basic fractional models in rheology, *The European Physical Journal Special Topics* 193 (2011) 133–160. doi:10.1140/epjst/e2011-01387-1.
- [45] M. A. A. Cavalcante, S. P. C. Marques, Homogenization of periodic materials with viscoelastic phases using the generalized fvdam theory, *Computational Materials Science* 87 (2014) 43–53. doi:10.1016/j.commatsci.2014.01.053.
- [46] G. Wang, M.-J. Pindera, Locally-exact homogenization theory for transversely isotropic unidirectional composites, *Mechanics Research Communications* 78 (2016) 2–14. doi:10.1016/j.mechrescom.2015.09.011.
- [47] M. E. Kouri, A. Bakkali, L. Azrar, Mathematical modeling of the overall time-dependent behavior of non-ageing viscoelastic reinforced composites, *Applied Mathematical Modelling* 40 (7) (2016) 4302–4322. doi:10.1016/j.apm.2015.11.031.
- [48] J. Bravo-Castillero, R. Guinovart-Díaz, R. Rodríguez-Ramos, F. J. Sabina, R. Brenner, Unified analytical formulae for the effective properties of periodic fibrous composites, *Materials Letters* 73 (2012) 68–71. doi:10.1016/j.matlet.2011.12.106.

- [49] R. Penta, K. Raum, Q. Grimal, S. Schrof, A. Gerisch, Can a continuous mineral foam explain the stiffening of aged bone tissue? a micromechanical approach to mineral fusion in musculoskeletal tissues, *Bioinspiration & Biomimetics* 11(3) (2016). doi:10.1088/1748-3190/11/3/035004.
- [50] L. Eberhardsteiner, C. Hellmich, S. Scheiner, Layered water in crystal interfaces as source for bone viscoelasticity: arguments from a multiscale approach, *Computer Methods in Biomechanics and Biomedical Engineering* 17 (1) (2014) 48–63. doi:10.1080/10255842.2012.670227.
- [51] S.-T. Nguyen, M.-B. Vu, M.-N. Vu, Q.-D. To, A homogenization approach for the effective drained viscoelastic properties of 2d porous media and an application for cortical bone, *Journal of the Mechanical Behavior of Biomedical Materials* 78 (2018) 134–142. doi:10.1016/j.jmbbm.2017.11.020.
- [52] G. Zhang, M. Wu, Connectivity and shape effects on the effective properties of piezoelectric–polymeric composites, *International Journal of Engineering Science* 48 (1) (2010) 37–51. doi:10.1016/j.ijengsci.2009.06.006.
- [53] R. Jayendiran, A. Arockiarajan, Numerical modelling and experimental characterization of temperature-dependent viscoelastic effect on the ferroelastic behaviour of 1–3 piezocomposites, *Sensors and Actuators A: Physical* 226 (2015) 81 – 97. doi:https://doi.org/10.1016/j.sna.2015.02.002.
- [54] S. Dumont, R. Rizzoni, F. Lebon, E. Sacco, Soft and hard inter-

face models for bonded elements, *Composites Part B: Engineering* 153 (2018) 480–490. doi:<https://doi.org/10.1016/j.compositesb.2018.08.076>.

[55] J. Ye, Y. Hong, H. Cai, Y. Wang, Z. Zhai, B. Shi, A new three-dimensional parametric fvdam for investigating the effective elastic moduli of particle-reinforced composites with interphase, *Mechanics of Advanced Materials and Structures* 26 (22) (2019) 1870–1880. doi:[10.1080/15376494.2018.1452321](https://doi.org/10.1080/15376494.2018.1452321).

[56] Z. Yang, Y. Sun, Y. Liu, T. Guan, H. Dong, A three-scale asymptotic analysis for ageing linear viscoelastic problems of composites with multiple configurations, *Applied Mathematical Modelling* 71 (2019) 223–242. doi:[10.1016/j.apm.2019.02.021](https://doi.org/10.1016/j.apm.2019.02.021).

[57] [Barthélémy, J.-F. and Giraud, A. and Sanahuja, J. and Sevostianov, I., Effective properties of ageing linear viscoelastic media with spheroidal inhomogeneities, \*International Journal of Engineering Science\* 144 \(2019\) 103104. doi:\[10.1016/j.ijengsci.2019.05.015\]\(https://doi.org/10.1016/j.ijengsci.2019.05.015\)](#).

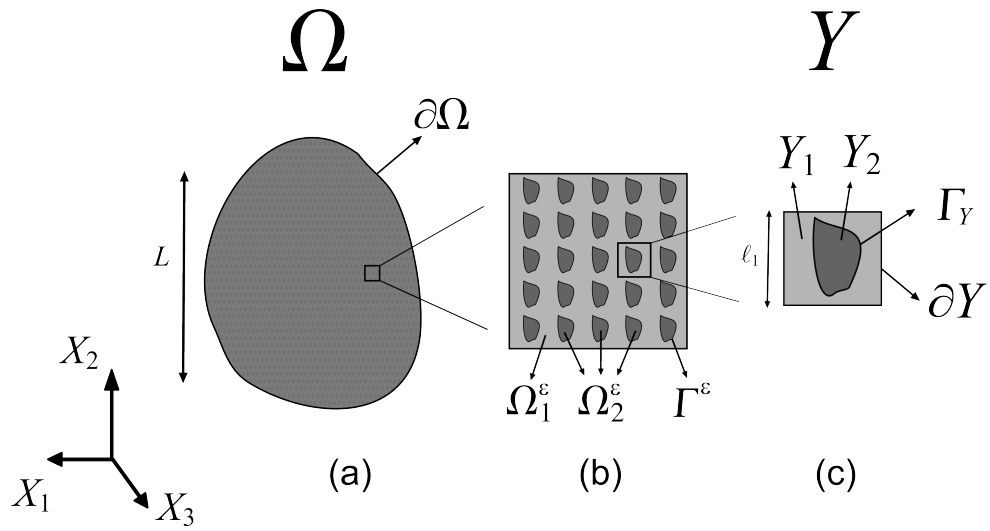


Figure 1: (a) Macroscale: viscoelastic heterogeneous material. (b)  $\varepsilon$ -structural level. (c) Microscale: periodic cell. The inclusions do not intersect the boundaries and the matrix and the sub-phases are perfectly bonded.

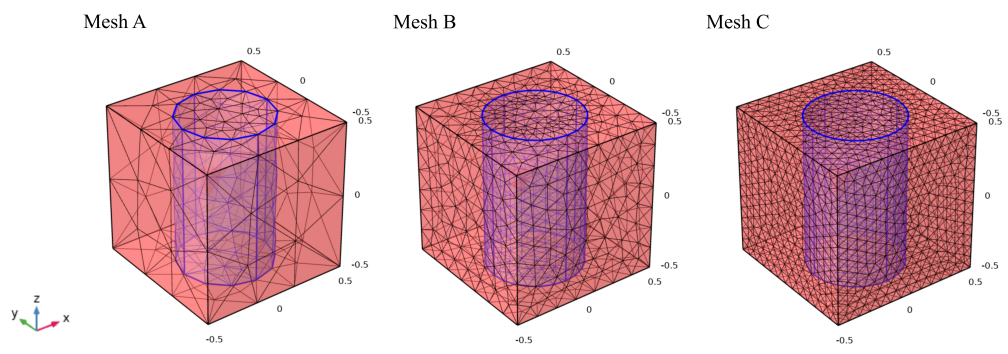


Figure 2: Three types of mesh discretization for the periodic cells: Mesh A, B and C.

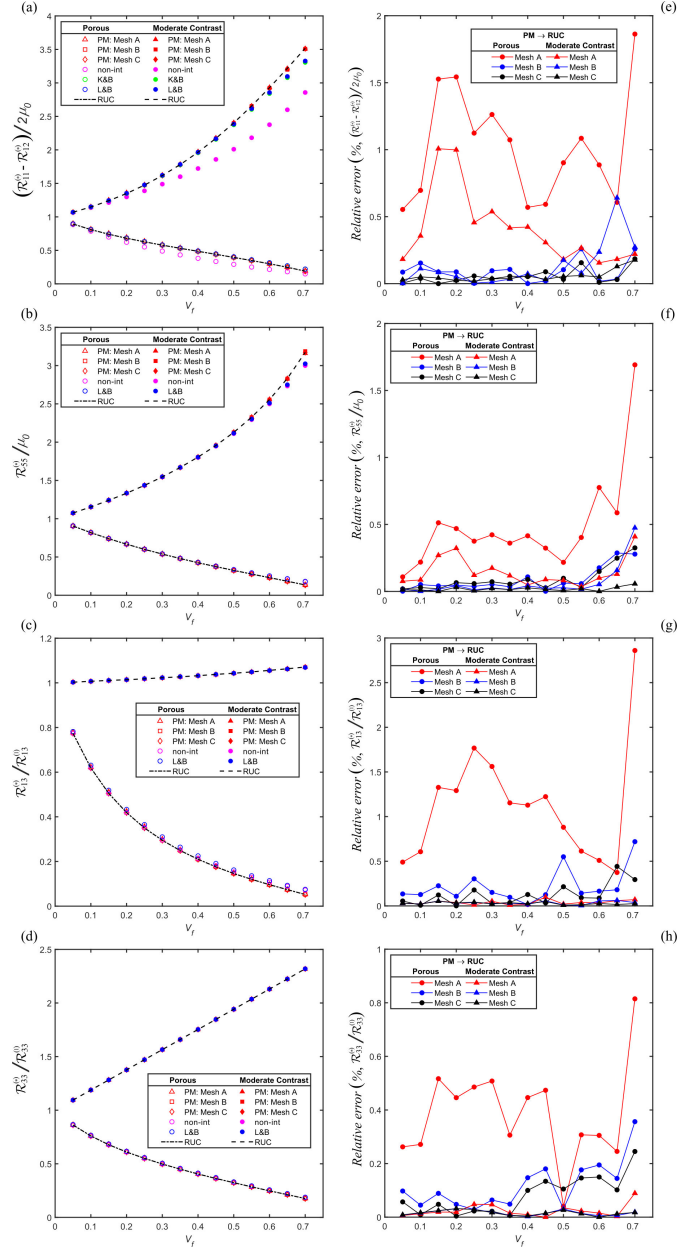


Figure 3: Charts (a)-(d) show the calculation of the instant elastic response for normalized effective coefficients. The comparisons are carried out with Table 1-6 of [43].

In addition, charts (e)-(h) display the relative errors with respect to *RUC*, for both porous and moderate contrast of the three mesh discretizations.



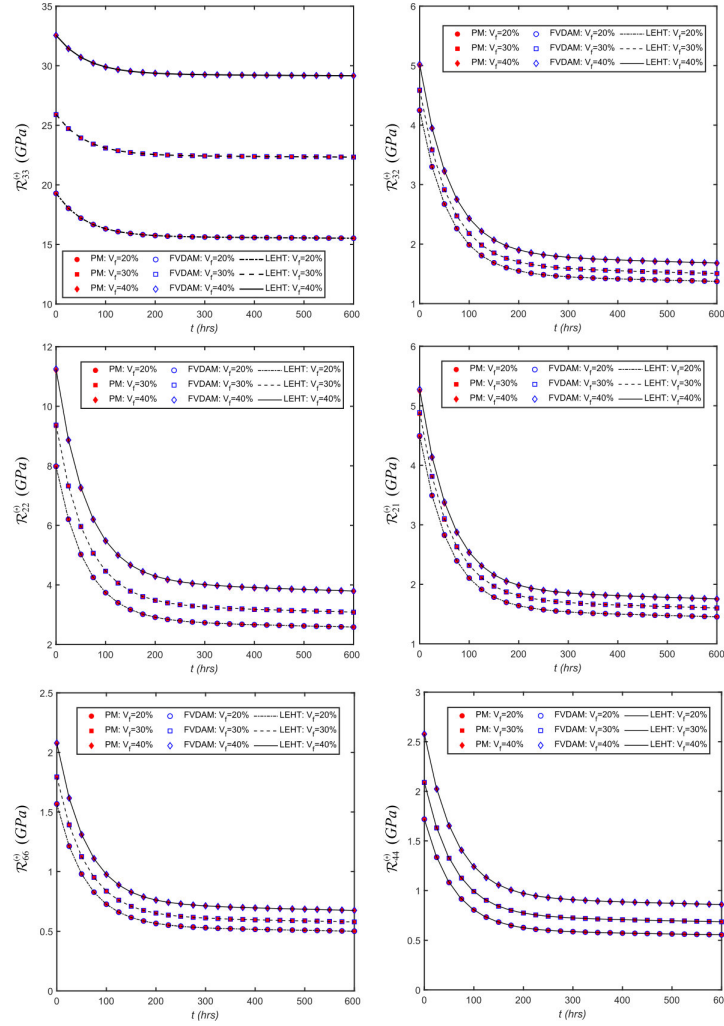


Figure 4: Computation of the effective relaxation modulus for unidirectionally-reinforced glass/epoxy composites and the comparison against LEHT and FVDAM. The comparisons are made with Fig. 11 of [33].

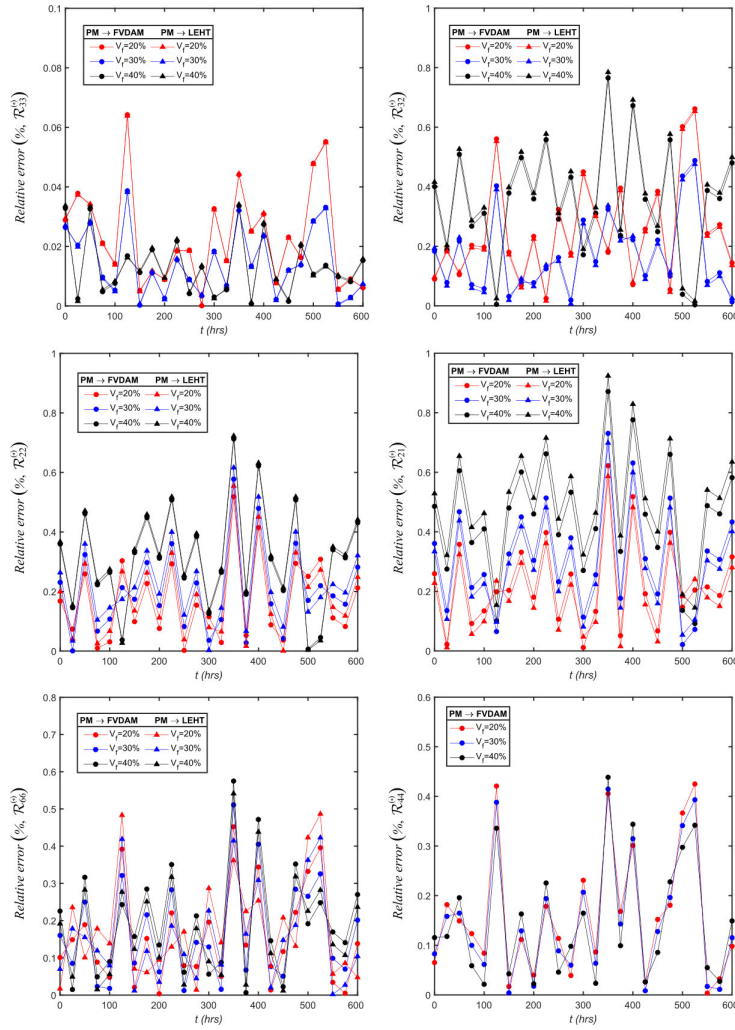


Figure 5: The estimation of relative errors of PM with respect to both FVDAM and LEHT for three different volume fractions.

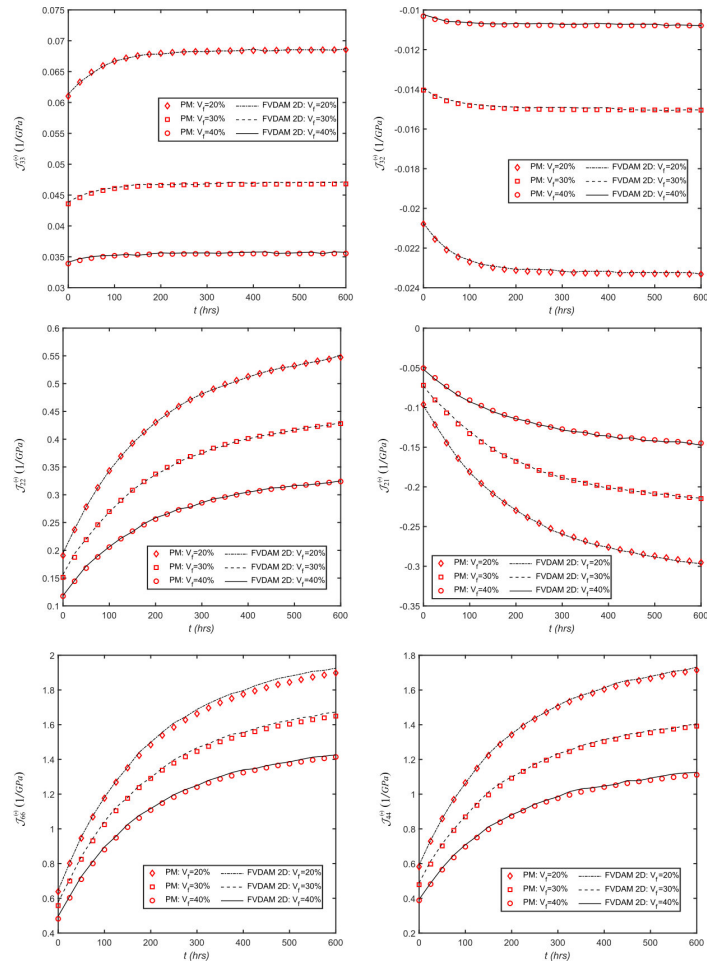


Figure 6: Computation of the effective creep compliance. The comparisons are performed with Fig. 12 of [45].

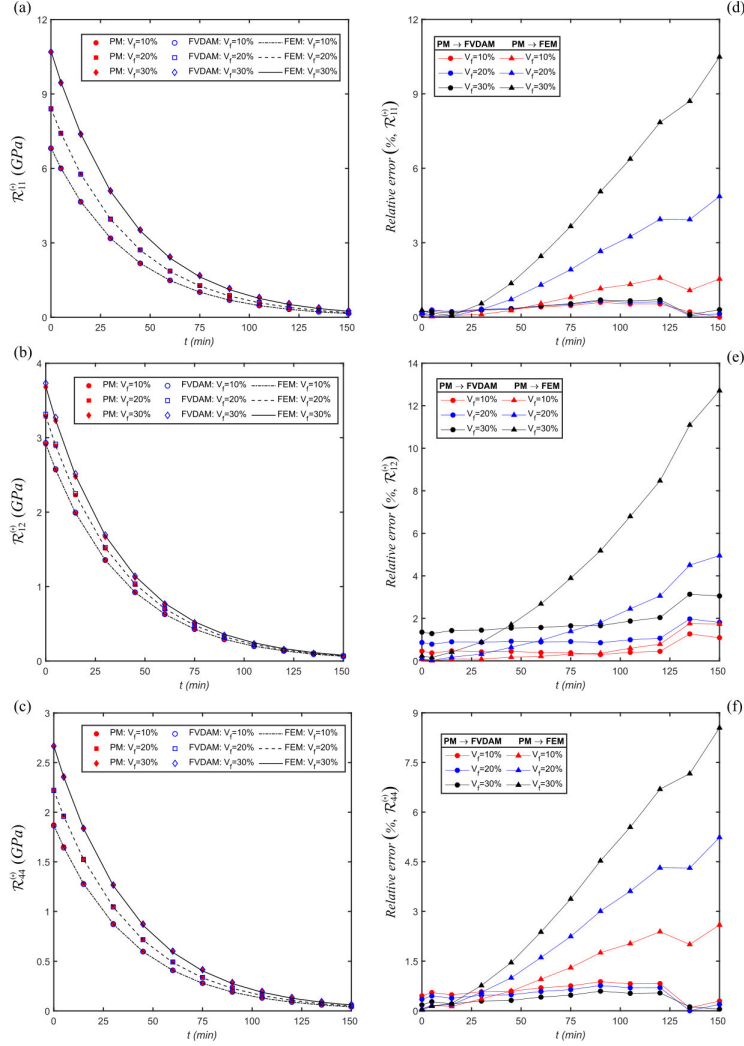


Figure 7: Charts (a)-(c) show the calculation of the effective relaxation modulus for spherical reinforced composites. Our results are compared with Fig. 6 of [33].

Moreover, charts (d)-(f) present the relative errors of PM with respect to FVDAM and FEM.

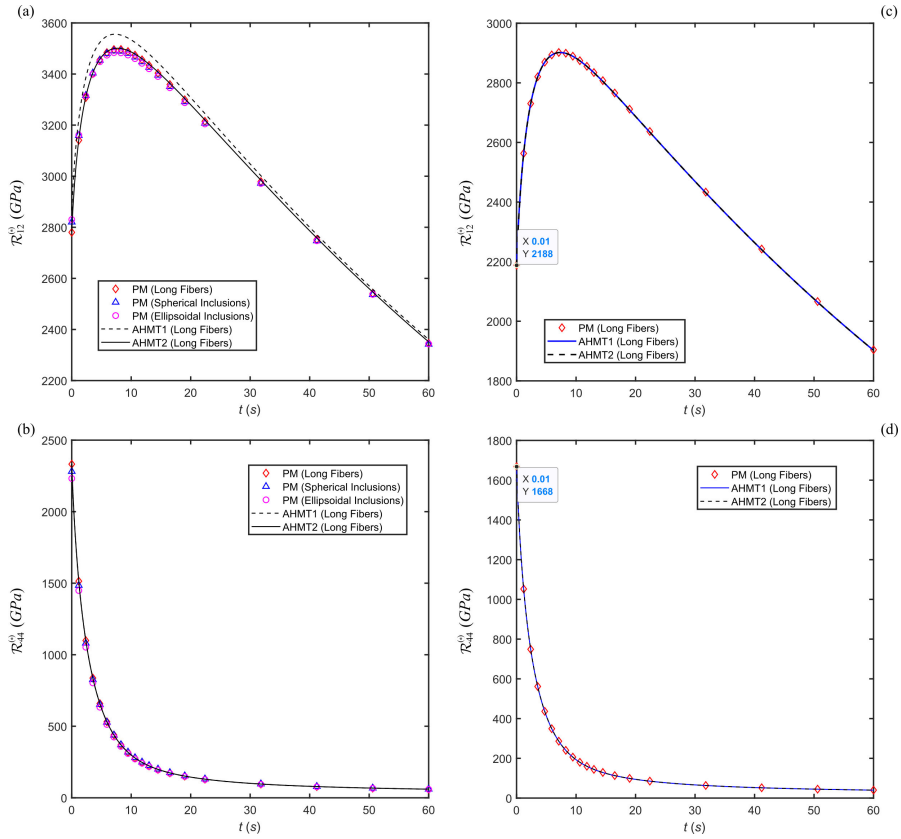


Figure 8: Charts (a)-(b) display comparisons with Fig. 2 and 3 of [47].

Charts (c)-(d) present the results of a numerical experiment for the fiber's volumetric fraction equal to zero.

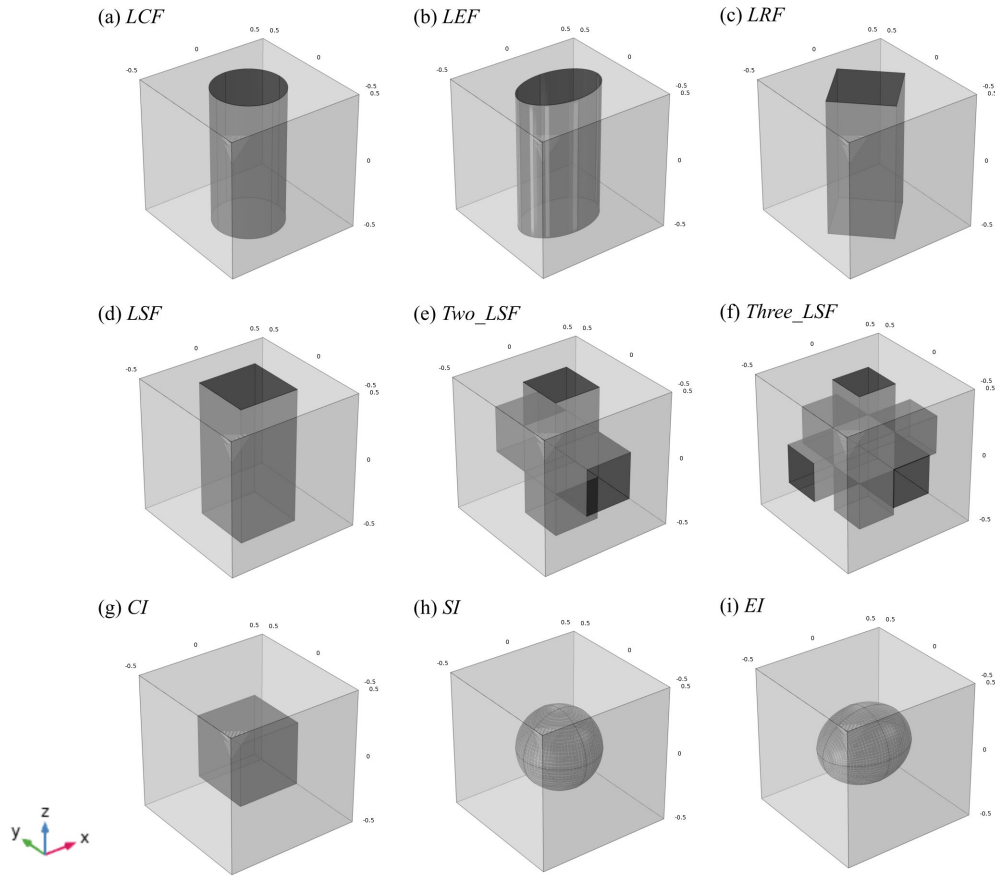


Figure 9: Representation of the analyzed periodic cells. The acronyms *LCF*, *LEF*, *LRF*, *LSF* stands for long circular, elliptical, rhombic and square fibers, respectively. In addition, we consider *Two\_LSF* and *Three\_LSF* to denote two and three long square fibers and *CI*, *SI*, *EI* for cubic, spherical and ellipsoidal inclusions, respectively.