

Available online at www.sciencedirect.com

ScienceDirect

journal homepage: www.elsevier.com/locate/hydro

New mechanism and improved kinetics of hydrogen absorption and desorption of Mg(In) solid solution alloy milling with CeF₃

H.C. Zhong^{a,b,*}, H.J. Lin^c, X.J. Lu^{a,b}, C.Y. Cao^{a,b}, C. Chen^b, J.J. Sun^b

^a Fujian Provincial Key Laboratory of Functional Materials and Applications, Xiamen University of Technology, Xiamen, 361024, China

^b School of Materials Science and Engineering, Xiamen University of Technology, Xiamen, 361024, China

^c Institute of Advanced Wear & Corrosion Resistance and Functional Materials, Jinan University, Guangzhou, 510632, China

HIGHLIGHTS

- Nanostructured CeIn₃ forms by hydrogenation.
- In-situ formed CeIn₃ impedes the agglomeration of MgIn.
- Mg(In, Ce) solid solution reversibly forms by de/hydrogenation.
- The reversible phase transition and CeIn₃ enhance de/hydrogenation reaction.
- Destabilization/lowering dehydrogenation enthalpy of MgH₂ is achieved.

ARTICLE INFO

Article history:

Received 22 May 2019

Received in revised form

27 June 2019

Accepted 13 July 2019

Available online 14 August 2019

Keywords:

Hydrogen absorption and desorption

Mg-based solid solution

Phase transition

CeF₃

Nanocomposite

Mechanical milling

ABSTRACT

This paper presents improving the hydrogen absorption and desorption of Mg(In) solid solution alloy through doped with CeF₃. A nanocomposite of Mg_{0.95}In_{0.05}-5 wt% CeF₃ was prepared by mechanical ball milling. The microstructures were systematically investigated by X-ray diffraction, scanning electron microscopy, scanning transmission electron microscopy. And the hydrogen storage properties were evaluated by isothermal hydrogen absorption and desorption, and pressure-composition-isothermal measurements in a temperature range of 230 °C–320 °C. The mechanism of hydrogen absorption and desorption of Mg_{0.95}In_{0.05} solid solution is changed by the addition of CeF₃. Mg_{0.95}In_{0.05}-5 wt% CeF₃ nanocomposite transforms to MgH₂, MgF₂ and intermetallic compounds of MgIn and CeIn₃ by hydrogenation. Upon dehydrogenation, MgH₂ reacts with the intermetallic compounds of MgIn and CeIn₃, forming a pseudo-ternary Mg(In, Ce) solid solution, which is a fully reversible reaction with a reversible hydrogen capacity ~4.0 wt%. The symbiotic nanostructured CeIn₃ impedes the agglomeration of MgIn compound, thus improving the dispersibility of element In, and finally improving the reversibility of hydrogen absorption and desorption of Mg(In) solution alloy. For Mg_{0.95}In_{0.05}-5 wt% CeF₃ nanocomposite, the dehydrogenation enthalpy is reduced to about 66.1 ± 3.2 kJ·mol⁻¹·H₂, and the apparent activation energy of dehydrogenation is significantly lowered to 71.9 ± 10.0 kJ·mol⁻¹·H₂, a reduction of ~73 kJ·mol⁻¹·H₂ relative to that for Mg_{0.95}In_{0.05} solid solution. As a result, Mg_{0.95}In_{0.05}-5 wt% CeF₃ nanocomposite can release ~57% H₂ in 10 min at 260 °C. The

* Corresponding author. School of Materials Science and Engineering, Xiamen University of Technology, Xiamen, 361024, PR China.

E-mail address: hczhong@xmut.edu.cn (H.C. Zhong).

<https://doi.org/10.1016/j.ijhydene.2019.07.114>

0360-3199/© 2019 Hydrogen Energy Publications LLC. Published by Elsevier Ltd. All rights reserved.

improvements of hydrogen absorption and desorption properties are mainly attributed to the reversible phase transition of Mg(In, Ce) solid solution combining with the multiphase nanostructure.

© 2019 Hydrogen Energy Publications LLC. Published by Elsevier Ltd. All rights reserved.

Introduction

Hydrogen as a clean and renewable energy carrier is an ideal substitution to current fossil fuels for satisfying the requirements of sustainable society [1,2]. One of key issues for the commercial applications of hydrogen energy, e.g., hydrogen fuel cell vehicles, is the efficient and safe hydrogen storage technologies [3]. The light-weight hydrides are generally regarded as the ultimate solution to the delivery and storage of hydrogen [2,3]. Over last decades, various hydrides, such as MgH_2 , LiBH_4 , NH_3BH_3 etc, have been developed as potential hydrogen storage materials [4–8]. Unfortunately, those high-capacity hydrides always suffer from over high thermodynamic stability and/or sluggish kinetics that result in impractical high operating temperature for on-board applications [9–11].

Magnesium as one of the most promising hydrogen storage materials, has many outstanding advantages, such as high capacity, good cycle stability, abundant resource, low cost, and environmentally friendly. But the high thermodynamic stability of MgH_2 ($-74.6 \text{ kJ}\cdot\text{mol}^{-1}\cdot\text{H}_2$) results in the high desorption temperature about 280°C under a pressure of 1 bar H_2 , and which will be further increased by the unfavorable kinetics due to the high activation energy barriers [12,13]. Recently, tremendous efforts have been made to lower the desorption temperature and improve the kinetics, such as alloying [13–16], doping catalysts [17–20], nanocrystallization and compositing [21–23], and achieving great progresses. For example, Yu et al. [24] synthesized MgH_2 nanocrystals together with catalytic Ni nanoparticles on the graphene, this MgH_2 nanocrystals presented fast hydrogen desorption rate at 200°C , and could be re-hydrogenated at room temperature. Using a similar synthetic route, Li et al. [25] prepared Mg_2NiH_4 single crystal nanoparticles covered by a thin layer ($\sim 3 \text{ nm}$) of MgO , this nanostructured Mg_2NiH_4 exhibited a low desorption activation energy of $31.2 \text{ kJ}\cdot\text{mol}^{-1}\cdot\text{H}_2$, and high structural stability during hydrogen absorption and desorption. It was considered that MgO played a critical role in keeping the thermal stability of Mg_2Ni single crystal, and improving the hydrogen absorption and desorption properties [25]. The dimension effects were also confirmed in MgH_2 @CA microspheres composite which released hydrogen with an activation energy of $114.8 \text{ kJ}\cdot\text{mol}^{-1}\cdot\text{H}_2$ [26]. It is generally regarded that nanocrystallization shortens the diffusion distance, decreases the thickness of H_2 -impermeable layer of MgH_2 , even weaken the Mg–H bonds, thus improving the kinetics. Doping catalytic additives, such as transition metals (Fe, Co, Ni, Cu, Ti, Nb, etc) [19,27,28], various nanosized metal oxides (TiO_2 , V_2O_5 , Cr_2O_3 , Fe_2O_3 , Nb_2O_5 , etc) [18,20,29], fluorides/halides (TlF_3 , TiCl_3 , LaF_3 , LaCl_3 , CeF_3 , CeCl_3 , etc) [30,31], and so on, is widely

used to enhance the de/hydrating kinetics. The comparative study indicated that elemental V had the best catalytic effect on dehydrogenation of MgH_2 among Ti, Mn, Fe and Ni [32]. For $0.75\text{Mg}-0.25\text{Ti}-\text{H}$ composite, the dehydrating activation energy was reduced to $53.6 \text{ kJ}\cdot\text{mol}^{-1}\cdot\text{H}_2$ [33]. Recently some multi-component oxides- $\text{TiVO}_{3.5}$, SrTiO_3 and $\text{BaFe}_{12}\text{O}_{19}$, were investigated as catalysts for de/hydrogenation of Mg [34–36]. Interestingly MgO was also found to have positive effect on enhancing the hydrogen absorption and desorption in some additives doped Mg systems, e.g. MgNiO_2 and MgFe_2O_4 doped MgH_2 systems [37,38]. Furthermore, the synergistic catalytic effects were found in some nanocomposite additives, e.g. the desorption temperature of MgH_2 was reduced to 210°C due to the introduction of symbiotic $\text{CeH}_{2.73}/\text{CeO}_2$ nanocomposite [39]. Other approaches to improve the kinetics include forming composites with other hydrogen storage materials or reactive additives, e.g. AlH_3 , ZrFe_2H_x , ZrMn_2 [23,40,41]. For example, $\text{MgH}_2 + 10 \text{ wt\% nano-ZrMn}_2$ composite showed a low desorption temperature of 181.9°C , and reduced dehydrogenation activation energy $\sim 83 \text{ kJ}\cdot\text{mol}^{-1}\cdot\text{H}_2$ [41]. Although crucial progresses have been achieved in improving the kinetics, the thermodynamic destabilization of MgH_2 is still facing big challenge at present.

With respect to thermodynamic destabilization, several strategies, namely nanostructuring, compositing with reactive additives, and alloying, have been employed [6,9,12,13,15,42,43]. Theoretically the stability of MgH_2 can be obviously lowered when the crystal size is reduced to less than 1.3 nm [44]. Nevertheless it is difficult to prepare this nanostructured Mg/MgH_2 . Furthermore, owing to the high surface energy, the original nanoparticles always tend to grow and aggregate, which is particularly obvious during the consecutive thermal treatments for H_2 absorption and desorption, based on the solid-state reactions involving mass transport, leading to a quick loss of the nanostructured morphology and continuing deterioration of storage properties. Another innovative method is altering the de/hydrating reaction pathways. Representative example is MgH_2 -Si system, which shows a significantly reduced dehydrating enthalpy of $36.4 \text{ kJ}\cdot\text{mol}^{-1}\cdot\text{H}_2$ due to the changed reaction route owing to the formation of Mg_2Si [42]. However, the reverse reaction was severely restricted by the high stability of Mg_2Si [42]. Additionally, forming intermetallic compounds by alloying with metal elements (e.g. Mg_2Ni , Mg_3MnNi_2) are effective approaches to tune the thermodynamics. Unfortunately these approaches are always suffered from a severe penalty of large capacity losses [45].

Mg -based solid solutions, performed minor modulations to the structure and composition of Mg , could be an alternative choice to avoid excessive capacity loss. Numerous works

demonstrated the improvements of hydrogen storage properties for Mg-base solid solutions, such as Mg–Ti/Co/Ni BCC/FCC structure solid solutions, metastable Mg–Y and Mg–Y–Ni supersaturated solid solutions by rapid solidification, and the equilibrium Mg–Li and Mg–Sc solid solutions [46–49]. However, those Mg-based solid solutions, whether in equilibrium or non-equilibrium state, could not recover from the hydrogenated products consisting of elemental hydrides and/or intermetallic compounds [50]. For instances, the supersaturated Mg–Y–Ni and Mg–Y–Zn solid solutions were irreversibly decomposed to MgH_2 , YH_2/YH_3 , Mg_2NiH_4 and/or $\text{Mg}_2\text{Zn}/\text{MgZn}_2$ by hydrogenation [48,49], and the equilibrium Mg–Li solid solution was irrecoverably hydrogenated to MgH_2 and LiH [50]. To the best of our knowledges, most of Mg-based solid solutions for hydrogen storage were limited by the unavoidable phase separation and poor structural reversibility.

Recently, it was confirmed that Mg(In) solid solutions could reversibly absorb and desorb hydrogen with lowered dehydrogenating enthalpy [6,51]. However, the intermetallic compound of MgIn (precipitated by hydrogenation) was easy to agglomerate, thus resulting in composition inhomogeneous, and further lowering the reaction rate of reforming Mg(In) solid solution, which deteriorated the de/hydrogenating kinetics [51]. As far as we know, Rare-earth fluorides/halides were confirmed to have catalytic effects on hydrogen absorption and desorption of Mg based alloys. Ismai et al. investigated the catalytic effects of CeCl_3 and LaCl_3 on MgH_2 , and considered the in situ formed Ce/La–Mg alloys and MgCl_2 as active species to catalyze hydrogen absorption and desorption of Mg [52,53]. On the other hand, it was regarded that the addition of Rare-earth fluorides could modify the microstructures and reduce the agglomeration/growth of nano Mg particles, thus improving the hydrogen storage properties [31]. Herein, cerium fluoride (CeF_3) was doped to Mg(In) solid solution synthesized a nanocomposite of $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 by ball milling. It was found that the nanostructured intermetallic compound of CeIn_3 instead of cerium hydrides ($\text{CeH}_2\sim\text{CeH}_3$) formed by hydrogenation of $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite, and this nanostructured CeIn_3 could limit the agglomeration of MgIn. Upon dehydrogenation, pseudo-ternary Mg(In, Ce) solid solution formed with reduced dehydrogenating enthalpy of $66.1 \pm 3.2 \text{ kJ mol}^{-1} \text{ H}_2$, and crucially lowered apparent activation energy of $71.9 \pm 10.0 \text{ kJ mol}^{-1} \text{ H}_2$ comparing with that for Mg(In) solid solution [51]. The results provide a new approach to improve the hydrogen storage properties of Mg based alloys.

Experimental details

Mg(In) binary solid solution was prepared by sintering and subsequent ball milling process. Firstly, powder mixtures of elemental Mg and In (99.9% purity, 200 meshes, Grimm Advanced Materials Co., Ltd., China) with designed composition of $\text{Mg}_{0.95}\text{In}_{0.05}$ (atomic ratio) were homogenized by ball milling, then pressed into pellets and sintered for 5 h at 573 K in a tube furnace under the protection of high purity argon (99.9999%) atmosphere. Secondly, the pellets were pulverized and milled with 5 wt% CeF_3 (99.9% purity, 300 meshes, Alfa Aesar) on a planetary mill (QM-3SP2, China) under the

protection of high purity argon atmosphere. The weight ratio of powders to stainless steel balls was 1:50. To prevent temperature over rising, the milling program was interrupted for 30 min after continuously running for 30 min. Finally, a nanocomposite of $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 was gotten by ball milling for 20 h.

The powders X-ray diffraction (XRD) was performed on the PANalytical X'Pert MRD diffractometer with Cu-K α radiation ($\lambda = 1.54056 \text{ \AA}$). The morphology and phase distribution were observed by scanning electron microscope (SEM, ZEISS Sigma 500 attached OXFORD X-Max^N EDS) and scanning transmission electron microscopy (STEM, FEI TALOS F200S attached BRUKER Super-X EDS). The hydrogen storage properties were characterized by the measurements of pressure-composition isotherm (PCI) and isothermal hydrogen absorption and desorption on an automatic Sievert-type apparatus (homemade). The powders sample with a weight of 0.4000 g was sealed in a sample holder and loaded into a stainless steel vessel for the following hydrogen absorption and desorption measurements. Firstly, the apparatus pipelines system and sample chamber were evacuated for about 30 min. Then the program began to calibrate the volume of sample chamber at room temperature and target temperature using high purity argon. And then the measurements started according to the pre-set programs. Before the data collection, the sample was activated completely by undergoing 5 cycles of hydrogen absorption and desorption at 300 °C. The isothermal hydrogen absorption was carried out under an initial hydrogen pressure of 2.5 MPa. The hydrogen desorption kinetic measurements started in near vacuum condition.

Results and discussions

Morphology and de/hydrogenating transition

Fig. 1 presents the phase components of $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite in different states. Fig. 1(a) is the XRD

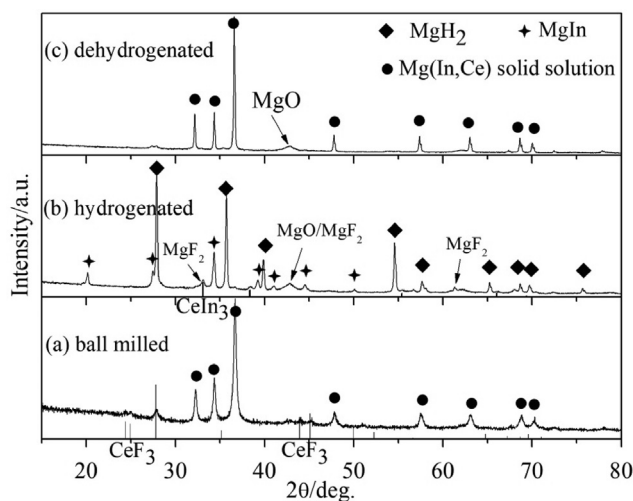


Fig. 1 – XRD patterns of ball milled $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite. (a) ball milled, (b) hydrogenated, (c) dehydrogenated.

pattern of ball milled powders, which shows two phases of primitive Mg(In) solid solution and the doped CeF_3 . By hydrogen absorption, the diffraction peaks of Mg(In) solid solution and CeF_3 were all disappeared accompanying with the appearances of the diffraction peaks of MgH_2 and intermetallic compounds of MgIn and CeIn_3 , and traces of MgO and MgF_2 could be also observed, as illustrated in Fig. 1(b). Fig. 1(c) is the XRD pattern of dehydrogenated $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite, in which only Mg together with trace of MgO could be observed. The intermetallic compounds of MgIn and CeIn_3 could have been decomposed by dehydrogenation, however there were no other new phases concerning In and Ce observed. So it is believed that MgIn and CeIn_3 have reacted with MgH_2 forming a pseudo-ternary Mg(In, Ce) solid solution by dehydrogenation, which is similar with the reversible de/hydrating mechanism of Mg(In) binary solid solution. However, there was an interesting phenomenon that the cerium fluoride (CeF_3) did not react with H_2 forming cerium hydrides (e.g. CeH_2 and CeH_3) as reported in other materials systems [30,31].

For understanding the microstructures of $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite, SEM and STEM were performed to observe the morphology and microstructures, the results are illustrated in Figs. 2–4. Fig. 2 is the back scattering electron images of $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite. From Fig. 2(a) and Fig. 2(b), it can be observed that the particle size of ball milled powders is in several micrometer degree. However, CeF_3 (the bright particles marked by arrows in Fig. 2(a)) was

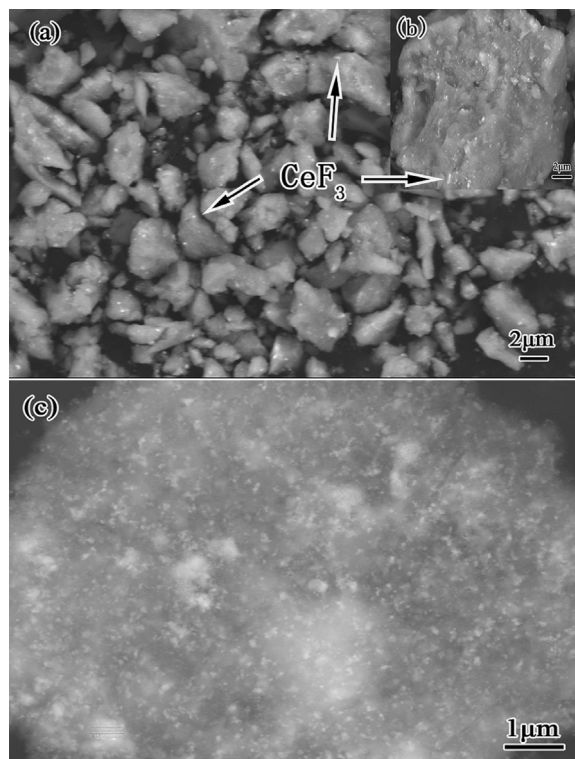


Fig. 2 – SEM (Back scattering electron) images of $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite. (a) and (b) ball milled powders, (c) hydrogenated $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite.

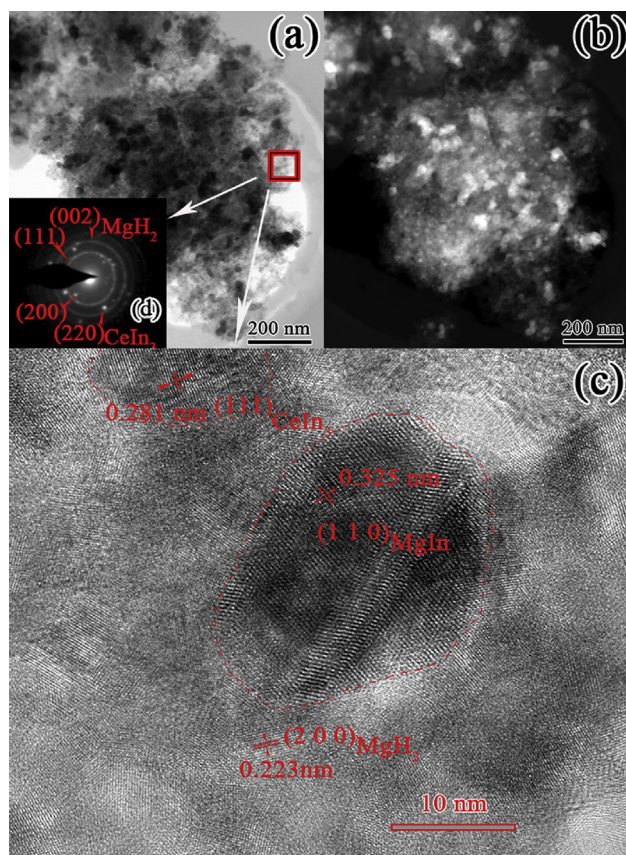


Fig. 3 – STEM images of the hydrogenated $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite, (a) bright field (BF) image, (b) high-angle annular dark field (HAADF) image, (c) high resolution image, (d) selected area electron diffraction patterns.

milled to nano size. Fig. 2(b) is the enlarged one particle. It shows that the CeF_3 nanoparticles are homogeneously dispersed in the Matrix of Mg(In) solid solution. Fig. 2(c) shows the morphology of the hydrogenated $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite. The bright nanoparticles are the intermetallic compounds of MgIn and CeIn_3 precipitated by hydrogenation. From Fig. 2(c) it is obviously observed that MgIn and CeIn_3 are homogeneously dispersed in the matrix of MgH_2 , and keeping high nanostructure stability during the hydrogen absorption and desorption process. Comparing with Mg(In) binary solid solutions, for the $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite the precipitated MgIn is much smaller in particle size and disperses more homogeneously in the matrix of MgH_2 , indicating that the agglomeration of MgIn is constrained by the symbiotic intermetallic compound of CeIn_3 . Fig. 3(a) and (b) are the bright field (BF) and high-angle annular dark field (HAADF) images for the hydrogenated $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite, which further confirm that the intermetallic compounds of MgIn and CeIn_3 are nanostructure and dispersively embed in the matrix of MgH_2 . Fig. 3(c) and (d) are the high resolution transmission electron image and selected area electron diffraction patterns respectively, from which MgH_2 , MgIn and CeIn_3 were all confirmed in the hydrogenated $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite. The results are consistent with the XRD analysis as shown in Fig. 1 (b).



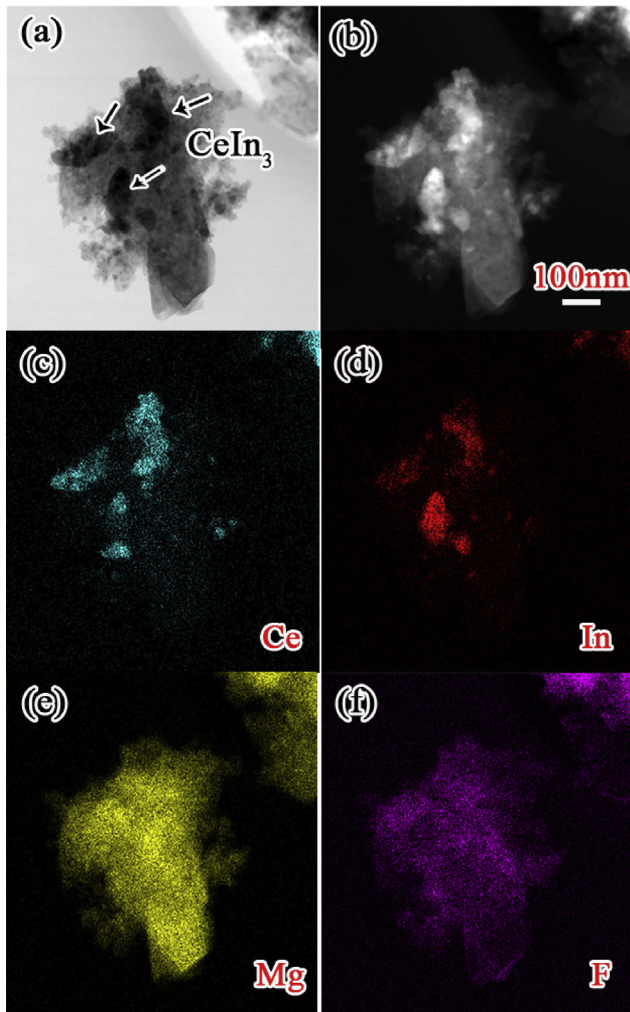


Fig. 4 – STEM images together with the corresponding element mapping for hydrogenated $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite. (a) BF image, (b) HAADF image.

Additionally the amorphous/nanocrystalline MgH_2 is found around the hydrogenation precipitates (MgIn or CeIn_3). Fig. 4 illustrates the BF and HAADF images together with the corresponding element mapping for the hydrogenated $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite. Fig. 4(a) is the BF image, and Fig. 4(b) is the corresponding HAADF image. Fig. 4(c) is the mapping of element Ce, which is highly overlapped with the mapping of element In (Fig. 4(d)), indicating that the dark particles in Fig. 4(a) (corresponding to the bright particles in Fig. 4(b)) are the intermetallic compound of CeIn_3 . The mapping of Mg (Fig. 4(e)) and F (Fig. 4(f)) confirms the existence of MgF_2 which covers on the surface of the particles with nanostructure. The SEM and STEM analysis reveal that the intermetallic compound of CeIn_3 is nanostructure, which benefits to inhibit the growth of MgIn and MgH_2 .

Based on the above phase analysis, it is considered that the ball milled $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite firstly absorbs hydrogen to transform to MgH_2 , MgF_2 and intermetallic compounds of MgIn and CeIn_3 ; conversely the decomposition of MgH_2 involves the intermetallic compounds of MgIn and CeIn_3 to form a pseudo-ternary $\text{Mg}(\text{In}, \text{Ce})$ solid solution,

which is a reversible de/hydrating reaction. The de/hydrating reaction of $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite can be described as:



Kinetics of hydrogen absorption and desorption

Fig. 5 shows the isothermal hydrating and dehydrating curves of $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite at different temperatures. The nanocomposite shows much faster hydrogen absorption rate than hydrogen desorption rate. But both the hydrating and dehydrating rates of $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite are faster than those for the corresponding $\text{Mg}_{0.95}\text{In}_{0.05}$ solid solution alloy without doped with CeF_3 . The hydrogen uptake content reached the maximum of 3.5 wt% in 20 min at 230 °C, but it only needed about 10 min to absorb 3.5 wt% H_2 when the hydrating temperature was elevated to 260 °C. However, it needed more than 30 min to release hydrogen at 260 °C. On the other hand, from Fig. 5(a) it can be

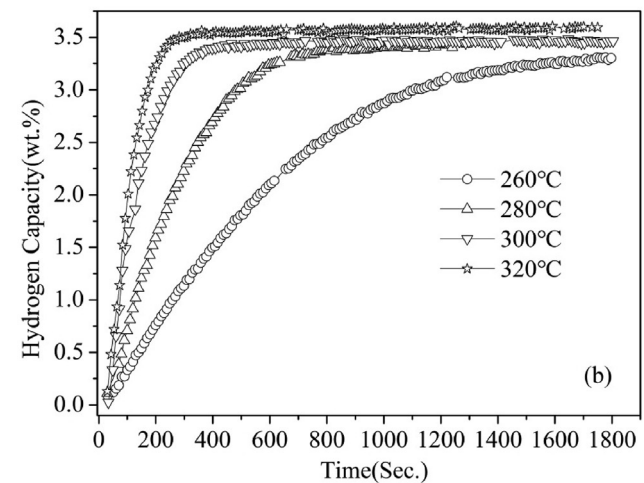
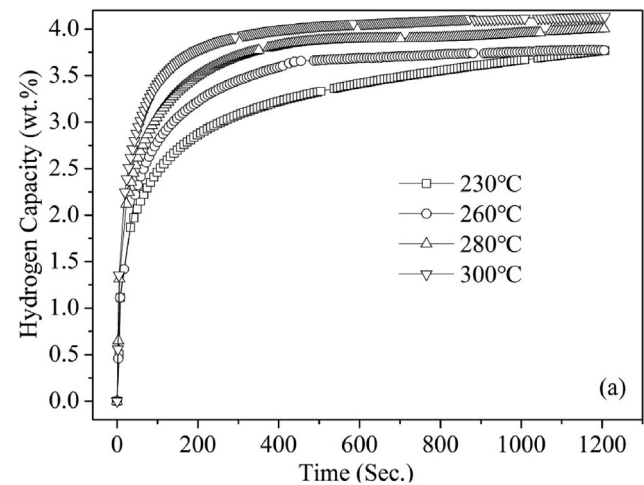


Fig. 5 – Isothermal hydrogen absorption and desorption of $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite. (a) hydrogen absorption, (b) hydrogen desorption.

observed that the hydrogen uptake content has an obvious increase (increasing to about 4.0 wt%) with the improvement of hydriding kinetics when the temperature increased to 280 °C, indicating a progress of the hydrogenation degree. It is well known that the diffusion rate of H atoms is far lower in MgH₂ than in Mg [24]. So the hydrogen absorption will be impeded and result in incomplete hydrogenation when the surface of powders is covered by a continuous layer of impermeable MgH₂. However the diffusion rate can be accelerated by the elevation of reaction temperature. And it could be also related to the formation of Mg(H_xF_{1-x})₂ as reported by Pighin [54]. As a result, the hydrogen uptake content increased with the elevated hydriding temperature in the experiment. For dehydrogenation, the reaction had a significant speeded-up by elevating the dehydriding temperature, as shown in Fig. 5(b). The hydrogen release time was reduced from 30 min to about 10 min by elevating the temperature from 260 °C to 280 °C.

The sorption datum shown in Fig. 5(a) were fitted using Johnson-Mehl-Avrami-Kolmogorov (JMAK) equation:

$$\alpha = 1 - \exp(1 - \kappa t)^\eta \quad (3)$$

where α is the reaction fraction, κ is the reaction rate, t is the reaction time, and η is the reaction exponent. JMAK equation is turned into the linear form as:

$$\ln[-\ln(1 - \alpha)] = \eta \ln(\kappa) + \eta \ln(t) \quad (4)$$

the linear plots of α and t were gotten in Fig. 6(a), from which κ values of different temperature were achieved and used to calculate the apparent activation energy (E_a) by Arrhenius equation:

$$\kappa = K_0 e^{-\left(\frac{E_a}{RT}\right)} \quad (5)$$

It can be changed into the form as following:

$$\ln(\kappa) = -\frac{E_a}{RT} + \ln(K_0) \quad (6)$$

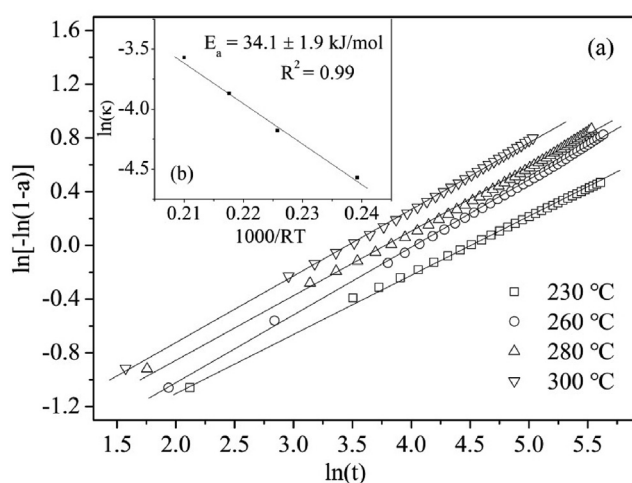


Fig. 6 – (a) the linear plots of $\ln[-\ln(1 - \alpha)]$ vs $\ln(t)$ and (b) the Arrhenius plot for hydrogen absorption of Mg_{0.95}In_{0.05}-5 wt% CeF₃ nanocomposite.

By this form the linear plots of $\ln(\kappa)$ and T^{-1} were achieved and illustrated in Fig. 6(b). The apparent activation energy of hydrogen absorption was calculated to be $34.1 \pm 1.9 \text{ kJ}\cdot\text{mol}^{-1} \text{ H}_2$ for Mg_{0.95}In_{0.05}-5 wt% CeF₃ nanocomposite, a notable decrease in comparing with the value of $48.1 \text{ kJ}\cdot\text{mol}^{-1} \text{ H}_2$ for Mg_{0.95}In_{0.05} solid solution [51]. Through the same method the apparent activation energy of hydrogen desorption was determined to be $71.9 \pm 10.0 \text{ kJ}\cdot\text{mol}^{-1} \text{ H}_2$ (as shown in Fig. 7), lowered about $73 \text{ kJ}\cdot\text{mol}^{-1} \text{ H}_2$ than $145 \text{ kJ}\cdot\text{mol}^{-1} \text{ H}_2$ for Mg_{0.95}In_{0.05} solid solution un-doped with CeF₃ [51].

The dehydriding mechanism of Mg_{0.95}In_{0.05}-5 wt% CeF₃ nanocomposite is similar with that of Mg_{0.95}In_{0.05} solid solution, the decomposition of MgH₂ involves the intermetallic compounds of MgIn and CeIn₃ to form pseudo-ternary Mg(In, Ce) solid solution and lease H₂. This means that the de/hydrogenation involves the diffusion of H atoms as well as In and Ce atoms in the Mg/MgH₂ lattice, which can be influenced by the microstructure characteristics, such as the grain/particle size, phase distribution and the interfaces. Previously it had been noticed that multi-phase microstructures with fine grain/particle size is beneficial to the diffusion of H and In atoms, and thus achieving kinetic improvement in the Mg–In–Al ternary system [51]. In the present work, the precipitated intermetallic compounds of MgIn and CeIn₃ were all nanostructure, and there were also some amorphous/nanocrystalline MgH₂, e.g. around the intermetallic compounds of MgIn and CeIn₃, as observed by STEM. Certainly these nanostructures are favorable for atom diffusing, thus accelerating the dehydriding reaction. On one hand, these nano grains also provide abundant boundaries/interfaces and defect sites which have been cited as important components for improving the kinetics of Mg-based materials [17,49]. On the other hand, the nanosized MgIn and CeIn₃ readily trigger the decomposition of MgH₂, once MgH₂ decomposes to elemental Mg and H₂, MgIn and CeIn₃ will incorporate the elemental Mg to form Mg(In, Ce) solid solution, which in turn further accelerates the decomposition of MgH₂ [6,51]. Therefore, the intermetallic compounds of MgIn and CeIn₃

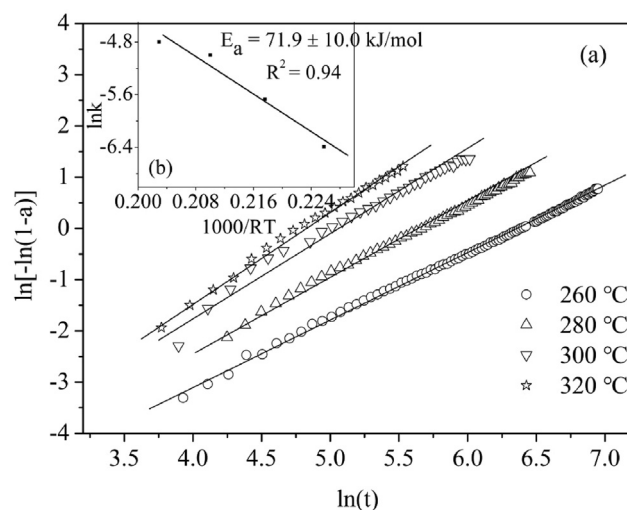


Fig. 7 – (a) the linear plots of $\ln[-\ln(1 - \alpha)]$ vs $\ln(t)$ and (b) the Arrhenius plot for hydrogen desorption of Mg_{0.95}In_{0.05}-5 wt% CeF₃ nanocomposite.

accelerate the decomposition of MgH_2 . Additionally, the surface of powders covered by a layer of amorphous MgF_2 , which could hinder the formation of continuous H-impermeable MgO , and help H atoms to penetrate to the internal of particles by forming $\text{Mg}(\text{H}_x\text{F}_{1-x})_2$. This amorphous MgF_2 possibly also has catalytic effects on hydrogen absorption and desorption of Mg as reported in Ref. [55]. At last but not the least, although cerium hydrides were not found in the hydrogenated $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite, however the multi-valent cerium could facilitate the diffusion and delivery of H atoms, thus accelerating the formation and decomposition of H_2 molecules [31,39]. That is to say the introduction of CeIn_3 plays an important role in improving the hydrogen absorption and desorption properties.

Thermodynamics of hydrogen absorption and desorption

It is expected that the reversible phase transition of $\text{Mg}(\text{In}, \text{Ce})$ solid solution benefits to destabilize MgH_2 as $\text{Mg}(\text{Al})$, $\text{Mg}(\text{In})$ and $\text{Mg}(\text{In}, \text{Al})$ solid solutions [6,13,51]. Generally the de/hydrating thermodynamics is evaluated through PCI measurements. Fig. 8 shows the PCI curves of $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite, and the comparison of PCI for $\text{Mg}_{0.95}\text{In}_{0.05}$ solid solution doped and un-doped with CeF_3 at 280 °C. For $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite, the lag of hydrogen absorption and desorption is reduced, and the plateau pressures are elevated, as illustrated in Fig. 8(b). And there was also another outstanding feature that about 0.5 wt% hydrogen released above the dehydrating plateau for $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite, which could be corresponding to the decomposition of amorphous MgH_2 around the intermetallic compounds of MgIn and CeIn_3 . The reduced lag is mainly attributed to the improved de/hydrating kinetics as discussed in above. However, the elevated plateau pressures definitely indicate a lowered thermodynamics of MgH_2 .

The equilibrium plateau pressure of metal hydrides is dependent on the reaction enthalpy (ΔH) and entropy (ΔS), both of which can be calculated by van't Hoff equation:

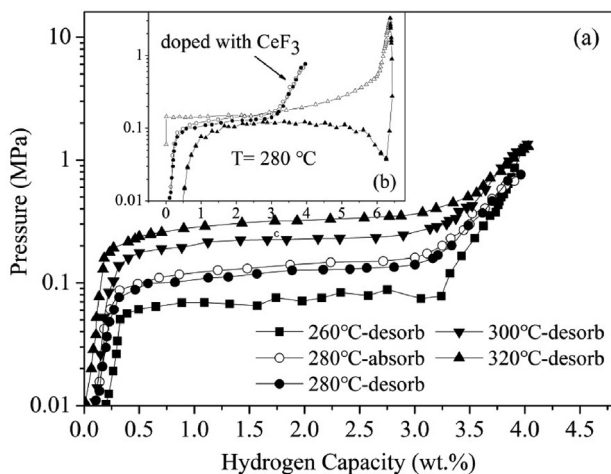


Fig. 8 – (a) the pressure-composition isotherm (PCI) curves of $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite, (b) the comparison of PCI for $\text{Mg}_{0.95}\text{In}_{0.05}$ solid solution doped and un-doped with 5 wt% CeF_3 .

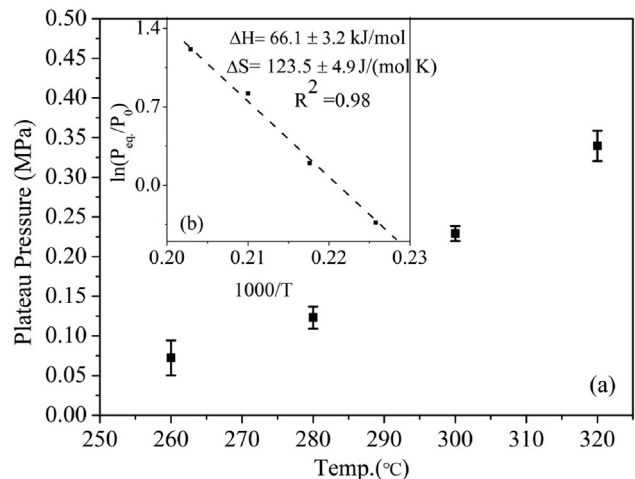


Fig. 9 – (a) the dehydrating plateau pressures and (b) van't Hoff plot for $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite.

$$\ln\left(\frac{P_{eq}}{p_0}\right) = \frac{\Delta H}{RT} - \frac{\Delta S}{R} \quad (7)$$

here, P_{eq} is the equilibrium plateau pressure, which was taken the average value of the dehydrating plateau pressures (corresponding to the pressure of midpoint at the plateau), the results are shown in Fig. 9(a), p_0 is the standard atmospheric pressure, R is the gas constant ($8.31 \text{ J K}^{-1} \text{ mol}^{-1}$), and T is the Kelvin temperature. The van't Hoff plot shows a linear relationship between the equilibrium pressures and the reaction temperatures as illustrated in Fig. 9(b). The calculated ΔH and ΔS for dehydrating reaction is $66.1 \pm 3.2 \text{ kJ} \cdot \text{mol}^{-1} \text{ H}_2$ and $123.5 \pm 4.9 \text{ J K}^{-1} \text{ mol}^{-1} \text{ H}_2$ respectively. The dehydrating enthalpy of $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite is lower than $68.1 \text{ kJ} \cdot \text{mol}^{-1} \text{ H}_2$ for $\text{Mg}_{0.95}\text{In}_{0.05}$ solid solution un-doped with CeF_3 [51]. The lowered dehydrating enthalpy could be mainly attributed to the altered reaction pathways of MgH_2 due to the formations of $\text{Mg}(\text{In}, \text{Ce})$ solid solution and the intermetallic compounds of MgIn and CeIn_3 , as Eq. (2). Recently, it was reported that the deformation of Magnesium lattice or plastic deformation could increase the hydrogen absorption and desorption plateau pressure and improve hydrogen absorption/desorption [56–58]. For $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt % CeF_3 nanocomposite, the dissolving of Ce and In (atomic radius larger than Mg) combining with the multiphase nanostructures generate severe lattice deformation, which helps to elevate the de/hydrating plateau pressures. And this deformation could also generate synergetic effects with the reversible phase transition on lowering the dehydrating enthalpy of MgH_2 .

Conclusions

The de/hydrating mechanism of $\text{Mg}_{0.95}\text{In}_{0.05}$ solid solution is changed by the introduction of CeF_3 through mechanical ball milling to form nanocomposite. $\text{Mg}_{0.95}\text{In}_{0.05}$ -5 wt% CeF_3 nanocomposite absorbs hydrogen transiting to MgH_2 , MgF_2 and the intermetallic compounds of MgIn and CeIn_3 . Upon

dehydrogenation, MgH_2 reacts with the intermetallic compounds of MgIn and CeIn_3 forming pseudo-ternary $\text{Mg}(\text{In}, \text{Ce})$ solid solution with reduced dehydriding enthalpy of $66.1 \pm 3.2 \text{ kJ}\cdot\text{mol}^{-1}\text{H}_2$ and significantly lowered dehydriding activation energy of $71.9 \pm 10.0 \text{ kJ}\cdot\text{mol}^{-1} \text{H}_2$. The symbiotic CeIn_3 benefits to impede the agglomeration of MgIn , which improves the reversibility of de/hydrogenation of $\text{Mg}(\text{In}, \text{Ce})$ solid solution, and enhances the hydrogen absorption and desorption. The lowered dehydriding enthalpy is mainly attributed to the reversible phase transition of $\text{Mg}(\text{In}, \text{Ce})$ solid solution and the multiphase nanostructures. In summary, the hydrogen storage properties of $\text{Mg}(\text{In})$ solid solution alloy could be significantly improved by doped with CeF_3 . And the results could serve as a new approach to improve the hydrogen storage properties of Mg based hydrogen storage materials.

Acknowledgements

This work was supported by the National Natural Science Foundation of China (51601090), the Natural Science Foundation of Fujian Province (2016J01266, 2018J01429), the Science and Technology Project of Education Department of Fujian Province (JZ160474), and the open fund of Fujian Provincial Key Laboratory of Functional Materials and Applications (Xiamen University of Technology).

REFERENCES

- [1] Salvi BL, Subramanian KA. Sustainable development of road transportation sector using hydrogen energy system. *Renew Sustain Energy Rev* 2015;51:1132–55.
- [2] Schlapbach L, Züttel A. Hydrogen-storage materials for mobile applications. *Mater Sust Energy* 2010;2:65–70. <https://doi.org/10.1142/7848>.
- [3] Lai QW, Paskevicius M, Sheppard DA, et al. Hydrogen storage materials for mobile and stationary applications: current state of the art. *Chem Sus Chem* 2015;8(17):2789–825.
- [4] Chen P, Xiong ZT, Luo JZ, Lin JY, Tan KL. Interaction of hydrogen with metal nitrides and imides. *Nature* 2002;420:302–4.
- [5] Vajo JJ, Skeith SL, Mertens F. Reversible storage of hydrogen in destabilized LiBH_4 . *J Phys Chem B* 2005;109(9):3719–22.
- [6] Zhong HC, Wang H, Liu JW, Sun DL, Zhu M. Altered desorption enthalpy of MgH_2 by the reversible formation of $\text{Mg}(\text{In})$ solid solution. *Scr Mater* 2011;65:285–7.
- [7] Qiu SJ, Ma XY, Wang ER, Chu HL, Huot J, et al. Enhanced hydrogen storage properties of $2\text{LiNH}_2/\text{MgH}_2$ through the addition of $\text{Mg}(\text{BH}_4)_2$. *J Alloy Comp* 2017;704:44–50.
- [8] Li YT, Ding XL, Wu FL, Sun DL, Zhang QA, Fang F. Enhancement of hydrogen storage in destabilized LiNH_2 with KMgH_3 by quick conveyance of N-containing species. *J Phys Chem C* 2016;120(3):1415–20.
- [9] Zhong HC, Xu JB. Tuning the de/hydriding thermodynamics and kinetics of Mg by mechanical alloying with Sn and Zn . *Int J Hydrogen Energy* 2019;44:2926–33.
- [10] Qiu SJ, Chu HL, Zou YJ, Xiang CL, Xu F, Sun LX. Light metal borohydrides/amides combined hydrogen storage systems: composition, structure and properties. *J Mater Chem A* 2017;5:25112–30.
- [11] Chen CG, Wang JL, Wang H, Liu T, Xu L, Li XG. Improved kinetics of nanoparticle-decorated Mg-Ti-Zr nanocomposite for hydrogen storage at moderate temperatures. *Mater Chem Phys* 2018;206:21–8.
- [12] Paskevicius M, Tian HY, Sheppard DA, Webb CJ, et al. Magnesium hydride formation within carbon aerogel. *J Phys Chem C* 2011;115:1757–66.
- [13] Zhong HC, Wang H, Ouyang LZ. Improving the hydrogen storage properties of MgH_2 by reversibly forming Mg-Al solid solution alloys. *Int J Hydrogen Energy* 2014;39:3320–6.
- [14] Li JD, Li B, Yu XQ, Zhao HJ, Shao HY. Geometrical effect in Mg -based metastable nano alloys with BCC structure for hydrogen storage. *Int J Hydrogen Energy* 2019. <https://doi.org/10.1016/j.ijhydene.2019.01.031>.
- [15] Lu YS, Wang H, Liu JW, Ouyang LZ, Zhu M. Destabilizing the dehydriding thermodynamics of MgH_2 by reversible intermetallics formation in Mg-Ag-Zn ternary alloys. *J Power Sources* 2018;396:796–802.
- [16] Zhou C, Fang ZZ, Lu J, Zhang X. Thermodynamic and kinetic destabilization of magnesium hydride using Mg-in solid solution alloys. *J Am Chem Soc* 2013;135:10982–5.
- [17] House SD, Vajo JJ, Ren C, Rockett AA, Robertson IM. Effect of ball-milling duration and dehydrogenation on the morphology, microstructure and catalyst dispersion in Ni-catalyzed MgH_2 hydrogen storage materials. *Acta Mater* 2015;86:55–68.
- [18] Chen M, Xiao XZ, Zhang M, Liu MJ, et al. Excellent synergistic catalytic mechanism of in-situ formed nanosized Mg_2Ni and multiple valence titanium for improved hydrogen desorption properties of magnesium hydride. *Int J Hydrogen Energy* 2019;44:1750–9.
- [19] Chen J, Xia GL, Guo ZP, Huang ZG, et al. Porous Ni nanofibers with enhanced catalytic effect on the hydrogen storage performance of MgH_2 . *J Mater Chem* 2015;3:15843–8.
- [20] Lan ZQ, Sun ZZ, Ding YC, et al. Catalytic action of Y_2O_3 @graphene nanocomposites on the hydrogen storage properties of Mg-Al alloys. *J Mater Chem* 2017;5:15200–7.
- [21] Lang CG, Ouyang LZ, Yang LL, Dai LY, Wu DF, Shao HY, Zhu M. Enhanced hydrogen storage kinetics in Mg@FLG composite synthesized by plasma assisted milling. *Int J Hydrogen Energy* 2018;43:17346–52.
- [22] Zhong HC, Wang H, Ouyang LZ, Zhu M. Microstructure and hydrogen storage properties of Mg-Sn nanocomposite by mechanical milling. *J Alloy Comp* 2011;509:4268–72.
- [23] Z Liu H, Wang XH, Liu YG, Dong ZH, et al. Hydrogen desorption properties of the $\text{MgH}_2\text{-AlH}_3$ composites. *J Phys Chem C* 2014;118(1):37–45.
- [24] Xia GL, Tan YB, Chen XW, Sun DL, et al. Monodisperse magnesium hydride nanoparticles uniformly self-assembled on graphene. *Adv Mater* 2015;27(39):5981–8.
- [25] Zhang JG, Zhu YF, Lin HJ, Liu YN, et al. Metal hydride nanoparticles with ultrahigh structural stability and hydrogen storage activity derived from microencapsulated nanoconfinement. *Adv Mater* 2017;29:1700760–5.
- [26] Peng DD, Ding ZM, Zhang L, Fu YK, Wang JS, Li Y, Han SM. Remarkable hydrogen storage properties and mechanisms of the shell-core MgH_2 @carbon aerogel microspheres. *Int J Hydrogen Energy* 2018;43:3731–40.
- [27] Xie XB, Chen M, Liu P, Shang JX, Liu T. Synergistic catalytic effects of the Ni and V nanoparticles on the hydrogen storage properties of Mg-Ni-V nanocomposite. *Chem Eng J* 2018;347:145–55.
- [28] Cui J, Liu J, Wang H, Ouyang LZ, Sun DL, Zhu M, et al. Mg-Tm (Tm: Ti, Nb, V, Co, Mo or Ni) core-shell like nanostructures: synthesis, hydrogen storage performance and catalytic mechanism. *J Mater A* 2014;2:9645–55.
- [29] Polanski M, Bystrzycki J. Comparative studies of the influence of different nano-sized metal oxides on the hydrogen sorption properties of magnesium hydride. *J Alloy Comp* 2009;486:697–701.

- [30] Lin HJ, Matsuda JK, Li HW, Zhu M, Akiba E. Enhanced hydrogen desorption property of MgH₂ with the addition of cerium fluorides. *J Alloy Comp* 2015;645: S392–S39.
- [31] Mao JF, Zou JX, Lu C, Zeng XQ, Ding WJ. Hydrogen storage and hydrolysis properties of core-shell structured Mg-MFx (M = V, Ni, La and Ce) nano-composites prepared by arc plasma method. *J Power Sources* 2017;366:131–42.
- [32] Liang G, Huot J, Boily S, Neste AV, Schulz R. Catalytic effect of transition metals on hydrogen sorption in nanocrystalline ball milled MgH₂-Tm (Tm=Ti, V, Mn, Fe and Ni) systems. *J Alloy Comp* 1999;292:247–52.
- [33] Korablov D, Besenbacher F, Jensen TR. Kinetics and thermodynamics of hydrogenation-dehydrogenation for Mg-25%TM(TM = Ti, Nb or V) composites synthesized by reactive ball milling in hydrogen. *Int J Hydrogen Energy* 2018;43:16804–14.
- [34] Zhang X, Shen ZY, Pan HG, et al. A novel complex oxide TiVO_{3.5} as a highly active catalytic precursor for improving the hydrogen storage properties of MgH₂. *Int J Hydrogen Energy* 2018;43:23327–35.
- [35] Yahya MS, Ismail M. Synergistic catalytic effect of SrTiO₃ and Ni on the hydrogen storage properties of MgH₂. *Int J Hydrogen Energy* 2018;43:6244–55.
- [36] Sazelee NA, Idris NH, Ismail M, et al. Synthesis of BaFe₁₂O₁₉ by solid state method and its effect on hydrogen storage properties of MgH₂. *Int J Hydrogen Energy* 2018;43:20853–60.
- [37] Ali NA, Idris NH, Ismail M, et al. Nanoflakes MgNiO₂ synthesised via a simple hydrothermal method and its catalytic roles on the hydrogen sorption performance of MgH₂. *J Alloy Comp* 2019;796:279–86.
- [38] Ali NA, Idris Nurul Hayati, Ismail M, et al. Nanolayer-like-shaped MgFe₂O₄ synthesised via a simple hydrothermal method and its catalytic effect on the hydrogen storage properties of MgH₂. *RSC Adv* 2018;8:15667–74.
- [39] Lin HJ, Tang JJ, Yu Q, Wang H, Ouyang LZ, et al. Symbiotic CeH_{2.73}/CeO₂ catalyst: a novel hydrogen pump. *Nano Energy* 2014;9:80–7.
- [40] Shahi RR, Bhatanagar A, Pandey SK, et al. MgH₂-ZrFe₂H_x nanocomposites for improved hydrogen storage characteristics of MgH₂. *Int J Hydrogen Energy* 2015;40:11506–13.
- [41] Zhang LT, Cai ZL, Yao ZD, Chen LX, et al. A striking catalytic effect of facile synthesized ZrMn₂ nanoparticles on the de/rehydrogenation properties of MgH₂. *J Mater Chem A* 2019;(7):5626–34.
- [42] Vajo JJ, Mertens F, Ahn CC, et al. Altering hydrogen storage properties by hydride destabilization through alloy formation: LiH and MgH₂ destabilized with Si. *J Phys Chem B* 2004;108:13977–83.
- [43] Yang T, Wang P, Xia CQ, Li Q, Liang CY, Zhang YH. Characterization of microstructure, hydrogen storage kinetics and thermodynamics of a melt-spun Mg₈₆Y₁₀Ni₄ alloy. *Int J Hydrogen Energy* 2019;44:6728–37.
- [44] Wagemans RW, van Lenthe JH, de Jongh PE, et al. Hydrogen storage in magnesium clusters: quantum chemical study. *J Am Chem Soc* 2005;127:16675–80.
- [45] Khan D, Zou JX, Zeng XQ, Ding WJ. Hydrogen storage properties of nanocrystalline Mg₂Ni prepared from compressed 2MgH₂-Ni powder. *Int J Hydrogen Energy* 2018;43:22391–400.
- [46] Kim H, Nakamura J, Shao H, Nakamura Y, Akiba E, et al. Insight into the hydrogenation properties of mechanically alloyed Mg₅₀Co₅₀ from the local structure. *J Phys Chem C* 2011;115:20335–41.
- [47] Shao H, Asano K, Enoki H, Akiba E. Preparation and hydrogen storage properties of nanostructured Mg–Ni bcc alloys. *J Alloy Comp* 2009;477:301–6.
- [48] Zhang QA, Zhang LX, Wang QQ. Crystallization behavior and hydrogen storage kinetics of amorphous Mg₁₁Y₂Ni₂ alloy. *J Alloy Comp* 2013;551:376–81.
- [49] Liu JW, Zou CC, Wang H, et al. Facilitating de/hydrogenation by long-period stacking ordered structure in Mg based alloys. *Int J Hydrogen Energy* 2013;38:10438–45.
- [50] Liang G. Synthesis and hydrogen storage properties of Mg-based alloys. *J Alloy Comp* 2004;370:123–8.
- [51] Wang H, Zhong HC, Ouyang LZ, Liu JW, Sun DL, Zhang QA, Zhu M. Fully reversible de/hydriding of Mg base solid solutions with reduced reaction enthalpy and enhanced kinetics. *J Phys Chem C* 2014;118(23):12087–96.
- [52] Ismail M, Mustafa NS, Juahir N, Halim Yap FA. Catalytic effect of CeCl₃ on the hydrogen storage properties of MgH₂. *Mater Chem Phys* 2016;170:77–82.
- [53] Ismai M. Effect of LaCl₃ addition on the hydrogen storage properties of MgH₂. *Energy* 2015;79:177–82.
- [54] Pighin SA, Coco B, Troiani H, Castro FJ, Urretavizcaya G. Effect of additive distribution in H₂ absorption and desorption kinetics in MgH₂ milled with NbH_{0.9} or NbF₅. *Int J Hydrogen Energy* 2018;43:7430–9.
- [55] Youn JS, Phan DT, Park CM, Jeon KJ. Enhancement of hydrogen sorption properties of MgH₂ with a MgF₂ catalyst. *Int J Hydrogen Energy* 2017;42:20120–4.
- [56] Skryabina N, Medvedeva N, Gabov A, et al. Impact of severe plastic deformation on the stability of MgH₂. *J Alloy Comp* 2015;645:S14–7.
- [57] Baldi A, Krishnan G, Kooi BJ, Dam B, Griessen R. Elastic versus alloying effects in Mg-based hydride films. *Phys Rev Lett* 2018;121:255503–11. 7.
- [58] Ngene P, Longo A, Mooij L, Bras W, Dam B. Metal-hydrogen systems with an exceptionally large and tunable thermodynamic destabilization. *Nat Commun* 2017;8:1846–51. 8.