

Catalysis Science & Technology

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: C. Mitchell, U. Terranova, A. M. Beale, W. Jones, D. J. Morgan, M. Sankar and N. H. De Leeuw, *Catal. Sci. Technol.*, 2020, DOI: 10.1039/D0CY01779E.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

COMMUNICATION

Received 00th
January 20xx,Accepted 00th
January 20xxDOI:
10.1039/x0xx00000xSurface Oxidised Fe-S catalyst for the Liquid Phase Hydrogenation of CO₂Claire E. Mitchell^a, Umberto Terranova^{a,b}, Andrew M. Beale^{c,d}, Wilm Jones^{c,d}, David J. Morgan^a, Meenakshisundaram Sankar^{a*}, Nora H. de Leeuw^{a,e*}

Rapidly increasing anthropogenic carbon dioxide (CO₂) emissions, coupled with irreversible climate change and depleting fossil fuel reserves, have significantly increased the drive for CO₂ utilisation. Iron sulfide as a catalyst for the hydrogenation of CO₂ has been discussed in the literature for decades, especially in an Origin-of-Life context, but little experimental evidence exists in the literature for its feasibility. Here we report the catalytic properties of pyrrhotite (Fe_{1-x}S) for the hydrogenation of CO₂ into formate. Advanced material characterisation methods in combination with computational studies have allowed us to identify surface S-Fe-O moieties as active sites for the reaction.

Due to the high natural abundance, low cost and low toxicity of iron and sulfur, the last decade has seen attention focussed on iron sulfide structures, including pyrrhotite (Fe_{1-x}S), pyrite (FeS₂) and greigite (Fe₃S₄), for their potential in green catalytic applications and energy storage. ¹⁻⁷ Fe-S phases have been hypothesised as potential membrane catalysts produced at hydrothermal vents, which reduce aqueous carbon dioxide (CO₂) in the formation of prebiotic molecules on the pathway to the emergence of life on early Earth, ⁸⁻¹⁰ owing to their unique similarities to iron and sulfur clusters within enzyme active sites. Following this lead, bio-inspired Fe-S catalysts such as FeS₂ ¹¹, Fe₃S₄ ¹ and Fe_{4.5}Ni_{4.5}S₈ ^{12,13} have been reported for the

electrochemical reduction of CO₂. However, in these systems the reduction potential of the H₂/2H⁺ couple is not sufficiently low to reduce CO₂ to formate (HCOO⁻), formaldehyde (HCHO) or similar oxygenates, ¹⁴ resulting in poor activity and low product yields. Thermal catalysis in an alkaline medium, using high pressure CO₂, can overcome such challenges, and can be potentially used in large scale industrial production.

Herein, we present the catalytic properties of iron sulfide-based materials for the hydrogenation of CO₂ to formate under alkaline hydrothermal conditions, proceeding *via* a HCO₃⁻ intermediate. After pyrite, pyrrhotite is the most common and abundant iron sulfide mineral in nature and one of the most stable Fe-S phases, occurring as an accessory mineral in many rocks and found in a wide range of hydrothermal deposits. ^{15,16} Pyrrhotite is highly sensitive to oxygen and upon contact with air or moisture, the surface of the material spontaneously oxidises through an established process. ¹⁶⁻¹⁹ Our work focuses on investigating the effect of oxidation on the catalytic efficacy of these iron sulfide materials. By enhancing the catalytic properties of these materials, *via* controlled calcination, we report new possibilities for a cheap, non-toxic, readily available pyrrhotite-based catalyst.

Pyrrhotite materials were prepared using an adapted method reported by Beal *et al.* ²⁰ (supplementary information). The synthesis methodology uses rapid *in situ* sulfidization of the decomposition product of Fe(acac)₂ with elemental sulfur to form Fe_{1-x}S ²¹⁻²³. Pyrrhotite can be identified as the majority phase, as confirmed by XRD, Figure 1a, presenting five major reflections at 2θ ≈ 31, 34, 44, 53 and 71 °, (JCPDS-PDF card no. 01-079-5974). Raman spectroscopy, Figure 1b, showing bands at 215, 277 and 384 cm⁻¹, also perfectly correlate with reported Raman spectra of natural pyrrhotite ²⁴. The XRD patterns in Figure S1 confirm the successful conversion of Fe(acac)₂ precursor to Fe_{1-x}S without any iron carbide formation. Elemental analysis revealed an Fe:S ratio of 0.96:1, (Table S1), which is consistent with the stoichiometry of hexagonal pyrrhotite ²⁵.

^a Cardiff Catalysis Institute, School of Chemistry, Cardiff University, Cardiff, CF10 4AT, United Kingdom; sankar@cardiff.ac.uk.

^b School of Postgraduate Medicine and Allied Health, Crewe campus, University of Buckingham, Crewe, CW1 5DU, United Kingdom.

^c Department of Chemistry, University College London, London, WC1H 0AJ, United Kingdom.

^d Research Complex at Harwell, Rutherford Appleton Laboratory, Harwell Science & Innovation Campus, Harwell, Didcot, OX11 0FA, United Kingdom.

^e School of Chemistry, University of Leeds, Leeds, LS2 9JT, United Kingdom; n.h.deleeuw@leeds.ac.uk.

Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. All data created during this research are openly available from the Cardiff University Research Portal. See DOI: 10.17035/d.2020.0098194792



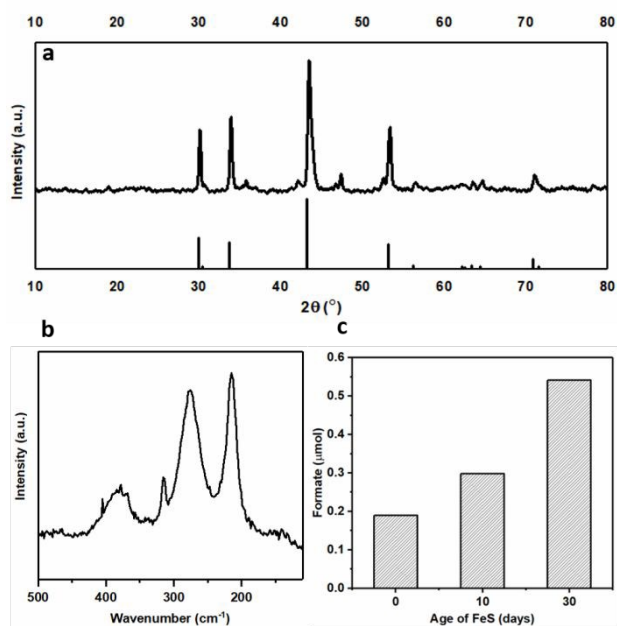


Figure 1: Freshly synthesised pyrrhotite analysed by (a) XRD with pyrrhotite reference peaks (JCPDS 01-079-5974 PDF file) and (b) Raman spectroscopy. (c) Effect of aging the pyrrhotite catalyst in air on formate production

The lab-synthesised pyrrhotite was tested for the liquid phase CO₂ hydrogenation in an aqueous 1M NaOH solution at 125 °C and at 20 bar pressure (CO₂:H₂, 1:1 at 25 °C), see supplementary information for full procedure. Previously, we have reported the hydrogenation of CO₂ using different alkaline solvents; NaOH, NaHCO₃ and Na₂CO₃²², and found that NaOH is the most suitable base for this reaction. When NaOH was used, all the formate is produced from CO₂ rather than from the alkaline salt.²² Based on these prior results, we have used NaOH in this study as well. After CO₂ dissolution, the pH of the reaction medium is ca. pH 6-8,²⁶ i.e. conditions favouring HCO₃⁻ species,²⁷ which is hence considered as the intermediate carbon species. Freshly synthesised pyrrhotite was found to be active for CO₂ hydrogenation, resulting in 0.19 μmols of formate after 3 days of reaction, Figure 1c. Interestingly, pyrrhotite aged in air at room temperature and pressure for 30 days displayed a much better activity, yielding 0.54 μmols of formate under identical reaction conditions, stimulating a hypothesis that oxidation improves the activity of the material. To investigate this suggestion further, fresh pyrrhotite was calcined at different temperatures and tested for CO₂ hydrogenation, Figure 2a. Calcination at 200 °C resulted in the most active catalyst, achieving the highest formate productivity of 1.00 μmol after 3 days, a significant improvement on the catalytic activity of pyrrhotite (0.29 μmol). However, increasing the calcination temperature above 200 °C resulted in reduced formate productivity (0.26 μmol for samples calcined at 250 °C). The first bar in Figure 2a is the productivity of fresh sample kept at room temperature (25 °C) for several days, hence the formate productivity is higher than the fresh catalyst presented in Figure 1c. XRD of a 200 °C calcined sample, Figure 2b, revealed the presence of a poorly crystalline sample of lower symmetry, comprising a number of phases although their identification is ambiguous. A comparison with JCPDS database entries suggests the 200 °C pattern may comprise contributions from the original pyrrhotite, marcasite (FeS₂) (JCPDS 01-074-1051 PDF file)

and Fe₂O₃ (JCPDS 01-085-0987 PDF file). However, an examination of the SEM before and after calcination (Figure S2) reveals no obvious formation of multiple phases (morphologies), but rather an overall reduction in particle size. The XRD pattern of a pyrrhotite sample calcined at 300 °C, Figure 2b, shows evidence of the presence of marcasite and iron oxide, Fe₂O₃. The formation of these new Fe-S or Fe-O phases in correlation with loss in activity implies that they are not the source of the enhanced activity. Increasing the temperature beyond 300 °C leads to the formation of primarily Fe₂O₃, as determined by XRD in Figure S3 and supported by TGA in Figure S4, which reveal a mass loss from 300 °C, implying Fe-S decomposition releasing SO₂. Commercial Fe₂O₃, Fe₃O₄ and FeSO₄ samples resulted in low formate productivity (Figure 2a), thus eliminating the

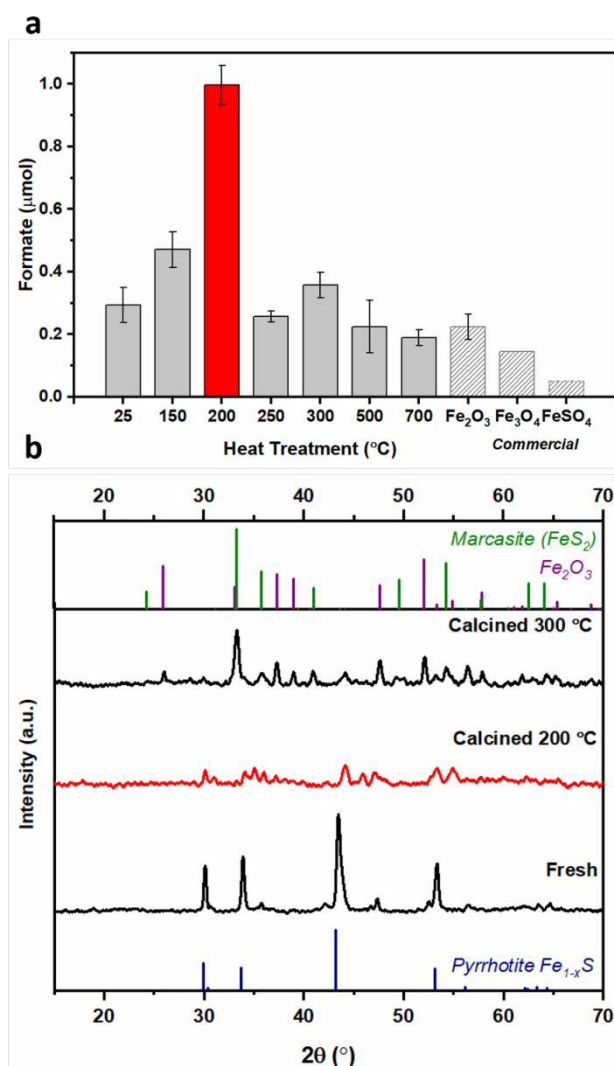


Figure 2: (a) Comparison of the effect of different calcination temperatures pyrrhotite catalyst for the hydrogenation of CO₂ to produce formate, Reaction conditions: catalyst: 20mg; 1M NaOH solution: 4 ml; pCO₂:H₂: (1:1) 20 bar; 125 °C for 3 days. (b) XRD spectra of pyrrhotite fresh, calcined at 200 °C, and calcined at 300 °C, compared to corresponding XRD patterns sourced PDF cards. (blue) – pyrrhotite, 01-079-5974; (green) – Marcasite, FeS₂, 01-074-1051; (purple) – Fe₂O₃, 01-085-0987.



possibility of their role as catalytic active site within our oxidised Fe-S catalyst. Heating pyrrhotite under an N₂ atmosphere at 200 °C also had little effect on the crystal structure of the pyrrhotite phase, and a reduced catalytic activity, most likely due to the absence of the surface oxide species (Figure S5). To understand the role of calcination on the structural properties of pyrrhotite and in turn its catalytic property, these materials were characterised by several spectroscopic and microscopic methods.

XPS spectra of a fresh pyrrhotite sample and a sample calcined at 200 °C are presented in Figure 3 a-d. The atomic surface ratio of Fe:S:O in a fresh pyrrhotite sample was 12:39:49, but in the calcined sample it was approximately 13:7:80. As pyrrhotite is highly air sensitive, exposure to oxygen forces Fe atoms to diffuse from the interior to the surface to combine with oxygen,²⁸ altering the surface Fe/S ratio. Calcination increased the rate of oxidation to form an oxygen-rich surface with an atomic percentage of 80%. TGA (Figure S4) revealed no significant mass loss at 200 °C, and therefore no sulfur had been removed from the surface as SO₂. Fe 2p analysis of fresh pyrrhotite surfaces, shown in Figure 3a, reveals three distinct peaks at 710.1-713.3 eV, indicating the presence of oxidised iron. Another, smaller peak at 707.3 eV, indicates the presence of Fe(II)-S species^{28,29}. Calcination of pyrrhotite increases the amount of surface Fe-O species and depletes surface Fe-S species (Figure 3b), calculated from the atom concentrations listed in Table S1. The S 2p spectrum (Figure c, d) is fitted with a doublet representing the spin-orbit splitting of S 2p_{3/2} and S 2p_{1/2} lines. They show a dominance of monosulfide (S²⁻) with peaks at 161.2 eV (2p_{3/2}), but also disulfides (S₂²⁻) with peaks at 162.2 eV (2p_{3/2}), indicating the presence of S-Fe bonds. Also shown are polysulfides (S_n²⁻) at 163.2 eV and elemental sulfur (164.1 eV). Finally, S 2p_{3/2} peaks are detected at binding energies of 166.6 and 168.2 eV, corresponding to SO₃²⁻ and SO₄²⁻ species, respectively. All mentioned binding energy values are similar to those reported by Pratt *et al.*²⁸ and Buckley *et al.*²⁹. Calcination at 200 °C, Figure 3d, reveals an increase in SO_x species, whilst the monosulfides decrease

in concentration with an increase in disulfides. The migration of Fe towards the surface to combine with oxygen, is evidenced by Fe-S (monosulfide) bond cleavage, leaving Fe vacancies within the structure and forcing the remaining Fe(II)-S to form disulfide bonds,^{17,28} as evident in Table S2. The formation of S-S bonds requires the oxidation of some sulfide (S²⁻) to S⁰, hence the increase in elemental sulfur²⁸. These results suggest a surface of an oxide/hydroxide-rich layer with a small concentration of surface iron sulfide, and a sulfide-rich layer buried beneath the surface. As shown, calcining the catalyst from 200 °C to 300 °C causes a large drop in its activity. XPS reveals pyrrhotite calcined at 300 °C (Figure S6) has an atomic surface ratio of Fe:S:O at approximately 19:4:77, a dominantly iron oxide surface with a diminished sulfur content from 7% at 200 °C calcination to 4%. These results demonstrate that a significant amount of sulfur within an oxygen dominant surface is crucial for facilitating optimum catalytic activity. Hence, following our previous work with pyrrhotites^{30,31}, density functional theory calculations have been employed to explore the role of sulfur atoms in the reduction of HCO₃⁻, which is the dominant reactant species under the reaction conditions.

Previous computational investigation on a different iron sulfide - mixed-valence Fe₃S₄ greigite material – has reported that the aqueous phase reduction of HCO₃⁻ to HCOO⁻ proceeds *via* the transfer of the OH⁻ species from a bridging adsorbate to the surface¹. The remaining CO₂ molecule is activated to a bent geometry, which undergoes subsequent hydrogenation on the carbon atom. Similar to greigite, our findings have determined that the most stable adsorption of HCO₃⁻ on a fully oxidised pyrrhotite surface (termination A, Figure S7a) corresponds to a bridging vertical geometry, with an adsorption energy of -2.34 eV and Fe-O distances of 2.01 Å (Figure 4a). However, we calculated that a considerable energy penalty of 2.08 eV was associated with the transfer of the OH group to the surface (Figure S8), which makes the greigite pathway thermodynamically unlikely, at least on the fully oxidised FeS (01-10) surface. Alternatively, the carbon atom can be attacked by a surface hydrogen, which reacts with the HCO₃⁻ hydroxyl group to eliminate a water molecule and the resulting CO₂ molecule can then be hydrogenated to HCOO⁻. A similar pathway has been reported for the hydrogenation of HCO₃⁻ on nickel catalysts³². To investigate this pathway, we optimised the first H₂CO₃⁻ intermediate, i.e. a structure where the carbon is hydrogenated and in a tetrahedral arrangement (Figure 4b). The corresponding energy was 1.41 eV higher than the reactant configuration, while the high activation energy of 2.61 eV was again in line with the low efficiency of the fully oxidised surface. Interestingly, we found that the subsequent elimination of H₂O (Figure S9) is endothermic by only 0.39 eV, with a relatively low activation barrier of 1.25 eV which we would not expect to hinder the reaction, suggesting that the preceding carbon hydrogenation is the rate-limiting step.

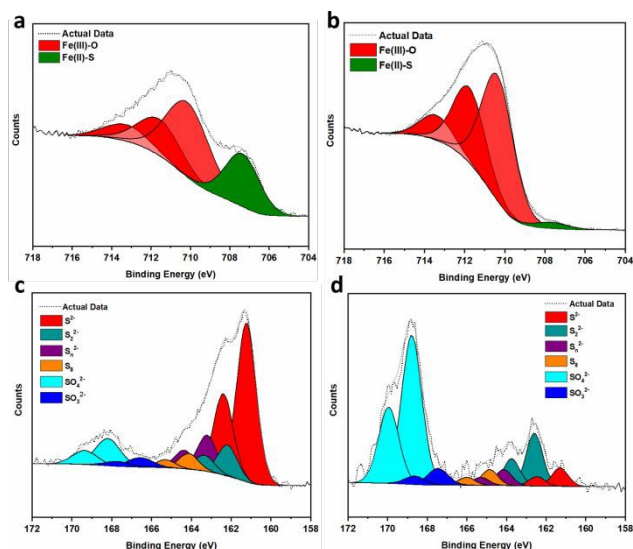


Figure 3: (a-d) XPS spectra of fresh and calcined samples (a) Fe2p, Fresh (b) Fe2p, Calcined 200 °C (c) S2p, Fresh (d) S2p, Calcined 200 °C. Plot details in (Table S2).



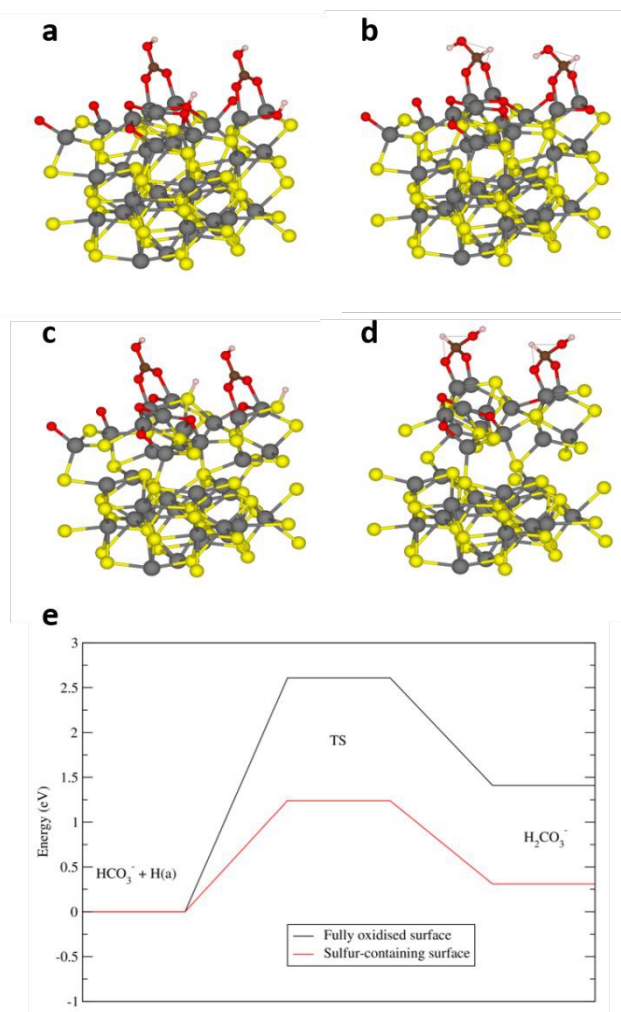


Figure 4: Adsorption (a & c) and hydrogenation (b & d) structures of HCO_3^- on the fully oxidised termination A (a & b) and sulfur-containing termination B (c & d) of FeS stoichiometric pyrrhotite. Colour code: Fe-grey, S-yellow, O-red, C-brown, H-white. (e) Energetics of the carbon hydrogenation step on the fully oxidised termination A and sulfur-containing termination B surface showing the position of reactants (HCO_3^-), products (H_2CO_3^-) and transition states (TS). The hydrogen species on the surface of the reactant configurations is indicated with H(a).

A sulfur-containing surface (termination B, Figure S7b) leads to a very different scenario. The adsorption of HCO_3^- , with an energy of -1.75 eV, is still favoured, but the presence of the bulkier sulfur atom bends the adsorbate (Figure 4c). In addition, the sulfur-bound hydrogen is closer to the carbon than the oxygen-bound hydrogen in termination A, which opens up the possibility of an alternative path for the hydrogen transfer leading to a tetrahedral carbon intermediate (Figure 4d), which is only 0.31 eV higher in energy than the HCO_3^- reactant. Furthermore, its activation energy barrier of 1.24 eV is significantly reduced compared to the 2.61 eV reported above for termination A, which clearly highlights the importance of surface sulfur atoms in the HCO_3^- reduction process, as illustrated in the diagram of Figure 4e.

To gain more understanding of the bulk structure, XAFS was employed. Data of fresh pyrrhotite, calcined at 200°C and calcined at 300°C , as well as a Fe_2O_3 reference are presented in Figure e & f. XANES analysis provided the opportunity to study the oxidation state of the Fe K-edge (Figure 5a). First to note is a very characteristic pre-edge (feature A) from the contribution of the Fe $1s \rightarrow 3d$ transition.³³ There is a shoulder to the edge (B), indicating the coordination between Fe and S and representing the normally forbidden Fe $1s \rightarrow 4s$ transition, which becomes more accessible, because the S $3p$ orbital overlap contributes p character to the Fe $4s$ orbital.³⁴ There is also white line intensity (C), corresponding to the first dipole-allowed Fe $1s \rightarrow 4p$ transition.^{35,36} Upon calcination at 200°C , there is a shift towards lower energy of feature B, indicating that iron is oxidising upon calcination from Fe(II) to Fe(III), in particular losing Fe-S character and acquiring more O ligands. This finding is re-enforced by the Fourier Transform EXAFS from a shift in radial distance at 2.2 \AA , indicated in Figure 5b. Calcination causes a small decrease in radial distance and a broader peak, indicating a mixture of Fe-S and Fe-O bonds. This effect is created owing to the fact that Fe(II) and S^{2-} are larger ions than Fe(III) and O^{2-} , therefore exhibiting a larger radial distance than Fe-O. Fe-S retains a bond distance in the range of $2.37\text{--}2.72 \text{ \AA}$, whereas the Fe-O bond distance ranges from $1.81\text{--}1.93 \text{ \AA}$. Our results show fresh pyrrhotite and Fe_2O_3 exhibit radial distances of 2.21 \AA and 1.78 \AA respectively, which are phase uncorrected results, hence the slight difference with actual Fe-O and Fe-S radial distances. The Fourier transform EXAFS reveals a particularly interesting feature: When the sample is calcined at 300°C , a peak at $\sim 2.8 \text{ \AA}$ starts to form. As this peak is also present in Fe_2O_3 , it can be assigned as the Fe-Fe

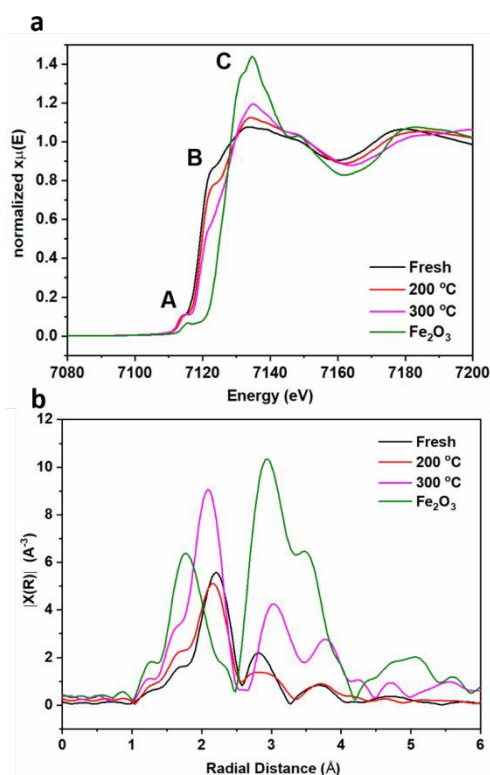


Figure 5: XAS data of Fe K-edge including (a) XANES and (b) Fourier Transform EXAFS for pyrrhotite samples; fresh (black), 200°C calcination (red), 300°C calcination (pink) and Fe_2O_3 reference sample (green). Blue arrows indicate direction of increasing oxygen ligands.



scattering component, consistent with the formation of bulk Fe₂O₃ from XRD. This peak is not present in the fresh and 200 °C calcined samples, showing that they do not contain iron oxide/iron hydroxide species. We have already confirmed that the 200 °C calcined sample shows that iron oxidation has occurred, whereas the shoulder edge B indicates Fe-S character, which together we suggest to be evidence for the formation of S-Fe-O species. Increasing the calcination temperature to 300 °C separates these species into separate Fe-O and Fe-S domains (as seen from the peak at ~2.8 Å). Since the formation of these Fe-O and Fe-S domains corresponds to a drop in the catalytic activity, S-Fe-O is a likely active species in this catalyst, corresponding well with the DFT calculations.

Conclusions

We have reported the synthesis of pyrrhotite (Fe_{1-x}S) and its catalytic activity towards the hydrogenation of CO₂ to formate under mild hydrothermal conditions, which is optimised by calcination. XPS and XAFS analysis has determined that oxidation of surface Fe-S species to form S-Fe-O species has a positive effect on the catalytic efficacy. Density functional theory calculations confirmed that the unique S-Fe-O interaction is critical in the carbon hydrogenation reaction, lowering the activation energy compared to the fully oxidised surface. The results from our preliminary investigation on the catalytic application of the Fe-S material, reported in this communication, is both exciting and promising. Further fine-tuning of this Fe-S material, inspired by the results presented here, has the potential to produce a more efficient, cheap and sustainable catalyst for CO₂ utilisation.

Acknowledgements

The authors thank the Cardiff University Scanning Electron Microscopy (SEM) and X-ray Absorption Spectroscopy (XPS) facilities, funded by EPSRC. We also thank the UK Catalysis Hub for allocating beamtime slots through the UK Catalysis Hub BAG allocation for X-ray acquisition of the transmission spectroscopic data at the Diamond synchrotron facility. This work was supported by the Engineering and Physical Sciences Research Council (grant EP/K009567/2) and used the ARCHER UK National Supercomputing Service (<http://www.archer.ac.uk>) via our membership of the UK's HEC Materials Chemistry Consortium, which is funded by EPSRC (EP/L000202). We acknowledge the support of the Supercomputing Wales project, which is part-funded by the European Regional Development Fund (ERDF) via Welsh Government. All data generated during this research are openly available from the Cardiff University Research Portal at <http://doi.org/10.17035/d.2020.0098194792>.

Conflicts of interest

There are no conflicts to declare.

References

- 1 A. Roldan, N. Hollingsworth, A. Roffey, H.-U. Islam, J. B. M. Goodall, C. R. A. Catlow, J. A. Darr, W. Bras, G. Sankar, K. B. Holt, G. Hogarth and N. H. de Leeuw, *Chem. Commun.*, 2015, **51**, 7501–7504.
- 2 C. Di Giovanni, A. Reyes-Carmona, A. Coursier, S. Nowak, J. M. Greneche, H. Lecoq, L. Mouton, J. Roziere, D. Jones, J. Peron, M. Giraud and C. Tard, *ACS Catal.*, 2016, **6**, 2626–2631.
- 3 R. Miao, B. Dutta, S. Sahoo, J. He, W. Zhong, S. A. Cetegen, T. Jiang, S. P. Alpay and S. L. Suib, *J. Am. Chem. Soc.*, 2017, **139**, 13604–13607.
- 4 M. S. Faber, M. A. Lukowski, Q. Ding, N. S. Kaiser and S. Jin, *J. Phys. Chem. C*, 2014, **118**, 21347–21356.
- 5 D. Susac, L. Zhu, M. Teo, A. Sode, K. C. Wong, P. C. Wong, R. R. Parsons, D. Bizzotto, K. A. R. Mitchell and S. A. Campbell, *J. Phys. Chem. C*, 2007, **111**, 18715–18723.
- 6 H. Li, J. Liu, J. Li, Y. Hu, W. Wang, D. Yuan, Y. Wang, T. Yang, L. Li, H. Sun, S. Ren, X. Zhu, Q. Guo, X. Wen, Y. Li and B. Shen, *ACS Catal.*, 2017, **7**, 4805–4816.
- 7 T. A. Pecoraro and R. R. Chianelli, *J. Catal.*, 1981, **67**, 430–445.
- 8 G. Wächtershäuser, *Syst. Appl. Microbiol.*, 1988, **10**, 207–210.
- 9 M. J. Russell, R. M. Daniel, A. J. Hall and J. A. Sherringham, *J. Mol. Evol.*, 1994, **39**, 231–243.
- 10 V. Sojo, B. Herschy, A. Whicher, E. Camprubí and N. Lane, *Astrobiology*, 2016, **16**, 181–197.
- 11 M. G. Vladimirov, Y. F. Ryzhkov, V. A. Alekseev, V. A. Bogdanovskaya, V. A. Otroshchenko and M. S. Kritsky, *Orig. Life Evol. Biosph.*, 2004, **34**, 347–360.
- 12 K. Pellumbi, M. Smialkowski, D. Siegmund and U. Apfel, *Chem. – A Eur. J.*, 2020, chem.202001289.
- 13 S. Piontek, K. Junge Puring, D. Siegmund, M. Smialkowski, I. Sinev, D. Tetzlaff, B. Roldan Cuenya and U.-P. Apfel, *Chem. Sci.*, 2019, **10**, 1075–1081.
- 14 N. Lane, *Cold Spring Harb. Perspect. Biol.*, 2014, **6**, a015982.
- 15 P. Toulmin III and P. B. Barton Jr, *Geochim. Cosmochim. Acta*, 1964, **28**, 641–671.
- 16 N. Belzile, Y.-W. Chen, M.-F. Cai and Y. Li, *J. Geochemical Explor.*, 2004, **84**, 65–76.
- 17 A. N. Buckley and R. Woods, *Appl. Surf. Sci.*, 1985, **22–23**, 280–287.
- 18 H. F. Steger and L. E. Desjardins, *Chem. Geol.*, 1978, **23**, 225–237.
- 19 M. P. Janzen, R. V. Nicholson and J. M. Scharer, *Geochim. Cosmochim. Acta*, 2000, **64**, 1511–1522.
- 20 J. H. L. Beal, P. G. Etchegoin and R. D. Tilley, *J. Solid State Chem.*, 2012, **189**, 57–62.
- 21 J. H. L. Beal, S. Prabakar, N. Gaston, G. B. Teh, P. G. Etchegoin, G. Williams and R. D. Tilley, *Chem. Mater.*, 2011, **23**, 2514–2517.
- 22 T. Li, H. Li, Z. Wu, H. Hao, J. Liu, T. Huang, H. Sun, J. Zhang, H. Zhang and Z. Guo, *Nanoscale*, 2015, **7**, 4171–4178.
- 23 A. Kirkeminde and S. Ren, *J. Mater. Chem. A*, 2013, **1**, 49–54.
- 24 Y. El Mendili, A. Abdelouas, H. El Hajj and J.-F. Bardeau, *RSC Adv.*, 2013, **3**, 26343.
- 25 F. Gronvold and H. Haraldsen, *Acta Chem. Scand.*, 1952, **6**, 1452–1469.
- 26 C. Mitchell, U. Terranova, I. AlShibane, D. J. Morgan, T.



- Davies, Q. He, J. Hargreaves, M. Sankar and N. H. De Leeuw, *New J. Chem.*, 2019, **43**, 13985–13997.
- 27 O. Pedersen, T. D. Colmer and K. Sand-Jensen, *Front. Plant Sci.*, 2013, **4**, 140.
- 28 A. R. Pratt, I. J. Muir and H. W. Nesbitt, *Geochim. Cosmochim. Acta*, 1994, **58**, 827–841.
- 29 A. N. Buckley and R. Woods, *Appl. Surf. Sci.*, 1985, **20**, 472–480.
- 30 U. Terranova and N. H. de Leeuw, *J. Phys. Chem. Solids*, 2017, **111**, 317–323.
- 31 U. Terranova, C. Mitchell, M. Sankar, D. Morgan and N. H. De Leeuw, *J. Phys. Chem. C*, 2018, **122**, 12810–12818.
- 32 C. S. He, L. Gong, J. Zhang, P. P. He and Y. Mu, *J. CO₂ Util.*, 2017, **19**, 157–164.
- 33 M. Wilke, F. Farges, P. E. Petit, G. E. Brown and F. Martin, *Am. Mineral.*, 2001, **86**, 714–730.
- 34 M. Womes, R. C. Karnatak, J. M. Esteva, I. Lefebvre, G. Allan, J. Olivier-Fourcade and J. C. Jumas, *J. Phys. Chem. Solids*, 1997, **58**, 345–352.
- 35 S. N. A. Zakaria, N. Hollingsworth, H. U. Islam, A. Roffey, D. Santos-Carballal, A. Roldan, W. Bras, G. Sankar, G. Hogarth, K. B. Holt and N. H. De Leeuw, *ACS Appl. Mater. Interfaces*, 2018, **10**, 32078–32085.
- 36 Y. Mikhlin, Y. Tomashevich, S. Vorobyev, S. Saikova, A. Romanchenko and R. Félix, *Appl. Surf. Sci.*, 2016, **387**, 796–804.

View Article Online
DOI: 10.1039/DOCY01779E



