

Synthesis of Composite Particles with Fe₃O₄ core and Ag Shell for the Development of Fingerprints

Ling-Yan Zhang* and Ting Chu

Forensic Identification Center, College of Criminal Investigation, Southwest University of Political Science and Law, Chongqing 401120, China. *E-mail: zly100@126.com
Received January 4, 2013, Accepted February 18, 2013

The Fe₃O₄-core and Ag-shell (Fe₃O₄@Ag nanoeggs) were prepared through the encapsulation of 3-aminopropyltriethoxysilane-coated magnetite nanoparticle in nano-Ag shell by a simple chemically controlled procedure. The Fe₃O₄@Ag nanoeggs were characterized by scanning electron microscopy, transmission electron microscopy, UV-vis spectrum and superconducting quantum interference device magnetometer, respectively. A detailed analysis is provided of how the hydrolysis and condensation of 3-aminopropyltriethoxysilane and the pH value are vital in fabricating the Fe₃O₄@Ag nanoeggs. The prepared Fe₃O₄@Ag nanoeggs possessed uniform size, improved monodispersity, stability against aggregation and high magnetization, which were utilized for the detection of latent fingerprints deposited onto different surfaces. The experimental results showed that the latent fingerprints developed with the Fe₃O₄@Ag nanoeggs powders exhibited excellent ridge details with minimal background staining.

Key Words : Fe₃O₄@Ag nanoeggs, Superparamagnet, Hydrolysis, Condensation, Latent fingerprints

Introduction

Latent fingerprints, which are present but invisible at a crime scene, are the most common form of fingerprint evidence in identification and generalized proof of identity.¹ In order to visualize a latent print, the application of physical or chemical techniques are required.² Fine, dry fingerprints powders are routinely used in the field of forensic fingerprint detection.³ However, this type of technique is limited in many aspects, especially in health and safety, selectivity, sensitivity.

Although, multifunctional magnetic nanoparticles, such as the core-shell nano-Au or nano-Ag combined with magnetic nanoparticles, which have many potential applications in various fields such as catalysis, biomedicine, magnetic resonance imaging, data storage, and environmental remediation.⁴⁻¹⁰ However, aggregation and precipitation of the nanoparticles often limited their application.¹¹ To fabricate multifunctional magnetic nanoparticles with good dispersity, Lee group¹² reported that TEOS was applied to protect the nanocrystals against agglomeration between the Fe₃O₄ nanoparticles. Subsequently 3-aminopropyltriethoxysilane (APTES) was used as a silane coupling agent to modify the surface of the Fe₃O₄@SiO₂ microspheres, and leave the terminal-NH₂ groups for nano-Au immobilization. Core-shell Fe₃O₄@Au nano-composites¹³ were prepared by layer-by-layer strategy based on the alternative assembly of oppositely-charged polyelectrolytes on to the colloidal templates. Caruntu's and O'Connor's groups¹⁴ and Quanguo He group¹⁵ have reported that APTES was hydrolyzed and condensed in the presence of Fe₃O₄ nanoparticles in ethanol under heating, resulting in silica-coated amine functionalized Fe₃O₄ nanoparticles. Then, the Fe₃O₄@Au nano-composites were prepared *via* sonolysis

of a solution mixture of HAuCl₄ and APTES-coated Fe₃O₄ nanoparticle with further drop-addition of sodium citrate. However, the complex preparation process, irregular core-shell structures and poor magnetic response have not been well solved in these reports.

In this study, the hydrolysis and condensation of APTES was completed in acidity. Then, Fe₃O₄ nanoparticles were functionalized by the as-prepared APTES at room temperature. After that, the Fe₃O₄@Ag nanoeggs were prepared through the encapsulation of APTES-coated Fe₃O₄ in nano-Ag shell. The Fe₃O₄@Ag nanoeggs have been fabricated through such simple, inexpensive method, and the as-obtained nanoeggs were allowed to detect the latent fingerprints deposited onto different surfaces. Successful results were obtained with detailed fingerprints offering a good contrast due to the Fe₃O₄@Ag nanoeggs with high magnetization and well-defined structure. Moreover, in comparison with commercial magnetic fingerprint powders, the Fe₃O₄@Ag nanoeggs exhibit health and safety, high selectivity, sensitivity as well as easiness of use in the forensic research arena, and hence are potentially useful in a broader range of applications.

Experimental

Materials. 3-Aminopropyltriethoxysilane, NH₃·H₂O and NaBH₄ were obtained from Sigma. NaOH, CH₃COOH, HCl, FeCl₃, FeCl₂ and AgNO₃ were purchased from Chemical Reagent Co, Sichuan, China. All other chemicals employed were of analytical grade and used as received, doubly distilled water was used throughout the experiments.

Instruments. The scan electron microscopy (SEM) images of the particles were obtained in a field emission scanning

electron microscopy (FE-SEM LEO 1530). The UV-vis spectrum was performed on a U-3310 (Hitachi LTD, Japan). Magnetic measurements were carried out using a superconducting quantum interference device magnetometer (HH-15 VSM, Nanking University Instrument Co., China). The detecting fingerprints was performed on a Video Spectral Comparator vsc 5000 (Foster and Freeman, LTD). Transmission electron microscopy (TEM) was performed on a FEI Tecnai G20 (FEI Co., America).

Synthesis of the Fe₃O₄ Nanoparticles. The Fe₃O₄ nanoparticles were first prepared following a method reported by the Yu-Chie Chen's method with slight modification.¹⁹ Briefly, a coprecipitation of ferric and ferrous chlorides (Fe/Fe ratio = 2.6) in 2.0 M HCl were added slowly into 1.5 M NaOH solution under vigorous stirring for 80 min at 80 °C and then was allowed to cool to room temperature in a nitrogen atmosphere. The resulting black product was washed several times with ethanol and dried at 60 °C for 6 h. The fabrication of Fe₃O₄@Ag nanoeggs was following a method reported by our previously method with major modification.¹⁷

Fabrication of the APTES-modified Fe₃O₄ Nanocomposites. For the functionalization of Fe₃O₄ nanoparticles with APTES, 1.0 mL Fe₃O₄ nanoparticles (~2.1 mg of Fe₃O₄/mL nanoparticles of ethanol) were dispersed in 8 mL ethanol for 2 h. After that, 9.15 mL APTES (0.45 mL of APTES mixed with 0.6 mL 25% CH₃COOH or 0.6 mL 25% NH₃·H₂O in 8 mL of ethanol), which was hydrolyzed and condensed under water bath vigorous stirring for 0.5 h, were added to the thus obtained Fe₃O₄ nanoparticles (9.15 mL). The mixture solution reacted under water bath vigorous stirring for 1.5 h. Then the precipitates were separated from the solution by a permanent magnet and washed repeatedly with ethanol for three times to remove the excess APTES, and redispersed in 8 mL of ethanol. The concentration of the APTES-modified Fe₃O₄ nanospheres was about 12.0 mg of Fe₃O₄/mL.

The Fabrication of Fe₃O₄@Ag Nanoeggs. Ag nanoparticles were synthesized according to the reported procedure¹⁸ with slight modification. Then, the 8 mL solution of APTES-modified Fe₃O₄ nanoparticles was mixed with 8 mL of the Ag nanoparticle solution (as seeds), and an adsorption time of 2 h was allowed. The excess Ag seeds were removed by three repeated magnetic separations, and then the particles were redispersed in 8 mL of ethanol. Eventually, a solid shell of Ag was formed onto the Ag-modified Fe₃O₄ magnetic nanocomposites by reducing aliquots of AgNO₃ (0.35 mL, 0.1 mM) with NaBH₄ (0.024 mL, 0.1 mM) in aqueous solution, the final products were collected by magnetic separation and dissolved in distilled water.

Results and Discussion

The Characterization of Different Nanoparticles. Observation by the SEM showed that the APTES-Fe₃O₄ nanoparticles obtained were dispersed, and nearly spherical in shape with an average diameter of 250 nm except a few big nanoparticles (Fig. 1(a)), and the Ag-modified Fe₃O₄ nano-

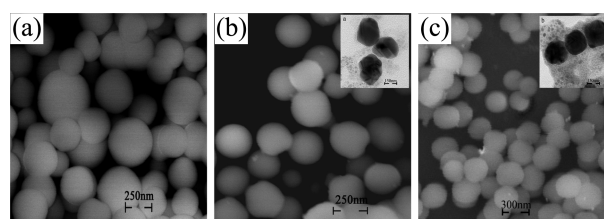


Figure 1. SEM of the APTES-coated Fe₃O₄ nanoparticles (a), Ag-modified Fe₃O₄ nanocomposite (b) and Fe₃O₄@Ag nanoeggs (c). (Inset)TEM images of the Ag-modified Fe₃O₄ (b) and Fe₃O₄@Ag nanoeggs (c).

composites (Fig. 1(b)) were larger (for about 280 nm) than APTES-Fe₃O₄ nanoparticles. Figure 1(c) indicated that the Fe₃O₄@Ag nanoeggs microspheres possess spherical shape with smooth surface, diameter of ~290 nm, more uniform size and morphology as well as excellent dispersibility than the Fe₃O₄@Au nanoeggs reported by Quanguo He.¹³ It showed that the formation of the shell of Ag was accomplished by reducing AgNO₃ using NaBH₄. This reduction chemistry has been found effective in making a uniform coating layer on Fe₃O₄ nanocomposites.^{19,20}

The representative TEM images of the Ag-modified Fe₃O₄ and Fe₃O₄@Ag nanoeggs were shown in Figure 1 insert. Compare with the Fe₃O₄@Ag nanoeggs (Fig. 1(b) insert), the Ag-modified Fe₃O₄ (Fig. 1(c) insert) possess the relatively poor size uniformity, which was similar to the SEM results.

UV-vis Spectroscopy and Superparamagnetic Characteristic. To further analyze the surface composition of different nanoparticles, UV-vis spectroscopy characterization was employed.^{20,21} Figure 2 confirmed the presence of Ag as the shell of the nanocomposite. Initial scans of APTES-coated Fe₃O₄ nanoparticles produced featureless spectra indicating an absence of surface plasmon resonance (Fig. 2(a)), when a layer of Ag seeds were attached onto APTES-coated Fe₃O₄ nanoparticles, an absorption peak developed at 385 nm (Fig. 2(c)). However, the peak was shifted to 425 nm (Fig. 2(b))

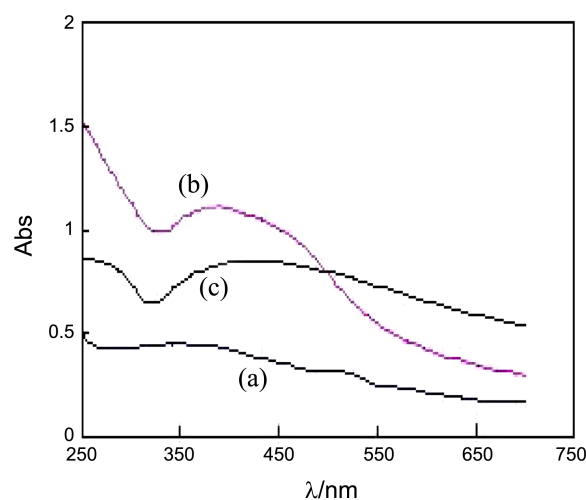


Figure 2. UV-vis absorption spectra of APTES-coated Fe₃O₄ nanoparticles (a), Fe₃O₄@Ag nanoeggs (b) and Ag-modified Fe₃O₄ nanoparticles (c).

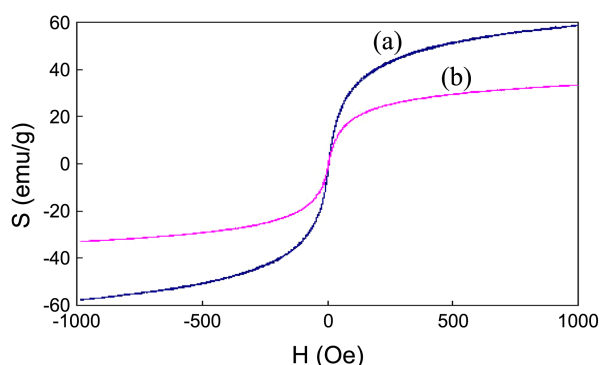


Figure 3. Magnetization curves of Fe_3O_4 nanoparticles (a) and $\text{Fe}_3\text{O}_4@Ag$ nanoeggs (b).

and broadened, owing to the particle-to-particle interactions which resulted from the higher packing density of the Ag particles after the deposition of Ag onto Ag-coated Fe_3O_4 nanoparticles.

Superparamagnetic Characteristic. The magnetic behavior of $\text{Fe}_3\text{O}_4@Ag$ nanoeggs is of importance for practical applications, and it is controlled in a straightforward fashion through the amount of Fe_3O_4 nanoparticles or NaBH_4 .²¹ Increasing the concentration of Fe_3O_4 nanoparticles attributed to much larger nanoparticles with higher magnetism. Meanwhile, the increase of NaBH_4 resulted in the thick shell of Ag on the Fe_3O_4 nanoparticles possessing much slighter magnetism. Therefore, 1.0 mL of 2.11 mg/mL Fe_3O_4 nanoparticles and 24 μL of 0.1 mM NaBH_4 were adopted for the fabrication of $\text{Fe}_3\text{O}_4@Ag$ nanoeggs while keeping all other parameters fixed.

Magnetic characterization using a magnetometer at 300 K showed that the Fe_3O_4 nanoparticles were superparamagnetic at room temperature before and after surface modification. The saturation magnetization of Fe_3O_4 nanoparticles, $\text{Fe}_3\text{O}_4@Ag$ nanoeggs were 60.8 (Fig. 3(a)) and 34.3 emu/g (Fig. 3(b)), respectively. Due to the additional cell that is extraordinary thin outside the Fe_3O_4 nanoparticles, the $\text{Fe}_3\text{O}_4@Ag$ nanoeggs exhibited higher magnetism comparison to the $\text{Fe}_3\text{O}_4@Au$ nanoeggs,^{22,14} slightly weaker magnetism compared to the Fe_3O_4 nanoparticles.

The Hydrolysis and Condensation of APTES. The Fe_3O_4 nanoparticles, which were prepared by coprecipitation of ferrous and ferric ions with $\text{NH}_3\cdot\text{H}_2\text{O}$ or NaOH , spontaneously aggregated to form magnetic clusters. Thus, it is generally required to protect the nanocrystals against agglomeration by inorganic and/or organic stabilizers. Several papers have reported that TEOS or chelating solvents¹²⁻¹⁵ was selected to prevent particles agglomeration. Subsequently, the silica or chelating solvents-coated Fe_3O_4 nanoparticles were further functionalized with APTES, in which APTES were usually hydrolyzed and condensed in the presence of the as-prepared Fe_3O_4 nanoparticles in alkalescence under heating. In our previous work, silica-coated Fe_3O_4 nanoparticles were achieved by two ways under room temperature.¹⁷ One was injecting sol-gol which was hydrolyzed and condensed into the Fe_3O_4 nanocrystals, the other one was

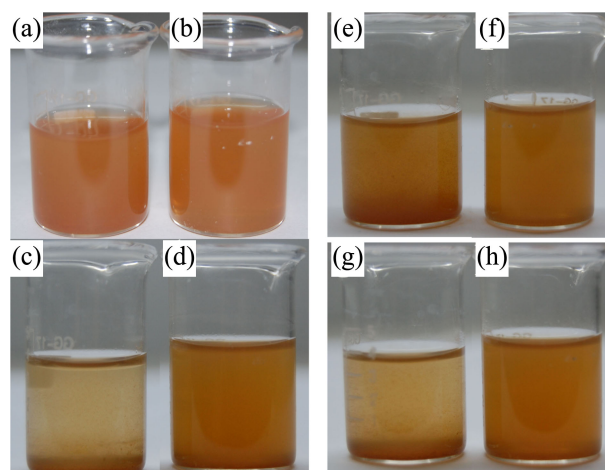


Figure 4. The APTES - Fe_3O_4 nanoparticles (in alkalescence) (a and c) and the APTES - Fe_3O_4 nanoparticles (in acidity) were dissolved in ethanol (b and d), respectively. The $\text{Fe}_3\text{O}_4@Ag$ nanoeggs were dissolved in distilled water (e and g) or ethanol (f and h), respectively.

hydrolyzing and condensing of sol-gol in the presence of the as-prepared Fe_3O_4 nanoparticles. We have testified that nanoparticles achieved by the first method have predefined size and shape, and improved monodispersity, which makes the first method to be used for the following research.

According to the Stber process, the hydrolysis and condensation of APTES was usually completed in alkalescence.¹² However, we found that APTES can be hydrolyzed and condensed in either acidity or alkalescence. In this case, APTES were hydrolyzed and condensed in acidity and alkalescence, respectively. After that, the APTES were employed as surface-capping in order to prevent the agglomeration between Fe_3O_4 nanoparticles, and left the terminal $-\text{NH}_2$ groups available for Ag seeds immobilization. The as-prepared APTES - Fe_3O_4 nanoparticles (in alkalescence) and the APTES - Fe_3O_4 nanoparticles (in acidity) were solubilized in ethanol, respectively, as shown in Figure 4(a, b), both forming brown solution. However, we can see that the APTES - Fe_3O_4 nanoparticles (in alkalescence) completely aggregated after the ultrasonication stopped for 15 min (Fig. 4(c)), while the APTES - Fe_3O_4 nanoparticles (in acidity) can be remained stable in ethanol for more than 190 min (Fig. 4(d)) after the ultrasonication stopped. Therefore, the $\text{Fe}_3\text{O}_4@Ag$ nanoeggs (the hydrolysis and condensation of APTES in acidity) were selected for the following works.

The Colloidal Stability of the $\text{Fe}_3\text{O}_4@Ag$ Nanoeggs. The Colloidal stability of the nanoparticles often limited their application.¹¹ The $\text{Fe}_3\text{O}_4@Ag$ nanoeggs were dissolved in ethanol and distilled water, respectively. As shown in Figure 4(e, f), both of the $\text{Fe}_3\text{O}_4@Ag$ nanoeggs possess high monodispersity. However, we can see that the $\text{Fe}_3\text{O}_4@Ag$ nanoeggs completely aggregated in distilled water after the ultrasonication stopped for 30 min (Fig. 4(g)), while the $\text{Fe}_3\text{O}_4@Ag$ nanoeggs can be remained suspended in ethanol for more than 150 min (Fig. 4(h)) after the ultrasonication stopped.

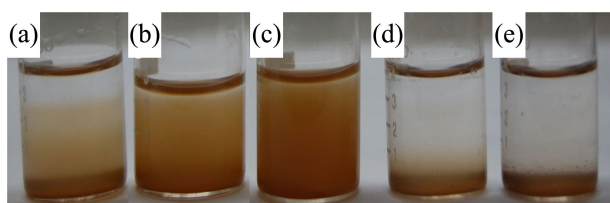


Figure 5. Different pH of $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs suspension: (a) 3.0, (b) 4.5, (c) 6.0, (d) 7.5, (e) 9.0.

The Influence of the Solution pH. It is important to note that the $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs was significantly influenced by pH.²³ We found the negatively charged $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs (negative due to the absorption of stabilizing borohydride) have high solubility and colloidal stability in ethanol (pH 6.0) (Fig. 5(c)). The pH of the $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs were adjusted by CH_3COOH or NaOH . As the pH was decreased from 4.5 to 3.0, the negative surface charge would be deprotonated, and the particles would become neutral in charge and precipitate gradually from solution (Fig. 5(a), (b)). However, it was found that the $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs aggregated immediately with an increase of pH from 7.5 to 9.0 (Fig. 5(d), (e)). The reason is probably that the $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs are hydrophobic, the binding of $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs with $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs to the surface of modified Fe_3O_4 nanoparticles may be facilitated by hydrophobic interactions, which resulted in the increased size of $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs and poor spherical morphologies of core/shell particles. After that, the $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs in different pH were collected by magnetic separation and dry to obtain the $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs powders.

Detection of Fingermarks Using the $\text{Fe}_3\text{O}_4@\text{Ag}$ Nanoeggs in Powder form. Fingerprint powdering remains the most usual technique for the detection of fingerprints.²⁴ The technique relies on the mechanical adherence of powders to the moisture and/or oily components of the skin ridge deposits,²⁵ and the excess powder should then be removed by dusting the surface with a gentle tapping, brushing and blowing. Therefore, the size and shape of which have a large influence on the amount of adhesion they have to the fingerprint.²⁶ Meanwhile, the fingerprint specialists' exposure while working at a crime scene to powder formulations could be a potential health hazard except magnetic fingerprint powders. For the magnetic fingerprint powders are specifically useful that only the magnetic powders touch the fingerprint ridges,

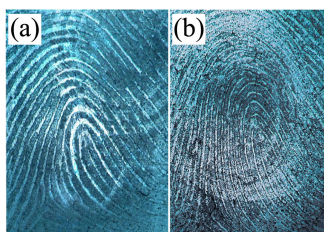


Figure 6. The fingerprints developed with $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs (Figure 6(a)) and Ag-modified Fe_3O_4 nanocomposites (Figure 6(b)) powders, respectively.

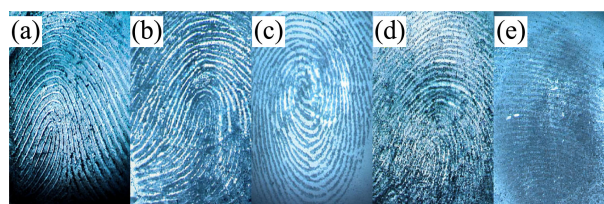


Figure 7. The fingerprints detection on glass surfaces treated with the $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs powders prepared in pH 3.0-9.0 accordingly.

while the excess powders can be removed by the magnetic brush.²⁴ Therefore, the magnetic powders are healthy and safe for fingerprints experts.

The magnetic property of the powders of the $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs (Fig. 6(a)) or Ag-modified Fe_3O_4 nanocomposites (Fig. 6(b)) was tested by using a magnetic brush. The powders of the Ag-modified Fe_3O_4 nanocomposites or $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs were found to be strongly attached to the brush. However, the $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs powders produced significantly less background development due to smooth and uniform Ag surfaces, resulting in good contrast between the fingerprints and the substrate than the Ag-modified Fe_3O_4 nanocomposites powders. Because the $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs powders possess more uniform size and nano-Ag shell exterior, they hold great promise for high absorption of the proteins in fingerprint systems.

The $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs in powder form prepared in pH 3.0, 4.5, 6.0, 7.5 and 9.0 were used to detect the fingerprints (Fig. 7(a), (b), (c), (d) and (e)), and the fingerprints can be viewed directly (Fig. 7(a), (b) and (c)), due to more clear ridge details. However, the fingerprints treated with the $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs prepared in higher pH value (Fig. 7(d), (e)) which have greater powder intensity with maximum background development result from the larger size of $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs in spherical shape.

Comparison experiment with commercial magnetic Fe_3O_4 powders were performed on non-porous or porous surfaces such as glass, ceramic, paper and polyethylene bags surfaces.

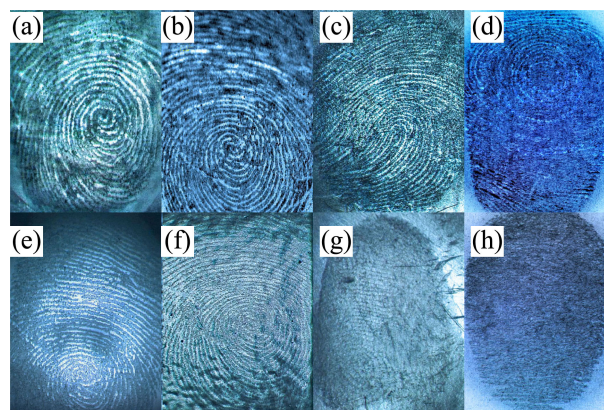


Figure 8. The fingerprints on glass, porcelain enamel, polyethylene pieces and paper surfaces developed with $\text{Fe}_3\text{O}_4@\text{Ag}$ nanoeggs powders (Figure 8(a)-(d)) and commercial magnetic Fe_3O_4 powders (Figure 8(e)-(h)).

The average particle size of the Fe₃O₄@Ag nanoeggs was approximately 290 nm, while those of the commercial magnetic powders were found to be about 119.7 and 82.3 μm, respectively.²⁷ The Fe₃O₄@Ag nanoeggs showed excellent ridge details with minimal background staining on glass, porcelain enamel, polyethylene pieces and paper surfaces (Fig. 8(a)-(d)), which lead to a better overall contrast for smaller particle adhere more effective to fingerprint residue than commercial magnetic Fe₃O₄ powders on the same surfaces (Fig. 8(e)-(h)). Compared with our previous paper,¹⁷ the present work was low-cost, in spite of both of them produced prints with good definition.

Conclusion

In conclusion, the Fe₃O₄@Ag nanoeggs were prepared through the encapsulation of APTES-coated Fe₃O₄ in nano-Ag shell, which possess a spherical shape with a smooth surface and a more uniform size, high monodispersity and magnetization. The thus obtained Fe₃O₄@Ag nanoeggs can be widely applied to the development of latent fingerprints on different surfaces. The results showed that the Fe₃O₄@Ag nanoeggs are much effective and convenient for workers to detect latent fingerprints in both the powder and the particle suspension forms.

Acknowledgments. This work was financially supported by NNSF of China (51102200), the Humanities and Social Sciences of Chinese Education Ministry Foundation (09XJC820016), the Natural Science Foundation Project of Chongqing CSTC (CSTC, 2009BB0135), the Education Committee Foundation of Chongqing City (KJ100105), China. Higher Education and Teaching Reform Project of Chongqing City (113127), Graduate Education and Teaching Reform Project of Chongqing City (yjg110304). And the publication cost of this paper was supported by the Korean Chemical Society.

References

1. Leem, G.; Sarangi, S.; Zhang, S.; Rusakova, I.; Brazdeikis, A.; Litvinov, D.; Lee, T. R. *Cryst. Growth Des.* **2009**, *9*, 32.
2. Schwarz, L. J. *Forensic Sci.* **2009**, *54*, 1323.
3. Jones, B. J.; Reynolds, A. J.; Richardson, M.; Sears, V. G. *Science and Justice* **2010**, *50*, 150.
4. Yu, Q. Z.; Shi, M. M.; Cheng, Y. N.; Wang, M.; Chen, H. Z. *Nanotechnology* **2008**, *19*, 1.
5. Shin, K. S.; Choi, J. Y.; Park, C. S.; Jang, H. J.; Kim, K. *Catal. Lett.* **2009**, *133*, 1.
6. Pankhurst, Q. A.; Connolly, J.; Jones, S. K.; Dobson, J. J. *Phys. D: Appl. Phys.* **2003**, *36*, R167.
7. Lens, P. N. L.; Hemminga, M. A. *Biodegradation* **1998**, *9*, 393.
8. Koch, C. C. *Nanostructured Materials; Processing, Properties, and Applications*: William Andrew Publishing: Norwich, NY, 2006.
9. Park, S. E.; Park, M. Y.; Han, P. K.; Lee, S. W. *Bull. Korean Chem. Soc.* **2006**, *27*, 1341.
10. Hesham, M. Z.; Saleh, A. H. *Journal of Materials Research* **2012**, *27*, 2798.
11. Shieh, D. B.; Cheng, F. Y.; Su, C. H.; Yeh, C. S. *etc. Biomaterials* **2005**, *26*, 7183.
12. Park, S. E.; Lee, J. W.; Haam, S. J.; Lee, S. W. *Bull. Korean Chem. Soc.* **2009**, *30*, 869.
13. Maceira, V. S.; Spasova, M.; Farle, M. *Adv. Funct. Mater.* **2005**, *15*, 1036.
14. Caruntu, D.; Cushing, B. L.; Caruntu, G.; O'Connor, J. C. *Chem. Mater.* **2005**, *17*, 3398.
15. Wu, W.; He, Q. G.; Chen, H.; Tang, J. X.; Nie, L. B. *Nanotechnology* **2007**, *18*, 1.
16. Huang, W. C.; Tsai, P. J.; Chen, Y. C. *Small* **2009**, *1*, 51.
17. Zhang, L. Y.; Zhou, X. F.; Chu, T. *Science China Chemistry* **2013**, *56*, 551.
18. Stöber, W.; Fink, A.; Bohn, E. J. *Colloid Interface Sci.* **1968**, *26*, 62.
19. Savka, I. S.; Huo, F. W.; Lee, J. S.; Mirkin, C. A. *J. Am. Chem. Soc.* **2005**, *127*, 15362.
20. Jennifer, L. L.; David, A. F.; Matthew, B. S.; Peter, S.; Mary, E. W. *Nano Letters* **2004**, 719.
21. Yu, H.; Chen, M.; Rice, P. M.; Wang, S. X.; White, R. L.; Sun, S. H. *Nano Letters* **2005**, 379.
22. Zhang, Z. B.; Duan, H. F.; Li, S. G.; Lin, Y. J. *Langmuir* **2010**, *26*, 6676.
23. Hajdú, A.; Illés, E.; Tombácz, E.; Borbáth, I. *Colloids and Surfaces A: Physicochemical. Eng. Aspects* **2009**, *347*, 104.
24. Stauffer, E.; Becue, A.; Singh, K. V.; Thampi, K. R.; Champod, C.; Margot, P. *Forensic Sci. Int.* **2007**, *168*, 1.
25. Sodhi, G. S.; Kaur, J. *Forensic Sci. Int.* **2001**, *120*, 172.
26. Choi, M. J.; Smoother, T.; Martin, A.; McDonagh, A. M. *Forensic Sci. Int.* **2007**, *173*, 154.
27. Thonglon, T.; Sc, B.; Chaikum, N. J. *Forensic Sci.* **2010**, *55*, 1343.