

## Short Communication

# Scission kinetic model for the prediction of polymer pyrolysis curves from chain structure

Luis A. Pérez-Maqueda,<sup>1\*</sup> Pedro E. Sánchez-Jiménez,<sup>1</sup> Antonio Perejón,<sup>1,2</sup> Cristina García-Garrido,<sup>1</sup> José M. Criado,<sup>1</sup> and Mónica Benítez-Guerrero<sup>3</sup>

<sup>1</sup> Instituto de Ciencia de Materiales de Sevilla (CSIC- Univ. Sevilla). C. Américo Vespucio 49, Sevilla 41092. Spain

<sup>2</sup> Department of Chemistry, University of Oxford, Inorganic Chemistry Laboratory, South Parks Road, Oxford OX1 3QR, UK

<sup>3</sup> Departamento de Ingeniería Civil, Materiales y Fabricación, Universidad de Málaga, C. Dr. Ortiz Ramos s/n, 29071 Málaga, Spain.

## Abstract

*There is a significant interest in correlating polymer structure with thermal degradation behavior. Thus, polymer pyrolysis curves could be predicted from the chemical structure of the polymer. Recent proposals correlate the kinetic temperature function directly with the chemical structure of the polymer by means of the dissociation energy while assuming a semiempirical first order model for the reaction fraction function. However, first order model lacks physical meaning and it produces significant deviations of the predicted curves, mostly under isothermal conditions. Thus, in this work an upgrade of the method is proposed by using a new random scission kinetic model. The newly proposed kinetic equation has been checked by fitting the experimental data reported by different authors for the thermal pyrolysis of polystyrene. It has been demonstrated that it accounts for the experimental data of polymer degradation under different heating schedule with considerably higher precision than the previously assumed first order kinetics.*

**Keywords:** Polymer; thermal degradation; pyrolysis; kinetics; prediction;

\*Corresponding author: [maqueda@cica.es](mailto:maqueda@cica.es). Phone (34)954489548

## 1. Introduction

Predictions of polymer properties, such as thermal stability could be assessed from quantitative structure-property relationships. Van Krevelen [1] in a pioneering work, proposed the Additive Molar Thermal Decomposition Function, based on the assumption that the thermal decomposition of a polymer is determined by a sum of contributions made by the different groups in the molecule. Bicerano approach considered additive contributions of atoms and bonds, while the environment of each atom and bond is taken into account [2, 3]. Very recently, Porter et al proposed an interesting approach to predict the mass loss curve as a function of time (and temperature) by the use of two functions:[4] an energy function, directly related to the dissociation energy of the chain backbone, and other a reaction fraction, defined for the sake of simplicity, by a first order, F1, kinetic model. The use of F1 models for polymer degradation studies is widely extended in literature since pioneering works by Van Krevelen et al. [5], Reich [6, 7], Broido [8] and others used such model. The simplicity of F1 (and in general of “n order”) model and the lack of alternative proposals would explain its extensive use, despite the importance of using proper models in kinetic studies. [9-14] In this communication, deviations in Porter et al prediction curves due to first order model assumption are discussed, while the use of a new model based on the polymeric chain scission and volatilization of the subunits is proposed. Prediction reliability of the method is tested with experimental curves under both linear heating and isothermal conditions.

## 2. Experimental

Atactic polystyrene (Goodfellow 261595) was used. Thermogravimetric experiments were performed in nitrogen flow (100mL min<sup>-1</sup>) using small mass samples (~10 mg) under either linear heating or isothermal conditions using a Q5000 TGA (TA Instruments).

## 3. Results and discussion

For polymer pyrolysis, the general kinetic equation correlates reaction rate,  $d\alpha/dt$ , with temperature,  $T$ , and reaction fraction,  $\alpha$ , by means of a function of temperature,  $k(T)$ , and a function of reaction fraction,  $f(\alpha)$ :

$$\frac{d\alpha}{dt} = k(T)f(\alpha) \quad (1).$$

Usually, the  $k(T)$  is approached by an Arrhenius equation defined in terms of the apparent activation energy and the Arrhenius preexponential factor, while  $f(\alpha)$  is the mathematical expression of an ideal kinetic model. Thus,  $k(T)$  and  $f(\alpha)$  are determined from the kinetic analysis of a series of experimental curves [15-19]. Once the temperature and reaction functions are determined, the thermal behavior could be modeled under any heating conditions. A different approach is that proposed by Porter that relates chemical structure with thermal behavior, in such a way that mass loss curves could be directly predicted from the knowledge of parameters such as dissociation energy [4]. In Porter’s approach,  $k(T)$  is defined in terms of the polymer chemical structure, by means of the following equation:

$$k(T) = 2.3 \cdot 10^{10} \theta_1 e^{-\frac{E_d}{H_T}} \quad (2),$$

where  $\theta_1$  is the Debye reference temperature,  $E_d$  is the dissociation energy and  $H_T$  is the thermal energy per group of atoms.  $H_T$  can be approximated by [4]

$$H_T \approx NR(T - 0.22\theta_1) \quad (3),$$

being  $N$  the number of degrees of freedom for characteristic structural group. Eq. (3) is valid for temperatures,  $T$ , higher than  $\theta_1$  [20, 21].

For the reaction fraction function,  $f(\alpha)$ , Porter's approach assumes a simple first order kinetic model.

$$f(\alpha) = (1 - \alpha) \quad (4)$$

From eqs (2), (3) and (4), the general kinetic equation (eq. (1)) can be written as follows:

$$\frac{d\alpha}{dt} = 2.3 \cdot 10^{10} \theta_1 e^{-\frac{E_d}{NR(T-0.22\theta_1)}} (1 - \alpha) \quad (5)$$

This equation is a general differential expression valid for any heating schedule. For different heating conditions, eq (5) can be integrated as follows [22]:

$$\int_0^\alpha \frac{d\alpha}{(1-\alpha)} = 2.3 \cdot 10^{10} \theta_1 \int_0^t e^{-\frac{E_d}{NR(T-0.22\theta_1)}} dt \quad (6),$$

The first order kinetic model in Porter's method is used as a *semiempirical* fitting function without any physical meaning. For its simplicity, this model is extensively used in polymer pyrolysis studies, but its application has been recently criticized as they provide significant deviations for experimental curves. Other physically sound approach is that based on the scission of the polymeric chain and volatilization of the subunits, such as Simha and Wall model that describes the reaction fraction in terms of the fraction of bonds broken, the initial degree of polymerization and the minimum length of the polymer that is not volatile [23]. This model is complex and require determining a number of parameters that are difficult to quantify experimentally. Therefore, its application to real systems is very scarce. Very recently, the model of Simha and Wall has been reformulated in terms of the reactions fraction, which could be determined from thermal analysis measurements [24, 25]. Thus, using the new functions, the reaction rate of the thermal degradation of polymers that go through a random scission mechanism could be directly related to the reacted fraction of the process.

For a polymer that degrades by cleavage of chemical bonds following first order kinetics, all breakable bonds within the polymer have the same probabilities to be broken [23]. Thus, the rate of bond breakage can be written as follows:

$$\frac{dx}{dt} = k_T (1 - x) \quad (6),$$

where  $x$  is the fraction of bonds broken and  $k_T$  the rate constant of bond breakage. Moreover,  $x$  and  $\alpha$  are related by the following approximated expression:

$$\alpha \approx 1 - (1 - x)^{L-1} [1 + x(L - 1)] \quad (7)$$

Being  $L$  the minimum length of not volatile polymer subunit. This equation (eq. (7)) relates  $\alpha$  (as for example mass loss) with the fraction of broken bonds. Nevertheless, as  $x$  cannot be measured by conventional techniques, and  $L$  is very difficult to determine experimentally, the application of eq. (7) is limited. Nevertheless, by differentiating eq. (7), and incorporating eq. (6), the value of the conversion function  $f(\alpha)$  can be determined [24, 25]:

$$f(\alpha) = L(L - 1)x(1 - x)^{L-1} \quad (10)$$

For  $L=2$ , a symbolic solution can be obtained:

$$f(\alpha) = 2(\alpha^{1/2} - \alpha) \quad (11)$$

For other values of  $L$ , the  $f(\alpha)$  conversion functions can be easily determined numerically [24, 25]:

Porter et al approach for the kinetic analysis of polymer degradation can be easily upgraded by considering a random scission kinetic model, L2, as the one described above, which has a physical significance, instead of the empirical F1 model. Thus, the general differential kinetic equation will take the following form:

$$\frac{d\alpha}{dt} = 2.3 \cdot 10^{10} \theta_1 e^{-\frac{E_d}{H_T}} 2(\alpha^{1/2} - \alpha) \quad (12)$$

This equation, eq. (12), is a general expression that is valid for predicting the thermal behavior under any heating schedule. Moreover, the shapes of  $f(\alpha)$  obtained for  $L$  in the range 2-8 are very similar[25] and, therefore, eq (12) could be consider as a general equation for any value of  $L$ .

Fig. 1 shows a comparison of the thermogravimetric experimental data (dots) for polystyrene (PS) at  $10 \text{ K min}^{-1}$ , as digitalized from Porter et al paper [4], and predictions using the same kinetic parameters as in Porter et al ( $E_d = 344 \text{ kJ mol}^{-1}$ ,  $\theta_1 = 285 \text{ K}$  and  $N = 2$ ) but assuming either F1 (dashed-line), as in Porter et al or the newly proposed L2 (solid-line) models. Whereas F1 provides a rough fitting of the experimental curve, L2 provides a much better fitting.

Fig. 2 shows three thermogravimetric curves corresponding to the thermal pyrolysis of polystyrene sample recorded at three heating rates, i.e. 1, 2 and  $5 \text{ K min}^{-1}$ . The comparison of the experimental curves (dots) and model predictions using the same kinetic parameters as in Fig. 1 and assuming F1 (dashed line) or L2 (solid line) kinetic models are also included in Fig. 2. For all three curves, as it happened with Porter et al experimental data shown above, the fitting is also much better for L2 than for F1.

It is well known that experimental thermogravimetric curves obtained under linear heating rate conditions present sigmoidal shapes independently of the kinetic parameters, including the kinetic model, that describe the process. Thus, it has been shown that a single curve obtained under linear heating rate conditions could be perfectly fitted by any of the kinetic models proposed in literature by properly selecting the other kinetic parameters, i.e. kinetic

1 energy and preexponential parameter [26]. Nevertheless, curves obtained under other heating  
2 schedules, such as isothermal or sample-controlled conditions, present a shape that is  
3 characteristic of the kinetic model that describes the process [9, 27, 28]. Curves corresponding  
4 to the pyrolysis of PS under isothermal conditions at different temperatures, i.e. 325°C and  
5 330°C, are included in Fig. 3. This figure (Fig. 3) also shows the curves simulated with the same  
6 values of  $E_a$ ,  $\theta_1$  and  $N$  as those used in Figs. 1 and 2 but for F1 (dashed-line) and L2 (solid-line).  
7 It is even clearer that the L2 model provides a much better fitting of the experimental curves.  
8 Thus, pyrolysis curves under isothermal conditions for the PS present sigmoidal shape with a  
9 characteristic small induction period that is nicely fitted by the random scission model in the  
10 entire range, while the first order one shows quite a different shape and both experimental  
11 and simulated curves are far away. Thus, for the first order model at  $\alpha=0.5$ , the deviations  
12 observed are larger than 80 and 110 minutes for the isothermal curves at 330 and 325°C,  
13 respectively.  
14  
15  
16  
17  
18  
19  
20

#### 21 **4. Conclusions**

22  
23 In conclusion, the novel method for predicting polymer pyrolysis curves under any heating  
24 schedule, recently proposed by Porter et al [4], has been modified by considering a kinetic  
25 model that describes the polymer chain breakage and evaporation of the subunits as a  
26 function of the reaction fraction. The proposed method is a simple approach that does not  
27 take into consideration all the complex processes that takes place during pyrolysis, but  
28 provides a simple tool for predicting the pyrolysis curves of polymers directly from the chain  
29 structure. The proposed method has been tested with the thermal pyrolysis of polystyrene. It  
30 has been observed that it provides a better modeling of the experimental curves, mostly for  
31 isothermal conditions where the shapes of the curves are quite dependent on the kinetic  
32 model followed by the process.  
33  
34  
35  
36  
37  
38  
39  
40  
41

#### 42 **Acknowledgments**

43  
44 This work was supported by projects TEP-7858 (Junta de Andalucia), CTQ2011-27626 (Spanish  
45 Government) and Feder funds.  
46  
47  
48  
49

#### 50 **References**

- 51  
52 [1] D.W. Van Krevelen, K. Te Nijenhuis, Properties of polymers their correlation with chemical  
53 structure; their numerical estimation and prediction from additive group contributions, Fourth  
54 ed., Elsevier, Amsterdam, The Netherlands, 2009.  
55 [2] J. Bicerano, Prediction of Polymer Properties, Marcel Dekker, Inc, New York, USA, 2002.  
56 [3] Synthia. Materials Studio 6.1, in, Accelrys.  
57 [4] D. Porter, F. Vollrath, K. Tian, X. Chen, Z. Shao, A kinetic model for thermal degradation in  
58 polymers with specific application to proteins, Polymer, 50 (2009) 1814-1818.  
59  
60  
61  
62  
63  
64  
65

- 1 [5] D. Van Krevelen, C. Van Heerden, F. Huntjens, Physicochemical aspects of the pyrolysis of  
2 coal and related organic compounds, *Fuel*, 30 (1951) 253-259.
- 3 [6] L. Reich, An approximate graphical estimation of activation energy from thermogravimetric  
4 traces, *Makromol Chem*, 105 (1967) 223.
- 5 [7] L. Reich, D. Levi, Thermal stability indices for polymeric materials based on energy  
6 considerations *Makromol Chem*, 66 (1963) 102-113.
- 7 [8] A. Broido, A simple, sensitive graphical method of treating thermogravimetric analysis data,  
8 *Journal of Polymer Science Part a-2-Polymer Physics*, 7 (1969) 1761-&.
- 9 [9] S. Vyazovkin, A.K. Burnham, J.M. Criado, L.A. Perez-Maqueda, C. Popescu, N. Sbirrazzuoli,  
10 ICTAC Kinetics Committee recommendations for performing kinetic computations on thermal  
11 analysis data, *Thermochimica Acta*, 520 (2011) 1-19.
- 12 [10] P.E. Sanchez-Jimenez, L.A. Perez-Maqueda, A. Perejon, J.M. Criado, Combined kinetic  
13 analysis of thermal degradation of polymeric materials under any thermal pathway, *Polymer*  
14 *Degradation and Stability*, 94 (2009) 2079-2085.
- 15 [11] P.E. Sanchez-Jimenez, L.A. Perez-Maqueda, A. Perejon, J.M. Criado, Nanoclay Nucleation  
16 Effect in the Thermal Stabilization of a Polymer Nanocomposite: A Kinetic Mechanism Change,  
17 *Journal of Physical Chemistry C*, 116 (2012) 11797-11807.
- 18 [12] P.E. Sanchez-Jimenez, L.A. Perez-Maqueda, A. Perejon, J.M. Criado, Limitations of model-  
19 fitting methods for kinetic analysis: Polystyrene thermal degradation, *Resources Conservation*  
20 *and Recycling*, 74 (2013) 75-81.
- 21 [13] P.E. Sanchez-Jimenez, L.A. Perez-Maqueda, A. Perejon, J. Pascual-Cosp, M. Benitez-  
22 Guerrero, J.M. Criado, An improved model for the kinetic description of the thermal  
23 degradation of cellulose, *Cellulose*, 18 (2011) 1487-1498.
- 24 [14] A. Perejon, P.E. Sanchez-Jimenez, E. Gil-Gonzalez, L.A. Perez-Maqueda, J.M. Criado,  
25 Pyrolysis kinetics of ethylene-propylene (EPM) and ethylene-propylene-diene (EPDM), *Polymer*  
26 *Degradation and Stability*, 98 (2013) 1571-1577.
- 27 [15] O. Bianchi, G.B. Repenning, L.B. Canto, R.S. Mauler, R.V.B. Oliveira, Kinetics of thermo-  
28 oxidative degradation of PS-POSS hybrid nanocomposite, *Polymer Testing*, 32 (2013) 794-801.
- 29 [16] R.R. Corsetti, T. Neumeyer, M. May, D. Jandrey, V. Altstaedt, N.S. Medeiros Cardozo,  
30 Modeling and estimation of parameters for the curing of an epoxy/amine system, *Polymer*  
31 *Testing*, 32 (2013) 647-654.
- 32 [17] Y. Lv, Y. Huang, M. Kong, G. Li, Improved thermal oxidation stability of polypropylene films  
33 in the presence of beta-nucleating agent, *Polymer Testing*, 32 (2013) 179-186.
- 34 [18] J.R. Robledo-Ortiz, C. Zepeda, C. Gomez, D. Rodrigue, R. Gonzalez-Nunez, Non-isothermal  
35 decomposition kinetics of azodicarbonamide in high density polyethylene using a capillary  
36 rheometer, *Polymer Testing*, 27 (2008) 730-735.
- 37 [19] F. Carrasco, L.A. Perez-Maqueda, P.E. Sanchez-Jimenez, A. Perejon, O.O. Santana, M.L.  
38 Maspoch, Enhanced general analytical equation for the kinetics of the thermal degradation of  
39 poly(lactic acid) driven by random scission, *Polymer Testing*, 32 (2013) 937-945.
- 40 [20] D. Porter, *Group Interaction Modelling of Polymer Properties*, Marcel Dekker, New York,  
41 USA, 1995.
- 42 [21] B. Wunderlich, S.Z.D. Cheng, K. Loufakis, *Encyclopedia of Polymer Science and*  
43 *Engineering*, in, Wiley-InterScience, New York, USA, 1989, pp. 767-807.
- 44 [22] L.A. Perez-Maqueda, P.E. Sanchez-Jimenez, J.M. Criado, Evaluation of the integral  
45 methods for the kinetic study of thermally stimulated processes in polymer science, *Polymer*,  
46 46 (2005) 2950-2954.
- 47 [23] R. Simha, L.A. Wall, Kinetics of chain depolymerization, *Journal of Physical Chemistry*, 56  
48 (1952) 707-715.
- 49 [24] P.E. Sanchez-Jimenez, L.A. Perez-Maqueda, A. Perejon, J.M. Criado, Generalized Kinetic  
50 Master Plots for the Thermal Degradation of Polymers Following a Random Scission  
51 Mechanism, *Journal of Physical Chemistry A*, 114 (2010) 7868-7876.
- 52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 [25] P.E. Sanchez-Jimenez, L.A. Perez-Maqueda, A. Perejon, J.M. Criado, A new model for the  
2 kinetic analysis of thermal degradation of polymers driven by random scission, *Polymer*  
3 *Degradation and Stability*, 95 (2010) 733-739.

4 [26] P.E. Sanchez-Jimenez, L.A. Perez-Maqueda, A. Perejon, J.M. Criado, Clarifications  
5 regarding the use of model-fitting methods of kinetic analysis for determining the activation  
6 energy from a single non-isothermal curve, *Chemistry Central Journal*, 7 (2013).

7 [27] P.E. Sanchez-Jimenez, L.A. Perez-Maqueda, A. Perejon, J.M. Criado, Constant rate thermal  
8 analysis for thermal stability studies of polymers, *Polymer Degradation and Stability*, 96 (2011)  
9 974-981.

10 [28] P.E. Sanchez-Jimenez, A. Perejon, J.M. Criado, M.J. Dianez, L.A. Perez-Maqueda, Kinetic  
11 model for thermal dehydrochlorination of poly(vinyl chloride), *Polymer*, 51 (2010) 3998-4007.  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

## Figure Captions


1  
2  
3  
4 **Fig. 1.** Comparison of the thermogravimetric experimental data (dots) for polystyrene (PS) at  $10 \text{ K min}^{-1}$ ,  
5 as digitalized from Porter et al paper, and model predictions employing the same kinetic parameters  
6 used by Porter et al ( $E_d = 344 \text{ kJ mol}^{-1}$  that corresponds to the average dissociation energy of the three  
7 key skeletal bonds,  $\theta_1 = 285 \text{ K}$  and  $N = 2$ ) and assuming either first order (dashed line), as in Porter et al  
8 proposal, or random scission (solid line) kinetic model.  
9

10  
11 **Fig. 2.** Comparison of the experimental curves (dots) for polystyrene (PS) at 1, 2 and  $5 \text{ K min}^{-1}$  and model  
12 predictions using the same kinetic parameters as in Fig. 1 and assuming first order (dashed line) or  
13 random scission (solid line) kinetic models.  
14


15  
16 **Fig. 3.** Comparison of curves corresponding to the thermal pyrolysis of PS under isothermal conditions at  
17  $325^\circ\text{C}$  and  $330^\circ\text{C}$  and curves simulated using the same values of  $E_d$ ,  $\theta_1$  and  $N$  as those used in Figs. 1 and  
18 2 but different kinetic model, i.e. first order (dashed line) and random scission (solid line).  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65



1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

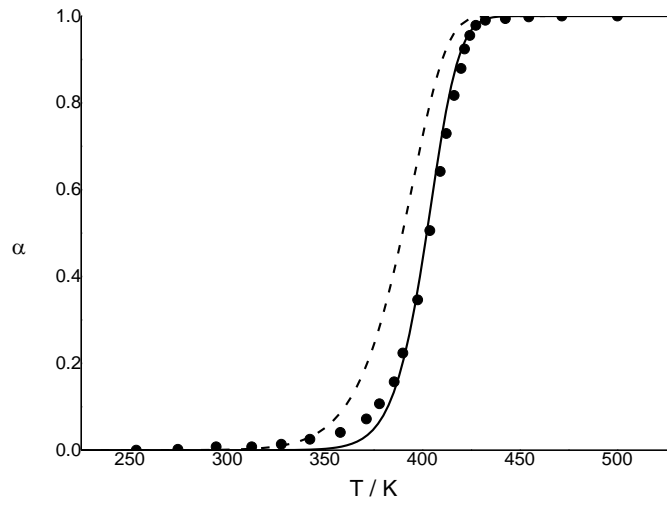


**Fig. 1.** Comparison of the thermogravimetric experimental data (dots) for polystyrene (PS) at  $10 \text{ K min}^{-1}$ , as digitalized from Porter et al paper, and model predictions employing the same kinetic parameters used by Porter et al ( $E_d = 344 \text{ kJ mol}^{-1}$  that corresponds to the average dissociation energy of the three key skeletal bonds,  $\theta_1 = 285 \text{ K}$  and  $N = 2$ ) and assuming either first order (dashed line), as in Porter et al proposal, or random scission (solid line) kinetic model.

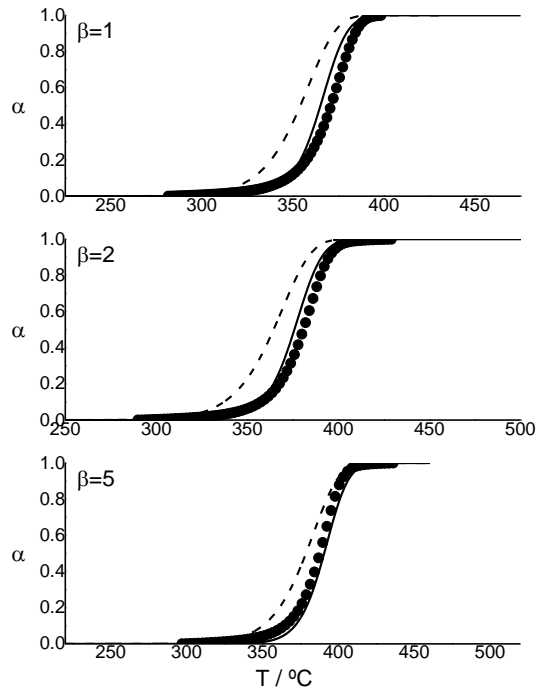

**Fig. 2.** Comparison of the experimental curves (dots) for polystyrene (PS) at 1, 2 and 5 K min<sup>-1</sup> and model predictions using the same kinetic parameters as in Fig. 1 and assuming first order (dashed line) or random scission (solid line) kinetic models.

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

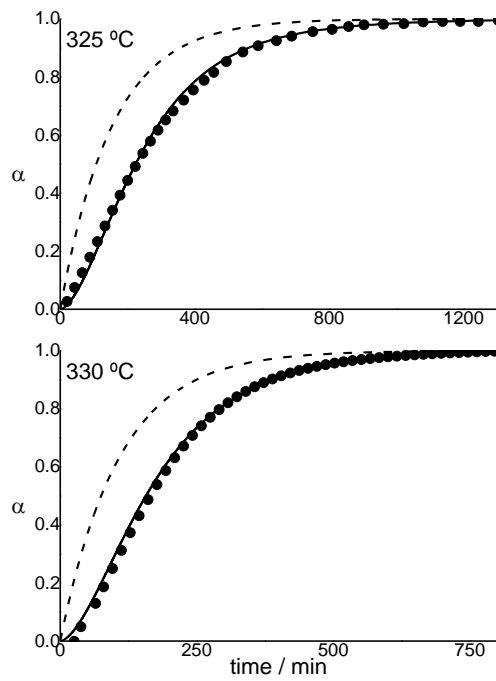

**Fig. 3.** Comparison of curves corresponding to the thermal pyrolysis of PS under isothermal conditions at 325°C and 330°C and curves simulated using the same values of  $E_a$ ,  $\theta_1$  and  $N$  as those used in Figs. 1 and 2 but different kinetic model, i.e. first order (dashed line) and random scission (solid line).