



Calhoun: The NPS Institutional Archive

Faculty and Researcher Publications

Faculty and Researcher Publications

2005-03-20

Effect of strain path on evolution of deformation bands during ECAP of pure aluminum

Oh-ishi, K.

Elsevier

Materials Science and Engineering A, v. 410-411, 2005, pp.83-187



Calhoun is a project of the Dudley Knox Library at NPS, furthering the precepts and goals of open government and government transparency. All information contained herein has been approved for release by the NPS Public Affairs Officer.

Dudley Knox Library / Naval Postgraduate School
411 Dyer Road / 1 University Circle
Monterey, California USA 93943

<http://www.nps.edu/library>

Effect of strain path on evolution of deformation bands during ECAP of pure aluminum

K. Oh-ishi, A.P. Zhilyaev¹, T.R. McNelley*

Department of Mechanical & Astronautical Engineering, Naval Postgraduate School, 700 Dyer Road, Monterey, CA 93943-5146, USA

Received in revised form 20 March 2005

Abstract

The influence of strain path during equal channel angular pressing (ECAP) has been evaluated in pure aluminum by orientation imaging microscopy (OIM) and transmission electron microscopy (TEM). The material was examined after four pressing operations by route B_C in a 90° die, or eight pressing operations by route B_C in a 135° die. The von Mises equivalent strains were essentially the same for these two ECAP procedures. The microtexture data indicate that the distortion during ECAP corresponds to a simple shear in a direction approximately parallel to die-channel exit and on a plane perpendicular to the flow plane. For both procedures, the OIM data reveal prominent meso-scale band-like features. Lattice orientations in each band correspond to a texture orientation but the particular combinations of orientations depend upon ECAP die angle. High-angle boundaries in the structure correspond to interfaces between the bands.

© 2005 Elsevier B.V. All rights reserved.

Keywords: Aluminum; Equal channel angular pressing (ECAP); Texture; Simple shear; Orientation imaging microscopy (OIM)

1. Introduction

Equal channel angular pressing (ECAP) is advantageous in producing of ultrafine-grained (UFG) structures in bulk material because the procedure may be applied repeatedly to a billet without changing its cross section [1]. This is in contrast to other methods, such as high-pressure torsion (HPT) [2] and accumulative roll-bonding (ARB) [3]. The applicability to bulk material of still other methods, such as friction stir processing (FSP) [4], must still be established. Although the first publications on ECAP appeared almost 25 years ago [5] in the last decade, there has been a surge of interest in the development of UFG structures in pure metals and alloys by this method. A survey of the literature reveals that most publications have been concerned with the capability of ECAP to produce highly refined grains in a range of industrially important materials. The roles of ECAP parameters (die-channel angle, the number of pressing passes, billet rotation between passes and relief angles in the die) in grain refinement have been of primary interest. In general, microstructure refinement and texture evolution during

ECAP have been studied separately and few systematic investigations have been conducted on the concomitant development of texture and microstructure.

The strain state during an ECAP pass depends strongly on the die angle. Band-like arrangements of characteristic texture orientations have been reported in the microstructure of pure aluminum processed by repetitive ECAP using a 90° die [6]. Recently, texture measurements after one ECAP pass through a 90° die for pure aluminum [7], pure copper [8] and pure aluminum again [9] have shown that simple shear tends to occur on a plane perpendicular to the flow plane and with shear direction nearly parallel to the axis of the die exit channel. These observations are in disagreement with the usual theoretical interpretation [5,10,11] of the strain state associated with ECAP processing, which assumes that shear occurs on the plane of the die-channel intersection in the direction of the bisector of the die angle. The discrepancy has been attributed to the combined effect of die wall friction, constitutive behavior of the billet material and use of the relief angle in ECAP die [7–9].

The role of the die angle in microstructure and texture development has been examined through scanning of large areas by orientation imaging microscopy (OIM) in pure aluminum processed by ECAP using route B_C with a 90° die (four passes) and a 135° die (eight passes). The development of the textures and band-like arrangements in the resulting microstructures has

* Corresponding author. Tel.: +1 831 656 2216; fax: +1 831 656 2238.
E-mail address: TMcNelley@nps.edu (T.R. McNelley).

¹ On leave from Institute of Mechanics, Russian Academy of Science, Ufa 450000, Russia.

been analyzed, and the band-to-band disorientations have been evaluated.

2. Experimental procedure

Full details of the materials and processes of this work have been given previously [12,13]. Briefly, the pure aluminum material (99.99%) was swaged to a rod 10 mm in diameter and 60 mm in length for pressing in the 90° die. The material was cold rolled and billets were machined with dimensions of 10 mm × 10 mm × 60 mm for pressing in the 135° die. Prior to ECAP, these materials were given annealing treatments resulting in initial, recrystallized grain sizes of ~1 mm. ECAP of these materials was conducted at room temperature following route B_C. The round billet was repetitively pressed four times in a die with an angle, Φ , between channels of 90° and a relief angle, Ψ , of ~20°, and is denoted here as the 90° sample. The square billet was pressed eight times through a 135° die with a relief angle of ~13°, i.e., the 135° sample. The accumulated equivalent strain values for each of these processes were calculated using the die-channel and relief angles in Eq. (1) [10]:

$$\varepsilon_N = \frac{N}{\sqrt{3}} \left[2 \cot \left(\frac{\Phi}{2} + \frac{\Psi}{2} \right) + \Psi \operatorname{cosec} \left(\frac{\Phi}{2} + \frac{\Psi}{2} \right) \right] \quad (1)$$

Thus, $\varepsilon_4 = 4.2$ for the 90° die and $\varepsilon_8 = 3.7$ for the 135° die and so the von Mises equivalent strains were effectively the same for these two procedures. Prior to examination by OIM, sam-

ples were, first, mechanically polished and then electropolished in the Buehler Electromet 4 apparatus using a 20% perchloric acid—80% ethanol electrolyte solution cooled to -25 °C. OIM analyses were always conducted on the flow plane. The symmetry of an ECAP billet is monoclinic, and so the senses of the coordinate axes in the flow plane were carefully ascertained. Transmission electron microscopy (TEM) foil preparation has been described previously [13].

3. Results and discussion

Fig. 1 shows gray-scale OIM maps and corresponding discrete pole figures that have been highlighted in colors, using a tolerance of 15°, according to the distinct orientations in the texture. Data for aluminum pressed following route B_C are included in for (a) the 90° sample and (b) the 135° sample. These microstructures and textures are represented in the flow plane and the insets that are included with the pole figures are aligned to illustrate the orientation of the ECAP dies for these data. Fig. 1 includes coordinate axes for both samples. Thus, the x - y plane is the flow plane and the billets exit their corresponding dies along the $-x$ direction. The shape changes in the flow plane for unit cubes after a single pass through each die are included in Fig. 1. Two distinct texture orientations are apparent in the 90° sample and the shapes of the regions that correspond to these orientations are congruent with the shape of a volume element subjected to a single ECAP pass through a 90° die. In

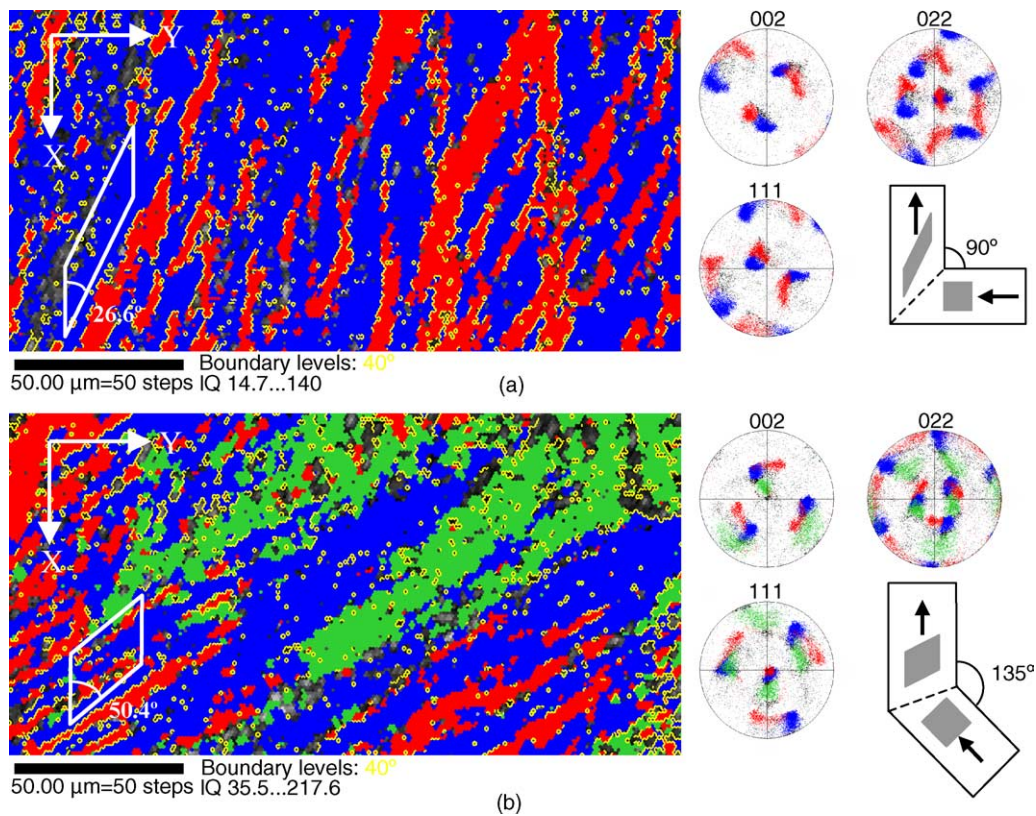


Fig. 1. OIM maps and pole figures for aluminum after (a) 90° sample, four passes and (b) 135° sample, eight passes. Gray-scale maps and pole figures were highlighted by different colors corresponding to characteristic orientations in the textures. The insets with the pole figures indicate the orientation of the die sets relative to the sample coordinates.

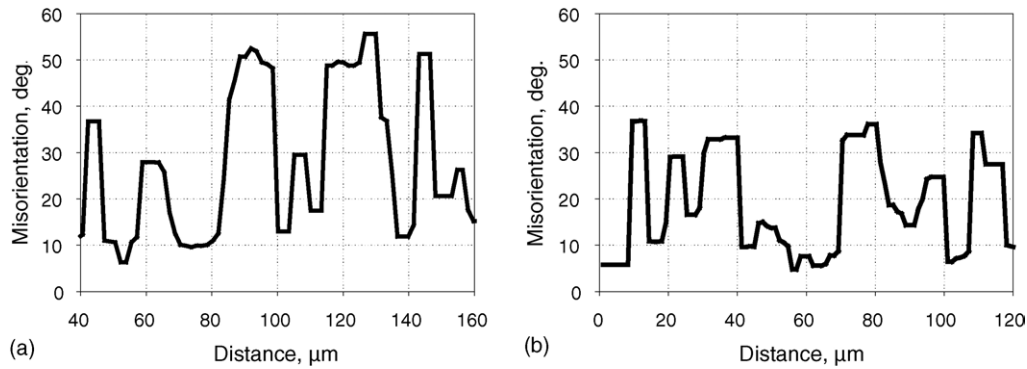


Fig. 2. Point-to-origin disorientation profiles for ECAP aluminum processed by route B_C: (a) the 90° sample, four passes and (b) the 135° sample, eight passes.

contrast, there are apparently three orientations in the 135° sample. Regions corresponding to these orientations are band-like in nature but are only partly congruent with the shape change of a volume element for this die angle.

For the 90° sample, a traverse was made along a line inclined at $\sim 63.4^\circ$ to the x -axis and the corresponding point-to-origin disorientation distribution is shown in Fig. 2(a); a similar traverse was made for the 135° sample, but at an angle of $\sim 39.6^\circ$ to the x -axis. This result is included in Fig. 2(b). In both cases, these traverses are approximately normal to a set of boundaries between texture orientations. Inspection of these disorientation profiles shows that the difference in lattice orientation across boundaries has a range of 45° – 50° for 90° sample and about 30° for 135° sample. Boundaries of disorientation $\geq 40^\circ$ are highlighted in yellow in Fig. 1 and it is apparent that there are more of these boundaries in the 90° sample.

Orientation distribution functions (ODFs) were calculated from the texture data for these samples using Bunge's definition of the Euler angles in relation to the axes indicated in Fig. 1. The results are depicted in Fig. 3 where the 3D-ODFs are represented by iso-surfaces of 1/8, 1/4 or 1/2 of maximum intensity in each case. In this representation, φ_1 is a rotation about z -axis (i.e., the flow plane normal), Φ is a rotation about the new x' -axis and φ_2 is a rotation about the final z'' -axis. The fundamental zone of the ODF involves $0^\circ \leq \varphi_1 \leq 180^\circ$ because of the monoclinic sym-

metry of an ECAP billet [9]. An ECAP pass is often described in terms of a simple shear in the flow plane. Canova et al. [14] have classified fcc torsion (shear) textures in terms of three components: the A-fiber, $\{111\}\langle hkl \rangle$, the B-fiber $\{hkl\}\langle 110 \rangle$ and the C-component $\{001\}\langle 110 \rangle$, where the notation refers to {plane parallel to the shear plane}⟨direction parallel to the shear direction⟩. In the coordinate system chosen here, observed and theoretical shear textures would differ only by an apparent rotation of the shear plane and shear direction about the flow plane normal (the z -axis). This would be reflected in a translation along φ_1 in the ODF.

The distinct orientations in the observed textures mainly lie near variants of the B-fiber in the ODF although the specific texture components differ for these two strain paths. A C-component (located at one end of the B-fiber) is also apparent in the 90° sample but does not appear in the 135° sample. The prominent lattice orientations and nearest ideal shear texture components for these samples are summarized in Table 1. In both samples, the experimental texture data suggest that the shear direction is more nearly aligned with the axis of the die exit channel rather than with the bisector of the die angle. It is implicit in Segal's analysis [15] that such an alignment reflects the effect of the wall friction and constitutive behavior.

Disorientations among the prominent orientations were calculated for each sample; the maximum disorientation was 55°

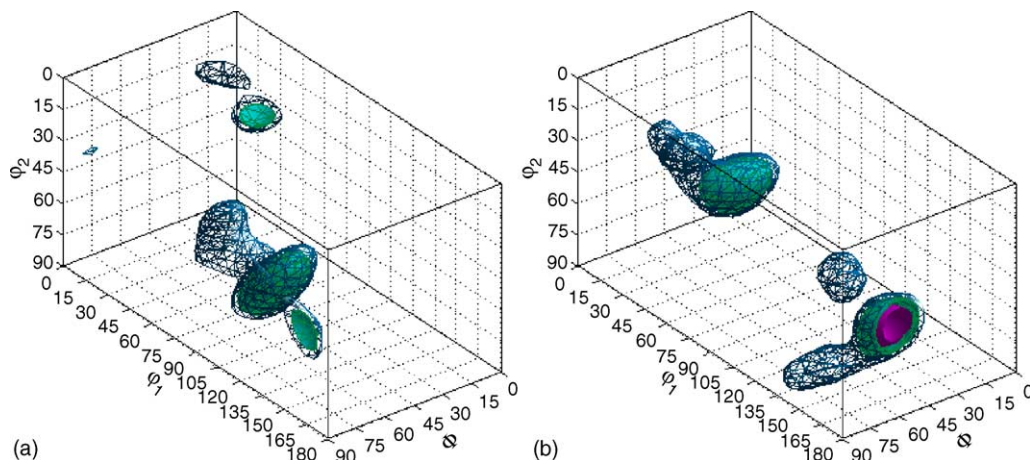


Fig. 3. 3D ODFs for ECAP aluminum processed by route B_C: (a) the 90° sample, four passes and (b) the 135° sample, eight passes. Iso-surfaces correspond to 1/8, 1/4 and 1/2 of the maximum intensity in each case.

Table 1
Prominent texture orientations observed in the 90° and 135° samples

ϕ_2	Experimental orientations	I/I_0	Nearby ideal shear texture components			Δ^b	Color
			Type	Euler angles (°)	FP//SP//SD ^a		
90° sample							
0	35, 35, 0	12	A	35, 45, 0	(0 1 1)//($\bar{1}$ $\bar{1}$ 1)//[2 $\bar{1}$ 1]	10	Red
	75, 45, 0	30	C	90, 45, 90	(0 1 1)//(1 0 0)//[0 $\bar{1}$ 1]	15	Blue
45	120, 90, 45	7	A	125, 90, 45	(1 1 0)//(1 $\bar{1}$ 1)//[$\bar{1}$ 1 2]	5	Red
	165, 90, 45	28	C	180, 90, 45	(1 1 0)//(0 0 1)//[$\bar{1}$ 1 0]	15	Blue
75	85, 45, 75	60	B	100, 45, 75	(4 1 4)//(1 $\bar{8}$ 1)//[$\bar{1}$ 0 1]	15	Blue
135° sample							
0	51, 81, 0	6	–	–	–	–	Green
	135, 82, 0	5	–	–	–	–	Green
45	15, 50, 45	12	B	0, 54, 45	(1 1 1)//(1 1 $\bar{2}$)//[1 $\bar{1}$ 0]	21	Red
	55, 55, 45	33	B	60, 54, 45	(1 1 1)//(2 $\bar{1}$ $\bar{1}$)//[0 $\bar{1}$ 1]	5	Blue
	140, 60, 45	12	B	120, 54, 45	(1 1 1)//(1 $\bar{2}$ 1)//[$\bar{1}$ 0 1]	21	Red
	175, 60, 45	49	B	180, 54, 45	(1 1 1)//($\bar{1}$ $\bar{2}$ 2)//[$\bar{1}$ 1 0]	8	Blue

^a (Flow plane)//(shear plane)//[shear direction].

^b Deviation from ideal position assuming that shear direction// x -axis, shear plane//(x - z) plane in Fig. 1.

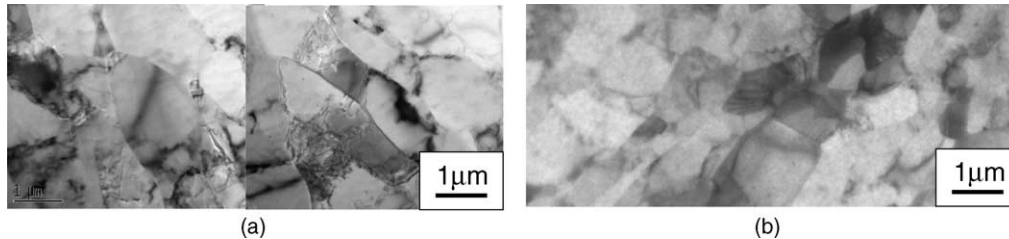


Fig. 4. TEM images of ECAP (route B_C) aluminum: (a) 90° sample, four passes and (b) 135° sample, eight passes.

about $\{1 0 1\}$ for the 90° sample and 35.5° about $\{3 2 0\}$ for the 135° sample. From these data, use of a 90° die results in texture variants of higher disorientation and, thus, is more effective in creating high-angle boundaries than use of a 135° die.

Fig. 4 shows typical TEM micrographs; these images reveal microstructures having comparable (sub)grain sizes ($\sim 1.2 \mu\text{m}$) and morphologies in these two samples. At the resolution of TEM, there is little difference in microstructure and a similar conclusion can be drawn from another study [12]. Comparison of the dimensional scales in Figs. 1 and 4 reveals that the regions examined by TEM may not include all relevant features of the microstructure. In particular, the distribution of the band- or block-like features apparent at a meso-scale in the OIM data would be difficult to establish by TEM examination alone.

4. Conclusions

1. Alternating band- or block-like features are apparent in aluminum after four passes through 90° die and eight passes through 135° die by route B_C.
2. Individual bands correspond to characteristic lattice orientations in the texture.
3. The band- or block-like features have shapes more or less congruent with the shape change of a volume element as it passes through the die-channel intersection.

4. Disorientations between these features are high angle boundaries (up to 55° for the 90° sample and up to 35° in the 135° sample).
5. From analysis of texture data, the shear plane and shear direction are rotated about the flow plane normal, and are almost parallel to the axis of the die exit channel.

Acknowledgements

The authors acknowledge provision of ECAPed materials by Profs. T.G. Langdon (University of Southern California, Los Angeles) and Z. Horita (Kyushu University, Fukuoka, Japan). One of the authors (APZ) thanks the National Research Council of the National Academy of Science (U.S.A.) for financial support.

References

- [1] Y.T. Zhu, T.G. Langdon, R.Z. Valiev, S.L. Semiatin, D.H. Shin, T.C. Lowe (Eds.), *Ultrafine Grained Materials III*, TMS, Warrendale, PA, 2004, 686 p.
- [2] N.A. Smirnova, V.I. Levit, V.I. Pilyugin, R.I. Kuznetsov, L.S. Davydova, V.A. Sazonova, *Fiz. Met. Metalloved.* 61 (1986) 1170.
- [3] Y. Saito, H. Utsunomiya, N. Tsuji, T. Sakai, *Acta Mater.* 47 (1999) 579.
- [4] K. Oh-ishi, T.R. McNelley, *Metall. Mater. Trans. A* 35 (2004) 2951.

- [5] V.M. Segal, V.I. Reznikov, A.E. Drobyshevskiy, V.I. Kopylov, Russ. Metall. (Metally) 1 (1981) 99.
- [6] T.R. McNelley, D.L. Swisher, in: Y.T. Zhu, T.G. Langdon, R.Z. Valiev, S.L. Semiatin, D.H. Shin, T.C. Lowe (Eds.), *Ultrafine Grained Materials III*, TMS, Warrendale, PA, 2004, p. 89.
- [7] A. Gholinia, P. Bate, P.B. Prangnell, *Acta Mater.* 50 (2002) 2121.
- [8] L.S. Tóth, R.A. Massion, L. Germain, S.C. Baik, S. Suwas, *Acta Mater.* 52 (2004) 1885.
- [9] D.L. Swisher, K. Oh-ishi, A.P. Zhilyaev, T.R. McNelley, in press.
- [10] Y. Iwahashi, J. Wang, Z. Horita, M. Nemoto, T.G. Langdon, *Scripta Mater.* 35 (1996) 143.
- [11] K. Xia, J. Wang, *Metall. Mater. Trans. A* 32 (2001) 2639.
- [12] K. Nakashima, Z. Horita, M. Nemoto, T.G. Langdon, *Acta Mater.* 46 (1998) 1589.
- [13] S.D. Terhune, D.L. Swisher, K. Oh-ishi, Z. Horita, T.G. Langdon, T.R. McNelley, *Metall. Trans. A* 33 (2002) 2173.
- [14] G.R. Canova, U.F. Kocks, J.J. Jonas, *Acta Metall.* 32 (1984) 211.
- [15] V.M. Segal, *Mater. Sci. Eng. A* 345 (2003) 36–46.