



UNIVERSITY
OF WOLLONGONG
AUSTRALIA

University of Wollongong
Research Online

Australian Institute for Innovative Materials - Papers

Australian Institute for Innovative Materials

2015

Enhanced electron lifetimes in dye-sensitized solar cells using a di-chromophoric porphyrin: the utility of inter-molecular forces

Long Zhao

University of Wollongong, lz796@uowmail.edu.au

Pawel W. Wagner

University of Wollongong, pawel@uow.edu.au

Holly van der Salm

University of Otago

Keith C. Gordon

University of Otago

Shogo Mori

Shinshu University

See next page for additional authors

Publication Details

Zhao, L., Wagner, P., van der Salm, H., Gordon, K. C., Mori, S. & Mozer, A. J. (2015). Enhanced electron lifetimes in dye-sensitized solar cells using a di-chromophoric porphyrin: the utility of inter-molecular forces. *ACS Applied Materials and Interfaces*, 7 (39), 22078-22083.

Research Online is the open access institutional repository for the University of Wollongong. For further information contact the UOW Library: research-pubs@uow.edu.au

Enhanced electron lifetimes in dye-sensitized solar cells using a di-chromophoric porphyrin: the utility of inter-molecular forces

Abstract

Electron lifetimes in dye-sensitized solar cells employing a porphyrin dye, an organic dye, a 1:1 mixture of the two dyes and a di-chromophoric dye design consisting of the two dyes using a non-conjugated linker were measured, suggesting that the dispersion force of the organic dyes has a significant detrimental effect on the electron lifetime and that the di-chromophoric design can be utilized to control the effect of the dispersion force.

Keywords

electron, lifetimes, dye, sensitized, solar, enhanced, cells, forces, di, chromophoric, porphyrin, utility, inter, molecular

Disciplines

Engineering | Physical Sciences and Mathematics

Publication Details

Zhao, L., Wagner, P., van der Salm, H., Gordon, K. C., Mori, S. & Mozer, A. J. (2015). Enhanced electron lifetimes in dye-sensitized solar cells using a di-chromophoric porphyrin: the utility of inter-molecular forces. *ACS Applied Materials and Interfaces*, 7 (39), 22078-22083.

Authors

Long Zhao, Pawel W. Wagner, Holly van der Salm, Keith C. Gordon, Shogo Mori, and Attila J. Mozer

Article

Enhanced electron lifetimes in dye-sensitized solar cells using a di-chromophoric porphyrin: the utility of inter-molecular forces

Long Zhao, Pawel Wagner, Holly van der Salm, Keith C Gordon, Shogo Mori, and Attila J. Mozer

ACS Appl. Mater. Interfaces, **Just Accepted Manuscript** • Publication Date (Web): 16 Sep 2015Downloaded from <http://pubs.acs.org> on September 22, 2015**Just Accepted**

“Just Accepted” manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides “Just Accepted” as a free service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. “Just Accepted” manuscripts appear in full in PDF format accompanied by an HTML abstract. “Just Accepted” manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are accessible to all readers and citable by the Digital Object Identifier (DOI®). “Just Accepted” is an optional service offered to authors. Therefore, the “Just Accepted” Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the “Just Accepted” Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these “Just Accepted” manuscripts.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Enhanced electron lifetimes in dye-sensitized solar cells using a di-chromophoric porphyrin: the utility of inter-molecular forces

Long Zhao,^a Pawel Wagner,^a Holly van der Salm,^b Keith C. Gordon,^b Shogo Mori^c and Attila J. Mozer^a*

^a ARC Centre of Excellence for Electromaterials Science, Intelligent Polymer Research Institute, University of Wollongong, Wollongong, NSW 2522, Australia. Email: attila@uow.edu.au; Tel: +61242981429

^b MacDiarmid Institute for Advanced Materials and Nanotechnology, Department of Chemistry, University of Otago, Dunedin, New Zealand.

^c Division of Chemistry and Materials, Faculty of Textile Science and Technology, Shinshu University, Ueda, Nagano 386-8567, Japan.

KEYWORDS: porphyrin, organic dye, electron lifetime, intermolecular force, dye-sensitized solar cell

ABSTRACT

1
2
3 Electron lifetimes in dye-sensitized solar cells employing a porphyrin dye, an organic dye, a 1:1
4
5 mixture of the two dyes and a di-chromophoric dye design consisting of the two dyes using a
6
7 non-conjugated linker were measured, suggesting that the dispersion force of the organic dyes
8
9 has a significant detrimental effect on the electron lifetime and that the di-chromophoric design
10
11 can be utilized to control the effect of the dispersion force.
12
13
14
15
16
17
18
19

20 **Introduction**

21
22
23 Retardation of charge recombination between injected electrons and oxidized species of redox
24
25 couples in dye-sensitized solar cells (DSSCs) is still an important issue especially when new
26
27 redox couples are employed.¹⁻³ The recombination can be retarded by surface treatment of the
28
29 TiO₂ surface⁴⁻⁷ and by selecting an appropriate electrolyte to some degree.⁸⁻¹⁰ In addition, the
30
31 electron lifetime has been controlled by tailoring the structure of dyes.^{2,11-14} The addition of alkyl
32
33 chains to dyes is one of the typical strategies.¹⁵ As factors influencing the electron lifetime,¹³ we
34
35 have proposed blocking effect, electrostatic force and dispersion force. The dispersion force of
36
37 dyes attracts redox couples in electrolyte solutions. Thus, when dyes having larger dispersion
38
39 force are employed in DSSCs, it results in faster recombination. The dispersion force is increased
40
41 as the HOMO-LUMO energy gap of dyes is decreased.¹⁴ Thus, if dyes absorb broad range of
42
43 solar spectrum, the dyes attract redox species inherently.
44
45
46
47
48
49

50 While the effect of the dispersion force seems significant, it has not been taken into account
51
52 explicitly to design new dyes. Previously, we reported that dimers, which consist of two
53
54 porphyrin cores connected with a non-conjugated linker, gave longer electron lifetimes than
55
56 porphyrin monomers.¹⁶ The longer electron lifetime was attributed to the addition of a blocking
57
58
59
60

1
2
3 effect without increasing the dispersion force. In view of the light absorption property, the
4
5 absorption spectrum of the dimer was similar to that of the monomer, and thus the optical benefit
6
7 of the dimer was a higher absorption coefficient.¹⁷ In this work, we extend the idea of the non-
8
9 conjugated dye design to obtain not only a longer electron lifetime, but also panchromatic
10
11 absorption by synthesizing a di-chromophoric dye consisting of porphyrin and organic dye
12
13 frameworks. We also demonstrate that this di-chromophoric design can be utilized to control the
14
15 effect of the dispersion force by comparison to individual and mixed monomers.
16
17
18
19
20
21
22
23

24 **Results and discussion**

25
26
27 Fig. 1 shows the UV-vis absorption spectrum of the dyes measured in solution, together with
28
29 their chemical structure. The synthesis and characterization (differential pulse voltammetry) of
30
31 the organic dye **6** and di-chromophoric dye **7** are reported in the Supporting Information, while
32
33 detailed characterization of the porphyrin dye **10** has been reported elsewhere (see Table 1).¹¹
34
35 Organic dye **6** was selected for this study due to its lower onset of absorption (660 nm) and
36
37 nearly twice as large extinction coefficient within the 450 nm to 650 nm wavelength range
38
39 compared to **10**, enabling increased light harvesting when used in a di-chromophoric design. The
40
41 porphyrin and organic dye chromophores are covalently attached using a phenylethenyl linker in
42
43 **7**. As DFT calculations show (see SI Fig. S4 and Fig. S5), the terthiophene unit of the sidechain
44
45 is twisted relative to the porphyrin plane by 64 degrees, preventing the overlap of π orbitals. The
46
47 lack of significant electronic communication in the ground state is evident from Fig. 1 showing
48
49 that the UV-vis absorption of **7** is a simple superposition of the spectrum of **10** and **6**. This is also
50
51 consistent with DFT calculations (see SI Fig. S4 and Fig. S5).
52
53
54
55
56
57
58
59
60

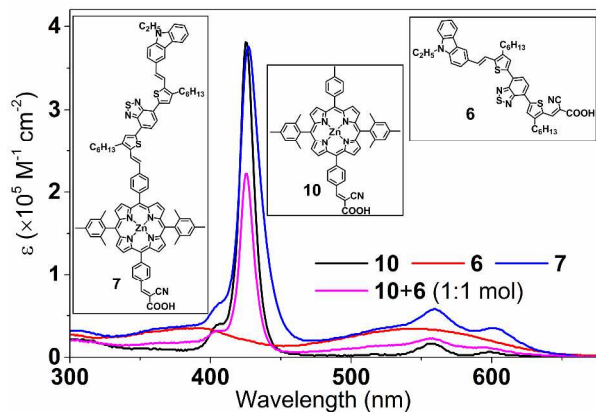


Figure 1. Molar extinction coefficient (ϵ) of the compounds measured in THF. The inset shows the molecular structure of the dyes.

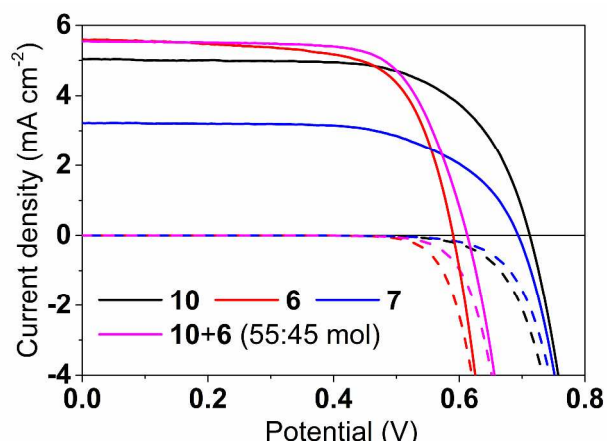


Figure 2. Current density-applied potential curves of DSSC measured under 100 mW cm^{-2} white light (solid lines) and dark (dashed lines). DSSCs were fabricated using $2.0 \pm 0.1 \mu\text{m}$ TiO_2 films.

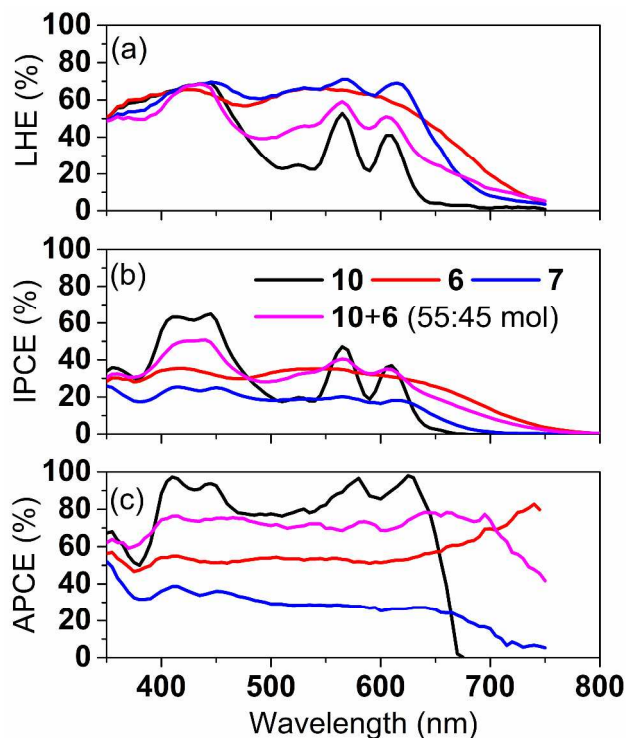


Figure 3. (a) Light harvesting efficiency (LHE), (b) Incident photon to converted electron (IPCE) and (c) Absorbed photon to collected electron (APCE) spectra of DSSCs using 2.0 ± 0.1 μm TiO_2 films.

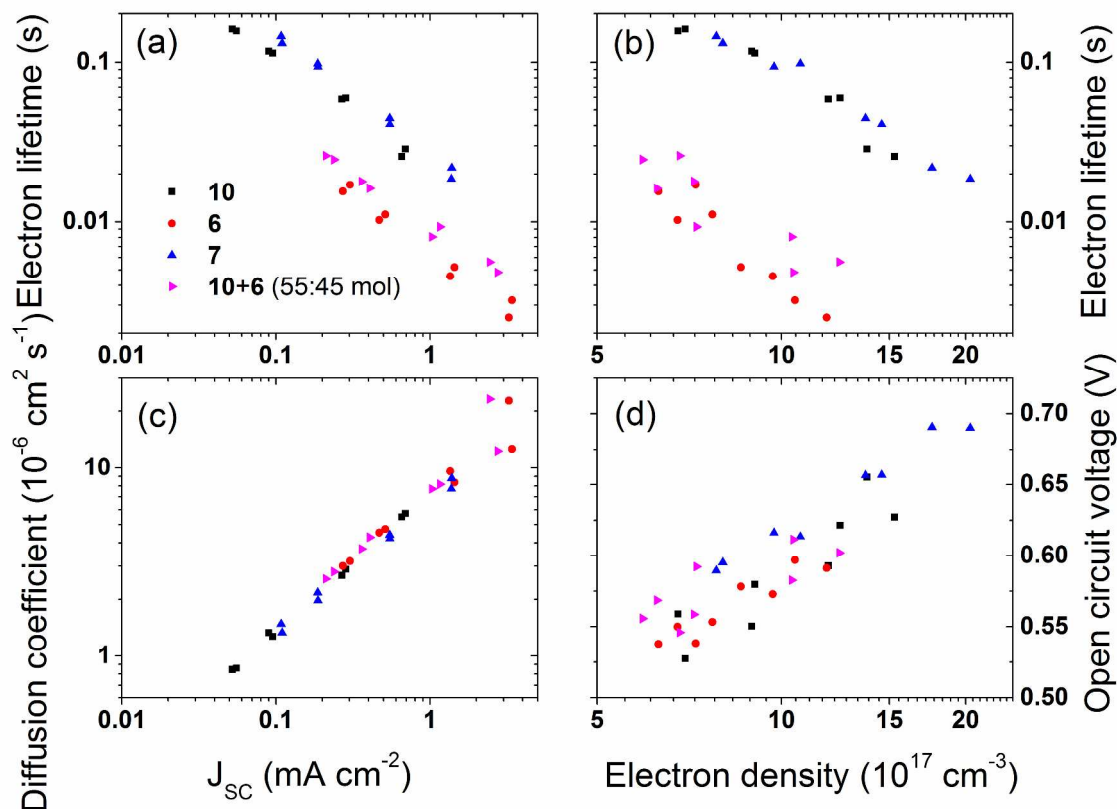


Figure 4. “Full” dye loading experiments; (a) Electron lifetime and (c) diffusion coefficient versus short circuit current density, (b) electron lifetime and (d) open circuit voltage versus electron density for DSSCs using the E1.

Fig. 2 shows the current density versus applied potential curves for DSSCs prepared using **10**, **6**, **7** and the mixture of **10** and **6** using thin, $2.0 \pm 0.1 \mu\text{m}$ transparent TiO_2 films. Measurements were recorded in the dark and under calibrated AM 1.5 100 mW cm^{-2} white light illumination. The organic dye **6** and the **10+6** mixture (approximately 1:1 by mol on surface, 3:1 by mol in solution) achieves the highest short circuit current density (5.6 mA cm^{-2}), a 10% increase compared to **10** and nearly twice as large as **7**. The open circuit voltage of DSSCs using the organic dye **6** is the lowest by 100 mV compared to the porphyrin dye **10**. DSSCs using the **10+6** mixture show 20 mV increase compared to

1
2
3 **6**, while the di-chromophoric porphyrin dye **7** shows 20 mV lower V_{OC} compared to **10**.
4
5 The power conversion efficiency is between 2.3% and 2.4% for DSSCs sensitized by **10**,
6
7 **6**, or the **10+6** dye mixture, while it is significantly lower at 1.4% for the DSSC sensitized
8
9 by dye **7**.
10
11

12
13 Fig. 3 (a) shows the light harvesting efficiency (LHE) of DSSCs calculated using the
14
15 absorption of the dye sensitized thin film and an optical model.¹⁷ The di-chromophoric
16
17 dye **7** has the largest LHE across the whole visible wavelength spectrum peaking around
18
19 70%.
20
21

22
23 Compared to the LHE of **10**, the benefits of attaching the organic chromophore in **7** is
24
25 evident both in a two to three fold increase in LHE values within the 500 nm to 650 nm
26
27 wavelength range, as well as extending LHE by 40 nm to lower photon energies. In
28
29 contrast, the improvement in LHE is less for the **10+6** mixed dye system. This is because
30
31 the total dye loading by **10+6** is 30% less ($0.9 \times 10^{-4} \text{ mol cm}^{-3}$) compared to **10**, **6**, and **7**
32
33 ($1.1 - 1.3 \times 10^{-4} \text{ mol cm}^{-3}$). By co-adsorbing **10** and **6**, the individual chromophores are
34
35 diluted, whereas using the di-chromophoric dye design, the total chromophore
36
37 concentration is doubled, clearly demonstrating the benefits of this approach when thin
38
39 TiO_2 electrodes are used.
40
41
42
43
44
45

46
47 Fig. 3 (b) and (c) show the IPCE and $\text{APCE} = \text{IPCE}/\text{LHE}$ values. The highest peak IPCE values
48
49 are measured for the porphyrin dye **10**. On the other hand, the organic dye **6** and the **10+6** mixed
50
51 dye DSSCs show lower IPCE values but a broader wavelength coverage, giving the higher short
52
53 circuit current densities compared to **10**.
54
55
56
57
58
59
60

1
2
3 The IPCE values measured for **7** are less than half of **10** or **6**, and have a higher energy onset
4 compared to **6** and **10+6**. APCE, which in thin film devices with nearly 100% charge collection
5 efficiency represents injection efficiency, is above 80% for **10** (see ref.¹¹), 50% for **6**, 75% for
6 **10+6**, and 30% for **7**. The APCE values are increased when using the same redox electrolyte
7 without the *tert*-butyl pyridine (*t*BP) additive (E2 electrolyte), causing a 100 mV shift in the open
8 circuit voltage versus charge density plots (see SI Fig. S8 and Fig. S9), suggesting that the TiO₂
9 conduction band edge has shifted positively in agreement with numerous reports in the
10 literature.^{8,12,18-20} A downward shift in the CB edge position leading to increased injection
11 efficiency¹² is the most likely cause for the increased IPCE values. The first reduction potential
12 of **6** and **7** is 300 mV more positive compared to **10**, which suggests the more pronounced
13 increase in IPCE of **6** and **7** using the E2 electrolyte (Table 1). The low IPCE of **7** even using
14 electrolyte E2 can be explained by the unfavorable electronic structure, i.e. the side chain
15 chromophore acting as an electron acceptor when the porphyrin core is photoexcited, creating a
16 competing charge separation pathway to electron injection into TiO₂ (see SI Fig. S8).
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36

37 Fig.4 shows the electron lifetime and diffusion coefficient values determined using transient
38 photovoltage and photocurrent decay measurements, together with using a charge extraction
39 technique to obtain charge density at open circuit voltage condition. Between the monomers, the
40 order of magnitude longer electron lifetime was observed at matched electron density in DSSCs
41 using **10** compared to **6** (Table 1). The difference is mainly due to the ability of complex
42 formation for the porphyrin with *t*BP, that is, the *t*BP could increase the blocking effect and / or
43 reduce the effect of dispersion force of the porphyrin. When *t*BP was removed from the
44 electrolyte, the lifetimes became comparable between the two dyes (see SI Fig. S9). The mixed
45 dye system **10+6** shows only a factor of two increase compared to **10**. The electron lifetime in
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 the mixed dye system appears to be less sensitive to the mixing ratio at lower concentrations of
4 the porphyrin dye **10:6** (15:85, 25:75, 55:45, see SI Fig. S6), with a slight increase when **10** is
5 larger than 50%. Since **6** attracts redox species strongly, the effect of **6** still dominates the
6 electron lifetime. The di-chromophoric dye **7** has the longest electron lifetime with a slight
7 increase compared to **10**. The V_{OC} versus electron density plot shows a less than 50 mV shift.
8 The difference in free energy cannot explain the order of magnitude difference in electron
9 lifetime using the di-chromophoric design. Dispersion force is caused by the induced dipole
10 moment of molecules. The di-chromophoric dye can have induced dipole moment in each
11 chromophore, that is, two dipole moments can be formed in **7**. The longest lifetime with **7**
12 suggests that the effect of the two dipole moments can be controlled individually. The effect of
13 the dispersion force due to the porphyrin core can be reduced by *t*BP in electrolyte, but the force
14 due to the organic framework chromophore is fully effective. Since the organic chromophore is
15 attached on the opposite side to TiO_2 binding group of the porphyrin core, even though the
16 thiophene-based chromophore attracts redox species, the attracted species are located a few
17 nanometers away from the surface of the TiO_2 . Thus, less facilitation of recombination is
18 expected. The organic chromophore can even block the diffusion of the redox species closer to
19 the surface of the TiO_2 , opening the possibility to utilize the dispersion force to elongate the
20 electron lifetime.
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45

46 To test the above hypothesis, electron lifetimes at reduced dye loading were compared in DSSCs
47 using **10** and **7** (Fig. 5). A new batch of TiO_2 films with slightly larger thickness (2.8 μm) were
48 used for these experiments, which resulted in a higher short circuit current density and only small
49 changes in the open circuit voltage at a “full” dye loading conditions (Table 1). As the dye
50 loading is reduced to 12% of the “full” loading condition, the short circuit current and the open
51
52
53
54
55
56
57
58
59
60

1
2
3 circuit voltage for both **10** and **7** drop. Despite the nearly identical short circuit current at these
4
5 reduced dye loading conditions, the open circuit voltage obtained using **7** is 50 mV higher than
6
7 that of **10**. Fig. 5(b) suggests that the higher V_{OC} is due to the five times longer electron lifetime
8
9 at reduced dye loading using **7** compared to **10** at the same electron density (Table 1). The TiO_2
10
11 conduction bottom edge potential remains the same (no shift in electron density versus V_{OC}) as
12
13 shown in Fig. 5(d). The important result is that the electron lifetime using **10** is greatly reduced
14
15 at reduced dye loading, consistent with our previous explanation of blocking effect of bulky *t*BP
16
17 molecules attracted to the Zn porphyrin molecule. At reduced dye loading, the blocking effect is
18
19 expected to diminish as the now exposed TiO_2 surface cannot be effectively blocked by the much
20
21 fewer molecules on the surface. In contrast, the electron lifetime at reduced dye loadings using **7**
22
23 remained long. This is consistent with the proposed dispersion force acting between the organic
24
25 chromophore and triiodide ions. The presence of the largely polarizable organic molecules a few
26
27 nanometres away from the TiO_2 interface, even at low concentrations, is effective to locate
28
29 triiodide ions away from the interface and therefore reduce the electron transfer rate between
30
31 TiO_2 electrons and triiodide ions. The proposed mechanisms are displayed graphically in Fig. 6.
32
33 The above experiments, while do not specifically probe the interaction between the dye
34
35 molecules and triiodide ions, provide a very useful practical guide to increasing electron lifetime
36
37 using low bandgap, hence highly polarizable chromophores using the di-chromophoric concept.
38
39 While the power conversion efficiencies of the dyes are not particularly high, the concept could
40
41 be applied to much more broadly absorption, champions DSSC sensitizers based on porphyrin
42
43 and phthalocyanine dyes with large extended π -conjugation systems.
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60


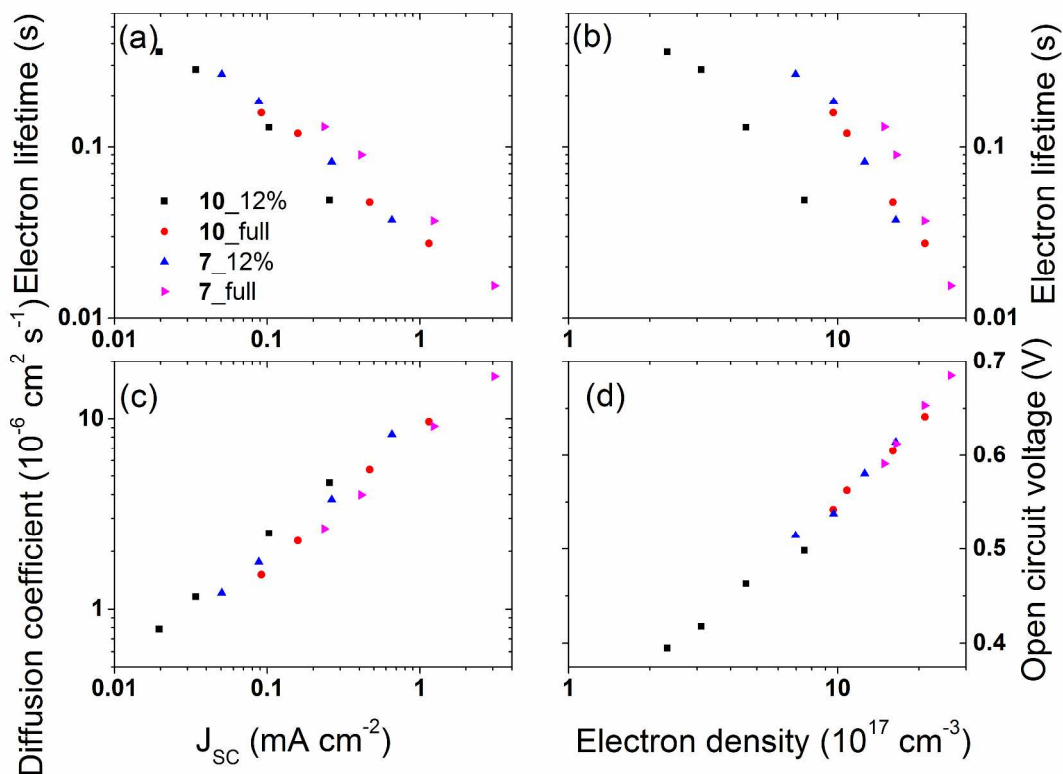


Figure 5. Reduced dye loading experiments: (a) Electron lifetime and (c) diffusion coefficient versus short circuit current density, (b) electron lifetime and (d) open circuit voltage versus electron density for DSSCs using the E1.

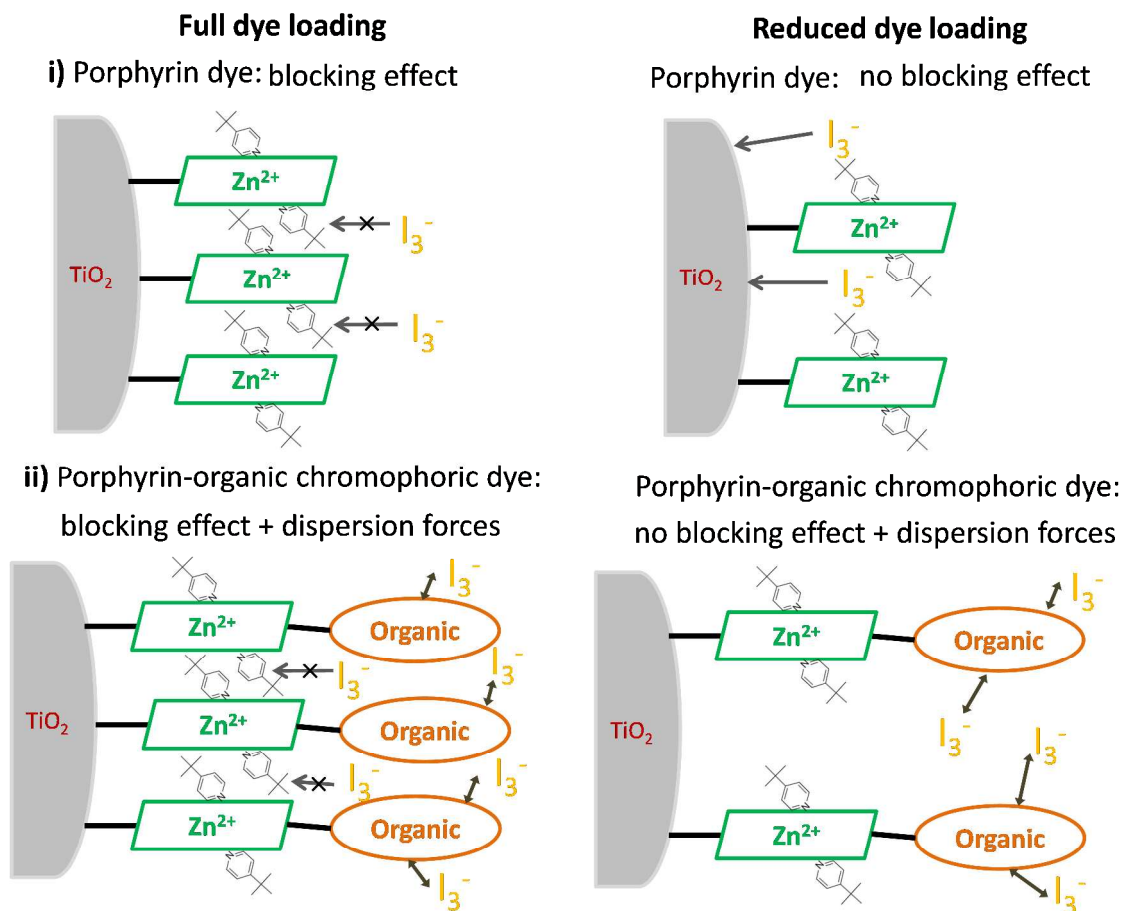

36
37
38
39
40
41
42
43
44
45
46

Figure 6. Graphical illustration of the effect of i) physically blocking the approach of triiodide ions by *t*BP attracted to the Zn porphyrin and ii) dispersion force by the organic chromophore at “full” and reduced dye loadings.

47 48 49 50 51 52 53 54 55 56 57 58 59 60

Conclusion

In summary, dye-sensitized solar cells were prepared with a porphyrin dye, an organic dye, the two dyes or a di-chromophore synthesized with the two dyes' frameworks with a non-conjugated linker. The electron lifetimes in the DSSCs were measured, showing the

1
2
3 dyad and the organic dye gave the longest and the shortest lifetimes, respectively, while
4
5 the porphyrin dye provided slightly shorter electron lifetime than the dyad and the mixed
6
7
8 dyes displayed slightly longer electron lifetime than the organic dye. The results are
9
10 explained by the organic dye having a larger attractive force to acceptor species in the
11
12 electrolytes than the porphyrin dye. When the organic dyes are on the TiO₂ surface, they
13
14 increase the concentration of the acceptor species in the vicinity of the TiO₂ surface. For
15
16 the dyad, the organic dye component is attached on the top of the porphyrin dye, and thus
17
18 the attracted acceptor species by the organic dye component are located far from the TiO₂
19
20 surface. This hypothesis is consistent with electron lifetime measurements at reduced dye
21
22 loadings, which shows a large decrease of the electron lifetime measured for **10**,
23
24
25 consistent with diminishing blocking effect, while remains relative long for **7**. Such
26
27 interpretation leads a design guide for such dyes, that is, the addition of the acceptor
28
29 attraction center to dyes can be utilized to control the recombination, and organic dyes
30
31 can be used as the attraction center.
32
33
34
35
36

37 **Experimental Section**

38
39
40 **The synthesis and chemical analysis** of the compounds is found in the Supporting Information.

41
42
43
44 **UV-visible (UV-vis) absorption spectroscopy** was recorded using a Shimadzu UV-3600
45
46 spectrophotometer in tetrahydrofuran (THF, 99.99%, Honeywell) solution at room temperature.
47
48

49
50 **Dye-sensitized solar cells (DSSCs) fabrication and characterization.** The photoanode
51
52 consisted of a fluorine doped tin oxide glass (FTO glass, 3 mm, 8 Ω/square, Nippon Sheet Glass)
53
54 substrate, spray coated titanium diisopropoxide bis(acetylacetonate) (TAA, 75% in isopropanol,
55
56 Aldrich) as a dense TiO₂ layer, screen-printed mesoporous TiO₂ layer (18-NRT, Dyesol) and a
57
58
59
60

1
2
3 TiCl₄ solution (99.0%, Sigma-Aldrich) post-treatment as the mesoporous layer.¹¹ The size of
4 each device active area was 4 mm × 4 mm. The photocathode was a thermally decomposed Pt
5 layer on FTO glass (2.2 mm, 7 Ω/square, TEC).
6
7
8
9

10
11 The photoanodes were immersed into a dye solution for 1.5 h to achieve dye-sensitization. The
12 solvent was THF (97%, Ajax), which was dried by activated alumina. The concentration of the
13 dyes 10, 7 and 6 was 0.2 mM for the “full” dye loading condition. For the mix dye devices
14 consisting of 10 and 6, three different mole ratios were selected with the total dye concentration
15 of 0.2 mM. The concentrations of 10 and 6 in the 1:3, 1:1 and 3:1 mixtures were 0.05 mM and
16 0.15 mM, 0.1mM and 0.1 mM and 0.15 mM and 0.05 mM, respectively. For the reduced dye
17 loading in Fig. 5, the photoanodes were immersed into a dye solution with the concentration of
18 0.01 mM.
19
20
21
22
23
24
25
26
27
28
29

30
31 The mole ratio in the mixture given in Fig. 1 and Table 1 was calculated for solutions, while for
32 Figs. 2-4 it refers to that on the TiO₂ film.
33
34
35

36
37 E1 electrolyte comprised of 0.6 M 1,2-dimethyl-3-propylimidazolium iodide (DMPIL,
38 synthesized in house), 0.1 M LiI (99.9%, Aldrich), 0.05 M I₂ (99.99%, Aldrich), 0.5 M *tert*-
39 butylpyridine (*t*BP, 96%, Aldrich) in acetonitrile (AN, 99.8%, Sigma-Aldrich): valeronitrile
40 (VN, 99.5%, Sigma-Aldrich) with a v/v ratio of 85:15. E2 electrolyte was same as E1, except it
41 did not contain *t*BP.
42
43
44
45
46
47
48

49
50 **Current density-voltage (J-V) measurements** were carried out using simulated 100 mW cm⁻²
51 AM 1.5 matched white light using a solar simulator (Newport). A Keithley 2400 source measure
52 unit was used for recording the current / voltage response. A 6 mm × 6 mm shadow mask was
53 used.
54
55
56
57
58
59
60

1
2
3 **Incident photon-to-current conversion efficiency (IPCE)** was measured using a QEX10
4 quantum efficiency measurement system (PV measurements). The illumination spot size was
5
6 smaller than the active area of the devices.
7
8

9
10
11 **Light harvesting efficiency (LHE) measurements** of the sensitized films was calculated from
12 the UV-vis absorption of the films, considering the reflection from both photoanode and
13 photocathode, as well as the absorption of the electrolyte.^{17,21}
14
15

16
17
18 **Absorbed photon-to-current conversion efficiency (APCE)** was calculated according to Eq. 1:
19
20

$$21 \quad APCE(\lambda) = \frac{IPCE(\lambda)}{LHE(\lambda)} \quad (1)$$

22
23
24
25
26
27

28 **Stepped light-induced measurements of photocurrent and photovoltage (SLIM-PCV) and**
29 **charge extraction** were carried out using the setup that was described elsewhere.^{11,12} A 635 nm
30 diode laser was employed as the light source. Electron lifetime (τ) was measured by < 1 mV
31 voltage decay after stepping down the laser intensity at open circuit condition. Electron diffusion
32 coefficient (D) was measured by < 10% current decay after stepping down the laser intensity at
33 short circuit condition. Electron density (ED) at open circuit condition was measured using a
34 nanosecond switch (AsamaLab) by switching off the laser totally followed by accumulating the
35 generated electrons using a multimeter (ADCMT 7461A).
36
37
38
39
40
41
42
43
44
45
46
47

48 **The amount of dye loading on TiO₂** was determined by desorbing the dyes from the TiO₂ using
49 0.1 M tetrabutylammonium hydroxide solution (TBAOH, 40 wt.% in water, Fluka) in DMF. The
50 absorbance of the desorbed dye solution was to calculate the dye concentrations. For the mixed
51 dye desorption studies, dye concentrations were calculated from absorbance at 388 nm and 432
52 nm for the organic chromophore and the porphyrin, respectively.
53
54
55
56
57
58
59
60

1
2
3 **Associated content**
4

5
6
7 **Supporting Information**
8

9
10 Material synthesis, Photoluminescence spectra, Differential pulse voltammetry, Energy diagram,
11
12 Detailed DFT calculations and resonance Raman spectroscopy, Detailed photovoltaic
13
14 characterization. This material is available free of charge via the Internet at <http://pubs.acs.org>.
15
16
17
18
19

20
21 **Author information**
22

23
24
25 **Corresponding Author**
26

27 * Email: attila@uow.edu.au
28
29
30
31
32
33

34 **Acknowledgement**
35

36
37
38 AJM, KCG, PW, and SM acknowledge support from the Australian Research Council
39
40 (ARC) through Discovery Project no. DP110102201 and ARC Centre of Excellence for
41
42 Electromaterials Science. AJM acknowledges funding for Australian Research Fellowship
43
44 (ARF). AJM, PW acknowledges support from ANFF. HvdS and KCG acknowledge the
45
46 University of Otago and the MacDiarmid Institute for Advanced Materials and
47
48 Nanotechnology for funding.
49
50
51
52
53
54
55

56 **References**
57
58
59
60

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

(1) O'Regan, B. C.; López-Duarte, I.; Martínez-Díaz, M. V.; Forneli, A.; Albero, J.; Morandeira, A.; Palomares, E.; Torres, T.; Durrant, J. R.: Catalysis of Recombination and Its Limitation on Open Circuit Voltage for Dye Sensitized Photovoltaic Cells Using Phthalocyanine Dyes. *J. Am. Chem. Soc.* **2008**, *130*, 2906-2907.

(2) Mozer, A. J.; Wagner, P.; Officer, D. L.; Wallace, G. G.; Campbell, W. M.; Miyashita, M.; Sunahara, K.; Mori, S.: The Origin of Open Circuit Voltage of Porphyrin-Sensitized TiO₂ Solar Cells. *Chem. Commun.* **2008**, *0*, 4741-4743.

(3) Yum, J.-H.; Baranoff, E.; Kessler, F.; Moehl, T.; Ahmad, S.; Bessho, T.; Marchioro, A.; Ghadiri, E.; Moser, J.-E.; Yi, C.; Nazeeruddin, M. K.; Grätzel, M.: A Cobalt Complex Redox Shuttle for Dye-Sensitized Solar Cells with High Open-Circuit Potentials. *Nat Commun* **2012**, *3*, 631.

(4) Palomares, E.; Clifford, J. N.; Haque, S. A.; Lutz, T.; Durrant, J. R.: Control of Charge Recombination Dynamics in Dye Sensitized Solar Cells by the Use of Conformally Deposited Metal Oxide Blocking Layers. *J. Am. Chem. Soc.* **2003**, *125*, 475-482.

(5) Fabregat-Santiago, F.; García-Cañadas, J.; Palomares, E.; Clifford, J. N.; Haque, S. A.; Durrant, J. R.; Garcia-Belmonte, G.; Bisquert, J.: The Origin of Slow Electron Recombination Processes in Dye-Sensitized Solar Cells with Alumina Barrier Coatings. *J. Appl. Phys.* **2004**, *96*, 6903-6907.

(6) Kopidakis, N.; Neale, N. R.; Frank, A. J.: Effect of an Adsorbent on Recombination and Band-Edge Movement in Dye-Sensitized TiO₂ Solar Cells: Evidence for Surface Passivation. *J. Phys. Chem. B* **2006**, *110*, 12485-12489.

(7) Kay, A.; Grätzel, M.: Dye-Sensitized Core-Shell Nanocrystals: Improved Efficiency of Mesoporous Tin Oxide Electrodes Coated with a Thin Layer of an Insulating Oxide. *Chem. Mater.* **2002**, *14*, 2930-2935.

(8) Nakade, S.; Kanzaki, T.; Kubo, W.; Kitamura, T.; Wada, Y.; Yanagida, S.: Role of Electrolytes on Charge Recombination in Dye-Sensitized TiO₂ Solar Cell (1): The Case of Solar Cells Using the I-/I₃- Redox Couple. *J. Phys. Chem. B* **2005**, *109*, 3480-3487.

(9) Fabregat-Santiago, F.; Bisquert, J.; Garcia-Belmonte, G.; Boschloo, G.; Hagfeldt, A.: Influence of Electrolyte in Transport and Recombination in Dye-Sensitized Solar Cells Studied by Impedance Spectroscopy. *Sol. Energy Mater. Sol. Cells* **2005**, *87*, 117-131.

(10) Ozawa, H.; YukiTawaraya; Arakawa, H.: Effects of the Alkyl Chain Length of Imidazolium Iodide in the Electrolyte Solution on the Performance of Black-Dye-Based Dye-Sensitized Solar Cells. *Electrochim. Acta* **2015**, *151*, 447-452.

(11) Zhao, L.; Wagner, P.; Elliott, A. B. S.; Griffith, M. J.; Clarke, T. M.; Gordon, K. C.; Mori, S.; Mozer, A. J.: Enhanced Performance of Dye-Sensitized Solar Cells Using Carbazole-Substituted Di-Chromophoric Porphyrin Dyes. *J. Mater. Chem. A* **2014**, *2*, 16963-16977.

(12) Zhao, L.; Wagner, P.; van der Salm, H.; Clarke, T. M.; Gordon, K. C.; Mori, S.; Mozer, A. J.: Dichromophoric Zinc Porphyrins: Filling the Absorption Gap between the Soret and Q Bands. *J. Phys. Chem. C* **2015**, *119*, 5350-5363.

(13) Miyashita, M.; Sunahara, K.; Nishikawa, T.; Uemura, Y.; Koumura, N.; Hara, K.; Mori, A.; Abe, T.; Suzuki, E.; Mori, S.: Interfacial Electron-Transfer Kinetics in Metal-Free Organic Dye-Sensitized Solar Cells: Combined Effects of Molecular Structure of Dyes and Electrolytes. *J. Am. Chem. Soc.* **2008**, *130*, 17874-17881.

(14) Marinado, T.; Nonomura, K.; Nissfolk, J.; Karlsson, M. K.; Hagberg, D. P.; Sun, L.; Mori, S.; Hagfeldt, A.: How the Nature of Triphenylamine-Polyene Dyes in Dye-Sensitized

1
2
3 Solar Cells Affects the Open-Circuit Voltage and Electron Lifetimes. *Langmuir* **2009**, *26*, 2592-
4 2598.

5 (15) Koumura, N.; Wang, Z.-S.; Mori, S.; Miyashita, M.; Suzuki, E.; Hara, K.: Alkyl-
6 Functionalized Organic Dyes for Efficient Molecular Photovoltaics. *J. Am. Chem. Soc.* **2006**,
7 *128*, 14256-14257.

8 (16) Sunahara, K.; Griffith, M. J.; Uchiyama, T.; Wagner, P.; Officer, D. L.; Wallace,
9 G. G.; Mozer, A. J.; Mori, S.: A Nonconjugated Bridge in Dimer-Sensitized Solar Cells Retards
10 Charge Recombination without Decreasing Charge Injection Efficiency. *ACS Appl. Mater.*
11 *Interfaces* **2013**, *5*, 10824-10829.

12 (17) Mozer, A. J.; Griffith, M. J.; Tsekouras, G.; Wagner, P.; Wallace, G. G.; Mori, S.;
13 Sunahara, K.; Miyashita, M.; Earles, J. C.; Gordon, K. C.; Du, L.; Katoh, R.; Furube, A.; Officer,
14 D. L.: Zn-Zn Porphyrin Dimer-Sensitized Solar Cells: Toward 3-D Light Harvesting. *J. Am.*
15 *Chem. Soc.* **2009**, *131*, 15621-15623.

16 (18) Jennings, J. R.; Wang, Q.: Influence of Lithium Ion Concentration on Electron
17 Injection, Transport, and Recombination in Dye-Sensitized Solar Cells. *J. Phys. Chem. C* **2009**,
18 *114*, 1715-1724.

19 (19) Boschloo, G.; Häggman, L.; Hagfeldt, A.: Quantification of the Effect of 4-tert-
20 Butylpyridine Addition to I-/I³⁺- Redox Electrolytes in Dye-Sensitized Nanostructured TiO₂
21 Solar Cells. *J. Phys. Chem. B* **2006**, *110*, 13144-13150.

22 (20) Kelly, C. A.; Farzad, F.; Thompson, D. W.; Stipkala, J. M.; Meyer, G. J.: Cation-
23 Controlled Interfacial Charge Injection in Sensitized Nanocrystalline TiO₂. *Langmuir* **1999**, *15*,
24 7047-7054.

25 (21) Kubo, W.; Sakamoto, A.; Kitamura, T.; Wada, Y.; Yanagida, S.: Dye-Sensitized
26 Solar Cells: Improvement of Spectral Response by Tandem Structure. *J. Photochem. Photobiol.,*
27 *A* **2004**, *164*, 33-39.
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Table 1. Optical and electrochemical properties of the compounds

-	Abs.		λ_{onset} (nm)	DPV			J-V performance					τ (s) at $ED = 1.5 \times 10^1$ cm^{-3}
	λ_{max} (nm)	$(\times 10^5 \text{ M}^{-1} \text{ cm}^{-1})$		E_{Re} (V vs. Fc/Fc ⁺)	E_{Ox} (V vs. Fc/Fc ⁺)	ΔE (eV)	J_{SC} (m A cm^{-2})	V_{OC} (mV)	FF	η (%)	Dye loading ($\times 10^{-4}$ mol cm^{-3})	
10[#]	426, 557, 599	3.80, 0.16, 0.07	620	-1.97	0.30, 0.59, 0.85	2.27	5.04	715	0.6 6	2.3 9	1.1	0.029
6[#]	392, 548	0.35, 0.34	663	-1.62	0.30, 0.83	1.92	5.59	595	0.6 8	2.2 5	1.2	0.002
7[#]	427, 560, 602	3.78, 0.58, 0.35	660	-1.67, - 1.97	0.30, 0.40, 0.91	1.97	3.22	695	0.6 4	1.4 3	1.3	0.040
10+6[#] (55:4 5 mol)	426, 558, 596	2.75, 0.19, 0.10	625	-	-	-	5.54	615	0.7 1	2.4	0.5+0. 4	0.003
10	-	-	-	-	-	-	6.67	705	0.5 6	2.6 4	1.2	0.053
10	-	-	-	-	-	-	2.63	605	0.6 3	1	0.14	0.012
7	-	-	-	-	-	-	5.91	695	0.6 6	2.7	1.4	0.117
7	-	-	-	-	-	-	2.15	655	0.6 7	0.9 4	0.16	0.052

[#]TiO₂ thickness 2.2 μm , ^{*}TiO₂ thickness 2.8 μm

#

Table of contents

