



*Citation for published version:*

Casanova, S, Liu, TY, Chew, J, Livingston, AG & Mattia, D 2020, 'High flux thin-film nanocomposites with embedded boron nitride nanotubes for nanofiltration', *Journal of Membrane Science*, vol. 597, 117749. <https://doi.org/10.1016/j.memsci.2019.117749>

*DOI:*

[10.1016/j.memsci.2019.117749](https://doi.org/10.1016/j.memsci.2019.117749)

*Publication date:*

2020

*Document Version*

Peer reviewed version

[Link to publication](#)

*Publisher Rights*

CC BY-NC-ND

## University of Bath

### Alternative formats

If you require this document in an alternative format, please contact:  
[openaccess@bath.ac.uk](mailto:openaccess@bath.ac.uk)

**General rights**

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

**Take down policy**

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

# 1 High Flux Thin-Film Nanocomposites with Embedded Boron Nitride 2 Nanotubes for Nanofiltration

3 *Serena Casanova,<sup>†‡</sup> Tian-Yin Liu,<sup>§</sup> Yong-Min J. Chew,<sup>†‡</sup> Andrew Livingston,<sup>§\*\*</sup> Davide Mattia<sup>†‡\*</sup>*

4 <sup>†</sup>Department of Chemical Engineering, University of Bath, BA2 7AY, UK

5 <sup>‡</sup>Centre for Advanced Separations Engineering, University of Bath, BA2 7AY, UK

6 <sup>§</sup>Department of Chemical Engineering, Imperial College London, South Kensington Campus, SW7 2AZ, UK

7 <sup>\*\*</sup>Department of Engineering and Material Sciences, Queen Mary University of London, London E1 4NS, UK

8

9 \* Address correspondence to [d.mattia@bath.ac.uk](mailto:d.mattia@bath.ac.uk)

## 10 **Abstract**

11 A novel thin film nanocomposite (TFN) membrane was obtained by incorporating boron nitride  
12 nanotubes (BNNTs) into a polyamide (PA) thin selective layer prepared via interfacial  
13 polymerisation. The addition of just 0.02 wt% of BNNTs led to a 4-fold increase in pure water  
14 permeance with no loss in rejection for divalent salts, methylene blue or humic acid compared  
15 to the pure PA membrane. Loadings higher than 0.02 wt% of BNNTs led to agglomeration  
16 with overall loss of performance. For the membranes containing 0.02 wt% BNNTs, the pure  
17 water permeance was 4.5 LMH@bar, with > 90% rejection of MgSO<sub>4</sub> and > 80% rejection of  
18 CaCl<sub>2</sub>. Fouling tests with humic acid showed a flux recovery ratio of > 95% with ~50% lower  
19 flux loss during the fouling cycle compared to the polyamide only membrane. These values  
20 represent a significant improvement over both commercial polyamide membranes and TFN  
21 membranes incorporating carbon nanotubes. We assert that the very small quantity of BNNTs  
22 needed to produce the enhanced performance opens the way to their use in water treatment  
23 applications where nanofiltration membranes are subject to severe organic fouling.

24

25

26 **Keywords:** Boron nitride nanotubes; Chemical vapour deposition; Interfacial Polymerisation; Nanofiltration

27

## 28      **1. Introduction**

29      Polymeric nanofiltration (NF) membranes have become a mainstay of water treatment  
30      processes, with high recovery rates [1], facile modular scale up [2] and economic viability  
31      across a broad range of feed [3]. NF membranes are particularly effective for the combinatorial  
32      rejection of salts, organic compounds, natural organic matter (NOM), and dyes. [4]. Industry,  
33      however, still faces challenges including high energy costs per unit volume of water purified  
34      [5], handling of retentate waste [6], membrane fouling, and a fundamental understanding of the  
35      mechanisms underlying the purification of complex feeds [7].

36      Thin-film composite (TFC) membranes composed of a very thin, dense selective layer  
37      supported by a porous support combine high flux and rejection with mechanical stability.  
38      Although TFC membranes are successfully used commercially [8], there is still need to  
39      increase efficiency, reduce energy consumption and extend chemical stability [9]. Many  
40      approaches have been explored to improve the performance of TFCs, including diverse  
41      fabrication methods, and the tuning of precursors used to fabricate the membranes [10].  
42      Another promising strategy is the incorporation of inorganic nanomaterials in the thin selective  
43      layer to form so-called thin-film nanocomposite (TFN) membranes [7]. Nanomaterial additions  
44      alter the structure of the selective layer by finely tuning properties such as hydrophilicity [11],  
45      porosity [12], surface zeta potential [13] and stability [14, 15]. Additionally, the nanomaterials  
46      can introduce desired features such as fouling resistance [16], adsorption [17] and  
47      photocatalytic characteristics [18] into the membranes.

48      Amongst the wide range of nanomaterials tested to date [2], carbon nanotubes (CNTs) have  
49      been considered for application in membrane technology due to their fast water transport and  
50      low tortuosity [19]. The reduced friction of water on the defect-free carbon surface in these  
51      nanotubes results in very high water permeances through the tubes [20], translating into higher  
52      efficiency (i.e. higher flux) per applied pressure [21]. However, efforts to create membranes  
53      with the CNTs aligned perpendicularly to the membrane's surface in a commercially scalable  
54      fashion have been have been, so far, unsuccessful [22-24]. On the other hand, the incorporation  
55      of randomly aligned CNTs in polymer matrices has led to the successful formation of selective  
56      membranes [25], but with only modest increases in water permeance and a decrease in  
57      selectivity [26, 27]. While the former can be attributed to the small fraction of tubes directly  
58      connecting feed and permeate, the latter is attributed to the formation of uncontrolled  
59      permeation pathways at the interface between the CNTs and the polymer, due to poor chemical

60 compatibility [28]. This aspect has been addressed by introducing an additional  
61 functionalisation step with acid groups, to form hydroxyl and carboxyl groups on the tube  
62 surface [29]. The functionalised CNTs have been added in relatively large amounts (1 wt% -  
63 10 wt%), with a corresponding increase in rejection of up to 5% and providing permeances up  
64 to 50% higher than those of the starting polyamide membrane [30, 31]. CNTs have also been  
65 functionalised with more complex zwitterion groups. However, these have penalised the water  
66 permeance when compared to pristine CNTs, though improving the rejection of NaCl from  
67 97.6% to 98.5% thanks to the steric hindrance of the zwitterion functional groups [32]. Despite  
68 these promising results, the potential for permeance increase is limited by the low loadings of  
69 hydrophobic nanomaterials that can be incorporated into the membrane matrix before the onset  
70 of agglomeration, which leads to the formation of pinholes, with a subsequent loss of  
71 performance [33].

72 Herein, boron nitride nanotubes (BNNTs) are investigated as nanomaterials for TFN  
73 fabrication. We speculate that their physico-chemical characteristics will overcome some of  
74 the limitations of CNT-based TFNs highlighted above. Hexagonal BNNTs (*hBN*) are  
75 isostructural to graphitic CNTs, but behaving as electrical insulators and showing higher  
76 resistance to oxidation [34]. Molecular dynamics simulations on BNNTs in the subcontinuum  
77 range, with diameters 0.8 nm, have shown faster pure water flux than in CNTs [35]. For such  
78 small diameters it was shown that increased van der Waals and electrostatic interactions  
79 between the nanotube walls and the water molecules contribute to an easier filling of the bore  
80 of BNNTs than for CNTs [36]. However, when the diameters of the tubes studied were larger,  
81 CNTs outperformed BNNTs in terms of improved water fluxes [37]. This was ascribed to  
82 differences in the electronic landscape in the two nanotube walls [38]. Simulations also showed  
83 that BNNTs have tunable cation and anion selective properties due to the partial charge on the  
84 boron and nitrogen atoms of the nanotube [39] and osmotic energy storage capabilities [40].  
85 Additionally, when boron nitride nanosheets were recently embedded in mixed matrix  
86 membranes, they showed improved fouling resistance [26]. Boron nitride nanotubes have  
87 recently been used to fabricate ultrafiltration membranes with improved thermal resistance and  
88 mechanical stability [41]. Moreover, CNTs have been shown to have antioxidant capabilities  
89 that slow down chlorine attack on polymeric membranes [28], however this effect is as yet  
90 unreported for BNNTs. Using BNNTs as membrane nanofillers is motivated, together with its  
91 novelty, by the fact that materials with high negative zeta potentials allow for rejection of  
92 pollutants not only by size but also by charge [42].

93 Despite the many potential advantages of BNNTs over CNTs, there has been notably less  
94 published research on BNNTs than on their carbon counterparts, attributed mainly to the lack  
95 of methods for the production of BNNTs at scale [34]. This obstacle has been overcome in this  
96 work, optimising a known technique [43] for the production of BNNTs by chemical vapour  
97 deposition (CVD). The nanomaterial was then embedded in the selective phase of an  
98 interfacially polymerised polyamide (PA-BNNT) membrane. BN is negatively charged in  
99 water over a broad pH range [44] and can adsorb OH<sup>-</sup> on its surface further increasing its  
100 negative charge [40].

## 101 **2. Materials and Methods**


### 102 **2.1 Materials**

103 Boron (B, ≥ 95%), magnesium oxide (MgO, ≥ 99.99%), iron oxide (Fe<sub>2</sub>O<sub>3</sub>, ≥ 99.9%) and MgO  
104 nanopowder (average particle size ≤ 50 nm, measured by BET [45]) were purchased from  
105 Sigma Aldrich. Ethanol (≥ 99%) was purchased from Fisher Scientific. P-type silicon wafers  
106 polished on one side were purchased by Agar Scientific. Hydrochloric acid (38%) was  
107 purchased from Sigma Aldrich. Commercial polyether sulfone (PES) membrane Microdyn  
108 Nadir PMUP010 with 10 kDa nominal molecular weight cut-off was purchased from Steriltech.  
109 Deionised (DI) water was used unless specified otherwise. Methanol (MeOH, anhydrous,  
110 99.8%), Piperazine (PIP, 99%) ReagentPlus®, with MW86, n-hexane (anhydrous, 95%) and  
111 trimesoyl chloride (TMC, 99%) were purchased from Sigma Aldrich. Diiodomethane (DIM,  
112 99%) was purchased from Sigma Aldrich. Salts (*e.g.*, NaCl, CaCl<sub>2</sub> and MgSO<sub>4</sub>) were purchased  
113 from Sigma Aldrich. Sodium hypochlorite technical solution was purchased from Fischer  
114 Scientific.

### 115 **2.2 BNNTs synthesis**

116 BNNTs synthesis (Fig. 1) with ammonia gas and boron powder precursors was catalysed by  
117 Fe<sub>2</sub>O<sub>3</sub> and MgO catalysts with a molar ratio of B:MgO:Fe<sub>2</sub>O<sub>3</sub> = 2:1:1. B, MgO and Fe<sub>2</sub>O<sub>3</sub> were  
118 pre-mixed at 250 r.p.m. for 12 h in a Fritsch Pulverisette P6 planetary ball mill, half filling a  
119 45 ml stainless steel grinding bowl with 2.2 g of B, MgO and Fe<sub>2</sub>O<sub>3</sub> in an ethanol suspension  
120 and 18 grinding balls with 5 mm diameter. After ball milling, 5 ml of precursor was poured in  
121 a Coors™ alumina combustion boat, which was then capped with a silicon wafer previously  
122 seeded with MgO nanopowder. The closed boat was then placed in a 15 cm long quartz test

123 tube (ID 18 mm, OD 19 mm) facing the gas inlet in the centre of a quartz tube reactor (H-  
124 Baumbach, ID 20 mm, OD 22 mm) in a three sections horizontal TZF 12/38/850 type  
125 CARBOLITE tubular furnace. Temperatures inside the furnace were monitored by external  
126 thermocouples. Gas flows were controlled with Omega FMA 5400A/5500A series mass flow  
127 controllers (MFCs) regulated by a LabVIEW program. The tube reactor was abundantly  
128 flushed with Ar and then let ramp up at 10 °C/min up to 1100 °C under a 200 sccm Ar flow.  
129 Then, the gas flow was switched to 145 sccm NH<sub>3</sub> and the temperature increased to 1200 °C at  
130 the same heating rate. This maximum temperature was kept for 1 hour before letting the system  
131 cool down to room temperature under a 200 sccm Ar stream. The exhaust NH<sub>3</sub> gas was  
132 neutralized with a sulphuric acid scrubber, generating ammonium sulphate salts. The BN  
133 nanotubes white powder was gently removed with a stainless steel spatula by scratching it from  
134 the silicon substrate and boat top and sides. The unreacted boron in the collected white powder  
135 was removed in air at 700 °C for 2 hours, where it reacted to form boric anhydrite vapour.  
136 BNNTs have high thermal stability and are resistant to oxidation up to 950 °C [45]. Catalysts  
137 were removed with a 3 hours 10% HCl (purity 36.5-38.0%, purchased from Sigma Aldrich)  
138 water cleaning at 40 °C, followed by washing of the products in DI water by vacuum filtration  
139 using a 0.45 µm pore size nylon membrane (Pall Corporation).

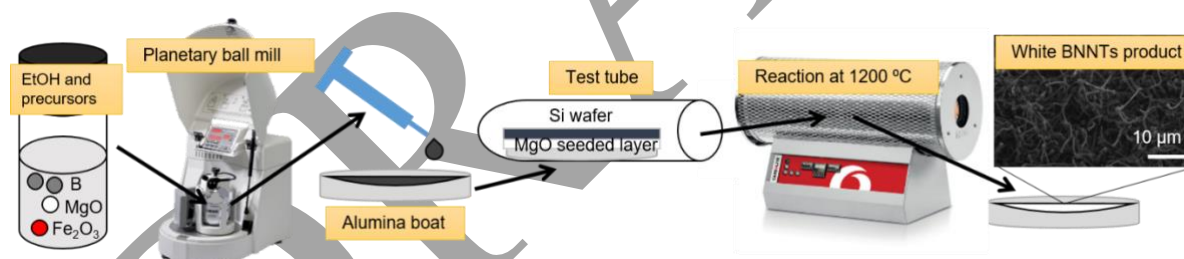

140  
141 **Fig. 1** Schematic of the CVD of boron nitride nanotubes production.

### 142 **2.3 Polyamide membrane fabrication**

143 The PA-BNNTs membranes were synthesized by interfacial polymerisation following an  
144 established vacuum filtration technique [46], which has been recently used for the fabrication  
145 of nanocomposite membranes [47]. The PES support membrane (Microdyn Nadir PMUP010)  
146 was cut in discs with 5.5 cm in diameter, and then flushed with 20 ml of water in a filtration  
147 setup prior to synthesis. Then, 1 wt% PIP aqueous solution (MeOH:H<sub>2</sub>O 50:50 v/v%) solution  
148 was prepared by rapidly dissolving the PIP flakes. For the PA-BNNT membranes, 0.01, 0.02  
149 or 0.03 wt% BNNTs were dispersed in the amine solution by ultrasonication for 1 h (Table 1).  
150 Then, 25 ml amine solution or amine solution with dispersed BNNT was pumped through the

151 support membrane until the entire amount of solution was filtered, while ensuring the  
 152 membrane remained wet. Subsequently, any residual drops on the side of the wetted membrane  
 153 were removed by using an air gun to avoid the formation of defects in the resulted amine-rich  
 154 film. In the interfacial polymerisation, a 0.8 wt% TMC n-hexane solution statically contacted  
 155 the amine-saturated support in the filtration setup. The reaction time was 3 min. The residual  
 156 organic solution was discarded, and the membrane was quenched with n-hexane for 1 min.  
 157 After reaction, the membrane was left to dry at room temperature for 24 h. Similarly, a thin  
 158 film was formed by contacting 1 ml of PIP solution with 1ml of TMC solution, specifically for  
 159 the analysis of a free standing film at the interface.

160 Membranes with different concentration of BNNTs in the starting solution were prepared; their  
 161 nomenclature, PIP solution composition, and the estimated weight of nanofiller deposited per  
 162 unit area by filtering 25 ml of amine solution are reported in Table 1. The concentrations to be  
 163 investigated were chosen in a range where no obvious large agglomeration could be observed  
 164 on the membrane top surface with the naked eye. It should be noted that there is an uncertainty  
 165 in the estimation of the amount of BNNTs per unit area, due to the possibility that some minor  
 166 fraction of nanomaterial filtered through the PES support.

167 **Table 1** Composition of the PIP solutions in MeOH:H<sub>2</sub>O 50:50 v/v% for the PA-BNNTs membranes.

Membrane	PIP (wt%)	MeOH/H <sub>2</sub> O (wt%)	BNNTs (wt%)	$c_S$ (mg/cm <sup>2</sup> )
PA-BARE	1.00	99.00	0.00	0.000
PA-BNNTs0.01	1.00	98.99	0.01	0.096
PA-BNNTs0.02	1.00	98.98	0.02	0.193
PA-BNNTs0.03	1.00	98.97	0.03	0.283

168

#### 169 **2.4 Characterisation of BNNTs powders**

170 The produced nanotubes were coated with 5 nm of chromium and positioned on carbon tape  
 171 for analysis with a JEOL JSM-6301F FESEM at 5kV. JEOL JSM-2100Plus TEM samples were  
 172 prepared by dispersing the nanotubes in ethanol. Two to five drops of the sample were then  
 173 placed on a TEM window (Lacey carbon purchased from EM Resolutions) until a desirable  
 174 concentration was reached. Analysis of structural features with ImageJ was done on a minimum  
 175 of 10 measurements. Optical Images of the substrates with BNNTs grown on them were taken  
 176 with a Digital Microscope VHX-6000 series. Raman spectroscopy was carried out on the as-  
 177 synthesized samples on a glass slide in a Renishaw Raman Microscope series 1000 using a  
 178 frequency-doubled argon ion laser (wavelength 244 nm, 5.08 eV) with spectral resolution of

179 5 - 10 cm<sup>-1</sup> and a 40 × UV objective lens. XRD tests of products of the synthesis were reduced  
180 into fine powders dispersed on a silicon wafer were carried on 1 mg of product with a Bruker  
181 D8 Advance for 10 < 2θ < 70 with a Vantec detector with Cu K-alpha radiation.

182 XPS was performed on powdered BNNTs samples using a Thermo Fisher Scientific K-alpha+  
183 spectrometer. Samples were analysed using a micro-focused monochromatic Al x-ray source  
184 (72 W) over an area of approximately 400 microns. Data was recorded at pass energies of 150  
185 eV for survey scans and 40 eV for high resolution scan with 1 eV and 0.1 eV step sizes  
186 respectively. Charge neutralisation of the sample was achieved using a combination of both  
187 low energy electrons and argon ions. Data analysis was performed in CasaXPS using a Shirley  
188 type background and Scofield cross sections, with an energy dependence of -0.6.

### 189 **2.5 Polyamide membrane characterisation**

190 Membranes were coated with 10 nm of Cr before imaging in a JEOL JSM-6301F FESEM.  
191 Micrographs were taken at 5kV. Atomic Force Microscopy (AFM) Nanosurf EasyScan 2 Flex  
192 scans were taken by using the Dynamic Force Mode with a 190Al-G tip on areas 5 μm × 5 μm  
193 with 256 points/line. The data was analysed with Gwyddyion and the software's internal  
194 functions were used to assess the membrane's average roughness ( $R_a$ ). Dataphysics Optical  
195 Contact Angle (OCA) Measuring Device with 0.5 μl wetting liquid drops was also used to  
196 characterise the membranes. The Young's contact angle ( $\theta_Y$ ) on a flat smooth surface is related  
197 to the measured contact angle ( $\theta_W$ ) via the Wenzel equation [48]:

$$\cos\theta_W = r \cos\theta_Y, \quad (1)$$

198 where  $r$  is the ratio between the membrane surface area and the projected area, obtained by  
199 AFM.

200 The surface zeta potential of samples with dimensions 2 × 1 cm or 1 × 1 cm was measured in  
201 a SurPASS electrokinetic analyser with adjustable gap cell in a pH range between 3 and 10.  
202 For each pH value, the measurement was repeated four times. A Perkin Elmer Spectrum FTIR-  
203 ATR Spectrometer was used to characterise the membranes' selective layer surface, with 16  
204 scans per run between 600 and 4000 cm<sup>-1</sup> and a spatial resolution of 2 cm<sup>-1</sup>.

205 Sections of the polyamide membranes top surface measuring 1 cm × 1 cm were also analysed  
206 by XPS. The ratio O/N from the XPS analysis was measured to assess the degree of  
207 crosslinking in relation to loading percentage. This was calculated from



$$crosslinking (\%) = \left( \frac{(O/N)_{XPS} - (O/N)_{fully\ cross-linked}}{(O/N)_{fully\ linear} - (O/N)_{fully\ cross-linked}} \right), \quad (2)$$

208 where  $(O/N)_{XPS}$  is the oxygen to nitrogen ratio obtained experimentally, neglecting the 398  
 209 eV contribution of the *h*BN nitrogen [49].  $(O/N)_{fully\ linear}$  and  $(O/N)_{fully\ crosslinked}$  are the  
 210 ratios for a fully linear and fully crosslinked polyamide, respectively [50].

211 Phillips CM200 TWIN TEM samples were prepared by gently depositing a thin film on a TEM  
 212 window and imaging it at 250 and 25k magnification.

### 213 **2.6 Membrane filtration performance**

214 Pure water flow was tested in cross flow mode (schematics in [26]) on a minimum of three  
 215 membranes per composition, with 24 h of compaction at 7 bar and three days of testing at 3  
 216 bar.

217 Dye and salts rejection was tested for 7 h with a 45 L h<sup>-1</sup> pump flow rate. Rejection of methylene  
 218 blue was assessed using a UV spectrophotometer (UV Cary 100, Agilent, U.K.), while rejection  
 219 of the salts was measured using an Orion Versastar ThermoScientific conductivity meter. The  
 220 feed concentration for the dye tests was 0.01 g L<sup>-1</sup>, whilst for salts rejection it ranged from 500  
 221 to 2000 ppm.

222 Humic acid fouling tests were performed on pre-compacted membranes in cross flow mode.  
 223 The 2.5 L feed of 1 g L<sup>-1</sup> humic acid in water was prepared beforehand and mixed with a  
 224 magnetic stirrer for 24 hours before the test. The fouling test consisted of two fouling cycles of  
 225 15 hours and two cleaning cycles of one hour each. The flow rate was set as 175 ml min<sup>-1</sup>  
 226 (Reynolds number,  $Re = 130$ ) and 750 ml/min ( $Re = 550$ ) for fouling and cleaning respectively.  
 227 Flux recovery ratio (*FRR*) was measured before each cycle as follows:

$$FRR (\%) = \left( \frac{J_{AF}}{J_{BF}} \right) \times 100, \quad (3)$$

228 where  $J_{BF}$  and  $J_{AF}$  are the two fluxes before fouling and after cleaning, calculated for each  
 229 cycle.

230 The membrane total resistance ( $R_t$ ) after 15 hours of fouling test was also calculated:

$$R_t = R_m + R_r + R_{ir}, \quad (4)$$

231 with  $R_m$ ,  $R_r$  and  $R_{ir}$  being the intrinsic membrane resistance and the reversible and irreversible  
232 fouling resistance, respectively. These are calculated by using:

$$R_m = \frac{\Delta P}{\mu \times J_{BF}}; \quad (5)$$

$$R_{ir} = \frac{\Delta P}{\mu \times J_{AF}} - R_m; \quad (6)$$

$$R_r = \frac{\Delta P}{\mu \times J_F} - R_m - R_{ir}. \quad (7)$$

233

234 The transmembrane pressure is indicated with  $\Delta P$  and the viscosity with  $\mu$ , while  $J_F$  is the flux  
235 in  $\text{m}^3 \text{s}^{-1}$  of humic acid after 15 hours of fouling. The term  $R_{\%}$  was used to assess the extent of  
236 reversible fouling in each membrane during fouling tests:

237

$$R_{\%} = \frac{R_r}{R_t} \times 100. \quad (8)$$

238

239 The first 10 ml of permeate were discarded in every test, to account for dead volume and  
240 permeate tubing. The mass balance for the rejection of component  $i$  is so calculated:

$$\text{mass balance } (\%) = \frac{V_{P,i}c_{P,i} + V_{R,i}c_{R,i}}{V_{F,i}c_{F,i}} \times 100, \quad (9)$$


241 where the subscripts  $P$ ,  $R$  and  $F$  stand for permeate, feed and retentate respectively;  $V$  is the  
242 volume and  $c$  the concentration.

243 Chlorine resistance tests were performed with 4 L feed water containing 2000 ppm NaOCl and  
244 2000 ppm  $\text{CaCl}_2$ . Rejection and permeance were monitored over a period of 5 hours and 30  
245 minutes, while the membranes were tested in cross flow mode with a pump velocity of 45 L h<sup>-1</sup>  
246 at 3 bar. Membranes were pre-compacted before rejection tests.

### 247 3. Results and Discussion

#### 248 3.1 BNNTs synthesis


249 BNNTs were synthesized via chemical vapour deposition, resulting in a dense product (Fig.  
250 2a), with the BNNTs having open ends (Fig. 2b) and homogeneously grown over the entire  
251 substrate area (Fig. 2c) with a vertical orientation (inset cross-sectional HRTEM). The BNNTs  
252 powder was collected with a yield of ~10 mg per run by simple scratching of the silicon wafer  
253 (W x L 14 x 70 mm) substrate. The diffraction pattern generated by a single tube (Fig. 2d)  
254 confirmed the *h*BN (002) crystal structure of boron nitride multiwalled (wall thickness ~4.5  
255 nm) nanotubes [51], with a straight inner channel of *c.a.* 8 nm in diameter and an outer diameter  
256 of *c.a.* 17 nm (Fig. 2e) where the interspace layer distance of *h*BN is 0.328 nm as expected  
257 from literature [34]. Combining the open ends and penetrating inner voids, the as-synthesized  
258 BNNTs are ideal candidates for creating nanoscale channels in TFN membranes [52]. The  
259 morphology of the BNNTs showed a relatively wide size distribution with outer diameters in  
260 the range of 5 to 105 nm and tube lengths in the range of 1 to 5  $\mu\text{m}$ , as statistically counted by  
261 200 tubes in TEM micrographs (Fig. 2f).

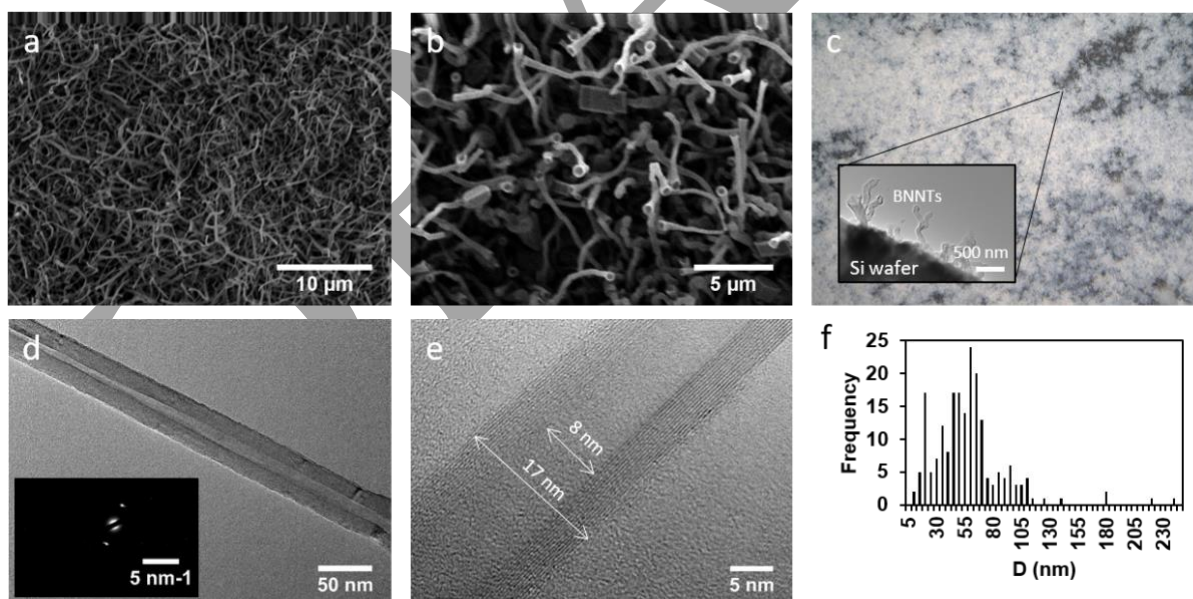

262  
263 **Fig. 2** (a) FESEM micrograph of BNNTs on the Si wafer taken at 3000 x magnification and (b) collected from  
264 the alumina boat taken at 5000 x magnification with 8 mm working distance. (c) Optical microscope image (500  
265 x) with a TEM micrograph inset showing BNNTs grown on a piece of silicon wafer; TEM micrographs and (d)  
266 corresponding diffraction pattern and (e) measures for inner and outer tube diameter of a selected BNNT tube  
267 where the *h*BN interlayer spacing can be observed. (f) Counts of outer diameter intervals for 200 tubes  
268 randomly imaged with TEM.

269 The BNNTs powder samples present the typical Raman *h*BN peak at 1369 cm<sup>-1</sup> (Fig. 3a). The  
 270 XRD spectra in Fig. 3b shows four main BN peaks at 2θ = 10.5° (*h*BN 001), 29° (*h*BN 002),  
 271 40° (*h*BN 100) and 53° (*h*BN 004) [53], alongside some iron and MgO peaks in the region 20°  
 272 < 2θ < 40°, identified as catalyst impurities. Boron nitride FTIR peaks are identified in Fig. 3c  
 273 for the vibration mode along the tubes' longitudinal axis at 1367 cm<sup>-1</sup>, in the tangential  
 274 direction at 1537 cm<sup>-1</sup> and the out of plane buckling mode at 795 cm<sup>-1</sup> [43]. The spectra also  
 275 presents peaks attributed to Si-O in the 1130-1000 cm<sup>-1</sup> region and Si-H in the 850-900 cm<sup>-1</sup>  
 276 region, as the spectra was taken before the BNNTs material was scraped from the Si substrate.  
 277 XPS results (Fig. 3d) identify a B/N atomic ratio of 1.18 in the powder BNNT sample, very  
 278 close to the theoretical value of 1. Peaks for *h*BN are identified at 190.41 eV and 398.00 eV  
 279 for B and N respectively, and a 3.75 at.% of N-B-O bonds can be observed in the B high  
 280 resolution spectra [49].

281

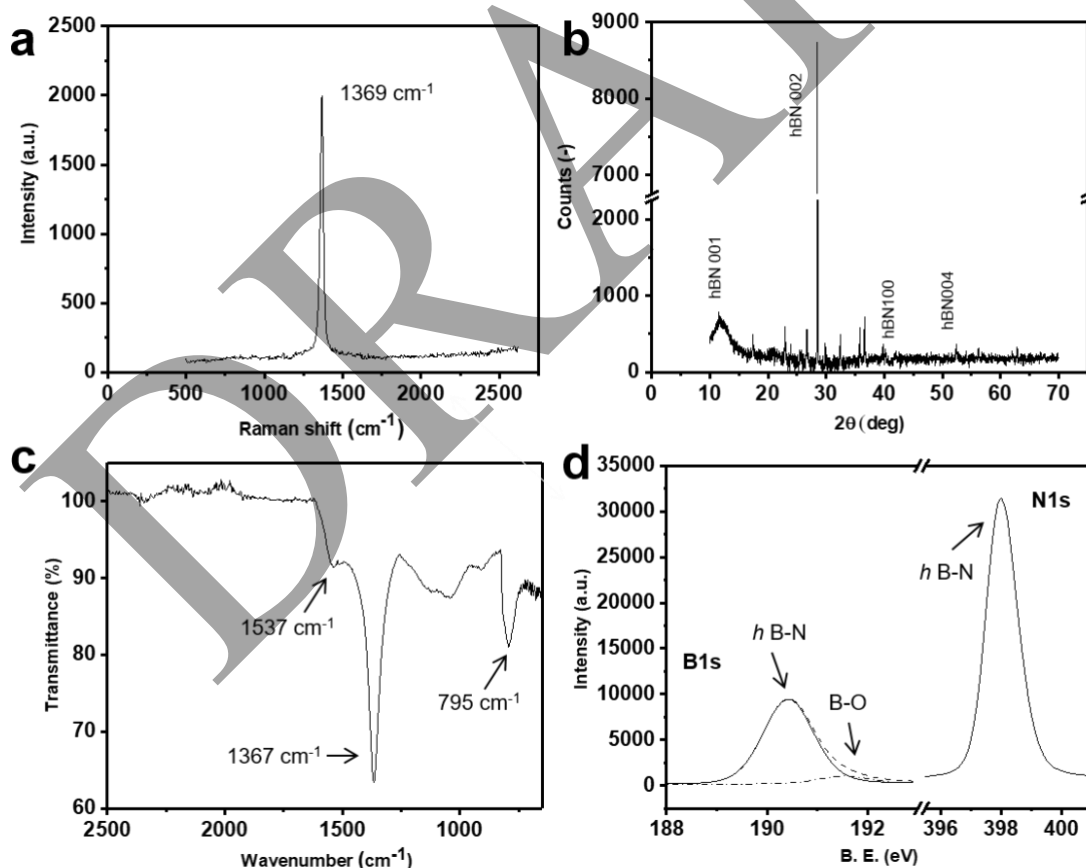


282


283 **Fig. 3** (a) Raman analysis of BNNTs with the characteristic *h*BN peak at 1369 cm<sup>-1</sup> and (b) XRD pattern of the  
 284 as produced BNNTs powder, showing four characteristic *h*BN peaks; (c) FTIR of BNNTs on silicon wafer; and  
 285 (d) B 1s and N 1s high resolution XPS spectra of the BNNTs.

286 **3.2 Characterisation of PA-BNNTs membranes**

287 The surface and cross-sectional morphologies of the produced polyamide membranes are  
288 shown in Fig. 4. The irregular morphology increased with BNNTs loading, which is consistent  
289 with an increase in the average surface roughness ( $R_a$ , nm) in Table 2, and therefore the ratio  
290 between the membrane surface area and the projected area,  $r$ , and morphological changes  
291 measured by AFM (Fig. 5). The crumpled areas observed in the PA-BNNTs membranes  
292 showed similar material stiffness as the rest of the membrane (see phase plot analysis in **Error!**  
293 **Reference source not found.**), indicating that no BNNTs protrude out of the membrane from  
294 the top surface.

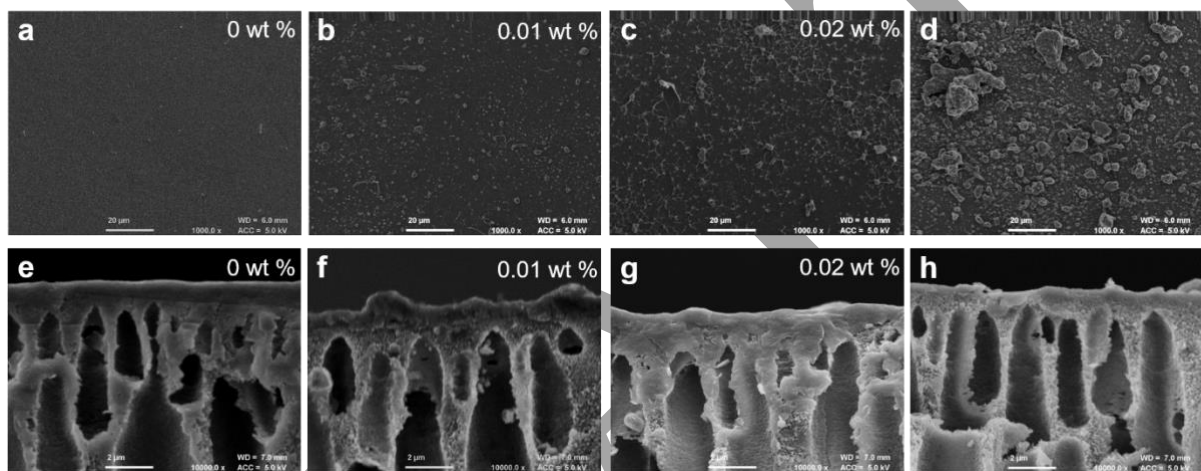

295 **Fig. 4** FESEM top and cross section of membranes prepared from solutions containing different percentages of  
296 nanofiller: (a,e) bare, (b,f) 0.01 wt%, (c,g) 0.02 wt% and (d,h) 0.03 wt% PA-BNNTs membranes.  
297

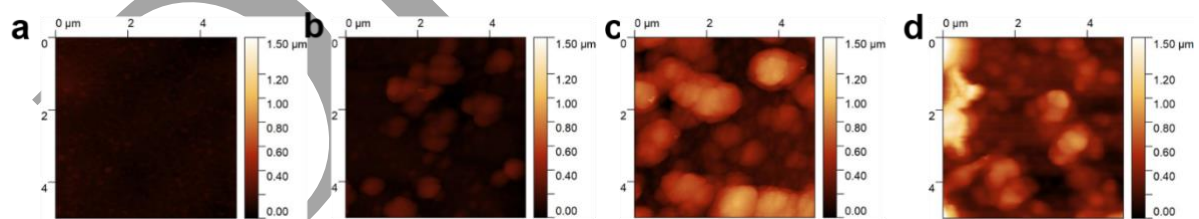

298 **Fig. 5** AFM maps of membranes (a) bare, (b) 0.01 wt%, (c) 0.02 wt% and (d) 0.03 wt% PA-BNNTs membranes.  
299


300 Measured contact angle varies as a function of BNNTs concentration (Table 2). Water contact  
301 angle increases by approximately 20% from PA-BARE to PA-BNNTs0.03, in agreement with  
302 both the increase in roughness  $R_a$  already observed in Fig. 5 and an observed reduced material  
303 hydrophilicity. When the measured contact angle and roughness are used to calculate values  
304 for the Young's contact angles *via* the Wenzel equation [48], an observable although not drastic  
305 increase in material hydrophilicity is observed, with Young's water contact angles increasing

306 by 15-20% for each 0.01 wt% of BNNT added. In contrast, the non-polar diiodomethane  
 307 contact angle ( $\theta_{Y\_DIM}$ ) decreased over the four membranes tested, in line with the loss of  
 308 hydrophilicity of the membrane.

309 **Table 2** Measured water ( $\theta_{WATER}$ ) and diiodomethane ( $\theta_{DIM}$ ) contact angles, Young water ( $\theta_{Y\_WATER}$ ) and  
 310 diiodomethane ( $\theta_{Y\_DIM}$ ) contact angles obtained applying the Wenzel equation, average surface roughness  $R_a$   
 311 results on PA-BARE and PA-BNNTs membranes and ratio  $r$  between the membrane surface area and the  
 312 projected area, obtained by AFM.

Membrane	$\theta_{WATER}$	$\theta_{DIM}$	$\theta_{Y\_WATER}$	$\theta_{Y\_DIM}$	$R_a$	$r$
		(deg, $\pm 2^\circ$ )			(nm)	(-)
PA-BARE	25	30	35	39	19	1.11
PA-BNNTs0.01	32	29	40	38	49	1.11
PA-BNNTs0.02	30	28	49	48	172	1.32
PA-BNNTs0.03	45	10	59	44	181	1.37


313 A free-standing film was placed in the TEM to observe the embedment of the BNNTs in the  
 314 polyamide (Fig. 6a). Wrinkles in the thin layer are created when this is transferred to the TEM  
 315 grid, but these formations can be clearly differentiated from the BNNTs as these show a hollow  
 316 nature as previously shown in Fig. 2 d,e and in the inset of Fig. 6a. Fig. 6b shows a picture of the  
 317 polyamide thin film formed at the interface between the PIP H<sub>2</sub>O/MeOH solution and TMC  
 318 in hexane solution.

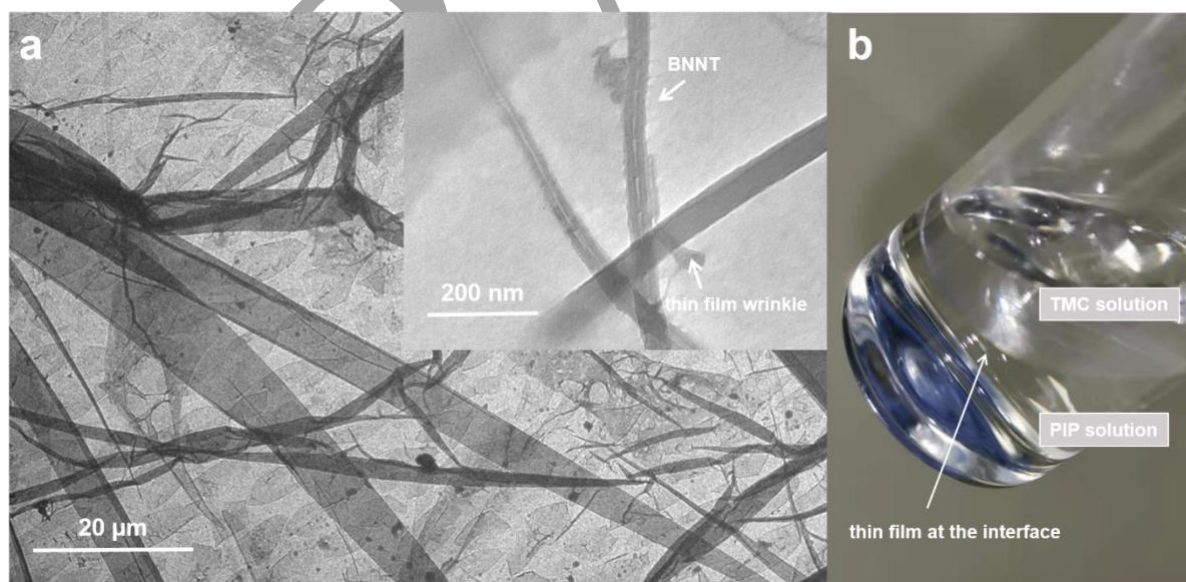

319  
 320 **Fig. 6 (a)** TEM micrograph of a free-standing film loaded with 0.01wt% BNNTs, observable in the magnified  
 321 inset. Wrinkles generate in the film when it is transferred to the TEM grid. **(b)** Picture of a thin film produced at  
 322 the interface between the TMC and PIP solutions.

323 As expected, the introduction of a negatively charged material in the texture of the IP  
324 membrane slightly decreased its surface zeta potential (Fig. 7). Although statistically  
325 significant (p-value=0.002), this change is not as dramatic as might be expected by the  
326 introduction of negatively charged nanomaterial, leading to the hypothesis that the vast  
327 majority of nanomaterial particles are surrounded by the selective polymer layer, and do not  
328 protrude from the top surface, consistent with the top layer stiffness results in **Error!**  
329 **Reference source not found..**


330

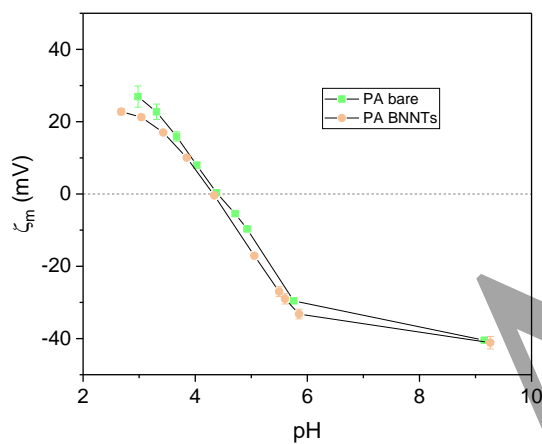

331

332 **Fig. 7** Surface zeta potential ( $\zeta_m$ ) vs. pH of a PA-BARE (IEP=4.40) and PA-BNNTs0.01 (IEP=4.32).

333

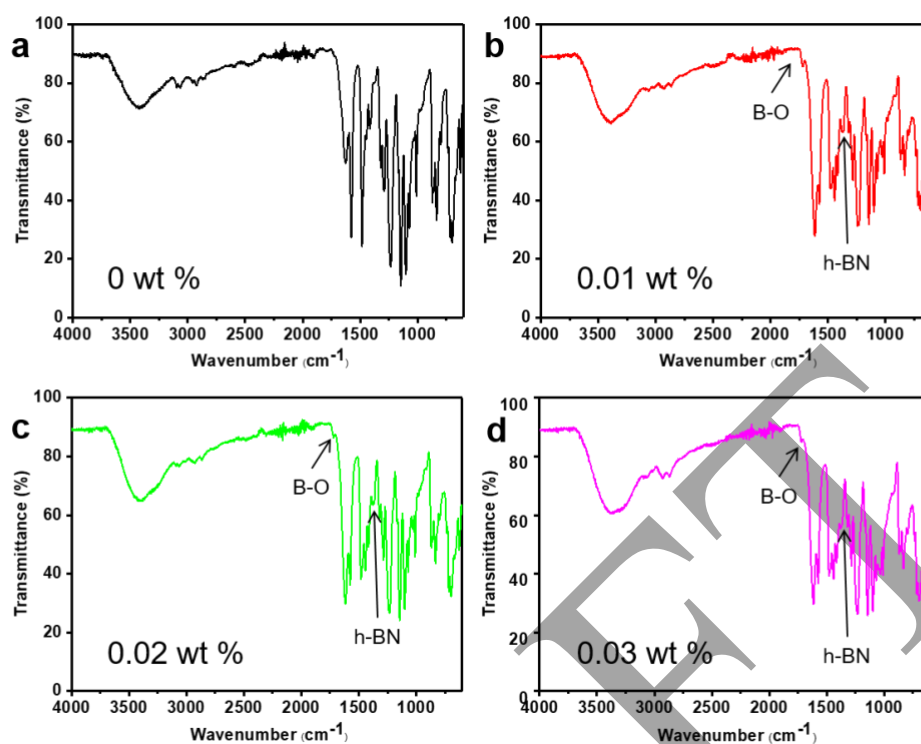

334

335 **Fig. 8** FTIR spectra for (a) bare, (b) 0.01 wt%, (c) 0.02 wt% and (d) 0.03 wt% PA-BNNTs membranes.

336 Fig. 8a reports the FTIR-ATR spectra for the IP BARE membrane [54], and Fig. 8b-c the scans  
 337 for membranes with increasing BNNT loading. The beam penetrates the sample for 0.5 - 2  $\mu\text{m}$   
 338 during testing [55], therefore representing the whole thickness of the membrane top layer and  
 339 not just the very top surface. Thus, at the highest BNNTs concentration, the predominance of  
 340 the 1375  $\text{cm}^{-1}$  BNNT' peak, corresponding to the longitudinal vibration mode of the tube, is  
 341 observed [43, 56], together with a B-O functionalisation peak at 1721  $\text{cm}^{-1}$  [57], showing a new  
 342 bond not observable in the FTIR for the BNNTs in powder form (Fig. 3c), and potentially  
 343 indicating some interaction between the boron nitride and the polymeric matrix already visible  
 344 for BNNTs concentrations of 0.01wt.%.

345 The  $O/N$  ratio for each membrane is reported in Table 3. A fully cross-linked polyamide,  
 346  $(O/N)_{\text{fully cross-linked}}$ , has a  $O/N$  ratio of 1 and a theoretically fully linear polyamide,  
 347  $(O/N)_{\text{fully linear}}$ , has a  $O/N$  ratio of 2 [50]. From these values, the degree of crosslinking was  
 348 calculated from XPS results using Eq. (2). While the addition of 0.01wt% BNNTs increases  
 349 the degree of crosslinking from 0.7 to 1.0, this declines moving to 0.02wt% and 0.03wt%,  
 350 seemingly increasing the density of transport pathways available in selective layer [58].



351 **Table 3** Experimental  $O/N$  from XPS and degree of crosslinking.

Membrane	$(O/N)_{XPS}$	crosslinking (%)
PA-BARE	1.3	0.7
PA-BNNTs0.01	1.0	1.0
PA-BNNTs0.02	1.6	0.4
PA-BNNTs0.03	1.7	0.3

352


### 353 **3.3 Filtration performance of PA-BNNTs membranes: permeance, rejection and fouling**

354 The permeance of the IP membranes evaluated increases with BNNT loading (Fig. 9a), from  
 355 an average of 1.1 LMH/bar for the bare membrane to 2.7 LMH/bar for the PA-BNNTs0.01,  
 356 4.5 LMH/bar for the PA-BNNTs0.02 and 4.1 LMH/bar for PA-BNNTs0.03. The permeance  
 357 values hints at a convex profile, often found in literature as a function of loading, as the initial  
 358 addition of nanomaterial generates an initial increase in pore size, and then a decrease [29].  
 359 The former is ascribed to the higher free volume provided by the BNNTs [59], whereas the  
 360 latter is due to increasing agglomeration [60]. The increase in water flow pathways however  
 361 does not impact the membrane's rejection performance up to 0.02 wt% loading, most likely  
 362 because the polyamide layer is still the main contribution to rejection up to that concentration  
 363 value [59]. This suggests that the addition of the BNNT fillers might have created additional  
 364 pathways for facile transport of water but not solutes [61, 62], and the slight increase in  
 365 membrane surface charge might also have contributed to maintain a high rejection [2]. The  
 366 slight decrease observed in the permeance value from PA-BNNTs0.02 to PA-BNNTs0.03 does  
 367 not, however, show a statistically significant difference (Student's  $t$ -test,  $p$ -value > 0.05).

368 Two batches of PA-BNNTs membranes (empty and filled symbols in Fig. 9a) were tested for  
 369 monovalent NaCl and divalent ( $\text{CaCl}_2$ ,  $\text{MgSO}_4$ ) salts rejection. Calibration curves for these  
 370 measurements are reported in **Error! Reference source not found.**-4, and ionic concentrations  
 371 in **Error! Reference source not found.**. The rejection for NaCl remains low (20 – 40 %) for  
 372 the whole concertation range investigated with 0.03 wt% BNNTs being the worst performing  
 373 case. However the membranes perform well for divalent salts rejection, with the rejection for  
 374  $\text{MgSO}_4$  is above 90 % for loading up to 0.02 wt% BNNTs, whilst it decreases to ~ 80 % for  
 375 PA-BNNTs0.03.  $\text{CaCl}_2$  rejection raises from 75 – 80 % for the bare PA membrane to 97% for  
 376 the PA-BNNTs0.01 and then decreases to around 40 % with further addition of nanofiller. The  
 377 mass balance for the rejection of salts was  $\geq 96\%$  for  $\text{CaCl}_2$  and NaCl, and  $\geq 90\%$  for  $\text{MgSO}_4$ .  
 378 In all cases, the addition of 0.03 wt% of BNNTs notably penalises the membranes rejection,

379 whilst the membranes show highly desirable performances for loadings  $\leq 0.02$  wt%, with PA-  
 380 BNNTs0.02, in particular, combining the highest permeance (4.5 LMH/bar) with the highest  
 381 divalent salt rejection. This is conceivably due to the additional free volume and thus water  
 382 pathways offered by the presence of the BNNTs in the matrix, while the polyamide enveloping  
 383 the nanomaterial provides salt rejection.


### 384 3.6

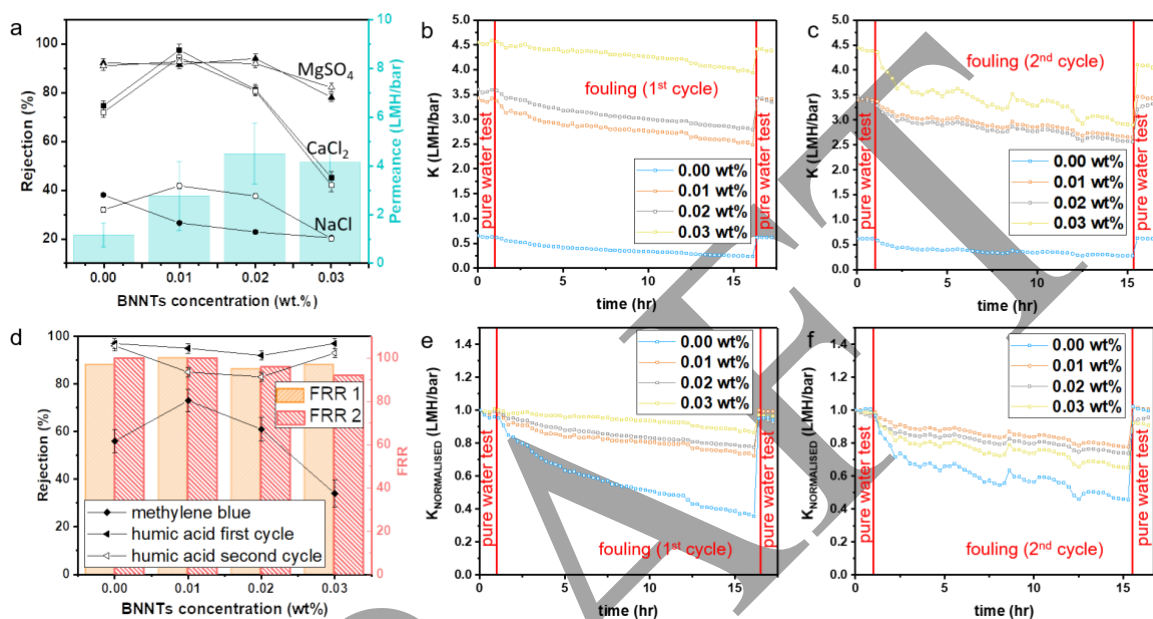

385  
 386 **Fig. 9** (a) Salt rejection (left axis) and permeance (right axis) of the bare and TFN membranes containing BNNTs;  
 387 rejection tests have been repeated on two batches of membranes indicated with full and empty dots for MgSO<sub>4</sub>,  
 388 CaCl<sub>2</sub> and NaCl; (b) First and (c) second fouling cycle; (d) Rejection of methylene blue (◆) and (◀, ◁) humic acid  
 389 together with flux recovery ratio (FRR) performances in the two fouling cycles in orange and red respectively; (e)  
 390 first and (f) second fouling cycle, as displayed in the top panel, but normalised by initial pure water permeance  
 391 for each membrane tested.

392 The observed behaviour showed little change in terms of recovering initial flux after two long  
 393 fouling sequences in Fig. 9b and c, with high FRR: 97%, 100%, 95%, 97 % for the first cycle  
 394 and 100%, 100%, 96, 92% in the second cycle for PA-BARE, PA-BNNTs0.01, PA-  
 395 BNNTs0.02 and PA-BNNTs0.03, respectively. The membranes, possessing a white, opaque  
 396 colour at the start, could be cleaned completely by vigorous water flushing and no irreversible  
 397 contamination could be observed visually after the test or by the FRR results in the fouling  
 398 cycles. The pump flow rate chosen in this study (175 ml min<sup>-1</sup>) is a common setting for  
 399 membrane fouling tests [26]. However, this behaviour might change if the test was carried out  
 400 at higher flows, where some irreversible fouling might be observed. However, Fig. 9e and f

401 explicitly show that PA-BARE reversibly fouls to a greater extent, decreasing to 40% of the  
 402 initial flux, compared to 80-90% for the TFN membranes. This is possibly due to the absence  
 403 of repulsion between the fouling material and nanofiller, which may lead to a higher percentage  
 404 flux decline during tests, even though this is eventually recovered after cleaning. The  
 405 contribution to total resistance during fouling can be observed in Fig.10.

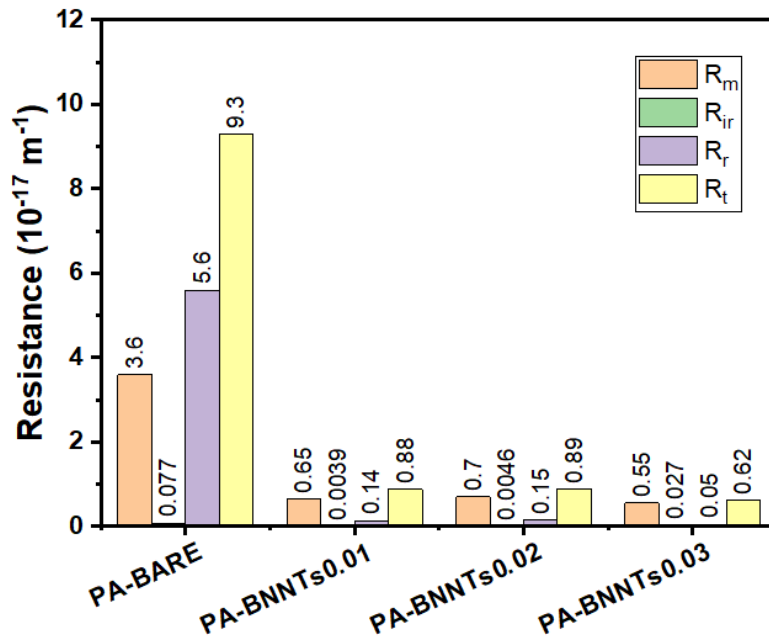

406  
 407 **Fig. 10** Calculated membrane ( $R_m$ ), irreversible ( $R_{ir}$ ), reversible ( $R_r$ ) and total ( $R_t$ ) resistances for the  
 408 membranes under analysis during the first fouling cycle.


409 The fouling layer resistance contribution to the total resistance decreased with increased BNNT  
 410 loading, as indicated by the decrease in value of the parameter  $R_r\%$  for the first fouling cycle  
 411 from 60.5% for PA-BARE to 8.0% for PA-BNNTs0.03 (**Error! Reference source not**  
 412 **found.**). This can be observed in **Error! Reference source not found.** for the second fouling  
 413 cycle as well, where, however, the benefit in terms of lower fouling layer resistance at high  
 414 BNNTs loading is attenuated by a slightly lower FRR in PA-BNNTs0.02 and PA-BNNTs0.03.

415 Fig. 9d shows high rejection (80-90%) of humic acid in all the membranes tested (UV-vis  
 416 calibration curve reported in **Error! Reference source not found.**). In addition to being able  
 417 to effectively reject the foulant, all membranes could recover  $\geq 95\%$  of their initial flux, with  
 418 PA-BNNTs0.03 recovering  $\geq 90\%$  of its flux after physical cleaning, indicating that the  
 419 increased membrane roughness can make the removal of the formed fouling layer harder [4].

420 Fig.9d also reports data on the rejection of methylene blue dye, with the addition of 0.01 wt%  
 421 BNNTs improving rejection by 17% compared to PA-BARE. Rejection then decreased with

422 increasing amounts of BNNTs added. As observed in the case of salts, the addition of 0.03 wt%  
423 of BNNTs to the thin film worsens rejection performances. The mass balance for the rejection  
424 of methylene blue was  $\geq 96\%$  for all samples.


425 The relation between rejection and  $\text{CaCl}_2$  concentration in the operational range 500 - 2000  
426 ppm was also studied (Fig. 11), with a stable selectivity between 500 and 1500 ppm. Above  
427 this value, when Donnan type rejection becomes predominant [63] a decrease in rejection is  
428 observed for the PA-BARE and PA-BNNTs0.03, but not for the PA-BNNTs0.01 and PA-  
429 BNNTs0.02 for a concentration of  $\text{CaCl}_2$  of 2000 ppm. When the PA layer is the major  
430 contributor to rejection, however, a constant rejection over different concentrations is expected  
431 [32]. We can therefore conclude that the PA layer is the major contributor to the rejection of  
432 the membranes analysed, for all membranes but PA-BNNTs, where hypothesized defects due  
433 to the high loading demonstrate a crucial concern particularly at high concentrations (2000  
434 ppm).

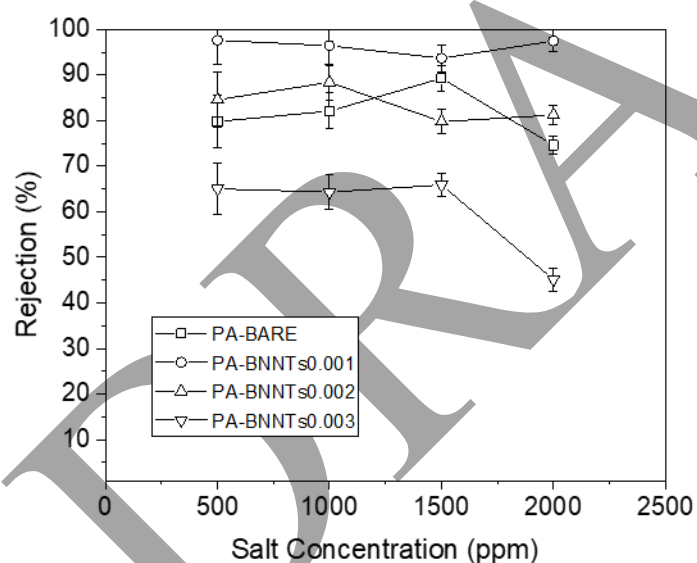

435  
436 **Fig. 11** Dependence of  $\text{CaCl}_2$  rejection on salt concentration for the membranes analysed in this work.

437 Membranes based on a polyamide linkage are prone to attack by chlorine in the feed, as free  
438 chlorine radicals tend to be attracted by the N-H electron density [2]. Thus,  $\text{NaOCl}$  exposure is  
439 studied here for the membranes under analysis. As observed in Fig. 12, the exposure to the  
440 chlorinating agent is more adverse for all PA-BNNTs membranes compared to the PA-BARE,  
441 indicating that the introduction of BNNTs in the polyamide structure exposes the amide bonds  
442 prone to chlorine attacks. Previously it was found that increasing the density of amide bonds  
443 in the PA membrane is a successful strategy for increasing chlorine resistance [64], and this is

444 consistent with the decrease in crosslinking in the PA-BNNTs membranes leading to premature  
 445 failure in presence of NaOCl. In fact, at an exposure of 5000 ppm over 1 hr, while CaCl<sub>2</sub>  
 446 rejection of PA-BARE decreased from 89% to 73%, PA-BNNT 0.01wt% plummeted from  
 447 97% to 32%. The permeance of PA-BNNTs 0.02wt% increased from 3.67 LMH/bar to 4.68  
 448 LMH/bar after 11000 ppm over 1 hr chlorine exposure. However, it remained fairly steady for  
 449 the other membranes, indicating that the maximum exposure tested did not dissolve the PA  
 450 layer, but was enough to perturb it and decrease notably its ion rejection.

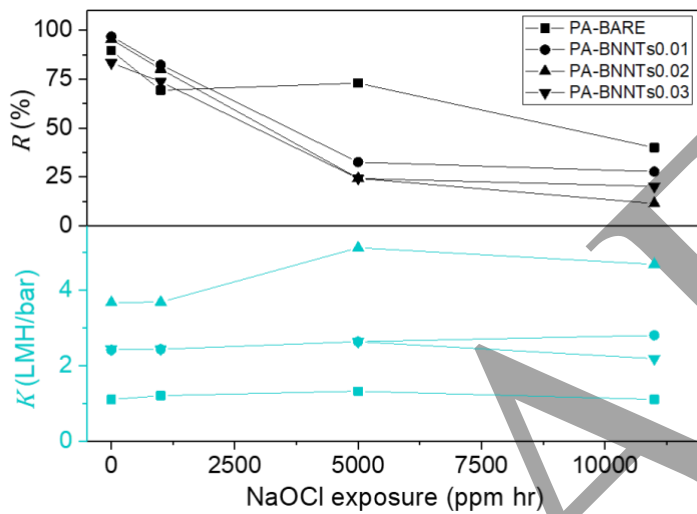

451

452 **Fig. 12** Rejection (*R*) of CaCl<sub>2</sub> and permeance (*K*) of PA-BARE, PA-BNNTs0.01, PA-BNNTs0.02 and PA-  
 453 BNNTs0.03 as a function of the exposure to sodium hypochlorite.

454 The best performing PA-BNNTs membrane in this work could provide 4 times higher  
 455 permeance than PA-BARE membranes with only 0.193 mg cm<sup>-2</sup> of nanofiller on the membrane  
 456 area. For their part, hydroxyl functionalised CNT membranes were reported to show 2 times  
 457 higher pure water permeance than thin film polyamide membranes, but required 13.3 mg cm<sup>-2</sup>  
 458 of filler [65]. An increase of permeance up to 2.7 times was reported in PA-CNTs, but this  
 459 required the use of 0.458 mg/cm<sup>2</sup> of modified MWCNTs. When compared with TFN  
 460 membranes based on CNTs, the membranes in this work have therefore the capability to  
 461 notably improve the permeance of pure polyamide using a limited amount of nanofiller (**Error!**  
 462 **Reference source not found.**) and without requiring any additional functionalisation step.

## 463 **Conclusions**

464 In this work, a known synthesis route for the production of boron nitride nanotubes was  
465 optimised and deployed for the production of larger amounts of boron nitride nanotubes, which  
466 were then used as a nanofillers in nanofiltration thin film nanocomposite membranes prepared  
467 via interfacial polymerisation of PA. BNNTs homogeneously integrate in the polyamide layer,  
468 forming a B-O bond between the nanofiller and the polymer. Rejection of divalent and  
469 monovalent salts is not compromised for up to 0.02wt% BNNTs added to the aqueous phase  
470 in interfacial polymerisation, while the average permeance at this concentration goes up four  
471 times compared to the permeance of a membrane with no nanofiller. This is ascribed to an  
472 increase in water transport pathways given by the boron nitride nanochannels enveloped by the  
473 selective layer, with no appreciable loss of selectivity compared to the bare PA membrane. A  
474 permeance 4.5 times higher than in a bare PA membrane can be observed for low amounts of  
475 BNNTs, thus considerably limiting costs of adding nanofillers. Nonetheless, potential  
476 nanofiller leaching and recycling will have to be further investigated prior to large scale  
477 application, as BNNTs may be hazardous for the environment. In addition, the BNNTs  
478 membranes show a high resistance to irreversible fouling. This is a desirable condition for  
479 applications in, for example, the food industry, where standard operations take place in highly  
480 fouling environments.

## 481 **Acknowledgments**

482 The Engineering and Physical Sciences Research Council (EPSRC) supported this research  
483 under the SynFabFun grant EP/M01486X/1. SC thanks Dr.s Jing Ji and Saeed Mazinani for  
484 their very useful suggestions. Many thanks to Prof. Kang Li's group for providing their  
485 Planetary Ball Mill for preliminary tests. XPS data collection was performed at the EPSRC  
486 National Facility for XPS ('HarwellXPS'), operated by Cardiff University and UCL, under  
487 contract No. PR16195. Research data for this work can be accessed at:  
488 <https://doi.org/10.15125/BATH-00686> .

## 489 **References**

490 [1] P. Xu, T.Y. Cath, A.P. Robertson, M. Reinhard, J.O. Leckie, J.E. Drewes, Critical review  
491 of desalination concentrate management, treatment and beneficial use, Environmental  
492 Engineering Science, 30 (2013) 502-514.

- 493 [2] J. Yin, B. Deng, Polymer-matrix nanocomposite membranes for water treatment, Journal  
494 of membrane science, 479 (2015) 256-275.
- 495 [3] E. Jones, M. Qadir, M.T. van Vliet, V. Smakhtin, S.-m. Kang, The state of desalination and  
496 brine production: A global outlook, Science of the Total Environment, (2018).
- 497 [4] B. Van der Bruggen, C. Vandecasteele, Removal of pollutants from surface water and  
498 groundwater by nanofiltration: overview of possible applications in the drinking water  
499 industry, Environmental pollution, 122 (2003) 435-445.
- 500 [5] M.W. Shahzad, M. Burhan, L. Ang, K.C. Ng, Energy-water-environment nexus  
501 underpinning future desalination sustainability, Desalination, 413 (2017) 52-64.
- 502 [6] S. Lee, J. Choi, Y.-G. Park, H. Shon, C.H. Ahn, S.-H. Kim, Hybrid desalination processes  
503 for beneficial use of reverse osmosis brine: Current status and future prospects, Desalination,  
504 454 (2019) 104-111.
- 505 [7] H.B. Park, J. Kamcev, L.M. Robeson, M. Elimelech, B.D. Freeman, Maximizing the right  
506 stuff: The trade-off between membrane permeability and selectivity, Science, 356 (2017)  
507 eaab0530.
- 508 [8] L.Y. Ng, A.W. Mohammad, C.P. Leo, N. Hilal, Polymeric membranes incorporated with  
509 metal/metal oxide nanoparticles: a comprehensive review, Desalination, 308 (2013) 15-33.
- 510 [9] W. Lau, A. Ismail, N. Misdan, M. Kassim, A recent progress in thin film composite  
511 membrane: a review, Desalination, 287 (2012) 190-199.
- 512 [10] S. Hermans, R. Bernstein, A. Volodin, I.F. Vankelecom, Study of synthesis parameters  
513 and active layer morphology of interfacially polymerized polyamide-polysulfone membranes,  
514 Reactive and Functional Polymers, 86 (2015) 199-208.
- 515 [11] Z. Fan, Z. Wang, N. Sun, J. Wang, S. Wang, Performance improvement of polysulfone  
516 ultrafiltration membrane by blending with polyaniline nanofibers, Journal of Membrane  
517 Science, 320 (2008) 363-371.
- 518 [12] Y. Mansourpanah, S. Madaeni, A. Rahimpour, M. Adeli, M. Hashemi, M. Moradian,  
519 Fabrication new PES-based mixed matrix nanocomposite membranes using polycaprolactone  
520 modified carbon nanotubes as the additive: property changes and morphological studies,  
521 Desalination, 277 (2011) 171-177.
- 522 [13] H. Zhao, L. Wu, Z. Zhou, L. Zhang, H. Chen, Improving the antifouling property of  
523 polysulfone ultrafiltration membrane by incorporation of isocyanate-treated graphene oxide,  
524 Physical Chemistry Chemical Physics, 15 (2013) 9084-9092.
- 525 [14] E.M. Hoek, A.K. Ghosh, X. Huang, M. Liang, J.I. Zink, Physical-chemical properties,  
526 separation performance, and fouling resistance of mixed-matrix ultrafiltration membranes,  
527 Desalination, 283 (2011) 89-99.
- 528 [15] S. Zhao, Z. Wang, X. Wei, X. Tian, J. Wang, S. Yang, S. Wang, Comparison study of the  
529 effect of PVP and PANI nanofibers additives on membrane formation mechanism, structure  
530 and performance, Journal of membrane science, 385 (2011) 110-122.
- 531 [16] J.M. Arsuaga, A. Sotto, G. del Rosario, A. Martínez, S. Molina, S.B. Teli, J. de Abajo,  
532 Influence of the type, size, and distribution of metal oxide particles on the properties of  
533 nanocomposite ultrafiltration membranes, Journal of membrane science, 428 (2013) 131-141.
- 534 [17] P. Daraei, S.S. Madaeni, N. Ghaemi, E. Salehi, M.A. Khadivi, R. Moradian, B. Astinchap,  
535 Novel polyethersulfone nanocomposite membrane prepared by PANI/Fe<sub>3</sub>O<sub>4</sub> nanoparticles

536 with enhanced performance for Cu (II) removal from water, *Journal of Membrane Science*, 415  
537 (2012) 250-259.

538 [18] A. Rahimpour, S. Madaeni, A. Taheri, Y. Mansourpanah, Coupling TiO<sub>2</sub> nanoparticles  
539 with UV irradiation for modification of polyethersulfone ultrafiltration membranes, *Journal of*  
540 *Membrane Science*, 313 (2008) 158-169.

541 [19] A. Berezhkovskii, G. Hummer, Single-file transport of water molecules through a carbon  
542 nanotube, *Phys Rev Lett*, 89 (2002) 064503.

543 [20] S. Casanova, M.K. Borg, Y.J. Chew, D. Mattia, Surface-controlled water flow in nanotube  
544 membranes, *ACS applied materials & interfaces*, 11 (2018) 1689-1698.

545 [21] M. Elimelech, W.A. Phillip, The future of seawater desalination: energy, technology, and  
546 the environment, *science*, 333 (2011) 712-717.

547 [22] D. Mattia, H. Leese, K.P. Lee, Carbon nanotube membranes: from flow enhancement to  
548 permeability, *Journal of Membrane Science*, 475 (2015) 266-272.

549 [23] M. Majumder, N. Chopra, B.J. Hinds, Effect of Tip Functionalization on Transport  
550 through Vertically Oriented Carbon Nanotube Membranes, *J. Am. Chem. Soc.*, 127 (2005)  
551 9062-9070.

552 [24] K.P. Lee, T.C. Arnot, D. Mattia, A review of reverse osmosis membrane materials for  
553 desalination—development to date and future potential, *Journal of Membrane Science*, 370  
554 (2011) 1-22.

555 [25] M. Baghbanzadeh, D. Rana, C.Q. Lan, T. Matsuura, Effects of inorganic nano-additives  
556 on properties and performance of polymeric membranes in water treatment, *Separation &*  
557 *Purification Reviews*, 45 (2016) 141-167.

558 [26] Z.-X. Low, J. Ji, D. Blumenstock, Y.-M. Chew, D. Wolverson, D. Mattia, Fouling resistant  
559 2D boron nitride nanosheet – PES nanofiltration membranes, *Journal of Membrane Science*,  
560 563 (2018) 949-956.

561 [27] F. Xiao, B. Wang, X. Hu, S. Nair, Y. Chen, Thin film nanocomposite membrane  
562 containing zeolitic imidazolate framework-8 via interfacial polymerization for highly  
563 permeable nanofiltration, *Journal of the Taiwan Institute of Chemical Engineers*, 83 (2018)  
564 159-167.

565 [28] H. Zhao, S. Qiu, L. Wu, L. Zhang, H. Chen, C. Gao, Improving the performance of  
566 polyamide reverse osmosis membrane by incorporation of modified multi-walled carbon  
567 nanotubes, *Journal of Membrane Science*, 450 (2014) 249-256.

568 [29] J. Yin, G. Zhu, B. Deng, Multi-walled carbon nanotubes (MWNTs)/polysulfone (PSU)  
569 mixed matrix hollow fiber membranes for enhanced water treatment, *Journal of membrane*  
570 *science*, 437 (2013) 237-248.

571 [30] C.C. Yu, H.W. Yu, Y.X. Chu, H.M. Ruan, J.N. Shen, Preparation thin film nanocomposite  
572 membrane incorporating PMMA modified MWNT for nanofiltration, in: *Key Engineering*  
573 *Materials*, Trans Tech Publ, 2013, pp. 882-886.

574 [31] H. Wu, B. Tang, P. Wu, MWNTs/polyester thin film nanocomposite membrane: an  
575 approach to overcome the trade-off effect between permeability and selectivity, *The Journal of*  
576 *Physical Chemistry C*, 114 (2010) 16395-16400.

577 [32] W.-F. Chan, H.-y. Chen, A. Surapathi, M.G. Taylor, X. Shao, E. Marand, J.K. Johnson,  
578 Zwitterion functionalized carbon nanotube/polyamide nanocomposite membranes for water  
579 desalination, *Acs Nano*, 7 (2013) 5308-5319.



- 580 [33] J. Park, W. Choi, S.H. Kim, B.H. Chun, J. Bang, K.B. Lee, Enhancement of chlorine  
581 resistance in carbon nanotube based nanocomposite reverse osmosis membranes, *Desalination*  
582 and *Water Treatment*, 15 (2010) 198-204.
- 583 [34] D. Golberg, Y. Bando, Y. Huang, T. Terao, M. Mitome, C. Tang, C. Zhi, Boron nitride  
584 nanotubes and nanosheets, *ACS nano*, 4 (2010) 2979-2993.
- 585 [35] M. Suk, A. Raghunathan, N. Aluru, Fast reverse osmosis using boron nitride and carbon  
586 nanotubes, *Applied Physics Letters*, 92 (2008) 133120.
- 587 [36] C.Y. Won, N. Aluru, Water permeation through a subnanometer boron nitride nanotube,  
588 *Journal of the American Chemical Society*, 129 (2007) 2748-2749.
- 589 [37] E. Secchi, S. Marbach, A. Niguès, D. Stein, A. Siria, L. Bocquet, Massive radius-  
590 dependent flow slippage in carbon nanotubes, *Nature*, 537 (2016) 210-213.
- 591 [38] J. Sokoloff, Enhancement of the water flow velocity through carbon nanotubes resulting  
592 from the radius dependence of the friction due to electron excitations, *Physical Review E*, 97  
593 (2018) 033107.
- 594 [39] T.A. Hilder, D. Gordon, S.H. Chung, Salt rejection and water transport through boron  
595 nitride nanotubes, *Small*, 5 (2009) 2183-2190.
- 596 [40] A. Siria, P. Poncharal, A.-L. Biance, R. Fulcrand, X. Blase, S.T. Purcell, L. Bocquet, Giant  
597 osmotic energy conversion measured in a single transmembrane boron nitride nanotube,  
598 *Nature*, 494 (2013) 455.
- 599 [41] H. Lim, B.L. Suh, M.J. Kim, H. Yun, J. Kim, B.J. Kim, S.G. Jang, High-performance,  
600 recyclable ultrafiltration membranes from P4VP-assisted dispersion of flame-resistive boron  
601 nitride nanotubes, *Journal of membrane science*, 551 (2018) 172-179.
- 602 [42] X. Lin, Q. Yang, L. Ding, B. Su, Ultrathin silica membranes with highly ordered and  
603 perpendicular nanochannels for precise and fast molecular separation, *ACS nano*, 9 (2015)  
604 11266-11277.
- 605 [43] C.H. Lee, J. Wang, V.K. Kayatsha, J.Y. Huang, Y.K. Yap, Effective growth of boron  
606 nitride nanotubes by thermal chemical vapor deposition, *Nanotechnology*, 19 (2008) 455605.
- 607 [44] M. Crimp, D. Oppermann, K. Krehbiel, Suspension properties of hexagonal BN powders:  
608 effect of pH and oxygen content, *Journal of materials science*, 34 (1999) 2621-2625.
- 609 [45] R.Y. Tay, H. Li, S.H. Tsang, L. Jing, D. Tan, M. Wei, E.H.T. Teo, Facile Synthesis of  
610 Millimeter-Scale Vertically Aligned Boron Nitride Nanotube Forests by Template-Assisted  
611 Chemical Vapor Deposition, *Chemistry of Materials*, 27 (2015) 7156-7163.
- 612 [46] K.P. Lee, J. Zheng, G. Bargeman, A.J. Kemperman, N.E. Benes, pH stable thin film  
613 composite polyamine nanofiltration membranes by interfacial polymerisation, *Journal of*  
614 *membrane science*, 478 (2015) 75-84.
- 615 [47] G. Lai, W. Lau, P. Goh, Y. Tan, B. Ng, A. Ismail, A novel interfacial polymerization  
616 approach towards synthesis of graphene oxide-incorporated thin film nanocomposite  
617 membrane with improved surface properties, *Arabian journal of chemistry*, (2017).
- 618 [48] R.N. Wenzel, Surface roughness and contact angle, *The Journal of Physical Chemistry*,  
619 53 (1949) 1466-1467.
- 620 [49] B. Liu, S. Yan, Z. Song, M. Liu, X. Ji, W. Yang, J. Liu, One-step synthesis of boron nitride  
621 quantum dots: Simple chemistry meets delicate nanotechnology, *Chemistry–A European*  
622 *Journal*, 22 (2016) 18899-18907.

- 623 [50] C.Y. Tang, Y.-N. Kwon, J.O. Leckie, Probing the nano-and micro-scales of reverse  
624 osmosis membranes—A comprehensive characterization of physiochemical properties of  
625 uncoated and coated membranes by XPS, TEM, ATR-FTIR, and streaming potential  
626 measurements, *Journal of Membrane Science*, 287 (2007) 146-156.
- 627 [51] A. Celik-Aktas, J.-M. Zuo, J.F. Stubbins, C. Tang, Y. Bando, Double-helix structure in  
628 multiwall boron nitride nanotubes, *Acta Crystallographica Section A: Foundations of*  
629 *Crystallography*, 61 (2005) 533-541.
- 630 [52] B.J. Hinds, N. Chopra, T. Rantell, R. Andrews, V. Gavalas, L.G. Bachas, Aligned  
631 multiwalled carbon nanotube membranes, *Science*, 303 (2004) 62-65.
- 632 [53] T. Chen, J. Xiao, G. Yang, Cubic boron nitride with an intrinsic peroxidase-like activity,  
633 *RSC Advances*, 6 (2016) 70124-70132.
- 634 [54] N. Saha, S. Joshi, Performance evaluation of thin film composite polyamide nanofiltration  
635 membrane with variation in monomer type, *Journal of Membrane Science*, 342 (2009) 60-69.
- 636 [55] F. Mirabella Jr, Practical spectroscopy series, *Internal Reflection Spectroscopy: Theory*  
637 *and Applications*, (1993) 17-52.
- 638 [56] B. Zhong, X. Huang, G. Wen, H. Yu, X. Zhang, T. Zhang, H. Bai, Large-scale fabrication  
639 of boron nitride nanotubes via a facile chemical vapor reaction route and their  
640 cathodoluminescence properties, *Nanoscale Res Lett*, 6 (2011) 36.
- 641 [57] W. Laosamathikul, T. Sawada, T. Serizawa, Alcoholysis-Assisted Exfoliation of Boron  
642 Nitride Nanosheets from Hexagonal Boron Nitride, *Transactions of the Materials Research*  
643 *Society of Japan*, 42 (2017) 135-138.
- 644 [58] M.L. Lind, D. Eumine Suk, T.-V. Nguyen, E.M. Hoek, Tailoring the structure of thin film  
645 nanocomposite membranes to achieve seawater RO membrane performance, *Environmental*  
646 *science & technology*, 44 (2010) 8230-8235.
- 647 [59] S. Roy, S.A. Ntim, S. Mitra, K.K. Sirkar, Facile fabrication of superior nanofiltration  
648 membranes from interfacially polymerized CNT-polymer composites, *Journal of Membrane*  
649 *Science*, 375 (2011) 81-87.
- 650 [60] J.S. Taurozzi, C.A. Crock, V.V. Tarabara, C60-polysulfone nanocomposite membranes:  
651 entropic and enthalpic determinants of C60 aggregation and its effects on membrane properties,  
652 *Desalination*, 269 (2011) 111-119.
- 653 [61] B.-H. Jeong, E.M. Hoek, Y. Yan, A. Subramani, X. Huang, G. Hurwitz, A.K. Ghosh, A.  
654 Jawor, Interfacial polymerization of thin film nanocomposites: a new concept for reverse  
655 osmosis membranes, *Journal of membrane science*, 294 (2007) 1-7.
- 656 [62] J. Yin, E.-S. Kim, J. Yang, B. Deng, Fabrication of a novel thin-film nanocomposite (TFN)  
657 membrane containing MCM-41 silica nanoparticles (NPs) for water purification, *Journal of*  
658 *membrane science*, 423 (2012) 238-246.
- 659 [63] F. Fornasiero, H.G. Park, J.K. Holt, M. Stadermann, C.P. Grigoropoulos, A. Noy, O.  
660 Bakajin, Ion exclusion by sub-2-nm carbon nanotube pores, *Proceedings of the National*  
661 *Academy of Sciences*, 105 (2008) 17250-17255.
- 662 [64] S.G. Kim, D.H. Hyeon, J.H. Chun, B.-H. Chun, S.H. Kim, Nanocomposite poly (arylene  
663 ether sulfone) reverse osmosis membrane containing functional zeolite nanoparticles for  
664 seawater desalination, *Journal of membrane science*, 443 (2013) 10-18.

665 [65] S.-M. Xue, Z.-L. Xu, Y.-J. Tang, C.-H. Ji, Polypiperazine-amide nanofiltration membrane  
666 modified by different functionalized multiwalled carbon nanotubes (MWCNTs), ACS applied  
667 materials & interfaces, 8 (2016) 19135-19144.

668 [66] H.-Z. Zhang, Z.-L. Xu, H. Ding, Y.-J. Tang, Positively charged capillary nanofiltration  
669 membrane with high rejection for  $Mg^{2+}$  and  $Ca^{2+}$  and good separation for  $Mg^{2+}$  and  $Li^+$ ,  
670 Desalination, 420 (2017) 158-166.

671 [67] J. nan Shen, C. chao Yu, H. min Ruan, C. jie Gao, B. Van der Bruggen, Preparation and  
672 characterization of thin-film nanocomposite membranes embedded with poly (methyl  
673 methacrylate) hydrophobic modified multiwalled carbon nanotubes by interfacial  
674 polymerization, Journal of membrane science, 442 (2013) 18-26.

675

DRAFT