

M. MATUSZEWSKI, J. MUSIAŁ, M. STYP-REKOWSKI

Faculty of mechanical engineering, university of technology and life sciences in Bydgoszcz

**INFLUENCE OF HYDROABRASIVE TREATMENT ON TRIBOLOGICAL  
PROPERTIS OF CONSTRUCTION STEEL**

*В статті представлені результати порівняльних досліджень шорсткості (важливий трибологічний параметр) поверхонь після різання методом абразивної водної реактивної механічної обробки (АВРМО). Різання виконувалося на зразках, зроблених з двох матеріалів: загартована і деформована легована сталь (1.2080), і мінеральний матеріал (сієніт). Змінні параметри в процесі різання включають: реактивний тиск і живлення. В результаті вимірювань, що залучають відібрані параметри шорсткості ( $R_a$ ,  $R_z$  і  $R_q$ ), виявлено, що більшість змінних параметрів мають істотний ефект на шорсткість при механічній обробці поверхні*

**Ключові слова:** гідроабразивна обробка, конструкційні сталі, шорсткість, сієніт

Cutting is operation very often existing in modern manufacturing processes. This process can be performed on a wide range of materials: from technical (metals, plastics) through mineral materials and derivative materials (rocks, ceramics) to biological materials (wood, straw, organic tissue). Cutting is applied at various stages of the production process and so the requirements concerning characteristics of cut surfaces are varied: different requirements will apply to cutting not followed by further operations or treatment and yet different to cutting followed by further treatment.

Investigations presented in the paper involve a cutting method which uses a concentrated jet of water and abrasive material (AWJM) – the method that is developing rapidly due to its advantages [1, 2], but still defined as non-conventional treatment [3, 4].

The main aim of the investigations was to verify to what extent parameters of cutting using the AWJM method affect surface layer, especially the geometrical structure of cut surfaces of elements made of material having very different features: steel, plastic and mineral material. Surface roughness is one of the most important features of surface layer, therefore selected roughness parameters are taken as the measure for cutting results assessment.

***Object of investigations and their range***

Experiments concern to cutting samples with following dimensions: 30 x 10 x 5 mm, ( $l \times b \times h$ ) made of different materials – metallic and mineral:

- very popular tool steel, numbered 1.2080, symbol acc. to European Standard: X210Cr12, quenched and tempered to 43 HRC,
- syenite.

Used in investigations materials have strength feature and crystalline structure quite differ. Both of chosen materials are applied in machine-tools building, nevertheless, both for different units and elements. Steel are used for a lot of elements produce and mineral material – for the body, or table. The main reason of such choice was need to determine the some roughness parameters obtained by abrasive-water jet cutting with defined parameters. Cutting operations were realized using abrasive-water contour machine, made of PR China marked DWJFB 1313. As independent variables in presented investigations following quantities were accepted:

- pressure of working fluid:  $p = 200, 250$  MPa,
- feed rate:  $f = 64, 80$  and  $96$  mm/min.

According to references, e.g. [5, 6], these factors essentially influences cutting surfaces features.

Fluid jet consists mixture of water and Garnet abrasive, mesh 80; nozzle diameter was 1.016 mm. During machining the cutting head was 2 mm from upper machined surface.

Results of cutting process were evaluated on the base of measurements of below mentioned three chosen roughness parameters:

- $Ra$  – arithmetic mean of profile deviation from the mean,
- $Rz$  – total height of profile,
- $Rq$  – quadratic mean of profile deviation from the mean,
- $Rz/Ra$  – calculated coefficient.

Measurements using profilograph Hommelwerke T 2000.were made in three places: 0,25, 0,50 і 0,75 of  $l$  dimension (length) on measuring length (4 mm) situated on the middle of samples thickness  $b$ .

Places of measures were shown in Fig. 1. As final result average value of 3 measurements ( $m_1, m_2, m_3$ ) was accepted.

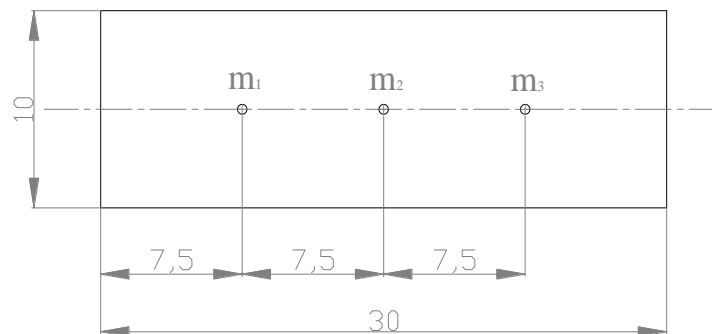


Fig. 1. Displacement of measuring places on the sample

Presented research have initial character, verifying methodic possibilities, so three elements set of roughness parameters, measured by means of mentioned device one accepted as adequate.

#### **Results of experimental investigations**

Cutting surface roughness measurement findings are taken down in below tables. The values of roughness parameters provided in Table 1 refer to the cutting of steel samples quenched and tempered up to 43 HRC. Based on the analysis of these results it was appeared that the tested cutting parameters had an effect on the obtained roughness. It was found that roughness is also higher for greater values of parameters, e.g.  $Ra$  parameter increased by 0.61 micrometer, i.e. by almost 30 % (from 2.16 to 2.77  $\mu\text{m}$ ), where there was a change in the feed rate  $f$  from 64 to 96 mm/min, i.e. for an increase by 50%.

The values roughness parameter are also caused by changes of the jet pressure. At the feed rate  $f = 64$  mm/min, an increase in the pressure  $p$  from 200 to 250 (25%) resulted in an increase in  $Ra$  parameter but only by ca. 12%. At different feed rates, an increase in roughness, expressed in a change of  $Ra$  parameter, is even lower (ca. 6%).

Table 1. Values of some roughness parameters of surface cut by means of AWJM for steel sample

Feed rate, <i>f</i> , mm/min Pressure <i>p</i> , MPa	64	80	96
	<b>Ra, μm</b>		
200	2,16	2,68	2,77
250	2,42	2,85	2,95
<b>Rz, μm</b>			
200	11,20	11,80	13,17
250	13,29	14,42	15,99
<b>Rq, μm</b>			
200	2,74	3,26	3,37
250	3,13	3,59	3,75

Changes found in the geometrical structure of the surface being cut are described by regression equations which have the following form in the analysed case – Table 2.

Table 2. Mathematical models obtained for steel samples for individual pressures

$p = 200 \text{ MPa:}$	$Ra = -0,215 \cdot f^2 + 1,165 \cdot f + 1,21$ $Rz = 0,385 \cdot f^2 - 0,555 \cdot f + 11,37$ $Rq = -0,205 \cdot f^2 + 1,135 \cdot f + 1,81$	$p = 250 \text{ MPa:}$	$Ra = -0,165 \cdot f^2 + 0,925 \cdot f + 1,66$ $Rz = 0,220 \cdot f^2 + 0,470 \cdot f + 12,60$ $Rq = -0,150 \cdot f^2 + 0,910 \cdot f + 2,37$
------------------------	--	------------------------	--

Statistical calculations demonstrate that the above equations record very well observed changes, what is confirmed by the values of correlation coefficients approximating to 1.0.

The second structural material used in the study was syenite – mineral material (rock), using e.g. in very precise machine-tools and measurement machines (tables, bodies). The results of measurements presented in Table 3 indicate that the surface roughness obtained as a result of abrasive-water jet cutting is similar for all analysed values of parameters.

Table 3. Results of roughness parameters measurements of surface cutting by means of AWJM for syenite samples

Feed rate, <i>f</i> , mm/min Pressure, <i>p</i> , MPa	64	80	96
	<b>Ra, μm</b>		
200	3,93	3,85	3,78
250	3,87	3,74	3,70
<b>Rz, μm</b>			
200	18,58	18,18	17,98
250	17,44	17,16	17,01
<b>Rq, μm</b>			
200	4,92	4,82	4,74
250	4,85	4,69	4,64

Change in feed from 64 to 96 mm/min, i.e. by 50 % results in a change of the average value of *Ra* parameter from 3.93 to 3.78 μm, i.e. its decrease but only ca. 4%. Similar situation occurs where jet pressure is

changed: an increase in the value of this process parameter from 200 to 250 MPa (25%) results in  $Ra$  parameter value being decreased from 3.93 to 3.87  $\mu\text{m}$ , i.e. only 1.5%. Similar relations occur for other roughness parameters analysed. Observed relations for this material were described by mathematical models. Their forms are presented in Table 4:

Table 4. Mathematical models obtained for syenite samples for individual pressures

$p = 200 \text{ MPa}$ :	$Ra = 0,045 \cdot f^2 - 0,265 \cdot f + 4,09$ $Rz = 0,100 \cdot f^2 - 0,700 \cdot f + 19,18$ $Rq = 0,055 \cdot f^2 - 0,325 \cdot f + 5,12$	$p = 250 \text{ MPa}$ :	$Ra = 0,005 \cdot f^2 - 0,095 \cdot f + 4,02$ $Rz = 0,065 \cdot f^2 - 0,475 \cdot f + 17,85$ $Rq = 0,010 \cdot f^2 - 0,130 \cdot f + 5,04$
-------------------------	--	-------------------------	--

It will be easier compare the results obtained for analysed materials. The analysis indicate that in analysed range of independent variables (feed rate and jet pressure) for both materials (steel and syenite) pressure has a minor influence on the obtained roughness parameter  $Ra$  but recorded gradient is greater for the cutting of steel. Other parameters are very similar in quality. Comparison of the results obtained for two structural materials very different from each other shows that there are essential differences – Fig.2.

An increase in steel treatment parameters (feed and pressure) resulted in an increase of roughness in cut surfaces, whereas in the case of mineral material a reverse tendency was observed: greater values of process parameters resulted in smaller surface roughness. Such situation may result from the water and abrasive jet containing mineral grains and so, in the case of syenite, mineral machines mineral making the hardness of the tool and the hardness of the machined object similar.

As far as the cutting of steel is concerned, the difference in hardness is greater and therefore the relations between analysed factors are similar to those in traditional machining. It is assumed that the hardness of the tool should be larger than that of the machined element by at least 30 HRC.

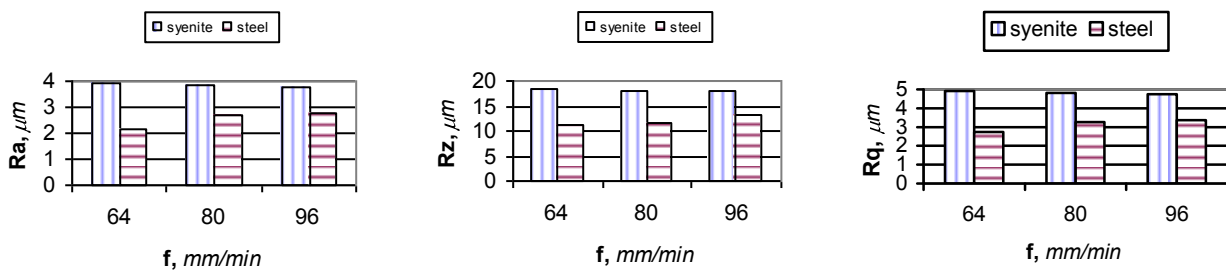


Fig. 2. Histograms presenting changes of roughness parameters:  $Ra$ ,  $Rz$  and  $Rq$  of the steel and syenite samples surfaces after AWJM at the jet pressure  $p = 200 \text{ MPa}$

Comparison of histograms shown in Fig. 2 and 3 indicate that the roughness of the cut surfaces, machined with the same parameters, is much greater (even 50%) for syenite than for steel. Furthermore, it can be seen that the values of all measured parameters of cut surfaces, machined in the same parameters, are greater for mineral material than for steel.

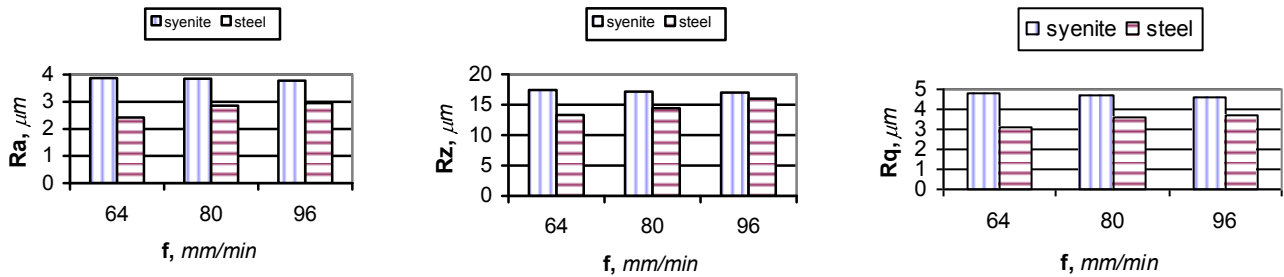


Fig. 3. Histograms presenting changes of roughness parameters:  $R_a$ ,  $R_z$  and  $R_q$  of the steel and syenite samples surfaces after AWJM at the jet pressure  $p = 250$  MPa

The parameters of cut surfaces roughness make this treatment to be defined as a roughing one, so it can be assumed that this method of cutting can be useful with regard to elements of which machined surfaces will be subject to further treatment. However, the AWJM method is not recommended for surfaces which are not machined after cutting.


Table 5 consists quotient values of two measured roughness parameters  $R_z$  and  $R_a$ . Value of this quotient is important for various reasons, among other for tribologic features of machined surfaces what is confirmed in [7].

Table 5. Values of quotient  $R_z/R_a$  for surfaces cut with different parameters


Jet pressure MPa	Values of quotient $R_z/R_a$			
	steel		syenite	
	feed rate $f$ , mm/min			
	64	96	64	96
200	5,22	4,75	4,68	4,82
250	5,53	5,42	4,49	4,61

On the ground of presented findings one can state that quotient of analysed parameters was increased together with machining accuracy increase. In Fig. 4 there were presented results of mentioned investigations. Shaping and finishing turning was compared. As the object of comparison 3D view of machined surfaces, ordinates distribution and load capacity curves were accepted.


*shaping turning,  $S_z/S_a = 5,573$*

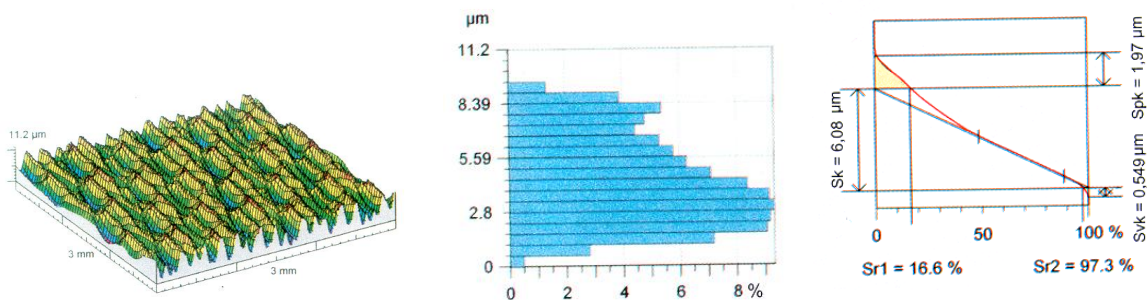

*finish turning,  $S_z/S_a = 6,740$*

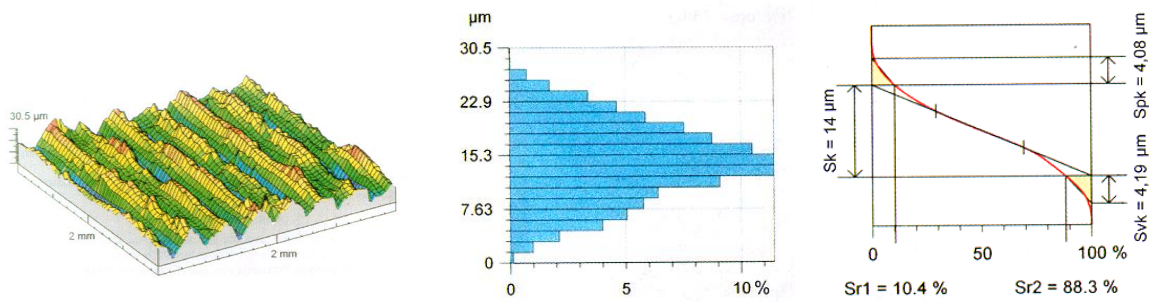

*finish diamond turning,  $S_z/S_a = 7,065$*

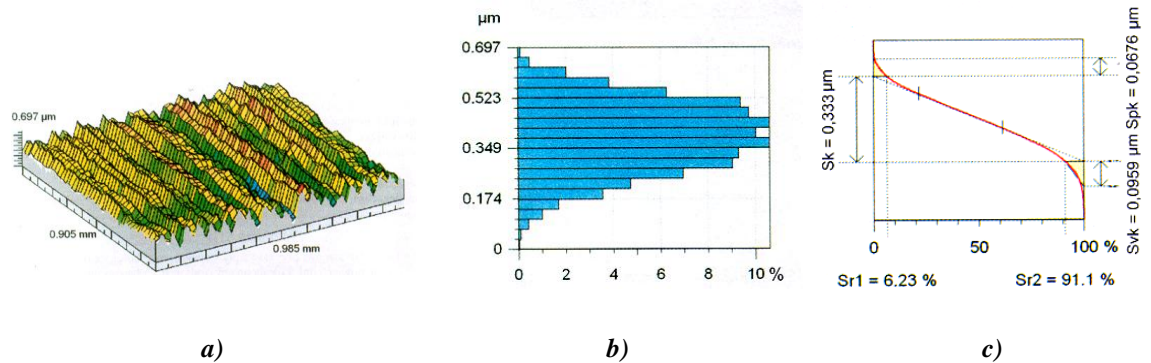

a)

b)

c)

Fig 4. Comparison of turning surfaces tribology features: a) 3D surface view, b) ordinates distribution, c) load capacity curve [7]

The views of machined surfaces are not much differentiated, besides kind of machining was differ. Visible difference were observed in ordinates distribution and load capacity curves. Allowing results of mentioned investigations, on the ground of findings contained in Table 5 one can state that for steel samples enlargement of jet pressure generates slight only (ca. 6%) increase of quotient, so load capacity of such surface will be greater too. Other relationships are for feed rate. Greater feed resulted smaller quotient value, so tribologic features will also worse. Analysing quotient of  $R_z$  and  $R_a$  values for syenite samples inversely (than for steel) relationships were observed, namely: greater jet pressure – smaller quotient value – worse tribology features and, greater feed rate – greater quotient value – better tribologic features.

#### Closure

On the ground of presented experiments and the analysis of the selected roughness parameters measurements results obtained from such experiments, conclusions of practical nature can be formulated. The most significant of which are as follows: abrasive water jet method can be used for the cutting of structural materials with various chemical compositions and structure – with satisfactory efficiency, roughness level of the cut surface using the AWJM method defines this method as roughing, influence of machining parameters of AWJM is differentiate for different machined material. As one said above, the experiments presented in this article have initial character, so on the base of obtained results one can conclude that the established aim of research was accomplished.

## REFERENCES

1. Oczóś K. E., 2003, Efektywność innowacyjnych technologii na przykładzie wybranych sposobów obróbki strumieniowo-erozyjnej. *Mechanik*, vol. 76, no. 8/9, 463–468.
2. Kosmol J., Wala T., Hassan A.I., 2001, Preliminary attempt to FEM modelling of AWJM of polymeric composites. *Materiały II Międzynarodowej Konferencji „Obróbka wysokociśnieniowym strumieniem wody – WJM 2001”*, Kraków, 39 – 48.
3. Ruszaj A., 1999, Niekonwencjonalne metody wytwarzania elementów maszyn i narzędzi. Instytut Obróbki Skrawaniem. Kraków.
4. Styp-Rekowski M., 2003, Obróbki hybrydowe i nietradycyjne jako uzupełnienie zbioru technik wytwarzania skoncentrowanymi nośnikami energii. w: Styp-Rekowski M. (red.). 2003, Wybrane zagadnienia obróbek skoncentrowaną wiązką energii. Wydawnictwo bydgoskiego towarzystwa naukowego, Bydgoszcz, 213–216.
5. Mazurkiewicz A., 2008, Czynniki wpływające na jakość powierzchni stali po cięciu strumieniem wodno-ściernym. *Inżynieria materiałowa*, nr 5, 1– 4.
6. Perec A., 1999, Przecinanie materiałów konstrukcyjnych strugą hydro-ścierną o obniżonym ciśnieniu. *Materiały konferencji «Mechanika’99. Nauka i praktyka»*, Wydawnictwo politechniki gdańskiej, Gdańsk, 135 – 136.
7. Oczóś K., Lubimov W.: *Struktura geometryczna powierzchni*. Oficyna Wydawnicza Politechniki Rzeszowskiej, Rzeszów 2003.

Стаття надійшла до редакції 20.07.2012

**Влияние гидроабразивной обработки на трибологические характеристики конструкционных сталей**

Матушевский М., Мусіал Я., Стип-Рековски М.

*Факультет общего машиностроения, университет технологии и природоведения в Быдгощи*

В статье представлены результаты сравнительных исследований шероховатости (важный трибологический параметр) поверхностей после резания методом абразивной водной реактивной механической обработки (АВРМО). Резание выполнялось на образцах, сделанных из двух материалов: закаленная и деформирована легированная сталь (1.2080), и минеральный материал (сиенит). Переменные параметры в процессе резания включают: реактивное давление и питание. В результате измерений, которые привлекают отобранные параметры шероховатости ( $R_a$ ,  $R_z$  и  $R_q$ ), обнаружено, что большинство переменных параметров имеют существенный эффект на шероховатость при механической обработке поверхности.

**Ключевые слова:** гидроабразивная обработка, конструкционные стали, шероховатость, сиенит.

**Influence of hydroabrasive treatment on tribological propertis of construction steel**

Matuszewski M., Musial J., Styp-Rekowski M.

*Faculty of mechanical engineering, university of technology and life sciences in Bydgoszcz*

In presented paper results of comparative studies into the roughness (very significant tribological factor) of surfaces after cutting using the AWJM method were presented. Cutting was performed on samples made of two materials: quenched and tampered alloy steel (1.2080), and mineral material (syenite). Variable parameters in the cutting process included: jet pressure and feed. As a result of measurements involving selected roughness parameters ( $R_a$ ,  $R_z$  and  $R_q$ ). It was discovered that the majority of variable factors had a significant effect on the roughness of machined surface.