



Title	Jahn-Teller effect and stability of the charge-ordered state in $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ ($0.5 \leq x \leq 0.9$) manganites
Author(s)	Li, XG; Zheng, RK; Li, G; Zhou, HD; Huang, RX; Xie, JQ; Wang, Z
Citation	Europhysics Letters, 2002, v. 60 n. 5, p. 670-676
Issued Date	2002
URL	http://hdl.handle.net/10722/42479
Rights	Creative Commons: Attribution 3.0 Hong Kong License

Jahn-Teller effect and stability of the charge-ordered state in $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ ($0.5 \leq x \leq 0.9$) manganites

X. G. LI¹(*), R. K. ZHENG¹, G. LI¹, H. D. ZHOU¹, R. X. HUANG¹,
J. Q. XIE² and Z. D. WANG^{1,3}

¹ *Structure Research Laboratory, Department of Materials Science and Engineering
University of Science and Technology of China - Hefei, Anhui, 230026, PRC*

² *Laboratory of Internal Friction and Defects in Solids, University of Science
and Technology of China - Hefei, Anhui, 230026, PRC*

³ *Department of Physics, University of Hong Kong - Hong Kong, PRC*

(received 22 May 2002; accepted in final form 12 September 2002)

PACS. 43.35.+d – Ultrasonics, quantum acoustics, and physical effects of sound.

PACS. 64.70.Kb – Solid-solid transitions.

PACS. 71.38.-k – Polarons and electron-phonon interactions.

Abstract. – The longitudinal ultrasonic sound velocity and attenuation, the resistivity, and lattice parameters were studied as a function of temperature from 30 K to 300 K in $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ ($0.5 \leq x \leq 0.9$). For all the samples, a dramatic stiffening of the sound velocity below the charge ordering transition temperature T_{CO} was directly driven by distinct changes of the lattice parameters due to the formation of long-range ordering of Jahn-Teller-distorted MnO_6 octahedra. The relative change of the sound velocity ($\Delta V/V$) below T_{CO} depends on the Ca concentration x and reaches the maximum at $x = 0.75$, implying that the effective strength of the electron-lattice interaction with the Jahn-Teller distortion is the strongest at $x = 0.75$ and hence the charge-ordered state is mostly stabilized near $x = 0.75$ and insensitive to the application of a magnetic field, which is supported by the charge transport properties under high magnetic fields up to 14 T.

Recently, the real-space charge ordering (CO) in perovskite-based manganites $\text{R}_{1-x}\text{D}_x\text{MnO}_3$ (R and D are trivalent rare-earth and divalent alkaline-earth ions, respectively) has been studied extensively [1–4]. The $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ compound is a well-known system showing both metal-insulator transition and CO phenomenon at different doping levels [5]. For instance, the compound is ferromagnetic metal-like at low temperature for $0.2 \leq x \leq 0.5$, while it shows a charge ordering transition and becomes a charge-ordered insulator at low temperature for $0.5 \leq x \leq 0.875$ [5]. Above the charge ordering transition temperature T_{CO} , Mn^{3+} and Mn^{4+} ions are randomly distributed within the MnO_2 plane in the lattice. With decreasing temperature the thermally activated charge carriers are gradually localized, and finally become ordered throughout the crystal structure (*i.e. charge ordering*) in the presence of a sufficiently strong long-range Coulomb interaction and/or an appropriate electron-lattice interaction with the Jahn-Teller distortion [6–10]. Neutron diffraction measurements [4, 11] on

(*) E-mail: lixg@ustc.edu.cn

the charge-ordered $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ ($x = 1/2, 2/3$) revealed that the distinct changes of the lattice parameters near T_{CO} are closely related to the development of a strong Jahn-Teller-type lattice distortion, implying that the Jahn-Teller effect plays an important role in the lattice instabilities and the CO state. On the other hand, the CO state can be dramatically suppressed or even “melted” by application of external magnetic fields via enhanced double-exchange (DE) interaction [12, 13], which pinpoints that the stability of the CO state is also related to the effective strength of the DE interaction. Besides, a lot of experimental data have shown that the stability of the CO state is sensitive to the commensurability of the doping concentration [1, 14]. These features indicate that the stability of the CO state depends on the interactions and competitions among the spin, charge, and lattice degree of freedoms.

The ultrasonic responses to the formation of the CO state in $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ system have been theoretically and experimentally studied by several groups. Based on the Hamiltonian of small polarons with strong nearest-neighbor repulsion and the electron-lattice interaction, it was theoretically found that a dramatic renormalization of the sound velocity around T_{CO} arises from the strong coupling of the acoustic phonons to the CO state for the half-doped $\text{R}_{0.5}\text{D}_{0.5}\text{MnO}_3$ systems [15]. On the other hand, it was observed experimentally that the formation of the CO state in $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ system is accompanied by a dramatic stiffening in the sound velocity below T_{CO} [2, 16, 17], which was attributed to a strong electron-lattice interaction. Despite these ultrasonic studies on the CO state, a systematic ultrasonic study and a comprehensive understanding on the stability of the CO state and its relationship to the electron-lattice interaction with Jahn-Teller distortion, the external magnetic field, and the concentration of the Mn^{3+} ions is still incomplete. In this letter, we present a systematic study of the ultrasonic sound velocity and attenuation, the lattice parameters, and the resistivity as functions of temperature and Ca concentration x in order to get more insight into the CO state and the electron-lattice interaction with Jahn-Teller distortion.

The polycrystalline $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ ($x = 0.5, 0.55, 0.6, 0.65, 0.7, 0.75, 0.8, 0.83, 0.85, 0.87, 0.9$) samples were prepared by a coprecipitation method using ammonium carbonate. The lattice parameters of the $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ samples were determined by a Japan MXP18AHF powder X-ray diffractometer (MAC Science Co. Ltd.) using $\text{Cu } K_\alpha$ radiation ($\lambda = 1.54056 \text{ \AA}$) from 30 K to 300 K. The resistivity $\rho(T)$ was measured by a standard four-probe technique from 30 K to 300 K under external magnetic fields up to 14 T. The ultrasonic sound velocity and attenuation were measured on the Matec-7700 series equipment (Matec Instrument Companies, USA) using a pulse-echo-overlap technique [18]. The relative change of the sound velocity $\Delta V/V$ in fig. 3 below was defined according to the following equation:

$$\Delta V/V = (V_{\text{max}} - V_{\text{min}})/V_{\text{min}} = (V_{\text{max}} - V_{T_{\text{CO}}})/V_{T_{\text{CO}}},$$

where V_{max} and $V_{\text{min}} (= V_{T_{\text{CO}}})$ are the maximal and minimum sound velocity in the temperature range from 25 K to 300 K, respectively.

In fig. 1 we show the temperature dependencies of the lattice parameters from 30 K to 300 K for the selected $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$. Near the charge ordering transition temperature of the system [4, 11], the distinct changes of lattice parameters of the a -axis, b -axis and c -axis can be observed. We note that the ratios of the orthorhombic lattice $(b/\sqrt{2})/a$ are smaller than 1 for $0.5 \leq x \leq 0.75$, while those for $x > 0.75$ are larger than 1, suggesting a compression (or elongation) of the b -axis and an elongation (or compression) of the a and c axes. The difference in the orthorhombic lattice for $x \leq 0.75$ and $x > 0.75$ suggests that there exist different types of orbital orderings due to different types of Jahn-Teller distortions for $0.5 \leq x \leq 0.75$ and $x > 0.75$. In fact, the orbital ordering below T_{CO} for the half-doped $\text{La}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$ is of $(3x^2 - r^2)/(3y^2 - r^2)$ type, while that for $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ ($x > 0.75$) is of $(3z^2 - r^2)$

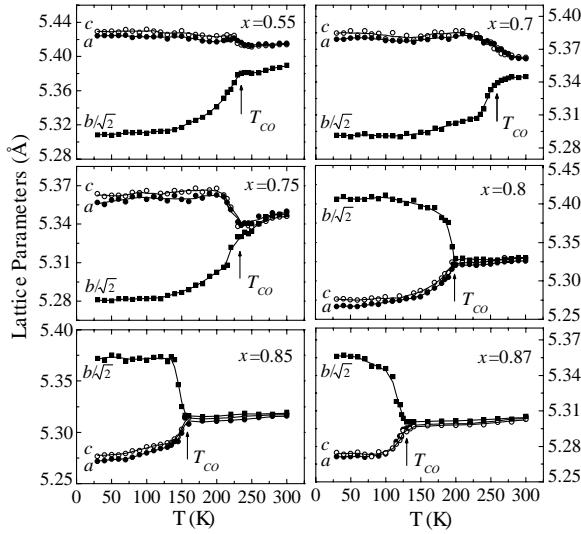


Fig. 1 – Temperature dependence of the lattice parameters for $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ ($x = 0.55, 0.7, 0.75, 0.8, 0.85, 0.87$). The solid lines are guides to the eyes.

type [19]. The former obviously originates from the Q_2 -mode Jahn-Teller distortion, and the latter is due to the Q_3 -mode [20]. These crossovers of different types of orbital orderings as well as crystal structures from tetragonal compressed orthorhombic one to tetragonal elongated orthorhombic one between $0.5 \leq x \leq 0.75$ and $x > 0.75$ are related to the change of Jahn-Teller vibration modes from Q_2 to Q_3 . We note here that these distinct changes of the lattice parameters were shown to be related to the effect of cooperative static Jahn-Teller distortion near T_{CO} [4, 11]. It is therefore expected that there are dramatic anomalies of a particular phonon mode near T_{CO} [21].

Figure 2 plots the temperature dependence of the longitudinal ultrasonic sound velocity (V) and attenuation (α) at zero magnetic field for the selected $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ samples. With decreasing temperature from room temperature to T_{CO} the sound velocities soften conspicuously and then stiffen dramatically below T_{CO} . These substantial sound velocity softening and stiffening accompanied by an attenuation peak around T_{CO} indicate the dramatic instabilities of a particular phonon mode related to the CO transition in these charge-ordered $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ manganites. Since many theoretical and experimental results including our previous ultrasonic measurement on the CaMnO_3 showed that a typical $\Delta V/V$ caused by antiferromagnetic (AFM) spin fluctuations near an AFM phase transition is merely of the order 0.1% [16, 22, 23], it is undoubtful that the large stiffening of the sound velocity (for example, $\Delta V/V = 7\%$ at $x = 0.5$ and 29% at $x = 0.75$, see fig. 3) in the present charge-ordered system below T_{CO} is closely related to the formation of the CO state in the presence of the strong electron-lattice interaction with the static Jahn-Teller distortion.

Figure 3 shows the relative change of the sound velocity $\Delta V/V$ as a function of the Ca concentration x below T_{CO} . One can find that $\Delta V/V$, which directly reflects the contribution of the formation of the CO state to the stiffening of the sound velocity, is strongly x -dependent. With increasing Ca concentration from $x = 0.5$ to $x = 0.75$, $\Delta V/V$ increases monotonously, suggesting an increasing effect of electron-lattice interaction with the Jahn-Teller distortion. When the Ca concentration increases further from $x = 0.75$, $\Delta V/V$ decreases slightly at

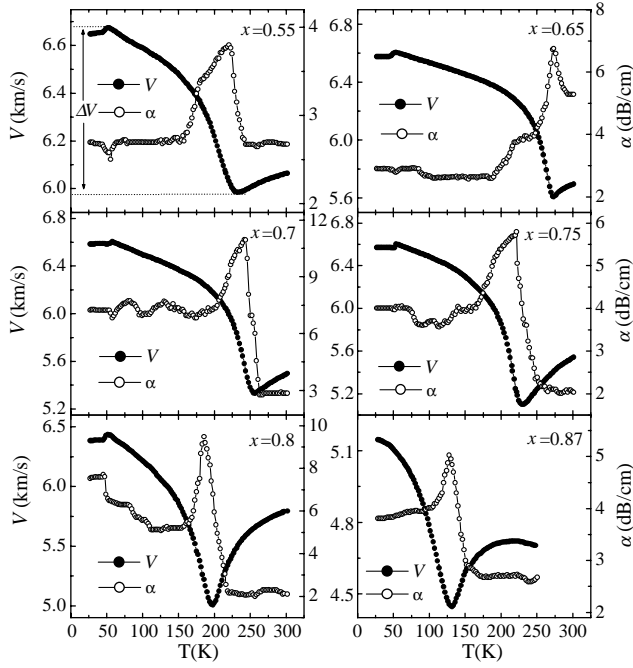


Fig. 2 – Temperature dependence of the longitudinal ultrasonic sound velocities and attenuations for $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ ($x = 0.55, 0.65, 0.7, 0.75, 0.8, 0.87$).

$x < 0.83$, and then drops rapidly to a low value at $x = 0.9$. From the $\Delta V/V$ - x relationship (fig. 3), one may conclude that the effective strength of electron-lattice interaction with the static Jahn-Teller distortion is the strongest near $x = 0.75$. Recently, Yunoki *et al.* [24] demonstrated theoretically that a charge-ordered state can easily be stabilized for half-doped ($x = 0.5$) manganites in the presence of a relatively strong electron-lattice interaction with Jahn-Teller distortion. Therefore, despite the fact that the CO states can be of “bi-stripe” type or “Wigner-crystal” type [5], their stability is expected to be the most robust near $x = 0.75$ because of the largest effective strength of the electron-lattice interaction with the Jahn-Teller distortion near $x = 0.75$, as determined from the magnitude of $\Delta V/V$ in fig. 3. Moreover, this robustness can also be seen from figs. 4 and 5 to be addressed below.

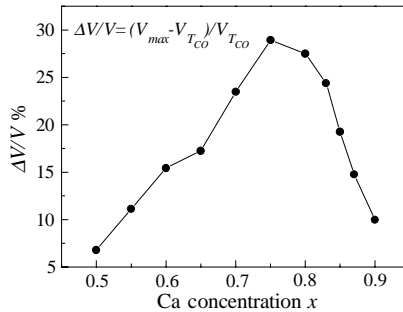


Fig. 3 – The relative change of longitudinal sound velocity $\Delta V/V$ vs. Ca concentration x in the CO state.

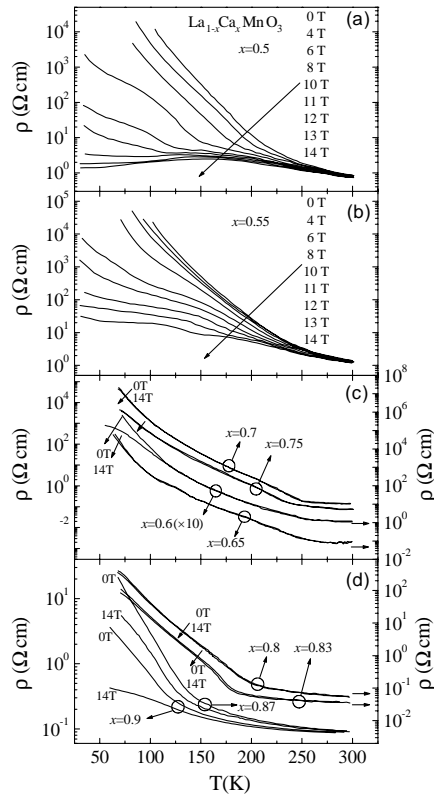


Fig. 4 – Variations of resistivity with temperature under different external magnetic fields up to 14 T for $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ ($x = 0.5, 0.55, 0.6, 0.65, 0.7, 0.75, 0.8, 0.83, 0.87, 0.9$).

Figure 4 shows the temperature dependence of the resistivity $\rho(T)$ under magnetic fields up to 14 T for $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ ($x = 0.5, 0.55, 0.6, 0.65, 0.7, 0.75, 0.8, 0.83, 0.87, 0.9$). With decreasing temperature the zero-field $\rho(T)$ curve at $x = 0.5$ shows a semiconductor-like behavior, but with a discernible change in the slope near T_{CO} signaling the onset of the formation of the CO state [11, 25]. When the magnetic field H increases from 0 T to 6 T, the resistivity reduces slightly, but for $6 \text{ T} < H \leq 11 \text{ T}$ the resistivity decreases dramatically

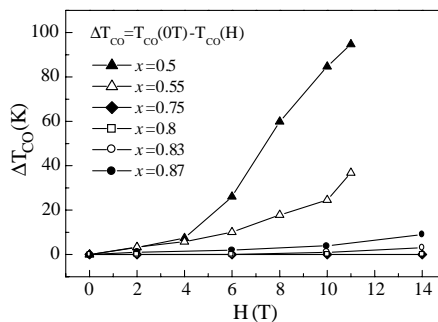


Fig. 5 – Magnetic-field dependence of ΔT_{CO} for $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ ($x = 0.5, 0.55, 0.75, 0.8, 0.83, 0.87$).

although it still remains semiconductor-like. For $H > 12$ T, a distinct change of $\rho(T)$ induced by the magnetic field appears, and a metal-insulator transition occurs around 150 K, which can be viewed as a sign of the collapse of the CO state. Furthermore, the T_{CO} , determined from the peak temperature of the $d \ln \rho / dT^1 - T$ curve [2] (see fig. 5), shifts dramatically to a lower temperature as the magnetic field increases. The field-dependent resistivity behaviors at $x = 0.5$ (fig. 4(a)), together with the electronic phase separation (*i.e.*, the coexistence of metallic ferromagnetic (FM) phase and the insulating CO phase) reported earlier in dark-field image and X-ray diffraction experiments by Radaelli *et al.* [11] and Mori *et al.* [26], unambiguously demonstrate that there is a particular strong competition between the electron-lattice interaction and the DE interaction. All these results may be understood based on this competition picture. As is well known, the strong electron-lattice interaction favors the localization of charge carriers, while the DE-induced ferromagnetism demands the active hopping of charge carriers. Therefore, it is the competition between these two interactions (*i.e.* the electron-lattice and the DE) that is mainly responsible for the charge transport properties and the stability of the CO state. An external magnetic field tends to align electron spins along its direction and thus results in the increase of the effective strength of DE interaction, which in turn enhances the FM coupling between neighboring Mn spins as well as the mobility of charge carriers, increasing the total size of the FM domains and reducing that of the insulating CO domains. Above a percolation threshold the metallic FM domains are connected in the whole sample, leading to a dramatic reduction of the resistivity. Similar to that observed at $x = 0.5$, $\rho(T)$ and T_{CO} at $x = 0.55$ were also significantly suppressed by the external magnetic field (see figs. 4(b) and 5). Nevertheless, we noticed that the magnetic-field effect on the resistivity and the CO state becomes less effective as x increases from 0.5 to 0.55 because of a stronger effective electron-lattice interaction at $x = 0.55$ which has a larger $\Delta V/V$ than that at $x = 0.5$.

In contrast with those observed for $x = 0.5$ and 0.55, $\rho(T)$ and T_{CO} at $x = 0.75$ are independent of external magnetic fields up to 14 T, as shown in figs. 4(c) and 5. The field-independent $\rho(T)$ behavior is consistent with the fact that the effective electron-lattice interaction with the Jahn-Teller distortion is very strong at (or near) $x = 0.75$, and indicates the robustness of the ordered state of the Jahn-Teller distortion at (or near) this x . As for the samples ($x = 0.65, 0.7, 0.8$ and 0.83) with large $\Delta V/V$ below T_{CO} (see fig. 3), $\rho(T)$ and T_{CO} are also almost field independent as the CO states may be considered as mixtures of some very stable CO states (like $x = 2/3$ and $3/4$ etc.) via a phase separation scenario [1, 5]. Nevertheless, with further increasing Ca concentration ($x > 0.83$) $\rho(T)$ becomes weakly field dependent. This weak field dependence of $\rho(T)$ may be related to the emergence of weak ferromagnetism [27] and the decrease of the effective electron-lattice interaction with the Jahn-Teller distortion for $x > 0.83$.

In summary, the above ultrasonic, resistivity and crystal structure changes in $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ ($0.5 \leq x \leq 0.9$) demonstrate that the stability of the CO state is closely related to the effective strength of the electron-lattice interaction with the Jahn-Teller distortion, which are consistent with the theoretical results in refs. [5, 19, 24, 28]. It was found that in the CO state the effective strength of the electron-lattice interaction with the Jahn-Teller distortion is rather strong, particularly near Ca concentration $x = 0.75$, where the CO state is mostly stabilized and insensitive to external magnetic fields.

* * *

This work was supported by the Chinese National Nature Science Fund, the Ministry of Science and Technology of China, and a CRCG grant at the University of Hong Kong.

REFERENCES

- [1] MORI S., CHEN C. H. and CHEONG S.-W., *Nature*, **392** (1998) 473.
- [2] RAMIREZ A. P., SCHIFFER P., CHEONG S.-W., CHEN C. H., BAO W., PALSTRA T. T. M., GAMMEL P. L., BISHOP D. J. and ZEGARSKI B., *Phys. Rev. Lett.*, **76** (1996) 3188.
- [3] WAGNER P., GORDON I., MANGIN S., MOSHCHALOV V. V., BRUYNSERAED E. Y., PINSARD L. and REVCOLEVSCHI A., *Phys. Rev. B*, **61** (2000) 529.
- [4] FERNÁNDEZ-DÍAZ M. T., MARTÍNEZ J. L., ALONSO J. M. and HERRERO E., *Phys. Rev. B*, **59** (1999) 1277.
- [5] DAGOTTO E., HOTTA T. and MOREO A., *Phys. Rep.*, **344** (2001) 1.
- [6] MISHRA S. K., PANDIT R. and SATPATHY S., *Phys. Rev. B*, **56** (1997) 2316.
- [7] MUTOU T. and KONTANI H., *Phys. Rev. Lett.*, **83** (1999) 3685.
- [8] LI J. Q., UEHARA M., TSURUTA C., MATSUI Y. and ZHAO Z. X., *Phys. Rev. Lett.*, **82** (1999) 2386.
- [9] YAMADA Y., SUZUKI J., OIKAWA K., KATANO S. and FERNANDEZ-BACA J. A., *Phys. Rev. B*, **62** (2000) 11600.
- [10] MUKHIN A. A., IVANOV V. Y., TRAVKIN V. D., LEBEDEV S. P., PIMENOV A., LOIDL A. and BALBASHOV A. M., *JETP Lett.*, **68** (1998) 356.
- [11] RADAELI P. G., COX D. E., MAREZIO M. and CHEONG S.-W., *Phys. Rev. B*, **55** (1997) 3015.
- [12] TOMIOKA Y., ASAMITSU A., MORITOMO Y., KUWAHARA H. and TOKURA Y., *Phys. Rev. Lett.*, **74** (1995) 5108.
- [13] TOMIOKA Y., ASAMITSU A., KUWAHARA H., MORITOMO Y. and TOKURA Y., *Phys. Rev. Lett.*, **53** (1996) R1689.
- [14] TOMIOKA Y. and TOKURA Y., in *Colossal Magnetoresistive Oxides*, edited by TOKURA Y. (Gordon and Breach Science Publishers) 2000, pp. 281-305.
- [15] LEE J. D. and MIN B. I., *Phys. Rev. B*, **55** (1996) R14713.
- [16] ZHENG R. K., ZHU C. F., XIE J. Q. and LI X. G., *Phys. Rev. B*, **63** (2001) 024427.
- [17] FUJISHIRO H., FUKASE T. and IKEBE M., *J. Phys. Soc. Jpn.*, **70** (2001) 628.
- [18] PAPADAKIS E. P., *Physical Acoustics*, edited by MASON W. P. and THURSTON R. N., Vol. **12** (Academic Press, New York) 1976, p. 337.
- [19] HOTTA T., MALVEZZI A. L. and DAGOTTO E., *Phys. Rev. B*, **62** (2000) 9432.
- [20] SAWADA H., MORITAKAWA Y., TERAKURA K. and HAMADA N., *Phys. Rev. B*, **56** (1997) 12154.
- [21] IBARRA M. I., TERESA J. M. DE., BLASCO J., ALGARABEL P. A., MARQUINA C., GARCÍA J., STANKIEWICZ J. and RITTER C., *Phys. Rev. B*, **56** (1997) 8252.
- [22] LEISURE R. G. and MOSS R. W., *Phys. Rev.*, **188** (1969) 840.
- [23] GOLDING B., *Phys. Rev. Lett.*, **20** (1968) 5.
- [24] YUNOKI S., HOTTA T. and DAGOTTO E., *Phys. Rev. Lett.*, **84** (2000) 3714.
- [25] MURAKAMI Y., SHINDO D., CHIBA H., KIKUCHI M. and SYONO, *J. Solid State Chem.*, **140** (1997) 331.
- [26] MORI S., CHEN C. H. and CHEONG S.-W., *Phys. Rev. Lett.*, **81** (1998) 3972.
- [27] FUJISHIRO H., IKEBE M., OHSHIDEN S. and NOTO K., *J. Phys. Soc. Jpn.*, **69** (2000) 1865.
- [28] HOTTA T., TAKADA Y., KOIZUMI H. and DAGOTTO E., *Phys. Rev. Lett.*, **84** (2000) 2477.