



# Direct Synthesis of Nanostructured Silver Antimony Sulfide Powders from Metal Xanthate Precursors

**DOI:**

[10.1038/s41598-021-82446-3](https://doi.org/10.1038/s41598-021-82446-3)

**Document Version**

Accepted author manuscript

[Link to publication record in Manchester Research Explorer](#)

**Citation for published version (APA):**

Alharbi, Y., Alam, F., Salhi, A., Missous, M., & Lewis, D. (2021). Direct Synthesis of Nanostructured Silver Antimony Sulfide Powders from Metal Xanthate Precursors. *Scientific Reports*. <https://doi.org/10.1038/s41598-021-82446-3>

**Published in:**

Scientific Reports

**Citing this paper**

Please note that where the full-text provided on Manchester Research Explorer is the Author Accepted Manuscript or Proof version this may differ from the final Published version. If citing, it is advised that you check and use the publisher's definitive version.

**General rights**

Copyright and moral rights for the publications made accessible in the Research Explorer are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

**Takedown policy**

If you believe that this document breaches copyright please refer to the University of Manchester's Takedown Procedures [<http://man.ac.uk/04Y6Bo>] or contact [uml.scholarlycommunications@manchester.ac.uk](mailto:uml.scholarlycommunications@manchester.ac.uk) providing relevant details, so we can investigate your claim.



# Direct Synthesis of Nanostructured Silver Antimony Sulfide Powders from Metal Xanthate Precursors

Yasser T. Alharbi,<sup>1</sup> Firoz Alam,<sup>1,2</sup> Abdelmajid Salhi,<sup>3</sup> Mohamed Missous<sup>3</sup> and David J. Lewis<sup>2\*</sup>

<sup>1</sup> *Department of Chemistry, The University of Manchester, Oxford Road, Manchester M13 9PL, UK.*

<sup>2</sup> *Department of Materials, The University of Manchester, Oxford Road, Manchester M13 9PL, UK.*

<sup>3</sup> *Department of Electrical and Electronic Engineering, The University of Manchester, Sackville Street, Manchester, M13 9PL, UK*

\*Correspondence and requests for materials should be addressed to D.J.L (email: david.lewis-4@manchester.ac.uk)

## ABSTRACT

Silver (I) ethylxanthate [AgS<sub>2</sub>COEt] (**1**) and antimony (III) ethylxanthate [Sb(S<sub>2</sub>COEt)<sub>3</sub>] (**2**) have been synthesised, characterised and used as precursors for the preparation of AgSbS<sub>2</sub> powders and thin films using a solvent-free melt method and spin coating technique, respectively. The as-synthesized AgSbS<sub>2</sub> powders were characterized by powder X-ray diffraction (XRD), Raman spectroscopy, scanning electron microscopy (SEM) and energy dispersive X-ray (EDX) spectroscopy. The crystalline AgSbS<sub>2</sub> powder was investigated using XRD, which shows that AgSbS<sub>2</sub> has cuboargyrite as the dominant phase, which was also confirmed by Raman spectroscopy. SEM was also used to study the morphology of the resulting material which is potentially nanostructured. EDX spectra gives a clear indication of the presence of silver (Ag), antimony (Sb) and sulfur (S) in material, suggesting that decomposition is clean and produces high quality AgSbS<sub>2</sub> crystalline powder, which is consistent with the XRD and Raman data. Electronic properties of AgSbS<sub>2</sub> thin films deposited by spin coating show a p-type conductivity with measured carrier mobility of 81 cm<sup>2</sup> V<sup>-1</sup> s<sup>-1</sup> and

carrier concentration of  $1.9 \times 10^{15} \text{ cm}^{-3}$ . The findings of this study reveal a new bottom-up route to these compounds, which have potential application as absorber layers in solar cells.

## Introduction

Considerable research attention has been focused on the application of binary, ternary and quaternary chalcogenides as absorber layers in thin film solar cells<sup>1-3</sup>. Metal chalcogenides have gained interest due to their potential in ferroelectric, thermoelectric devices and for their non-linear optical properties<sup>4-11</sup>. Copper indium gallium selenide (CIGS) and cadmium telluride (CdTe) are the most commonly used light-absorbing materials in thin film solar cell<sup>12</sup>. However, low cost, earth-abundant and cadmium-free materials can be used as an alternative. The development of alternative materials would not only avoid the high toxicity presented by cadmium but also the scarcity of indium in the Earth's crust<sup>13</sup>.

The creation of inorganic ternary materials containing three elements is desirable due to the range of possible new materials with novel electronic properties. As such, there has been significant scientific interest in the creation of such materials, and more specifically, ternary chalcogenides, for the creation of highly efficient, cheap and environmentally friendly solar cells<sup>14</sup>. Such ternary materials can be created by mixing elements from different groups such as  $\text{NiCo}_2\text{S}_4$ <sup>15</sup>,  $\text{Ag}_8\text{SnS}_6$ <sup>16</sup>. Focusing on I-III-VI<sub>2</sub>-type and I-III<sub>2</sub>-VI<sub>4</sub>-type, of the group I (Cu, Ag), group III (Ga and In) and group VI (S and Se) are used and result in chalcopyrite-type materials. These are desirable due to their reduced toxicity, high absorption coefficients often extending across the visible to near-infrared wavelengths<sup>17</sup>.

A variety of compounds, including  $\text{CuSbS}_2$  ( $E_g = 1.5 \text{ eV}$ ),  $\text{SnS}$  ( $E_g = 1.1 \text{ eV}$ ),  $\text{Cu}_2\text{SnS}_3$  ( $E_g = 1.15 \text{ eV}$ )  $\text{AgSbSe}_2$  ( $E_g = 1 \text{ eV}$ ) and  $\text{AgSbS}_2$  ( $E_g = 1.7 \text{ eV}$ ) have desirable optical


properties for solar cell applications, mainly due to their bandgap commensurate with AM 1.5G photon flux maxima<sup>18–22</sup>.

Interest in chalcogenides such as AAsSe<sub>2</sub> (A = Li, Na) and AgSbEQ<sub>2</sub> (EQ= S, Se) has predominantly been due to the distinct ferroelectric, thermoelectric and non-linear optical properties they present<sup>23–26</sup>. Alloys consisting of AgSbSe<sub>2</sub> have potential use in solar cells due to their high optical-absorption coefficient of  $> 10^4 \text{ cm}^{-1}$  across the Vis-NIR region of the electromagnetic spectrum and band gap energies of 0.9–1.1 eV, which can maximise the theoretical power conversion efficiency according to the Shockley-Queisser limit (ca. 24% at these values of  $E_g$ )<sup>27–29</sup>. Usually, AgSbSe<sub>2</sub> crystallises in the halite structure, whereby Ag and Sb randomly occupy the crystallographic Wyckoff positions<sup>30</sup>. The AgSbS<sub>2</sub> ternary chalcogenide may be modified to give rise to quaternary compounds of the form (MS)<sub>1-x</sub>(AgSbS<sub>2</sub>)<sub>x</sub> (M=Ge, Sn, Pb), which represent a family of semiconductors and semi-metals with low to narrow optical band gap energies in the range 0.01 - 0.6 eV<sup>31,32</sup>. At elevated temperatures, AgSbS<sub>2</sub> exists as cubic  $\beta$ -AgSbS<sub>2</sub><sup>33</sup>, whilst at low temperatures (<380 °C) monoclinic  $\alpha$ -AgSbS<sub>2</sub><sup>33</sup> is the dominant phase (Fig. 1)<sup>33–35</sup>. The crystalline structure of  $\alpha$ -AgSbS<sub>2</sub> has been studied over a number of decades by a series of authors, including Hofmann (1938)<sup>36</sup>, Knowles (1964)<sup>37</sup> and Smith *et al.*, (1997)<sup>34</sup>. Effenberger *et al.* (2002) revealed that the structure is comprised of pyramids of SbS<sub>3</sub> and chains linked by linear S-Ag-S and AgS<sub>4</sub> polyhedral<sup>38</sup>.

A variety of techniques have been established for the formation of AgSbS<sub>2</sub> thin films including thermal evaporation<sup>39</sup>, pulsed-laser deposition<sup>40</sup>, RF-magnetron sputtering<sup>41</sup> and laser ablation<sup>42</sup>. For each of the above techniques the starting material is prepared by direct fusion of stoichiometric quantities of the elements, which can be problematic due to the formation of sub phases caused by inequivalent ion migration rates in the

solid state. The use of metal xanthate precursors, however, may circumvent this problem as the mixing prior to thermal decomposition occurs at the nanoscale and hence final products should be homogeneous and of a single crystalline phase, with the bottom up nature of the process allowing for exquisite control of elemental constitution. Due to the pre-formed bonds between metal and chalcogenide atoms, metal xanthates can act as efficient precursors for the formation of solid state metal sulfides. This has led to the extensive application of, for instance, xanthate complexes for the production of thin films<sup>43,44</sup>. Advantages conferred by this sort of synthetic route include the ability to carry out low temperature decomposition, the ease of synthesis and stability of the resulting compound in air, along with the fact that by-products for these materials are generally gaseous. O'Brien & Lewis have reported a number of such syntheses for a range of main group and transition metal sulfides<sup>45-50</sup>.

In this paper, we describe a metal xanthate precursor route to produce ternary silver antimony sulfide ( $\text{AgSbS}_2$ ) as a single well-defined phase via thermal decomposition of metal xanthate precursors in stoichiometric ratios.  $\text{AgSbS}_2$  is rarely found in nature but possesses potentially excellent properties for solar cell applications<sup>51, 52</sup>.

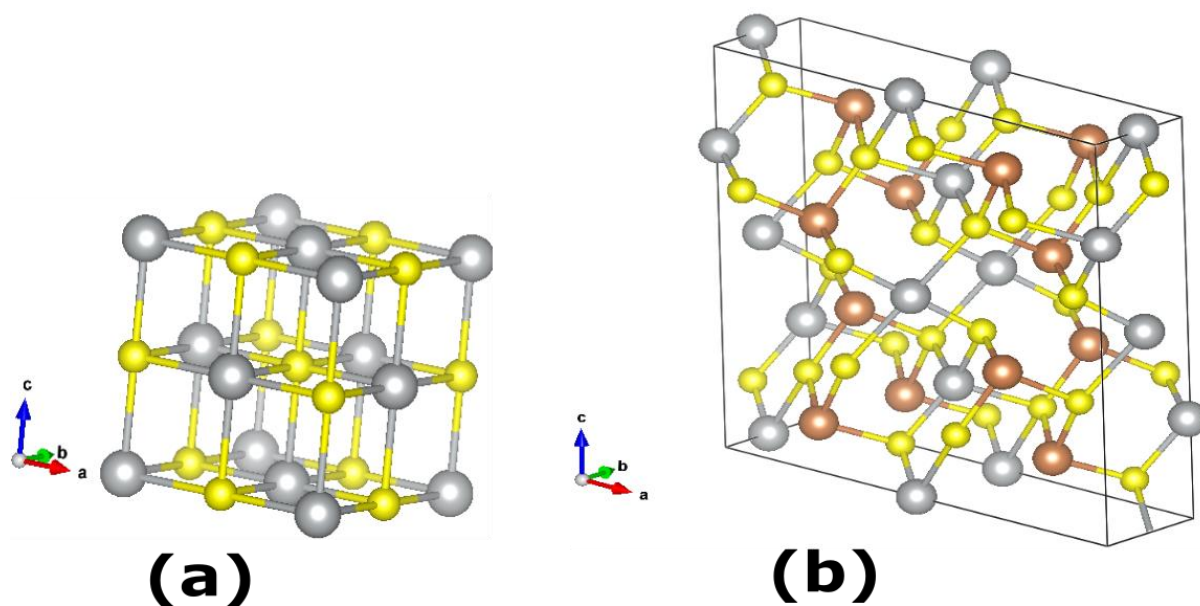


**Fig. 1** (a) Cubic cuboargyrite  $\beta$ -AgSbS<sub>2</sub> reported by Geller and Wernick, with the silver and antimony indistinguishable<sup>33</sup>. (b) monoclinic  $\alpha$ -AgSbS<sub>2</sub> miargyrite was obtained by Smith<sup>34</sup>. In all cases silver atoms (Ag) are represented by silver spheres, Antimony (Sb) by brown spheres and S by yellow spheres.

## Results and discussion

Metal xanthate complexes of the form [AgS<sub>2</sub>COEt] (**1**) and [Sb(S<sub>2</sub>COEt)<sub>3</sub>] (**2**) were synthesised via metathesis reaction of the nitrate/chloride metal with suitable potassium ethyl xanthate<sup>52–54</sup>. Infrared (IR) and nuclear magnetic resonance (NMR) spectroscopies were used in tandem to assess the purity of complexes (**1**) and (**2**) and the spectra recorded are shown in the ESI (Fig. S1.1 and S1.2). The Ag<sub>2</sub>S and Sb<sub>2</sub>S<sub>3</sub> powders synthesised from [AgS<sub>2</sub>COEt] (**1**) and [Sb(S<sub>2</sub>COEt)<sub>3</sub>] at three different temperatures (400 °C, 450 °C and 500 °C) were then characterised using XRD shows a pure phase Acanthite Ag<sub>2</sub>S (Fig. S2.1) and stable Stibnite phase of Sb<sub>2</sub>S<sub>3</sub> (Fig. S2.2), respectively. The Raman spectra of both metal sulfide (Ag<sub>2</sub>S and Sb<sub>2</sub>S<sub>3</sub>) synthesised from precursors (**1**) and (**2**) at three different temperatures (400 °C, 450 °C and 500 °C) are shown in Fig. S2.3 and Fig. S2.4, respectively.

### **Thermogravimetric Analysis of [AgS<sub>2</sub>COEt] (1) and [Sb(S<sub>2</sub>COEt)<sub>3</sub>] (2) Complexes**


Thermogravimetric analysis of (1) and (2) was performed in the temperature range of 0 °C to 550 °C under a nitrogen atmosphere. Both of the complexes exhibited a large mass loss between 80 °C and 250 °C (Fig. 2). The decomposition of precursor (1) started at 96 °C and ended at 177 °C with the remaining weight determined to be 54%, which is matching the calculated value of 54%. Both experimental and theoretical values confirmed the phase of Ag<sub>2</sub>S. In similar manner the TGA of precursor (2) exhibit the main decomposition step between 100 °C and 161 °C. The final residue of 35% is in good agreement with the calculated value of 35% confirm the phase of Sb<sub>2</sub>S<sub>3</sub>. The minor decomposition step with < 3% mass loss attributed to loss of sulfur which was also observed in a recent paper by Alqhatani *et al*<sup>54</sup>. TGA of mixtures of the two complexes (Fig. 2) shows a single step decomposition at ca. 200 °C with a remaining weight of 41% which corresponds to the formation of AgSbS<sub>2</sub>. This low temperature decomposition of AgSbS<sub>2</sub> clearly indicates that this material can be easily produced within polymer matrices and can be used as an absorber layers in polymer nanocrystal based hybrid solar cells<sup>55-57</sup>. O'Brien *et al.* has reported the preparation of PbS nanocrystals in polymer matrix via decomposition of lead(II) xanthates in polystyrene matrices as a potential absorber material for flexible hybrid photovoltaic devices<sup>58</sup>.

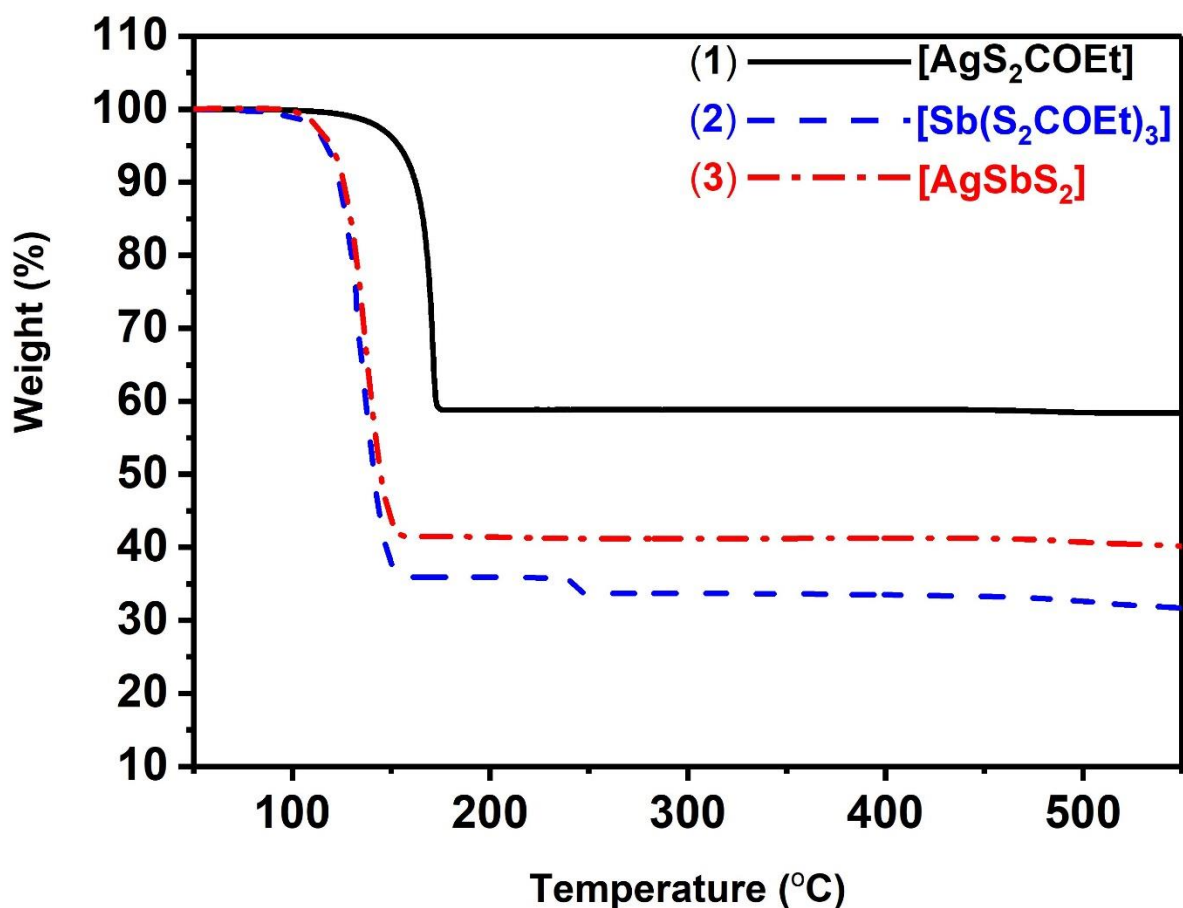

**Fig. 2** Thermogravimetric analysis (TGA) of (1) [AgS<sub>2</sub>COEt], (2) [Sb(S<sub>2</sub>COEt)<sub>3</sub>], and (3) mixtures of Ag and Sb xanthates to form AgSbS<sub>2</sub>.


The mixtures of the solid precursors form a homogenous molten intermediate reactive melt, when the temperature increased. Before undergoing decomposition to form the final solid products. The volatile organic components are evacuated through the constant nitrogen flow<sup>53,59,60</sup>. The mechanism of xanthate decomposition follows a Chugaev elimination reaction which involves the production of a cyclic transition state to produce carbonyl sulfide molecules (OCS) and alkenic side products (Scheme 1)<sup>61,62</sup>. Alanazi *et al* has previously reported the synthesis of stannite Cu<sub>2</sub>FeSnS<sub>4</sub> (CFTS) quaternary chalcogenides from mixtures of metal (O-ethylxanthato) (M= Cu, Fe and Sn) complexes, which shows that combining xanthate precursors in tandem in reactive melts is a promising approach to these materials<sup>63</sup>.



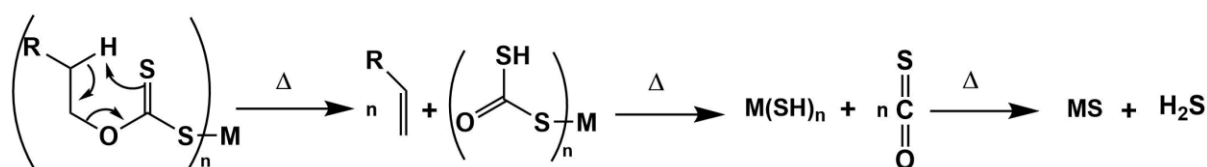


**Scheme 1.** Xanthate pyrolysis by the Chugaev elimination mechanism<sup>62, 63</sup>.

Therefore, pyrolysis of a mixture of Ag and Sb precursors were carried out at various temperature such as (300 °C, 350 °C 400 °C, 450 °C and 500 °C). The XRD pattern of AgSbS<sub>2</sub> powders synthesised at 300 and 350 °C have some impurity peaks as shown in ESI (Fig. S2.5). The XRD pattern of polycrystalline AgSbS<sub>2</sub> powders synthesised at 400 °C shows a cubic AgSbS<sub>2</sub> (cuboardyrite, ICDD No. 00-017-0456, space group [Fm-3m] and  $a = 5.6520 \text{ \AA}$ ) with Bragg peaks at  $2\theta = 27.4^\circ, 31.7^\circ, 45.3^\circ, 53.7^\circ, 56.7^\circ, 66.0^\circ, 72.8^\circ, 75.0^\circ$  that could be indexed to the (1 1 1), (2 0 0), (2 2 0), (3 1 1) (2 2 2) (4 0 0) (3 3 1) and (4 2 0) planes respectively (Fig. 3). The positions of the peaks of curve a (black line) in Fig. 3 are shifted toward smaller  $2\theta$  values with respect to the ones of curve b and c. Since all the peaks are shifted by same  $2\theta$  value, it could potentially be a measurement error. Additionally, we have also observed that the peaks become more intense and the FWHM of each peak is reduced when the synthesis temperature was increased from 400 °C to 500 °C. The average crystallite size of AgSbS<sub>2</sub> powders synthesised at 400 °C, 450 °C and 500 °C are 34 nm, 43 nm and 59 nm respectively, which was calculated using Scherrer's equation<sup>64</sup> (Fig. 4). It is clear from the Fig. 4 that the size of AgSbS<sub>2</sub> powders were found to increase with increasing the temperature, which is in good agreement with literature<sup>65-67</sup>.

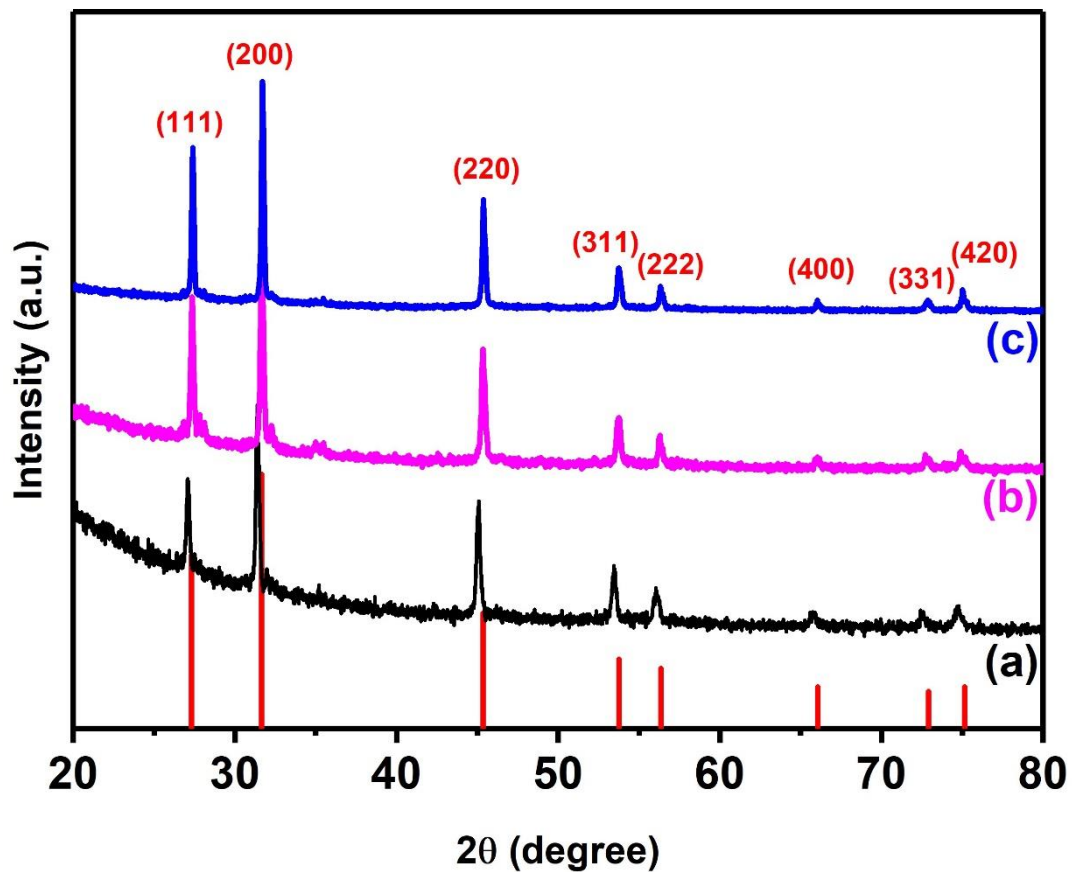


**Fig. 3** XRD patterns of  $\text{AgSbS}_2$  powders synthesised at various temperatures (a) 400 °C (b) 450 °C, and (c) 500 °C for 1 h under nitrogen. The red sticks correspond to the standard powder diffraction pattern of cubic  $\text{AgSbS}_2$  (cuboargyrite, ICDD no. 00-017-0456).

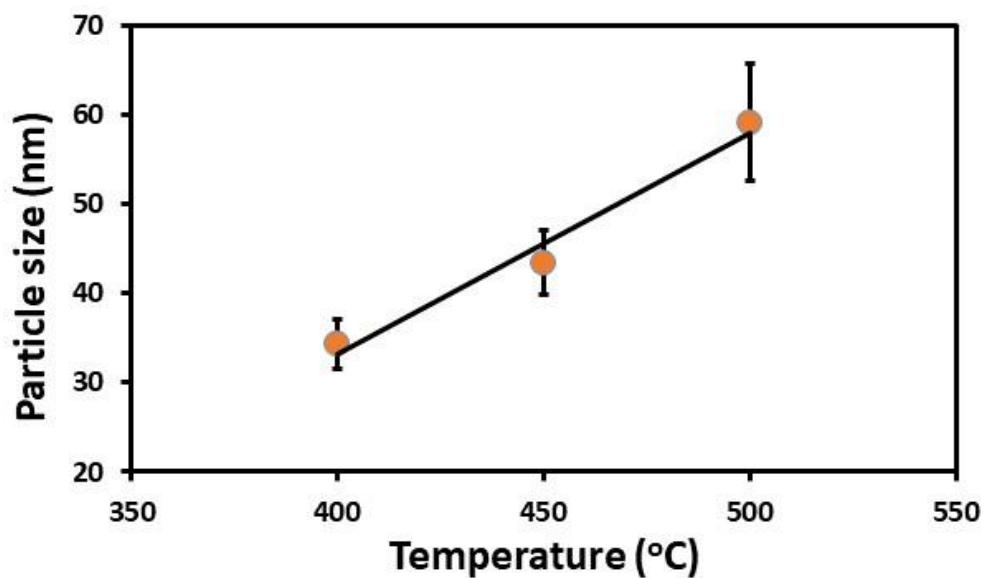


**Fig. 4** Average crystallite domain size of  $\text{AgSbS}_2$  powders calculated using Scherrer's equation as a function of synthesis temperature.

Raman spectroscopy was conducted on the  $\text{AgSbS}_2$  powder produced at  $500\text{ }^\circ\text{C}$  (Fig. 5). Raman resonances can be seen at  $80.2$ ,  $115.4$ ,  $185.9$ ,  $249.2$ ,  $368.9$  and  $448.1\text{ cm}^{-1}$  respectively, and the spectral positions of these peaks agree with those reported previously for  $\text{AgSbS}_2$ <sup>68</sup>. The electrical properties of  $\text{AgSbS}_2$  films were measured using the Van Der Pauw method. Silver paste was used to form the four contacts on  $7\times 7\text{ mm}^2$  sample area. The measured carrier mobility and carrier concentration are  $81\text{ cm}^2\text{V}^{-1}\text{s}^{-1}$  and  $1.9\times 10^{15}\text{ cm}^{-3}$ , respectively. These values are comparable to values obtained for  $\text{Cu}_2\text{FeSnS}_4$  (CFTS) films<sup>63</sup>. Hall effect measurements revealed that the films exhibit p-type conductivity.

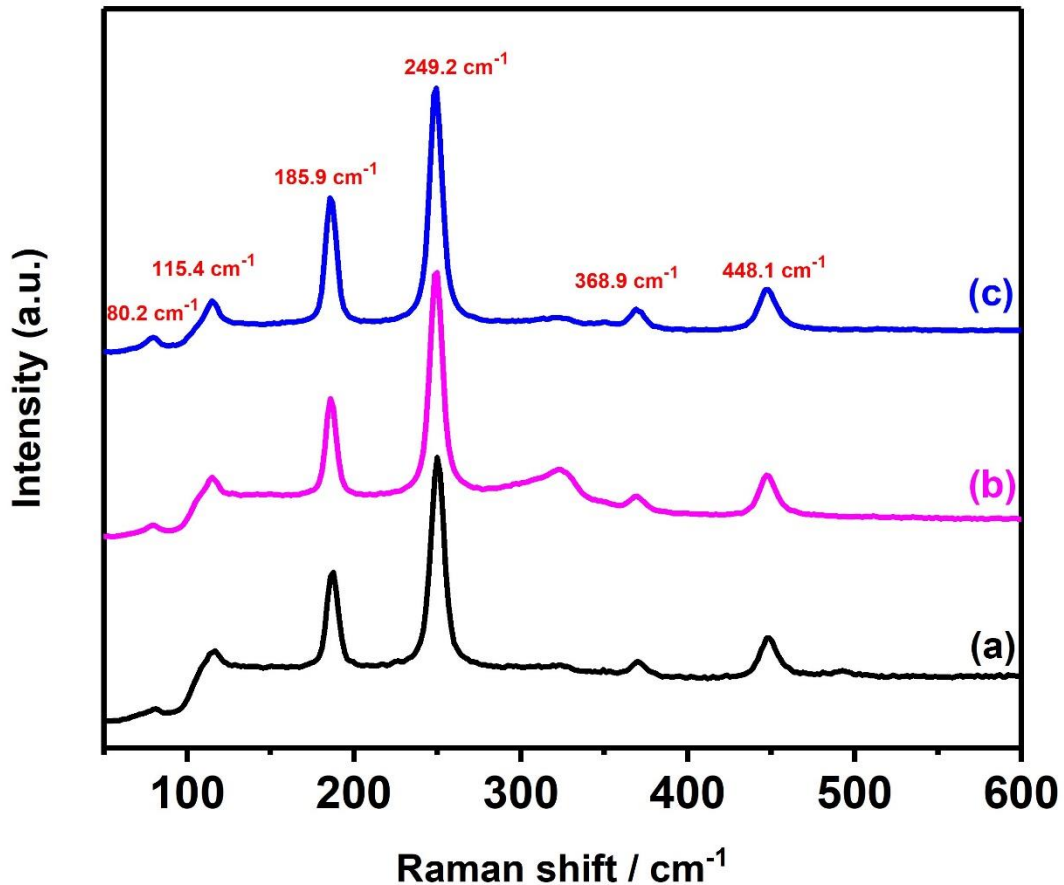

**Fig. 5** Raman spectra of  $\text{AgSbS}_2$  powders synthesised at different temperatures (a)  $400\text{ }^\circ\text{C}$ , (b)  $450\text{ }^\circ\text{C}$  and (c)  $500\text{ }^\circ\text{C}$  for 1 h under nitrogen.

Secondary electron scanning electron microscopy (SEM) was used to reveal the surface morphologies of the powders produced at different temperatures. Cubic structures are revealed for powders produced at 400 °C which changed to a porous appearance when the temperature of the synthesis was increased to 450 °C. When the temperature was increased to 500 °C, the morphology changed to flakes as shows in Fig. 6 and ESI (Fig. S2.6). Influence of the increasing temperature on the crystal structure has been reported by Habe *et al*<sup>69</sup>. The AgSbS<sub>2</sub> powders prepared at 400, 450 and 500 °C were analysed using energy-dispersive X-ray (EDX). EDX mapping gives information on the spatial distribution of elements at the micro to nanoscale and to ensure that the distribution of elements is homogeneous. Representative elemental mapping (Fig. 6) of these components showed a uniform distribution of the silver, antimony and sulfur. EDX spectra show that the samples consist only of silver, antimony and sulfur, suggesting that decomposition is clean and produces high quality crystalline materials which is consistent with the XRD and Raman data from the same materials (see supporting information for EDX sum spectra Figs. S2.7 to S2.11).

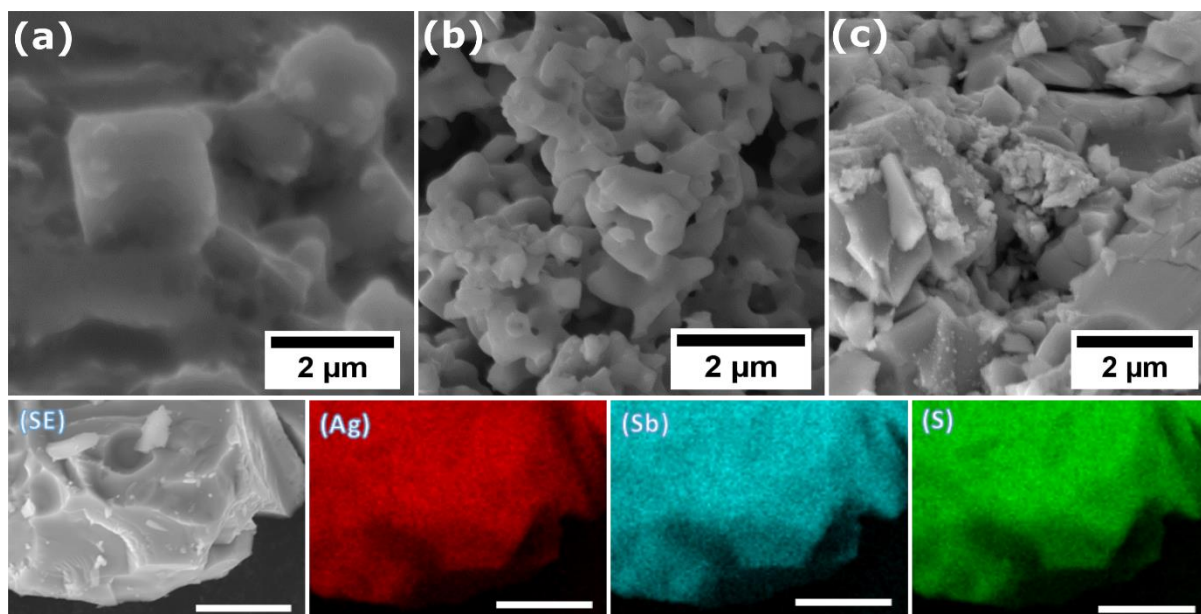

**Fig. 6** Top: SEM images of  $\text{AgSbS}_2$  powders produced at (a) 400, (b) 450 and (c) 500 °C, respectively. Bottom: EDX elemental maps revealing the distribution of Ag, Sb and S elements at the microscale for  $\text{AgSbS}_2$  produced at 500 °C (Ag  $K\alpha$ , Sb  $K\alpha$  and S  $K\alpha$ ). The unlabelled scale bars represent 10  $\mu\text{m}$ .

## Conclusions

A novel, efficient and low temperature method for the synthesis of  $\text{AgSbS}_2$  powders has been demonstrated. Silver(I) ethylxanthate [ $\text{AgS}_2\text{COEt}$ ] (**1**) and antimony(III) ethylxanthate [ $\text{Sb}(\text{S}_2\text{COEt})_3$ ] (**2**) metal xanthates precursors have been used to produce the  $\text{AgSbS}_2$  crystalline powders that have a high degree of atom efficiency. Ternary cubic  $\text{AgSbS}_2$  (cuboargyrite) was successfully produced which was evidenced by XRD and Raman spectroscopy. The XRD shows that crystallite size increase with increasing the temperature. SEM images show the change in the morphology from cubic to flakes with increasing the temperature. EDX mapping gives a clear indication of the presence of Ag, Sb and S with no other impurities. Use of solvents can be avoided altogether through the melt method which has great potential for the mass production of nanocrystalline powders of ternary materials.

## Methods

Methanol (99.8%), silver nitrate (99.9%), antimony (III) chloride (99%), potassium ethyl xanthate (96%) and chloroform-d (99%). All chemicals were purchased from Sigma-Aldrich and used as received.

### Synthesis of [AgS<sub>2</sub>COEt] (1)

Silver nitrate (1.7g, 10.0 mmol) was dissolved in 20.0 ml of deionised water. The solution was added dropwise to aqueous potassium ethyl xanthate (2.0 g, 10.6 mmol) with a constant stirring from 40 min at room temperature. The silver ethyl xanthate precursor rapidly forms. A shiny green solid of the title compound was obtained by filtration and dried at room temperature. Yield 1.9 g (86%). Melting point (M.p). 150–154 °C Anal. calc. for. Ag S<sub>2</sub>COC<sub>3</sub>H<sub>5</sub> (%): C 15.73, H 2.20, S 27.94, Ag 47.14. Found: C 15.84, H 2.13, S 27.89, Ag 46.91. FT-IR solid ( $\nu_{\max}/\text{cm}^{-1}$ ): 2978.03 (w), 2938.5 (w), 1472.38 (w), 1355.23 (m), 1184.08 (s), 1136.83 (s), 1012.45 (s), 995.57 (s). <sup>13</sup>C NMR:  $\sigma$  227.55 ppm (S<sub>2</sub>C),  $\sigma$  69.49 ppm (CH<sub>2</sub>) and  $\sigma$  13.92 ppm (CH<sub>3</sub>).

### Synthesis of [Sb(S<sub>2</sub>COEt)<sub>3</sub>] (2)

Precursor (2) was prepared as per complex (1), but with antimony trichloride (2.0 g, 8.7 mmol) dissolved in 20 ml of methanol. The resulting solution was added dropwise to potassium ethyl xanthate (4.2 g, 26.2 mmol) which was dissolved in 80 ml of methanol. The crude product was isolated by filtration and recrystallized from chloroform to give pale yellow crystals. Yield: 3.5g (80%). M.p. 88-92 °C. Anal. Calc. for Sb(S<sub>2</sub>COEt)<sub>3</sub> (%) : C 22.28, H 3.12, S 39.58, Sb 25.12. Found: C 22.11, H 2.87, S 39.54, Sb 24.46. FT-IR solid ( $\nu_{\max}/\text{cm}^{-1}$ ): 2988.64 (w), 2938.50 (w), 1468.05 (w), 1359.05 (w), 1186.49 (w), 1109.83 (s), 993.64 (s). <sup>13</sup>C NMR:  $\sigma$  222.49 ppm (S<sub>2</sub>C),  $\sigma$  72.07 ppm (CH<sub>2</sub>) and  $\sigma$  13.90 ppm (CH<sub>3</sub>).

## Synthesis of AgSbS<sub>2</sub> powders

A homogenised mixture of [AgS<sub>2</sub>COEt] (1) and [Sb(S<sub>2</sub>COEt)<sub>3</sub>] (2) complexes (1:1 mole ratio) was placed in a ceramic boat that was subsequently placed in the centre of a glass tube which was then inserted into a Carbolite tube furnace. One end of the glass tube was directly connected to nitrogen gas through a Schlenk line in the fume hood, and the other end of the tube was carefully sealed with a rubber septum. A primary vacuum was used to remove any oxygen from the glass tube, and the glass tube was then refilled with nitrogen gas. After that the mixture was heated in the Carbolite furnace at 400 °C, 450 °C and 500 °C, respectively and kept it at each temperature for 1 h under nitrogen atmosphere to produce AgSbS<sub>2</sub> powders. The final product was collected for further analysis after the system was slowly cooled to room temperature. In addition, AgSbS<sub>2</sub> thin films were also deposited by spin coating technique using the same complexes, as per the synthesis of AgSbS<sub>2</sub> powders. Full details of thin film deposition and characterisation are presented in section 3 of ESI.

## Materials Characterisation

A Specac single reflectance ATR instrument (4000–400 cm<sup>-1</sup>) with resolution 4 cm<sup>-1</sup> was used to record the infrared spectra (IR). Melting points of the complexes were obtained using a Barloworld SMP10. <sup>13</sup>C NMR spectra were obtained using a Bruker AC400 FT-NMR spectrometer. Elemental analysis was performed with a Carlo Erba EA 1108 instrument. Thermogravimetric analysis (TGA), was performed using a Seiko SSC/S200 at a heating rate of 10 °C min<sup>-1</sup> under nitrogen. Powder X-ray diffraction (XRD) measurements were carried out by a Bruker Xpert diffractometer, utilising Cu-K $\alpha$  radiation (1.54 Å). Raman spectra were recorded using a Renishaw 1000 microscope

system equipped with laser excitation of 514 nm. Scanning electron microscopy (SEM) images were obtained using a Tescan SC Oxford SEM. Electrical properties of the thin films were measured using the Van Der Pauw method by means of a custom-build Hall effect measurement system.

## References

1. Matthews, P. D., McNaughter, P. D., Lewis, D. J. & O'Brien, P. Shining a light on transition metal chalcogenides for sustainable photovoltaics. *Chem. Sci.* **8**, 4177–4187, <https://doi.org/10.1039/C7SC00642J> (2017).
2. Xuelian, Y., Shavel, A., Xiaoqiang, A., Luo, Z., Ibanez & M., Cabot, A. Cu<sub>2</sub>ZnSnS<sub>4</sub>-Pt and Cu<sub>2</sub>ZnSnS<sub>4</sub>-Au heterostructured nanoparticles for photocatalytic water splitting and pollutant degradation. *J. Am. Chem. Soc.* **26**, 9236–9239, <https://doi.org/10.1021/ja502076b> (2014).
3. Green, M. A., Emery, K., King, D. L., Igari, S., & Warta, W. Solar cell efficiency tables (Version 55), *Prog. Photovoltaics*. **28**, 3–15, <https://doi.org/10.1002/pip.3228> (2020)
4. Gusain, M., Rawat, P. & Nagarajan, R. Soft chemical synthesis of Ag<sub>3</sub>SbS<sub>3</sub> with efficient and recyclable visible light photocatalytic properties. *Mater. Res. Bull.* **60**, 872–875, <https://doi.org/10.1016/j.materresbull.2014.09.084> (2014).
5. Tubtimtae, A., Huang, C.-L., Shi, J.-B. & Lee, M.-W. Ag<sub>3</sub>SbS<sub>3</sub> thin films formed by annealing hydrothermally synthesized Ag<sub>3</sub>SbS<sub>3</sub> nanoparticles. *Mater. Lett.* **177**, 58–60, <https://doi.org/10.1016/j.matlet.2016.04.165> (2016).
6. Schönau, K. A. & Redfern, S. A. T. High-temperature phase transitions, dielectric relaxation, and ionic mobility of proustite, Ag<sub>3</sub>AsS<sub>3</sub>, and pyrargyrite, Ag<sub>3</sub>SbS<sub>3</sub>. *J. Appl. Phys.* **92**, 7415–7424, <https://doi.org/10.1063/1.1520720> (2002).
7. Kunioka, A. & Sakai, Y. Electrical and optical properties of CdO-Si junctions. *Jpn. J. Appl. Phys.* **7**, 1138, <https://doi.org/10.1143/JJAP.7.1138> (1968).
8. Sreedhar, A. K., Sharma, B. L. & Purohit, R. K. Efficiency calculations of heterojunction solar energy converters. *IEEE Trans. Electron Devices*. **16**, 309–312, <https://doi.org/10.1109/T-ED.1969.16746> (1969).
9. Goodwin, A. & Selway, P. Gain and loss processes in GaAlAs-GaAs heterostructure lasers. *IEEE J. Quantum Electron.* **6**, 285–290, <https://doi.org/10.1109/JQE.1970.1076463> (1970).
10. Castellano, A. GaSe detectors for x-ray beams. *Appl. Phys. Lett.* **48**, 298–299, <https://doi.org/10.1063/1.96586> (1986).
11. Vopdorp, C. & Vrakking, J. Photo-effects in isotype heterojunctions. *Solid-State Electron.* **10**, 955–971, [https://doi.org/10.1016/0038-1101\(67\)90011-1](https://doi.org/10.1016/0038-1101(67)90011-1) (1967).



12. Mali, S. S., Patil, P. S., & Hong, C. K. Low-cost electrospun highly crystalline kesterite  $\text{Cu}_2\text{ZnSnS}_4$  nanofiber counter electrodes for efficient dye-sensitized solar cells. *ACS Appl. Mater. Interfaces*. **3**, 1688-1696, <https://doi.org/10.1021/am404586n> (2014).
13. Yang, B., Wang, L., Han, J., Zhou, Y., Song, H., Chen, S., Zhong, J., Lv, L., Niu, D. & Tang, J.  $\text{CuSbS}_2$  as a promising earth-abundant photovoltaic absorber material: A combined theoretical and experimental study. *Chem. Mater.* **26**, 3135–3143, <https://doi.org/10.1021/cm500516v> (2014).
14. Revaprasadu, N. Nanoscience. Volume 6. United Kingdom: *Roy. Soc. Chem*: (2020).
15. Gervas, C., Dilshad Khan, M., Zhang, C., Zhao, C., Gupta, K., Carleschi, E., Doyle, B. & Revaprasadu, N. Effect of cationic disorder on the energy generation and energy storage applications of  $\text{Ni}_x\text{Co}_{3-x}\text{S}_4$  thiospinel. *RSC Adv.* **8**, 24049–24058, <https://doi.org/10.1039/C8RA03522A> (2018).
16. He, Q., Huang, S., Wang, C., Qiao, Q., Liang, N., Xu, M., Chen, W., Zai, J. & Qian, X. The Role of Mott–Schottky Heterojunctions in  $\text{Ag–Ag}_8\text{SnS}_6$  as Counter electrodes in dye-sensitized solar cells. *ChemSusChem*. **8**, 817–820, <https://doi.org/10.1002/cssc.201403343> (2015).
17. Omata, T., Nose, K. & Otsuka-Yao-Matsuo, S. Size dependent optical band gap of ternary I-III-VI<sub>2</sub> semiconductor nanocrystals. *J. Appl. Phys.* **105**, 073106, <https://doi.org/10.1063/1.3103768> (2009).
18. Rabhi, A., Kanzari, M. & Rezig, B. Optical and structural properties of  $\text{CuSbS}_2$  thin films grown by thermal evaporation method. *Thin Solid Films*. **517**, 2477–2480, <https://doi.org/10.1016/j.tsf.2008.11.021> (2009).
19. Avellaneda, D., Delgado, G., Nair, M. T. S. & Nair, P. K. Structural and chemical transformations in SnS thin films used in chemically deposited photovoltaic cells. *Thin Solid Films*. **515**, 5771–5776, <https://doi.org/10.1016/j.tsf.2006.12.078> (2007).
20. Bouaziz, M., Amlouk, M. & Belgacem, S. Structural and optical properties of  $\text{Cu}_2\text{SnS}_3$  sprayed thin films. *Thin Solid Films*. **517**, 2527–2530, <https://doi.org/10.1016/j.tsf.2008.11.039> (2009).
21. González, J. O., Shaji, S., Avellaneda, D., Castillo, A. G., Roy, T. K. D. & Krishnan, B.  $\text{AgSb}(\text{S}_x\text{Se}_{1-x})_2$  thin films for solar cell applications. *Mater. Res. Bull.* **48**, 1939–1945, <https://doi.org/10.1016/j.materresbull.2013.01.040> (2013).
22. Capistrán-Martínez, J. & Nair, P. K. Photoconductive thin films of  $\text{AgSbS}_2$  with cubic crystalline structure in solar cells. *Phys. Status Solidi A*. **212**, 2869–2876, <https://doi.org/10.1002/pssa.201532496> (2015).
23. Galdámez, A., López-Vergara, F., Veloso Cid, N., Manríquez, V. & Ávila, R. E. Copper substitutions in synthetic miargyrite  $\alpha\text{-AgSbS}_2$  mineral: Synthesis, characterization and dielectrical properties. *Mater. Chem. Phys.* **143**, 1372–1377, <https://doi.org/10.1016/j.matchemphys.2013.11.048> (2014).
24. Bera, T. K., Song, J.-H., Freeman, A. J., Jang, J. I., Ketterson, J. B. & Kanatzidis, M. G. Soluble direct-band-gap semiconductors  $\text{LiAsS}_2$  and  $\text{NaAsS}_2$ : Large electronic structure

- effects from weak As···S interactions and strong nonlinear optical response. *Angew. Chem. Int. Ed. Engl.* **47**, 7828–7832, <https://doi.org/10.1002/anie.200801392> (2008).
25. Bera, T. K., Jang, J. I., Song, J.-H., Malliakas, C. D., Freeman, A. J., Ketterson, J. B. & Kanatzidis, M. G. Soluble semiconductors AAsSe<sub>2</sub> (A = Li, Na) with a direct-band-gap and strong second harmonic generation: A combined experimental and theoretical study. *J. Am. Chem. Soc.* **132**, 3484–3495, <https://doi.org/10.1021/ja9094846> (2010).
26. Hamam, M., El-Gendy, Y. A., Selim, M. S., Teleb, N. H. & Salem, A. M. Temperature dependence of the structural and optical properties of the amorphous-to-crystalline transition in AgSbSe<sub>2</sub> thin films. *Chalcogenide Lett.* **6**, 359–365, (2009).
27. Garza, J. G., Shaji, S., Rodriguez, A. C., Das Roy, T. K. & Krishnan, B. AgSbSe<sub>2</sub> and AgSb(S,Se)<sub>2</sub> thin films for photovoltaic applications. *Appl. Surf. Sci.* **257**, 10834–10838, <https://doi.org/10.1016/j.apsusc.2011.07.115> (2011).
28. Soliman, H. S., Abdel-Hady, D. & Ibrahim, E. Optical properties of thermally vacuum evaporated AgSbSe<sub>2</sub> thin films. *J. Phys. Condens. Matter.* **10**, 847–856, <https://doi.org/10.1088/0953-8984/10/4/013> (1998).
29. Bindu, K., Campos, J., Nair, M. T. S., Sánchez, A. & Nair, P. K. Semiconducting AgSbSe<sub>2</sub> thin film and its application in a photovoltaic structure. *Semicond. Sci. Technol.* **20**, 496–504, <https://doi.org/10.1088/0268-1242/20/6/004> (2005).
30. Wang, K., Steimer, C. & Wuttig, M. Phase change properties of ternary AgSbSe<sub>2</sub> chalcogenide films. *J. Ovonic Res.* **2**, 61–65, (2006).
31. Baranova, E. R., Kobelev, V. L., Kobeleva, O. L., Melnikova, N. V., Zlokazov, V. B., Kobelev, L. Y. & Perfiliev, M. V. Electric conductivity and dielectric permittivity of mixed electronic–ionic conductivity compounds (BS)<sub>1-x</sub>(DAsS<sub>2</sub>)<sub>x</sub> (B=Ge, Pb; D=Ag, Cu). *Solid State Ion.* **124**, 255–261, [https://doi.org/10.1016/S0167-2738\(99\)00209-X](https://doi.org/10.1016/S0167-2738(99)00209-X) (1999).
32. Baranova, E. R., Kobelev, V. L., Kobeleva, O. L., Nugaeva, L. L., Zlokazov, V. B. & Kobelev, L. Y. Ionic conductivity in (AS)<sub>1-x</sub>(AgSbS<sub>2</sub>)<sub>x</sub>, (A=Ge,Sn,Pb). *Solid State Ion.* **146**, 415–421, [https://doi.org/10.1016/S0167-2738\(01\)01025-6](https://doi.org/10.1016/S0167-2738(01)01025-6) (2002).
33. Geller, S. & Wernick, J. H. Ternary semiconducting compounds with sodium chloride-like structure: AgSbSe<sub>2</sub>, AgSbTe<sub>2</sub>, AgBiS<sub>2</sub>, AgBiSe<sub>2</sub>. *Acta Crystallogr.* **12**, 46–54, <https://doi.org/10.1107/S0365110X59000135> (1959).
34. Smith, J. V., Pluth, J. J. & Han, S.-X. Crystal structure refinement of miargyrite, AgSbS<sub>2</sub>. *Mineral. Mag.* **61**, 671–675, <https://doi.org/10.1180/minmag.1997.061.408.05> (1997).
35. Kelleher, I., Redfern, S. A. T. & Pattrick, R. A. D. Cadmium substitution in miargyrite (AgSbS<sub>2</sub>) and related phases: An experimental reconnaissance. *Mineral. Mag.* **60**, 393–401, <https://doi.org/10.1180/minmag.1996.060.400.01> (1996).
36. Hofmann, W. Die struktur von miargyrit, AgSbS<sub>2</sub>. *B Preuss Akad Wiss.* **24**, 111–119, (1938).
37. Knowles, C. R. A redetermination of the structure of miargyrite, AgSbS<sub>2</sub>. *Acta Crystallogr.* **17**, 847–851, <https://doi.org/10.1107/S0365110X64002274> (1964).

38. Effenberger, H., Paar, W. H., Topa, D., Criddle, A. J. & Fleck, M. The new mineral baumstarkite and a structural reinvestigation of aramayoite and miargyrite. *Am. Mineral.* **87**, 753–764, <https://doi.org/10.2138/am-2002-5-619> (2002).
39. Maćkowski, S., Janik, E., Kyrychenko, F. & Kossut, J. Magneto-optical properties of CdTe quantum wells with ternary MgMnTe and quaternary CdMnMgTe barriers. *Thin Solid Films.* **367**, 223–226, [https://doi.org/10.1016/S0040-6090\(00\)00694-5](https://doi.org/10.1016/S0040-6090(00)00694-5) (2000).
40. Wagner, T., Gutwirth, J., Nemeč, P., Frumar, M., Wagner, T., Vlček, M., Perina, V., Mackova, A. & Hnatovitz, V. Amorphous chalcogenide AgSbS<sub>2</sub> films prepared by pulsed laser deposition. *Appl. Phys. A.* **79**, 1561–1562, <https://doi.org/10.1007/s00339-004-2847-z> (2004).
41. Gutwirth, J., Wágner, T., Kotulánová, E., Bezdička, P., Peřina, V., Hrdlička, M., Vlček, M., Drařar, Ā. & Frumar, M. On RF magnetron-sputtering preparation of Ag–Sb–S thin films. *J. Phys. Chem. Solids.* **68**, 835–840, <https://doi.org/10.1016/j.jpcs.2007.03.030> (2007).
42. Houřka, J., Peņa-Méndez, E. M., Kolář, J., Frumar, M., Wágner, T. & Havel, J. Laser ablation of AgSbS<sub>2</sub> and cluster analysis by time-of-flight mass spectrometry. *Rapid Commun. Mass Spectrom.* **23**, 1715–1718, <https://doi.org/10.1002/rcm.4048> (2009).
43. Nair, P. S., Radhakrishnan, T., Revaprasadu, N., Kolawole, G., & O'Brien. Cadmium ethylxanthate: A novel single-source precursor for the preparation of CdS nanoparticles. *J. Mater. Chem.* **9**, 2722–2725, <https://doi.org/10.1039/B202072F> (2002).
44. Rath, T., MacLachlan, A. J., Brown, M. D., & Haque, S. A. Structural, optical and charge generation properties of chalcostibite and tetrahedrite copper antimony sulfide thin films prepared from metal xanthates. *J. Mater. Chem.A.* **47**, 24155–24162, <https://doi.org/10.1039/C5TA05777A> (2015).
45. Masikane, S.C., McNaughte, P.D., Lewis, D.J., Vitorica-Yrezabal, I., Doyle, B.P., Carleschi, E., O'Brien, P. & Revaprasadu, N. Important Phase Control of Indium Sulfide Nanomaterials by Choice of Indium (III) Xanthate Precursor and Thermolysis Temperature. *Eur. J. Inorg. Chem.* **10**, 1421–1432, <https://doi.org/10.1002/ejic.201900007> (2019).
46. Alderhami, S.A., Collison, D., Lewis, D.J., McNaughte, P.D., O'Brien, P., Spencer, B.F., Vitorica-Yrezabal, I. & Whitehead, G. Accessing  $\gamma$ -Ga<sub>2</sub> S<sub>3</sub> by solventless thermolysis of gallium xanthates: a low-temperature limit for crystalline products. *Dalton Trans.* **48**, 15605–15612, <https://doi.org/10.1039/C9DT02061F> (2019).
47. Akhtar, M., Malik, M.A., Tuna, F. and O'Brien, P. & synthesis of iron sulfide nanocrystals from tris (O-alkylxanthato) iron (III) complexes. *J. Mater. Chem. A.* **31**, 8766–8774, <https://doi.org/10.1039/C3TA12178J> (2013).
48. Saah, S.A., McNaughte, P.D., Malik, M.A., Awudza, J.A., Revaprasadu, N. & O'Brien, P. PbS<sub>x</sub> Se<sub>1-x</sub> thin films from the thermal decomposition of lead(II) dodecylxanthate and bis(N,N-diethyl-N'-naphthoylselenoureato)lead(II) precursors. *J. Mater. Sci.* **53**, 4283–4293, <https://doi.org/10.1007/s10853-017-1836-5> (2018).
49. Masikane, S.C., McNaughte, P.D., Lewis, D.J., Vitorica-Yrezabal, I., Doyle, B.P., Carleschi, E., O'Brien, P. & Revaprasadu, N. Important Phase Control of Indium Sulfide

- Nanomaterials by Choice of Indium(III) Xanthate Precursor and Thermolysis Temperature. *Eur. J. Inorg. Chem.* **10**, 1421-1432, <https://doi.org/10.1002/ejic.201900007> (2019).
50. Saah, S.A., Khan, M.D., Awudza, J.A., Revaprasadu, N. & O'Brien, P. A Facile Green Synthesis of Ultranarrow PbS Nanorods. *J Inorg Organomet Polym.* **29**, 2274–2281, <https://doi.org/10.1007/s10904-019-01185-1> (2019).
51. Al-Shakban, M., Matthews, P. D., Deogratias, G., McNaughter, P. D., Raftery, J., Vitorica-Yrezabal, I., Mubofu, E. B. & O'Brien, P. Novel xanthate complexes for the size-controlled synthesis of copper sulfide nanorods. *Inorg. Chem.* **56**, 9247–9254, <https://doi.org/10.1021/acs.inorgchem.7b01288> (2017).
52. Zhang, C., Zhang, S., Yu, L., Zhang, Z., Zhang, P. & Wu, Z. Size-controlled synthesis of monodisperse Ag<sub>2</sub>S nanoparticles by a solventless thermolytic method. *Mater. Lett.* **85**, 77–80, <https://doi.org/10.1016/j.matlet.2012.06.112> (2012).
53. Khan, M. D., Murtaza, G., Revaprasadu, N. & O'Brien, P. Synthesis of chalcopyrite-type and thiospinel minerals/materials by low temperature melts of xanthates. *Dalton Trans.* **47**, 8870–8873, <https://doi.org/10.1039/C8DT00953H> (2018).
54. Alqahtani, T., Dilshad Khan, M., J. Kelly, D., J. Haigh, S., J. Lewis, D. & O'Brien, P. Synthesis of Bi<sub>2-2x</sub>Sb<sub>2x</sub>S<sub>3</sub> (0 ≤ x ≤ 1) solid solutions from solventless thermolysis of metal xanthate precursors. *J. Mater. Chem. C.* **6**, 12652–12659, <https://doi.org/10.1039/C8TC02374C> (2018).
55. Fradler, C., Rath, T., Dunst, S., Letofsky-Papst, I., Saf, R., Kunert, B., Hofer, F., Resel, R. & Trimmel, G. Flexible polymer/copper indium sulfide hybrid solar cells and modules based on the metal xanthate route and low temperature annealing. *Sol. Energy Mater. Sol. Cells.* **124**, 117–125, <https://doi.org/10.1016/j.solmat.2014.01.043> (2014).
56. Leventis, H. C., King, S. P., Sudlow, A., Hill, M. S., Molloy, K. C. & Haque, S. A. Nanostructured hybrid polymer–inorganic solar cell active layers formed by controllable in situ growth of semiconducting sulfide networks. *Nano Lett.* **10**, 1253–1258, <https://doi.org/10.1021/nl903787j> (2010).
57. Rath, T., Padeste, C., Vockenhuber, M., Fradler, C., Edler, M., Reichmann, A., Letofsky-Papst, I., Hofer, F., Ekinici, Y. & Griesser, T. Direct extreme UV-lithographic conversion of metal xanthates into nanostructured metal sulfide layers for hybrid photovoltaics. *J. Mater. Chem. A.* **1**, 11135–11140, <https://doi.org/10.1039/C3TA12592K> (2013).
58. Lewis, E. A., McNaughter, P. D., Yin, Z., Chen, Y., Brent, J. R., Saah, S. A., Raftery, J., Awudza, J. A. M., Malik, M. A., O'Brien, P. & Haigh, S. J. In situ synthesis of PbS nanocrystals in polymer thin films from lead(II) xanthate and dithiocarbamate complexes: Evidence for size and morphology control. *Chem. Mater.* **27**, 2127–2136, <https://doi.org/10.1021/cm504765z> (2015).
59. Al-Shakban, M., Xie, Z., Savjani, N., Malik, M. A. & O'Brien, P. A facile method for the production of SnS thin films from melt reactions. *J. Mater. Sci.* **51**, 6166–6172, <https://doi.org/10.1007/s10853-016-9906-7> (2016).
60. Al-Shakban, M., Matthews, P. D., Savjani, N., Zhong, X. L., Wang, Y., Missous, M. & O'Brien, P. The synthesis and characterization of Cu<sub>2</sub>ZnSnS<sub>4</sub> thin films from melt reactions

- using xanthate precursors. *J. Mater. Sci.* **52**, 12761–12771, <https://doi.org/10.1007/s10853-017-1367-0> (2017).
61. McNaughter, P. D., Saah, S. A., Akhtar, M., Abdulwahab, K., Malik, M. A., Raftery, J., Awudza, J. A. M. & O'Brien, P. The effect of alkyl chain length on the structure of lead(II) xanthates and their decomposition to PbS in melt reactions. *Dalton Trans.* **45**, 16345–16353, <https://doi.org/10.1039/C6DT02859D> (2016).
62. Buckingham, M. A., Catherall, A. L., Hill, M. S., Johnson, A. L. & Parish, J. D. Aerosol-assisted chemical vapor deposition of CdS from xanthate single source precursors. *Cryst. Growth Des.* **17**, 907–912, <https://doi.org/10.1021/acs.cgd.6b01795> (2017).
63. Alanazi, A. M., Alam, F., Salhi, A., Missous, M., Thomas, A. G., O'Brien, P. & Lewis, D. J. A molecular precursor route to quaternary chalcogenide CFTS (Cu<sub>2</sub>FeSnS<sub>4</sub>) powders as potential solar absorber materials. *RSC Adv.* **9**, 24146–24153, <https://doi.org/10.1039/C9RA02926E> (2019).
64. Kibasomba, P. M., Dhlamini, S., Maaza, M., Liu, C.-P., Rashad, M. M., Rayan, D. A. & Mwakikunga, B. W. Strain and grain size of TiO<sub>2</sub> nanoparticles from TEM, Raman spectroscopy and XRD: The revisiting of the Williamson-Hall plot method. *Results Phys.* **9**, 628–635, <https://doi.org/10.1016/j.rinp.2018.03.008> (2018).
65. Zhou, B., Li, M., Wu, Y., Yang, C., Zhang, W.-H. & Li, C. Monodisperse AgSbS<sub>2</sub> nanocrystals: Size-control strategy, large-scale synthesis, and photoelectrochemistry. *Chem. Eur. J.* **21**, 11143–11151, <https://doi.org/10.1002/chem.201501000> (2015).
66. Almanqur, L., Alam, F., Whitehead, G., Vitorica-yrezabal, I., O'Brien, P. & Lewis, D. J. Synthesis of iron sulfide thin films and powders from new xanthate precursors. *J. Cryst. Growth.* **522**, 175–182, <https://doi.org/10.1016/j.jcrysgro.2019.05.029> (2019).
67. Wang, T., Farvid, S. S., Abulikemu, M. & Radovanovic, P. V. Size-tunable phosphorescence in colloidal metastable  $\gamma$ -Ga<sub>2</sub>O<sub>3</sub> nanocrystals. *J. Am. Chem. Soc.* **132**, 9250–9252, <https://doi.org/10.1021/ja101333h> (2010).
68. Minceva-Sukarova, B., Jovanovski, G., Makreski, P., Soptrajanov, B., Griffith, W., Willis, R. & Grzetic, I. Vibrational spectra of M<sup>I</sup>M<sup>III</sup>S<sub>2</sub> type synthetic minerals (M<sup>I</sup>=Tl or Ag and M<sup>III</sup>=As or Sb). *J. Mol. Struct.* **651–653**, 181–189, [https://doi.org/10.1016/S0022-2860\(03\)00105-4](https://doi.org/10.1016/S0022-2860(03)00105-4) (2003).
69. Versavel, M. Y. & Haber, J. A. Structural and optical properties of amorphous and crystalline antimony sulfide thin-films. *Thin Solid Films.* **515**, 7171–7176, <https://doi.org/10.1016/j.tsf.2007.03.043> (2007).
70. Lewis, D.J & Winpenny, R.E.P. Paul O'Brien. 22 January 1954—16 October 2018 *Biog. Mem. Fell. Roy. Soc.* **69**, 443-446. <https://doi.org/10.1098/rsbm.2019.0041> (2020)

## **Acknowledgements**

Y.T.A. would like to acknowledge the Ministry of education (King Salman scholarship program) for financial support. F.A. and D.J.L. would like to acknowledge funding from EPSRC UK grant number EP/R020590/1. The authors thank Prof. David Collison for his guidance and support and the inspiration of Paul O'Brien<sup>70</sup> (22 January 1954—16 October 2018).

## **Author contributions**

D.J.L. conceived and supervised the project. Y.T.A. performed the experimental work on synthesis and characterization of the precursors and silver antimony sulfide powders and thin films. D.J.L., Y.T.A. and F.A. analysed data. The electrical properties were measured by A.S and M.M. D.J.L., F.A. and Y.T.A. wrote the manuscript.

## **Additional Information**

Electronic Supporting Information

**Competing financial interests:** The authors declare no competing financial interests