

Review

# Powder Bed Fusion Additive Manufacturing using CRM materials: a review

Vladimir V. Popov <sup>1\*</sup>, Maria Luisa Grilli <sup>2</sup>, Andrey Koptug <sup>3</sup>, Lucyna Jaworska <sup>4</sup>, Alexander Katz-Demyanetz <sup>1</sup>, Damjan Klobčar <sup>5</sup>, Sebastian Balos <sup>6</sup>, Bogdan O. Postolnyi <sup>7,8</sup> and Saurav Goel <sup>9,10,11</sup>

- <sup>1</sup> Israel Institute of Metals, Technion R&D Foundation, 3200003, Haifa, Israel, [vvp@technion.ac.il](mailto:vvp@technion.ac.il)
- <sup>2</sup> ENEA–Italian National Agency for New Technologies, Energy and Sustainable Economic Development, Casaccia Research Centre, Via Anguillarese 301, 00123 Rome, Italy, [marialuisa.grilli@enea.it](mailto:marialuisa.grilli@enea.it)
- <sup>3</sup> SportsTech Research Center, Mid Sweden University, Akademigatan 1, Östersund, Sweden, [Andrey.Koptug@miun.se](mailto:Andrey.Koptug@miun.se)
- <sup>4</sup> Faculty of Non-Ferrous Metals, AGH University of Science and Technology, 30-059 Krakow, Poland, [ljaw@agh.edu.pl](mailto:ljaw@agh.edu.pl)
- <sup>5</sup> Faculty of Mechanical Engineering, University of Ljubljana, Aškerčeva c. 6, 1000 Ljubljana, Slovenia, [Damjan.Klobcar@fs.uni-lj.si](mailto:Damjan.Klobcar@fs.uni-lj.si)
- <sup>6</sup> Department of Production Engineering, Faculty of Technical Science, University of Novi Sad, Novi Sad, Serbia, [sebab@uns.ac.rs](mailto:sebab@uns.ac.rs)
- <sup>7</sup> IFIMUP – Institute of Physics for Advanced Materials, Nanotechnology and Photonics, Department of Physics and Astronomy, Faculty of Sciences, University of Porto, 687 Rua do Campo Alegre, 4169-007 Porto, Portugal, [b.postolnyi@gmail.com](mailto:b.postolnyi@gmail.com)
- <sup>8</sup> Department of Nanoelectronics and Surface Modification, Sumy State University, 2 Rymskogo-Korsakova st., 40007 Sumy, Ukraine, [b.postolnyi@gmail.com](mailto:b.postolnyi@gmail.com)
- <sup>9</sup> School of Engineering, London South Bank University, London, SE10AA, UK, [GoeLs@Lsbu.ac.uk](mailto:GoeLs@Lsbu.ac.uk)
- <sup>10</sup> School of Aerospace, Transport and Manufacturing, Cranfield University, Cranfield, MK43 0AL, UK, [GoeLs@Lsbu.ac.uk](mailto:GoeLs@Lsbu.ac.uk)
- <sup>11</sup> Department of Mechanical Engineering, Shiv Nadar University, Gautam Budh Nagar, 201314, India, [GoeLs@Lsbu.ac.uk](mailto:GoeLs@Lsbu.ac.uk)
- \* Correspondence: [vvp@technion.ac.il](mailto:vvp@technion.ac.il)

**Abstract:** The term "Critical Raw Materials" (CRMs) refers to various metals and non-metals that are crucial to Europe's economic progress. Modern technologies enabling effective use and recyclability of CRMs are in critical demand for the EU industry. The use of CRMs especially in the field of biomedical, aerospace, electric vehicles, and energy application is almost irreplaceable. Additive Manufacturing (also referred to as 3D printing) is one of the key enabling technologies in the field of manufacturing which underpins the fourth Industrial Revolution. Not only does 3D printing suppresses waste but it also provides an efficient buy-to-fly ratio and possesses the potential to entirely change supply and distribution chains significantly reducing costs and revolutionizing all logistics. This review provides comprehensive new insights into CRM-containing materials processed by modern AM techniques and outlines the potential for increasing the efficiency of CRM utilisation and reducing the dependence on CRMs through wider industrial incorporation of AM and specifics of powder-bed AM methods making them prime candidates for such developments.

**Keywords:** Additive Manufacturing; Critical Raw Materials; CRM; recyclability; powders for additive manufacturing; Powder Bed Fusion

## 1. Introduction

There is a growing global concern about securing access to metals and minerals needed for developing economic production. The dependence of industrial sectors on scarce materials, in many cases almost entirely dependent on remote sources, represents



European initiatives were broadening, and in 2011 EU together with Japan and the US started a trilateral dialogue to promote cooperation in the field of critical materials, identifying the main areas of cooperation in collecting raw materials data, analysing trade, waste recycling and options for CRM substitution. Representatives of the European Commission (EC), the US Department of Energy (DOE), and Japan's Ministry of Economy, Trade and Industry (METI) and the New Energy and Industrial Technology Development Organization for Japan, decided to meet annually since 2011 for discussing CRM issues via a Trilateral Conference.

The growing interest of researchers in solving the problem associated with the supply risk of raw materials can be testified by the increasing number of publications published during the last decade covering topics such as CRMs applications, manufacturing, recycling and life cycle analysis. A simple search through research databases for the keywords, "critical raw materials" returns 330 publications as of February 2021 in the Scopus database alone, with first publication reported in 1975 [9] and annual publication numbers increasing considerably since 2012. Results also indicate that the publications mostly focus on recycling, substitution, circular economy and rare earth elements. This search concerns only the publications specifically addressing as keyword "critical raw materials", while other publications on manufacturing technologies, industrial applications and disposal of individual elements coupled with the keyword CRM would yield even more papers.

The corresponding report on the assessment of the methodology for establishing the EU CRMs list screened 212 communications dealing with critical raw materials: around 233 organisations were identified as being involved in criticality studies. Among these, 72 developed their methodology and 58 organizations developed their CRMs lists [10]. In 2018, the Department of the Interior of the United States published the list of 36 critical minerals and elements (including aluminum, arsenic, barite, beryllium, bismuth, cesium, chromium, cobalt, fluorspar, gallium, germanium, graphite, hafnium, helium, indium, lithium, magnesium, manganese, niobium, platinum group metals, potash, the rare earth elements group, rhenium, rubidium, scandium, strontium, tantalum, tellurium, tin, titanium, tungsten, uranium, vanadium, and zirconium), and declared their 100% import reliance on 14 minerals [11,12].

Currently, known approaches to address the problem of CRMs are summarized in Fig. 2. They are related to securing the supply chain (through raw materials diplomacy and developing own mining and recycling), extending the lifetime of the products containing CRMs, developing more sustainable production methods for materials containing CRMs and introducing new CRM-free materials. In absence of having immediate availability of raw materials, novel solutions for improving raw material production, recycling, reducing the consumption and substitution of CRMs move to the top of the agenda [8,13,14].



**Figure 2.** Primary solutions to tackle and address the issue of critical raw materials.

One of the technologies capable of solving some of the discussed challenges is Additive Manufacturing (AM) of metals and non-metallic materials. AM adds a material layer-by-layer in contrast to the traditional methods of subtractive manufacturing, removing material from large ingots by turning, drilling and milling. Unique advantages of AM methods include achieving unprecedented freedom in the shape, significant reduction of waste and, in many cases, reduction of energy consumption [15–17]. Specific processing conditions characteristic to AM allow for developing new materials with unique properties not possible to manufacture by other methods, including bulk metallic glasses [18,19], high entropy alloys [20–22] and different composites [23,24]. Due to these reasons, Additive Manufacturing was identified as an essential part of the upcoming 4th industrial revolution, and in particular, as an effective and promising method to reduce CRM used in a wide variety of industrial production processes [8,13].

Today, AM technologies are capable of utilising a variety of different materials. This review focuses on the AM methods capable of working with metallic and ceramic materials, most relevant to the CRMs. This review also aims to outline emerging possibilities provided by AM capable to mitigate critical CRM challenges, and to highlight the recent trends in AM of CRMs.

A carefully designed and developed methodology was used to screen the materials presented in this review paper. As such three separate lines of the search were performed from the openly available research publications and legislature documents. Corresponding databases used were Google Scholar, Science Direct (Scopus), Springer Link, Wiley Online Library, EU public document and decision databases (Public Register Europa - Europa EU, Documents and publications by EU - Consilium.europa.eu) and open Google search.

The first line of search concerned the issues related to CRMs and corresponding future challenges. The material obtained from this search pattern is the basis of Chapter 1. The second line of search concerned the use of CRMs in additive manufacturing- as individual elements and as parts of alloys. Particular focus was on the precursor material manufacturing methods, AM methodology and material recycling, which has informed the writing of Chapters 2 and 3. The third line of the search was partially based on own databases of the research publications, and on additional search on the advantages of AM and future trends in AM development relevant to solving critical issues and future challenges for CRMs.

Since the primary scope for this research is focused on the additive manufacturing of CRMs, corresponding approach is material- and technology-focused. From this point of view, a full initial database of the publications involved results of all three searches. Corresponding inclusion criteria were official documents and open scientific publications from peer-reviewed sources. The corresponding initial database was split into three subsets referring to three lines of the search described earlier. One should note, that some of the papers were presented in two or even all three sub-sets.


## 2. Powder materials used for Additive Manufacturing

Powder precursor materials are the base for a large family of AM technologies currently used in industry, such as:

1. Powder Bed Fusion (PBF) including Selective Laser Sintering (SLS), Selective Laser Melting (SLM) and Electron Beam Melting (EBM);
2. Nano-Particle Jetting (XJET process);
3. Binder Jetting Printing (BJP);
4. Laser Engineering Net Shaping (LENS).

The requirements for powder precursor materials depend on specific AM technology (see Fig.3). The fundamental requirements to metal and ceramic powders include grain shape (spherical, irregular, granulated); grain size (nano-, submicron-, or micron powder);

composition (pre-alloyed or blended); gas infusions; powder flowability; tendency to oxidise; sintering/melting conditions; etc.

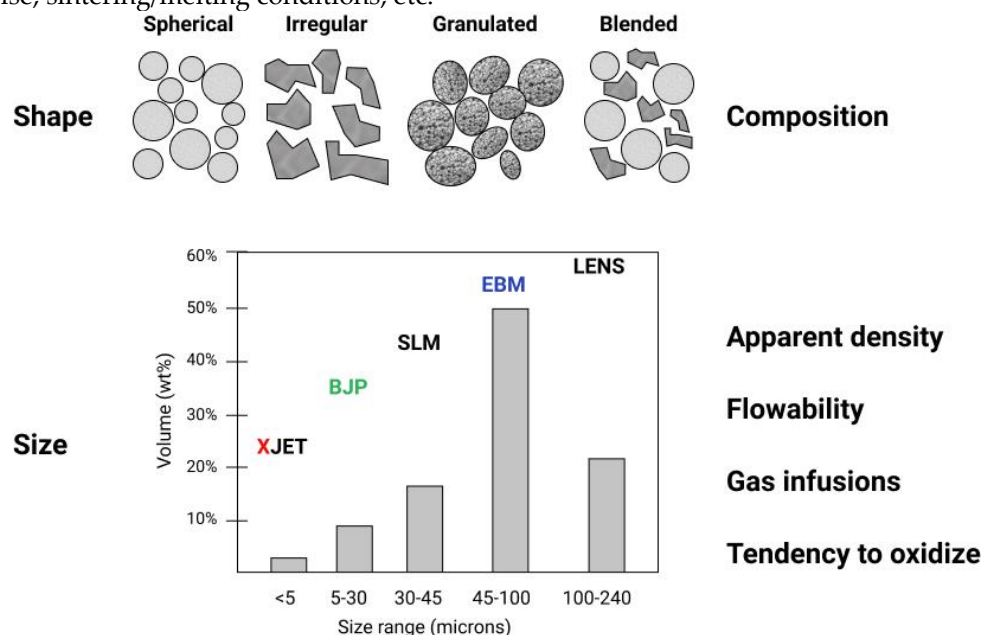

**Figure 3.** Crucial powder characteristics in additive manufacturing

Fig.3 illustrates the typical powder grain size distribution required by different AM systems by taking an example of titanium alloy powders produced by gas atomization [25]. EBM uses a nominal particle size distribution between 45–106  $\mu\text{m}$ , whilst SLM uses finer powders between 15–45  $\mu\text{m}$ . Particle size distribution has a serious impact on the capabilities of the corresponding AM technology. Powders with finer grains allow to achieve better control on the layer thickness which aids to improve print resolution while reducing the as-printed roughness of the components [26]. On the other hand, thicker layers with larger size grain powder potentially allow faster manufacturing. The presence of finer powder fractions in the distribution allows for higher packing density since small particles help in filling the voids between larger ones increasing the volume of solid metal produced from the powder layer. Small particles (smaller than 15–10  $\mu\text{m}$ ) reduce the flowability of the powder and increase the risks during powder handling. So a trade-off in the particle size distribution is needed to obtain high packing density and good flow properties [27,28].

Powder bed AM technologies, such as SLM, EBM and LENS predominantly rely on using individual elemental or pre-alloyed powders. During atomization, processing, intermediate handling and subsequent shipping at air atmosphere, the metal powder can become contaminated adsorbing gases such as argon from atomization, oxygen, nitrogen and moisture from the air.

Surface oxide of metal powders (composition, phases/inclusions and their distribution, thickness etc.) is connected to the cooling rate and other conditions during atomization, the particle size and secondary dendrite arm spacing, the type of atomization (e.g., water-, gas-atomization, or rotating electrode process), and the oxygen availability [29,30]. The undesirable entrapped or adsorbed gases and moisture become the source of pores in manufactured components and can react during the AM process forming oxide or nitride inclusions and layers at the microstructure boundary surfaces. These oxides result in thin, inherently weak grain boundaries and limit the bonding forces between individual powder particles during AM processing. A powder thermal pre-treatment, which involves degassing the powder at an elevated temperature in a vacuum, is one of the possible ways

of dealing with the issue. With laser-based AM technologies, it becomes a common addition to the main process, while in EBM it happens inside the machine as one of the essential process stages. Without powder thermal pre-treatment, other undesired effects during melting can also occur, including the formation of the “balls” fused randomly to the top of a processed solid layer severely distorting the process [31].

The powder particle size and shape are quite critical. Together with the powder elemental content and level of purity, they play a crucial role in powder selection for AM [32]. It is quite difficult to obtain high-density products with the powders, having irregular grains strongly deflecting from spherical, or having large numbers of so-called “satellites” (smaller particles fused with the main grain). In such a case, it commonly results in materials with high porosity and heterogeneity of the microstructure and even anisotropy of properties. In addition, powder particles with a specific surface have a greater tendency to adsorb gases and humidity from the atmosphere. An important parameter for the overall quality of AM parts is the apparent density of powder before sintering or melting. Though it is not definite, a common “rule of thumb” for example for EBM suggests that the apparent density of the loose powders should generally be between 50 and 75% for the solidified material. Studies have shown that the control and selection of powder particle shape and size distribution can increase the apparent density of the powder deposited in a layer. Experiments show that the apparent density of thin powder layers increases from 53% to 63% of solid material when adding 30 volume % of fine powder to the coarse one [33].

### 2.1. Metal powders for Additive Manufacturing

Metallic elemental and alloy powders grain shape, size distribution, surface morphology and composition, and overall purity are of great importance in the production of good quality and fully dense components [34]. It is valid not only for the freshly manufactured powders but for the powders after storage and recycling. Even for the materials having no tendency to easily react with oxygen, the presence of surface oxide can strongly impact the property of additively manufactured components (e.g. [35,36]).


The characterisation of powders is commonly made by using different analytical techniques including X-ray Photoelectron Spectroscopy (XPS), Auger Electron Spectroscopy (AES), scanning/transmission electron microscopy (SEM/TEM), electron backscattered diffraction (EBSD) and X-ray Diffraction (XRD). These techniques are limited in terms of either spatial or lateral resolution or chemical information of phases and hence are often required to be done together to obtain more meaningful information [37]. Both the characteristics of the metal powder and the type of the AM process determine the properties of the product. Since during AM, powder is commonly recycled, characterization of its properties is performed not only for the as-received samples, but also at regular intervals throughout the manufacturing process.

### 2.2. Production of metal powders for Additive Manufacturing

Metal powders can be produced using several methods, some of which are solid-state reduction, milling, electrolysis, chemical processes, and atomisation [38]. Atomisation so far is the most common route for producing metal powders for AM, dominating the market for powder-bed AM. Corresponding atomization technologies are well established. They allow producing powders with different grain sizes in adequate shapes from a variety of metallic materials. These methods are quite cost-competitive and allow for bulk production of powders for both AM and traditional powder metallurgy. The first stage of the overall production chain involves traditional mining and extraction of an ore to form a pure or alloyed bulk metal product (ingot, wire, rod). The second stage is powder production itself (atomization process) followed by sifting into different fractions, size and shape classification and validation. For PBF, additional flow tests are commonly added to the validation protocol.

The specific atomization process can be different depending on the chosen AM technology. Gas and plasma atomization producing particles of quite regular, close to spherical shape with rather small porosity and high uniformity are the most relevant ones for the powder-based AM (see Fig.4a-b). Annual powder production using water atomisation so far well exceeds the volumes produced by gas atomization. However, water atomization results in particles with a highly irregular morphology as the particles solidifies faster than their spheroidization time. The resulting powders can contain trapped water and, with some metallic materials, metal hydrides. This renders the water atomization process unsuitable for AM [26].

All atomization processes consist of three main integrated steps: melting, atomization and solidification. Melting can be accomplished by different techniques such as vacuum induction melting, plasma arc melting, induction drip melting, or direct plasma heating [39]. Though ideal powder grain shape is near spherical, depending on the method of powder production used, non-spherical particles, joined particles and particles with different intrinsic morphology (e.g., "tear-drop" shapes) and irregularly shaped ones may occur [32]. In some cases, fractions of irregular-shaped grains can be accepted for AM precursor materials if they do not strongly disturb the powder flowability or apparent density.

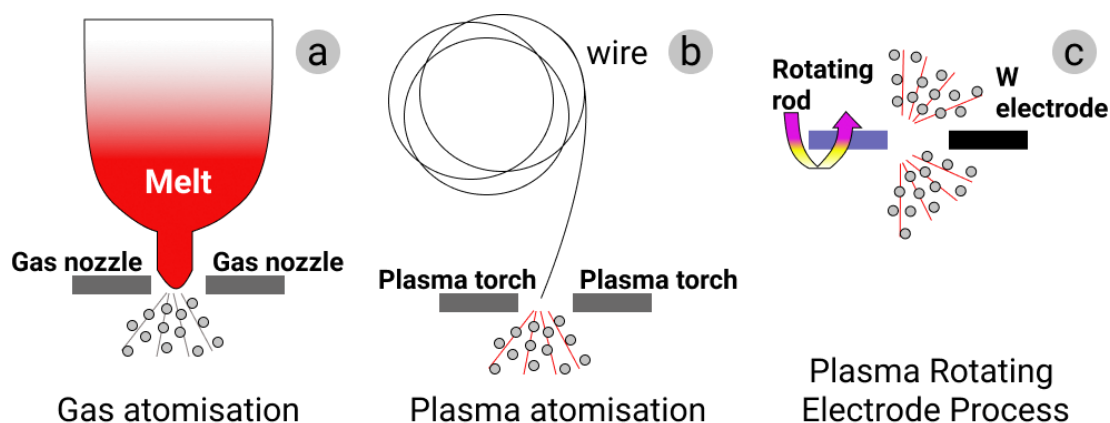

**Figure 4.** Production of metal powders: a – gas atomization; b – plasma atomization; c – plasma rotating electrode process.

### 2.2.1. Gas Atomisation

In Gas Atomization (GA), the feedstock elemental metal or alloy is melted in a furnace, usually in a vacuum induced melting (VIM) one. The furnace is positioned above the atomisation chamber for direct material discharge into the atomiser. In gas atomization, the stream of liquid metal is broken by a high velocity gas flow (air, nitrogen, argon, or helium) (Fig.4a). Air is commonly used for the atomization of ferrous alloys, and inert gases are used for non-ferrous ones [40,41]. A high solidification rate characteristic for this method results in powders with good material microstructure and quite a homogeneous composition. The particle size distribution can be modulated to a certain extent by adjusting the ratio of gas to melt flow rate. Commercial gas atomized powders commonly have near to spherical grains with small numbers of attached satellites. Median particle size is in the range of 50  $\mu\text{m}$  to 300  $\mu\text{m}$ . For a given particle size, cooling rates are about one order of magnitude lower than in water atomization. Some of the powder materials produced by gas atomisation are nickel, iron, aluminium, titanium and cobalt. The characteristic particle size plays a crucial role in the micro-morphology, porosity and gas content of the atomized powders. Pore size and pore presence within powders gradually increase with the increase of average grain size [42]. Although the yield of the fine powder prepared by the GA method is high, such powders are generally characterized by wide particle size distribution and high fraction of hollow powders, which is detrimental to the performance

of resultant AM products. Consequently, the yield of the powder with a defined selected grain size fraction after sieving can become significantly lower.

#### 2.2.2. Plasma Atomization

Plasma atomization (PA) has been developed to produce fine, spherical powders. PA utilises multiple direct-current arc plasma steps to accelerate the atomization gas. In the PA process, metal wires are fed into the apex of the gas plasma flow, where they melt and are atomized in a single step (see Fig.4b). This process offers a unique ability to produce spherical powders of reactive metals with a typical average particle size of 40  $\mu\text{m}$  and the particle size distribution from nanometres to 250  $\mu\text{m}$  [43]. Plasma Atomization produces premium quality spherical powders of reactive and high melting point materials such as titanium, nickel, zirconium, molybdenum, niobium, tantalum, tungsten and their alloys. This process offers the highest purity powders with trueness in spherical shape of the particles and minimal satellite content. The powder obtained using this method exhibits exceptionally flow ability and good packing properties [44].

#### 2.2.3. Plasma rotating electrode process

A more specialised method called plasma rotating electrode process (PREP) makes use of a rotating bar instead of a wire as the source of metal, whereby on entry to the atomisation chamber, the bar extremity is melted by the plasma torches and solidifies before reaching the encompassing walls of the chamber [45] (see Fig.4c). This process results in powders of high purity, with quite spherical grains, and fine particle sizes (from several nanometres to 100  $\mu\text{m}$ ). Titanium and exotic materials can be produced by PREP [26,46]. The PREP powder is widely recognized to have very high purity and near-perfect spherical shape. Certain presence of satellites on powder grains not only reduces the fluidity of the powder but also adversely affects the performance of the final products. Present research on *Ti-6Al-4V*, *316L* austenitic stainless steel and Co-Cr-Mo alloy, suggests that it is barely possible to avoid the presence of satellites and joined powder grains during PREP in its present shape [46].

#### 2.2.4. Mechanical spheroidization of metal powders

Certain strategies for improving the powders having irregular shapes after atomization were reported, including mechanical spheroidization of the grains [47]. The flow ability of irregularly shaped powders can be significantly improved by tapering sharp edges on the particles through high-speed blending or high shear milling. Nonetheless, the particles produced by this method are only quasi-spherical, which may limit the applications of such powders. In addition, this method should be used with certain care, because of potential mechanical and mechano-chemical effects including particle surface strengthening and compaction, the formation of oxide and nitride surface films, and changes in material microstructure. Such changes can affect the AM process parameters and the quality of manufactured material and components.

### 2.3. Metal powders processed in Additive Manufacturing

There is a wide range of metallic powders that are already used in AM. Their choice depends on the desired properties of the product and employed AM technology. Some of the common metal powders utilised in AM are nickel, steel, aluminium, cobalt-chromium, and titanium alloys. This publication describes issues regarding materials, most of which, do not belong to the group of critical materials. However, it should be remembered that not all alloying elements for these materials belong to the critical materials, and in many cases, the CRMs share in such alloys is relatively small. However, with growing demand for the additive manufacturing of such alloys, they are widely accepted by the industry, when produced by more traditional methods.

#### 2.3.1. Tungsten alloys



Tungsten (*W*) has the highest melting and boiling point among other elements and the lowest thermal expansion coefficient (CTE) among metals [48]. It is mainly produced from wolframite and scheelite and the main producer is China having about 50% of the world's reserves.

Cemented carbides, *WC-Co* is the main application of tungsten [49]. Studies are reported on additive manufacturing of *WC-12%Co* using BJP [50]. The additively manufactured parts passed high-temperature sintering (1485 °C) under the pressure of 1.83 MPa with resulted density near to theoretical one - 14.1 to 14.2 g/cm<sup>3</sup>.

Another application of tungsten is as an alloying element in high-speed steels for working, cutting and forming metal components. As an alloying element, *W* has been used in nickel and cobalt-based superalloys for aircraft engines and turbine blades, because of their high-temperature strength, creep strength, high thermal fatigue resistance, good oxidation resistance and excellent hot corrosion resistance [49]. Another application is in light bulb filaments, electrodes, wires, a component of X-ray and cathode-ray tubes, heat and radiation shielding, heating elements in furnaces, etc., which accounts for about 10% of the *W* market [49].

Tungsten and its alloys can be processed by PBF AM techniques having high energy density beams [51,52]. For these alloys, the initial apparent powder density is crucial for the resulted final density of the manufactured components. That means that selection of a proper powder feedstock has a significant impact on the mechanical properties of the manufactured components and should be taken into account during the process parameter optimization.

### 2.3.2. Chromium and Cobalt alloys

Despite strategic importance and widespread use, chromium was not included in the CRM lists released in 2011 and 2017. The main chromium producers are South Africa (about two-fifths of the chromite ores and concentrates), together with Kazakhstan (produces one-third of *Cr*). India, Russia and Turkey are also substantial producers of *Cr*.

Significant chromium demand comes for the production of iron-based alloys. As one of the major alloying elements in stainless steel, *Cr* content range between a mass fraction of 10.5% and 30% [13]. Owing to its strong reactivity with oxygen, it provides the ability to passivate the surface by an adherent, insoluble, ultrathin layer that protects the underlying metal against attacks of the corrosive agents, mainly acids and/or chloride-containing environments. *Cr* is also responsible for surface self-healing in presence of oxygen [13].

Another widespread use of *Cr* is in surface coatings, such as conversion chromate coatings [53], hard chrome [54,55] and PVD *CrN*-containing coatings [56–59]. Such coatings are used to improve the resistance to high temperature, corrosion and wear of substrates. However, electroplated *Cr* and conversion chromate coatings present health issues and are banned in many applications, with some exceptions for military and aerospace ones. These coatings contain hexavalent *Cr*, which recognized to have carcinogenic effects.

In additive manufacturing, *Cr* is widely used in alloys such as *CoCrMo*. These alloys are of high demand for specific biomedical implant elements, where high fatigue and wear resistance are of high importance (e.g. knee joints) [60].

The main producer of cobalt worldwide is the Democratic Republic of Congo. Cobalt (*Co*) is a metal used in several commercial, industrial, and military applications [61]. *Co* is rarely used as a structural material in its pure form but rather is employed as an alloying element [61].

Stellite is one of the most popular examples of *Co*-based superalloys. Patented in 1907, originally developed to produce fine cutlery, the Stellite alloys have found widespread applications as tool material for cutting, high speed machining, etc. Cobalt-based super-alloys have higher melting points than nickel-based ones and retain their strength at high temperatures. They also show superior weldability, and better hot corrosion and

thermal fatigue resistance than nickel-based alloys, making them suitable for use in turbine blades for gas turbines and jet aircraft engines. Stellite can be additively manufactured using Direct Energy Deposition processes [62].

As it was mentioned above, *Co* is used in *WC-Co* cemented carbides that could be processed by BJP [50]. Around 12% of the consumed *Co* is for this application, where *Co* is used as the metal binder due to its excellent wetting, adhesion and mechanical properties. Also, *Co* is recognized to have genotoxic and cancerogenic activity.

### 2.3.3. Natural graphite and graphite –derived materials

Graphite is a carbon mineral, where atoms are arranged in layers with relatively weak bonds between them, which confer it high anisotropy in thermal and electrical transport and quite specific mechanical properties [63]. It is used in numerous applications ranging from electrical machines and vehicles, refractories, foundries, construction industry, lubricating agent etc. Natural graphite is mined in three different shapes: vein, flake and microcrystalline [64]. The bulk producer of graphite is China. Production of synthetic graphite is mainly concentrated in the US, EU and Japan, and the forecast indicates for synthetic graphite market an increasing trend, owing to an increase in demand from the steel and electric battery industry.

Additive Manufacturing using graphite- derived materials (GDM), such as carbon nanotubes, graphene, graphene oxide and reduced graphene oxide, is one of the perspectives, intensively developing modern trends [65–69]. It is experimentally shown that the addition of relatively small (up to 10 volume %) amount of carbon nanotubes and especially graphene can significantly improve the mechanical properties and abrasion resistance of metallic materials (e.g. [70–72]). The majority of the experiments were carried out using the blends of the main metallic material and fine GDM powders. In these cases, special complicated procedures such as dispersion-based/wet-mixing process were used to provide a uniform dispersion of GDM through the powder blend [68,73–75]. Unfortunately blending of the powders with so dissimilar apparent densities leads to the deterioration in GDM distribution uniformity after recycling. However, modern technologies already allow for the effective manufacturing of the GDM-coated powders well suitable for the powder-bed AM [76].

### 2.3.4. Titanium alloys

Commercial spherical *Ti* powder production methods include gas atomization (GA), plasma atomization (PA), and plasma rotating electrode process (PREP). The requirements of the particle size distribution (PSD) vary with applications, for example, 20–45  $\mu\text{m}$  for SLM, 10–45  $\mu\text{m}$  for cold spraying, and 45–175  $\mu\text{m}$  for EBM. Most applications require the oxygen content in *Ti* powder to be less than 0.15 wt.% [39]. *Ti-6Al-4V (Ti64)* is a widely used  $\alpha+\beta$  alloy known for its enhanced processability and high strength at moderate to high temperatures [77,78]. Aluminium stabilizes the  $\alpha$ -phase whereas vanadium stabilizes the  $\beta$ -phase. Due to the high cooling rates during PBF, the  $\beta$ -phase solidifies into primarily  $\alpha'$ -martensite microstructures. This leads to embrittlement and decreasing elongation of particles [79,80]. The martensitic phase has the same chemical composition as the  $\beta$ -phase but its crystalline structure is hexagonal pseudo-compact resulting in high residual stresses [81]. The  $\alpha$ -phase increases hardness and strength, though also leads to a more brittle sample, whereas the  $\beta$ -phase improves ductility whilst reducing hardness and tensile strength. So far, no comprehensive studies contains a full life cycle analysis of the titanium-based powders used for AM. However, certain conclusions can be drawn from the analysis carried out on the traditional industrially used *Ti* powders [82].

### 2.3.5. Zirconium, Niobium, Tantalum

The promising application of zirconium (*Zr*) is related to titanium-based alloys. Binary and ternary *Ti*-based alloys with zirconium, niobium and tantalum are regarded as the most promising substitution of the *Ti64* for biomedical applications [83], showing significantly better biocompatibility and having mechanical properties much closer to that of

the human bones [16,17,84–87]. Growing demand for the prosthesis and implants and the ability of additive manufacturing to functionalize them will determine the demand for *Zr* as an alloying element rather than an individual material.

*Zr* and *Zr* alloys are a promising new class of biomaterials. In the past, the main problem of using the powder metallurgy of *Zr* and *Zr*-alloys was the absence of adequate powder that is possible to use in AM. Patented solutions were not sufficient to introduce this manufacturing technique into the production of zirconium parts. There are many methods for producing *Zr* metal and *Zr* powder. The following ones are suitable for powder production: reduction of zirconium dioxide with *Ca*, *Al*, *Mg* or *C*; reduction of  $ZrCl_4$  with *Ca*, *Na*, *Mg* or *Al*; reduction of  $Na_5Zr_2F_{13}$ ,  $K_2ZrF_6$  with *Na*, *K*, *Al*; electrolysis of molten mixtures of  $K_2ZrF_6$  and electrolytes; and hydrogenation of zirconium sponge or zirconium lump [88]. However, the powders manufactured using these methods are often characterized by elongated shape grains and a high content of impurities. At present, most zirconium products are obtained by foundry methods. New technologies such as direct laser sintering and microwave sintering, used to manufacture high-quality components, require spherical powders with narrow particle size distribution as this affects the packing density and sintering mechanism [89]. *Zr*, especially in the state of powder, has a very strong activity and strong chemical affinity for oxygen, nitrogen and hydrogen, so it must be prepared, handled and processed in tightly controlled technological conditions such as high vacuum, and atmosphere of extra-pure inert gas [90]. Nevertheless, the progress of gas atomization methods already allows for the manufacturing of complex AM-grade powders such as highly biocompatible HEA *TiNbTaZrMo* ones [91,92]. The powders for manufacturing of components from pure *Zr* also should be chemically pure because the impurities such as *H*, *O*, *C*, *N*, *S* can cause brittleness. These impurities have a significant influence on metal properties such as tensile strength, hardness and ductility and increase surface tension during processing. New metal powder processes developed for zirconium synthesis (and the spheroidization) have been developed over the past few years. For example, The South African Nuclear Energy Corporation produces *Zr* powders for the nuclear industry via a plasma process [93].

### 2.3.6. Steels and iron-based alloys

Some steels and cast iron alloying elements (Chromium, Niobium, Tungsten, and Hafnium) are CRMs or near CRMs. Thus, iron-based pre-alloyed powders for AM are also the focus of the present paper. Such powders are typically fabricated using advanced powder fabrication techniques such as EIGA (Electrode Induction Melting Gas Atomization), VIGA (Vacuum Induction Melting Inert Gas Atomization), or plasma atomisation. Corresponding powders are high purity ones and have spherical shape grains. In the EIGA process, the metal is melted from an induction-heated rod, from which the liquid metal drops into the atomization nozzle without any contact with the surrounding walls. In the VIGA method, the materials are melted using electromagnetic induction, which delivers heating power into the crucible/material under vacuum or in the inert gas atmosphere without contact with any potentially contaminating material. Once the desired melt homogeneity and chemical composition are achieved, the material is poured into a tundish by crucible tilting. A high-pressure, inert-gas jet atomizes the metal stream flowing from the tundish orifice into the atomization nozzle system. The combination of molten metal and gas jet creates a spray of micro-droplets which solidifies in the atomization tower and form fine powder with spherical grains [94]. Not all AM techniques are suitable for processing iron-based materials. Specific solidification conditions, including thermal gradients in and around melt pool, and different solidification rates characteristic to AM processes result in different material microstructure. This leads to the differences in phase composition (austenite or martensitic), grain dimension and alignment, and carbide precipitation in the grain boundaries of the additively manufactured steels and high carbon content alloys, as compared to the materials processed by traditional methods. Neverthe-

less, proper optimisation of the AM processing parameters can lead to materials with superior microstructure and better mechanical properties as compared to traditional manufacturing of the same constituent materials (e.g. [95–98]).

Iron-based powder grains are typically covered with a relatively homogeneous oxide layer formed by the main element (iron oxide in case of stainless or tool steels). The thickness of the oxide layer is between 1 and 4 nm, depending on alloy composition, powder manufacturing method and powder handling. The rare presence of the particulate oxide features with size up to 20 nm, rich in oxygen-sensitive elements, was also observed [99]. In many cases presence of a thin oxide layer does not impact the quality of manufactured components, but successive powder recycling, especially in presence of air humidity, it can limit the effective lifetime of the iron-based powders. Mechanical properties and performance of additively-manufactured components can also be improved by post-manufacture heat-treatment [96,100]. Other classes of iron-based alloys leading to the amorphous materials that have the potential of reducing CRM consumption are discussed in a separate paragraph related to the upcoming trends.

### 2.3.7. Aluminium alloys


Although Aluminum does not belong to critical raw materials currently, a part of alloying elements forming a high number of important aluminum alloys, namely silicon, magnesium, and scandium, are listed as CRM. Moreover, *Al* is of high economic importance and even though it so far has low supply risks, it deserves consideration, already being listed as CRM by the US authorities and as a potential CRM for EU in near future. At present, gas atomization (GA) is the main commercial production method for aluminium and its alloy powders [101,102]. Due to high affinity of aluminium to oxygen, caution should be taken in preventing any possible ignition of the powder or explosion of fine powder fraction suspended in the air. Atomization in air leads to immediate partial oxidation of the liquid material and prevents the liquid metal from transforming into a spherical shape making the powder unsuitable for additive manufacturing processes. The GA technology for aluminium is a dangerous process and special safety measures are required, which considerably raises the manufacturing costs [103]. The high thermal conductivity of aluminium and its alloys makes them difficult to cast and weld. For Powder bed AM technologies, things get worse: aluminium powders are inherently light and have a poor flow ability during recoating. They are also highly reflective making problems for laser-based AM and have a high thermal conductivity when compared to other materials [104]. Nevertheless, continuing research on the PBF-AM of *Al* is going forward. It is shown that microstructure of *Al-Si* (*AlSi7Mg*, *AlSi10Mg*) parts produced by laser methods are characterized by finer grain size in the microstructure as compared to that of cast or wrought parts.

### 2.4. Production of metal powders for Additive Manufacturing

Additive manufacturing has already successfully incorporated ceramic materials. According to the form of the precursor, these technologies can generally be divided into slurry-based, powder-based and bulk solid-based methods (laminated object manufacturing). The mechanical properties of resulting materials depend significantly on the degree of neck growth between grains, as well as porosity and pore size in the resulting material. Regardless of the specific method, additive manufacturing of ceramics mainly uses materials such as  $Al_2O_3$ ,  $ZrO_2$ ,  $SiO_2$ ,  $Y_2O_3$ ,  $TiC$ ,  $TiN$ ,  $TiB$ ,  $AlN$ ,  $SiC$ ,  $Si_3N_4$ ,  $WC$ ,  $Ti_3SiC_2$ ,  $CaCO_3$  and others. Out of the elements used in the mentioned ceramic materials only silicon, cobalt and tungsten are on the CRM list, with zirconium and aluminum expected to be on the CRM list in the near future. However, ceramic and ceramic-containing materials have potential in substituting some of the CRM-dependent ones and thus deserve corresponding analysis.

In solid-phase reaction synthesis of ceramic powders, there are three types of chemical reactions: oxidation or reduction of a solid, thermal decomposition of a solid, and

solid-state reaction between two types of solid. With liquid phase synthesis of ceramic powders, there are five different methods: drying of a liquid, precipitation, sol-gel synthesis, hydrothermal synthesis, and reactions of a liquid metal melt with gas to give a solid ceramic. There are three operational principles for precipitation: temperature change, evaporation, and chemical reaction. These methods are generally broken into three categories: solid phase reactant, liquid phase reactant, gas phase reactant synthesis and the later is essentially a precipitation method; however, the solid precipitated is of nanometer size and can be organized into a gel network or sol particle depending on conditions. Hydrothermal synthesis methods use high pressure to make a specific solid phase insoluble. Gas phase ceramic powder synthesis methods include evaporation-condensation and chemical reactions in the gas phase. These gas phase reactions include thermal decomposition, oxidation or, reduction, as well as chemical combination reactions [105]. The most common is the use of AM for  $Al_2O_3$  and  $ZrO_2$  [106]. It is known that when using free sintering or pressure sintering methods, the highest relative density values and thus the best mechanical properties are obtained for very fine powders, preferably sub-micrometer ones (Fig. 5a). Commercial powders are available usually in the form of weak agglomerates or granules prepared from very fine powders (Fig.5.b). Isometric shape particles and granules of ceramic powders are preferred, in free and pressure sintering processes because of the better formation and consolidation of the grains. Many multicomponent nano-sized ceramic powders have been prepared using an aqueous sol-gel method.

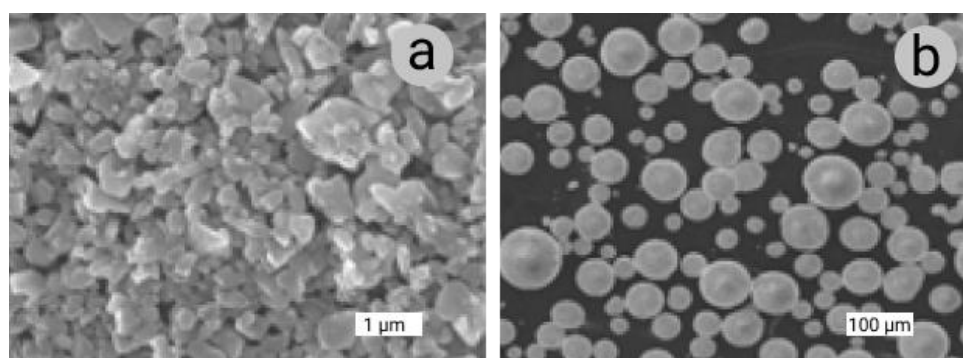

**Figure 5.** Morphology of powders: a –  $Al_2O_3$  submicron powders, mean particles size  $0.7 \mu m$ , prod. Alcoa A16SG, specific surface area  $8.9 m^2/g$ , shape factor  $\beta=1.42$ ; b -  $ZrO_2$  granules TZ-3Y, partially-stabilized zirconia powder with a uniform dispersion of 3 mol % yttria, 40 nm, prod. Tosoh Corporation.

In industrial production, the granulation methods of ceramic powders mainly include dry roller granulation, cold isostatic pressing and spray granulation. In the case of free and pressure sintering, small amounts of additives, e.g.  $MgO$  to  $Al_2O_3$ ,  $Y_2O_3$  to  $ZrO_2$  or carbon for  $SiC$  sintering are introduced into the powders. These additives limit grain growth, stabilize selected phases that we want to keep or improve the stoichiometry of the product and facilitate sintering by lowering the sintering temperature.

A large part of the research conducted in the field of ceramics - AM is based on powders with a larger size of 40-100 microns. These powders are characterized by lower relative density, and this determines the lower strength of the sintered contacts (necks) after sintering (using AM methods), which is the basic problem of using ceramics indirect AM manufacturing. For this reason, in order to increase the density of AM ceramic products, finer size powder is fed to the process of granulation or functionalization of their surface in order to improve the flow ability and sintering performance of these powders. High values of particle spheroidization and fractional composition homogeneity are achieved after plasma treatment. A comparative study of thermal barrier coatings based on yttria-

stabilized zirconium oxide powder demonstrated that deposited coating thickness, powder dispersion degree and material efficiency of plasma spheroidized powder is comparable to a high-quality commercial powder [107].

### 2.5. Ceramic powders for direct additive manufacturing

The direct additive manufacturing of ceramic components is still at an early phase of development, although it was attempted by Lakshminarayan et al. [108] in 90s. For some AM processes to produce ceramic parts, cracks are still the most critical flaws that compromise the mechanical strength. During single-step processes, i.e. direct energy deposition and single step PBF processes, thermal cracks are generally caused by thermal shocks introduced by the laser-beam heating [109]. The direct AM process is very challenging due to the ceramic material properties, such as high melting temperature, high melt viscosity and poor thermal shock resistance. Sources like a focused laser, electron and infrared beams are used as a heating-sintering tool. The process of heating allows the powder to take the shape of the intended object. This greatly improves the productivity of additively manufactured ceramic components because the time-intensive debinding and sintering phases characteristic of indirect methods are not necessary. The use of granulate composed of micrometric yttria-stabilized zirconia with sub-micrometric alumina improved the homogeneity of the microstructure. Thermal post-processing in some cases can improve the mechanical properties of the resulting material. For example, it allows the amorphous alumina in corresponding ceramic parts to crystallize [110]. An important phenomenon that should be taken into account during ceramic powder consolidation by direct AM methods is the formation of the glassy phase, which can affect the fragility of products.

### 2.6. Ceramic powders for additive manufacturing of MCC

One of the promising application of ceramic powders in AM is using them together with metallic ones for producing metal-ceramic composites (MCCs) in AM processes initially developed entirely for metal precursors. Experiments carried out using different AM technologies [111–114] indicate that this method allows improving mechanical properties and abrasion resistance of the basic alloys. Experiments were carried out both using powder blends in which ceramics phase was a very fine powder, and using different technologies providing agglomerated grains containing both ceramic and metal powders (e.g. [115]). Different mechanisms responsible for the property improvement were suggested, including the ability of sub-micrometre ceramic inclusions to act as dislocation traps. The resulting microstructure strongly depends on the melting temperature of the ceramic and the temperatures reached in the melting pool, and on the wettability of the ceramics in the molten metallic material. At current stages of research, it is not possible to forecast which combination of materials in MCC-AM will be successful in producing materials with superior properties. However, definitely, this line of development has potential in relation to sparing CRM in industrial applications.

### 2.7. Ceramic powders for slurry based methods

Slurry-based ceramic 3D printing technologies generally involve fine ceramic particles dispersed in liquid or binder, in the form of relatively low viscosity inks or viscous pastes. The slurry content can be additively manufactured by either photopolymerisation, inkjet printing or extrusion [116]. All slurry methods are commonly multi-step ones, initially producing the non-dense semi-finished parts that are commonly called “green bodies”, followed by de-binding and firing processes yielding final components.

Binder jetting is an additive manufacturing process in which a liquid bonding agent is selectively deposited to join powder materials [117]. Currently, the density of the ceramic parts made by binder jetting is rather low and their mechanical properties are far

from adequate. The main reason comes from the low sinterability of current powder feed-stock due to large particle size (10–100 $\mu\text{m}$ ) and the inability to deposit a smooth layer of the precursor. The coarse powder exhibits good flow ability, and the fine powder that can provide better sintering has poor flow ability [118]. Many studies have reported that the quality of parts using binder jetting is significantly different when coarse powders are used. Studies have shown that the accuracy and strength of ceramic parts are closely related to powder and binder choice, printing parameters, equipment, and post-treatment. Studies have focused on the optimization of binder jetting employing multimodal filler particles for improving the strength and performance of binder-jetted parts [119]. One of the solutions to improve the compaction of the material is the use of nano-powders. Smaller particles as densifiers occupy the inter-granular pores in the powder and improve the density of green printed parts but the applied nano-suspension can quickly clog the jetting nozzles [120]. The shape of ceramic powders mainly affects the flow ability of slurry, the tap density, the powder bed (packing) density, the pore structure of the green body, and the contact mode between the particles. Generally speaking, spherical particles have better flow ability in the slurry and higher tap densities than irregular ones. However, during the printing process, the powders will be spread by the roller, which means that the powders will not be compacted; thus, the contribution of spherical morphology to packing density will be reduced. In contrast, irregular powders have a relatively high packing density [121]. Suwanprateeb et al. [122] reported that irregular hydroxyapatite has a higher packing density than spherical shapes powder. This is because the spherical particles undergo a low uniaxial pressure, and their good flow ability causes the particles to roll towards each other. Although the particles are re-arranged and slipped, they are still in point contact and, thus, cannot effectively reduce the pore volume. For irregular particles, after being re-arranged and slipped, the larger internal friction causes them to combine and become compact, while the point contact between some of the particles becomes surface contact, which can effectively reduce the pore volume. Therefore, the irregular powders will result in a higher green density than the spherically shaped ones. The green body density is usually positively correlated with green strength. This higher green strength improves the handling characteristic of the as-fabricated green body. The original morphology of as-purchased hydroxyapatite powders prior to preparation commonly exhibit agglomerates of needle-like crystals [122].

A new powder surface modification method, i.e., particle coating, sol-gel process was used to synthesize the amorphous phase material and applied to increase the powder sinterability and the part strength. Specifically, coarse crystalline alumina particles (70 and 10  $\mu\text{m}$  on average) were coated with amorphous alumina, in which the micro-sized core was designed to provide the high flow ability and the amorphous shell to promote sintering due to its high activity [123]. The coarse crystalline core can help to maintain the high flow ability and the amorphous shell can promote sintering due to its high activity [123].

### 2.8. Ceramic powders for porous bone implants

While research on ceramic scaffolds for bone regeneration has progressed rapidly, the clinical outcome of these synthetic bone implants remains limited, especially for major load-bearing applications. Not only should these scaffolds provide adequate mechanical support, but also possess sufficient porosity to facilitate nutrient/metabolite transportation and bone tissue ingrowth [124]. At the same time, ceramic implant-scaffolds have a great potential of substituting metallic ones due to their advanced biocompatibility, reducing the dependence on certain CRMs traditionally used in metallic implants in future orthopaedics.

One of the additive manufacturing techniques, direct ink writing (DIW), also known as robocasting, has attracted considerable attention in bone tissue engineering. In the robocasting fabrication method, a filament or ink is extruded through a nozzle in a layer-wise fashion and ultimately forms a 3-D mesh structure with interpenetrating struts. After

the initial layer is created, the X-Y stage is incremented in the Z-direction and another layer is deposited. This process is repeated until the desired scaffold structure is created. While robocasting can fabricate regular and controllable patterns in the X-Y plane, its ability to maintain high precision with sophisticated structures in the Z direction is restricted due to depositing ceramic struts on top of one another [125]. This technique has been used to fabricate scaffolds with a wide variety of ceramic materials such as bioactive glass [126], hydroxyapatite (HA), calcium phosphates [127], calcium silicate (CSi) and Sr-HT Gahnite [128], as well as other composite materials, exhibiting significant potentials. Polylactide or polycaprolactone scaffolds with pore sizes ranging between 200-500  $\mu\text{m}$  and hydroxyapatite contents up to 70 wt. % , and scaffolds containing bioactive glasses were also 3D-printed [129,130].

Ceramic scaffolds and implants for osteogenesis are based mainly on hydroxyapatite since this is the inorganic component of bone. The usual fabrication technique for ceramic implants is the sintering of the ceramic powder at high temperatures.

Porosity control in ceramic additive manufacturing is quite challenging. One should separate what is the scaffold porosity, and what is a material porosity. Scaffold porosity mainly relates to the ratio of the solid material and free space in the manufactured scaffold or “porous” implant section. This property is strongly related to the part design and ability of the material and chosen AM method to produce the part without deflecting from the designed shape. As a thumb rule, it is very hard to design holes in AM structures smaller than five times the average size of the powder grains. Pores (micro-pores) in resulting solid materials (e.g., struts in the porous-by-design lattice scaffolds) are mainly related to the material, AM technology, and process parameters. These micro-pores commonly have different shapes and sizes, and their distribution is not uniform. The micro-pore morphology can be partly influenced by controlling the size distribution and morphology of the precursor powder. The porosity of materials can also be controlled by an appropriate selection of sintering conditions (time, temperature, pressure, atmosphere) [131,132]. For example, hydroxyapatite samples additively manufactured from milled powders are significantly stronger than samples manufactured from spray-dried powders. This is a combination of the specifics of the manufacturing and the difference in morphology of the prepared powders. In the case of milled powders, these factors induce better packing and rearrangement in the green state and improve densification and pore characteristics in the sintered state. Although the spray drying technique of powder preparation is more convenient and faster, the grinding route is preferable when the greater strength of fabricated components is considered [122]. Another ceramic material for bone implants is bioglass (materials with different compositions of  $\text{SiO}_2$ ,  $\text{CaO}$ ,  $\text{Na}_2\text{O}$ , and  $\text{P}_2\text{O}_5$ ) [133].

### 2.9. Powder handling safety issues

Safety precautions in handling CRM-containing powders used in AM are always mandatory. Many of the CRM- containing materials are listed as “dangerous” in quite different ways, so studying the safety precautions and safety data sheets related to the involved chemical elements and materials are advised. Handling with care is always advised, avoiding spillage and anything promoting contaminating the air with fine material powders. Fine particles can cause severe dysfunctions, skin problems, lung diseases, cancer when exposed to or directly inhaled. Some of the metals in prolonged exposures were linked to the onset of Alzheimer’s disease [134]. Special powder-safe respirators should be used to prevent small particles from reaching the bronchus and lungs, powder-free gloves should protect the hands.

In addition to potential health risks, metal powders are combustible, flammable, and when aerated present a risk for explosion. Facilities, where metallic powders are kept or handled, should have proper protection from electrostatic and electrical sparks (including



non-static flooring, special clothing and shoes for the staff, grounding wires, special vacuum cleaners- as the majority of domestic ones have spark-producing electric motors, etc.). Also, only specialised fire extinguishers rated for combusting metals should be used in such facilities.

At the same time, with correctly deployed preventive measures and proper handling protocol implementation in corresponding AM facilities no higher levels of danger than many common industrial facilities are found.

### 3. Additive Manufacturing processes

The main consolidation mechanism of AM technologies are partial melting, full melting and solid-state sintering, which might act together, and it is not always obvious what consolidation mechanism is dominating [135].

The role of additive manufacturing is going to increase with the world entering the fourth industrial revolution. Following key advantages of the AM methods will define their fundamental role in future manufacturing. Additive manufacturing is capable of extremely high flexibility in producing small and medium series of complex parts, complemented by seamless switching to the manufacturing of the parts with a completely different design. Manufacturing capacity with the AM methods is highly scalable, which would be beneficial to both industrial giants and SMEs. AM methods allows not only to achieve a higher flexibility to achieve any desirable shape but also for the cost- and time- effective functionalization and individualization of the parts. The digital nature of the design for AM allows for reducing cost and time for component modification which reduces the need for inventory as they can be manufactured on demand using the library of digital files. With the development of the 'service points' for additive manufacturing across the world, there is a potential for a significant reduction of the transportation costs for the raw materials and especially- manufactured components. Recycling of the precursor powders can be almost completely performed at the manufacturing sites. The high degree of recyclability of the powders along with other aspects of material and energy saving allows for significantly decreasing environmental impacts of industrial production. Along with the possibility of reducing the amounts of CRMs per component, and with newly developed materials- with the ability to avoid using them, additive manufacturing will be a major contributing factor in solving the CRMs problem and reaching the goals set by EU Commission.

#### 3.1. Industrial Additive Manufacturing for CRM-containing materials

Perez et al. [136] presented the general AM standards related to terminology, data formats, design rules, qualification guidance and generally outlined different additive manufacturing technologies. A comprehensive overview of AM processes and standards with emphasis on materials, processing and testing methods is given by Riipinen et al. [137]. The well-established additive manufacturing processes are classified according to ISO/ASTM 52900-2017 into single step and multi-step AM processes [117]. These are further divided into processes where AM is done as a fusion of similar materials, or as adhesion of dissimilar materials. In both groups, processes are divided according to used material classes into metallic, polymer, ceramics, and composites, while also secondary processing such as sintering and infiltration is mentioned. Figure 6 presents the most mature and widely used AM processes such as Vat Photo Polymerisation (VPP), Binder Jetting (BJ), Powder Bed Fusion (PBF), Material Jetting (MJ), Direct Energy Deposition (DED), Sheet Lamination (SL), and Material Extrusion (ME), together with materials that can be used in a particular process. A more complete interactive map of additive manufacturing processes, which also includes materials as cement, hydrogels and bioinks, with a directory of more than 800 companies manufacturing AM hardware can be accessed at [3dprintingmedia.net](http://3dprintingmedia.net) [138].

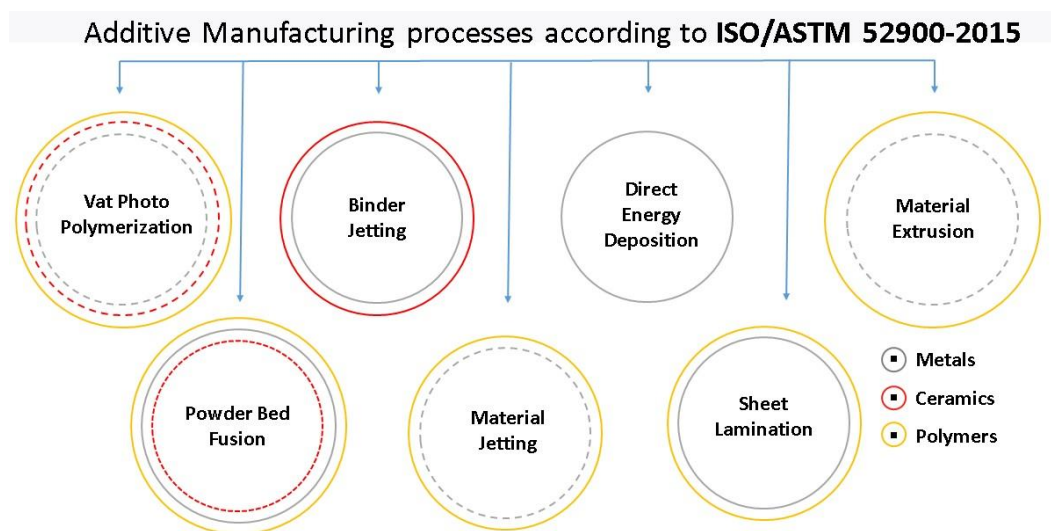


Figure 6. Additive manufacturing processes as defined in [139]

Today, the most promising AM technologies from the CRM point of view are Powder Bed Fusion, PBF, and Direct Energy Deposition, DED, which are also the most widely used in the industry. These are followed by Binder Jetting and Material Extrusion (ME) [140,141]. The less industrially known AM technologies, which uses ultrasonic, friction and friction stir welding, together with thermal spraying (e.g. cold spraying) also present high potential [142–144]. Their main advantages compared to PBF and DED are in the possibilities to join dissimilar materials, some better energy efficiency and smaller heat input, a protective chamber or atmosphere is generally not needed, and the processes have a promising buy-to-fly ratio.

Within PBF-AM, one can distinguish SLM and EBM technologies. Both of them uses powder precursors, and the manufacturing is performed in a closed chamber in an inert atmosphere (SLM) or high vacuum (EBM). In both PBF-AM technologies selective melting of desired parts of layer of powder by intense beam, with a non-melted powder enabling partial support of manufactured components and acts as a heat insulator, makes the product. The process continues by adding and melting consecutive layers of powder.

Laser-based PBF-AM methods allow for industrial manufacturing of functional parts and tools with complex shapes from metals (stainless steels, tool steels, *Co-Cr* alloys, *Ni* based superalloys, *Ti* alloys, *Al* alloys) and ceramic powders. The component surfaces have excellent to moderate finish in an as-manufactured state, good functional properties, and can be micro- and nano-structured. The products are usually made from one material, which enables high recyclability of the powder. Powder preheating is done using infrared heaters or beams of lower intensity, and laser beam deflection is done using mirrors.

Electron beam melting generally enables working beams of higher intensity and higher (up to 60 cc/h) material deposition rate but is generally limited only to the electrically conductive powders. This defines the quite limited selection of materials available for industrial EBM manufacturing, including *Ti* (grades 1, 2, 23 and 5), nickel base alloys, aluminium alloys (*Al-Si*), stainless steel (*316L*, *M300*, *17-4 PH*) and *CoCrMo* [44]. It also enables the production of functional parts of complex geometry, but its resolution is lower and surface roughness of components is higher than that provided by the laser-based methods due to the larger average grain sizes of precursor powders. The process is carried out in a deep vacuum, which enables close to 95 % energy-efficiency, which is 5-10 times higher than that for laser-based PBF. The vacuum is also perfect for processing reactive metals like *Ti* and *Al*, maintaining the chemical composition, and reducing the heat loss to the environment. The additional advantage is due to the powder bed preheating. Being

793

794

795

796

797

798

799

800

801

802

803

804

805

806

807

808

809

810

811

812

813

814

815

816

817

818

819

820

821

822

823

824

825

826

827

828

an essential prerequisite for the conductive powder melting (partially sintering it and preventing forming clouds of charged particles in the working chamber), it efficiently removes moisture and gases adsorbed on the powder surfaces. EBM- manufactured parts also exhibit significantly lower internal stress, as the process is carried out at elevated temperatures, continuously annealing the produced material.

Corresponding disadvantages of the electron beam PBF as compared to the laser-based ones are smaller available working volumes (and thus maximum component dimensions), complications of the semi- sintered powder recovery from holes and crevices, higher surface roughness of components in as manufactured state, and longer times for reloading the machines. Additionally, laser-based AM technologies are already strongly incorporated into the Hybrid Manufacturing chains using precise machining after AM, and can provide higher technology readiness levels of as-manufactured parts. At the same time, it should be noted that both laser- and electron beam-based PBF AM technologies are continuously developing and are slowly overcoming their current limitations.

SLM, another PBF-AM representative, enables the production of complex parts with high technology readiness levels (TLR) for aerospace (TLR 5-7), tooling (TLR 9), automotive (TLR 4-5), and medical industries (TLR 9-10). Typical products for the aerospace industry are fuel injection components, structural elements and turbine blades. In the tooling industry, inserts are made, usually with complex internal cooling channels that enable efficient cooling/heating and prolongation of tool life. In the automotive industry, different structural and functional components are successfully manufactured in low series. In the medical industry medical instruments, artificial hip joints, different implants for reconstructive surgery, crowns and copings in dentistry, are produced [141,142,145–148].

Another powder- using AM technology, DED, is less widespread for metal AM as compared to PBF ones due to lower accuracy and requirement of post-processing. However, it enables higher deposition rates, production of bigger parts without limitation to small chamber size, component reparations, and production of functionally graded materials, as well as multi-materials components. Corresponding equipment includes a feeding “nozzle” mounted on a multi-axis arm or robotic system with an external rotating table and protecting chamber in case of manufacturing using reactive metals. The material in powder or wire form is supplied through the nozzle and is melted by the electron or laser beam together with the surface of the product. The wire is a cheaper precursor material, it enables higher deposition rates but such systems have lower accuracy compared to powder-based ones. Materials in powder form are more expensive, and the atomization process of powder production is less energy efficient (11-59 %). In contrast to wire-based systems, powder ones can return into processing from 20 to 90-98 % of precursor directly or after sifting [136, 143–146]. However, the wire is cheaper, more widely available in larger quantities, and demands less stringent safety precautions in handling concerning metal powder. Wire with its much lower surface to volume ratio is less prone to absorbing moisture, nitrogen and oxygen and other undesired elements from the atmosphere, and thus it affects the deposition process much less and provides materials with lower numbers of residual pores, as compared to powder-based technologies. An interesting new technology that will soon be industrially available is the so-called “Joule Printing”. It is quite similar to wire-based DED AM technology but uses resistive heating (as in the welding process) instead of electron or laser beams. Its advantages are lower energy consumption and low heat input (1.4 -1.6 Wh/cc), which only turns the precursor material up to a mushy state avoiding the formation of the melt pool. The process enables producing near-net-shape structures with high deposition speed (1000 cc/hr), which is 2-10 times faster than DED-Powder, and similar rate to DED-ARC, while the resolution is compared to DED-Powder [153]. Manufacturing can be done in demanding environments, with high material efficiency, using commercially available welding wires, while the output material properties are close to wrought/cast metal ones [153].

In general, DED enables the production of less complex parts as compared to PBF. DED parts usually need post-processing (e.g. heat treatment), mechanical treatment and machining to obtain the desired shape and mechanical properties. DED is typically used for repair of worn components, modification of tooling for re-use, for rapid prototyping of bigger parts and direct manufacturing of large components. DED processes are generally classified as Electron Beam Additive Manufacturing (EBAM), Laser metal deposition (LMD wire/powder) and Wire and Arc Additive Manufacturing (WAAM) [145,153–157].

EBAM uses precursor material in the wire form. It produces bigger near-net-shaped parts of the highest quality inside the vacuum chamber. Parts are made with high deposition rates ranging from 3 to 11 kg/h. In the process, a variety of materials can be used: titanium and titanium alloys, Inconel, nickel alloys, stainless steel, aluminium alloys, cobalt alloys, zircalloy, tantalum, tungsten, niobium, and molybdenum [158]. During the EBAM and post-machining overall high material efficiency is achieved [157].

LMD uses the material in a wire or powder form, which is fed through the nozzle. The fabrication can be done in a local protective atmosphere or an inert gas chamber. Deposition layer thickness varies between 0.1 mm and ~ 3 mm, deepening if a high-resolution printing or fast manufacturing rate is targeted. Deposition rates for wire LMD are much higher than for SLM or powder- LMD. A vast variety of different materials and alloys can be used for processing. Good metallurgical bonding with a low dilution level can be achieved with low impact on base material properties [157].

WAAM uses an electrical arc from power sources typical for welding like Gas Metal Arc (GMA), Tungsten Inert Gas (TIG), Plasma (PL) or their combination together with the precursor material in a wire form. The process achieves high deposition rates from 1 to 10 kg/h, with moderate surface finish and low to medium part complexities. Major benefits are lower equipment and precursor material cost, a big variety of precursor materials and high material efficiency [155,156]. This makes the process extremely well suited for the manufacturing of large parts with up to medium complexity, at a much lower price compared to other AM processes. The main drawback is potentially higher residual stresses, distortions and coarse grain microstructure as the consequence of higher temperature gradients. Additional post-processing with mechanical treatment, heat treatment and/or machining may be needed to obtain industry- acceptable products [95,96,145,154–156,159–161].

Table 1 presents a comparison for most common PBF and DED additive manufacturing processes in terms of processing conditions, component complexity and qualities, deposition rates and capability of multi-material processing. Inability of multi-material processing stated for SLM and EBM is related to the industrial-grade processing, although experimental confirmations for its feasibility are already demonstrated experimentally.

**Table 1:** Comparison of most common metal PBF and DED additive manufacturing processes [95,137,145,153,155,157–159,161–170].

	PBF			DED		
	SLM	EBM	LMD - powder	LMD - wire	EBAM - wire	WAAM
Type of atmosphere	Inert (Ar, N)	Vacuum	Inert	Inert	Vacuum	Inert
Relative part density	≥ 99,5		≥ 98	≥ 98		≥ 98
Typical layer thickness [μm]	10-100	50-200	10 - 100 (250 - 1000)	130 – 1000	3000	3000
Part complexity	almost unlimited	some limited	limited	Limited	limited	limited
Minimal wall thickness [mm]	≥ 0.1 mm	≥ 0.x mm	≥ 1 mm	≥ 1.5 mm	≥ 1.5 mm	≥ 1.5 mm

	PBF			DED		
	SLM	EBM	LMD - powder	LMD - wire	EBAM - wire	WAAM
Surface roughness Ra [ $\mu\text{m}$ ]	5 - 15	~ 20	2-91	10 - 91	20	20 - 100
Deposition rate [ $\text{cm}^3/\text{h}$ ]	10-25 (100 for multi-laser)	3 - 11 kg/h	< 70	100 - 200 (<500);	100 - 200 (<500)	100 - 200 (<500); 1 - 10 kg/h
Multi-material	no*	no*	possible	possible	possible	possible
Process energy density [ $\text{Wh}/\text{cm}^3$ ]			17.4	9.2	36	4.9
Energy efficiency [%]	10-20	95		2-5	15-20	< 90

### 3.2. Recycling of metal powders for Additive Manufacturing

Powder recyclability is a crucial parameter of powder lifecycle and overall manufacturing efficiency. In metal-based processes (PBF, LENS) the microstructure of the virgin (not recycled) powder has a certain tendency to change due to repetitive re-use and recycling [14,171,172]. The flow ability and powder morphology can change because of thermal cycling during processing and mechanical impacts during layer deposition, powder recovery and sifting. Increased temperatures of the powder in the AM process can force surfaces of powder to react with ambient atmospheric gases or their residual content in the protection volume. An increase of oxygen content in the powder often results in reducing the mechanical performance of the printed metal parts [14,171]. Most often, powders are passed through a sieve before being used again. That may cause particle deformation and breakage of the grains that formed joining necks. Recycled powders show a minor decrease in the amount of fine ( $< 10 \mu\text{m}$ ) particles, a slight increase in average particle diameter, and a slightly wider grain size distribution [14,173,174]. Sieving also can remove some of the satellites, leading in some cases to better flow ability of the recycled powders.

Additional contamination, either through impurities coming from the sieves and vessels, foreign bodies or interstitial elements may be introduced to the powder as a result of handling during pre-processing or post-processing stages [26]. It is clear that the amount of powder belonging to each separate virgin batch is constantly decreasing as part of it forms solid components. At some point, the volume of the powder becomes lower than the minimum demanded by the AM machine. Three strategies are commonly used: topping up the reused powder with virgin one, saving small batches of recycled powders and mixing them for further manufacturing, using recycled powder from virgin batch without topping or mixing at all. The third option is preferable for manufacturing parts destined for critical applications. However, there is no consensus on which of the first two options should be preferred and in which cases. Nevertheless, it is agreed that each recycled powder should have its “passport” stating the date of virgin batch purchase and its initial elemental content, history of the builds using it, number of recycling procedures, and results of regular powder analysis. It is also clear that for increasing powder lifetime, the recycling process and storage conditions for the powder should be strictly regulated, including humidity and temperature control, and specialized ventilation with filtering of the incoming air control in the operating rooms.

An interesting approach to use beam-based technologies for material recycling is also starting to develop. Recently, some authors have investigated the feasibility of turning recycled powders that are not fit for further use due, for example, to some excessive agglomeration into metal bars [175]. Powder-bed machine manufactures thin-walled cylinders with the powder enclosed in them. This does not require high purity of the precursor and is not depending on the high spatial resolution. This is followed by HIP-treatment of

919

920

921

922

923

924

925

926

927

928

929

930

931

932

933

934

935

936

937

938

939

940

941

942

943

944

945

946

947

948

949

950

951

952

953

954

955

956

957

the cylinders resulting in solid metal bars. Studies have shown that it is quite realistic when using EBM, as the processing happens in a vacuum and powder inside the sealed cylinders does not have any encapsulated gases. This approach is inspired by the recycling pathway using laser or electron beam- based equipment with simplified control of the beam used just for melting scrap material into ingots [176–178], but has an advantage of essentially full recycling at the manufacturing site without any need of costly and hazardous transporting of powders to a specialized recycling site.

**4. Modern and future trends in Additive Manufacturing of CRM-based materials**

Table 2 outlines the modern status of additive manufacturing of CRM and CRM-containing materials. Further progress in solving CRM-related challenges belongs to the developing trends in AM and its deep integration with other processing modalities. Several AM-related possibilities to reduce and optimize the use of CRMs and CRM- based materials are discussed in this review:

- use of Hybrid Manufacturing [137,144,179],
- production of multi-material components [180,181],
- production of functionally graded materials (FGMs) [156,164,182,183]
- repairing and remanufacturing i.e. using additive manufacturing[141,184–187].

This review also provides a brief overview of laser-shock peening, as one of the potential industrial post- processing routes allowing for reducing residual stresses in additively manufactured components and increasing their value as CRM-reducing and CRM-sparing manufacturing routes.

**Table 2.** Applied AM technologies for CRM and CRM-containing materials

CRM	Material extrusion (FDM)	PBF	DED	Vat photo polymerization	Sheet Lamination	Binder Jetting	Main application
Ti - alloys		[188]	[189]			[190,191]	Aerospace & bio-medicine
Ni-alloys		[188,192,193]	[193,194]			[195,196]	Aerospace
Al-alloys	[197]	[98,198]	[165]		[199,200]		Aerospace
Cu-alloys	[197]	[201–203]		[204]		[205,206]	Electric-magnetic
Mg		[207,208]					Medical
W		[51,52,209]	[210]			[52]	Nuclear reactor
RE-based materials	[211,212]	[213,214]		[214]		[215]	Permanent magnets
Si / SiC / SiO2	[216]	[217]		[216]	[218]	[219]	Tooling, optics, medical
Au		[220,221]					Jewelry
Co-Cr alloys		[60,222,223]				[223]	Bio-medicine
Nb/Zr/Ta containing alloys		[224,225]	[89]				Bio-medicine
Graphite	[197]		-	[66]	-	[63,226]	Thermal

*4.1. Hybrid manufacturing technologies*

Hybrid manufacturing is commonly described as the combination of additive manufacturing and subtractive manufacturing in a single machine or a set of closely linked

machines in a single production line [227,228]. Manufacturing of the component in such a case could start from a billet or a plate, followed by pre-machining, manufacturing and post-machining stages, when one or more of these stages uses some AM technologies. Each of the stages most efficiently uses its best advantages, thus combining in final product high complexity, high precision and best surface finish. In hybrid manufacturing mode parts with precise complex geometry, multi-material components, parts with conformal cooling channels, multi-material-tools etc. can be produced with high efficiency and optimized use of precursor materials. Lightweight structures, turbine blades, different housings, structural elements and multi-material components for the aerospace and automotive industry can be manufactured by optimising the use of CRMs and increasing the buy-to-fly ratio [229]. Different medical tools, fixation elements and implants with patient-specific and functionally optimized geometries and elements for optimal tissue ingrowth, biocompatible and bacteria hostile surfaces and with suitable mechanical properties can be efficiently produced by AM, while their precision elements (threaded holes, sliding balls with mirror surface finish etc.) are effectively completed by traditional machining. Many of the post-processing stages such as additional machining, polishing, heat treatment and surface modifications that today are separated from AM technology can be included in the hybrid manufacturing systems.

Reduced consumption of CRMs can also be obtained using repair welding and repair additive manufacturing of worn out or damaged products, so the need for new parts is significantly reduced [230,231]. This option is increasingly utilized in the industrial tooling sector, where an improved repair welding (cladding) technology and proper selection of materials can lead to restoration of the tool several times. This approach not only reduces the use of CRMs but also saves other resources and reduces the waste and greenhouse gas footprint of the manufacturing.

#### 4.2. In-situ alloying

CRMs used in aerospace and biomedical industries are main constituents of composition wise and microstructurally complicated alloys with mechanical, physical and thermal properties adjusted to the service conditions of the critical components. Today pre-alloyed powders are the main precursor for additive manufacturing of CRM-containing materials. However, low availability and high cost of quality-produced atomized spherical pre-alloyed powders may be a vulnerable point in the production chain of the critical components. In addition, not all desired materials can be alloyed effectively in stationary conditions, further limiting the possibilities of additive manufacturing of CRM-containing materials. Despite numerous advantages of AM, it hampers the development of technology implementation as a preferential production route for CRM-containing components [95,232–236]. In-situ alloying of blended/elemental powders during AM process enables overcoming this obstacle [237].

**Titanium based alloys** belong to the most popular CRM-based ones used in aerospace, automotive and biomedical applications with the domination of precursor material in a form of pre-alloyed spherical powders [188,238]. Certain attempts to perform PBF-AM of the microstructurally complicated *Ti*-based materials via successful in-situ alloying of elemental powder blends were performed during the last years and reported in the literature.

Vrancken et al. [239] studied SLM in-situ alloying of *Ti64* and 10% *Mo* powders. Molybdenum powder with 5–10  $\mu\text{m}$  sized particles was used. SLM- produced alloy have a good combination of high strength (919 MPa), excellent ductility (20.1%) and low Young's modulus (73 GPa).

Dzogbewu et al. [240] reported SLM manufacturing of *Ti15Mo* alloy for biomedical applications using *Ti* and *Mo* elemental powders as raw materials. Various blend compositions and various scanning strategies were studied, and the obtained as-printed materials were characterized to optimize the process parameters. It was concluded that although

achieving the final product with good homogeneity remains a challenge, in-situ alloying involving beam-based AM like SLM has a high potential for developing new materials.

Yadroitsev et al. [241] reported on the trials to alloy *Ti15Mo* and *Ti64* with *Cu* and *Mo* introduced as elemental powders. The effect of the process parameters, i.e., energy input and scanning strategy were studied. The viability of the in-situ alloying assisted SLM as a production route has been confirmed.

Fischer et al. [242] investigated and reported the microstructure and mechanical properties of *Ti-26Nb* alloy synthesized by powder bed SLM form of a mixture of *Ti* and *Nb* elemental powders.

Surmeneva et al. [224] reported on the in-situ alloying of binary *Ti10at%Nb* by EBM of elemental powders. Despite quite unfavorable grain size distribution and shape of used *Nb* powder, it was possible to achieve test samples of reasonable quality. At the same time, the uneven distribution of *Nb* fraction through the material led to the local gradients in the *Ti-Nb* mixing ratios. Though unfavorable for industrial process, this allowed for studying the microstructure of EBM-processed *Ti-Nb* materials with different elemental content. It was concluded that for effective in-situ alloying and production of porosity-free *Ti-Nb* alloys further process parameter optimization, and agglomerated powders in adjusted mixing ratios are essential.

**Nickel and Iron based alloys** belong to high-performance structural materials, which are widely used in aggressive environments and at elevated temperatures. The urgent need for components having compositional and functional gradient combined with high geometrical complexity causes a growing interest in the implementation of AM manufacturing routes for these alloys [243].

Li et al. [243] studied and reported on in-situ alloying assisted SLM synthesis and characterisation of *Fe-Cr-Ni* alloy from pre-mixed blend of elemental metal powders. The authors investigated precursor materials (blending ratios and particle sizes) and manufacturing parameters (heat input and scanning strategy). Phase compositions and microstructural formation were thermodynamically calculated and predicted, and compared with the obtained experimental results. The corrosion resistance of the synthesized functionally graded material was examined, and the applicability of the in-situ assisted thermal AM-SLM route has been confirmed.

Li et al. [244,245] synthesized and investigated a novel heterogeneous material, alloying *Ti64* and *SS316* with multi-metallic fillers. The authors concluded that the studied material is promising for critical spacecraft components, which require lightweight, high strength-weight-ratio and corrosion resistance.

Shah et al. [246] synthesized an Inconel-stainless steel-based functionally graded material with strong corrosion resistance at high temperatures. This material should be used as a critical raw material in light-water reactors subjected to a large variety of high temperatures, pressures and stresses [247].

**High entropy alloys (HEA)** are a novel promising class of materials, in which the formation of a single-phase solid solution is thermodynamically preferable over the formation of intermetallic compounds [248]. Refractory metals containing HEAs are usually composed of body-centered cubic (BCC) solid solutions [249] and have a high potential to substitute presently used critical raw materials due to their high-temperature mechanical strength [249]. Sometimes, full or partial substitution of refractory elements like *W*, *Ta* and *Mo* by transition metals [250,251], or *Al* [252] is performed to decrease the specific weight of the alloy and to improve corrosion resistance. Although this substitution is useful for achieving the mentioned aims, it may result in a poor mixing of the raw constituents, which causes low homogeneity of the finally obtained material. Furthermore, since the conventional way to produce HEAs is a vacuum arc melting [253–256] the main problem arises due to the difference in melting points and vapor pressures of the alloying elements at high temperatures. Additionally, oxidation resistance of the alloying refractory elements required an extremely high operating vacuum, at which low-melting constituents



usually evaporate. The problems mentioned above bring PBF AM technologies into focus as the most promising manufacturing technology for this class of materials. However, some of them contain CRMs, but there is a high potential of an overall reduction of their use when HEA substitutes more conventionally manufactured CRM-containing materials with similar properties. Since the production of HEA-parts often requires complicated, expensive and low-available pre-alloyed precursor powders, in-situ alloying of pre-mixed elemental powder blends seems the most promising synthesizing way for these class of materials. In this regard, molecular dynamics simulation can be used as an efficient predictive tool to investigate the mechanical and deposition properties of HEA and other materials [257].

Bulk metallic glasses (BMGs) are a class of materials that can significantly benefit from in-situ alloying. As with HEAs, manufacturing of these materials should strongly benefit from the PBF-AM production route, as BMGs lose their most attractive properties, such as high corrosion resistance, very special elastic properties and hardness if heated above glass transition temperatures and subjected to slow cooling [18,19]. Thus, beam-based AM methods including PBF ones providing extreme melting and solidification rates are very promising BMG manufacturing options. Many of the BMG materials introduced for industrial applications contain CRMs [18,258,259]. However, the recent introduction of the BMG compositions without CRM content together with their in situ alloying manufacturing possibilities allow for CRM-sparing manufacturing of these materials [19,259–262].

Li [263] discussed the prospects of AM routes for the production of HEAs and BMG. SLM is one of the presented possible approaches for HEA fabrication. The author mentioned that SLM of powders blends could be used for HEAs synthesizing, including manufacturing of advanced composite alloys.

Ocelik et al. [264] synthesised three-layered coatings made of HEA by SLM from pre-mixed elemental powder. The authors found solidification conditions to be the most critical parameter for successful HEA processing, while high-power laser beam with regulated power density and speed is mentioned as a unique advantage of the used additive technology.

Haase et al. [265] reported on successful simulation and experiments made using SLM of HEA from the blend of elemental powders. The authors mentioned this approach as very attractive due to the ease of modifying target material composition. HEAs produced by this route demonstrated high strength and homogeneous composition. The authors noted the importance of proper adjustment of the laser beam power and scan strategy for obtaining high homogeneity of the final as-printed components.

Dobbelstein et al. [266] reported on direct metal deposition assisted synthesis of  $MoNbTaW$  refractory HEA. The applied experimental set-up permitted to perform in-situ alloying of the pre-mixed powder blend. The authors also discussed the effect of process parameters on final product oxidation and the formed microstructure and mechanical properties.

Joseph et al. [267] reported on a comparison of microstructure and mechanical properties of the direct laser fabricated (DLF) and arc-melted  $Al_xCoCrFeNi$  HEA. The process and the effect of the production parameters on phase formation, oxidation behavior and mechanical properties of the final product, are described in detail. The authors concluded that the DLF production route permits obtaining materials with the microstructure and properties similar to those obtained by conventional processing, i.e. arc melting.

Cui et al. [20] discussed a thermodynamic approach permitting to predict the stability of HEAs. Several examples for successful attempts of laser-based additive manufacturing of these multi-component alloys from blended elemental  $Al$ ,  $Co$ ,  $Cr$ ,  $Fe$ ,  $Ni$  and  $Cu$  powders are given.

Popov et al. [21] reported on a successful trial synthesizing  $Al_{0.5}CrMoNbTa_{0.5}$  high entropy alloy by EBM and comparing the test sample microstructure and homogeneity with

the one for material synthesized by a conventional arc melting route. Although the obtained product's microstructure should be more homogeneous, i.e., that the production process must be improved, the authors conclude about a principal possibility to synthesize HEAs by AM routes.

#### 4.3. 3D Laser Shock Peening

As mentioned, the SLM process is a very attractive technology for fabricating components with very complex spatial shapes, such as near-net-shape parts that are impossible or prohibitively complicated to produce through conventional production routes [268]. Indeed, optimization of the AM processing of such components resulted in achieving only slightly lower static mechanical properties than those obtained with conventional processes. However, as with other processes that include layer-by-layer crystallization and solidification, the generation of Tensile Residual Stresses (TRS) can be considered one of the major deficiencies of many AM methods. In such processes, external energy is supplied with high local density to the last processed layer, leading to the temperature gradients and anisotropic partial annealing of the processed components. Except for the case of EBM, where the build is kept at a strongly elevated temperature, it results in significant accumulation of TRS or even considerable component distortion [269]. A considerable effort was devoted to the reduction of TRSs in laser-based technologies, including in-situ heating (preheating or high-energy laser re-melting) or post-annealing. This strategy is successful to some degree and up to 70 % reduction of TRS with annealing was reported by Mercelis and Kruth [270]. The main drawback of these methods is that they cannot completely remove either tensile or compressive residual stresses (CRS). Alternative approaches were tested, and several options emerged: Shot Peening (SP), Laser Shock Peening (LSP) and 3D Laser Shock Peening (3D LSP) [269].

LSP, similar to SP, deforms the surface layer of the part, by the application of the shock wave induced by the localized plasma pressure on the component. To enhance this effect, water or solid (glass) confinement is used, together with a corresponding laser wavelength setup of 532 and 1064 nm, respectively. It was soon realised that LSP could be performed during the laser-based AM process itself. 3D LSP process, patented by the Laboratory of Thermomechanical Metallurgy (LMTM) [268] refers to the combination of the SLM process with LSP. LSP treatment is used after several completed layers so that CRS can be handled throughout the component. To achieve this, the LSP setup must be integrated into the SLM device [271]. Several publications proved the benefits of this approach, which can mainly improve the fatigue, wear and corrosion properties, as well as improve geometrical accuracy of parts fabricated by this hybrid manufacturing system, significantly increasing the service life of parts.

Bending fatigue properties of 316L produced by a combination of SLM and 3D LSP (hybrid SLM-LSP) were significantly higher than manufactured samples and conventionally produced in both machined and non-machined conditions [272]. It was shown that by employing 3D LSP fatigue life is increased more than 14 times compared to AM samples, and 57 times over that of conventionally produced material.

It was reported that LSP with solid confinement does increase the microhardness near the surface region, through the accelerated recrystallization kinetics upon heat treatment, which results in refined equiaxed grains [273].

Kalentic et al. [268] successfully applied the SLM-LSP process for Ti64 alloy bridge-like samples. It was shown that LSP has reduced the distortion angle by up to 75 % compared to as-built specimens. Furthermore, 3D LSP was used for nickel-based alloy produced by SLM [274]. A 95 % reduction of the number of cracks in this very crack-prone alloy wiring welding has been observed.

Thus, Laser Shock Peening's introduction is following a general trend of Hybrid Manufacturing, and the development of additive manufacturing technology integrating

AM with other important technologies not only into the same processing line but essentially into the same process.

## 5. Conclusions

Additive manufacturing (AM) technologies are becoming critical to manufacture and repair to achieve sustainable use of Critical Raw Materials, vital to the European Industries. The wider introduction of AM technologies in their present shape, their development and incorporation into the hybrid manufacturing production chain along with the development of smart recycling routes for the components using CRMs and CRM-containing alloys is one of the developing trends in sparing utilisation of critical materials. The key advantages of AM such as shape optimisation and possibilities of on-demand manufacturing present the nearest opportunities to the manufacturing industries. The additional opportunity presented by modern AM is in the development of newer compositions with unique properties reducing or even eliminating the use of CRMs. In this aspect, beam-based PBF AM seems to be the most promising technique since it generates unique conditions of fast-melting and solidification, beam energy manipulation possibilities for microstructure engineering, in-situ alloying, and possibilities of metal-metal and metal-ceramic composite manufacturing. Fast melting and solidification are capable of preserving the unique metastable microstructure of materials, which is not possible with traditional manufacturing methods. This opens wide possibilities for manufacturing materials with unique properties including high entropy alloys and bulk metallic glasses as well as new composite materials for aerospace and biomedical industries. Development of new alloys for AM, specifically targeting preservation of metastable microstructure already shows possibilities in reducing the consumption of CRMs. An additional benefit of varying beam energy application rates, not only layer from layer but within each layer, characteristic to beam-based AM, promises further possibilities for microstructural and property enhancement along all three dimensions, allowing for material savings.

The ecology friendliness and sustainable nature of AM technologies make further research and development in this area critical for further progress in the field of “material-oriented manufacturing” and “solid freeform fabrication”.

**Author Contributions:** V.P., M.L.G., and A.K. conceived the work. V.P. organized the work and focused on additive manufacturing review and recycling aspects; A.K., D.K. focused on advanced metal 3D printing techniques; A.K., A.K.-D. and B.O.P. focused on bulk metallic glasses and high entropy alloys; L.J. focused on powders methodology and ceramics processing techniques; V.P. A.K., S.B., D.K., S.G. and A.K.-D. focused on modern trends in additive manufacturing, B.O.P. made Figures 1, 2, and together with MLG contributed to the CRM issues review. Writing was performed by all the authors. Review and editing was performed by A.K. and S.G. All authors have read and agreed to the published version of the manuscript.

**Funding:** This research received no external funding.

**Data Availability Statement:** As this is a review paper, no new data was generated for this paper.

**Acknowledgments:** This article is based on work from COST Action 15102 “Solutions for Critical Raw Materials under Extreme Conditions” and COST INNOVATORS' GRANT IG15102 “Innovative and sustainable Technologies for reducing critical raw materials dependence for Cleaner transportation Applications”, supported by COST (European Cooperation in Science and Technology). All authors greatly acknowledge the financial support provided by the UKRI via Grants No. EP/L016567/1, EP/S013652/1, EP/S036180/1, EP/T001100/1 and EP/T024607/1, Royal Academy of Engineering via Grants No. IAPP18-19\295, TSP1332 and EXPP2021\1\277, EU Cost Action (CA15102, CA18125, CA18224 and CA16235) and Newton Fellowship award from the Royal Society (NIF\R1\191571). SG is particularly thankful to European Regional Development Funds (ERDF) sponsored A2i project at LSBU that have catalysed several industrial partnerships. This work was supported by the Ministry of Higher Education, Science and Technology of the Republic of Slovenia, research program P2-0270. Part of this work was supported by EU Regional Development Fund through the Interreg Sweden-Norway program, a grant from the Rolf and Gunilla Enströms Trust

and a grant Nr 20202610 from Swedish Agency for Economic and Regional Growth. BP acknowledges that part of the contributions for this research was funded and supported by the Ukrainian state budget via research project number 0120U100475.

**Conflicts of Interest:** The authors declare that they have no conflict of interests.

## References

- [1] European Commission, Methodology for establishing the EU list of critical raw materials, Brussels, 2017. <https://doi.org/10.2873/769526>.
- [2] General Secretariat of the EU Council, Outcome of proceedings of the Council (Competitiveness) 21-22 May 2007 - Industrial Policy, 2007.
- [3] Commission of the European Communities, The raw materials initiative: meeting our critical needs for growth and jobs in Europe, (2008).
- [4] European Commission, Communication from the Commission to the European Parliament, the Council, the European Economic and Social Committee and the Committee of the Regions: Tackling the Challenges in Commodity Markets and on Raw Materials, (2011).
- [5] European Commission, Communication from the Commission to the European Parliament, the Council, the European Economic and Social Committee and the Committee of the Regions: On the Review of the List of Critical Raw Materials for the EU and the Implementation of the Raw Materi, (2014).
- [6] European Commission, Communication from the Commission to the European Parliament, the Council, the European Economic and Social Committee and the Committee of the Regions on the 2017 list of Critical Raw Materials for the EU, (2017).
- [7] S. Bobba, S. Carrara, J. Huisman, F. Mathieux, C. Pavel, Critical Raw Materials for Strategic Technologies and Sectors in the EU - a Foresight Study, 2020. <https://doi.org/10.2873/58081>.
- [8] A. Rizzo, S. Goel, M.L. Grilli, R. Iglesias, L. Jaworska, V. Lapkovskis, P. Novak, B.O. Postolnyi, D. Valerini, The critical raw materials in cutting tools for machining applications: A review, *Materials (Basel)*. 13 (2020). <https://doi.org/10.3390/ma13061377>.
- [9] A.W. Connar, Steel Capacity and Critical Raw Materials: an Outlook for Growth, *SAE Trans.* 84 (1975) 494–506. <http://www.jstor.org/stable/44681946>.
- [10] G.A. Blengini, D. Blagoeva, J. Dewulf, C. Torres de Matos, V. Nita, B. Vidal-Legaz, C.E.L. Latunussa, Y. Kayam, L. Talens Peirò, C. Baranzelli, S. Manfredi, L. Mancini, P. Nuss, A. Marmier, P. Alves-Dias, C. Pavel, E. Tzimas, F. Mathieux, D. Pennington, C. Ciupagea, Assessment of the Methodology for Establishing the EU List of Critical Raw Materials, Luxemburg, 2017. <https://doi.org/10.2760/73303>.
- [11] Department of the Interior of the US, Final List of Critical Minerals 2018, *Fed. Regist.* 83 (2018) 23295–23296.
- [12] J.A. Ober, Mineral commodity summaries 2018, Reston, VA, 2018. <https://doi.org/10.3133/70194932>.
- [13] M.L. Grilli, T. Bellezze, E. Gamsjäger, A. Rinaldi, P. Novak, S. Balos, R.R. Piticescu, M.L. Ruello, Solutions for critical raw materials under extreme conditions: A review, *Materials (Basel)*. 10 (2017) 1–23. <https://doi.org/10.3390/ma10030285>.
- [14] V. Popov, A. Katz-Demyanetz, A. Garkun, M. Bamberger, The effect of powder recycling on the mechanical properties and microstructure of electron beam melted Ti-6Al-4 V specimens, *Addit. Manuf.* 22 (2018). <https://doi.org/10.1016/j.addma.2018.06.003>.
- [15] M. Baumers, C. Tuck, R. Wildman, I. Ashcroft, R. Hague, Shape Complexity and Process Energy Consumption in Electron Beam Melting: A Case of Something for Nothing in Additive Manufacturing?, *J. Ind. Ecol.* 21 (2017) S157–S167. <https://doi.org/10.1111/jiec.12397>.
- [16] Z. Liu, Q. Jiang, F. Ning, H. Kim, W. Cong, C. Xu, H.C. Zhang, Investigation of energy requirements and environmental

- performance for additive manufacturing processes, *Sustain.* 10 (2018). <https://doi.org/10.3390/su10103606>. 1287
- [17] F. Le Bourhis, O. Kerbrat, J.-Y. Hascoet, P. Mognol, Sustainable manufacturing: evaluation and modeling of environmental impacts in additive manufacturing, *Int. J. Adv. Manuf. Technol.* 69 (2013) 1927–1939. <https://doi.org/10.1007/s00170-013-5151-2>. 1288  
1289  
1290
- [18] L. Krämer, Y. Champion, R. Pippin, From powders to bulk metallic glass composites, *Sci. Rep.* 7 (2017) 6651. <https://doi.org/10.1038/s41598-017-06424-4>. 1291  
1292
- [19] C. Suryanarayana, A. Inoue, Iron-based bulk metallic glasses, *Int. Mater. Rev.* 58 (2013) 131–166. <https://doi.org/10.1179/1743280412Y.0000000007>. 1293  
1294
- [20] W. Cui, X. Zhang, F. Liou, Additive manufacturing of high-entropy alloys: A review, *Proc. 28th Annu. Int. Solid Free. Fabr. Symp. e An Addit. Manuf. Conf.* 20 (2017) 712–724. <https://doi.org/10.3390/e20120937>. 1295  
1296
- [21] V. Popov, A. Katz-Demyanetz, A. Koptuyug, M. Bamberger, Selective electron beam melting of Al<sub>0.5</sub>CrMoNbTa<sub>0.5</sub> high entropy alloys using elemental powder blend, *Heliyon.* 5 (2019) e01188. <https://doi.org/10.1016/j.heliyon.2019.e01188>. 1297  
1298
- [22] V. Buranich, V. Rogoz, B. Postolnyi, A. Pogrebnjak, Predicting the Properties of the Refractory High-Entropy Alloys for Additive Manufacturing-Based Fabrication and Mechatronic Applications, in: *2020 IEEE 10th Int. Conf. Nanomater. Appl. Prop.*, 2020: pp. 1–5. <https://doi.org/10.1109/NAP51477.2020.9309720>. 1299  
1300  
1301
- [23] T.D. Ngo, A. Kashani, G. Imbalzano, K.T.Q.Q. Nguyen, D. Hui, Additive manufacturing (3D printing): A review of materials, methods, applications and challenges, *Compos. Part B Eng.* 143 (2018) 172–196. <https://doi.org/10.1016/j.compositesb.2018.02.012>. 1302  
1303  
1304
- [24] A. Bandyopadhyay, B. Heer, Additive manufacturing of multi-material structures, *Mater. Sci. Eng. R Reports.* 129 (2018) 1–16. <https://doi.org/10.1016/j.mser.2018.04.001>. 1305  
1306
- [25] Wohlers Associates, Wohlers Report 2018, (2018) 276. [https://doi.org/ISBN 978-0-9913332-0-2](https://doi.org/ISBN%20978-0-9913332-0-2). 1307
- [26] J. Dawes, R. Bowerman, R. Trepleton, Introduction to the additive manufacturing powder metallurgy supply chain, *Johnson Matthey Technol. Rev.* 59 (2015) 243–256. <https://doi.org/10.1595/205651315X688686>. 1308  
1309
- [27] S. Cacace, A.G. Demir, Q. Semeraro, Densification Mechanism for Different Types of Stainless Steel Powders in Selective Laser Melting, in: *Procedia CIRP*, The Author(s), 2017: pp. 475–480. <https://doi.org/10.1016/j.procir.2016.06.010>. 1310  
1311
- [28] D. Bourell, A.B. Spierings, N. Herres, G. Levy, Influence of the particle size distribution on surface quality and mechanical properties in AM steel parts, *Rapid Prototyp. J.* 17 (2011) 195–202. <https://doi.org/10.1108/13552541111124770>. 1312  
1313
- [29] L. Nyborg, M. Norell, I. Olefjord, Surface studies of powder metallurgical stainless steel, *Surf. Interface Anal.* 19 (1992) 607–614. <https://doi.org/10.1002/sia.7401901113>. 1314  
1315
- [30] Y. Hedberg, M. Norell, J. Hedberg, P. Szakálos, P. Linhardt, I. Odnevall Wallinder, Surface characterisation of fine inert gas and water atomised stainless steel 316L powders: Formation of thermodynamically unstable surface oxide phases, *Powder Metall.* 56 (2013) 158–163. <https://doi.org/10.1179/1743290112Y.0000000041>. 1316  
1317  
1318
- [31] B. Engel, D.L. Bourell, Titanium alloy powder preparation for selective laser sintering, *Rapid Prototyp. J.* 6 (2000) 97–106. <https://doi.org/10.1108/13552540010323574>. 1319  
1320
- [32] J.A. Slotwinski, E.J. Garboczi, P.E. Stutzman, C.F. Ferraris, S.S. Watson, M.A. Peltz, Characterization of metal powders used for additive manufacturing, *J. Res. Natl. Inst. Stand. Technol.* 119 (2014) 460–493. <https://doi.org/10.6028/jres.119.018>. 1321  
1322
- [33] G. Egger, P.E. Gygax, R. Glardon, N.P. Karapatis, Optimization of powder layer density in selective laser sintering, in: *10th Solid Free. Fabr. Symp.*, 1999: pp. 255–263. <http://infoscience.epfl.ch/record/153069>. 1323  
1324
- [34] S. Vock, B. Klöden, A. Kirchner, T. Weißgärber, B. Kieback, Powders for powder bed fusion: a review, *Prog. Addit. Manuf.* 4 (2019) 383–397. <https://doi.org/10.1007/s40964-019-00078-6>. 1325  
1326
- [35] N.E. Gorji, R. O'Connor, D. Brabazon, XPS, XRD, and SEM characterization of the virgin and recycled metallic powders for 3D printing applications, *IOP Conf. Ser. Mater. Sci. Eng.* 591 (2019) 12016. <https://doi.org/10.1088/1757-899x/591/1/012016>. 1327  
1328

- [36] W.A. Grell, E. Solis-Ramos, E. Clark, E. Lucon, E.J. Garboczi, P.K. Predecki, Z. Loftus, M. Kumosa, Effect of powder oxidation on the impact toughness of electron beam melting Ti-6Al-4V, *Addit. Manuf.* 17 (2017) 123–134. <https://doi.org/10.1016/j.addma.2017.08.002>.
- [37] Y. Hedberg, M. Norell, P. Linhardt, H. Bergqvist, I. Odnevall Wallinder, Influence of surface oxide characteristics and speciation on corrosion, electrochemical properties and metal release of atomized 316L stainless steel powders, *Int. J. Electrochem. Sci.* 7 (2012) 11655–11677.
- [38] P. Novak, *Advanced Powder Metallurgy Technologies*, Materials (Basel). (2020) 13–15.
- [39] P. Sun, Z.Z. Fang, Y. Zhang, Y. Xia, Review of the Methods for Production of Spherical Ti and Ti Alloy Powder, *JOM.* 69 (2017) 1853–1860. <https://doi.org/10.1007/s11837-017-2513-5>.
- [40] C.F. Yolton, Method for producing titanium particles, 5,084,091, 1992. <https://patents.justia.com/inventor/charles-f-yolton>.
- [41] J.J. Dunkley, Advances in atomisation techniques for the formation of metal powders, in: I. Chang, Y.B.T.-A. in P.M. Zhao (Eds.), *Woodhead Publ. Ser. Met. Surf. Eng.*, Woodhead Publishing, 2013: pp. 3–18. <https://doi.org/https://doi.org/10.1533/9780857098900.1.3>.
- [42] G. Chen, S.Y. Zhao, P. Tan, J. Wang, C.S. Xiang, H.P. Tang, A comparative study of Ti-6Al-4V powders for additive manufacturing by gas atomization, plasma rotating electrode process and plasma atomization, *Powder Technol.* 333 (2018) 38–46. <https://doi.org/10.1016/j.powtec.2018.04.013>.
- [43] M. Entezarian, F. Allaire, P. Tsantrizos, R.A.L. Drew, Plasma atomization: A new process for the production of fine, spherical powders, *JOM.* 48 (1996) 53–55. <https://doi.org/10.1007/BF03222969>.
- [44] GE Additive, Plasma Atomization Technology, (2020). <https://www.ge.com/additive/plasma-atomization-technology>.
- [45] A.R. Kaufmann, Method and Apparatus for Making Powder, 3-099-041, 1963. <https://patentimages.storage.googleapis.com/ce/e9/ee/7aae8cc72f866d/US3099041.pdf>.
- [46] Y. Nie, J. Tang, B. Yang, Q. Lei, S. Yu, Y. Li, Comparison in characteristic and atomization behavior of metallic powders produced by plasma rotating electrode process, *Adv. Powder Technol.* (2020). <https://doi.org/10.1016/j.apt.2020.03.006>.
- [47] G. Gai, Y. Yang, L. Jin, X. Zou, Y. Wu, Particle shape modification and related property improvements, *Powder Technol.* 183 (2008) 115–121. <https://doi.org/10.1016/j.powtec.2007.11.026>.
- [48] S. Goel, G. Cross, A. Stukowski, E. Gamsjäger, B. Beake, A. Agrawal, Designing nanoindentation simulation studies by appropriate indenter choices: Case study on single crystal tungsten, *Comput. Mater. Sci.* 152 (2018) 196–210. <https://doi.org/https://doi.org/10.1016/j.commatsci.2018.04.044>.
- [49] K. Pulidindi, A. Prakash, Tungsten Market Size By Application (Tungsten Carbide, Metal Alloys, Mill Products), By End-use (Automotive Parts, Aerospace Components, Drilling, Boring & Cutting Equipment, Logging Equipment, Electrical & Electronics Appliances), *Industry Analysis Repor*, 2018. <https://www.gminsights.com/industry-analysis/tungsten-market>.
- [50] R.K. Enneti, K.C. Prough, T.A. Wolfe, A. Klein, N. Studley, J.L. Trasorras, Sintering of WC-12%Co processed by binder jet 3D printing (BJ3DP) technology, *Int. J. Refract. Met. Hard Mater.* 71 (2018) 28–35. <https://doi.org/https://doi.org/10.1016/j.ijrmhm.2017.10.023>.
- [51] A.C. Field, L.N. Carter, N.J.E. Adkins, M.M. Attallah, M.J. Gorley, M. Strangwood, The Effect of Powder Characteristics on Build Quality of High-Purity Tungsten Produced via Laser Powder Bed Fusion (LPBF), *Metall. Mater. Trans. A Phys. Metall. Mater. Sci.* 51 (2020) 1367–1378. <https://doi.org/10.1007/s11661-019-05601-6>.
- [52] J. Wright, Additive Manufacturing of Tungsten via Selective Laser Melting and Electron Beam Melting, The University of Sheffield, 2020.
- [53] M. Doerre, L. Hibbitts, G. Patrick, N.K. Akafuah, Advances in automotive conversion coatings during pretreatment of the body structure: A review, *Coatings.* 8 (2018). <https://doi.org/10.3390/COATINGS8110405>.
- [54] E. Bozyazi, M. Ürgen, A.F. Çakır, Comparison of reciprocating wear behaviour of electrolytic hard chrome and arc-PVD

- CrN coatings, *Wear*. 256 (2004) 832–839. [https://doi.org/https://doi.org/10.1016/S0043-1648\(03\)00523-4](https://doi.org/https://doi.org/10.1016/S0043-1648(03)00523-4). 1371
- [55] B.O. Postolnyi, O.V. Bondar, K. Zaleski, E. Coy, S. Jurga, L. Rebouta, J.P. Araujo, Multilayer Design of CrN/MoN Superhard Protective Coatings and Their Characterisation, in: A. Pogrebnjak, V. Novosad (Eds.), *Adv. Thin Film. Nanostructured Mater. Coatings*, Springer Singapore, 2019. [https://doi.org/10.1007/978-981-13-6133-3\\_2](https://doi.org/10.1007/978-981-13-6133-3_2). 1372  
1373  
1374
- [56] Y. Xiao, J. Xiong, Z. Guo, J. Liu, L. Zhou, J. Ye, W. Zhao, Microstructures and properties of PVD TiAlN coating deposited on cermets with different Ti(C, N) grain size, *J. Cent. South Univ.* 27 (2020) 721–735. <https://doi.org/10.1007/s11771-020-4326-x>. 1375  
1376  
1377
- [57] S.K. Singh, S. Chattopadhyaya, A. Pramanik, S. Kumar, A.K. Basak, S.M. Pandey, Q. Murtaza, S. Legutko, G. Litak, Tribological Properties of Chromium Nitride on the Cylinder Liner under the Influence of High Temperature, *Mater. (Basel, Switzerland)*. 13 (2020) 4497. <https://doi.org/10.3390/ma13204497>. 1378  
1379  
1380
- [58] O. V Maksakova, R.F. Webster, R.D. Tilley, V.I. Ivashchenko, B.O. Postolnyi, O. V Bondar, Y. Takeda, V.M. Rogoz, R.E. Sakenova, P. V Zukowski, M. Opielak, V.M. Beresnev, A.D. Pogrebnjak, Nanoscale architecture of (CrN/ZrN)/(Cr/Zr) nanocomposite coatings: Microstructure, composition, mechanical properties and first-principles calculations, *J. Alloys Compd.* 831 (2020) 154808. <https://doi.org/https://doi.org/10.1016/j.jallcom.2020.154808>. 1381  
1382  
1383  
1384
- [59] B. Postolnyi, O. Bondar, M. Opielak, P. Rogalski, J.P. Araújo, Structural analysis of multilayer metal nitride films CrN/MoN using electron backscatter diffraction (EBSD), in: *Proc.SPIE*, 2016. <https://doi.org/10.1117/12.2243279>. 1385  
1386
- [60] F. Jiang, W. Zhu, C. Zhao, Y. Li, P. Wei, T. Wan, H. Ye, S. Pan, F. Ren, A strong, wear- and corrosion-resistant, and antibacterial Co–30 at.% Cr–5 at.% Ag ternary alloy for medical implants, *Mater. Des.* 184 (2019) 108190. <https://doi.org/10.1016/J.MATDES.2019.108190>. 1387  
1388  
1389
- [61] K.B. Shedd, A. Hwang, Mineral Industry Surveys: Cobalt, 2020. <https://prd-wret.s3.us-west-2.amazonaws.com/assets/palladium/production/atoms/files/mis-202006-cobal.pdf>. 1390  
1391
- [62] M. Moradi, A. Ashoori, A. Hasani, Additive manufacturing of stellite 6 superalloy by direct laser metal deposition – Part 1: Effects of laser power and focal plane position, *Opt. Laser Technol.* 131 (2020) 106328. <https://doi.org/10.1016/j.optlastec.2020.106328>. 1392  
1393  
1394
- [63] V. Popov, A. Fleisher, G. Muller-Kamskii, A. Shishkin, A. Katz-Demyanetz, N. Travitzky, S. Goel, Novel hybrid method to additively manufacture denser graphite structures using Binder Jetting, *Sci. Rep.* 11 (2021) 2438. <https://doi.org/10.1038/s41598-021-81861-w>. 1395  
1396  
1397
- [64] Critical Raw Materials Innovation Network (CRM\_InnoNet), Substitution of Critical Raw Materials, Critical Raw Materials Substitution Profiles., n.d. <http://www.criticalrawmaterials.eu/wp-content/uploads/D3.3-Raw-Materials-Profiles-final-submitteddocument.pdf>. 1398  
1399  
1400
- [65] E. García-Tuñón, S. Barg, J. Franco, R. Bell, S. Eslava, E. D’Elia, R.C. Maher, F. Guitian, E. Saiz, Printing in Three Dimensions with Graphene, *Adv. Mater.* 27 (2015) 1688–1693. <https://doi.org/10.1002/adma.201405046>. 1401  
1402
- [66] H. Guo, R. Lv, S. Bai, Recent advances on 3D printing graphene-based composites, *Nano Mater. Sci.* 1 (2019) 101–115. <https://doi.org/10.1016/j.nanoms.2019.03.003>. 1403  
1404
- [67] Y. Li, Z. Feng, L. Huang, K. Essa, E. Bilotti, H. Zhang, T. Peijs, L. Hao, Additive manufacturing high performance graphene-based composites: A review, *Compos. Part A Appl. Sci. Manuf.* 124 (2019) 105483. <https://doi.org/10.1016/j.compositesa.2019.105483>. 1405  
1406  
1407
- [68] A. Azhari, E. Marzbanrad, D. Yilman, E. Toyserkani, M.A. Pope, Binder-jet powder-bed additive manufacturing (3D printing) of thick graphene-based electrodes, *Carbon N. Y.* 119 (2017) 257–266. <https://doi.org/10.1016/j.carbon.2017.04.028>. 1408  
1409
- [69] W. Zhou, X. Sun, K. Kikuchi, N. Nomura, K. Yoshimi, A. Kawasaki, Carbon nanotubes as a unique agent to fabricate nanoceramic/metal composite powders for additive manufacturing, *Mater. Des.* 137 (2018) 276–285. <https://doi.org/10.1016/j.matdes.2017.10.034>. 1410  
1411  
1412

- [70] D. Lin, C. Richard Liu, G.J. Cheng, Single-layer graphene oxide reinforced metal matrix composites by laser sintering: Microstructure and mechanical property enhancement, *Acta Mater.* 80 (2014) 183–193. <https://doi.org/10.1016/j.actamat.2014.07.038>.
- [71] S. Wen, K. Chen, W. Li, Y. Zhou, Q. Wei, Y. Shi, Selective laser melting of reduced graphene oxide/S136 metal matrix composites with tailored microstructures and mechanical properties, *Mater. Des.* 175 (2019) 107811. <https://doi.org/10.1016/j.matdes.2019.107811>.
- [72] M. Li, X. Wu, Y. Yang, Q. Wei, C. Yan, C. Cai, J. Liu, W. Li, Y. Shi, TiAl/RGO (reduced graphene oxide) bulk composites with refined microstructure and enhanced nanohardness fabricated by selective laser melting (SLM), *Mater. Charact.* 143 (2018) 197–205. <https://doi.org/10.1016/j.matchar.2018.05.040>.
- [73] J. Cui, M. Kramer, L. Zhou, F. Liu, A. Gabay, G. Hadjipanayis, B. Balasubramanian, D. Sellmyer, Current progress and future challenges in rare-earth-free permanent magnets, *Acta Mater.* 158 (2018) 118–137. <https://doi.org/10.1016/J.ACTAMAT.2018.07.049>.
- [74] A. Azhari, E. Toyserkani, C. Villain, Additive Manufacturing of Graphene–Hydroxyapatite Nanocomposite Structures, *Int. J. Appl. Ceram. Technol.* 12 (2015) 8–17. <https://doi.org/10.1111/ijac.12309>.
- [75] Z. Chen, P. Wei, S. Zhang, B. Lu, L. Zhang, X. Yang, K. Huang, Y. Huang, X. Li, Q. Zhao, Graphene reinforced nickel-based superalloy composites fabricated by additive manufacturing, *Mater. Sci. Eng. A.* 769 (2020) 138484. <https://doi.org/10.1016/j.msea.2019.138484>.
- [76] M. Taher, A hybrid ionic graphene nanocomposite with layered structure, WO2019054931, 2017. <https://www.graphmatech.com/>.
- [77] A.G. Illarionov, A.G. Nezhdanov, S.I. Stepanov, G. Muller-Kamskii, A.A. Popov, Structure, Phase Composition, and Mechanical Properties of Biocompatible Titanium Alloys of Different Types, *Phys. Met. Metallogr.* 121 (2020) 367–373. <https://doi.org/10.1134/S0031918X20040055>.
- [78] C. Liu, S. Goel, I. Llavori, P. Stolf, C.L. Giusca, A. Zabala, J. Kohlscheen, J.M. Paiva, J.L. Endrino, S.C. Veldhuis, G.S. Fox Rabinovich, Benchmarking of several material constitutive models for tribology, wear, and other mechanical deformation simulations of Ti6Al4V, *J. Mech. Behav. Biomed. Mater.* 97 (2019) 126–137. <https://doi.org/https://doi.org/10.1016/j.jmbbm.2019.05.013>.
- [79] K. Dietrich, J. Diller, S. Dubiez-Le Goff, D. Bauer, P. Forêt, G. Witt, The influence of oxygen on the chemical composition and mechanical properties of Ti-6Al-4V during laser powder bed fusion (L-PBF), *Addit. Manuf.* 32 (2020). <https://doi.org/10.1016/j.addma.2019.100980>.
- [80] C. Leyens, M. Peters, Titanium and Titanium Alloys. Fundamentals and Applications, WILEY-VCH Verlag GmbH & Co. KGaA, Weinheim, 2003.
- [81] G.W. Boyer, Military Handbook - Titanium and Titanium Alloys, Department, Washington, D.C., 1974.
- [82] T.E. Norgate, G. Wellwood, The potential applications for titanium metal powder and their life cycle impacts, *JOM.* 58 (2006) 58–63. <https://doi.org/10.1007/s11837-006-0084-y>.
- [83] S. Goel, B. Beake, C.-W. Chan, N. Haque Faisal, N. Dunne, Twinning anisotropy of tantalum during nanoindentation, *Mater. Sci. Eng. A.* 627 (2015) 249–261. <https://doi.org/https://doi.org/10.1016/j.msea.2014.12.075>.
- [84] L.Y. Chen, Y.W. Cui, L.C. Zhang, Recent development in beta titanium alloys for biomedical applications, *Metals (Basel).* 10 (2020) 1–29. <https://doi.org/10.3390/met10091139>.
- [85] M.T. Mohammed, Z.A. Khan, A.N. Siddiquee, Beta Titanium Alloys: The Lowest Elastic Modulus for Biomedical Applications: A Review Surface Modifications through FSP View project MACHINING View project, *Int. J. Chem. Nucl. Metall. Mater. Eng.* 8 (2014) 726–731. <https://www.researchgate.net/publication/265396160>.
- [86] A. Bansiddhi, T.D. Sargeant, S.I. Stupp, D.C. Dunand, Porous NiTi for bone implants: A review, *Acta Biomater.* 4 (2008)



- 773–782. <https://doi.org/10.1016/j.actbio.2008.02.009>. 1455
- [87] Y.U. Loginov, S.I. Stepanov, E. V Khanykova, Effect of pore architecture of titanium implants on stress-strain state upon compression, *Solid State Phenom.* 265 SSP (2017) 606–610. <https://doi.org/10.4028/www.scientific.net/SSP.265.606>. 1456
- [88] H.H. Hausner, H.S. Kalish, R.P. Angier, Powder Metallurgy of Zirconium, *JOM.* 3 (1951) 625–633. 1458  
<https://doi.org/10.1007/BF03397356>. 1459
- [89] A. Harooni, M. Iravani, A. Khajepour, J.M. King, A. Khalifa, A.P. Gerlich, Mechanical properties and microstructures in zirconium deposited by injected powder laser additive manufacturing, *Addit. Manuf.* 22 (2018) 537–547. 1460  
<https://doi.org/10.1016/j.addma.2018.05.037>. 1462
- [90] L. Jaworska, J. Panasiuk, P. Putyra, M. Stępień, P. Noga, P. Pałka, A. Zwoliński, The influence of powder characteristics on the sintering behaviour and impurity content of spark-plasma-sintered zirconium, *Int. J. Refract. Met. Hard Mater.* 82 (2019) 259–267. <https://doi.org/10.1016/j.ijrmhm.2019.04.018>. 1463
- [91] T. Hori, T. Nagase, M. Todai, A. Matsugaki, T. Nakano, Development of non-equiatomic Ti-Nb-Ta-Zr-Mo high-entropy alloys for metallic biomaterials, *Scr. Mater.* 172 (2019) 83–87. <https://doi.org/10.1016/j.scriptamat.2019.07.011>. 1466
- [92] T. Ishimoto, R. Ozasa, K. Nakano, M. Weinmann, C. Schnitter, M. Stenzel, A. Matsugaki, T. Nagase, T. Matsuzaka, M. Todai, H.S. Kim, T. Nakano, Development of TiNbTaZrMo bio-high entropy alloy (BioHEA) super-solid solution by selective laser melting, and its improved mechanical property and biocompatibility, *Scr. Mater.* 194 (2021) 113658. 1468  
<https://doi.org/10.1016/j.scriptamat.2020.113658>. 1471
- [93] H. Bissett, I.J. Van Der Walt, J.L. Havenga, J.T. Nel, Titanium and zirconium metal powder spheroidization by thermal plasma processes, *J. South. African Inst. Min. Metall.* 115 (2015) 937–942. <https://doi.org/10.17159/2411-9717/2015/v115n10a6>. 1472
- [94] ALD Vacuum Technologies, VIGA Systems, (n.d.). <https://www.ald-vt.com>. 1475
- [95] W.E. Frazier, Metal additive manufacturing: A review, *J. Mater. Eng. Perform.* 23 (2014) 1917–1928. 1476  
<https://doi.org/10.1007/s11665-014-0958-z>. 1477
- [96] J.J. Lewandowski, M. Seifi, Metal Additive Manufacturing: A Review of Mechanical Properties, *Annu. Rev. Mater. Res.* 46 (2016) 151–186. <https://doi.org/10.1146/annurev-matsci-070115-032024>. 1478
- [97] M. Qian, W. Xu, M. Brandt, H.P. Tang, Additive manufacturing and postprocessing of Ti-6Al-4V for superior mechanical properties, *MRS Bull.* 41 (2016) 775–784. <https://doi.org/DOI:10.1557/mrs.2016.215>. 1480
- [98] T.M. Mower, M.J. Long, Mechanical behavior of additive manufactured, powder-bed laser-fused materials, *Mater. Sci. Eng. A.* 651 (2016) 198–213. <https://doi.org/10.1016/j.msea.2015.10.068>. 1482
- [99] E. Hryha, R. Shvab, H. Gruber, A. Leicht, L. Nyborg, Surface oxide state on metal powder and its changes during additive manufacturing: An overview, in: *Proc. Euro PM 2017 Int. Powder Metall. Congr. Exhib.*, 2018. 1484
- [100] V. Popov, A. Katz-Demyanetz, A. Garkun, G. Muller-Kamskii, E. Strokin, H. Rosenson, Effect of Hot Isostatic Pressure treatment on the Electron-Beam Melted Ti-6Al-4V specimens, *Procedia Manuf.* 21 (2018) 125–132. 1486  
<https://doi.org/10.1016/j.promfg.2018.02.102>. 1488
- [101] A. Gromov, A. Ilyin, U. Förster-Barth, U. Teipel, Characterization of Aluminum Powders: II. Aluminum Nanopowders Passivated by Non-Inert Coatings, *Propellants, Explos. Pyrotech.* 31 (2006) 401–409. 1489  
<https://doi.org/https://doi.org/10.1002/prop.200600055>. 1491
- [102] H. Khaing, T.T. Kywe, Production of Fine Aluminum Powder from Metallic Aluminum, in: *First Int. Conf. Interdiscip. Res. Dev.*, Thailand, 2011. 1492
- [103] O.D. Neikov, *Production of Aluminum Alloy Powders*, 2nd ed., Elsevier Ltd., 2019. <https://doi.org/10.1016/b978-0-08-100543-9.00016-6>. 1494
- [104] L. Langnau, Will aluminum become the new hot material in metal additive manufacturing?, *Makes Parts Fast Netw.* (2018). 1496

- <https://www.makepartsfast.com/will-aluminum-become-new-hot-new-material-in-metal-additive-manufacturing/>. 1497
- [105] T.A. Ring, *Fundamentals of Ceramic Powder Processing and Synthesis*, Academic Press, Inc., San Diego, California, 1996. 1498  
<https://www.elsevier.com/books/fundamentals-of-ceramic-powder-processing-and-synthesis/ring/978-0-12-588930-8>. 1499
- [106] Y. Oh, V. Bharambe, B. Mummareddy, J. Martin, J. McKnight, M.A. Abraham, J.M. Walker, K. Rogers, B. Conner, P. Cortes, E. MacDonald, J.J. Adams, Microwave dielectric properties of zirconia fabricated using NanoParticle Jetting™, *Addit. Manuf.* 27 (2019) 586–594. <https://doi.org/10.1016/j.addma.2019.04.005>. 1500  
1501  
1502
- [107] K. Nagulin, R. Nazarov, I. Efimochkin, A. Gilmutdinov, Optimization of radio-frequency plasma parameters for spheroidization of zirconium oxide powders, *Surf. Coatings Technol.* 382 (2020). 1503  
<https://doi.org/10.1016/j.surfcoat.2019.125196>. 1504  
1505
- [108] U. Lakshminarayan, S. Ogrydziak, H.L. Marcus, Selective Laser Sintering of Ceramic materials, in: *1st Solid Free. Fabr. Symp*, 1990: pp. 16–26. <http://sffsymposium.engr.utexas.edu/Manuscripts/1990/1990-03-Lakshminarayan.pdf>. 1506  
1507
- [109] J. Wilkes, Y.C. Hagedorn, W. Meiners, K. Wissenbach, Additive manufacturing of ZrO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub> ceramic components by selective laser melting, *Rapid Prototyp. J.* 19 (2013) 51–57. <https://doi.org/10.1108/13552541311292736>. 1508  
1509
- [110] F. Verga, M. Borlaf, L. Conti, K. Florio, M. Vetterli, T. Graule, M. Schmid, K. Wegener, Laser-based powder bed fusion of alumina toughened zirconia, *Addit. Manuf.* 31 (2020) 100959. <https://doi.org/10.1016/j.addma.2019.100959>. 1510  
1511
- [111] C.L.A. Leung, S. Marussi, M. Towrie, J. del Val Garcia, R.C. Atwood, A.J. Bodey, J.R. Jones, P.J. Withers, P.D. Lee, Laser-matter interactions in additive manufacturing of stainless steel SS316L and 13-93 bioactive glass revealed by in situ X-ray imaging, *Addit. Manuf.* 24 (2018) 647–657. <https://doi.org/10.1016/j.addma.2018.08.025>. 1512  
1513  
1514
- [112] W.H. Yu, S.L. Sing, C.K. Chua, C.N. Kuo, X.L. Tian, Particle-reinforced metal matrix nanocomposites fabricated by selective laser melting: A state of the art review, *Prog. Mater. Sci.* 104 (2019) 330–379. <https://doi.org/10.1016/j.pmatsci.2019.04.006>. 1515  
1516
- [113] F. Brueckner, M. Riede, M. Müller, F. Marquardt, R. Willner, A. Seidel, E. Lopéz, C. Leyens, E. Beyer, Enhanced manufacturing possibilities using multi-materials in laser metal deposition, *J. Laser Appl.* 30 (2018) 32308. <https://doi.org/10.2351/1.5040639>. 1517  
1518  
1519
- [114] J. Shi, Y. Wang, Development of metal matrix composites by laser-assisted additive manufacturing technologies: a review, *J. Mater. Sci.* 55 (2020) 9883–9917. <https://doi.org/10.1007/s10853-020-04730-3>. 1520  
1521
- [115] L. Portolés Griñán, J.R. Blasco Puchades, M. Sanchez, M. Martinez, NANOTUN3D: Development of the complete workflow for producing and using a novel nanomodified Ti-based alloy for additive manufacturing in special applications., in: *Euro PM2018 Congr. Exhib.*, 2018. <https://www.epma.com/epma-free-publications/product/ep18-3992724>. 1522  
1523  
1524
- [116] Z. Chen, Z. Li, J. Li, C. Liu, C. Lao, Y. Fu, C. Liu, Y. Li, P. Wang, Y. He, 3D printing of ceramics: A review, *J. Eur. Ceram. Soc.* 39 (2019) 661–687. <https://doi.org/10.1016/j.jeurceramsoc.2018.11.013>. 1525  
1526
- [117] ASTM International, F2792-12a - Standard Terminology for Additive Manufacturing Technologies, 2013. <https://doi.org/10.1520/F2792-12A.2>. 1527  
1528
- [118] K. Lu, M. Hiser, W. Wu, Effect of particle size on three dimensional printed mesh structures, *Powder Technol.* 192 (2009) 178–183. <https://doi.org/10.1016/j.powtec.2008.12.011>. 1529  
1530
- [119] M. Lanzetta, E. Sachs, Improved surface finish in 3D printing using bimodal powder distribution, *Rapid Prototyp. J.* 9 (2003) 157–166. <https://doi.org/10.1108/13552540310477463>. 1531  
1532
- [120] S. Huang, C. Ye, H. Zhao, Z. Fan, Additive manufacturing of thin alumina ceramic cores using binder-jetting, *Addit. Manuf.* 29 (2019) 100802. <https://doi.org/10.1016/j.addma.2019.100802>. 1533  
1534
- [121] X. Lv, F. Ye, L. Cheng, S. Fan, Y. Liu, Binder jetting of ceramics: Powders, binders, printing parameters, equipment, and post-treatment, *Ceram. Int.* 45 (2019) 12609–12624. <https://doi.org/10.1016/j.ceramint.2019.04.012>. 1535  
1536
- [122] J. Suwanprateeb, R. Sanngam, T. Panyathanmaporn, Influence of raw powder preparation routes on properties of hydroxyapatite fabricated by 3D printing technique, *Mater. Sci. Eng. C.* 30 (2010) 610–617. 1537  
1538

- <https://doi.org/10.1016/j.msec.2010.02.014>. 1539
- [123] W. Du, X. Ren, C. Ma, Z. Pei, Ceramic binder jetting additive manufacturing: Particle coating for increasing powder sinterability and part strength, *Mater. Lett.* 234 (2019) 327–330. <https://doi.org/10.1016/j.matlet.2018.09.118>. 1540
- [124] V. Karageorgiou, D. Kaplan, Porosity of 3D biomaterial scaffolds and osteogenesis, *Biomaterials*. 26 (2005) 5474–5491. <https://doi.org/10.1016/j.biomaterials.2005.02.002>. 1542
- [125] J. Russias, E. Saiz, S. Deville, K. Gryn, G. Liu, R.K. Nalla, A.P. Tomsia, Fabrication and in vitro characterization of three-dimensional organic/inorganic scaffolds by robocasting, *J. Biomed. Mater. Res. Part A*. 83A (2007) 434–445. <https://doi.org/10.1002/jbm.a.31237>. 1544
- [126] W. Xiao, M.A. Zaeem, B.S. Bal, M.N. Rahaman, Creation of bioactive glass (13–93) scaffolds for structural bone repair using a combined finite element modeling and rapid prototyping approach, *Mater. Sci. Eng. C*. 68 (2016) 651–662. <https://doi.org/10.1016/j.msec.2016.06.011>. 1547
- [127] R.C. Richard, R.N. Oliveira, G.D.A. Soares, R.M.S.M. Thiré, Direct-write assembly of 3D scaffolds using colloidal calcium phosphates inks, *Rev. Mater.* 19 (2014) 61–67. <https://doi.org/10.1590/S1517-70762014000100009>. 1550
- [128] S.I. Roohani-Esfahani, P. Newman, H. Zreiqat, Design and Fabrication of 3D printed Scaffolds with a Mechanical Strength Comparable to Cortical Bone to Repair Large Bone Defects, *Sci. Rep.* 6 (2016) 1–8. <https://doi.org/10.1038/srep19468>. 1552
- [129] H.W. Kim, J.C. Knowles, H.E. Kim, Hydroxyapatite porous scaffold engineered with biological polymer hybrid coating for antibiotic Vancomycin release, *J. Mater. Sci. Mater. Med.* 16 (2005) 189–195. <https://doi.org/10.1007/s10856-005-6679-y>. 1554
- [130] Q.Z. Chen, I.D. Thompson, A.R. Boccaccini, 45S5 Bioglass®-derived glass–ceramic scaffolds for bone tissue engineering, *Biomaterials*. 27 (2006) 2414–2425. <https://doi.org/10.1016/j.biomaterials.2005.11.025>. 1556
- [131] Academic Press, *Handbook of Advanced Ceramics. 2nd Edition. Materials, Applications, Processing, and Properties*, Academic Press, Inc., 2013. <https://www.elsevier.com/books/handbook-of-advanced-ceramics/somiya/978-0-12-385469-8>. 1558
- [132] M. Fukushima, Y. Zhou, H. Miyazaki, Y.I. Yoshizawa, K. Hirao, Y. Iwamoto, S. Yamazaki, T. Nagano, Microstructural characterization of porous silicon carbide membrane support with and without alumina additive, *J. Am. Ceram. Soc.* 89 (2006) 1523–1529. <https://doi.org/10.1111/j.1551-2916.2006.00931.x>. 1560
- [133] I.D. Xynos, M.V.J. Hukkanen, J.J. Batten, L.D. BATTERY, L.L. Hench, J.M. Polak, Bioglass®45S5 stimulates osteoblast turnover and enhances bone formation in vitro: Implications and applications for bone tissue engineering, *Calcif. Tissue Int.* 67 (2000) 321–329. <https://doi.org/10.1007/s002230001134>. 1563
- [134] L. Gridelet, P. Delbecq, L. Hervé, P. Boissolle, D. Fleury, S. Kowal, G. Fayet, Proposal of a new risk assessment method for the handling of powders and nanomaterials, *Ind. Health*. 53 (2015) 56–68. <https://doi.org/10.2486/indhealth.2014-0046>. 1566
- [135] J. Deckers, J. Vleugels, J.P. Kruth, Additive manufacturing of ceramics: A review, *J. Ceram. Sci. Technol.* 5 (2014) 245–260. <https://doi.org/10.4416/JCST2014-00032>. 1568
- [136] M. Puerto Perez-Perez, M.A. Sebastián, E. Gómez, Análisis y propuesta para la utilización de los contenidos en normas técnicas para la enseñanza de la Fabricación Aditiva Teaching innovation on industrial technologies in productive areas View project Innovation in Materials Selection and Evaluation for, in: CNIM, XXII Congr. Natl. Ingeniería Mecánica, 2018: pp. 286–299. 1570
- [137] T. Riipinen, V. Kujanpää, E. Komi, P. Kilpeläinen, M. Savolainen, P. Puukko, J. Vihinen, E. Coatanea, H. Mokhtarian, Industrialization of hybrid and additive manufacturing - Implementation to Finnish industry (HYBRAM), 2018. 1574
- [138] D. Sher, The 3dpbm interactive map of commercially available AM technologies By material families and key AM hardware manufacturers, (2019). 1576
- [139] ASTM International, *Standard Terminology for Additive Manufacturing – General Principles – Terminology*, 2015. <https://doi.org/10.1520/F2792-12A.2>. 1578
- [140] *Digital Alloys’ Guide to Metal Additive Manufacturing, Metal Binder Jetting*, (2019). 1580

- [141] M. Schmidt, M. Merklein, D. Bourell, D. Dimitrov, T. Hausotte, K. Wegener, L. Overmeyer, F. Vollertsen, G.N. Levy, Laser based additive manufacturing in industry and academia, in: CIRP Ann., CIRP, 2017: pp. 561–583. <https://doi.org/10.1016/j.cirp.2017.05.011>.
- [142] W.J. Sames, F.A. List, S. Pannala, R.R. Dehoff, S.S. Babu, The metallurgy and processing science of metal additive manufacturing, *Int. Mater. Rev.* 61 (2016) 315–360. <https://doi.org/10.1080/09506608.2015.1116649>.
- [143] Digital Alloys' Guide to Metal Additive Manufacturing, Cold Spray, (2020).
- [144] A. Hehr, M. Norfolk, A comprehensive review of ultrasonic additive manufacturing, *Rapid Prototyp. J.* 26 (2019) 445–458. <https://doi.org/10.1108/RPJ-03-2019-0056>.
- [145] Jon Izeta, State of the art of additive manufacturing technologies: Technologies, trends, opportunitiues, challenges and applications to the aerospace sector, 2017.
- [146] E. Sacco, S.K. Moon, Additive manufacturing for space: status and promises, *Int. J. Adv. Manuf. Technol.* 105 (2019) 4123–4146. <https://doi.org/10.1007/s00170-019-03786-z>.
- [147] V. Popov, G. Muller-Kamskii, A. Katz-Demyanetz, A. Kovalevsky, S. Usov, D. Trofimcow, G. Dzhenzhera, A. Koptuyug, Additive manufacturing to veterinary practice: recovery of bony defects after the osteosarcoma resection in canines, *Biomed. Eng. Lett.* 9 (2019) 97–108. <https://doi.org/10.1007/s13534-018-00092-7>.
- [148] E. Kudryavtseva, V. Popov, G. Muller-Kamskii, E. Zakurinova, V. Kovalev, Advantages of 3D Printing for Gynecology and Obstetrics: Brief Review of Applications, Technologies, and Prospects, in: 2020 IEEE 10th Int. Conf. Nanomater. Appl. Prop., 2020: pp. 02SAMA09-1-02SAMA09-5. <https://doi.org/10.1109/NAP51477.2020.9309602>.
- [149] J.M.C. Azevedo, A. CabreraSerrenho, J.M. Allwood, Energy and material efficiency of steel powder metallurgy, *Powder Technol.* 328 (2018) 329–336. <https://doi.org/10.1016/j.powtec.2018.01.009>.
- [150] Isaac Chang Yuyuan Zhao, ed., *Advances in Powder Metallurgy, Properties, Processing and Applications*, 1st Editio, Woodhead Publishing, 2013.
- [151] B. Barroqueiro, A. Andrade-Campos, R.A.F. Valente, V. Neto, Metal additive manufacturing cycle in aerospace industry: A comprehensive review, *J. Manuf. Mater. Process.* 3 (2019) 1–21. <https://doi.org/10.3390/jmmp3030052>.
- [152] J. Dunkley Dr, *Advances in atomisation techniques for the formation of metal powders*, Woodhead Publishing Limited, 2013. <https://doi.org/10.1533/9780857098900.1.3>.
- [153] Digital Alloys' Guide to Metal Additive Manufacturing – Part 13, Joule Printing™ Vs. Wire DED, (2019).
- [154] D. Number, S.W.W. Waammat, A. Oct, Use of WAAM for manufacture of reconfigurable tooling with conformal features, (2015).
- [155] T.A. Rodrigues, V. Duarte, R.M. Miranda, T.G. Santos, J.P. Oliveira, Current status and perspectives on wire and arc additive manufacturing (WAAM), *Materials (Basel)*. 12 (2019). <https://doi.org/10.3390/ma12071121>.
- [156] B. Wu, Z. Pan, D. Ding, D. Cuiuri, H. Li, J. Xu, J. Norrish, A review of the wire arc additive manufacturing of metals: properties, defects and quality improvement, *J. Manuf. Process.* 35 (2018) 127–139. <https://doi.org/10.1016/j.jmapro.2018.08.001>.
- [157] D.G. Ahn, Direct metal additive manufacturing processes and their sustainable applications for green technology: A review, *Int. J. Precis. Eng. Manuf. - Green Technol.* 3 (2016) 381–395. <https://doi.org/10.1007/s40684-016-0048-9>.
- [158] Sciaky Inc., Benefits of Wire vs. Powder Metal 3D Printing, (n.d.).
- [159] F. Xu, V. Dhokia, P. Colegrove, A. McAndrew, S. Williams, A. Henstridge, S.T. Newman, Realisation of a multi-sensor framework for process monitoring of the wire arc additive manufacturing in producing Ti-6Al-4V parts, *Int. J. Comput. Integr. Manuf.* 31 (2018) 785–798. <https://doi.org/10.1080/0951192X.2018.1466395>.
- [160] J. Mehnen, J. Ding, H. Lockett, P. Kazanas, Design study for wire and arc additive manufacture, *Int. J. Prod. Dev.* 19 (2014) 2–20. <https://doi.org/10.1504/IJPD.2014.060028>.

- [161] J.R. Hönnige, P.A. Colegrove, S. Ganguly, E. Eimer, S. Kabra, S. Williams, Control of residual stress and distortion in aluminium wire + arc additive manufacture with rolling, *Addit. Manuf.* 22 (2018) 775–783. <https://doi.org/10.1016/j.addma.2018.06.015>.
- [162] J. Gonzalez-Gutierrez, S. Cano, S. Schuschnigg, C. Kukla, J. Sapkota, C. Holzer, Additive manufacturing of metallic and ceramic components by the material extrusion of highly-filled polymers: A review and future perspectives, *Materials (Basel)*. 11 (2018). <https://doi.org/10.3390/ma11050840>.
- [163] W.Y. Yeong, C.Y. Yap, M. Mapar, C.K. Chua, State-of-the-art review on selective laser melting of ceramics, in: *High Value Manuf. Adv. Res. Virtual Rapid Prototyp. - Proc. 6th Int. Conf. Adv. Res. Rapid Prototyping, VR@P 2013, 2014*: pp. 65–70. <https://doi.org/10.1201/b15961-14>.
- [164] G. Marinelli, F. Martina, S. Ganguly, S. Williams, Development of Wire + Arc additive manufacture for the production of large-scale unalloyed tungsten components, *Int. J. Refract. Met. Hard Mater.* 82 (2019) 329–335. <https://doi.org/10.1016/j.ijrmhm.2019.05.009>.
- [165] J. Gu, B. Cong, J. Ding, S.W. Williams, Y. Zhai, WIRE+ARC additive manufacturing of aluminium, 25th Annu. Int. Solid Free. Fabr. Symp. &#65533; An Addit. Manuf. Conf. SFF 2014. (2014) 451–458.
- [166] J. Akram, P. Chalavadi, D. Pal, B. Stucker, Understanding grain evolution in additive manufacturing through modeling, *Addit. Manuf.* 21 (2018) 255–268. <https://doi.org/10.1016/j.addma.2018.03.021>.
- [167] T. Duda, L.V. Raghavan, 3D Metal Printing Technology, *IFAC-PapersOnLine*. 49 (2016) 103–110. <https://doi.org/10.1016/j.ifacol.2016.11.111>.
- [168] Digital Alloys' Guide to Metal Additive Manufacturing, *Energy Consumption in Metal Additive Manufacturing*, (2019).
- [169] Digital Alloys' Guide to Metal Additive Manufacturing, *Economics of Metal Additive Manufacturing*, (2019).
- [170] S. Balos, M. Dramicanin, P. Janjatovic, I. Zabunov, D. Klobcar, M. Busic, M.L. Grilli, Metal Oxide Nanoparticle-Based Coating as a Catalyzer for A-TIG Welding: Critical Raw Material Perspective, *Metals (Basel)*. (2019). <https://doi.org/10.3390/met9050567>.
- [171] G. Shanbhag, M. Vlasea, The effect of reuse cycles on Ti-6Al-4V powder properties processed by electron beam powder bed fusion, *Manuf. Lett.* 25 (2020) 60–63. <https://doi.org/10.1016/j.mfglet.2020.07.007>.
- [172] D. Powell, A.E.W. Rennie, L. Geekie, N. Burns, Understanding powder degradation in metal additive manufacturing to allow the upcycling of recycled powders, *J. Clean. Prod.* 268 (2020) 122077. <https://doi.org/10.1016/j.jclepro.2020.122077>.
- [173] M.J. Heiden, L.A. Deibler, J.M. Rodelas, J.R. Koepke, D.J. Tung, D.J. Saiz, B.H. Jared, Evolution of 316L stainless steel feedstock due to laser powder bed fusion process, *Addit. Manuf.* 25 (2019) 84–103. <https://doi.org/10.1016/j.addma.2018.10.019>.
- [174] P.A. Carroll, A.J. Pinkerton, J. Allen, W.U.H. Syed, H.K. Sezer, P. Brown, G. Ng, R. Scudamore, L. Li, The effect of powder recycling in direct metal laser deposition on powder and manufactured part characteristics, in: *Proc. AVT-139 Spec. Meet. Cost Eff. Manuf. via Net Shape Process. NATO Res. Technol. Organ.*, 2006: pp. 1–8. <http://eprints.lancs.ac.uk/59645/>.
- [175] A. Leicht, M. V. Sundaram, E. Hryha, L. Nyborg, M. Ahlfors, L.-E. Rännar, A. Koptuyug, K. Frisk, As-HIP Microstructure of EBM Fabricated Shell Components, in: *World Powder Metall. 2016 Congr. Exhib., Hamburg; Germany, 2016*. <https://www.epma.com/publications/euro-pm-proceedings/product/ep16-3297141>.
- [176] K. Vutova, V. Vassileva, Electron-Beam Melting and Reuse of Metallic Materials, *Met. Sci. Heat Treat.* 62 (2020) 345–348. <https://doi.org/10.1007/s11041-020-00566-5>.
- [177] K. Vutova, V. Vassileva, E. Koleva, N. Munirathnam, D.P. Amalnerkar, T. Tanaka, Investigation of tantalum recycling by electron beam melting, *Metals (Basel)*. 6 (2016) 19–21. <https://doi.org/10.3390/met6110287>.
- [178] K. Vutova, V. Vassileva, V. Stefanova, D. Amalnerkar, T. Tanaka, Effect of electron beam method on processing of titanium technogenic material, *Metals (Basel)*. 9 (2019) 1–9. <https://doi.org/10.3390/met9060683>.

- [179] S. Singh, S. Ramakrishna, R. Singh, Material issues in additive manufacturing: A review, *J. Manuf. Process.* 25 (2017) 185–200. <https://doi.org/10.1016/J.JMAPRO.2016.11.006>. 1665  
1666
- [180] Y. Oh, C. Zhou, S. Behdad, Part decomposition and assembly-based (Re) design for additive manufacturing: A review, *Addit. Manuf.* 22 (2018) 230–242. <https://doi.org/10.1016/j.addma.2018.04.018>. 1667  
1668
- [181] A. Mitchell, U. Lafont, M. Hołyńska, C. Semprimoschnig, Additive manufacturing — A review of 4D printing and future applications, *Addit. Manuf.* 24 (2018) 606–626. <https://doi.org/10.1016/j.addma.2018.10.038>. 1669  
1670
- [182] L. Yan, Y. Chen, F. Liou, Additive manufacturing of functionally graded metallic materials using laser metal deposition, *Addit. Manuf.* 31 (2020). <https://doi.org/10.1016/j.addma.2019.100901>. 1671  
1672
- [183] P.C. Collins, L.J. Bond, H. Taheri, T.A. Bigelow, M.R.B.M. Shoaib, L.W. Koester, Powder-based additive manufacturing - a review of types of defects, generation mechanisms, detection, property evaluation and metrology, *Int. J. Addit. Subtractive Mater. Manuf.* 1 (2017) 172. <https://doi.org/10.1504/ijasmm.2017.10009247>. 1673  
1674  
1675
- [184] M. Yakout, M.A. Elbestawi, S.C. Veldhuis, A review of metal additive manufacturing technologies, *Solid State Phenom.* 278 SSP (2018) 1–14. <https://doi.org/10.4028/www.scientific.net/SSP.278.1>. 1676  
1677
- [185] D. Klobčar, J. Tušek, B. Taljat, L. Kosec, M. Muhič, Suitability of maraging steel weld cladding for repair of die casting tooling Part II: Influence of ageing during aluminium alloy die casting on maraging steel weld microstructure, mechanical properties and crack growth, *Int. J. Mater. Res.* 99 (2008). <https://doi.org/10.3139/146.101733>. 1678  
1679  
1680
- [186] D. Klobčar, J. Tušek, L. Kosec, Suitability of maraging steel weld cladding for repair of die-casting tooling: Part I: Influence of welding and aging heat treatment on 18 % Ni maraging steel weld microstructure and mechanical properties, *Int. J. Mater. Res.* 100 (2009). <https://doi.org/10.3139/146.110078>. 1681  
1682  
1683
- [187] M. Pleterski, J. Tušek, D. Klobčar, L. Kosec, M. Muhič, The influence of laser pulse shape in repair welding of tool steels, in: *ICALEO 2009 - 28th Int. Congr. Appl. Lasers Electro-Optics, Congr. Proc.*, 2009. 1684  
1685
- [188] A. Katz-Demyanetz, V. Popov, A. Kovalevsky, D. Safranchik, A. Koptyug, Powder-bed additive manufacturing for aerospace application: Techniques, metallic and metal/ceramic composite materials and trends, *Manuf. Rev.* 6 (2019) 5. <https://doi.org/10.1051/mfreview/2019003>. 1686  
1687  
1688
- [189] B. Dutta, S. Palaniswamy, J. Choi, L.J. Song, J. Mazumder, Additive Manufacturing by Direct Metal Deposition, *Adv. Mater. Process.* (2011) 33–36. [www.asminternational.org/heattreat](http://www.asminternational.org/heattreat). 1689  
1690
- [190] P. Yadav, Z. Fu, M. Knorr, N. Travitzky, Binder Jetting 3D Printing of Titanium Aluminides Based Materials: A Feasibility Study, *Adv. Eng. Mater.* n/a (2020) 2000408. <https://doi.org/10.1002/adem.202000408>. 1691  
1692
- [191] J.J.S. Dilip, H. Miyanaji, A. Lassell, T.L. Starr, B. Stucker, A novel method to fabricate TiAl intermetallic alloy 3D parts using additive manufacturing, *Def. Technol.* 13 (2017) 72–76. <https://doi.org/10.1016/j.dt.2016.08.001>. 1693  
1694
- [192] N.J. Harrison, I. Todd, K. Mumtaz, Reduction of micro-cracking in nickel superalloys processed by Selective Laser Melting: A fundamental alloy design approach, *Acta Mater.* 94 (2015) 59–68. <https://doi.org/10.1016/j.actamat.2015.04.035>. 1695  
1696
- [193] E. Hosseini, V.A. Popovich, A review of mechanical properties of additively manufactured Inconel 718, *Addit. Manuf.* 30 (2019) 100877. <https://doi.org/10.1016/j.addma.2019.100877>. 1697  
1698
- [194] F. Liu, F. Lyu, F. Liu, X. Lin, C. Huang, Laves phase control of inconel 718 superalloy fabricated by laser direct energy deposition via  $\delta$  aging and solution treatment, *J. Mater. Res. Technol.* 9 (2020) 9753–9765. <https://doi.org/10.1016/j.jmrt.2020.06.061>. 1699  
1700  
1701
- [195] A. Mostafaei, Y. Behnamian, Y.L. Krimer, E.L. Stevens, J.L. Luo, M. Chmielus, Effect of solutionizing and aging on the microstructure and mechanical properties of powder bed binder jet printed nickel-based superalloy 625, *Mater. Des.* 111 (2016) 482–491. <https://doi.org/10.1016/j.matdes.2016.08.083>. 1702  
1703  
1704
- [196] M. Turker, D. Godlinski, F. Petzoldt, Effect of production parameters on the properties of IN 718 superalloy by three-dimensional printing, *Mater. Charact.* 59 (2008) 1728–1735. <https://doi.org/10.1016/j.matchar.2008.03.017>. 1705  
1706

- [197] P.M. Angelopoulos, M. Samouhos, M. Taxiarchou, Functional fillers in composite filaments for fused filament fabrication; a review, *Mater. Today Proc.* (2020). <https://doi.org/10.1016/j.matpr.2020.07.069>. 1707  
1708
- [198] D. Saltzman, M. Bichnevicius, S. Lynch, T.W. Simpson, E.W. Reutzel, C. Dickman, R. Martukanitz, Design and evaluation of an additively manufactured aircraft heat exchanger, *Appl. Therm. Eng.* 138 (2018) 254–263. 1709  
<https://doi.org/10.1016/j.applthermaleng.2018.04.032>. 1710  
1711
- [199] H.T. Fujii, M.R. Sriraman, S.S. Babu, Quantitative Evaluation of Bulk and Interface Microstructures in Al-3003 Alloy Builds Made by Very High Power Ultrasonic Additive Manufacturing, *Metall. Mater. Trans. A.* 42 (2011) 4045–4055. 1712  
<https://doi.org/10.1007/s11661-011-0805-x>. 1713  
1714
- [200] Y. Zhang, X. He, S. Du, J. Zhang, Al<sub>2</sub>O<sub>3</sub> Ceramics Preparation by LOM (Laminated Object Manufacturing), *Int. J. Adv. Manuf. Technol.* 17 (2001) 531–534. <https://doi.org/10.1007/s001700170154>. 1715  
1716
- [201] P. Frigola, O. Harrysson, T. Horn, H. West, R. Aman, J. Rigsbee, D. Ramirez, F. Medina, R. Wicker, E. Rodriguez, Fabricating Copper Components, *Adv. Mater. Process.* (2014) 20. 1717  
1718
- [202] S. Scudino, C. Unterdörfer, K.G. Prashanth, H. Attar, N. Ellendt, V. Uhlenwinkel, J. Eckert, Additive manufacturing of Cu-10Sn bronze, *Mater. Lett.* 156 (2015) 202–204. <https://doi.org/10.1016/j.matlet.2015.05.076>. 1719  
1720
- [203] C. Silbernagel, L. Gargalis, I. Ashcroft, R. Hague, M. Galea, P. Dickens, Electrical resistivity of pure copper processed by medium-powered laser powder bed fusion additive manufacturing for use in electromagnetic applications, *Addit. Manuf.* 29 (2019) 100831. <https://doi.org/10.1016/j.addma.2019.100831>. 1721  
1722  
1723
- [204] Q. Wang, J.A. Jackson, Q. Ge, J.B. Hopkins, C.M. Spadaccini, N.X. Fang, Lightweight Mechanical Metamaterials with Tunable Negative Thermal Expansion, *Phys. Rev. Lett.* 117 (2016) 175901. <https://doi.org/10.1103/PhysRevLett.117.175901>. 1724  
1725
- [205] B. Yun, W.C. B, An exploration of binder jetting of copper, *Rapid Prototyp. J.* 21 (2015) 177–185. <https://doi.org/10.1108/RPJ-12-2014-0180>. 1726  
1727
- [206] H. Miyajima, D. Ma, M.A. Atwater, K.A. Darling, V.H. Hammond, C.B. Williams, Binder jetting additive manufacturing of copper foam structures, *Addit. Manuf.* 32 (2020). <https://doi.org/10.1016/j.addma.2019.100960>. 1728  
1729
- [207] R. Karunakaran, S. Ortgies, A. Tamayol, F. Bobaru, M.P. Sealy, Additive manufacturing of magnesium alloys, *Bioact. Mater.* 5 (2020) 44–54. <https://doi.org/10.1016/j.bioactmat.2019.12.004>. 1730  
1731
- [208] H. Hyer, L. Zhou, G. Benson, B. McWilliams, K. Cho, Y. Sohn, Additive manufacturing of dense WE43 Mg alloy by laser powder bed fusion, *Addit. Manuf.* 33 (2020) 101123. <https://doi.org/10.1016/j.addma.2020.101123>. 1732  
1733
- [209] R.S. Khmyrov, V.A. Safronov, A. V Gusarov, Obtaining Crack-free WC-Co Alloys by Selective Laser Melting, *Phys. Procedia.* 83 (2016) 874–881. <https://doi.org/10.1016/j.phpro.2016.08.091>. 1734  
1735
- [210] W. Jeong, Y.-S. Kwon, D. Kim, Three-dimensional printing of tungsten structures by directed energy deposition, *Mater. Manuf. Process.* 34 (2019) 986–992. <https://doi.org/10.1080/10426914.2019.1594253>. 1736  
1737
- [211] C. Huber, C. Abert, F. Bruckner, M. Groenefeld, S. Schuschnigg, I. Teliban, C. Vogler, G. Wautischer, R. Windl, Di. Suess, 3D Printing of Polymer-Bonded Rare-Earth Magnets with a Variable Magnetic Compound Fraction for a Predefined Stray Field, *Sci. Rep.* 7 (2017) 1–8. <https://doi.org/10.1038/s41598-017-09864-0>. 1738  
1739  
1740
- [212] H.A. Khazdozian, J.S. Manzano, K. Gandha, I.I. Slowing, I.C. Nlebedim, Recycled Sm-Co bonded magnet filaments for 3D printing of magnets, *AIP Adv.* 8 (2018). <https://doi.org/10.1063/1.5007669>. 1741  
1742
- [213] T. Kolb, F. Huber, B. Akbulut, C. Donocik, N. Urban, D. Maurer, J. Franke, Laser Beam Melting of NdFeB for the production of rare-earth magnets, 2016 6th Int. Electr. Drives Prod. Conf. EDPC 2016 - Proc. (2016) 34–40. 1743  
<https://doi.org/10.1109/EDPC.2016.7851311>. 1744  
1745
- [214] C. Huber, G. Mitterramskogler, M. Goertler, I. Teliban, M. Groenefeld, D. Suess, Additive manufactured isotropic NdFeB magnets by stereolithography, fused filament fabrication, and selective laser sintering, *ArXiv.* 1 (2019) 1–6. 1746  
1747
- [215] L. Li, A. Tirado, B.S. Conner, M. Chi, A.M. Elliott, O. Rios, H. Zhou, M.P. Paranthaman, A novel method combining 1748

- additive manufacturing and alloy infiltration for NdFeB bonded magnet fabrication, *J. Magn. Mater.* 438 (2017) 163–1749  
167. <https://doi.org/10.1016/j.jmmm.2017.04.066>. 1750
- [216] F. Liravi, E. Toyserkani, Additive manufacturing of silicone structures: A review and prospective, *Addit. Manuf.* 24 (2018) 1751  
232–242. <https://doi.org/10.1016/j.addma.2018.10.002>. 1752
- [217] C.S. Ramesh, C.K. Srinivas, Friction and wear behavior of laser-sintered iron-silicon carbide composites, *J. Mater. Process. Technol.* 209 (2009) 5429–5436. <https://doi.org/10.1016/j.jmatprotec.2009.04.018>. 1753  
1754
- [218] L. Weisensel, N. Travitzky, H. Sieber, P. Greil, Laminated Object Manufacturing (LOM) of SiSiC Composites, *Adv. Eng. Mater.* 6 (2004) 899–903. <https://doi.org/https://doi.org/10.1002/adem.200400112>. 1755  
1756
- [219] A. Fleisher, D. Zolotaryov, A. Kovalevsky, G. Muller-Kamskii, E. Eshed, M. Kazakin, V. Popov, Reaction bonding of silicon carbides by Binder Jet 3D-Printing, phenolic resin binder impregnation and capillary liquid silicon infiltration, *Ceram. Int.* 45 (2019) 18023–18029. <https://doi.org/10.1016/j.ceramint.2019.06.021>. 1757  
1758  
1759
- [220] U.E. Klotz, D. Tiberto, F. Held, Optimization of 18-karat yellow gold alloys for the additive manufacturing of jewelry and watch parts, *Gold Bull.* 50 (2017) 111–121. <https://doi.org/10.1007/s13404-017-0201-4>. 1760  
1761
- [221] M. Khan, P. Dickens, Selective Laser Melting (SLM) of pure gold, *Gold Bull.* 43 (2010) 114–121. 1762  
<https://doi.org/10.1007/BF03214976>. 1763
- [222] Z. Wang, S.Y. Tang, S. Scudino, Y.P. Ivanov, R.T. Qu, D. Wang, C. Yang, W.W. Zhang, A.L. Greer, J. Eckert, K.G. Prashanth, Additive manufacturing of a martensitic Co–Cr–Mo alloy: Towards circumventing the strength–ductility trade-off, *Addit. Manuf.* (2020) 101725. <https://doi.org/10.1016/j.addma.2020.101725>. 1764  
1765  
1766
- [223] A. Mostafaei, J. V Gordon, A.D. Rollett, Additive Manufacturing of Cobalt Alloys, *Addit. Manuf. Process.* 24 (2020) 0. 1767  
<https://doi.org/10.31399/asm.hb.v24.a0006573>. 1768
- [224] M.A. Surmeneva, A. Koptuyg, D. Khrapov, Y.F. Ivanov, T. Mishurova, S. Evsevlev, O. Prymak, K. Loza, M. Epple, G. Bruno, R.A. Surmenev, In situ synthesis of a binary Ti–10at% Nb alloy by electron beam melting using a mixture of elemental niobium and titanium powders, *J. Mater. Process. Technol.* 282 (2020) 116646. 1769  
1770  
1771  
<https://doi.org/10.1016/j.jmatprotec.2020.116646>. 1772
- [225] C. Sungail, A.D. Abid, Additive manufacturing of tantalum – A study of chemical and physical properties of printed tantalum, *Met. Powder Rep.* 75 (2020) 28–33. <https://doi.org/10.1016/j.mprp.2019.03.001>. 1773  
1774
- [226] H. Miyanaji, J.M. Akbar, L. Yang, Fabrication and characterization of Graphite / Nylon 12 composite via binder Jetting additive manufacturing, in: *Proc. 28th Annu. Int. Solid Free. Fabr. Symp. – An Addit. Manuf. Conf.*, 2017: pp. 593–604. 1775  
1776
- [227] V.V. Popov, A. Fleisher, Hybrid additive manufacturing of steels and alloys, *Manuf. Rev.* 7, 6 (2020) 6. 1777  
<https://doi.org/10.1051/mfreview/2020005>. 1778
- [228] S.Z. Chavoshi, S. Goel, P. Morantz, Current trends and future of sequential micro-machining processes on a single machine tool, *Mater. Des.* 127 (2017) 37–53. <https://doi.org/https://doi.org/10.1016/j.matdes.2017.04.057>. 1779  
1780
- [229] M. Godec, S. Malej, D. Feizpour, Č. Donik, M. Balažic, D. Klobčar, L. Pambaguian, M. Conradi, A. Kocijan, Hybrid additive manufacturing of Inconel 718 for future space applications, *Mater. Charact.* 172 (2021) 110842. 1781  
1782  
<https://doi.org/10.1016/j.matchar.2020.110842>. 1783
- [230] Y. Li, Q. Han, I. Horváth, G. Zhang, Repairing surface defects of metal parts by groove machining and wire + arc based filling, *J. Mater. Process. Technol.* 274 (2019) 116268. <https://doi.org/10.1016/j.jmatprotec.2019.116268>. 1784  
1785
- [231] M. Praniewicz, T. Kurfess, C. Saldana, Adaptive geometry transformation and repair for hybrid manufacturing, in: *Procedia Manuf.*, Elsevier, 2018: pp. 228–236. <https://doi.org/10.1016/J.PROMFG.2018.07.031>. 1786  
1787
- [232] D. Herzog, V. Seyda, E. Wycisk, C. Emmelmann, Additive manufacturing of metals, *Acta Mater.* 117 (2016) 371–392. 1788  
<https://doi.org/10.1016/j.actamat.2016.07.019>. 1789
- [233] N. Guo, M.C. Leu, Additive manufacturing: Technology, applications and research needs, *Front. Mech. Eng.* 8 (2013) 215–1790



243. <https://doi.org/10.1007/s11465-013-0248-8>. 1791
- [234] I. Gibson, D. Rosen, B. Stucker, Additive manufacturing technologies: 3D printing, rapid prototyping, and direct digital manufacturing, second edition, 2015. <https://doi.org/10.1007/978-1-4939-2113-3>. 1792
- [235] A.A. Shapiro, J.P. Borgonia, Q.N. Chen, R.P. Dillon, B. McEnerney, R. Polit-Casillas, L. Soloway, Additive manufacturing for aerospace flight applications, *J. Spacecr. Rockets*. 53 (2016) 952–959. <https://doi.org/10.2514/1.A33544>. 1793
- [236] G.B. Kannan, D.K. Rajendran, A Review on Status of Research in Metal Additive Manufacturing BT - Advances in 3D Printing & Additive Manufacturing Technologies, in: D.I. Wimpenny, P.M. Pandey, L.J. Kumar (Eds.), Springer Singapore, Singapore, 2017: pp. 95–100. [https://doi.org/10.1007/978-981-10-0812-2\\_8](https://doi.org/10.1007/978-981-10-0812-2_8). 1794
- [237] A. Katz-Demyanetz, A. Koptuyug, V. V Popov, In-situ Alloying as a Novel Methodology in Additive Manufacturing, in: 2020 IEEE 10th Int. Conf. Nanomater. Appl. Prop., 2020: pp. 02SAMA05-1-02SAMA05-4. <https://doi.org/10.1109/NAP51477.2020.9309652>. 1795
- [238] S. Liu, Y.C. Shin, Additive manufacturing of Ti6Al4V alloy: A review, *Mater. Des.* 164 (2019) 107552. <https://doi.org/10.1016/j.matdes.2018.107552>. 1796
- [239] B. Vrancken, L. Thijs, J.-P. Kruth, J. Van Humbeeck, Microstructure and mechanical properties of a novel  $\beta$  titanium metallic composite by selective laser melting, *Acta Mater.* 68 (2014) 150–158. <https://doi.org/10.1016/j.actamat.2014.01.018>. 1797
- [240] T.C. Dzugbewu, I. Yadroitsev, P. Krakhmalev, I. Yadroitsava, A. Du Plessis, Optimal process parameters for in-situ alloyed Ti15Mo structures by Direct Metal Laser Sintering, in: SSF 2017-The 28th Annu. Int. Solid Free. Fabr. Symp. Austin, August 7-9, 2017., University of Texas, Austin, 2017: pp. 75–96. 1798
- [241] I. Yadroitsev, P. Krakhmalev, I. Yadroitsava, Titanium Alloys Manufactured by In Situ Alloying During Laser Powder Bed Fusion, *JOM*. 69 (2017) 2725–2730. <https://doi.org/10.1007/s11837-017-2600-7>. 1799
- [242] M. Fischer, D. Joguet, G. Robin, L. Peltier, P. Laheurte, In situ elaboration of a binary Ti–26Nb alloy by selective laser melting of elemental titanium and niobium mixed powders, *Mater. Sci. Eng. C*. 62 (2016) 852–859. <https://doi.org/10.1016/j.msec.2016.02.033>. 1800
- [243] W. Li, X. Chen, L. Yan, J. Zhang, X. Zhang, F. Liou, Additive manufacturing of a new Fe–Cr–Ni alloy with gradually changing compositions with elemental powder mixes and thermodynamic calculation, *Int. J. Adv. Manuf. Technol.* 95 (2018) 1013–1023. <https://doi.org/10.1007/s00170-017-1302-1>. 1801
- [244] W. Li, L. Yan, S. Karnati, F. Liou, J. Newkirk, K.M.B. Taminger, W.J. Seufzer, Ti–Fe intermetallics analysis and control in joining titanium alloy and stainless steel by Laser Metal Deposition, *J. Mater. Process. Technol.* 242 (2017) 39–48. <https://doi.org/10.1016/j.jmatprotec.2016.11.010>. 1802
- [245] W. Li, S. Karnati, C. Kriewall, F. Liou, J. Newkirk, K.M. Brown Taminger, W.J. Seufzer, Fabrication and characterization of a functionally graded material from Ti–6Al–4V to SS316 by laser metal deposition, *Addit. Manuf.* 14 (2017) 95–104. <https://doi.org/10.1016/j.addma.2016.12.006>. 1803
- [246] K. Shah, I. Haq, A. ul Khan, S.A. Shah, M. Khan, A.J. Pinkerton, Parametric study of development of Inconel–steel functionally graded materials by laser direct metal deposition, *Mater. Des.* 54 (2014) 531–538. <https://doi.org/10.1016/j.matdes.2013.08.079>. 1804
- [247] A. Hinojos, J. Mireles, A. Reichardt, P. Frigola, P. Hosemann, L.E. Murr, R.B. Wicker, Joining of Inconel 718 and 316 Stainless Steel using electron beam melting additive manufacturing technology, *Mater. Des.* 94 (2016) 17–27. <https://doi.org/10.1016/j.matdes.2016.01.041>. 1805
- [248] J.W. Yeh, S.K. Chen, S.J. Lin, J.Y. Gan, T.S. Chin, T.T. Shun, C.H. Tsau, S.Y. Chang, Nanostructured high-entropy alloys with multiple principal elements: Novel alloy design concepts and outcomes, *Adv. Eng. Mater.* 6 (2004) 299–303. <https://doi.org/10.1002/adem.200300567>. 1806
- [249] O.N. Senkov, G.B. Wilks, J.M. Scott, D.B. Miracle, Mechanical properties of Nb25Mo25Ta25W25 and 1807

- V<sub>20</sub>Nb<sub>20</sub>Mo<sub>20</sub>Ta<sub>20</sub>W<sub>20</sub> refractory high entropy alloys, *Intermetallics*. 19 (2011) 698–706. 1833  
<https://doi.org/10.1016/j.intermet.2011.01.004>. 1834
- [250] O.N. Senkov, S.V. Senkova, C. Woodward, D.B. Miracle, Low-density, refractory multi-principal element alloys of the Cr–Nb–Ti–V–Zr system: Microstructure and phase analysis, *Acta Mater.* 61 (2013) 1545–1557. 1835  
<https://doi.org/10.1016/J.ACTAMAT.2012.11.032>. 1837
- [251] O.N. Senkov, J.M. Scott, S. V. Senkova, D.B. Miracle, C.F. Woodward, Microstructure and room temperature properties of a high-entropy TaNbHfZrTi alloy, *J. Alloys Compd.* 509 (2011) 6043–6048. <https://doi.org/10.1016/j.jallcom.2011.02.171>. 1838
- [252] O.N. Senkov, S. V. Senkova, C. Woodward, Effect of aluminum on the microstructure and properties of two refractory high-entropy alloys, *Acta Mater.* 68 (2014) 214–228. <https://doi.org/10.1016/j.actamat.2014.01.029>. 1840
- [253] E. Eshed, N. Larianovsky, A. Kovalevsky, V. Popov, I.I. Gorbachev, V. Popov, A. Katz-Demyanetz, Microstructural evolution and phase formation in 2nd-generation refractory-based high entropy alloys, *Materials (Basel)*. 11 (2018). 1842  
<https://doi.org/10.3390/ma11020175>. 1844
- [254] N. Larianovsky, A. Katz-Demyanetz, E. Eshed, M. Regev, Microstructure, tensile and creep properties of Ta<sub>20</sub>Nb<sub>20</sub>Hf<sub>20</sub>Zr<sub>20</sub>Ti<sub>20</sub> high entropy alloy, *Materials (Basel)*. 10 (2017). <https://doi.org/10.3390/ma10080883>. 1845
- [255] E. Eshed, N. Larianovsky, A. Kovalevsky, A. Katz Demyanetz, Effect of Zr on the Microstructure of Second- and Third-Generation BCC HEAs, *JOM*. 71 (2019) 673–682. <https://doi.org/10.1007/s11837-018-3198-0>. 1847
- [256] A. Katz-Demyanetz, I.I. Gorbachev, E. Eshed, V. V Popov, V. V Popov, M. Bamberger, High entropy Al<sub>0.5</sub>CrMoNbTa<sub>0.5</sub> alloy: Additive manufacturing vs. casting vs. CALPHAD approval calculations, *Mater. Charact.* 167 (2020) 110505. 1849  
<https://doi.org/10.1016/j.matchar.2020.110505>. 1851
- [257] S. Goel, M. Knaggs, G. Goel, X.W. Zhou, H.M. Upadhyaya, V.K. Thakur, V. Kumar, G. Bizarri, A. Tiwari, A. Murphy, A. Stukowski, A. Matthews, Horizons of modern molecular dynamics simulation in digitalized solid freeform fabrication with advanced materials, *Mater. Today Chem.* 18 (2020) 100356. <https://doi.org/https://doi.org/10.1016/j.mtchem.2020.100356>. 1852
- [258] J.J. Marattukalam, V. Pacheco, D. Karlsson, L. Riekehr, J. Lindwall, F. Forsberg, U. Jansson, M. Sahlberg, B. Hjörvarsson, Development of process parameters for selective laser melting of a Zr-based bulk metallic glass, *Addit. Manuf.* 33 (2020) 101124. <https://doi.org/10.1016/j.addma.2020.101124>. 1855
- [259] P. Bordeenithikasem, M. Stolpe, A. Elsen, D.C. Hofmann, Glass forming ability, flexural strength, and wear properties of additively manufactured Zr-based bulk metallic glasses produced through laser powder bed fusion, *Addit. Manuf.* 21 (2018) 312–317. <https://doi.org/10.1016/j.addma.2018.03.023>. 1858
- [260] P. Gargarella, A. Almeida, R. Vilar, C.R.M. Afonso, S. Peripolli, C.T. Rios, C. Bolfarini, W.J. Botta, C.S. Kiminami, Formation of Fe-based glassy matrix composite coatings by laser processing, *Surf. Coatings Technol.* 240 (2014) 336–343. 1861  
<https://doi.org/10.1016/j.surfcoat.2013.12.049>. 1863
- [261] Z. Mahbooba, L. Thorsson, M. Unosson, P. Skoglund, H. West, T. Horn, C. Rock, E. Vogli, O. Harrysson, Additive manufacturing of an iron-based bulk metallic glass larger than the critical casting thickness, *Appl. Mater. Today*. 11 (2018) 264–269. <https://doi.org/10.1016/j.apmt.2018.02.011>. 1864
- [262] A. Koptuyug, L.-E. Rännar, M. Bäckström, R. Langlet, Bulk Metallic Glass Manufacturing Using Electron Beam Melting, in: *Int. Conf. Addit. Manuf. 3D Print.*, Nottingham, UK, 2013. <http://urn.kb.se/resolve?urn=urn:nbn:se:miun:diva-20588>. 1867
- [263] X. Li, Additive Manufacturing of Advanced Multi-Component Alloys: Bulk Metallic Glasses and High Entropy Alloys, *Adv. Eng. Mater.* 20 (2018) 1–18. <https://doi.org/10.1002/adem.201700874>. 1869
- [264] V. Ocelík, N. Janssen, S.N. Smith, J.T.M. De Hosson, Additive Manufacturing of High-Entropy Alloys by Laser Processing, *JOM*. 68 (2016) 1810–1818. <https://doi.org/10.1007/s11837-016-1888-z>. 1871
- [265] C. Haase, F. Tang, M.B. Wilms, A. Weisheit, B. Hallstedt, Combining thermodynamic modeling and 3D printing of elemental powder blends for high-throughput investigation of high-entropy alloys – Towards rapid alloy screening and 1874

- design, *Mater. Sci. Eng. A.* 688 (2017) 180–189. <https://doi.org/10.1016/J.MSEA.2017.01.099>. 1875
- [266] H. Dobbstein, M. Thiele, E.L. Gurevich, E.P. George, A. Ostendorf, Direct Metal Deposition of Refractory High Entropy Alloy MoNbTaW, in: *Phys. Procedia*, 2016: pp. 624–633. <https://doi.org/10.1016/j.phpro.2016.08.065>. 1876  
1877
- [267] J. Joseph, T. Jarvis, X. Wu, N. Stanford, P. Hodgson, D.M. Fabijanic, Comparative study of the microstructures and mechanical properties of direct laser fabricated and arc-melted AlxCoCrFeNi high entropy alloys, *Mater. Sci. Eng. A.* 633 (2015) 184–193. <https://doi.org/10.1016/j.msea.2015.02.072>. 1878  
1879  
1880
- [268] N. Kalentics, A. Burn, M. Cloots, R.E. Logé, 3D laser shock peening as a way to improve geometrical accuracy in selective laser melting, *Int. J. Adv. Manuf. Technol.* 101 (2019) 1247–1254. <https://doi.org/10.1007/s00170-018-3033-3>. 1881  
1882
- [269] N. Kalentics, E. Boillat, P. Peyre, C. Gorny, C. Kenel, C. Leinenbach, J. Jhabvala, R.E. Logé, 3D Laser Shock Peening – A new method for the 3D control of residual stresses in Selective Laser Melting, *Mater. Des.* 130 (2017) 350–356. <https://doi.org/10.1016/j.matdes.2017.05.083>. 1883  
1884  
1885
- [270] P. Mercelis, J.P. Kruth, Residual stresses in selective laser sintering and selective laser melting, *Rapid Prototyp. J.* 12 (2006) 254–265. <https://doi.org/10.1108/13552540610707013>. 1886  
1887
- [271] N. Kalentics, R. Loge, E. Boillat, Method and Device for implementing laser shock peening or warm laser shock peening during selective laser melting, 2017/0087670670 A1, 2017. 1888  
1889
- [272] N. Kalentics, M.O. V. de Seijas, S. Griffiths, C. Leinenbach, R.E. Logé, 3D laser shock peening – A new method for improving fatigue properties of selective laser melted parts, *Addit. Manuf.* 33 (2020) 101112. <https://doi.org/10.1016/j.addma.2020.101112>. 1890  
1891  
1892
- [273] N. Kalentics, K. Huang, M. Ortega Varela de Seijas, A. Burn, V. Romano, R.E. Logé, Laser shock peening: A promising tool for tailoring metallic microstructures in selective laser melting, *J. Mater. Process. Technol.* 266 (2019) 612–618. <https://doi.org/10.1016/j.jmatprotec.2018.11.024>. 1893  
1894  
1895
- [274] N. Kalentics, N. Sohrabi, H.G. Tabasi, S. Griffiths, J. Jhabvala, C. Leinenbach, A. Burn, R.E. Logé, Healing cracks in selective laser melting by 3D laser shock peening, *Addit. Manuf.* 30 (2019) 100881. <https://doi.org/10.1016/j.addma.2019.100881>. 1896  
1897  
1898