



TITLE:

# Anomalously Large Formula Unit Volume and Its Effect on the Thermal Behavior of LiBF

AUTHOR(S):

Matsumoto, Kazuhiko; Hagiwara, Rika; Mazej, Zoran; Goreshnik, Evgeny; emva, Boris

---

CITATION:

Matsumoto, Kazuhiko ...[et al]. Anomalously Large Formula Unit Volume and Its Effect on the Thermal Behavior of LiBF. The Journal of Physical Chemistry B 2006, 110(5): 2138-2141

ISSUE DATE:

2006-02-01

URL:

<http://hdl.handle.net/2433/260596>

RIGHT:

This document is the Accepted Manuscript version of a Published Work that appeared in final form in The Journal of Physical Chemistry B, copyright © American Chemical Society after peer review and technical editing by the publisher. To access the final edited and published work see <https://doi.org/10.1021/jp0564795>; This is not the published version. Please cite only the published version.; この論文は出版社版ではありません。引用の際には出版社版をご確認ください。

# Anomalously large formula unit volume and its effect on the thermal behavior of $\text{LiBF}_4$

*Kazuhiko Matsumoto,<sup>†</sup> Rika Hagiwara, \*<sup>†</sup>Zoran Mazej,<sup>‡</sup> Evgeny Goreshnik,<sup>‡</sup> Boris Žemva,<sup>‡</sup>*

Department of Fundamental Energy Science, Kyoto University, Yoshida, Sakyo-ku, Kyoto 606-8501,  
Japan, and Department of Inorganic Chemistry and Technology, Jožef Stefan Institute, Jamova 39,  
SI-1000 Ljubljana, Slovenia

[hagiwara@energy.kyoto-u.ac.jp](mailto:hagiwara@energy.kyoto-u.ac.jp)

RECEIVED DATE

\* To whom correspondence should be addressed. E-mail: [hagiwara@energy.kyoto-u.ac.jp](mailto:hagiwara@energy.kyoto-u.ac.jp). Tel: +81-75-753-5822. Fax: +81-75-753-5906. <sup>†</sup> Department of Fundamental Energy Science, Kyoto University. <sup>‡</sup> Jožef Stefan Institute.

**Abstract.** Crystal structure of  $\text{LiBF}_4$  has been determined by single-crystal X-ray diffraction.  $\text{LiBF}_4$  crystallizes as a merohedral twin in the trigonal space group  $P3_121$  with  $a = 4.892(5) \text{ \AA}$ ,  $c = 11.002(12) \text{ \AA}$ ,  $V = 228.0(4) \text{ \AA}^3$ ,  $Z = 3$  at 200 K. The twin is generated by a twofold rotation about  $[1 \bar{1} 0]$  direction. Lithium cation is coordinated by four fluorine atoms in a distorted tetrahedral manner, where two Li-F distances of 1.862(5) and 1.846(5)  $\text{ \AA}$  are observed. The formula unit volume ( $FUV = V / Z$ ) of 77.9  $\text{ \AA}^3$  for  $\text{LiBF}_4$  at 298 K is considerably larger than 72.7  $\text{ \AA}^3$  for  $\text{NaBF}_4$  and 72.5  $\text{ \AA}^3$  for  $\text{AgBF}_4$  in spite of the smaller size of  $\text{Li}^+$ , indicating a loose ionic packing of  $\text{LiBF}_4$ . Thermodynamic evaluation of the decomposition temperature for  $\text{LiBF}_4$  is performed by using the empirical relationship between the standard entropy and FUV obtained. The result indicates that the large FUV of  $\text{LiBF}_4$  contributes to its higher decomposition temperature than that of  $\text{LiPF}_6$ .

## Introduction

Lithium salts are now widely used for supporting electrolytes of primary and secondary lithium batteries.<sup>1</sup> Crystal structures of lithium salts give some hints to understand their physical properties including the coordination environment around the lithium cation in the solution.<sup>2</sup> Description of the structures of some lithium hexafluoro-complex ( $\text{LiAF}_6$ ) salts have been seen in the literatures since 1956 and they have been compared with a series of other alkali metal and silver hexafluoro-complex salts. All the  $\text{LiAF}_6$ -type ( $A = \text{P, V, As, Nb, Mo, Ru, Rh, Sb, Ta, W, Re, Os, Ir, Pt}$  and  $\text{Au}$ ) salts exhibit rhombohedral symmetry and are isostructural with each other.<sup>3-7</sup> The structure of  $\text{LiClO}_4$  which crystallizes into an orthorhombic space group was determined in a recent report.<sup>8</sup> Lithium salts of bulky anions such as  $\text{CF}_3\text{SO}_3^-$  and  $\text{N}(\text{SO}_2\text{CF}_3)_2^-$  are also structurally characterized from their powder diffraction data.<sup>9,10</sup>

Although  $\text{LiBF}_4$  is known as one of the common electrolytes for lithium batteries and the large number of reports are available on the structures of other  $\text{MBF}_4$ -type ( $M = \text{univalent cation}$ ) salts,<sup>11-15</sup> all the attempts to determine the crystal structure of  $\text{LiBF}_4$  have been unsuccessful.<sup>15-17</sup>

In this study, we report the first successful results of the crystal structure determination of  $\text{LiBF}_4$ . Thermal behavior of lithium salts has been investigated in relation to the drying process of the salts at elevated temperatures. According to previous reports,  $\text{LiBF}_4$  is thermally more stable than  $\text{LiPF}_6$ .<sup>18-22</sup> The effect of structural characteristics of  $\text{LiBF}_4$  on its thermal decomposition temperature will be described using thermodynamic calculations to explain the higher thermal stability of  $\text{LiBF}_4$  than  $\text{LiPF}_6$ .

## Experimental Section

**Apparatus and Reagents.** Volatile materials ( $\text{BF}_3$ ,  $\text{aHF}$ ) were handled in an all PTFE vacuum line equipped with PTFE valves. Manipulation of the non-volatile materials was performed in a dry box (M. Braun). The residual water in the atmosphere within the dry-box never exceeded 1 ppm. The reactions were carried out in FEP (tetrafluoroethylene-hexafluoropropylene) reaction vessels (height 250–300 mm with inner diameter 15.5 mm and outer diameter 18.75 mm) equipped with PTFE valves and PTFE coated stirring bars. Prior to their use all reaction vessels were treated with elemental fluorine. Anhydrous HF (Fluka, Purum) was treated with  $\text{K}_2\text{NiF}_6$  (Ozark Mahoning) for

several hours prior to use. LiF (Merck, 99.99 %) and BF<sub>3</sub> (Union Carbide Austria GmbH, 99.5%) were used as supplied. LiBF<sub>4</sub> was prepared by reaction of LiF with BF<sub>3</sub> in HF.

**Preparation of Single Crystals of LiBF<sub>4</sub>.** LiBF<sub>4</sub> (approximately 150 mg) was placed into the wider tube of the T-shaped reaction vessel and dissolved in anhydrous HF. This solution was decanted into the narrower arm of the reaction vessel. The crystals were grown with a small temperature gradient of 10 K (running tap water-ambient temperature). Crystals were isolated from the mother liquid, immersed in perfluorinated oil (ABCR, FO5960) in the dry-box, selected under microscope, and transferred into the cold nitrogen stream of the diffractometer.

**Crystal Structure Determination.** Single-crystal data from LiBF<sub>4</sub> were collected on a Mercury CCD area detector coupled with a Rigaku AFC7S diffractometer using monochromatized MoK $\alpha$ -radiation. Crystals of LiBF<sub>4</sub> exhibit a strong affinity to twinning resulting in non-reproducible unit cell parameters for each crystal. After several quick tests, an appropriate single crystal with the minor amounts of extra-domains was selected. Obtained data were corrected for Lorentz, polarization and absorption effects, and processed using Rigaku CrystalClear software suite program package.<sup>23</sup> Using the SIR-92<sup>24</sup> program implemented in program package TeXsan<sup>25</sup> an appropriate model was found. Because of rather high R-value (~0.15) for complete model, the TwinRotMax utility from program package PLATON<sup>26</sup> was used for twinning detecting. The twinning matrix of [0-1 0 -1 0 0 0 -1], corresponding to a two-fold rotation around [1  $\bar{1}$  0] direction, and estimated domains ratio of 0.63 : 0.37 were determined. Britton and Yeates tests, being performed using TWIN3.0 software,<sup>27</sup> have detected the same twinning law with approximate 0.6 : 0.4 domains ratio. Finally structure was refined by the SHELXL-97<sup>28</sup> program applying the twinning matrix. Refined ratio between two domains appears to be equal to 0.61 : 0.39.

## Results and Discussion

The unit cell parameters and refinement statistics for LiBF<sub>4</sub> are given in Table 1. Selected bond distances and angles are listed in Table 2.

**Structural Characteristics of LiBF<sub>4</sub>.** The structure of LiBF<sub>4</sub> was solved using the data at 200 K. LiBF<sub>4</sub> crystallizes in the trigonal space group *P*3<sub>1</sub>21. ORTEP diagram of the unit cell is shown in Fig. 1. The asymmetric unit contains one Li, one B and two F atoms. Li cations are located at positions on *z* = 0, 1/3 and 2/3 planes which are related to each other by the 3<sub>1</sub> screw symmetry. B atoms in BF<sub>4</sub><sup>-</sup> occupy positions on *z* = 1/6, 1/2 and 5/6 planes which are also related to each other by the 3<sub>1</sub> screw symmetry. BF<sub>4</sub><sup>-</sup> exhibits an ideal tetrahedral shape (B-F = 1.387(3) and 1.391(3) Å; F-B-F = 109.2(3) – 109.74(14)°) without any disordering. Figure 2 shows the coordination environment around Li<sup>+</sup> in LiBF<sub>4</sub>. Li<sup>+</sup> is coordinated by four fluorine atoms belonging to four different BF<sub>4</sub> anions, where two bond distances of 1.846(5) and 1.862(5) are observed. The shortest F...F distance, corresponding to fluorine atoms belonging to two different BF<sub>4</sub><sup>-</sup> anions, is 2.939 Å. Table 3 gives the structural parameters of a series of MBF<sub>4</sub> salts (M = Na, Ag, K, Rb and Cs) which were reported in previous studies.<sup>29-32</sup> AgBF<sub>4</sub>, KBF<sub>4</sub>, RbBF<sub>4</sub> and CsBF<sub>4</sub> are isostructural and show orthorhombic symmetry (BaSO<sub>4</sub>-type structure), whereas NaBF<sub>4</sub> exhibits a different orthorhombic structure (CaSO<sub>4</sub>-type structure). The structure of LiBF<sub>4</sub> determined in the present study belongs to a trigonal system which has never been found in known MBF<sub>4</sub> salts. The coordination number around M<sup>+</sup> in MBF<sub>4</sub> decreases with decrease in size of M<sup>+</sup> in the order of ten for AgBF<sub>4</sub>, KBF<sub>4</sub>, RbBF<sub>4</sub> and CsBF<sub>4</sub>, eight for NaBF<sub>4</sub> and four for LiBF<sub>4</sub>. It should be noted that lithium ion is coordinated by six ClO<sub>4</sub><sup>-</sup> anions even in the case of LiClO<sub>4</sub> where ClO<sub>4</sub><sup>-</sup> is a little larger tetrahedral ion.<sup>8</sup> The unusually small coordination number of four around Li<sup>+</sup> in LiBF<sub>4</sub> enables the formation of wide space surrounded by the frame forming an infinite network structure in the lattice (Figure 3).

**Thermal Stability of LiBF<sub>4</sub>.** As mentioned in the introduction part, it is known that the decomposition temperature of LiBF<sub>4</sub> is higher than that of LiPF<sub>6</sub>.<sup>18-22</sup> Thermal decompositions of MBF<sub>4</sub> and MPF<sub>6</sub> proceed according to the following reactions (1) and (2), respectively:



Table 4 shows some thermodynamic parameters at 298 K related to the decomposition of  $\text{LiBF}_4$  and  $\text{LiPF}_6$ . The standard entropy values,  $S^\circ$ , of  $\text{LiF}$ ,  $\text{BF}_3$  and  $\text{PF}_5$  are literarily available.<sup>33</sup> The decomposition enthalpy,  $\Delta_{\text{dec}}H^\circ$ , (reactions (1) and (2)) are also reported previously.<sup>34,35</sup> The standard entropy values of  $\text{LiBF}_4$  and  $\text{LiPF}_6$  in Table 4 were calculated by using the following method. An empirical relationship between  $S^\circ$  and  $FUV$  (formula unit volume =  $V/Z$ ) for solid crystalline compounds was first proposed by Mallouk and Bartlett.<sup>36,37</sup> Jenkins and Glasser added a theoretical meaning to this correlation and extended it to a wide variety of compounds.<sup>38</sup> For inorganic salts, the regression line takes the form of the equation (3):<sup>36,37</sup>

$$S^\circ (\text{J mol}^{-1} \text{K}^{-1}) = 1.757 \times FUV(\text{\AA}^3) \quad (3)$$

The decomposition entropy,  $\Delta_{\text{dec}}S^\circ$ , of  $\text{MBF}_4$  and  $\text{MPF}_6$  is introduced by the following equations (4) and (5):

$$\Delta_{\text{dec}}S^\circ = S^\circ(\text{MF}) + S^\circ(\text{BF}_3) - S^\circ(\text{MBF}_4) \quad (4)$$

$$\Delta_{\text{dec}}S^\circ = S^\circ(\text{MF}) + S^\circ(\text{PF}_5) - S^\circ(\text{MPF}_6) \quad (5)$$

Finally, the decomposition temperature,  $T_{\text{dec\_calc}}$ , is estimated from the room temperature reaction entropy and enthalpy change by the equations (6), (7) and (8):<sup>38</sup>

$$\Delta_{\text{dec}}G^\circ_{298} = \Delta_{\text{dec}}H^\circ_{298} - T_{\text{dec\_calc}}\Delta_{\text{dec}}S^\circ_{298} \quad (6)$$

$$\Delta_{\text{dec}}G^\circ_{T_{\text{dec}}} = \Delta_{\text{dec}}H^\circ_{T_{\text{dec}}} - T_{\text{dec\_calc}}\Delta_{\text{dec}}S^\circ_{T_{\text{dec}}} = 0 \quad (7)$$

$$T_{\text{dec\_calc}} = \Delta_{\text{dec}}H^\circ_{T_{\text{dec}}} / \Delta_{\text{dec}}S^\circ_{T_{\text{dec}}} \approx \Delta_{\text{dec}}H^\circ_{298} / \Delta_{\text{dec}}S^\circ_{298} \quad (8)$$

The approximation used in the equation (8) is introduced by the fact that  $\Delta H$  and  $\Delta S$  are temperature-dependent quantities, but in general they do not change very much with temperature unless a phase transition is involved.

It should be noted that either  $\text{LiBF}_4$  or  $\text{LiPF}_6$  does not exhibit any phase transition up to the decomposition temperatures.<sup>14,15,35</sup> The  $T_{\text{dec\_calc}}$  of  $\text{LiBF}_4$  in Table 4 is certainly higher than that of

LiPF<sub>6</sub>, which agrees with the experimental data.<sup>18-22,35</sup> Since the difference between  $\Delta_{\text{dec}}H^{\circ}_{298}$  values of the two compounds is not large compared with the difference between  $\Delta_{\text{dec}}S^{\circ}_{298}$  values, the contribution of the latter is expected to be dominant. When one compares thermal stabilities of MBF<sub>4</sub> and MPF<sub>6</sub>, where M is common, MBF<sub>4</sub> seems to have an advantage of being thermally more stable than MPF<sub>6</sub> from the equations (4) and (5) because  $S^{\circ}(\text{BF}_3)$  is smaller than  $S^{\circ}(\text{PF}_5)$  and  $S^{\circ}(\text{MF})$  is common in both the cases. However, the difference in their lattice volumes, which influences the third terms of the right sides in the equations (4) and (5) through the equation (3), could be large enough to make the PF<sub>6</sub> salt more thermally stable. For the purpose of using this calculation, the unit cell parameters for LiBF<sub>4</sub> were also determined at 298 K (Table 1). LiBF<sub>4</sub> has the same structure at 298 K as that at 200 K with a little lattice expansion. The *FUV* of LiBF<sub>4</sub> calculated from the crystallographic data is 77.9 Å<sup>3</sup> at 298 K which is unexpectedly much larger than those of NaBF<sub>4</sub> (72.7 Å<sup>3</sup>) and AgBF<sub>4</sub> (72.5 Å<sup>3</sup>) in spite of the smaller size of Li<sup>+</sup> than those of Na<sup>+</sup> and Ag<sup>+</sup> (see Table 3 and 5).<sup>30,32,40</sup> The unit cell parameters of LiPF<sub>6</sub> are shown in Table 3. The *FUV* for LiPF<sub>6</sub> (88.2 Å<sup>3</sup>) is 79.9 % of that for NaPF<sub>6</sub> (110.4 Å<sup>3</sup>), whereas the *FUV* for LiBF<sub>4</sub> is 104.5 % of that for NaBF<sub>4</sub>. It may be easy to understand this point by comparing the *FUV* of LiBF<sub>4</sub> (77.9 Å<sup>3</sup>) with that of LiClO<sub>4</sub> (71.4 Å<sup>3</sup>) which is composed of Li<sup>+</sup> and a slightly larger tetrahedral ClO<sub>4</sub><sup>-</sup> anion (average Cl-O bond length: 1.44 Å).<sup>8</sup> Because Li-F bond distances observed in LiBF<sub>4</sub> are not longer than expected from their ionic radii (Table 2 and 5), one can say that the LiBF<sub>4</sub> lattice contains more empty space than those of the other tetrafluoroborates (see Fig. 3). The loose LiBF<sub>4</sub> structure, i.e. large *FUV* value, results in the small  $\Delta_{\text{dec}}S^{\circ}$  through the equations (3) and (4), leading the higher decomposition temperature of LiBF<sub>4</sub> than that of LiPF<sub>6</sub>.

## Conclusion

Crystal structure of LiBF<sub>4</sub> determined by single-crystal X-ray diffraction has been reported. LiBF<sub>4</sub> crystallizes in the trigonal unit cell, where lithium cation is coordinated by four fluorine atoms in a distorted tetrahedral manner. Formula unit volume ( $\text{FUV} = V / Z$ ) of LiBF<sub>4</sub> at 298 K (77.9 Å<sup>3</sup>) is considerably larger than those for NaBF<sub>4</sub> (72.7 Å<sup>3</sup>) and AgBF<sub>4</sub> (72.5 Å<sup>3</sup>) in spite of the smaller ionic radius of Li<sup>+</sup>. It has been elucidated using an empirical relationship between the standard entropy



and FUV that the loose ionic packing of the  $\text{LiBF}_4$  structure contributes to the large standard entropy of  $\text{LiBF}_4$  and the higher decomposition temperature of  $\text{LiBF}_4$  than that of  $\text{LiPF}_6$ .

**Acknowledgment.** The authors would like to thank Prof. Takaaki Sonoda of Kyushu University for his suggestion on this study.

**Supporting Information Available:** Crystallographic data (CIF) is available free of charge via the Internet at <http://pubs.acs.org>.

**Table 1.** Crystal data and refinement results for LiBF<sub>4</sub>

LiBF <sub>4</sub>		
	Li <sub>1</sub> B <sub>1</sub> F <sub>4</sub>	Li <sub>1</sub> B <sub>1</sub> F <sub>4</sub> <sup>c</sup>
Empirical formula	Li <sub>1</sub> B <sub>1</sub> F <sub>4</sub>	Li <sub>1</sub> B <sub>1</sub> F <sub>4</sub> <sup>c</sup>
Formula weight	93.75	93.75
Crystal system	Trigonal	Trigonal
Space group	<i>P</i> 3 <sub>1</sub> 21	<i>P</i> 3 <sub>1</sub> 21
<i>a</i> / Å	4.892(5)	4.9458(8)
<i>c</i> / Å	11.002(12)	11.035(2)
<i>V</i> / Å <sup>3</sup>	228.0(4)	233.76(12)
<i>Z</i>	3	3
<i>T</i> / K	200	298
<i>d<sub>c</sub></i> / g cm <sup>-3</sup>	2.048	1.998
<i>μ</i> / mm <sup>-1</sup>	0.283	-
<i>R</i> <sub>1</sub> ( <i>I</i> > 2σ( <i>I</i> )) <sup>a</sup>	0.0384	-
<i>wR</i> <sub>2</sub> ( <i>I</i> > 2σ( <i>I</i> )) <sup>b</sup>	0.0882	-

<sup>a</sup>  $R_1 = \frac{\sum ||F_o| - |F_c||}{\sum |F_o|}$ .

<sup>b</sup>  $wR_2 = [\frac{\sum w[|F_o|^2 - |F_c|^2]^2}{\sum w|F_o|^2}]^{1/2}$

<sup>c</sup> Only the unit cell parameters were determined.

**Table 2.** Selected bond distances (Å) and angles (degree) for LiBF<sub>4</sub>

---

B1-F1	1.387(3)
B1-F2	1.391(3)
Li1-F1	1.862(5)
Li1-F2	1.846(5)
F1-B1-F1	109.7(4)
F1-B1-F2	109.21(12)
F1-B1-F2	109.74(14)
F2-B1-F2	109.2(3)
F2-Li1-F2	117.1(5)
F2-Li1-F1	107.67(10)
F2-Li1-F1	104.87(11)
F1-Li1-F1	115.1(4)

---

**Table 3.** Structural parameters for MBF<sub>4</sub> (M = Na, Ag, K, Rb and Cs) and LiPF<sub>6</sub>


	NaBF <sub>4</sub> <sup>b</sup>	AgBF <sub>4</sub> <sup>c</sup>	KBF <sub>4</sub> <sup>d</sup>	RbBF <sub>4</sub> <sup>e</sup>	CsBF <sub>4</sub> <sup>e</sup>	LiPF <sub>6</sub> <sup>f</sup>
Space group	<i>Cmcm</i>	<i>Pnma</i>	<i>Pnma</i>	<i>Pnma</i>	<i>Pnma</i>	<i>R3</i>
<i>a</i> / Å	6.2619	5.312	5.4800	5.63	5.88	5.077
<i>b</i> / Å	6.7916	6.752	7.0299	7.29	7.64	-
<i>c</i> / Å	6.8368	8.089	8.6588	9.10	9.67	-
<i>α</i> / °	-	-	-	-	-	57.98
<i>V</i> / Å <sup>3</sup>	290.8	290.1	333.6	373.5	434.4	88.2
<i>Z</i>	4	4	4	4	4	1
<i>FUV</i> / Å <sup>3a</sup>	72.7	72.5	83.4	93.4	108.6	88.2
<i>T</i> / °	r.t.	-73	r.t.	r.t.	r.t.	r.t.

<sup>a</sup> *FUV* = *V* / *Z*. <sup>b</sup> Ref. 30. <sup>c</sup> Ref. 32. <sup>d</sup> Ref. 31. <sup>e</sup> Ref. 29. <sup>f</sup> Ref. 3.

**Table 4.** Some thermodynamic parameters related to the decompositions of LiBF<sub>4</sub> and LiPF<sub>6</sub>

$S^{\circ}_{298}$			$\Delta_{\text{dec}}S^{\circ}_{298}$ <sup>a</sup>	$\Delta_{\text{dec}}H^{\circ}_{298}$ <sup>a</sup>	$T_{\text{dec\_calc}}$ <sup>a, b</sup>	$T_{\text{dec\_obs}}$ <sup>a</sup>
/ J mol <sup>-1</sup> K <sup>-1</sup>			/ J mol <sup>-1</sup> K <sup>-1</sup>	/ kJ mol <sup>-1</sup>	/K	/K
LiBF <sub>4</sub> (c)	LiF(c)	BF <sub>3</sub> (g)				
136.9 <sup>c</sup>	35.7 <sup>d</sup>	254.4 <sup>d</sup>	153.2	89.5 <sup>e</sup>	584	>573 <sup>g, h</sup> , 583 <sup>i</sup>
LiPF <sub>6</sub> (c)	LiF(c)	PF <sub>5</sub> (g)				
155.0 <sup>c</sup>	35.7 <sup>d</sup>	300.8 <sup>d</sup>	181.5	84.3 <sup>f</sup>	464	467 <sup>f</sup> , 500 <sup>i</sup>

<sup>a</sup> $\Delta_{\text{dec}}S^{\circ}_{298}$  and  $\Delta_{\text{dec}}H^{\circ}_{298}$ : Entropy and enthalpy values for decomposition at 298 K.  
 $T_{\text{dec\_calc}}$  and  $T_{\text{dec\_obs}}$ : Calculated and observed thermal decomposition temperatures.  
 Thermal decompositions of LiBF<sub>4</sub> and LiPF<sub>6</sub> occur according to the equations:



$${}^b T_{\text{dec\_calc}} = \Delta_{\text{dec}}H^{\circ}_{298} / \Delta_{\text{dec}}S^{\circ}_{298}$$

<sup>c</sup> These values are obtained according to the reported numerical relationship:<sup>36,37</sup>

$$S^{\circ}_{298} (\text{J mol}^{-1} \text{K}^{-1}) = 1.757 \times FUV(\text{\AA}^3)$$

The  $FUV$  of LiBF<sub>4</sub> at 298 K is 77.92  $\text{\AA}^3$  (See Table 1.)

<sup>d</sup> Ref. 33. <sup>e</sup> Ref. 34. <sup>f</sup> Ref. 35. <sup>g</sup> Ref. 18. <sup>h</sup> Ref. 19. <sup>i</sup> Ref. 20.

**Table 5.** Ionic radii of  $M^+$  ions<sup>40</sup>

$M^+$	$r_+$ (C.N. = 4) <sup>a</sup>	$r_+$ (C.N. = 6) <sup>a</sup>
Li <sup>+</sup>	0.59	0.76
Na <sup>+</sup>	0.99	1.02
Ag <sup>+</sup>	1.00	1.15
K <sup>+</sup>	1.37	1.38
Rb <sup>+</sup>	-	1.52
Cs <sup>+</sup>	-	1.67

<sup>a</sup> C.N. means coordination number.

## Figure captions

**Fig. 1** ORTEP diagram of the  $\text{LiBF}_4$  unit cell: (a) the view from the  $z$ -axis and (b) the view perpendicular to the  $z$ -axis. Displacement ellipsoids are shown at 50 % probability level.

**Fig. 2** Coordination environment around  $\text{Li}^+$  in the  $\text{LiBF}_4$  structure.

**Fig. 3** The network structure in the  $\text{LiBF}_4$  lattice containing wide space. The large and small open spheres denote B and F atom, respectively. The octant-shaded sphere denotes Li atom.

## References


- (1) For recent reviews: (a) *Advances in Lithium-Ion Batteries*, van Schalkwijk, W. A.; Scrosati, B., Eds., Kluwer Academic/Plenum Publishers: New York. 2002. (b) Xu, K. *Chem. Rev.* **2004**, *104*, 4303. (c) Whittingham, M. S. *Chem. Rev.* **2004**, *104*, 4271.
- (2) For examples: (a) Soetens, J.-C.; Millot, C.; Maigret, B. *J. Phys. Chem.* **1998**, *102*, 1055. (b) Arnaud, R.; Benrabah, D.; Sanchez, J.-Y. *J. Phys. Chem.* **1996**, *100*, 10882. (c) Wang, Z.; Gao, W.; Huang, X.; Mo, Y.; Chen, L. *J. Raman Spectrosc.* **2001**, *32*, 900. (d) Johansson, P.; Jacobsson, P. *J. Phys. Chem. A* **2001**, *105*, 8504. (e) Hayamizu, K.; Aihara, Y.; Nakagawa, H.; Nukuda, T.; Price, W. S. *J. Phys. Chem. B* **2004**, *108*, 19527. (f) Borodin, O.; Smith, G. D.; Douglas, R. *J. Phys. Chem. B* **2003**, *107*, 6824. (g) Tsunekawa, H.; Narumi, A.; Sano, M.; Hiwara, A.; Fujita, M.; Yokoyama, H. *J. Phys. Chem. B* **2003**, *107*, 10962. (h) Andreev, Y. G.; Seneviratne, V.; Khan, M.; Henderson, W. A.; Frech, R. E.; Bruce, P. G.; *Chem. Mater.* **2005**, *17*, 767. (i) Burba, C. M.; Frech, R. *J. Phys. Chem. B* **2005**, *109*, 15161. (k) Popov, S. E.; Nikiforov, A. E.; Bushkova, O. V.; Zhukovsky, V. M. *J. Phys. Chem. A* **2004**, *108*, 10280.
- (3) Kemmitt, R. D. W.; Russell, D. R.; Sharp, D. W. A. *J. Chem. Soc.* **1963**, 4408.
- (4) Cox, B. *J. Chem. Soc.* **1956**, 876.
- (5) Wells, A. F. *Structural Inorganic Chemistry*, 5th ed., Clarendon Press, Oxford, 1984, p. 456.
- (6) Burns, J. H. *Acta Crystallogr.* **1962**, *15*, 1098.
- (7) Graudejus, O.; Wilkinson, A. P.; Chacón, L. C.; Bartlett, N. *Inorg. Chem.* **2000**, *39*, 2794.
- (8) Henderson, W. A.; Brooks, N. R. *Inorg. Chem.* **2003**, *42*, 4522.
- (9) Nowinski, J. L.; Lightfoot, P.; Bruce, P. G. *J. Mater. Chem.* **1994**, *4*, 1579.



- (10) Tremayne, M.; Lightfoot, P.; Mehta, M. A.; Bruce, P. G.; Harris, K. D. M.; Shankland, K.; Gilmore, C. J.; Bricogne, G. *J. Solid State Chem.* **1992**, *100*, 191.
- (11) Ding, M. S. *J. Chem. Eng. Data* **2004**, *49*, 1102.
- (12) Garvrichev, K. S. *Inorg. Mater.* **2003**, *39*, S89.
- (13) Reynhardt, E. S.; Lourens, J. A. J. *J. Chem. Phys.* **1984**, *80*, 6240.
- (14) Dworkin, A. S. *J. Chem. Eng. Data* **1972**, *17*, 284.
- (15) Cantor, S.; McDermott, D. P.; Gilpatrick, L. O. *J. Chem. Phys.* **1970**, *52*, 4600.
- (16) Plakhotnik, V. N.; Kovtun, Y. V.; Tul'chinskii, B. V.; *Russ. J. Inorg. Chem.* **1986**, *31*, 2687.
- (17) Bogdanov, V. S.; Kondrashev, Y. D. *Russ. J. Inorg. Chem.* **1987**, *32*, 1657.
- (18) Schäfer, H.; Rebeneck, H. *Z. Anorg. Allg. Chem.* **1987**, *545*, 224.
- (19) Shapiro, I.; Weiss, H. G. *J. Am. Chem. Soc.* **1953**, *75*, 1753.
- (20) Kanamura, K. In *Fluorinated Materials for Energy Conversion devices*, Nakajima, T.; Groult, H., Eds., Elsevier, 2005, p. 253.
- (21) Momota, K. *Batt. Technol.* **1996**, *8*, 108.
- (22) Sasaki, Y.; Nanbu, N. In *Materials Chemistry in Lithium Batteries*, Kumagai, N.; Komaba, S.; Wakihara, M., Eds., Research Signpost, Trivandrum, India, 2002, p. 415.
- (23) *CrystalClear*: Rigaku Corporation, Woodlands, TX, 1999.
- (24) Altomare, A.; Cascarano, G.; Giacovazzo, C.; Guagliardi, A. *J. Appl. Crystallogr.* **1993**, *26*, 343.
- (25) Molecular Structure Corporation. (1997-1999). *teXsan* for Windows. Single Crystal Structure Analysis Software, Version 1.06.
- (26) Spek, A. L. *J. Appl. Cryst.* **2003**, *36*, 7.

- (27) Kahlenberg V.; Messner, T., *TWIN3.0. a program for testing twinning by merohedry. J. Appl. Cryst.* **2001**, *34*, 405.
- (28) Sheldrick, G. M., *SHELXL97*. Program for crystal structure refinement. University of Goettingen, Germany, 1997.
- (29) Clark, M. J. R.; Lynton, H. *Can J. Chem.* **1969**, *47*, 2579.
- (30) Brunton, G. *Acta Crystallogr., Sect. B* **1968**, *24*, 1703.
- (31) Brunton, G. *Acta Crystallogr., Sect. B* **1969**, *25*, 2161.
- (32) Goreshnik, E.; Mazej, Z. *Solid State Sci.* **2005**, *7*, 1225.
- (33) Chase Jr., M. W. *NIST-JANAF Thermochemical Tables*, 4th Ed., J. Phys. Chem. Ref. Data, Monograph 9, 1998.
- (34) Gross, P.; Hayman, C.; Joel, H. A. *Trans. Faraday Soc.* **1968**, *64*, 317.
- (35) Gavritchev, K. S.; Sharpataya, G. A.; Smagin, A. A.; Malyi, E. N.; Matyukha, V. A. *J. Therm. Anal. Cal.* **2003**, *73*, 71.
- (36) Bartlett, N.; Yeh, S.; Kourtakis, K.; Mallouk, T. E. *J. Fluorine Chem.* **1984**, *26*, 97.
- (37) Shen, C. S.; Hagiwara, R., Mallouk, T. E. Bartlett, N. In *Inorganic Fluorine Chemistry Toward the 21st Century*, American Chemical Society, Washington, DC, 1994, p. 26.
- (38) Jenkins, H. D. B.; Glasser, L. *Inorg. Chem.* **2003**, *42*, 8702.
- (39) Shriver, D. F.; Atkins, P. W.; Langford, C. H. *Inorganic Chemistry*, Oxford Univ. Press, 2nd ed., 1994.
- (40) Shannon, R. D. *Acta Crystallogr., Sect. A* **1976**, *32*, 751.

(a)

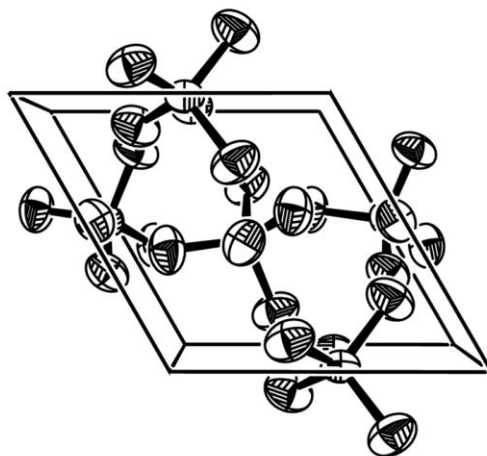

(b)

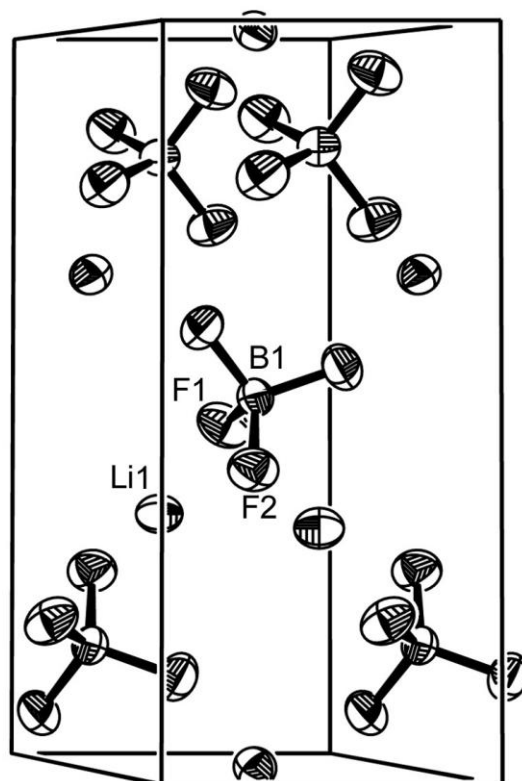


Fig. 1 ORTEP diagram of the  $\text{LiBF}_4$  unit cell: (a) the view from the  $z$ -axis and (b) the view perpendicular to the  $z$ -axis. Displacement ellipsoids are shown at 50 % probability level.

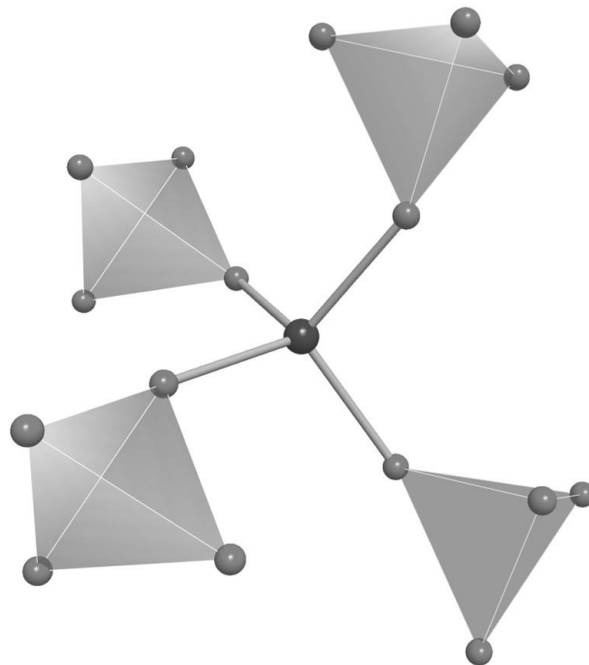


Fig. 2 Coordination environment around  $\text{Li}^+$  in the  $\text{LiBF}_4$  structure.

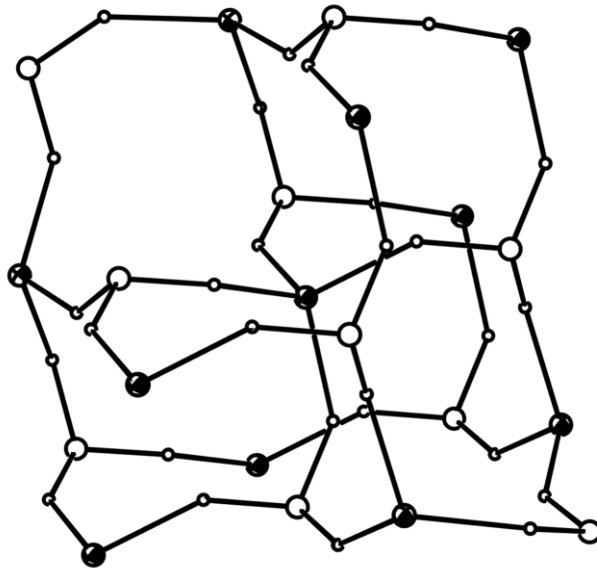


Fig. 3 The network structure in the  $\text{LiBF}_4$  lattice. The large and small open spheres denote B and F atom, respectively. The octant-shaded sphere denotes Li atom.