

Title	A gene transfection for rat mesenchymal stromal cells in biodegradable gelatin scaffolds containing cationized polysaccharides.
Author(s)	Kido, Yuichiro; Jo, Jun-ichiro; Tabata, Yasuhiko
Citation	Biomaterials (2011), 32(3): 919-925
Issue Date	2011-01
URL	http://hdl.handle.net/2433/131964
Right	© 2010 Elsevier Ltd
Type	Journal Article
Textversion	author

1
2
3 **A gene transfection for rat mesenchymal stromal cells in biodegradable**
4 **gelatin scaffolds containing cationized polysaccharides**
5
6
7

8
9 Yuichiro Kido, Jun-ichiro Jo, and Yasuhiko Tabata
10

11
12
13
14 **Short / Running Title: Gene transfection of BMSC in 3D scaffolds**
15
16
17
18
19
20
21
22

23 Department of Biomaterials, Institute for Frontier Medical Sciences, Kyoto University,
24
25 53 Kawara-cho Shogoin, Sakyo-ku Kyoto 606-8507, Japan
26
27
28
29
30
31
32
33
34
35
36
37

38 Correspondence to Dr. Yasuhiko Tabata, Department of Biomaterials, Field of Tissue
39
40 Engineering, Institute for Frontier Medical Sciences, Kyoto University, 53 Kawara-cho
41
42 Shogoin, Sakyo-ku Kyoto 606-8507, Japan.
43
44
45

46 TEL +81-75-751-4121
47

48 FAX +81-75-751-4646
49

50 E-mail yasuhiko@frontier.kyoto-u.ac.jp
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Abstract

The objective of this study was to design three-dimensional scaffolds of bone marrow-derived stem cells capable of their gene transfection and evaluate the transfection extent. Three-dimensional scaffolds of gelatin and β -tricalcium phosphate (β -TCP) were prepared. Spermine-introduced pullulan (spermine-pullulan) was prepared as the non-viral carrier of gene transfection. The spermine-pullulan was mixed with a luciferase plasmid DNA to prepare their polyion complex. The scaffolds were treated with succinylated gelatin (suc-gel) at different concentrations, treated in different methods of freeze-drying and dehydrothermal treatment, and placed in the aqueous of complexes to prepare various scaffolds containing the complex. When the stem cells were seeded into the scaffolds to evaluate the gene transfection of cells, the level of plasmid DNA transfection depended on the method of complex containing scaffolds preparation. The complexes were released with time from the scaffolds although the release profile depended on the type of scaffolds. The order of gene transfection for the stem cells in the scaffolds was in good accordance with that of plasmid DNA released. It is possible that cells were transfected with the complexes released from the scaffolds.

Keywords

Drug release; gelatin; genetic engineering; polysaccharide; scaffold; stem cells.

1. Introduction

Most of the current research work on stem cells is being performed in the culture system of two-dimension (2D) which is quite different from that of living body [1]. Needless to say, the natural extracellular environment of cells in the body is of three-dimensional (3D) structure. It has been generally recognized that cells are strongly influenced by their extracellular environment [2]. When compared between the 2D and 3D cell culture systems, the cell-cell and cell-substrate interactions must be different and consequently affect the property and biological activity of stem cells [2]. Taken together, it will be physiologically better to perform cell experiments in the 3D environment which is close to the natural in vivo condition of cells. Similarly, the gene transfection of cells will be influenced by the 3D culture.

Several researches of gene transfection have been reported for cells cultured in the 3D scaffolds of fibrin hydrogels [3], non-woven fabrics of polyethylene terephthalate (PET) [4, 5], and the sponges of synthetic polymers [6-8]. However, most of scaffold materials are generally prepared from non-degradable polymers.

Bone marrow mesenchymal stromal cells (BMSC) are one of the most important cells not only for basic researches of biology and medicine, but also for the clinical applications, because they have their own potentials to differentiate into various cell lineages, such as osteocytes [9], chondrocytes [10], adipocytes [11], dopamine-producing cells [12, 13], and tenocytes [14]. BMSC can be isolated from patients themselves and easily expanded in vitro, which is useful from the clinical viewpoint. In addition, BMSC have been widely used to make clear the mechanism of cell proliferation and differentiation [15, 16]. Gene transfection is one of the technologies necessary to actively proceed the basic cell researches. However, generally,

1
2
3 the efficiency of gene transfection is low for the BMSC compared with that of other
4
5 cells. It is, therefore, necessary to develop the technology and methodology of gene
6
7 transfection for stem cells.
8
9

10 In this study, a new technology of gene transfection for BMSC is introduced
11
12 with the 3D scaffolds of sponge type prepared from biodegradable components. The
13
14 biodegradable 3D scaffolds were prepared from gelatin and β -tricalcium phosphate
15
16 (β -TCP). Gelatin is a denatured collagen and bioabsorbable, and has been clinically
17
18 used. It is reported that the scaffold of gelatin could release growth factors (basic
19
20 fibroblast growth factors [17], bone morphogenic protein-2 [18], transforming growth
21
22 factor β 1 [19]), nucleic acids (plasmid DNA [20] and small interfering RNA [21, 22]),
23
24 and low-molecular-weight drugs [23, 24]. The combination of bioactive substances by
25
26 use of gelatin is very promising when a scaffold is applied to build up tissue-like
27
28 structures in vitro by the cells culture. β -TCP is a non-toxic and bioabsorbable ceramics
29
30 which have been clinically used. In this study, it is used to combine the scaffold for the
31
32 mechanical reinforcement, which is essential to maintain the porous structure of
33
34 scaffold in cell culture [25]. The porous structure enables cells to give a steric space for
35
36 their proliferation and differentiation in the scaffold as well as the oxygen and nutrient
37
38 supply.
39
40
41
42
43
44

45 As a non-viral carrier of gene transfection, spermine-introduced pullulan
46
47 (spermine-pullulan) has been explored [26]. This carrier showed a high efficiency of
48
49 plasmid DNA transfection for BMSC because of an enhanced internalization of plasmid
50
51 DNA into cells due to the efficient interaction of sugar-residues in pullulan with the
52
53 asialoglycoprotein receptor of cells [27].
54
55
56

57 The objective of study is to evaluate the feasibility of gelatin and β -TCP
58
59
60
61
62
63
64
65

1
2
3 scaffolds containing the complex of spermine-pullulan and plasmid DNA in the gene
4
5 transfection for BMSC. To improve the gene transfection efficiency for BMSC in the
6
7 scaffold, the way to combine the complex with the scaffold was contrived. To improve
8
9 the extent of complex combination, the scaffold was treated with succinylated gelatin
10
11 derivatives of negative charge (suc-gel). The suc-gel treatment will enhance the
12
13 combination of complex, resulting in the increased gene transfection. The 3D
14
15 gelatin/ β -TCP scaffolds were prepared by different methods of suc-gel treatment, and
16
17 the effect of scaffold type on the gene transfection for BMSC was evaluated. We
18
19 examine the profile of plasmid DNA from scaffolds containing the complexes and
20
21 compare with that of gene transfection.
22
23
24
25
26
27
28

29 **2. Materials and methods**

30 **2.1. Materials**

31
32
33
34 A gelatin sample with an isoelectric point (IEP) of 9.0, prepared by an acid
35
36 process of porcine skin, that with an IEP of 5.0, prepared by a base process of bovine
37
38 bone, and succinylated gelatin were kindly supplied from Nitta Gelatin Co. (Osaka,
39
40 Japan). β -TCP granules (average size = 2.9 μm) were obtained from Taihei Chemical
41
42 Industries, Nara, Japan. Pullulan with a weight-average molecular weight of 47,300 was
43
44 purchased from Hayashibara Biochemical Laboratories, Inc., Okayama, Japan.
45
46 Spermine was purchased from Sigma Chemical Co., St. Louis, MO. Other chemicals
47
48 were obtained from Nacalai Tesque. Inc., Kyoto, Japan and used without further
49
50 purification.
51
52
53
54
55
56

57 **2.2. Plasmid DNA**

58
59
60
61
62
63
64
65

1
2
3 The plasmid DNA used was the pGL3 vector (5.26 kb) coding for a firefly
4 luciferase gene (Luciferase Reporter Vectors-pGL3, Promega, Madison, WI). The
5 plasmid DNA was multiplied in *E. coli* (strain DH5a) and purified using QIAGEN
6 plasmid Mega kit (Qiagen K.K., Tokyo, Japan) according to the manufacturers'
7 instructions. The yield and purity of the plasmid DNA were evaluated using ultraviolet
8 spectroscopy (DU® 800 Spectrophotometer, Beckman Coulter, Inc., Fullerton, CA). The
9 absorbance ratio at wavelengths of 260 to 280 nm for the plasmid DNA solution was
10 measured to be between 1.8 and 2.0.
11
12
13
14
15
16
17
18
19
20
21
22
23

24 **2.3. Preparation of cationized pullulan derivatives**

25
26 Spermine was introduced to the hydroxyl groups of pullulan by a
27 *N,N'*-carbonyldiimidazole (CDI) activation method [28]. Dehydrated dimethyl sulfoxide
28 (50 ml) containing 50 mg of pullulan was mixed with 263 mg of CDI and subsequently
29 1.87 g of spermine. Following agitation with a magnetic stirrer at 37 °C for 24 hr, the
30 reaction mixture was dialyzed against ultra-pure double-distilled water (DDW) for 2
31 days with a dialysis membrane (the cut-off molecular weight of dialysis membrane is
32 12,000–14,000, Viskase Companies, Inc, Willowbrook, Illinois). Then, the solution
33 dialyzed was freeze-dried to obtain the samples of spermine-introduced pullulan
34 (spermine–pullulan). The spermine introduction, expressed by the molar percentage of
35 spermine introduced to the hydroxyl groups of pullulan, was 11.8 mole/mole%, when
36 determined by the conventional elemental analysis.
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53

54 **2.4. Preparation of polyion complexes of plasmid DNA and spermine-pullulan**

55
56 The spermine-pullulan aqueous solution (223 µg/ml) was mixed with
57
58
59
60
61
62
63
64
65

1
2
3 phosphate-buffered saline solution (PBS, 10 mM, pH 7.4) containing 100 µg/ml of
4
5 plasmid DNA, followed by leaving for 15 min at room temperature to obtain the
6
7 polyion complex.
8
9

10 11 12 **2.5. Preparation of sponge scaffolds of gelatin and β-TCP for gene transfection**

13
14
15 Gelatin scaffolds of sponge type incorporating β-TCP were prepared as
16
17 previously reported [25]. Briefly, 3 wt% aqueous solution of gelatin containing different
18
19 amounts of β-TCP was mixed at 5,000 rpm at 37 °C for 3 min by using a homogenizer
20
21 (ED-12, Nihonseiki Co., Tokyo, Japan). After aqueous solution of glutaraldehyde (GA)
22
23 was added to the mixed solution, the mixed β-TCP and gelatin solution was further
24
25 agitated for 15 sec by the homogenizer. The resulting bubbled solution was cast into a
26
27 polypropylene dish, followed by leaving at 4 °C for 12 hr for gelatin crosslinking. Then,
28
29 the crosslinked gelatin scaffold of sponges was freeze-dried, and then placed in 100 mM
30
31 aqueous glycine solution at 37 °C for 1 hr to block the residual aldehyde groups of
32
33 glutaraldehyde, thoroughly washed with DDW, and freeze-dried, followed by cut into
34
35 discs with 6 mm in diameter and 3 mm thickness. The average pore size, porosity,
36
37 compression modulus of the scaffolds were measured as previously reported [25].
38
39
40
41
42

43
44 The scaffold discs were immersed in the aqueous solution of succinylated
45
46 gelatin (suc-gel, 100 µl) at 37 °C for 24 hr, freeze-dried, and dehydrothermally
47
48 crosslinked under vacuum at 140 °C for 32 hr in a vacuum oven (Sato vacuum
49
50 machinery industrial Co., LTD., Tokyo, Japan). After the removal of excess suc-gel by
51
52 rinsing with PBS, 100 µl of polyion complex solution was added to the suc-gel-treated
53
54 scaffold, followed by incubation at 37 °C for 2 hr to allow the complex to associate in
55
56 the scaffold.
57
58
59
60
61
62
63
64
65

2.6. Cell culture

BMSC were isolated from the bone shaft of femurs and tibias of 3-wk-old male Wistar rats (Japan SLC, Inc., Shizuoka, Japan) according to the technique reported by Lennon et al [29]. Briefly, both the ends of rat femurs were cut away from the epiphysis, and the bone marrow was flushed out using a syringe (21 gauge needle) with 1 ml of alpha minimum essential medium (α MEM) supplemented with 15 vol% fetal calf serum (FCS), penicillin (50 U/ml), and streptomycin (50 U/ml). The cell suspension (5 ml) was placed into two 25 cm² flasks (Iwaki Glass, Funabashi, Chiba, Japan) and cultured at 37 °C in a 95% air-5% carbon dioxide atmosphere. The medium was changed 2 and 3 days after culture and thereafter every 3 days. When the cells of the first passage became sub-confluent, usually 7 to 10 days after seeding, the cells were detached from the flask using treatment for 5 min at 37 °C with PBS solution containing 0.25 wt% trypsin and 0.02 wt% ethylenediaminetetraacetic acid (Sigma-aldrich, Inc., St Louis, MO). Cells were normally subcultured at a density of 2×10^4 cells/cm². Second-passaged cells in a sub-confluence condition were used for all the experiments.

2.7. Cell culture in scaffolds for gene transfection

BMSC were seeded into the scaffolds by an agitated seeding method reported previously [30]. Briefly, 350 μ l of cell suspension (2×10^6 cells/ml) and one scaffold were placed in 5-ml tube with 12 mm of inner diameter (IWAKI Glass Co. Ltd., Chiba, Japan) and agitated on an orbital shaker (Bellco Glass, Inc., Vineland, NJ) at 300 rpm for 6 hr. The cell-seeded scaffolds were spired by a needle and immobilized in the spinner flasks (Bellco Glass, Inc., Vineland, NJ). The spinner flask was filled with 150

1
2
3 ml of culture medium and the medium was stirred at the rate of 50 rpm. The medium
4
5 was totally changed every 3 days. At different time intervals, the scaffold with cells was
6
7 washed with PBS once, and stored at -80 °C for further experiments.
8
9

10 11 12 **2.8. Evaluation of Suc-gel amount remaining in scaffolds**

13
14 The amount of suc-gel remaining in the scaffolds was evaluated by use of
15
16 suc-gel labeled with rhodamine B (suc-rhoB). The suc-rhoB was prepared according to
17
18 the procedure reported previously [28]. Briefly, dehydrated DMSO (25 ml) containing 1
19
20 mg/ml of rhodamine B isothiocyanate was gently added to 500 ml of sodium carbonate
21
22 buffer (0.1 M, pH 9.0) containing 2 mg/ml of acidic gelatin. After gentle stirring for 10
23
24 hr at 4 °C, 25 ml of ammonium chloride aqueous solution (1.1 M) was added to the
25
26 mixture to stop the labeling reaction with gentle stirring for 2 hr at 25 °C. Acidic gelatin
27
28 labeled with rhodamine B was purified by dialysis against DDW for 2 days with a
29
30 dialysis membrane with the cut-off molecular weight of 12,000–14,000, and then
31
32 freeze-dried. The rhodamine-labeled gelatin was dissolved dehydrated DMSO, while
33
34 succinic anhydride (Wako Pure Chemical Industries, Ltd., Osaka, Japan) was added to
35
36 the DMSO solution, followed by leaving for 8 hr at 25°C. The amount of primary amino
37
38 groups remaining of suc-rhoB was determined by the trinitrobenzene sulfonic acid
39
40 (TNBS) method to experimentally confirm the 100% conversion to the amino groups of
41
42 gelatin to carboxyl ones.
43
44
45
46
47
48
49

50
51 Scaffolds treated with rhodamine-labeled suc-gel by different methods were
52
53 rinsed with PBS or α MEM without phenol red containing 10 vol% of FCS. Then, the
54
55 scaffolds were enzymatically degraded by incubating at 37 °C for 1 hr in 150 μ l of PBS
56
57 containing 0.1 w/v% of trypsin (Sigma-aldrich, Inc., St Louis, MO). After separation of
58
59
60
61
62
63
64
65

1
2
3 β -TCP granules by centrifugation, the fluorescent intensity of supernatant was measured
4
5 at the excitation and emission wavelengths of 544 and 590 nm, respectively. A
6
7 calibration curve was prepared for the scaffolds treated with pre-determined
8
9 concentrations of rhodamine-labeled suc-gel to evaluate the amount of suc-gel
10
11 associated in the scaffold.
12
13

14 15 16 17 **2.9. Evaluation of polyion complexes release from gelatin/ β -TCP scaffolds**

18
19 The release of spermine-pullulan and plasmid DNA complexes was evaluated
20
21 by use of ^{125}I -labeled plasmid DNA. Briefly, the plasmid DNA was labeled with ^{125}I
22
23 according to the method reported previously [20]. Similar procedure was done to
24
25 prepare the scaffolds containing the complex other than using ^{125}I -labeled plasmid DNA.
26
27 After the cell culture of scaffold, the amount of plasmid DNA immobilized and released
28
29 was determined by assessing the radioactivity of scaffolds remaining.
30
31
32
33
34
35

36 37 **2.10. Luciferase assay**

38
39 Scaffold with cells was immersed in 200 μl of cell culture lysis reagent
40
41 (Promega Corp., Madison, WI) in a micro reaction tube, then crushed using Tissue
42
43 Lyser (Retsch GmbH & Co. KG, Haan, Germany) at room temperature with for 10 min.
44
45 The debris of cells and scaffold were separated by centrifugation (17,800 rpm, 20 min).
46
47 Then, 100 μl of luciferase assay reagent (Promega Corp., Madison, WI) was added to 20
48
49 μl of supernatant, and the relative light unit (RLU) of the sample was determined using
50
51 a luminometer (MicroLumatPlus LB 96V, Berthold, Tokyo, Japan).
52
53
54

55
56 The total protein of cells in each scaffold was determined using a bicinchonnic
57
58 acid (BCA) protein assay kit (Pierce, Rockford, IL) according to the manufacturers'
59
60
61
62
63
64
65

1
2
3 instructions. The amount of scaffold protein was subtracted with the appropriate
4
5 background. The RLU was divided by the protein amount to normalize the number of
6
7 cells on the luciferase activity. Each experimental group was carried out 3 times
8
9 independently.

10 11 12 13 14 15 **2.11. Statistical analysis**

16
17 Data were expressed as means \pm standard deviations. Data were analyzed using
18
19 Tukey-Kramer paired comparison test, while the significance was accepted at $p < 0.05$.
20
21
22
23

24 **3. Results**

25 26 **3.1. Preparation of gelatin/ β -TCP scaffolds**

27
28 **Table 1** shows the characteristics of scaffolds prepared at different amounts of
29
30 β -TCP and GA. The average pore size was about 200 μm , irrespective of the preparing
31
32 condition of scaffolds.
33
34

35 36 **3.2. Gene transfection ability of scaffolds**

37
38 **Figure 1** shows that the gene transfection level of cells cultured in the
39
40 gelatin/ β -TCP scaffolds prepared by different methods. When the β -TCP content was
41
42 75% and higher, the gene expression level of cells significantly decreased. The
43
44 maximum gene expression was observed for the scaffolds prepared at the GA
45
46 concentrations of 26 and 52 moles/moles. The gene expression level of cells depended
47
48 on the preparation method of scaffolds and the highest level was observed for the
49
50 scaffold prepared by the method C. The gene transfection was influenced by the
51
52 concentration of suc-gel treated with the scaffolds and became maximum at the
53
54 concentrations of 50 and 500 μg / scaffold.
55
56
57
58
59
60
61
62
63
64
65

3.3. Remaining of suc-gel in gelatin/ β -TCP scaffolds

Figure 2 shows the amount of suc-gel remaining in the scaffolds prepared by different methods and different amounts of suc-gel treated after rinsing of PBS with or without the culture medium. A large amount of suc-gel was detached from scaffold by rinsing with the culture medium for scaffolds prepared by the method A, in contrast to those prepared by the methods B and C. There was significant difference in the amount of suc-gel remaining in scaffolds treated between the methods B and C.

The percentage of suc-gel remaining in scaffolds depended on the amount of suc-gel added to scaffolds. As the amount of suc-gel treated increased, the percentage of suc-gel detached from scaffolds also increased.

3.4. The amount of plasmid DNA remaining and release profile

Figure 3 shows the amount of plasmid DNA immobilized in scaffolds prepared by different methods of suc-gel treatment or at various amounts of suc-gel. The amount of plasmid DNA remaining was influenced by the method of suc-gel treatment and the amount of suc-gel treated, and increased at the suc-gel concentration of 5 and 50 μ g.

Figure 4 shows the profiles of complex release from scaffolds. Irrespective of the initial amount of plasmid DNA immobilized in scaffolds, the plasmid DNA was released.

3.5 Gene transfection of gelatin/ β -TCP scaffolds containing complex

Figure 5 shows the relationship between the gene expression level of MSC cultured in gelatin/ β -TCP scaffolds prepared different methods and the amount of

1
2
3 plasmid DNA released. The gene transfection depended on the preparation method of
4 scaffolds containing the complex and the amount of suc-gel treated. The level of gene
5 expression was in good accordance with that of plasmid DNA released.
6
7
8
9

10 **Figure 6** shows the proliferation of cells in scaffolds prepared at different
11 amounts of suc-gel added. On day 1 and 7, there is no significant difference in the cell
12 number among the experimental groups.
13
14
15
16
17
18

19 **4. Discussion**

20
21
22 The present study clearly demonstrates that the plasmid DNA transfection for
23 MSC was successfully achieved by their culturing in the gelatin/ β -TCP 3D scaffolds
24 containing the plasmid DNA complexed with spermine-pullulan. The level of plasmid
25 DNA transfection depended on the method of scaffolds preparation and the order was in
26 good accordance with that of plasmid DNA released. It is possible that cells were
27 transfected by the complex released from the scaffold in culture.
28
29
30
31
32
33
34
35

36 In this culture system, BMSC were cultured and transfected on the inner
37 surface of 3D scaffolds which is immobilized with the plasmid DNA complexes.
38 Considering the positioning of cells and the complex, it is likely that the complex
39 always exists near the cells to be transfected. It is highly conceivable that both the
40 continuous exposure of complex to cells and the confirm attachment between cells and
41 the substrate which minimizes the serum influence on the transfection activity of
42 complex, result in such an enhanced plasmid DNA transfection. This transfection
43 system, called the reverse transfection, has been reported () and the transfection
44 efficiency was high compared with that of conventional method where the complex is
45 added into the medium for transfection culture of cells. This study is to demonstrate that
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3 the reverse transfection system was applicable to the 3D scaffold of cell culture.
4

5 The level of gene expression for MSC on the 3D scaffold was lower than that
6 of the 2D scaffold (data not shown). Considering the fact that the cells conditions are
7 strongly influenced by their extracellular environment, it is understandable that the 3D
8 environment is suitable to cells for gene transfection. Further investigation is needed to
9 understand the mechanism of superior gene transfection of 3D scaffolds to 2D ones.
10
11
12
13
14
15
16

17 The gene expression level of cells cultured in scaffolds was influenced by the
18 amount of β -TCP and GA in the scaffolds (**Figure 1**). On the other hand, the cell
19 proliferation was also affected by the preparing procedure of scaffolds (data not shown).
20
21 As the amount of β -TCP and GA increased, the number of cells proliferated in scaffolds
22 increased. It is highly conceivable that the increased amount enhanced the mechanical
23 strength of scaffolds, which can contain the porous structure necessary for cell
24 proliferation. As the result, the cell proliferation was enhanced and consequently the
25 gene transfection was increased. However, at the higher amounts of β -TCP and GA, the
26 level decreased. The reason is not clear at present although the scaffold stiffness may
27 affect the gene transfection.
28
29
30
31
32
33
34
35
36
37
38
39
40

41 The amount of suc-gel remaining in scaffolds increased as that of suc-gel
42 treated became high (**Figure 2a**). This result can be explained by the suc-gel
43 detachment. The detachment of suc-gel from scaffolds may be due to replacement of
44 suc-gel by proteins present in FCS since the PBS rinsing did not cause the detachment.
45
46 Suc-gel treated by the method A would bind to the scaffolds by the interaction weaker,
47 such as the electrostatic interaction, than that with the methods B and C. By
48 freeze-drying (method B), the interaction between the suc-gel and scaffold will become
49 stronger. This is because other interaction forces including the hydrophobic interaction
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3 were added. By heating under vacuum (method C), chemical bonds can be formed
4
5 between the carboxyl groups of suc-gel and the amino groups or hydroxyl groups of
6
7 gelatin through dehydrothermal reaction. Taken together, the dehydrothermal process
8
9 would increase the interaction between the suc-gel and the gelatin of scaffold, which
10
11 results in high resistance of suc-gel against FCS replacement and the consequent
12
13 increase in the amount of suc-gel remaining in the scaffolds. When the scaffolds were
14
15 treated with more than 500 μg of suc-gel, the percentage of suc-gel detached from
16
17 scaffolds increased (**Figure 2b**). This can be explained by an increase in the amount of
18
19 suc-gel that is not interacted with the components of scaffolds.
20
21
22
23

24 The suc-gel of negative charge can strong bind to the gelatin molecules of
25
26 scaffolds. This enables the complex of positive charge to increase the amount associated
27
28 with the scaffold. Comparing the amount of plasmid DNA immobilized with that of
29
30 suc-gel remaining (**Figures 2 and 3**), it is clear that the scaffolds with less detachable
31
32 suc-gel could associate higher amount of plasmid DNA. This relationship clearly
33
34 indicates that the suc-gel mediated the association of polyion complexes to the scaffold.
35
36 This was experimentally confirmed by the result of plasmid DNA associated at the
37
38 concentrations ranging from 0 to 50 μg . At the higher amounts of suc-gel, it is possible
39
40 that suc-gel can be detached easily from the scaffold together with polyion complex,
41
42 resulting in suppressed amount of plasmid DNA immobilized.
43
44
45
46
47

48 When compared among the scaffolds with different suc-gel treatments, it was
49
50 revealed that the amount of plasmid DNA immobilized corresponded to that of plasmid
51
52 DNA released (**Figures 3a and 5a**). The finding suggests that the interaction strength
53
54 between the plasmid DNA and the suc-gel treated is similar, irrespective of suc-gel
55
56 treatment method.
57
58
59
60
61
62
63
64
65

1
2
3 There was good correlation between the amount of plasmid DNA released and
4
5 the gene expression level (**Figure 5**). This can be explained from the viewpoint of
6
7 plasmid DNA release. The complex would be released into culture medium during the
8
9 cell culture, and then the complex would be taken up by the cells cultured in the
10
11 scaffold. The profile of gene expression could be regulated by changing that of
12
13 complexes released. This trend was also observed for 2D substrates. The complex
14
15 released from the substrate surface was taken up by cells and the consequent gene
16
17 transfection was observed [4].
18
19
20
21

22 Although the gene expression level of cells was influenced by the amount of
23
24 β -TCP or GA in the scaffolds, there was no difference in the amount of plasmid DNA
25
26 released from the scaffolds (**Figure 4**). This finding suggests that the extracellular
27
28 environment, such as elasticity or hydrophilicity, affects the culture conditions of cells
29
30 in scaffolds, resulting in changed level of gene expression.
31
32
33

34 There have been reported on 3D scaffolds containing plasmid DNA [2, 5, 6, 8].
35
36 The scaffolds are basically prepared by simultaneously mixing a plasmid DNA or the
37
38 complex with the scaffold material. In the system, since the plasmid DNA or the
39
40 complex is homogenously in the bulk of scaffold, the release behavior of plasmid DNA
41
42 or the complex is governed by the material property of scaffold. On the other hand, in
43
44 the case of the present gelatin/ β -TCP 3D scaffold, the plasmid DNA complexed with
45
46 spermine-pullulan is treated to immobilize after the preparation of gelatin/ β -TCP
47
48 scaffold itself. Considering the molecular size of gelatin mesh in the scaffold and
49
50 complex, it is conceivable that the complex cannot penetrate into the inside of scaffold
51
52 matrix and is localized only in the surface of scaffold. Therefore, the release profile of
53
54 complexes is governed only by the interaction strength between the complex and
55
56
57
58
59
60
61
62
63
64
65

1
2
3 scaffold material. Since the degradability of scaffold itself and the release of complex
4
5 can be separately regulated, it is highly expected that in the present scaffold system, the
6
7 regulation of complex release in the 3D scaffold can be readily controlled. The complex
8
9 release system governed by the interaction with suc-gel can be regulated and applied for
10
11 other scaffolds which can bind the suc-gel. This system is applicable for the scaffold of
12
13 basic cell biology and tissue regeneration.
14
15

16
17 Gelatin sponges were used as biodegradable 3D scaffolds for plasmid DNA
18
19 transfection. It has been reported that growth factors, nucleic acids, and
20
21 low-molecular-weight drugs, could be released from the gelatin scaffold in the
22
23 controlled fashion. Therefore, the 3D scaffold of gelatin for plasmid DNA transfection
24
25 can be combined with other bioactive substances. This combination will be effective in
26
27 design and preparation of cell scaffolds with biological functions which can open a new
28
29 field of cell biology and regenerative medical therapy.
30
31
32
33
34
35

36 **5. Conclusions**

37
38 The plasmid DNA transfection for MSC was successfully achieved by their culturing in
39
40 the gelatin/ β -TCP 3D scaffolds containing the plasmid DNA complexed with
41
42 spermine-pullulan. The level of plasmid DNA transfection depended on the method of
43
44 scaffolds preparation and the order was in good accordance with that of plasmid DNA
45
46 released.
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3 **References**
4

- 5
6 1. Schindler M, Nur EKA, Ahmed I, Kamal J, Liu HY, Amor N, et al. Living in
7
8 three dimensions: 3D nanostructured environments for cell culture and regenerative
9
10 medicine. *Cell Biochem Biophys* 2006;45(2):215-227.
11
12
13
14
15 2. Dawson E, Mapili G, Erickson K, Taqvi S, Roy K. Biomaterials for stem cell
16
17 differentiation. *Adv Drug Deliv Rev* 2008;60(2):215-228.
18
19
20
21 3. Lei P, Padmashali RM, Andreadis ST. Cell-controlled and spatially arrayed
22
23 gene delivery from fibrin hydrogels. *Biomaterials* 2009;30(22):3790-3799.
24
25
26
27 4. Okazaki A, Jo J, Tabata Y. A reverse transfection technology to genetically
28
29 engineer adult stem cells. *Tissue Eng* 2007;13(2):245-251.
30
31
32
33 5. Xie Y, Yang ST, Kniss DA. Three-dimensional cell-scaffold constructs promote
34
35 efficient gene transfection: implications for cell-based gene therapy. *Tissue Eng*
36
37 2001;7(5):585-598.
38
39
40
41
42 6. Jang JH, Houchin TL, Shea LD. Gene delivery from polymer scaffolds for
43
44 tissue engineering. *Expert Rev Med Devices* 2004;1(1):127-138.
45
46
47
48
49 7. Hosseinkhani H, Inatsugu Y, Hiraoka Y, Inoue S, Shimokawa H, Tabata Y.
50
51 Impregnation of plasmid DNA into three-dimensional scaffolds and medium perfusion
52
53 enhance in vitro DNA expression of mesenchymal stem cells. *Tissue Eng*
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3 2005;11(9-10):1459-1475.
4
5

6 8. Nie H, Wang CH. Fabrication and characterization of PLGA/HAp composite
7 scaffolds for delivery of BMP-2 plasmid DNA. J Control Release
8
9 2007;120(1-2):111-121.
10
11
12
13

14
15
16 9. Marie PJ, Fromigue O. Osteogenic differentiation of human marrow-derived
17 mesenchymal stem cells. Regen Med 2006;1(4):539-548.
18
19
20
21

22 10. Vilquin JT, Rosset P. Mesenchymal stem cells in bone and cartilage repair:
23 current status. Regen Med 2006;1(4):589-604.
24
25
26
27

28 11. Rodriguez JP, Astudillo P, Rios S, Pino AM. Involvement of adipogenic
29 potential of human bone marrow mesenchymal stem cells (MSCs) in osteoporosis. Curr
30 Stem Cell Res Ther 2008;3(3):208-218.
31
32
33
34
35
36

37 12. Nagane K, Kitada M, Wakao S, Dezawa M, Tabata Y. Practical induction
38 system for dopamine-producing cells from bone marrow stromal cells using
39 spermine-pullulan-mediated reverse transfection method. Tissue Eng Part A
40
41
42
43
44
45
46
47 2009;15(7):1655-1665.
48
49

50 13. Bahat-Stroomza M, Barhum Y, Levy YS, Karpov O, Bulvik S, Melamed E, et
51 al. Induction of adult human bone marrow mesenchymal stromal cells into functional
52 astrocyte-like cells: potential for restorative treatment in Parkinson's disease. J Mol
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3 Neurosci 2009;39(1-2):199-210.
4
5

6 14. Ouyang HW, Cao T, Zou XH, Heng BC, Wang LL, Song XH, et al.
7
8 Mesenchymal stem cell sheets revitalize nonviable dense grafts: implications for repair
9
10 of large-bone and tendon defects. Transplantation 2006;82(2):170-174.
11
12

13 15. Solchaga LA, Penick K, Porter JD, Goldberg VM, Caplan AI, Welter JF. FGF-2
14
15 enhances the mitotic and chondrogenic potentials of human adult bone marrow-derived
16
17 mesenchymal stem cells. J Cell Physiol 2005;203(2):398-409.
18
19
20
21

22 16. Pricola KL, Kuhn NZ, Haleem-Smith H, Song Y, Tuan RS. Interleukin-6
23
24 maintains bone marrow-derived mesenchymal stem cell stemness by an
25
26 ERK1/2-dependent mechanism. J Cell Biochem 2009;108(3):577-588.
27
28
29
30

31 17. Tabata Y, Hijikata S, Ikada Y. Enhanced vascularization and tissue granulation
32
33 by basic fibroblast growth factor impregnated in gelatin hydrogels. J Control Release
34
35 1994;31:189-199.
36
37
38
39
40
41

42 18. Yamamoto M, Takahashi Y, Tabata Y. Controlled release by biodegradable
43
44 hydrogels enhances the ectopic bone formation of bone morphogenetic protein.
45
46 Biomaterials 2003;24(24):4375-4383.
47
48
49
50

51 19. Yamamoto M, Tabata Y, Hong L, Miyamoto S, Hashimoto N, Ikada Y. Bone
52
53 regeneration by transforming growth factor beta1 released from a biodegradable
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3 hydrogel. J Control Release 2000;64(1-3):133-142.
4
5

6 20. Fukunaka Y, Iwanaga K, Morimoto K, Kakemi M, Tabata Y. Controlled release
7 of plasmid DNA from cationized gelatin hydrogels based on hydrogel degradation. J
8
9 Control Release 2002;80(1-3):333-343.
10
11
12
13

14 21. Matsumoto G, Kushibiki T, Kinoshita Y, Lee U, Omi Y, Kubota E, et al.
15
16 Cationized gelatin delivery of a plasmid DNA expressing small interference RNA for
17
18 VEGF inhibits murine squamous cell carcinoma. Cancer Sci 2006;97(4):313-321.
19
20
21
22

23 22. Nakamura M, Jo J, Tabata Y, Ishikawa O. Controlled delivery of T-box 21
24
25 siRNA ameliorates autoimmune alopecia (alopecia areata) in C3H/HeJ mouse model.
26
27
28
29
30
31
32 Am J Pathol 2008;172(3):650-658.
33
34

35 23. Konishi M, Tabata Y, Kariya M, Hosseinkhani H, Suzuki A, Fukuhara K, et al.
36
37
38 In vivo anti-tumor effect of dual release of cisplatin and adriamycin from biodegradable
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

66 24. Tanigo T, Takaoka R, Tabata Y. Sustained release of water-insoluble
67
68
69
70
71
72
73
74
75
76
77
78
79
80
81
82
83
84
85
86
87
88
89
90
91
92
93
94
95
96
97
98
99
100
101
102
103
104
105
106
107
108
109
110
111
112
113
114
115
116
117
118
119
120
121
122
123
124
125
126
127
128
129
130
131
132
133
134
135
136
137
138
139
140
141
142
143
144
145
146
147
148
149
150
151
152
153
154
155
156
157
158
159
160
161
162
163
164
165
166
167
168
169
170
171
172
173
174
175
176
177
178
179
180
181
182
183
184
185
186
187
188
189
190
191
192
193
194
195
196
197
198
199
200
201
202
203
204
205
206
207
208
209
210
211
212
213
214
215
216
217
218
219
220
221
222
223
224
225
226
227
228
229
230
231
232
233
234
235
236
237
238
239
240
241
242
243
244
245
246
247
248
249
250
251
252
253
254
255
256
257
258
259
260
261
262
263
264
265
266
267
268
269
270
271
272
273
274
275
276
277
278
279
280
281
282
283
284
285
286
287
288
289
290
291
292
293
294
295
296
297
298
299
300
301
302
303
304
305
306
307
308
309
310
311
312
313
314
315
316
317
318
319
320
321
322
323
324
325
326
327
328
329
330
331
332
333
334
335
336
337
338
339
340
341
342
343
344
345
346
347
348
349
350
351
352
353
354
355
356
357
358
359
360
361
362
363
364
365
366
367
368
369
370
371
372
373
374
375
376
377
378
379
380
381
382
383
384
385
386
387
388
389
390
391
392
393
394
395
396
397
398
399
400
401
402
403
404
405
406
407
408
409
410
411
412
413
414
415
416
417
418
419
420
421
422
423
424
425
426
427
428
429
430
431
432
433
434
435
436
437
438
439
440
441
442
443
444
445
446
447
448
449
450
451
452
453
454
455
456
457
458
459
460
461
462
463
464
465
466
467
468
469
470
471
472
473
474
475
476
477
478
479
480
481
482
483
484
485
486
487
488
489
490
491
492
493
494
495
496
497
498
499
500
501
502
503
504
505
506
507
508
509
510
511
512
513
514
515
516
517
518
519
520
521
522
523
524
525
526
527
528
529
530
531
532
533
534
535
536
537
538
539
540
541
542
543
544
545
546
547
548
549
550
551
552
553
554
555
556
557
558
559
560
561
562
563
564
565
566
567
568
569
570
571
572
573
574
575
576
577
578
579
580
581
582
583
584
585
586
587
588
589
590
591
592
593
594
595
596
597
598
599
600
601
602
603
604
605
606
607
608
609
610
611
612
613
614
615
616
617
618
619
620
621
622
623
624
625
626
627
628
629
630
631
632
633
634
635
636
637
638
639
640
641
642
643
644
645
646
647
648
649
650
651
652
653
654
655
656
657
658
659
660
661
662
663
664
665
666
667
668
669
670
671
672
673
674
675
676
677
678
679
680
681
682
683
684
685
686
687
688
689
690
691
692
693
694
695
696
697
698
699
700
701
702
703
704
705
706
707
708
709
710
711
712
713
714
715
716
717
718
719
720
721
722
723
724
725
726
727
728
729
730
731
732
733
734
735
736
737
738
739
740
741
742
743
744
745
746
747
748
749
750
751
752
753
754
755
756
757
758
759
760
761
762
763
764
765
766
767
768
769
770
771
772
773
774
775
776
777
778
779
780
781
782
783
784
785
786
787
788
789
790
791
792
793
794
795
796
797
798
799
800
801
802
803
804
805
806
807
808
809
810
811
812
813
814
815
816
817
818
819
820
821
822
823
824
825
826
827
828
829
830
831
832
833
834
835
836
837
838
839
840
841
842
843
844
845
846
847
848
849
850
851
852
853
854
855
856
857
858
859
860
861
862
863
864
865
866
867
868
869
870
871
872
873
874
875
876
877
878
879
880
881
882
883
884
885
886
887
888
889
890
891
892
893
894
895
896
897
898
899
900
901
902
903
904
905
906
907
908
909
910
911
912
913
914
915
916
917
918
919
920
921
922
923
924
925
926
927
928
929
930
931
932
933
934
935
936
937
938
939
940
941
942
943
944
945
946
947
948
949
950
951
952
953
954
955
956
957
958
959
960
961
962
963
964
965
966
967
968
969
970
971
972
973
974
975
976
977
978
979
980
981
982
983
984
985
986
987
988
989
990
991
992
993
994
995
996
997
998
999
1000

239 25. Takahashi Y, Yamamoto M, Tabata Y. Osteogenic differentiation of
240
241
242
243
244
245
246
247
248
249
250
251
252
253
254
255
256
257
258
259
260
261
262
263
264
265
266
267
268
269
270
271
272
273
274
275
276
277
278
279
280
281
282
283
284
285
286
287
288
289
290
291
292
293
294
295
296
297
298
299
300
301
302
303
304
305
306
307
308
309
310
311
312
313
314
315
316
317
318
319
320
321
322
323
324
325
326
327
328
329
330
331
332
333
334
335
336
337
338
339
340
341
342
343
344
345
346
347
348
349
350
351
352
353
354
355
356
357
358
359
360
361
362
363
364
365
366
367
368
369
370
371
372
373
374
375
376
377
378
379
380
381
382
383
384
385
386
387
388
389
390
391
392
393
394
395
396
397
398
399
400
401
402
403
404
405
406
407
408
409
410
411
412
413
414
415
416
417
418
419
420
421
422
423
424
425
426
427
428
429
430
431
432
433
434
435
436
437
438
439
440
441
442
443
444
445
446
447
448
449
450
451
452
453
454
455
456
457
458
459
460
461
462
463
464
465
466
467
468
469
470
471
472
473
474
475
476
477
478
479
480
481
482
483
484
485
486
487
488
489
490
491
492
493
494
495
496
497
498
499
500
501
502
503
504
505
506
507
508
509
510
511
512
513
514
515
516
517
518
519
520
521
522
523
524
525
526
527
528
529
530
531
532
533
534
535
536
537
538
539
540
541
542
543
544
545
546
547
548
549
550
551
552
553
554
555
556
557
558
559
560
561
562
563
564
565
566
567
568
569
570
571
572
573
574
575
576
577
578
579
580
581
582
583
584
585
586
587
588
589
590
591
592
593
594
595
596
597
598
599
600
601
602
603
604
605
606
607
608
609
610
611
612
613
614
615
616
617
618
619
620
621
622
623
624
625
626
627
628
629
630
631
632
633
634
635
636
637
638
639
640
641
642
643
644
645
646
647
648
649
650
651
652
653
654
655
656
657
658
659
660
661
662
663
664
665
666
667
668
669
670
671
672
673
674
675
676
677
678
679
680
681
682
683
684
685
686
687
688
689
690
691
692
693
694
695
696
697
698
699
700
701
702
703
704
705
706
707
708
709
710
711
712
713
714
715
716
717
718
719
720
721
722
723
724
725
726
727
728
729
730
731
732
733
734
735
736
737
738
739
740
741
742
743
744
745
746
747
748
749
750
751
752
753
754
755
756
757
758
759
760
761
762
763
764
765
766
767
768
769
770
771
772
773
774
775
776
777
778
779
780
781
782
783
784
785
786
787
788
789
790
791
792
793
794
795
796
797
798
799
800
801
802
803
804
805
806
807
808
809
810
811
812
813
814
815
816
817
818
819
820
821
822
823
824
825
826
827
828
829
830
831
832
833
834
835
836
837
838
839
840
841
842
843
844
845
846
847
848
849
850
851
852
853
854
855
856
857
858
859
860
861
862
863
864
865
866
867
868
869
870
871
872
873
874
875
876
877
878
879
880
881
882
883
884
885
886
887
888
889
890
891
892
893
894
895
896
897
898
899
900
901
902
903
904
905
906
907
908
909
910
911
912
913
914
915
916
917
918
919
920
921
922
923
924
925
926
927
928
929
930
931
932
933
934
935
936
937
938
939
940
941
942
943
944
945
946
947
948
949
950
951
952
953
954
955
956
957
958
959
960
961
962
963
964
965
966
967
968
969
970
971
972
973
974
975
976
977
978
979
980
981
982
983
984
985
986
987
988
989
990
991
992
993
994
995
996
997
998
999
1000

1
2
3 beta-tricalcium phosphate. *Biomaterials* 2005;26(17):3587-3596.
4
5

6
7 26. Jo J, Ikai T, Okazaki A, Yamamoto M, Hirano Y, Tabata Y. Expression profile
8
9 of plasmid DNA by spermine derivatives of pullulan with different extents of spermine
10
11 introduced. *J Control Release* 2007;118(3):389-398.
12
13

14
15
16 27. Jo J, Okazaki A, Nagane K, Yamamoto M, Tabata Y. Preparation of cationized
17
18 polysaccharides as gene transfection carrier for bone marrow-derived mesenchymal
19
20 stem cells. *J Biomater Sciences Polym Eds* 2010;21(2):185-204.
21
22

23
24
25 28. Hermanson GT. *Bioconjugate Techniques*: Academic Press, 1996.
26
27

28
29 29. Lennon DP, Caplan AI. Isolation of rat marrow-derived mesenchymal stem
30
31 cells. *Exp Hematol* 2006;34(11):1606-1607.
32
33

34
35 30. Takahashi Y, Tabata Y. Homogeneous seeding of mesenchymal stem cells into
36
37 nonwoven fabric for tissue engineering. *Tissue Eng* 2003;9(5):931-938.
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Figure Legends

Figure 1. The gene expression level of cells after culture in gelatin/ β -TCP scaffolds containing plasmid DNA. The amount of plasmid DNA added was 5 μ g/scaffold. The scaffolds were prepared in different conditions: (a) The β -TCP content, (b) the amount of GA added, (c) the method of suc-gel treatment, and (d) the amount of suc-gel added. (a) The amounts of GA and suc-gel added were 52 mole/mole gelatin and 50 μ g/scaffold, respectively. The scaffolds were prepared by the method C. *, $p < 0.05$; significant against the gene expression level of cells cultured in the scaffolds with 0% of β -TCP. (b) The β -TCP content and the amount of suc-gel added were 50 wt% and 50 μ g/scaffold, respectively. The scaffolds were prepared by the method C. *, $p < 0.05$; significant against the gene expression level of cells cultured in the scaffolds with 208 mole/mole gelatin of GA. (c) The β -TCP content was 50 wt%. The amounts of GA and suc-gel added were 52 mole/mole gelatin and 50 μ g/scaffold, respectively. The method A: scaffolds treated with suc-gel aqueous solution at 37 °C for 24 hr, the method B: scaffolds freeze-dried following the method A, and the method C: scaffolds treated at 140°C for 32 hr under vacuum following the method B. *, $p < 0.05$; significant against the gene expression level of cells cultured in other methods. (d) The β -TCP content and the amount of GA added were 50 wt% and 52 mole/mole gelatin, respectively. The scaffolds were prepared by the method C. *, $p < 0.05$; significant against the gene expression level of cells cultured in other groups.

Figure 2. (a) The amount of suc-gel remaining in gelatin/ β -TCP scaffolds prepared by different methods: (A) scaffolds treated with suc-gel aqueous solution at 37 °C for 24 hr, (B) scaffolds freeze-dried following the method A, and (C) scaffolds treated at 140°C

for 32 hr under vacuum following the method B. The β -TCP content was 50 wt%. The amounts of GA and suc-gel added were 52 mole/mole gelatin and 50 μ g/scaffold, respectively. The amount of suc-gel remaining was determined after rinsing the scaffolds with PBS (solid columns) or the culture medium (open columns). *, P<0.05: significant against the amount of suc-gel remaining in scaffolds prepared by the method A at the corresponding rinsing procedure. †, P<0.05: significant against the amount of suc-gel remaining in scaffolds prepared by the method B at the corresponding rinsing procedure.

(b) Percentage of suc-gel remaining in gelatin/ β -TCP scaffolds treated with different amounts of suc-gel. The β -TCP content and the amount of GA added were 50 wt% and 52 mole/mole gelatin, respectively. The scaffolds were prepared by the method C. *, P<0.05: significant against the amount of suc-gel remaining in scaffolds prepared by the method A at the corresponding rinsing procedure. †, P<0.05: significant against the amount of suc-gel remaining in scaffolds prepared by the method B at the corresponding rinsing procedure.

Figure 3. The amount of pDNA remaining in gelatin/ β -TCP scaffolds prepared by different methods (a), or those treated with different amounts of suc-gel (b) after cell seeding: (A) scaffolds treated with suc-gel aqueous solution at 37 °C for 24 hr, (B) scaffolds freeze-dried following the method A, and (C) scaffolds treated at 140°C for 32 hr under vacuum following the method B. The amount of plasmid DNA added was 5 μ g/scaffold. (a) The β -TCP content was 50 wt%. The amounts of GA and suc-gel added were 52 mole/mole gelatin and 50 μ g/scaffold, respectively. *, P<0.05: significant against the amount of plasmid DNA remaining in scaffolds without suc-gel treatment (0

μg / scaffold). (b) The β -TCP content and the amount of GA added were 50 wt% and 52 mole/mole gelatin, respectively. The scaffolds were prepared by the method C. *, $P < 0.05$: significant against the amount of plasmid DNA remaining in scaffolds without suc-gel treatment ($0 \mu\text{g}$ / scaffold). †, $P < 0.05$: significant against the amount of plasmid DNA remaining in scaffolds treated with $5 \mu\text{g}$ /scaffold of suc-gel.

Figure 4. The time profiles of plasmid DNA release from gelatin/ β -TCP scaffolds prepared by different methods (a), or those treated with different amounts of suc-gel (b) during cell culture. The amount of plasmid DNA added was $5 \mu\text{g}$ /scaffold. (a) (○) scaffolds without suc-gel treatment, (△) scaffolds treated with suc-gel aqueous solution at 37°C for 24 hr (method A), (□) scaffolds freeze-dried following the method A (method B), and (●) scaffolds treated at 140°C for 32 hr under vacuum following the method B (method C). The β -TCP content was 50 wt%. The amounts of GA and suc-gel added were 52 mole/mole gelatin and $50 \mu\text{g}$ /scaffold, respectively. (b) scaffolds treated with 0 (○), 5 (△), 50 (□), 500 (●), and 1500 μg /scaffold of suc-gel (▲). The β -TCP content and the amount of GA added were 50 wt% and 52 mole/mole gelatin, respectively. The scaffolds were prepared by the method C.

Figure 5. Relationship between the gene expression level of MSC cultured in gelatin/ β -TCP scaffolds prepared by different methods (a), or those treated with different amounts of suc-gel (b) for 3 days (○) and the amount of plasmid DNA released from the scaffolds during 3 days of cell culture (△).

Figure 6. The number of MSC cultured for 1 (open columns) and 7 days (solid

columns) in gelatin/ β -TCP scaffolds treated with different amounts of suc-gel. The β -TCP content and the amount of GA added were 50 wt% and 52 mole/mole gelatin, respectively. The scaffolds were prepared by the method C.

Table 1. Characteristics of β -TCP/gelatin scaffolds used.

β -TCP (wt%)	GA (mole/mole gelatin)	Average pore size (μm)	Porosity (%)	Water content ((w/w)%)
0		172.3 \pm 50.2	98.5 \pm 0.1	
12.5		189.0 \pm 35.6	98.4 \pm 0.0	
25	52	179.2 \pm 36.4	97.9 \pm 0.0	97.6 \pm 0.07
50		191.0 \pm 55.0	97.9 \pm 0.1	
75		191.9 \pm 29.9	96.8 \pm 0.3	
90		172.9 \pm 40.3	93.6 \pm 0.3	
	13	183.5 \pm 38.4	97.8 \pm 0.2	98.2 \pm 0.09
	26	185.3 \pm 36.3	97.5 \pm 0.5	97.8 \pm 0.09
50	52	191.0 \pm 55.0	97.9 \pm 0.1	97.6 \pm 0.07
	104	208.0 \pm 35.9	97.9 \pm 0.0	97.3 \pm 0.10
	208	187.1 \pm 31.6	97.9 \pm 0.1	97.3 \pm 0.07

Figure 1

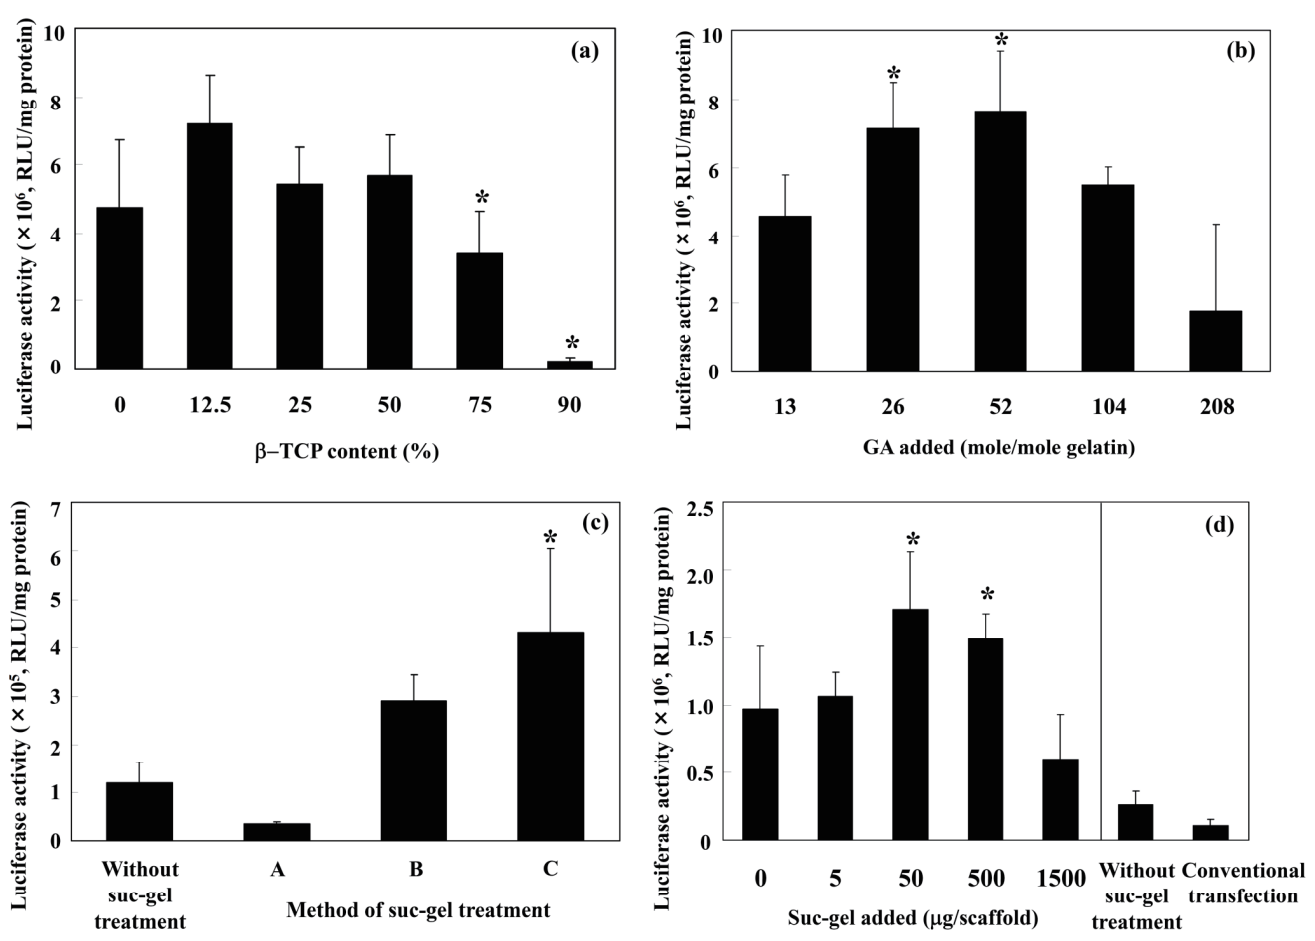


Figure 1. Kido et al.

Figure 2

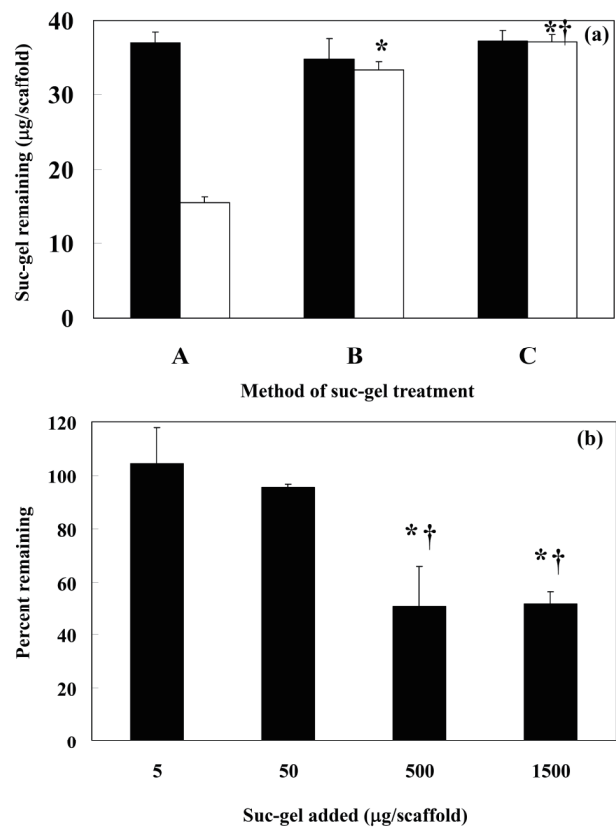


Figure 2. Kido et al.

Figure 3

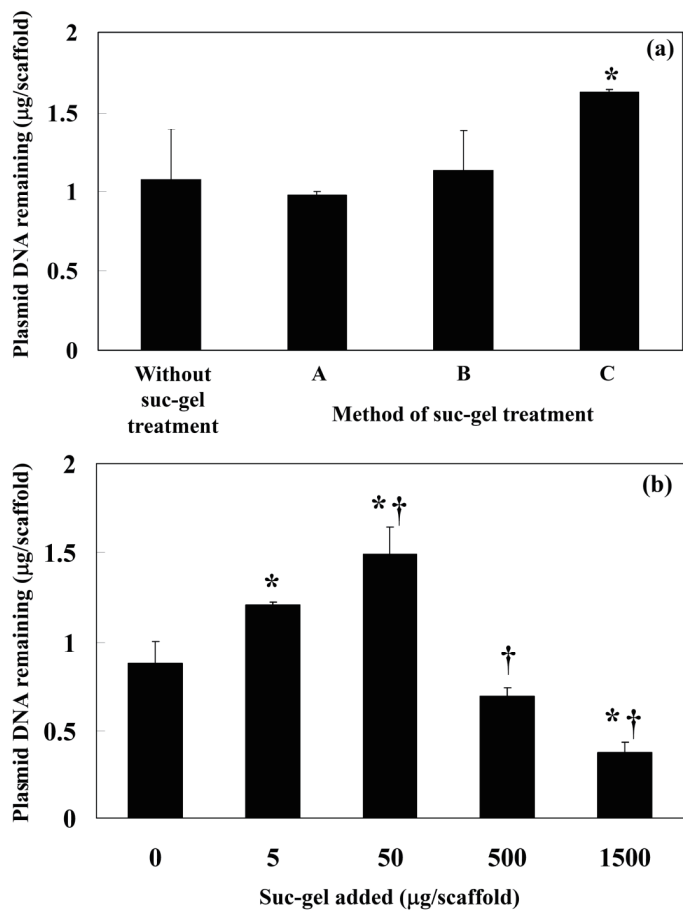


Figure 3. Kido et al.

Figure 4

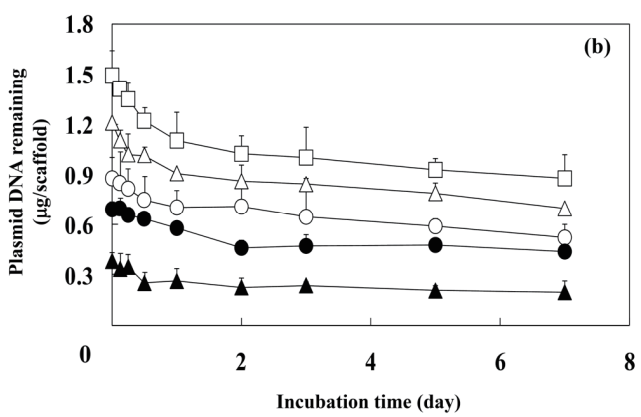
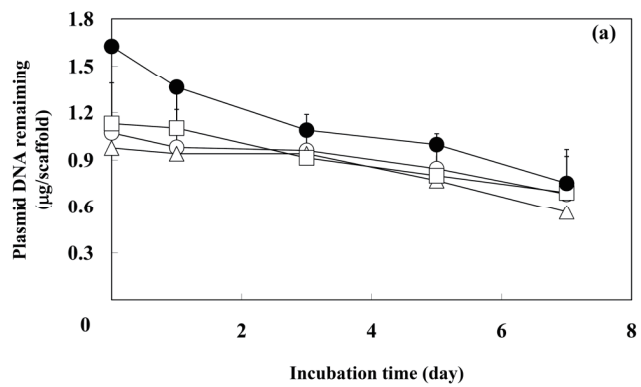


Figure 4. Kido et al.

Figure 5

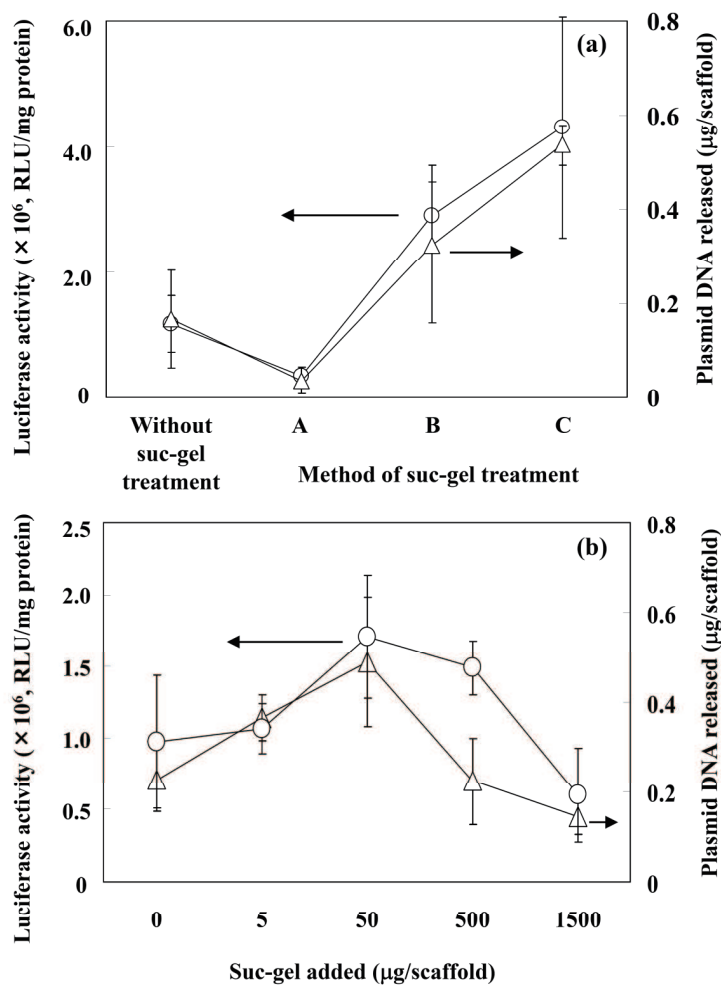


Figure 5. Kido et al.

Figure 6

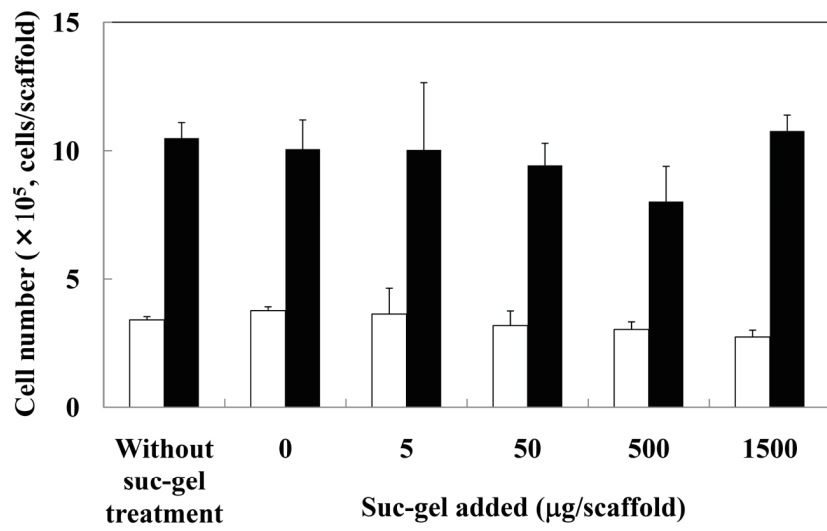


Figure 6. Kido et al.