



LJMU Research Online

Al-Khafaji, ZS, Majdi, A, Shubbar, AAF, Nasr, MS, Al-Mamoori, SF, Alkhulaifi, A, Al-Mufti, RL, Al-Rifaie, A, Alkhayyat, A and Hashim, KS

Impact of high volume GGBS replacement and steel bar length on flexural behaviour of reinforced concrete beams

<http://researchonline.ljmu.ac.uk/id/eprint/14681/>

Article

Citation (please note it is advisable to refer to the publisher's version if you intend to cite from this work)

Al-Khafaji, ZS, Majdi, A, Shubbar, AAF, Nasr, MS, Al-Mamoori, SF, Alkhulaifi, A, Al-Mufti, RL, Al-Rifaie, A, Alkhayyat, A and Hashim, KS (2021) Impact of high volume GGBS replacement and steel bar length on flexural behaviour of reinforced concrete beams. IOP Conference Series: Materials Science

LJMU has developed **LJMU Research Online** for users to access the research output of the University more effectively. Copyright © and Moral Rights for the papers on this site are retained by the individual authors and/or other copyright owners. Users may download and/or print one copy of any article(s) in LJMU Research Online to facilitate their private study or for non-commercial research. You may not engage in further distribution of the material or use it for any profit-making activities or any commercial gain.

The version presented here may differ from the published version or from the version of the record. Please see the repository URL above for details on accessing the published version and note that access may require a subscription.

For more information please contact researchonline@ljmu.ac.uk

<http://researchonline.ljmu.ac.uk/>

PAPER • OPEN ACCESS

Impact of high volume GGBS replacement and steel bar length on flexural behaviour of reinforced concrete beams

To cite this article: Zainab S. Al-Khafaji *et al* 2021 *IOP Conf. Ser.: Mater. Sci. Eng.* **1090** 012015

View the [article online](#) for updates and enhancements.



240th ECS Meeting ORLANDO, FL

Orange County Convention Center Oct 10-14, 2021



Abstract submission due: April 9

SUBMIT NOW

Impact of high volume GGBS replacement and steel bar length on flexural behaviour of reinforced concrete beams

Zainab S. Al-Khafaji¹, Ali Majdi², Ali A. Shubbar^{3,4,*}, Mohammed Salah Nasr⁵, Shahad F. Al-Mamoori⁴, Abdullah Alkhulaifi³, Rafal Latif Al-Mufti³, Ali Al-Rifaie⁶, Ahmed Alkhayat⁷ and Khalid Hashim³

¹ Al-Furra Al-Awsat Distribution Foundation \ Ministry of Oil \ Babylon, Iraq.

² Department of Civil Engineering, Al- Mustaqbal University College, Babylon, Iraq

³ Department of Civil Engineering, Liverpool John Moores University, UK

⁴ Department of Civil Engineering, College of Engineering, University of Babylon, Iraq

⁵ Technical Institute of Babylon, Al-Furat Al-Awsat Technical University (ATU), Iraq.

⁶ College of Engineering, Al-Muthanna University, Samawah, 66001, Iraq.

⁷ Department of Building and Construction Technical Engineering, College of Technical Engineering, the Islamic University, 54001 Najaf, Iraq.

* Corresponding author: alishubbar993@gmail.com , A.A.Shubbar@2014.ljmu.ac.uk

Abstract. The Ordinary Portland Cement (OPC) is one of the major ingredient utilized for the manufacture of concrete. The manufacturing of cement includes the release of huge amounts of CO₂ gas as a main contributor for greenhouse influence and global warming. Several researchers have investigated the characteristics of OPC concrete utilizing cementitious materials like fly ash, silica fume, and Ground Granulated Blast furnace Slag (GGBS) as replacement materials. The article aims to investigate experimentally the flexural behavior of concrete beams with GGBS. The experimental work was divided into three stages, the first one consists of six reinforced concrete beam specimens with (0%, 40% and 60%) of GGBS. During this stage, the used steel bars were 8 mm diameter and 500 mm in length. In the second stage, the length of the steel bars was reduced to 400 mm with the best mixture of (GGBS+OPC) that obtained from stage 1. In the third stage, the best length of steel bars was used with the best (GGBS+OPC) ratio to be tested at 7, 14 and 28 days from the date of casting. Consequences of this exploration suggests that replacement of OPC with 40 percent GGBS with 500 mm steel bar length can be used in reinforced concrete specimens as it shows comparable results relative to control mixtures (0% GGBS).

1. Introduction

Concrete is a necessary material utilized in the Building field [1,2], and as the construction is growing quickly around the globe, the demand for concrete is increasing along with it [3,4]. Concrete constitutes of aggregate and cement mainly. It has been reported that almost 1.35 billion tonnes of Portland cement is consumed [4–6] and in other studies, the consumption was reported to be over 2



billion tonnes annually [3]. Evidently, the energy intensive process of producing Ordinary Portland Cement (OPC) has been increasing in cost [3]. During the recent years, governments and companies in the cement industry has become aware of the negative effects and drawbacks of the usage of the OPC on the environment such as the carbon dioxide (CO₂) emissions [7–11]. The production of 1 tonne of OPC equals to 1 tonne of carbon dioxide emitted to the atmosphere. Worth to note that, approximately 7 % of the emissions of the CO₂ is attributed to the cement industry [12–15]. Therefore, to preserve the environment, CO₂ emissions must be reduced [16]. This led the industry and researchers to investigate suitable replacement to the OPC to decrease this negative influence on the environment [8]. Cementitious waste and/or by-products materials including Meta-kaolin [17], rice husk ash [18], Ground granulated blast furnace slag (GGBS) [19], silica fume [20–25], fly ash [26], waste paper [27], stainless steel powder [28], etc., have been utilized as a replacement to OPC.

The GGBS is a by-product remaining from the steel manufacturing, and utilized as a supplemental cementitious material in the manufacture of concrete. GGBS is extracted from a blast furnace via quenching melted iron slag in water or steam, as result of that, a glassy, granular material would be produced and would require drying and grinding to be turned into a fine powder [3]. The chemical properties of GGBS has shown similarities to the OPC's properties [29], for example, both materials have the formation of CSH gel, however it was stated that; it exists more in GGBS than in OPC and that is a factor in allowing the concrete to gain its strength once GGBS is used as an admixture [30]. The use of GGBS in concrete structure is spreading and chosen often in Europe and recording a grow in utilization in United States of America, Japan and Singapore [31]. Suresh and Nagaraju [31] stated the major benefits of using GGBS in ready mixed concrete such as improving the workability, reducing the risk of thermal cracking, reduce the Alkali Silica Reaction (ASR) and reduce the possibility of reinforcement corrosion.

The OPC replacement with GGBS in the mixing of concrete to be used in reinforced concrete structure members such as beams has been under the study by many authors. Deepa and Anup [3] conducted experimental investigation with the aim of decreasing the cost and environmental impact of normal concrete by using GGBS and recycled coarse aggregate (RCA) in casting reinforced beams. The study found that the combination of 20% of both GGBS and RCA is the optimum mix that would attain the maximum strength for beams with similar flexural behavior, deflection and crack pattern to ordinary reinforced concrete beams. Hawileh et al [7] and Abbas et al [32] argued that there was a lack of research done on high replacement percentage of OPC with GGBS on beams. The study conducted tests on eight beams sample with replacement of 50, 70, and 90%. The samples were compared relatively against beams with 0% GGBS. The investigation reported that the 70% replacement of OPC with GGBS is the optimum combination as it showed similarities in performance to the control mixture (0% GGBS). Concrete is known to be a fragile material that would fail under brittle failure.

Limited studies explored the combined impact of substituting OPC by GGBS and length of steel bars on the flexural performance of reinforced concrete beams. Therefore, this research was conducted with the aim of investigating both the impact of substituting the OPC by high volume (40% and 60%) GGBS and the utilization of steel bars with different lengths (400 mm and 500 mm) on the flexural strength of reinforced concrete beams.

2. Materials and Methodology

2.1. Materials

2.1.1. Binder Materials

The binders that utilized in this article were GGBS and OPC. The kind of cement was CEM-II/A/LL 32.5-N. The binder materials (GGBS and OPC) were supplied by Hanson Heidelberg Cement and CEMEX, United Kingdom, respectively. The GGBS and OPC chemical compositions was investigated by an Energy Dispersive X-ray Florescence Spectrometer (EDXRF) brand Shimadzu EDX-720. Table 1 demonstrated the GGBS and OPC chemical analysis.

Table 1. Chemical Analysis of GGBS and OPC.

Composition	OPC	GGBS
CaO	65.21	42.51
SiO ₂	24.56	41.06
Al ₂ O ₃	1.7	5.12
Fe ₂ O ₃	1.64	-
MgO	01.3	4.25
Na ₂ O	01.34	3.09
K ₂ O	0.82	0.69
SO ₃	2.62	1.27
TiO ₂	-	0.98
LOI	0.28	0.37
pH	12.73	11.02

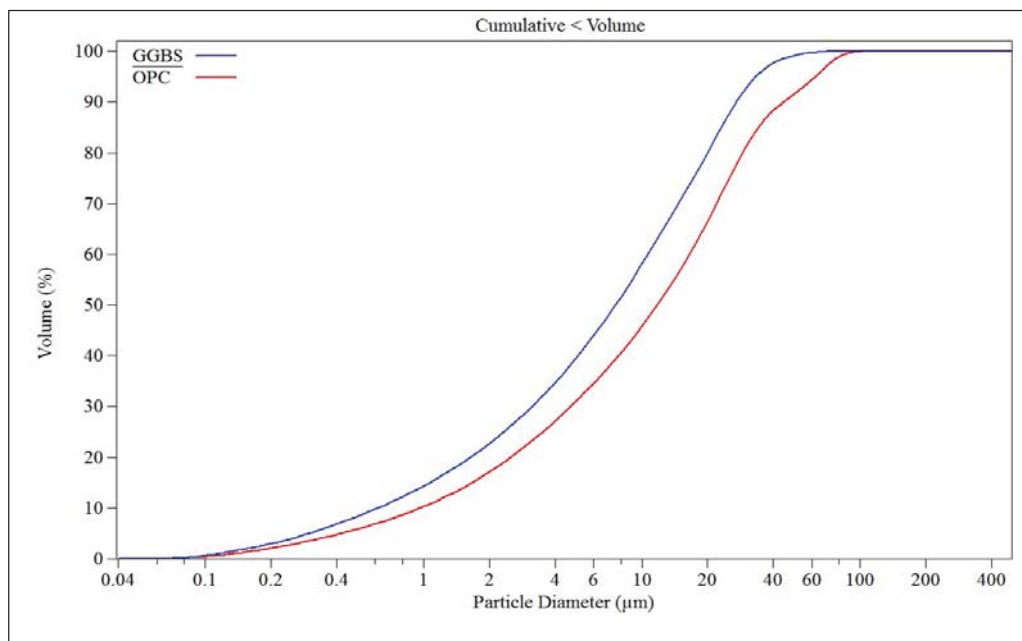


Figure 1. GGBS and OPC particle distribution curve.

The distribution of particle size (PSD) is a major physical examination that gives details on the binder materials scale. The (GGBS and OPC) particle size distribution collected from the analyser laser particle size as demonstrated in Figure 1. The compressive strength of concrete and mortar is greatly influenced by the PSD of the binder components (GGBS and OPC). In concrete and mortar manufacturing, the fine particles of the substance utilized as partial substitute for cement, in order to gain the better compressive strength [33]. In Figure 1, it could be shown from the distribution line graph of particle size that GGBS is finer particles compared to OPC. This implies that the performance of concrete beams will be increased by applying GGBS.

2.1.2. *Fine and Coarse Aggregate.* For the preparation of the mortar specimens, building sand moving from sieve size 3.35 mm has been utilized. The British standard BS EN 196-1 defines this form of sand. The distribution of the particle size of the sand is given in Figure 2. Additionally, limestone coarse aggregate was used with 20 mm maximum size in preparing all the concrete mixtures.

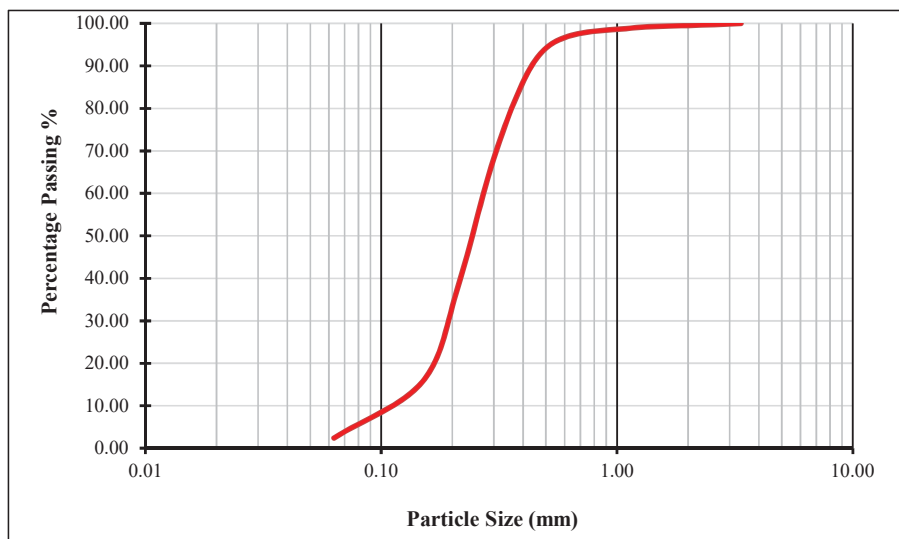


Figure 2. Sand particle distribution curve

2.1.3. *Steel bar.* Steel bars with 8 mm diameter with different length 400 mm and 500 mm was used as a reinforcement for concrete beam.

2.2. Methodology

2.2.1. *Step one.* Three sets of samples (six beams) have been cast and checked by Phase One. 2 beams have been evaluated as follows to every set.

All the selected beams were checked for flexural strength and the findings were contrasted with the control beam of 100 percent Portland cement (First Set). The optimum performed beam has been sent to the second stage for 400 mm steel bar length testing. The approach of using one steel bar reinforcement is suggested by the authors.

Table 2. Mixing proportions for step one.

	OPC	GGBS	Age of test	The length of steel bars
First Set	100%	0%	Seven days	500 mm
Second Set	40%	60%	Seven days	500 mm
Third Set	60%	40%	Seven days	500 mm

2.2.2. *Step two.* At the step two, either the 60 percent or 40 percent concrete based GGBS will be tested at 7 days based on their performance at the first step but with 400 mm steel bar this time. The main aim of decreasing the length of the steel bar is to reduce the cost of the used materials and this approach is suggested by the authors. The increasing in the GGBS% which may resist the flexural strength, is the more eco-friendly concrete (With less OPC).

At the same Step, two beams were tested and the results were compared with the specimens of the similar percent but various steel bar length.

2.2.3. *Step three.* Depending on the results gained from the Step 2, the optimum specimen with best performance (either 60 percent or 40 percent GGBS with steel bar length of 400 mm or 500 mm) will be chosen for the third stage.

At the same Step, three beams were tested at age (7, 14 and 28 days to determine the performance at various testing ages

The performance of different reinforced concrete beams with dimensions of 500 x 100 x 100 mm (Figure 3) was evaluated by flexural strength test that was conducted through four points loading (Figure 4). Table 3 provided details about the concrete mix design used in this investigation.

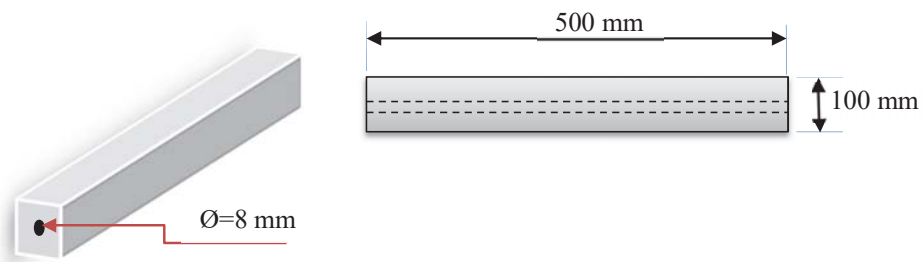


Figure 3. Beam cross-section and details.

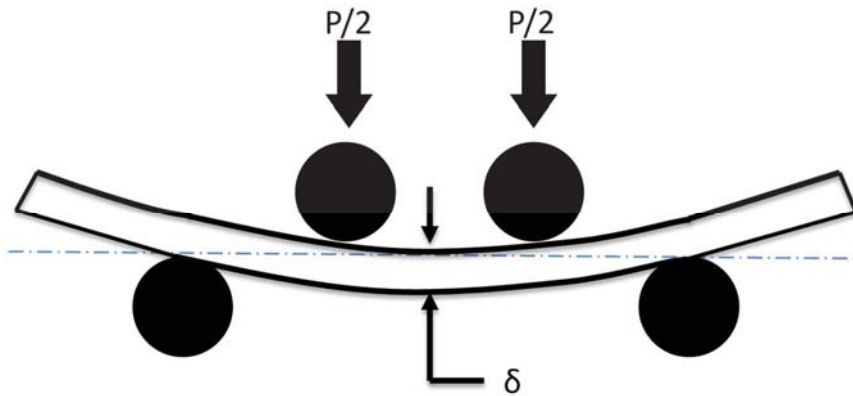


Figure 4. Loading condition for all tested beams.

Table 3. The mixing design of the Concrete

Amounts	Cement	Water	Fine aggregate	Coarse aggregate
Per m ³	456	205	528	1231
0.005 m ³ (for every beam)	2.28	1.025	2.64	6.155

*All materials was measured in kg

3. Results and Discussion

3.1. Effect of GGBS

The using of GGBS in concrete works as an alternative material that showed similar behavior as normal concrete with OPC only due to the similar chemical composition OPC and GGBS as shown in Table 1. Table 4 and Figure 5 show that with increasing GGBS replacing ratio the average flexural Strength decreased. Using of 40% and 60% GGBS lead to decrease the average flexural Strength from 1.625 MPa for control sample with 0% GGBS to 1.19 MPa and 0.905 MPa, respectively. As the mixture with 40% GGBS (Second Set) showed better performance than the mixture with 60% GGBS (Third Set), therefore, Second Set mixtures was used in Step 2.

Table 4. Step 1 flexural strength results (MPa) at the age of 7 days.

Step 1					
OPC	GGBS	The length of bars	Specimen 1	Specimen 2	Average flexural Strength (MPa)
100%	0%	500 mm	1.63	1.62	1.625
60%	40%	500 mm	1.18	1.2	1.19
40%	60%	500 mm	0.89	0.92	0.905

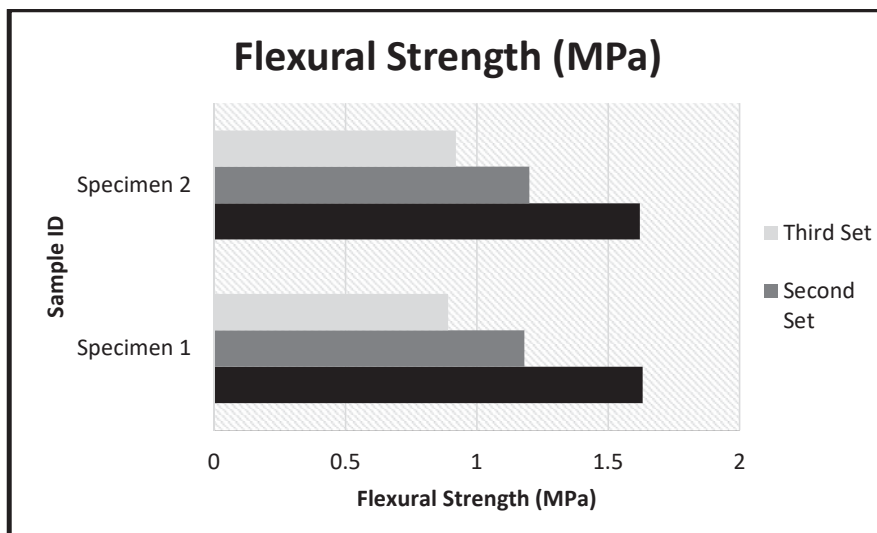


Figure 5. Flexural Strength Results using 500 mm steel bars.

3.2. Effect of steel bar length

The changing in the steel bar length cause an effect on the Average flexural Strength. Table 5 shows that the decreasing the steel bar length affected negatively on the Average flexural Strength (MPa) at 7 curing age. In comparison with second set in the first step, it has been shown decreasing steel bar length from 500 mm to 400 mm lead to decrease the average flexural Strength from 1.19 MPa to 0.885 MPa. Therefore, 500 mm steel bar length was considered as the optimum bar length that utilised in Step 3.

Table 5. Step 2 flexural strength (MPa) at the age of 7 days

Step 2					
OPC	GGBS	The length of bars	Specimen 1	Specimen 2	Average flexural Strength (MPa)
60%	40%	400 mm	0.89	0.88	0.885

3.3. Effect of curing age

As well known the curing age has significant effect on the strength of the concrete samples with Pozzalanic materials due to the hydration of cement and creating of cement gel increase with extend the curing age from 7 to 28 days. Table 6 shows that with 500 mm steel bar length, the average flexural strength was increases from 1.19 MPa at 7 days to 1.72, 1.995 MPa after 14 and 28 days of curing, respectively. This improvement in the flexural strength with increasing the age of curing is mainly attributed to the glassy phase of GGBS, which takes longer time to react with water [34–38].

Table 6. Step 3 flexural strength (MPa) at age 7, 14 and 28 days

Step 3					
OPC	GGBS	bar length (mm)	Ave flexural (MPa)Strength at 7 days	Ave flexural (MPa)Strength at 14 days	Ave flexural (MPa)Strength at 28 days
60	40	500	1.19	1.72	1.995

4. Conclusion

The aim of this research was to investigate the impact of high volume GGBS replacement and steel bar length on flexural behaviour of reinforce concrete beams. Based on the obtained results, it can conclude that:

1. The use of slag in concrete resulted in decreasing the average flexural strength and the ratio of decreasing increased with increase the GGBS content
2. The reduction in the length of steel bar lead to decrease the average flexural strength for the same replacement ratio.
3. There is a significant improvement in the flexural strength of concrete beams incorporated GGBS with extending the age of curing from 7 to 28 days by about 68%.

5. Recommendations for future studies

It is worth mentioning that the drawn conclusions are within the study limitations and conditions. Therefore, changing any of the conditions could significantly affect the results. For future investigations, authors recommended the utilization of different waste and/or by products in the production of RC beams to improve the sustainability and reduce the cost of such wastes and/ or by product materials. For example, industrial wastes [39–45], agricultural waste [46,47], municipal solid wastes [48] and waste from water and wastewater planes [19,49]. Moreover, due to the role of openings in reducing time and cost for bending pipes under the beams [50], the application of the replacement method used in this study to reinforced concrete beams with openings is a worthy issue

[51]. Additionally, modeling the RC beams using artificial intelligence model [52] is also recommended.

References

- [1] Hasan Z A, Abed M K and Nasr M S 2019 Studying the Mechanical Properties of Mortar Containing Different Waste Materials as a Partial Replacement for Aggregate *Int. Rev. Civ. Eng.* **10** 155–61
- [2] Shubbar A A, Al-Khafaji Z S, Nasr M S and Falah M W 2020 Using Non-Destructive Tests for Evaluating Flyover Footbridge: Case Study *Knowledge-Based Eng. Sci.* **1** 23–39
- [3] Deepa P R and Anup J 2016 Experimental Study on the Effect of Recycled Aggregate and GGBS on Flexural Behaviour of Reinforced Concrete Beam *Appl. Mech. Mater.* **857** 101–6
- [4] Srinivasa A S 2019 Experimental investigation of Mechanical properties of Geo polymer concrete with GGBS and Hybrid Fibers Experimental investigation of Mechanical properties of Geo polymer concrete with GGBS and Hybrid Fibers
- [5] Zainab S A K, Zainab A M, Jafer H, Dulaimi A F and Atherton W 2018 The effect of using fluid catalytic cracking catalyst residue (FC3R) as a cement replacement in soft soil stabilisation" *Int. J. Civ. Eng. Technol.* **9** 522–33
- [6] Al-Khafaji Z S, AL-Naely H K and Al-Najar A E 2018 A Review Applying Industrial Waste Materials in Stabilisation of Soft Soil *Electron. J. Struct. Eng.* **18** 2
- [7] Hawileh R A, Abdalla J A, Fardmanesh F, Shahsana P and Khalili A 2017 Performance of reinforced concrete beams cast with different percentages of GGBS replacement to cement *Arch. Civ. Mech. Eng.* **17** 511–9
- [8] Kupwade-patil K, Wolf C De, Chin S and Ochsendorf J 2018 Impact of Embodied Energy on materials / buildings with partial replacement of ordinary Portland Cement (OPC) by natural Pozzolanic Volcanic Ash *J. Clean. Prod.* **177** 547–54
- [9] Obaid M K, Nasr M S, Ali I M, Shubbar A A and Hashim K S 2021 Performance of Green Mortar Made from Locally Available Waste Tiles and Silica Fume *J. Eng. Sci. Technol. Technol.* **16**
- [10] Nasr M S, Ali I M, Hussein A M, Shubbar A A, Kareem Q T and AbdulAmeer A T 2020 Utilization of locally produced waste in the production of sustainable mortar *Case Stud. Constr. Mater.* **13** e00464
- [11] Jafer H, Jawad I, Majeed Z and Shubbar A 2021 The development of an ecofriendly binder containing high volume of cement replacement by incorporating two by-product materials for the use in soil stabilization *Sci. Rev. Eng. Environ. Sci.* **30**
- [12] Nasr M S, Hasan Z A and Abed M K 2019 Mechanical Properties of Cement Mortar Made with Black Tea Waste Ash as a Partial Replacement of Cement *Eng. Technol. J.* **37, Part C** 45–9
- [13] Shubbar A A, Sadique M, Shanbara H K and Hashim K 2020 The Development of a New Low Carbon Binder for Construction as an Alternative to Cement *Advances in Sustainable Construction Materials and Geotechnical Engineering* (Springer) pp 205–13
- [14] Shubbar A A, Sadique M, Kot P and Atherton W 2019 Future of clay-based construction materials—A review *Constr. Build. Mater.* **210** 172–87
- [15] Kubba H Z, Nasr M S, Al-Abdaly N M, Dhahir M K and Najim W N 2020 Influence of Incinerated and Non-Incinerated waste paper on Properties of Cement Mortar *IOP Conference Series: Materials Science and Engineering* vol 671 (IOP Publishing) p 12113
- [16] Als Salman A, Assi L N, Ghotbi S, Ghahari S and Shubbar A 2020 Users, Planners, and Governments Perspectives: A Public Survey on Autonomous Vehicles Future Advancements *Transp. Eng.*
- [17] Hasan Z A, Nasr M S and Abed M K 2021 Properties of reactive powder concrete containing different combinations of fly ash and metakaolin *Mater. Today Proc.* **34**
- [18] Nayel I H, Burhan S K and Nasr M S 2018 Characterisation of prepared rice husk ash and its

- effects on strength development in recycled aggregate concrete *IOP Conference Series: Materials Science and Engineering* vol 433 (Institute of Physics Publishing) p 12009
- [19] Abdulraheem F S, Al-Khafaji Z S, Hashim K S, Muradov M, Kot P and Shubbar A A 2020 Natural filtration unit for removal of heavy metals from water *IOP Conference Series: Materials Science and Engineering* vol 888 (IOP Publishing) p 12034
- [20] Nasr M S, Hussain T H, Kubba H Z and Shubbar A A 2020 Influence of using high volume fraction of silica fume on mechanical and durability properties of cement mortar *J. Eng. Sci. Technol.* **15** 2492–506
- [21] Nasr M S, Salih S A and Hassan M S 2016 Pozzolanic Activity and Compressive Strength of Concrete Incorporated nano/micro Silica *Eng. Technol. J.* **34** 483–96
- [22] Nasr M S, Salih S A and Hassan M S 2016 Some Durability Characteristics of Micro Silica and Nano Silica Contained Concrete *J. Babylon Univ. Sci.* **24** 980–90
- [23] Hasan Z A, Nasr M S and Abed M K 2019 Combined Effect of Silica Fume, and Glass and Ceramic Waste on Properties of High Strength Mortar Reinforced with Hybrid Fibers *Int. Rev. Civ. Eng.* **10** 267–73
- [24] Hussain T H, Nasr M S and Salman H J 2019 Effect of elevated temperature on degradation behaviour of reactive powder concrete made with rubber tire wastes as an aggregate replacement *ARPJ. Eng. Appl. Sci.* **14** 775–80
- [25] Tuama W K, Kadhum M M, Alwash N A, Al-Khafaji Z S and Abdulraheem M S 2020 Effect of Crude Oil Products on the Mechanical Characteristics of Reactive-Powder and Normal Strength-Concrete *Period. Polytech. Civ. Eng.* **64** 422–9
- [26] Nasr M S, Hasan Z A, Abed M K, Dhahir M K, Najim W N, Shubbar A A and Dhahir H Z 2021 Utilization of High Volume Fraction of Binary Combinations of Supplementary Cementitious Materials in the Production of Reactive Powder Concrete *Period. Polytech. Civ. Eng.* **65** 335–43
- [27] Shubbar A A, Sadique M, Nasr M S, Al-Khafaji Z S and Hashim K S 2020 The impact of grinding time on properties of cement mortar incorporated high volume waste paper sludge ash *Karbala Int. J. Mod. Sci.* **6** 396–403
- [28] Al Hawesah H, Shubbar A and Al Mufti R L 2018 Non-destructive assessment of early age mortar containing stainless steel powder *Proceedings of the LJMU 17th Annual International Conference on: Asphalt, Pavement Engineering and Infrastructure* (Liverpool, UK: LIVERPOOL CENTRE FOR MATERIALS TECHNOLOGY)
- [29] Shubbar A A, Jafer H, Abdulredha M, Al-Khafaji Z S, Nasr M S, Al Masoodi Z and Sadique M 2020 Properties of cement mortar incorporated high volume fraction of GGBFS and CKD from 1 day to 550 days *J. Build. Eng.* **30** 101327
- [30] Rajaram M, Ravichandran A and Muthadhi A 2019 Flexural performance of over-reinforced beam containing hybrid fibres with GGBS *SN Appl. Sci.* **1**
- [31] D.Suresh and K.Nagaraju 2015 Ground Granulated Blast Slag (GGBS) In Concrete – A Review *J. Mech. Civ. Eng.* **12** 76–82
- [32] Abbas A N, Al-Naely H K, Abdulzahra H H and Al-Khafaji Z S 2018 Structural behavior of reinforced concrete beams having construction joint at different elevation *Int. J. Civ. Eng. Technol.* **9** 712–20
- [33] Shubbar A A F, Atherton W, Jafer H M, Dulaimi A F and Al-Faluji D 2017 The Development of a New Cementitious Material Produced from Cement and GGBS *The 3rd BUiD Doctoral Research Conference-Faculty of engineering and IT (BUiD)* pp 51–63
- [34] Shubbar A A, Al-Shaer A, AlKizwini R S, Hashim K, Al Hawesah H and Sadique M 2019 Investigating the influence of cement replacement by high volume of GGBS and PFA on the mechanical performance of cement mortar *IOP Conference Series: Materials Science and Engineering* vol 584 (IOP Publishing) p 12022
- [35] Shubbar A A F, Jafer H M, Dulaimi A F D, Atherton W and Al-Rifaie A 2017 The Development of a Low Carbon Cementitious Material Produced from Cement, Ground

- Granulated Blast Furnace Slag and High Calcium Fly Ash *Int. J. Civil, Environ. Struct. Constr. Archit. Eng.* **11** 905–8
- [36] Majidi H S, Shubbar A A, Nasr M S, Al-Khafaji Z S, Jafer H, Abdulredha M, Masoodi Z Al, Sadique M and Hashim K 2020 Experimental data on compressive strength and ultrasonic pulse velocity properties of sustainable mortar made with high content of GGBFS and CKD combinations *Data Br.* **31** 105961
- [37] Shubbar A A, Al-Jumeily D, Aljaaf A J, Alyafei M, Sadique M and Mustafina J 2019 Investigating the Mechanical and Durability Performance of Cement Mortar Incorporated Modified Fly Ash and Ground Granulated Blast Furnace Slag as Cement Replacement Materials *2019 12th International Conference on Developments in eSystems Engineering (DeSE) (IEEE)* pp 434–9
- [38] Shubbar A A, Jafer H, Dulaimi A, Hashim K, Atherton W and Sadique M 2018 The development of a low carbon binder produced from the ternary blending of cement, ground granulated blast furnace slag and high calcium fly ash: an experimental and statistical approach *Constr. Build. Mater.* **187** 1051–60
- [39] Shanbara H K, Shubbar A, Ruddock F and Atherton W 2020 Characterizing the Rutting Behaviour of Reinforced Cold Mix Asphalt with Natural and Synthetic Fibres Using Finite Element Analysis *Advances in Structural Engineering and Rehabilitation* (Springer) pp 221–7
- [40] Ali I M, Naje A S and Nasr M S 2020 Eco-Friendly Chopped Tire Rubber as Reinforcements in Fly Ash Based Geopolymer Concrete *Glob. NEST J.* **22** 342–7
- [41] Nayel I H, Nasr M S and Abdulridha S Q 2020 Impact of elevated temperature on the mechanical properties of cement mortar reinforced with rope waste fibres *IOP Conference Series: Materials Science and Engineering* vol 671 (Institute of Physics Publishing)
- [42] Hussain A J and Al-Khafaji Z S 2020 The fields of applying the recycled and used oils by the internal combustion engines for purposes of protecting the environment against pollutions *J. Adv. Res. Dyn. Control Syst.* **12** 698–706
- [43] Nasr M S, Shubbar A A, Abed Z A-A R and Ibrahim M S 2020 Properties of eco-friendly cement mortar contained recycled materials from different sources *J. Build. Eng.* **31** 101444
- [44] Abed M, Nasr M and Hasan Z 2018 Effect of silica fume/binder ratio on compressive strength development of reactive powder concrete under two curing systems *MATEC Web of Conferences* vol 162 (EDP Sciences) p 02022
- [45] Nasr M S, Hussain T H and Najim W N 2018 Properties of cement mortar containing biomass bottom ash and sanitary ceramic wastes as a partial replacement of cement *Int. J. Civ. Eng. Technol.* **9** 153–65
- [46] Ali I M, Nasr M S, Naje A S, Salah N M and Samir N A 2020 Enhancement of cured cement using environmental waste: particleboards incorporating nano slag *Open Eng.* **10** 273
- [47] Al Khafaji Z S and Ruddock F 2018 Study the retardant effect of using different sugar's types on setting time and temperature of cement paste *Int. J. Civ. Eng. Technol.* **9** 519–30
- [48] Abdulredha M, Abdulridha A, Shubbar A A, Alkhaddar R, Kot P and Jordan D 2020 Estimating municipal solid waste generation from service processions during the Ashura religious event *IOP Conference Series: Materials Science and Engineering* vol 671 (IOP Publishing) p 12075
- [49] Mohammed A-H, Hussein A H, Yeboah D, Al Khaddar R, Abdulhadi B, Shubbar A A and Hashim K S 2020 Electrochemical removal of nitrate from wastewater *IOP Conference Series: Materials Science and Engineering* vol 888 (IOP Publishing) p 12037
- [50] Shubbar A A F, Alwan H, Phur E Y, McLoughlin J and Al-khaykan A 2017 Studying the Structural Behaviour of RC Beams with Circular Openings of Different Sizes and Locations Using FE Method *Int. J. Civil, Environ. Struct. Constr. Archit. Eng.* **11** 849–52
- [51] Jabbar D N, Al-Rifaie A, Hussein A M, Shubbar A A, Nasr M S and Al-Khafaji Z S 2021 Shear behaviour of reinforced concrete beams with small web openings *Mater. Today Proc.* **34**
- [52] Zhang G, Ali Z H, Aldlemy M S, Mussa M H, Salih S Q, Hameed M M, Al-Khafaji Z S and

Yaseen Z M 2020 Reinforced concrete deep beam shear strength capacity modelling using an integrative bio-inspired algorithm with an artificial intelligence model *Eng. Comput.* 1–14