



LJMU Research Online

Hanoon, DS, Sallal, AK, Shubbar, AAF, Al-Khafaji, ZS, Nasr, MS, Al-Mamoori, SF, Al-Fehaida, A, Abdulraheem, MS, Abdulzahra, FR, Alkhayyat, A, Al-Rifaie, A and Hashim, KS

Early age assessment of cement mortar incorporated high volume fly ash

<http://researchonline.ljmu.ac.uk/id/eprint/14682/>

Article

Citation (please note it is advisable to refer to the publisher's version if you intend to cite from this work)

Hanoon, DS, Sallal, AK, Shubbar, AAF, Al-Khafaji, ZS, Nasr, MS, Al-Mamoori, SF, Al-Fehaida, A, Abdulraheem, MS, Abdulzahra, FR, Alkhayyat, A, Al-Rifaie, A and Hashim, KS (2021) Early age assessment of cement mortar incorporated high volume fly ash. IOP Conference Series: Materials

LJMU has developed **LJMU Research Online** for users to access the research output of the University more effectively. Copyright © and Moral Rights for the papers on this site are retained by the individual authors and/or other copyright owners. Users may download and/or print one copy of any article(s) in LJMU Research Online to facilitate their private study or for non-commercial research. You may not engage in further distribution of the material or use it for any profit-making activities or any commercial gain.

The version presented here may differ from the published version or from the version of the record. Please see the repository URL above for details on accessing the published version and note that access may require a subscription.

For more information please contact researchonline@ljmu.ac.uk

<http://researchonline.ljmu.ac.uk/>

PAPER • OPEN ACCESS

Early age assessment of cement mortar incorporated high volume fly ash

To cite this article: Dhoha Saad Hanoon *et al* 2021 *IOP Conf. Ser.: Mater. Sci. Eng.* **1090** 012019

View the [article online](#) for updates and enhancements.



240th ECS Meeting ORLANDO, FL

Orange County Convention Center **Oct 10-14, 2021**



Abstract submission due: April 9

SUBMIT NOW

Early age assessment of cement mortar incorporated high volume fly ash

Dhoha Saad Hanoon ¹, Ali Kadhim Sallal ¹, Ali A. Shubbar ^{2,*}, Zainab S. Al-Khafaji ³, Mohammed Salah Nasr ⁴, Shahad F. Al-Mamoori ⁵, Ali Al-Fehaida ², Mustafa S. Abdulraheem ⁵, Firas R. Abdulzahra ⁶, Ahmed Alkhayyat ⁷, Ali Al-Rifaie ⁸ and Khalid Hashim²

¹ Ministry of Iraqi Oil / Oil Product Distribution Company, Babylon, Iraq.

² Department of Civil Engineering, Liverpool John Moores University, UK.

³ Al-Furra Al-Awsat Distribution Foundation \ Ministry of Oil \ Babylon, Iraq.

⁴ Babylon Technical Institute, Al-Furat Al-Awsat Technical University, 51015 Babylon, Iraq.

⁵ Department of Civil Engineering, College of Engineering, University of Babylon, Iraq.

⁶ Department of planning and Development, General Company of Electricity Distribution for the Middle Region, Karbala Branch, Karbala, Iraq.

⁷ Department of Building and Construction Technical Engineering, College of Technical Engineering, the Islamic University, 54001 Najaf, Iraq.

⁸ College of Engineering, Al-Muthanna University, Samawah, 66001, Iraq.

* Corresponding author: alishubbar993@gmail.com , A.A.Shubbar@2014.ljmu.ac.uk

Abstract. The technique of replacing the cement with other alternative materials focuses on the production of materials with similar performance and reduced environmental impacts relative to traditional cement. The main aim of this study is to investigate the effect of replacing the cement content with high volume of Pulverised Fuel Ash (PFA) on the mechanical performance of cement mortar. Three mixtures were prepared with different percentages of PFA (20%, 40% and 60%) as replacement of cement along with other mixture that made with 100% cement as a control mixture. In order to evaluate the performance of the cement mortars, compressive strength and Ultrasonic Pulse Velocity (UPV) tests after 7, 14 and 28 days of curing was used. The results indicated that for all ages of curing, the increase of PFA contents caused a reduction in the compressive strength and UPV in comparison with the control mixture. After 28 days of curing, the results indicated that the mixture incorporated 20% PFA has similar UPV value relative to the control mixture. Such findings will significantly contribute in reducing the cost of the produced mortar by reducing the amount of used cement and this consequently reduce the cement demands/manufacturing. Less production of cement will reduce the Carbon Dioxide (CO₂) emissions of the cement industry.

1. Introduction

After water, the second most used material in the world is concrete [1]. Cement is the indispensable component in concrete. When blend cement, sand and water produced cement mortar (The word "mortar" comes from Latin mortarium, meaning crushed). It is the most common and economic binding materials used in construction industry. It is used in many phases of civil engineering workings such as masonry, brickwork, flooring, roofing, etc. wherefore, the demand for cement is increasing. According



to International Energy Agency (IEA) [2] and particularly in India, the growing countries of Asia and Africa, cement is not expected to decline in the coming years, to build and develop their infrastructure, but contrarily it is gradually increasing. Cement industry caused for about 5-8% of greenhouse gases that affected badly on the weather [3-12]. The third-largest anthropogenic source (human-caused) emissions of carbon dioxide, after destroying forests and burning fossil fuels for transport and electricity generation is the manufacturing of cement industry [13-17]. Cement industry produces about 7% of global anthropogenic emissions of CO₂ [18-29].

The main raw materials used in cement industry are clay and limestone in addition to sand and iron. From a chemically point of view, cement is composed of four oxides: SiO₂, Al₂O₃, CaO, and Fe₂O₃. A rock that consists mostly of calcium carbonate (CaCO₃) is limestone. In order to break CaCO₃ down into CaO and CO₂ the calcined limestone is heated in a furnace. The resulting CO₂ is free to the atmosphere. Calcination releases about 0.5 kg of carbon dioxide in producing 1 kg of clinker (dry powder). In order to complete this chemical reaction, in special ovens or kilns a large amounts of fuel are burned to provide heat for calcination. During calcination of limestone in conventional kilns much of the heat energy supplied by fuel-burning is wasted, through replacing more efficient equipment and using "dry" calcination processes rather than "wet" calcination processes, direct fuel usage can be reduced by up to 48%, which would reduce CO₂ emissions by 27% [2]. Without diminishing profits, some estimates of how much efficiency can be enhanced are as low as 11%, which would yield a CO₂ reduction of only 5% [2]. To reduce CO₂, low carbon fuels can be used such as natural gas, as well as converting construction practices to the use of mixed cement, it is the cement in which is used industrial wastes such as coal fly ash (the ash left over from burning coal in power plants) or volcanic ash instead of some limestone-based clinker [30].

In coal-fired electricity power stations when pulverized coal burns, it's produced ash that's call pulverized fuel ash (PFA). Electrostatic precipitators remove very fine ash from the flue gases. The PFA chemical composition is slightly different from Portland Cement (PC). In order to hydrate the PFA, it needs lime and water together not water directly. In combination with PC, always used fly ash, usually in range (20% PFA to 80% PC) up to (40% PFA to 60% PC) according to application. The aim of using fly ash in the concrete engineering as important mineral admixtures is reducing concrete materials cost, environmental problems reducing and conserving energy and resources [19, 23].

2. Materials and Methodology

2.1. Materials

The Portland Cement (PC) and Pulverised Fuel Ash (PFA) materials were used in this research. The cement was PC type CEM-II/A/LL 32.5-N. By CEMEX ltd Company, Warwickshire, UK, both PC and PFA were supplied.

By an Energy Dispersive X-ray Florescence Spectrometer (EDXRF) type Shimadzu EDX-720, the elemental composition of PC and PFA was analysed. The PC and PFA chemical compositions are shown in Table 1.

Table 1. Chemical composition of PC and PFA.

Item	PC	PFA
CaO %	65.21	4.81
SiO ₂ %	24.56	58.83
Al ₂ O ₃ %	1.70	18.83
Fe ₂ O ₃ %	1.64	5.54
MgO %	1.30	3.86
Na ₂ O %	1.34	1.17
K ₂ O %	0.82	2.04
SO ₃ %	2.62	1.06
TiO ₂ %	-	1.19
LOI %	0.28	2.67
pH	12.73	10.68
Specific Gravity	2.94	2.49

2.2. Mixing proportions

In this study, three different binary blends designed by using different proportion mixtures of PC and PFA in addition to the traditional binder (0% PFA) as illustrated in Table 2. The ratio of sand to binder (S/B) and water to binder (W/B) were, 2.5 and 0.4, respectively for all mortar blends.

Table 2. Mixing proportions.

No.	Cement %	PFA %	Ratio of Sand to binder	Ratio of Water to binder
Control Mix	100	0	2.5	0.4
PFA 20%	80	20	2.5	0.4
PFA 40%	60	40	2.5	0.4
PFA 60%	40	60	2.5	0.4

2.3. Experiments method

In this study, the UPV test and compressive strength test for all samples were subjected to an extensive range of curing period included early (1,2,3 and 7 days) ages and later (14, 21 and 28 days), to assess how compressive strength and UPV of different samples affected by curing period.

2.3.1. Compressive strength

According to BS EN 196-1 [31], the test of compressive strength was achieved by using two specimens with dimensions of 40x40x160 mm at different curing periods (1-28 days), to evaluate the mechanical characteristics of the cement mortars. Every specimen was broken by three loading points into two part of the prism samples and the result of compressive strength was represented by an average value of four parts.

2.3.2. UPV test

UPV test of concrete is a non-destructive test to evaluate the durability and homogeneity of concrete according to BS 1881-203 [32]. (Three specimens with dimensions of (10x10x10) cm were produced for each mixing proportion at each curing period).

3. Experimental Results

3.1. The compressive strength results

All mixtures strength was increased constantly with time. Figures (1 and 2) showed that compared with control mix, all the mixtures contains (PFA) given lower strength at all ages and strength decreased as PFA content increased.

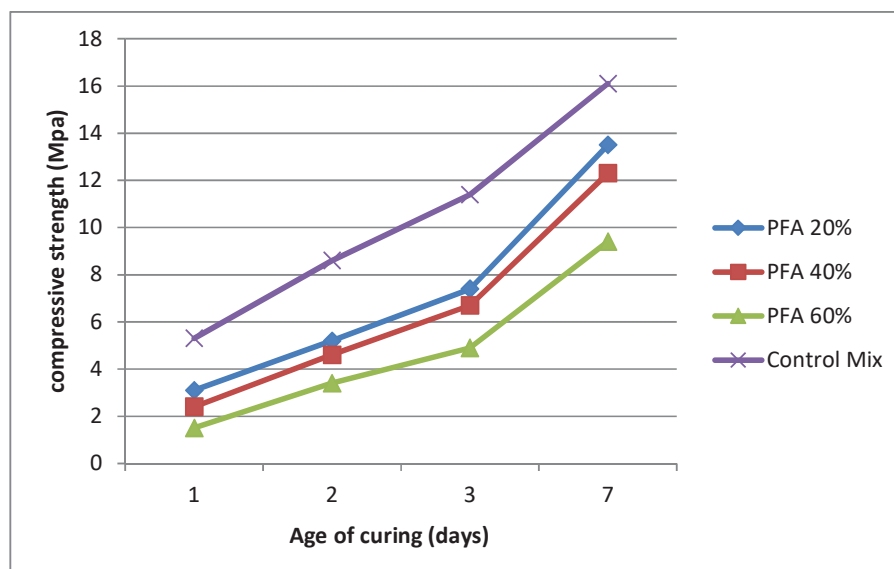


Figure 1. Compressive strength development of different mixtures at early ages.

The mixtures PFA20%, PFA40% and PFA60% have showed about 58%, 45% and 28% of the control mix's compressive strength, at one day of the curing period. The mixtures compressive strength was improved relative to the control blend at 7 days of curing. In comparison with control mixture, the compressive strength of PFA20%, PFA40% and PFA60% at 7 days were 83%, 76% and 58%, respectively. With an increasing the percentages of PFA, during the first week there is a decrease in compressive strength might be refer to the slow gaining of strength for blend mortars with high volume of PFA at early curing periods [33, 34]. The control mixture improvement was about 18% after 14 days of curing, while all other mixtures compressive strength have been improved by about 21% relative to that at the 7 days of curing. The mixtures PFA20%, PFA40% and PFA60% compressive strength were about 85%, 74% and 67%, respectively, 14 days after curing. The mixture PFA20% compressive strength was 19.7 MPa, at the age of 28 days that was about 84% of the control mixture compressive

strength (23.2 MPa). Nevertheless, the blends PFA40% and PFA60% providing about 75% and 68%, respectively relative to control mixture's compressive strength.

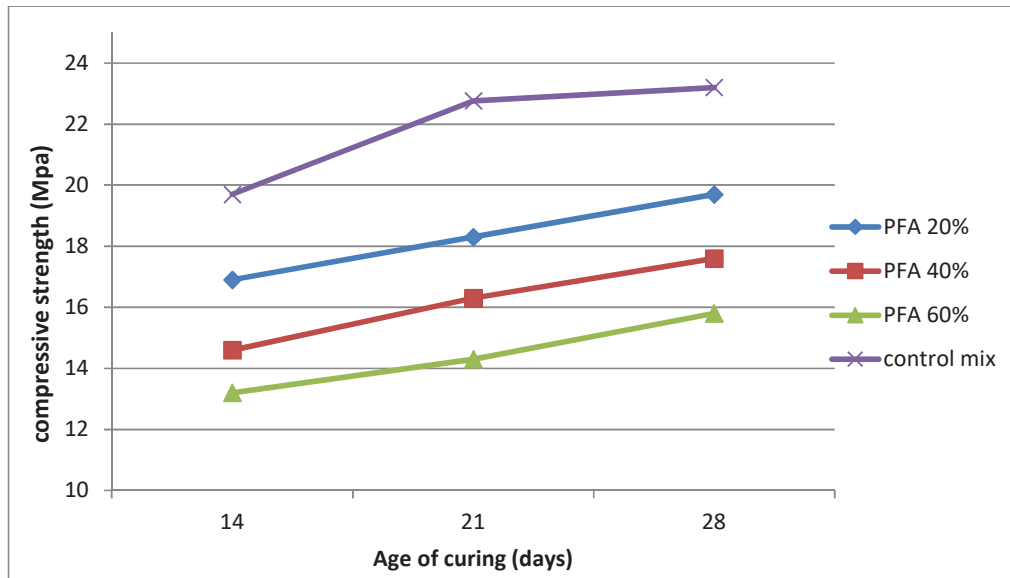


Figure 2. Compressive strength development of different mix proportion at later ages

3.2. The UPV results

Figures 3 and 4 present the results of the UPV of all mixtures during the investigated curing periods. As can be seen from both Figure 3 that the value of the UPV decreased when the PFA content increasing at early ages (1, 2, 3 and 7 days). Additionally, for all mixtures with PFA, the UPV values were lower than that of the control mix. On the other hand, increasing the age of curing to 14 and days, the results showed that the mixture with PFA 60% showed higher UPV value relative to the mixture PFA 40%. At the age of 28 days, the results in Figure 4 showed that the mixture PFA 20% has similar UPV value relative to the control mixture. Moreover, after 28 days of curing the mixture PFA 40% has better UPV value relative to the mixture PFA 60%.

It has been reported previously by Mohseni et al. [35] and Shubbar et al. [36] that the UPV value of mortar is in the range between 3660 m/s to 4575 m/s, the mortar can be classified as good durability mortar. According to Figure 4, the mixture PFA 20% can be classified as good durability mortar after only 3 days of curing, while the other mixtures (PFA 40 % and PFA 60%) needed about 21 days of curing to become mortars with good durability.

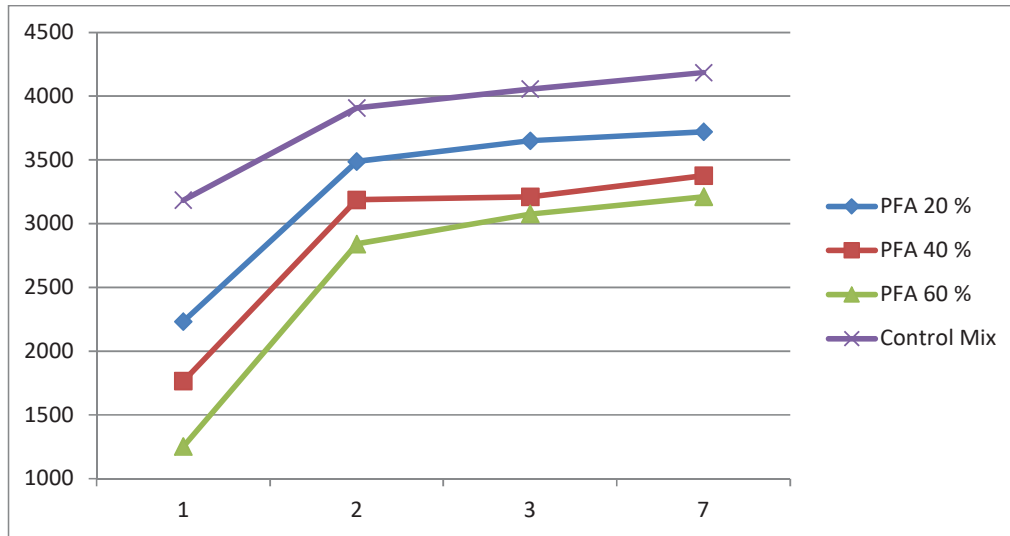


Figure 3. UPV result of different mix proportion at early ages (days)

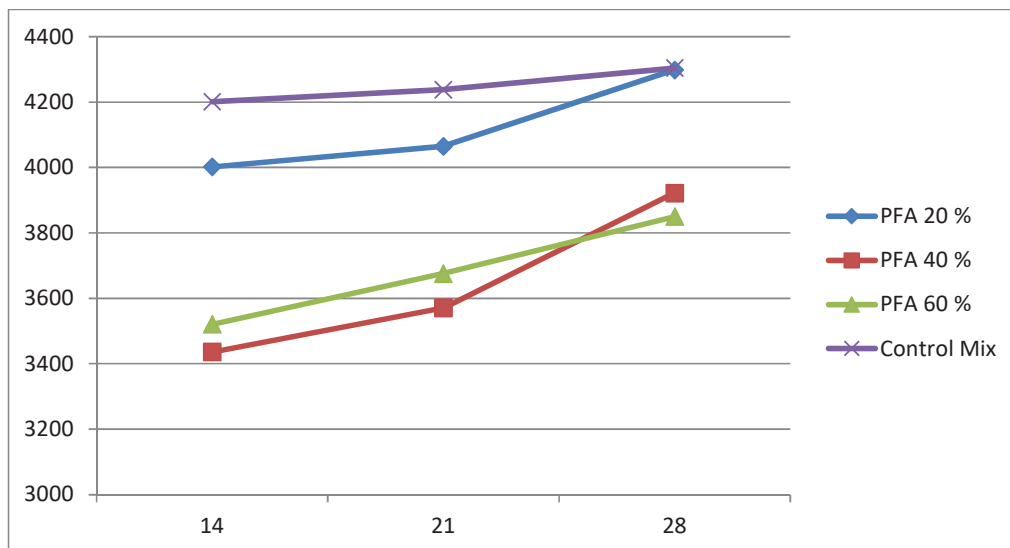


Figure 4. UPV result of different mixtures at later ages (days)

4. Conclusion

The main conclusions from the results of this study are following:

- At early ages (1, 2, 3 and 7) days there was an illustrated significantly decreasing in compressive strength for all sample with different PFA content.
- The use of PFA showed significant increase in the degradation of compressive strength at ages 1 & 7 days with higher percentages of PFA.
- At later ages (14, 21 and 28) days there was a slight strength gain for all sample.

- UPV test showed a decreased in homogeneity and durability of concrete with higher percentages of PFA.
- After 28 days of curing, the mixture PFA 40% showed similar UPV value relative to the control mixture.

For future investigations, authors highly recommending the use of other waste and by/product materials in combination with PFA to enhance the properties of the produced mortars. For example, industrial wastes such as Ground Granulated Blast Furnace Slag (GGBS), Cement Kiln Dust (CKD), stainless steel, silica fume and crude oil wastes [37-58] municipal solid wastes [59] and waste from water and wastewater planes [60-63].

References

- [1] Mineral Products Association 2019 UK cement industry.
- [2] IEA 2019 Tracking industry. (Paris
- [3] Hasan Z, Nasr M and Abed M 2019 Combined Effect of Silica Fume, and Glass and Ceramic Waste on Properties of High Strength Mortar Reinforced with Hybrid Fibers *Int. Rev. Civ. Eng.(IRECE)* **10**
- [4] Kubba H Z, Nasr M S, Al-Abdaly N M, Dhahir M K and Najim W N 2020 Influence of Incinerated and Non-Incinerated waste paper on Properties of Cement Mortar. In: *IOP Conference Series: Materials Science and Engineering*: IOP Publishing) p 012113
- [5] Shubbar A A, Sadique M, Kot P and Atherton W 2019 Future of clay-based construction materials—A review *Construction and Building Materials* **210** 172-87
- [6] Shubbar A A, Sadique M, Shanbara H K and Hashim K 2020 *Advances in Sustainable Construction Materials and Geotechnical Engineering*: Springer) pp 205-13
- [7] Al-Khafaji Z S, Al Masoodi Z, Jafer H, Dulaimi A and Atherton W 2018 The Effect Of Using Fluid Catalytic Cracking Catalyst Residue (FC3R)" As A Cement Replacement In Soft Soil Stabilisation *International Journal Of Civil Engineering And Technology (IJCIET) Volume* **9** 522-33
- [8] Nasr M S, Hussain T H and Najim W N 2018 Properties of Cement Mortar Containing Biomass Bottom Ash and Sanitary Ceramic Wastes as a Partial Replacement of Cement *International Journal of Civil Engineering and Technology (IJCIET)* **9** 153–65
- [9] Hussain A and Al-Khafaji Z 2020 The fields of applying the recycled and used oils by the internal combustion engines for purposes of protecting the environment against pollutions *J. Adv. Res. Dyn. Control Syst.* **12**
- [10] Dulaimi A, Shanbara H K and Al-Rifaie A 2020 The mechanical evaluation of cold asphalt emulsion mixtures using a new cementitious material comprising ground-granulated blast-furnace slag and a calcium carbide residue *Construction and Building Materials* **250** 118808
- [11] Dulaimi A, Shanbara H K, Jafer H and Sadique M 2020 An evaluation of the performance of hot mix asphalt containing calcium carbide residue as a filler *Construction and Building Materials* **261** 119918
- [12] Shubbar A A, Sadique M, Nasr M S, Al-Khafaji Z S and Hashim K S 2020 The impact of grinding time on properties of cement mortar incorporated high volume waste paper sludge ash *Karbala International Journal of Modern Science* **6**
- [13] Nayel I H, Nasr M S and Abdulridha S Q 2020 Impact of elevated temperature on the mechanical properties of cement mortar reinforced with rope waste fibres. In: *IOP Conference Series: Materials Science and Engineering*: IOP Publishing) p 012080
- [14] Nayel I, Burhan S and Nasr M 2018 Characterisation of prepared rice husk ash and its effects on strength development in recycled aggregate concrete. In: *IOP Conference Series: Materials Science and Engineering*, p 012009
- [15] Al-Khafaji Z and Falah M 2020 Applications of high density concrete in preventing the impact of radiation on human health *J Adv Res Dyn Control Syst* **12**

- [16] Al Khafaji Z S and Ruddock F 2018 Study the retardant effect of using different sugar's types on setting time and temperature of cement paste *International Journal of Civil Engineering and Technology* **9**
- [17] Nasr M S, Salih S A and Hassan M S 2016 Some Durability Characteristics of Micro Silica and Nano Silica Contained Concrete *Journal of University of Babylon* **24** 980-90
- [18] Nasr M S, Hasan Z A and Abed M K 2019 Mechanical Properties of Cement Mortar Made with Black Tea Waste Ash as a Partial Replacement of Cement *Engineering and Technology Journal* **37** 45-8
- [19] Shubbar A A, Al-Shaer A, AlKizwini R S, Hashim K, Al Hawesah H and Sadique M 2019 Investigating the influence of cement replacement by high volume of GGBS and PFA on the mechanical performance of cement mortar. In: *IOP Conference Series: Materials Science and Engineering*: IOP Publishing) p 012022
- [20] Shubbar A A, Jafer H, Dulaimi A, Hashim K, Atherton W and Sadique M 2018 The development of a low carbon binder produced from the ternary blending of cement, ground granulated blast furnace slag and high calcium fly ash: An experimental and statistical approach *Construction and Building Materials* **187** 1051-60
- [21] Shubbar A, Jafer H M, Dulaimi A, Atherton W and Al-Rifaie A 2017 The Development of a Low Carbon Cementitious Material Produced from Cement, Ground Granulated Blast Furnace Slag and High Calcium Fly Ash *International Journal of Civil, Environmental, Structural, Construction and Architectural Engineering* **11** 905-8
- [22] Nasr M S, Shubbar A A, Abed Z A-A R and Ibrahim M S 2020 Properties of eco-friendly cement mortar contained recycled materials from different sources *Journal of Building Engineering* 101444
- [23] Shubbar A A, Al-Jumeily D, Aljaaf A J, Alyafei M, Sadique M and Mustafina J 2019 Investigating the Mechanical and Durability Performance of Cement Mortar Incorporated Modified Fly Ash and Ground Granulated Blast Furnace Slag as Cement Replacement Materials. In: *2019 12th International Conference on Developments in eSystems Engineering (DeSE)*: IEEE) pp 434-9
- [24] Hasan Z A, Nasr M S and Abed M K 2021 Properties of reactive powder concrete containing different combinations of fly ash and metakaolin *Materials Today: Proceedings* **34**
- [25] Nasr M S, Ali I M, Hussein A M, Shubbar A A, Kareem Q T and AbdulAmeer A T 2020 Utilization of locally produced waste in the production of sustainable mortar *Case Studies in Construction Materials* **13** e00464
- [26] Nasr M S, Hasan Z A, Abed M K, Dhahir M K, Najim W N, Shubbar A A and Habeeb Z D 2021 Utilization of High Volume Fraction of Binary Combinations of Supplementary Cementitious Materials in the Production of Reactive Powder Concrete *Periodica Polytechnica Civil Engineering* **65** 335-43
- [27] Obaid M K, Nasr M S, Ali I M, Shubbar A A and Hashim K S 2021 Performance of Green Mortar Made from Locally Available Waste Tiles and Silica Fume *Journal of Engineering Science and Technology* **16**
- [28] Shubbar A A, Al-Khafaji Z S, Nasr M S and Falah M W 2020 Using Non-Destructive Tests for Evaluating Flyover Footbridge: Case Study *Knowledge-Based Engineering and Sciences* **1** 23-39
- [29] Jafer H, Jawad I, Majeed Z and Shubbar A 2021 The development of an ecofriendly binder containing high volume of cement replacement by incorporating two by-product materials for the use in soil stabilization *Scientific Review Engineering and Environmental Sciences* **30**
- [30] Aprianti S E 2017 A huge number of artificial waste material can be supplementary cementitious material (SCM) for concrete production – a review part II *Journal of Cleaner Production* **142** 4178-94
- [31] BSI 2005 Methods of testing cement–Part 1: Determination of strength. (London: British Standard Institute)

- [32] BSI 1986 BS 1881-203: Part 203: Recommendations for measurement of velocity of ultrasonic pulses in concrete. . (LONDON: BSI)
- [33] Limbachiya V, Ganjian E and Claisse P 2016 Strength, durability and leaching properties of concrete paving blocks incorporating GGBS and SF *Construction and Building Materials* **113** 273-9
- [34] Attari A, McNally C and Richardson M G 2016 A probabilistic assessment of the influence of age factor on the service life of concretes with limestone cement/GGBS binders *Construction and Building Materials* **111** 488-94
- [35] Mohseni E, Naseri F, Amjadi R, Khotbehsara M M and Ranjbar M M 2016 Microstructure and durability properties of cement mortars containing nano-TiO₂ and rice husk ash *Construction and Building Materials* **114** 656-64
- [36] Shubbar A A, Jafer H, Abdulredha M, Al-Khafaji Z S, Nasr M S, Al Masoodi Z and Sadique M 2020 Properties of cement mortar incorporated high volume fraction of GGBFS and CKD from 1 day to 550 days *Journal of Building Engineering* 101327
- [37] Majdi H S, Shubbar A A, Nasr M S, Al-Khafaji Z S, Jafer H, Abdulredha M, Al Masoodi Z, Sadique M and Hashim K 2020 Experimental data on compressive strength and ultrasonic pulse velocity properties of sustainable mortar made with high content of GGBFS and CKD combinations *Data in Brief* **31** 105961
- [38] Al Hawesah H, Shubbar A and Al Mufti R L 2018 Non-destructive assessment of early age mortar containing stainless steel powder. In: *The 17th Annual International Conference on Asphalt, Pavement Engineering and Infrastructure 21st-22nd February*,
- [39] Shanbara H K, Shubbar A, Ruddock F and Atherton W 2020 *Advances in Structural Engineering and Rehabilitation: Springer* pp 221-7
- [40] Shubbar A, Alwan H, Phur E Y, McLoughlin J and Al-khaykan A 2017 Studying the Structural Behaviour of RC Beams with Circular Openings of Different Sizes and Locations Using FE Method
- [41] Shubbar A, Atherton W, Jafer H M, Dulaimi A and Al-Faluji D 2017 The Development of a New Cementitious Material Produced from Cement and GGBS. In: *The 3rd BUiD Doctoral Research Conference-Faculty of engineering and IT: BUiD*) pp 51-63
- [42] Nasr M S, Hussain T, Kubba H and Shubbar A 2020 Influence of Using High Volume Fraction of Silica Fume on Mechanical and Durability Properties of Cement Mortar *Journal of Engineering Science and Technology* **15** 2494-506
- [43] Hussain T H, Nasr M S and Salman H J 2019 Effect of elevated temperature on degradation behavior of reactive powder concrete made with rubber tire wastes as an aggregate replacement *ARN J. Eng Appl. Sci* **14** 775-80
- [44] Hassan M S, Salih S A and Nasr M S 2016 Pozzolanic Activity and Compressive Strength of Concrete Incorporated nano/micro Silica *Engineering and Technology Journal* **34** 483-96
- [45] Hasan Z, Abed M and Nasr M 2019 Studying the Mechanical Properties of Mortar Containing Different Waste Materials as a Partial Replacement for Aggregate *Int. Rev. Civ. Eng.(IRECE)* **10**
- [46] Zhang G, Ali Z H, Aldlemy M S, Mussa M H, Salih S Q, Hameed M M, Al-Khafaji Z S and Yaseen Z M 2020 Reinforced concrete deep beam shear strength capacity modelling using an integrative bio-inspired algorithm with an artificial intelligence model *Engineering with Computers* 1-14
- [47] Tuama W K, Kadhum M M, Alwash N A, Al-Khafaji Z S and Abdurraheem M S 2020 RPC Effect of Crude Oil Products on the Mechanical Characteristics of Reactive-Powder and Normal-Strength Concrete *Periodica Polytechnica Civil Engineering* **64** 422-9
- [48] Al-Rifaie A, Al-Husainy A S and Shanbara H K 2020 Numerical study on the behaviour of end-plate beam-to-column connections under lateral impact loading *International Journal of Structural Engineering* **10** 150-73

- [49] Shanbara H K, Ruddock F and Atherton W 2017 Improving the Mechanical Properties of Cold Mix Asphalt Mixtures Reinforced by Natural and Synthetic Fibers. In: *International Conference on Highway Pavements & airfield Technology*, pp 102-11
- [50] Ali I M, Naje A S and Nasr M S 2020 Eco-Friendly Chopped Tire Rubber as Reinforcements in Fly Ash Based Geopolymer Concrete *Global NEST Journal* **22**
- [51] Al-Salim N H A, Hassan R F and Jaber M H 2018 Compression Zone Rehabilitation of Damaged RC Beams Using Poleyster Glue Line *Journal of Engineering and Applied Sciences* **13** 1195-200
- [52] Hassan R F, Jaber M H, Al-Salim N H and Hussein H H 2020 Experimental research on torsional strength of synthetic/steel fiber-reinforced hollow concrete beam *Engineering Structures* **220** 110948
- [53] Jaber M H, Al-Salim N H A and Hassan R F 2018 flexural behavior of hollow rectangular steel (HRS) section beams filled with reactive powder concrete *Technology* **9** 1177-87
- [54] Hassan R F, Al-Salim N H A and Jaber M H 2018 Effect of Polyvinyl Alcohol on flexural behavior of RC Bubble slabs under linear load *Journal of Engineering and Applied Sciences* **13** 3979-84
- [55] Ali I M, Nasr M S and Naje A S 2020 Enhancement of cured cement using environmental waste: particleboards incorporating nano slag *Open Engineering* **10** 273-81
- [56] Abed M, Nasr M and Hasan Z 2018 Effect of silica fume/binder ratio on compressive strength development of reactive powder concrete under two curing systems. In: *MATEC Web of Conferences: EDP Sciences*) p 02022
- [57] Alsalman A, Assi L N, Ghotbi S, Ghahari S and Shubbar A 2021 Users, Planners, and Governments Perspectives: A Public Survey on Autonomous Vehicles Future Advancements *Transportation Engineering* 100044
- [58] Jabbar D N, Al-Rifaie A, Hussein A M, Shubbar A A, Nasr M S and Al-Khafaji Z S 2021 Shear behaviour of reinforced concrete beams with small web openings *Materials Today: Proceedings* **34**
- [59] Abdulredha M, Abdulridha A, Shubbar A, Alkhaddar R, Kot P and Jordan D 2020 Estimating municipal solid waste generation from service processions during the Ashura religious event. In: *IOP Conference Series: Materials Science and Engineering: IOP Publishing*) p 012075
- [60] Abdulraheem F S, Al-Khafaji Z S, Hashim K S, Muradov M, Kot P and Shubbar A A 2020 Natural filtration unit for removal of heavy metals from water. In: *IOP Conference Series: Materials Science and Engineering: IOP Publishing*) p 012034
- [61] Mohammed A-H, Hussein A H, Yeboah D, Al Khaddar R, Abdulhadi B, Shubbar A A and Hashim K S 2020 Electrochemical removal of nitrate from wastewater. In: *IOP Conference Series: Materials Science and Engineering: IOP Publishing*) p 012037
- [62] Alenezi A K, Hasan H A, Hashim K S, Amoako-Attah J, Gkantou M, Muradov M, Kot P and Abdulhadi B 2020 Zeolite-assisted electrocoagulation for remediation of phosphate from calcium-phosphate solution. In: *IOP Conference Series: Materials Science and Engineering: IOP Publishing*) p 012031
- [63] Al-Marri S, AlQuzweeni S S, Hashim K S, AlKhaddar R, Kot P, AlKizwini R S, Zubaidi S L and Al-Khafaji Z S 2020 Ultrasonic-Electrocoagulation method for nitrate removal from water. In: *IOP Conference Series: Materials Science and Engineering: IOP Publishing*) p 012073