



Pergamon

Cement and Concrete Research, Vol. 27, No. 9, pp. 1439–1449, 1997

Copyright © 1997 Elsevier Science Ltd

Printed in the USA. All rights reserved

0008-8846/97 \$17.00 + 00

PII S0008-8846(97)00127-0

ON THE PREPARATION OF SINGLE CRYSTALS OF $11\text{CaO}\cdot 7\text{Al}_2\text{O}_3\cdot \text{CaF}_2$ AND THE CONFIRMATION OF ITS CRYSTAL STRUCTURE**Yu Qijun* and Shuichi Sugita**Department of Civil Engineering, Hachinohe Institute of Technology, Myo,
Hachinohe 031, Japan

*From Wuhan University of Technology, P.R. China

Feng Xiuji and Mi JinxiaoInstitute of Materials Science and Engineering, Wuhan University of Technology,
Wuhan 430070, P.R. China

(Refereed)

(Received May 7, 1996; in final form July 7, 1997)

ABSTRACT

Single crystals of $11\text{CaO}\cdot 7\text{Al}_2\text{O}_3\cdot \text{CaF}_2$ ($\text{C}_{11}\text{A}_7\cdot \text{CaF}_2$) of 40–120 μm in size were prepared by a flux evaporation method. The crystals were colorless trigonal tristetrahedrons with a refractive index of 1.601. By the method of single crystal X-ray diffraction it has been confirmed that the $\text{C}_{11}\text{A}_7\cdot \text{CaF}_2$ is cubic, with $a = 11.981\text{\AA}$, space group $\bar{I}43d$, $Z = 2$ and $D_X = 2.720\text{ g cm}^{-3}$. The calcium atom is coordinated either to six oxygen atoms in an irregular $[\text{CaO}_6]$ coordination with 2.380 \AA , 2.401 \AA and 2.502 \AA for Ca-O distances or to six oxygen atoms and one fluorine atom in an asymmetric arrangement with 2.816 \AA for F-Ca distance. The aluminum atoms are coordinated to four oxygen atoms forming two different AlO_4 tetrahedra: (1) the $[\text{Al}(1)\text{O}(2)_4]$, with symmetry $\bar{4}$ and $\text{Al}(1)\text{--O}(2)$ distance = 1.745 \AA ; and (2) the $[\text{Al}(2)\text{O}_4]$ composed of one $\text{Al}(2)$ atom, one $\text{O}(1)$ atom and three $\text{O}(2)$ atoms, with symmetry 3, $\text{Al}(2)\text{--O}(1)$ distance = 1.740 \AA and $\text{Al}(2)\text{--O}(2)$ distance = 1.757 \AA . Neighboring AlO_4 tetrahedra are connected with each other by sharing oxygen atoms resulting in a three dimensional $[\text{AlO}_4]$ network-the basic framework of the crystal structure of $\text{C}_{11}\text{A}_7\cdot \text{CaF}_2$. © 1997 Elsevier Science Ltd

Introduction

It is well known that the utilization of a composite mineralizer composed of fluor spar and gypsum possesses energy-saving advantages and can improve the quality of cement clinker, especially clinker produced in shaft kilns. Sometimes, though, fluoride-bearing cement sets abnormally; a fact which has been observed in both laboratories and plants. Consequently, the application of said cement has been subject to various problems (1–3). Many researchers attributed the reason for the cement's abnormal setting (flash or retarded setting) to: (a) the amount and crystal size of the $\text{C}_{11}\text{A}_7\cdot \text{CaF}_2$ phase; and (b) the variation in hydration activity

TABLE 1
Coordinates of Atoms in the Crystal of $C_{11}A_7\cdot CaF_2$ (After Ref. 6)

Atom	x	y	z	B	Occupancy factor
Ca (1)	0.10824	0	1/4	0.90	0.744
Ca (2)	0.06738	0	1/4	0.90	0.254
Al (1)	3/8	0	1/4	0.37	
Al (2)	0.98089	0.98089	0.98089	0.33	
O (1)	0.06977	0.06977	0.06977	0.79	
O (2)	0.19091	0.28616	0.09919	0.94	
F	7/8	0	1/4	1.29	0.238

of alite in the clinker. Because it is different from C_3A in hydration properties and plays an important role in the setting and hardening of fluoride-bearing cement, $C_{11}A_7\cdot CaF_2$ has attracted much attention. Many studies on its formation and stability at high temperatures as well as its setting and hydration behaviors under different conditions have been done in recent years (1–5).

The crystal structure of $C_{11}A_7\cdot CaF_2$ was revealed by Williams (6,7), who based his observations on powder X-ray diffraction data (Table 1). For purposes of comparison, the coordinates of atoms of $C_{12}A_7$, one of the phases closely related to $C_{11}A_7\cdot CaF_2$, are also presented in Table 2 (8). Table 1 shows that in the unit cell of $C_{11}A_7\cdot CaF_2$ there exist two kinds of calcium atoms: Ca(1) and Ca(2), but from the coordinates of which it can be found that their interatomic distance is only 0.489Å, less than the radius of Ca^{2+} ion ($R_{Ca^{2+}} = 1.00\text{Å}$). From the standpoint of crystallography, it is evident that the Ca sites were somewhat inappropriately determined in this solution. Based on the data shown in Table 1, we tried to analyze the bonding in $C_{11}A_7\cdot CaF_2$ crystal utilizing a quantum chemistry method but ultimately failed. As we have learned through the method of single crystal X-ray diffraction, it is possible to obtain a more exact solution to crystal structure. Thus, single crystal studies will be required to improve on the structure reported by Williams. Using an ordinary crystal growth method will be very difficult to prepare single crystals of $C_{11}A_7\cdot CaF_2$ with a size larger than 50 μm . This difficulty is because a significant amount of fluorine in $C_{11}A_7\cdot CaF_2$ will be released when the heating temperature rises above 1200°C. Feng and Liao *et al.* found single crystals of $C_4A_3\bar{S}$, $11CaO\cdot 7Al_2O_3\cdot CaCl_2$ and $3CaO\cdot 3Al_2O_3\cdot SrSO_4$ greater than 100 μm in size could be obtained at temperatures below 1100°C by a flux evaporation method in which $PbCl_2$ was used as a flux (9,10).

TABLE 2
Coordinates of Atoms in the Crystal of $C_{12}A_7$ (After Ref. 8)

Atom	Wyckoff equipoint symbols	x	y	z
Ca	24d	0.1397	0	1/4
Al (1)	16c	0.0187	0.0187	0.0187
Al (2)	12b	7/8	0	1/4
O (1)	48e	0.1510	-0.0370	0.0570
O (2)	16c	-0.0641	-0.0641	-0.0641
O (3)	24d	-0.3370	0	1/4

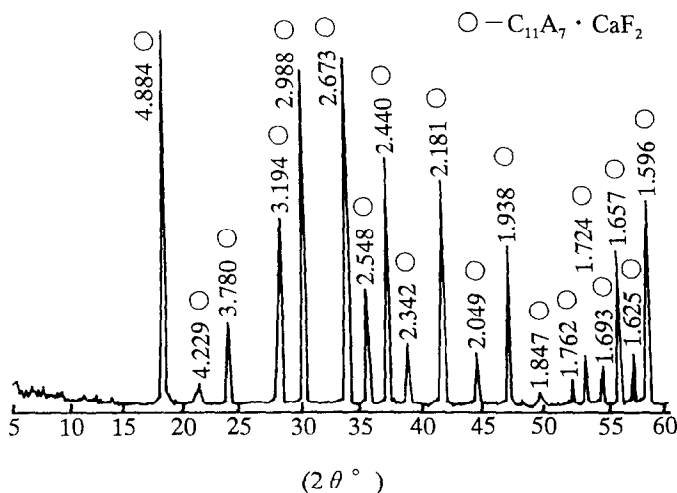


FIG. 1.

Powder X-ray diffraction pattern (Cu K α 1 radiation, spacings in Å) of the product.

Experimental

Preparation of the Single Crystals of C₁₁A₇·CaF₂. Analytically pure CaCO₃, Al₂O₃ and CaF₂, oven dried at 105°C for 2 hours, were ground to pass through a 60 μ m sieve. Considering a volatilization loss of 8.01% CaF₂ during the whole growth process of the crystals (5,11,12), a homogeneous mixture of the above agents with a molar ratio of CaCO₃ : Al₂O₃ : CaF₂ = 11.00 : 7.00 : 1.08 was fired at 1250°C for 2 hours in a silicon-carbide furnace and then quenched to room temperature in the air of R.H. less than 5%. By comparison to PDF-25-394, the product was proved to be C₁₁A₇·CaF₂.

In this study PbCl₂ was also used as a flux. The mixture of PbCl₂ and C₁₁A₇·CaF₂ at a weight ratio of 30 : 1 was placed in a Pt crucible and fired at 650°C for 2 hours, 850°C for 24 hours, 980°C for 30 hours and 1050°C for 10 hours sequentially under an oxidizing atmosphere. The final product contains 43.83% CaO, 50.91% Al₂O₃ and 5.26% CaF₂(C_{11.02}A_{7.04}C_{0.95}, C = CaO, A = Al₂O₃, C = CaF₂). Fig. 1 shows that the crystalline

TABLE 3
Experimental Powder X-ray Diffraction Pattern of the
Final Product (2θ : 5–60°)

d(Å)	h k l	I	d(Å)	h k l	I	d(Å)	h k l	I
4.884	2 1 1	100	2.440	4 2 2	44	1.724	4 4 4	8
4.229	2 2 0	4	2.342	5 1 0	10	1.693	7 1 0	6
3.780	3 1 0	14	2.181	5 2 1	38	1.657	6 4 0	26
3.194	3 2 1	33	2.049	5 3 0	6	1.625	5 5 2	10
2.988	4 0 0	37	1.938	5 3 2	20	1.596	6 4 2	30
2.673	4 2 0	75	1.847	5 4 1	3			
2.548	3 3 2	13	1.762	6 3 1	4			

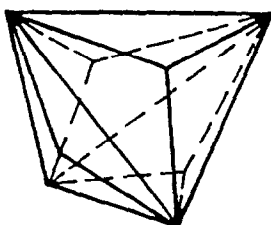


FIG. 2.

The form of the single crystal of $C_{11}A_7 \cdot CaF_2$ -trigonal tristetrahedron.

phase in it is only $C_{11}A_7 \cdot CaF_2$, the observed d-I data of which are given in Table 3. Table 3 shows that the final product produces a pattern close to the calculated pattern PDF-25-394 in the range of $5-60^\circ$ (2θ , Cu $K\alpha_1$ radiation). Microscopic observation proved that there were large numbers of colorless trigonal tristetrahedrons (Fig. 2) in the product. Their sizes ranged from $40 \mu\text{m}$ to $120 \mu\text{m}$, and they had a refractive index of 1.601. The crystals of $C_{11}A_7 \cdot CaF_2$ contained in industrial fluoride-bearing clinkers always appear in the form of rounded grains or dendrites (13). The difference of morphology between the single crystal of $C_{11}A_7 \cdot CaF_2$ and the $C_{11}A_7 \cdot CaF_2$ crystals in fluoride-bearing clinker may be possibly due to the great differences that exist between their growth conditions. During the sintering process of clinker, $C_{11}A_7 \cdot CaF_2$ crystals can only grow in a much limited space for a short time.

Determination of the Crystal Structure of $C_{11}A_7 \cdot CaF_2$. The single crystal of $C_{11}A_7 \cdot CaF_2$ under examination was a well-grown trigonal tristetrahedron of about $0.07 \times 0.07 \times 0.07 \text{ mm}^3$; its elemental composition is shown in Table 4. The intensity data were collected by a RASA-5RP Four-circle single-crystal diffractometer under the following conditions:

Monochromator : graphite, Radiation : $MoK\alpha_1(0.70926\text{\AA})$, Temperature : 25°C ,
 Voltage : 50kV, Current : 130mA, Scanning mode : $2\theta/\omega$,
 Scanning rate : $4^\circ/\text{min}$, Scanning width : $\Delta\omega = 1.0 + 0.5\text{tg}\theta$,
 Scanning range : $2\theta = 0-75^\circ$, $h = 0-20$, $k = 0-0$, $l = 0-20$

The unit cell parameters were obtained by using 20 strong reflections. 2529 original reflections were collected, among which there were 1944 reflections possessing $F > \sigma(F)$. All of the collected data were corrected for LP factor and T factor. By using SHELX 76 program the symmetry equivalent reflections in the original were combined and averaged. 286 symmetry independent reflections were accepted in the final structure solution after rejecting the reflections with $F < 5\sigma(F)$ and $\sin \theta/\lambda > 0.8$. The crystal data and calculated X-ray diffraction pattern (40 reflections) of the single crystal of $C_{11}A_7 \cdot CaF_2$ are shown in Table 5 and Table 6 respectively.

TABLE 4
 Elemental Composition of the Single Crystal of $C_{11}A_7 \cdot CaF_2$ Under Examination
 (by EPMA)

Atom	O	F	Si	Al	Cl	Pb	Fe	Ca
Observed (%)	50.85	3.10	0.03	24.41	2.16	0.22	0.02	19.21
Calculated (%)	53.30	3.30	0.00	23.40	0.00	0.00	0.00	20.00

TABLE 5
Crystal Data for the Single Crystal of C₁₁A₇·CaF₂ (Figure in the Bracket is Error)

Molecu. weight	1408.68	Unit cell parameters	a = b = c = 11 981(2) Å α = β = γ = 90°	D _x	2.72 g cm ⁻³
Crystal system	Cubic	Observed diffractions	h + k + l = 2n, 0kl: k + l = 2n, hhl: 2h + l = 4n, h00, h = 4n	D _m	2.69 g cm ⁻³
Space group	I43d	Linear absorp. coefficient	21.43 cm ⁻¹		
Z	2	Cell volume	1719.80 Å ³		

Results and Analysis

Heating Sequence Adopted in the Experiment. When a flux evaporation method is used, the size and purity of the product are closely related to the adopted heating sequence. Generally speaking, the heating sequence is mainly dependent on both the flux and the characteristics of the single crystals to be synthesized. Because (a) the melting point and boiling point of PbCl₂ (under standard atmosphere) are 498°C and 954°C respectively; and (b) the fluorine in C₁₁A₇·CaF₂ will be released at a relatively high rate when the heating temperature is over 1200°C (11,12), the following heating processes were specially adopted in this experiment. Firstly, the mixture of PbCl₂ and C₁₁A₇·CaF₂ was heated at 650°C for 2 hours in order to completely melt the PbCl₂ and, subsequently, dissolve C₁₁A₇·CaF₂ in the molten PbCl₂. Secondly, the mixture was heated at 850°C (below the boiling point of PbCl₂) for 24 hours so as to slowly evaporate PbCl₂ and to keep the solution from being quickly supersaturated with C₁₁A₇·CaF₂. Thirdly and finally, it was heated at 980°C (over the boiling point of PbCl₂) for 30 hours and then at 1050°C for 10 hours in order to evaporate any possible remains of PbCl₂. The heating time adopted at the above stages was determined on a trial basis.

TABLE 6
Calculated X-ray Diffraction Pattern of the Single Crystal of C₁₁A₇·CaF₂

d(Å)	h k l	I	d(Å)	h k l	I	d(Å)	h k l	I
4.8910	2 1 1	100	1.7665	6 3 1	4	1.2772	6 6 4	3
4.2360	2 2 0	3	1.7293	4 4 4	9	1.2629	8 5 1	1
3.7887	3 1 0	6	1.6944	7 1 0	3	1.2357	9 3 2	2
3.2021	3 2 1	13	1.6615	6 4 0	22	1.2103	9 4 1	2
2.9952	4 0 0	28	1.6304	5 5 2	4	1.1863	7 7 2	1
2.6790	4 2 0	85	1.6010	6 4 2	23	1.1748	10 2 0	2
2.5544	3 3 2	4	1.5216	6 5 1	2	1.1423	7 6 5	3
2.4456	4 2 2	37	1.4976	8 0 0	4	1.1124	10 4 0	4
2.3497	5 1 0	8	1.4748	7 4 1	5	1.1029	9 6 1	1
2.1874	5 2 1	33	1.3928	7 4 3	4	1.0937	10 4 2	3
2.1180	4 4 0	1	1.3566	7 5 2	2			
2.0547	5 3 0	3	1.3395	8 4 0	4			
1.9436	5 3 2	22	1.3231	9 1 0	1			
1.8944	6 2 0	1	1.3072	8 4 2	7			
1.8487	5 4 1	2	1.2919	9 2 1	1			

TABLE 7
Coordinates, Occupancy Factor and Isotropic Thermal Vibration Parameter (U_{11}) of Atoms in the Single Crystal of $C_{11}A_7CaF_2$ (Figures in Brackets are Errors)

Atom	Wyckoff equipoint symbols	X/A	Y/B	Z/C	Occupancy factor	Isotropic thermal vibration parameter
Ca	24d	0.1104 (1)	0	0.2500	1.0	0.0086 (5)
Al (1)	24d	0.3750 (2)	0	0.2500	1.0	0.09 (1)
Al (2)	16c	0.2324 (1)	0.2324 (1)	0.2324 (1)	1.0	0.04 (1)
O (1)	16c	0.0661 (1)	0.0661 (1)	0.0661 (1)	1.0	0.019 (3)
O (2)	48e	0.1955 (2)	0.2852 (1)	0.1004 (2)	1.0	0.014 (2)
F	48e	0.2500	0.1250	0.5000	0.333	0.024 (4)

Coordinates of Atoms in the Single Crystal of $C_{11}A_7CaF_2$. Using the 286 symmetry independent reflections with $F > 5\sigma$ (F), the coordinates and isotropic thermal vibration parameters of 6 sets of atoms (1 set of Ca, 2 sets of Al, 2 sets of O and 1 set of F) were finally obtained after multiple-cycles by the least squares method (Table 7). The coordinates of Al and Ca atoms were determined by using the direct method proposed by Gilmore (14). The coordinates of O and F atoms were deduced from the result of successive differential calculation of electron density and the knowledge of crystal chemistry. The final deviation factor R and R_w are all equal to 0.090, thus showing that the precision of this solution can meet the requirement of accuracy defined in the solution of crystal structure (<0.100).

The unit cell of $C_{11}A_7CaF_2$ crystal is composed of the following 120 atoms: 24 Ca, 12 Al(1), 16 Al(2), 48 O(2), 16 O(1) and 4 F. The coordinates of all the atoms in the unit cell of $C_{11}A_7CaF_2$ crystal can be easily deduced from Table 7 and (15).

The projection drawing of the structure of $C_{11}A_7CaF_2$ on (001) plane is shown in Fig. 3. This figure, when applying methods of quantum chemistry, will greatly assist in selecting the appropriate calculation model for analyzing its bond structure and bond formation (5). The data of bond distances and bond angles for the single crystal of $C_{11}A_7CaF_2$ are shown in Table 8 and Table 9 respectively.

Description of the Crystal Structure of $C_{11}A_7CaF_2$. Fig. 4 is an axonometric drawing of the structure of $C_{11}A_7CaF_2$ in the range of $x = -0.2a-1.2a$, $y = -0.2a-1.2a$, $z = -0.2a-0.4a$. Fig. 5 shows the distribution of AlO_4 tetrahedra in the same range. There are two different $[AlO_4]$ in the structure of $C_{11}A_7CaF_2$, i.e. the $[Al(1)O_4]$ with symmetry $\bar{4}$ (Fig. 6) and the $[Al(2)O_4]$ with symmetry 3 (Fig. 7). The former is a fairly regular tetrahedron composed of one Al(1) atom and four O(2) atoms, with Al–O distance = 1.745\AA (4 equivalent bonds); the latter, extended along its triad axis, is made up of one Al(2) atom, three O(2) atoms and one O(1) atom, with Al(2)–O(2) distance = 1.757 (3 equivalent bonds) and Al(2)–O(1) distance = 1.740\AA . From Fig. 4 and Fig. 5 it can be found that: (a) neighboring two $[AlO_4]$ are connected by one shared O atom; (b) an $[AlO_4]$ ring is formed by every 8 $[AlO_4]$; (c) the $[AlO_4]$ rings are further linked up by sharing O atoms resulting in a three dimensional $[AlO_4]$ network—the basic framework of the structure of $C_{11}A_7CaF_2$; (d) each of the four corners of every $[AlO_4]$ is shared between neighboring AlO_4 tetrahedra; and (e) Ca and F atoms fill in the large cavity surrounded by the 8 AlO_4 tetrahedra.

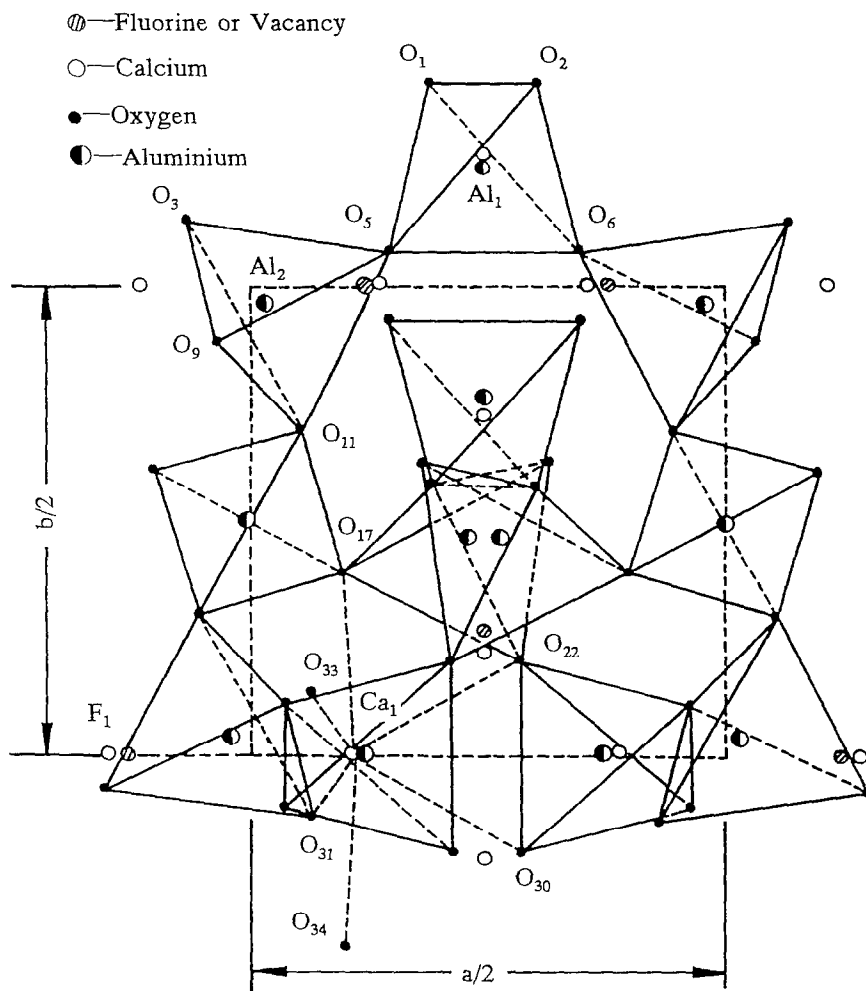


FIG. 3.

Projection drawing of the crystal structure of $C_{11}A_7\text{-CaF}_2$ on (001) plane along C axis.

TABLE 8
Data of Bond Distances for the Single Crystal of $C_{11}A_7\text{-CaF}_2$ (Å)

Ca—O(F)	Bond Distance	Al—O	Bond Distance
Ca—O(1)	2.401 ($\text{Ca}_1\text{—O}_{31}, \text{O}_{33}$)	Al(1)—O(2)	1.745 ($\text{Al}_1\text{—O}_1, \text{O}_2, \text{O}_5, \text{O}_6$)
Ca—O(2)	2.380 ($\text{Ca}_1\text{—O}_{17}, \text{O}_{34}$)	Al(2)—O(1)	1.740 ($\text{Al}_2\text{—O}_3$)
	2.502 ($\text{Ca}_1\text{—O}_{22}, \text{O}_{30}$)	Al(2)—O(2)	1.757 ($\text{Al}_2\text{—O}_5, \text{O}_9, \text{O}_{11}$)
Ca—F	2.816 ($\text{Ca}_1\text{—F}_1$)		

TABLE 9
Data of Bond Angle for the Single Crystal of $C_{11}A_7\cdot CaF_2$ (Degree)*

A_1	CA	A_2	Angle	A_1	CA	A_2	Angle	A_1	CA	A_2	Angle				
O_{33}	-Ca ₁	-O ₃₁	54.76	O_{17}	-Ca ₁	-O ₃₄	174.65	O_1	-Al ₁	-O ₅	112.33				
		-O ₁₇	80.03			-O ₂₂	67.19			-O ₆	112.33				
		-O ₃₄	98.78			-O ₃₀	117.76			-O ₅	112.33				
		-O ₂₂	77.50			-F ₁	87.33			-O ₆	112.33				
		-O ₃₀	125.60			O_{34}	-Ca ₁			-O ₂₂	117.76	O_5	-Al ₁	φO_6	103.90
-F ₁	77.38	-O ₃₀	67.19	O_3	-Al ₂			-O ₅	117.18						
O_{31}	-Ca ₁	-O ₁₇	98.78					-F ₁	87.33	-O ₉	117.18				
		-O ₃₄	80.03					O_{22}	-Ca ₁	-O ₃₀	66.40			-O ₁₁	117.18
		-O ₂₂	125.60							-F ₁	146.80			O_5	-Al ₂
		-O ₃₀	77.50			-F ₁	146.80			-O ₁₁	100.78				
		-F ₁	77.38	O_1	-Al ₁	-O ₂	103.90			O_9	-Al ₂	-O ₁₁	100.78		

* A_1 -atom 1, A_2 -atom 2, CA-central atom

In $C_{11}A_7\cdot CaF_2$ crystals, there are four F atoms. They distribute statistically between the following 12 sites: $(-1/8, 0, 1/4)$, $(5/8, 0, 3/4)$, $(1/4, 7/8, 0)$, $(3/4, 5/8, 0)$, $(0, 1, 4, 7/8)$, $(0, 3/4, 5/8)$, $(3/8, 1/2, 3/4)$, $(1/8, 1/2, 1/4)$, $(3/4, 3/8, 1/2)$, $(1/4, 1/8, 1/2)$, $(1/2, 3/4, 3/8)$ and $(1/2, 1/4, 1/8)$. The unoccupied eight sites are retained as vacancies.

One Ca atom is connected to 2 O(1) and 4 O(2) atoms forming an irregular CaO_6 octahedron, with Ca-O(1) distance = 2.401Å, Ca-O(2) distance = 2.380Å and 2.502Å. On the other hand, one Ca atom can also be coordinated to six O atoms and one F atom in some sites resulting in a deformed polyhedron (coordination number = 7), with a Ca F distance of 2.816Å (Table 8). The ratio between the number of Ca atoms with coordination number 6 and that with coordination number 7 is 5 : 1. $[Al(1)O_4]$, $[Al(2)O_4]$ and $[CaO_6]$ are joined by sharing O atoms (Fig. 3). It should be noted that the Ca-F bond distance is quite long for the ionic interactions occurring in such a strong bond. It was observed that the Ca-Cl distance in

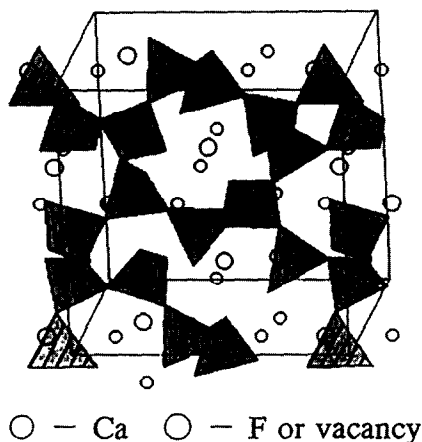


FIG. 4.
Axonometric chart of the crystal structure of $C_{11}A_7\cdot CaF_2$.


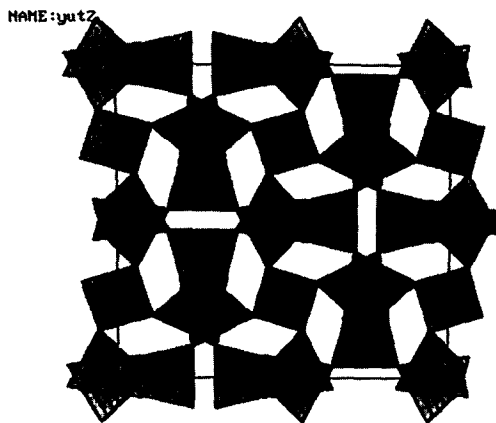


FIG. 5.

Schematic distribution of AlO_4 tetrahedra and the formation of AlO_4 framework.

$\text{C}_{11}\text{A}_7\cdot\text{CaCl}_2$ is about 2.73\AA (6), which is also greater than the Ca-Cl distance (2.483\AA) in CaCl_2 (16). Due to the limitation of experimental conditions and the authors' poor understanding of crystal chemistry, a clear explanation for the puzzling Ca-F distance can not be given in this study.

Table 2 shows that there is only one kind of site for calcium atoms in the structure of C_{12}A_7 as determined by Bartl (8), which happens to be the same as that in the structure of $\text{C}_{11}\text{A}_7\cdot\text{CaF}_2$ as observed in this study. Studies on C_{12}A_7 shows its crystal structure to be built from Ca^{2+} ions, an incomplete framework of corner-sharing AlO_4 tetrahedra and empirical composition $\text{Al}_7\text{O}_{16}^{11-}$, and one O^{2-} ion per formula unit distributed statistically between 12 sites (17). The form of the AlO_4 framework of C_{12}A_7 is the same as that of $\text{C}_{11}\text{A}_7\cdot\text{CaF}_2$ (18). However, compared to C_{12}A_7 , there are four extra F atoms in the unit cell of $\text{C}_{11}\text{A}_7\cdot\text{CaF}_2$. The F atoms fill in the large cavities surrounded by AlO_4 tetrahedra and coordinate with Ca and O atoms to form a pseudo-octahedron, which reduces the internal potential of $\text{C}_{11}\text{A}_7\cdot\text{CaF}_2$ and stabilizes the structure of $\text{C}_{11}\text{A}_7\cdot\text{CaF}_2$. Besides this lattice stabilization, the presence of

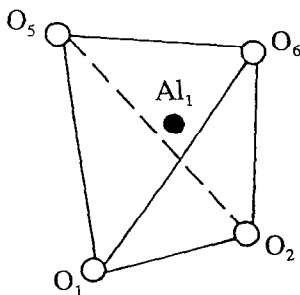

$\text{Al}_1 - \text{Al}(1)$, $\text{O}_1, \text{O}_2, \text{O}_5, \text{O}_6 - \text{O}(2)$

FIG. 6.

AlO_4 tetrahedron with symmetry $\bar{4}$.


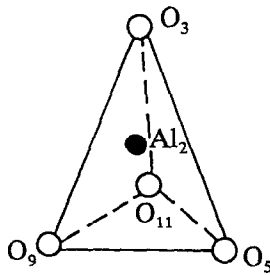


FIG. 7.

AlO_4 tetrahedron extended along its triad axis, with symmetry 3.

the extra F atoms in the structure also has a strengthening effect on the Al-O bonds by modifying the net charges around Al and O atoms. Li (18) found the Mulliken ionic bond orders of the Al(1)-O and Al(2)-O of $\text{C}_{11}\text{A}_7\text{CaF}_2$ are 0.1610 and 0.0490, while those of the Al(1)-O and Al(2)-O of C_{12}A_7 are only 0.0351 and 0.0257. Therefore, the crystal structure of $\text{C}_{11}\text{A}_7\text{CaF}_2$ is more stable than that of C_{12}A_7 . In other words, the hydration activity of $\text{C}_{11}\text{A}_7\text{CaF}_2$ is poorer than that of C_{12}A_7 (5,18).

Comparison of the XRD Pattern of $\text{C}_{11}\text{A}_7\text{CaF}_2$ Obtained in This Study With Those of Before. There are two patterns of $\text{C}_{11}\text{A}_7\text{CaF}_2$ in the Powder Diffraction File, i.e. PDF-25-394 and PDF-36-678. The former is often used to identify the $\text{C}_{11}\text{A}_7\text{CaF}_2$ that exists in fluoride-bearing cement clinker (1-5) because it gives more perfect data than the latter does. Table 3 shows that in the range of 5-60° (2θ , Cu $\text{K}\alpha_1$ radiation), the powder X-ray diffraction pattern of $\text{C}_{11}\text{A}_7\text{CaF}_2$ observed in this study is very close to the calculated pattern PDF-25-394 reported by Williams. Yet, by using single crystal X-ray diffraction, a more detailed pattern, as shown in Table 6, has been obtained. In the new pattern some missing distances in PDF 25-394, such as $d = 2.1180\text{\AA}$, 1.8944\AA , 1.3231\AA , 1.2357\AA , 1.1863\AA , 1.1748\AA and 1.1029\AA , have been presented. If possible, the authors will submit the experimental and calculated patterns of $\text{C}_{11}\text{A}_7\text{CaF}_2$ obtained in this study to the ICDD for inclusion in the PDF.

Conclusions

1. Single crystals of $\text{C}_{11}\text{A}_7\text{CaF}_2$ measuring 40-120 μm suitable for single crystal study could be prepared by a flux evaporation method in which PbCl_2 was used as a flux. The single crystal of $\text{C}_{11}\text{A}_7\text{CaF}_2$ is cubic, with $a = 11.981\text{\AA}$, space group $\bar{I}43d$, $Z = 2$, $n = 1.601$, and $D_x = 2.720 \text{ g cm}^{-3}$.
2. The calcium atom of $\text{C}_{11}\text{A}_7\text{CaF}_2$ is coordinated either to six oxygen atoms in an irregular $[\text{CaO}_6]$ coordination or to six oxygen atoms and one fluorine atom resulting in a pseudo-octahedron with a coordination number of 7. The aluminum atom is bonded to four oxygen atoms forming two different Al-O tetrahedra. Every 8 $[\text{AlO}_4]$ form a $[\text{AlO}_4]$ ring. Furthermore, the rings join each other resulting in a three dimensional $[\text{AlO}_4]$ framework in the crystal of $\text{C}_{11}\text{A}_7\text{CaF}_2$.

3. Fluorine atoms only occupy 1/3 of the available sites in the structure of C₁₁A₇·CaF₂; the unoccupied 2/3 sites are retained as vacancies.
4. The distorted and irregular coordination of atoms; the presence of large cavities and vacancies in the structure; and the random distribution of fluorine atoms make C₁₁A₇·CaF₂ have high internal potential as well as be active when it is exposed to water. But compared to C₁₂A₇, C₁₁A₇·CaF₂ is more stable in crystal structure and slower in hydration due to the presence of fluorine atoms in its structure.

Acknowledgment

This work was sponsored financially by Chenguang Foundation of Wuhan Science and Technology Committee. The authors are grateful to Prof. Tong Damao and Prof. Shen Jinchuan for their insightful comments. The first author also wishes to acknowledge the Aomori Society of Promoting Technology and Education of Japan for its assistance in his work.

References

1. Wang Shanba and Ding Wucheng, *Journal of Chinese Ceramics Society*, 16(4), 305 (1988).
2. Fan Yueming, Zhong Jingyu and Yang Jiazhi, *Journal of Chinese Ceramics Society*, 13(3), 284 (1985).
3. Xue Gungan, Tong Xueli and Li Xiuying, *Proc. of 1985 Beijing Inter. Symp. on Cem. and Concr.*, Vol. I, 191 (1985).
4. Lu Ping, On the clinkering, hydration and strength development of fluoride-bearing clinker in the system of CaO-Al₂O₃-SiO₂-SO₃, Masters Thesis, Tongji University (1981).
5. Yu Qijun, On the crystal structure and characteristics of C₁₁A₇·CaF₂, Ph D Thesis, Wuhan University of Technology, 17-37, 52-108 (1992).
6. Perter P. Williams, *Proc. 5th Inter. Symp. on the Chem. of Cem.*, Tokyo, Vol. I, 366-369 (1968).
7. Perter P. Williams, *Acta Crystallogr.*, Sec. B, 29, 1550 (1973).
8. H. Bartl and T. Scheller, *Neues Jahrb. Mineral. Monatsh.* 404 (1969).
9. Liao Guanglin, On the structure and properties of C₄A₃S̄ and its derivants, Master Thesis, Wuhan University of Technology, 15-40 (1987).
10. Feng Xiuji, Liao Guanglin and Long Shizong, *IL Cemento*, No. 1 (1991).
11. Yu Qijun and Xu Lin, Investigation on the formation dynamics of C₁₁A₇·CaF₂ and its stability at high temperatures, in preparation.
12. Ye Ruilun, Wu Bolin and Ma Weidong, *Proc. of 1985 Beijing Inter. Symp. on Cem. and Concr.*, Vol. I, 205 (1985).
13. Southern China University of Science and Technology, Beijing University of Technology and Wuhan University of Technology, *Petrography of Silicates*, China Architectural Industry Press, Beijing, 439 (1980).
14. G.J. Gilmore, MITHRIL: A Computer Program for the Automatic Solution of Crystal Structure from X Ray Data, University of Glasgow, Scotland (1983).
15. Theo Hahn, *International Tables for Crystallography*, Vol. A (Space-Group Symmetry), D. Reidel Publishing Company, Holland, U.S.A., 659-661 (1983).
16. L.E. Sutton, ed., *Tables of Interatomic Distances and Configuration in Molecules and Ions*, The Chemical Society Special Publication, No. 11, 18, The Chemical Society, London, (1958, 1965).
17. H.F.M. Taylor, *Cement Chemistry*, Academic Press, 36 (1990).
18. Li Beixing, On the relationship between valence-bond-structure and hydration activity of some calcium aluminates with quantum chemistry, Masters Thesis, Wuhan University of Technology, 32-40 (1995).