

inorganic compounds



Acta Crystallographica Section E

Structure Reports

Online

ISSN 1600-5368

Lithium manganese(II) diaquaboro-phosphate monohydrate

Rong-Chuan Zhuang,^a Xue-Yun Chen^b and Jin-Xiao Mi^{a*}^aDepartment of Materials Science and Engineering, College of Materials, Xiamen University, Xiamen 361005, Fujian Province, People's Republic of China, and^bDepartment of Chemistry and Biochemical Engineering, College of Chemistry and Chemical Engineering, Xiamen University, Xiamen 361005, Fujian Province, People's Republic of ChinaCorrespondence e-mail: jxmi@xmu.edu.cn

Received 23 May 2008; accepted 23 June 2008

Key indicators: single-crystal X-ray study; $T = 295$ K; mean $\sigma(\text{Mn}-\text{O}) = 0.004$ Å; H-atom completeness 67%; disorder in main residue; R factor = 0.040; wR factor = 0.097; data-to-parameter ratio = 14.5.

The title compound, $\text{LiMn}(\text{H}_2\text{O})_2[\text{BP}_2\text{O}_8]\cdot\text{H}_2\text{O}$, is built up of an open framework of helical borophosphate ribbons interconnected by $\text{MnO}_4(\text{H}_2\text{O})_2$ octahedra, forming one-dimensional channels along [001] occupied by Li^+ cations and disordered H_2O molecules (site occupancy 0.5). The Li cations reside in two partially occupied sites [occupancies = 0.42 (3) and 0.289 (13)] near the helices.

Related literature

For related structures, see: Boy & Kniep (2001*a,b*) for $\text{LiCu}(\text{H}_2\text{O})_2[\text{BP}_2\text{O}_8]\cdot(\text{H}_2\text{O})$ and $\text{LiZn}(\text{H}_2\text{O})_2[\text{BP}_2\text{O}_8]\cdot\text{H}_2\text{O}$; Ge *et al.* (2003) for $\text{LiCd}(\text{H}_2\text{O})_2[\text{BP}_2\text{O}_8]\cdot\text{H}_2\text{O}$; Lin *et al.* (2008) for $\text{LiMg}(\text{H}_2\text{O})_2[\text{BP}_2\text{O}_8]\cdot\text{H}_2\text{O}$. For related literature, see: Ewald *et al.* (2006); Kniep *et al.* (1997).

Experimental

Crystal data

$\text{LiMn}(\text{H}_2\text{O})_2[\text{BP}_2\text{O}_8]\cdot\text{H}_2\text{O}$ $Z = 6$
 $M_r = 316.68$ Mo $K\alpha$ radiation
 Hexagonal, $P6_322$ $\mu = 2.01$ mm⁻¹
 $a = 9.5765$ (4) Å $T = 295$ (2) K
 $c = 15.857$ (1) Å $0.16 \times 0.12 \times 0.12$ mm
 $V = 1259.4$ (1) Å³

Data collection

Rigaku AFC-7 CCD diffractometer 9731 measured reflections
 Absorption correction: multi-scan 1230 independent reflections
 (*CrystalClear*; Rigaku, 2005) 1223 reflections with $I > 2\sigma(I)$
 $T_{\min} = 0.740$, $T_{\max} = 0.795$ $R_{\text{int}} = 0.032$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.040$ Only H-atom coordinates refined
 $wR(F^2) = 0.097$ $\Delta\rho_{\text{max}} = 0.61$ e Å⁻³
 $S = 1.19$ $\Delta\rho_{\text{min}} = -0.44$ e Å⁻³
 1230 reflections Absolute structure: Flack (1983),
 85 parameters 443 Friedel pairs
 1 restraint Flack parameter: -0.01 (4)

Table 1

Selected geometric parameters (Å, °).

Mn1—O4 ⁱ	2.133 (3)	B1—O1 ^{iv}	1.463 (4)
Mn1—O3	2.139 (3)	B1—O2 ⁱⁱ	1.470 (4)
Mn1—O5	2.311 (4)	Li1—O5 ⁱⁱ	2.111 (4)
P1—O3	1.504 (3)	Li1—O3 ⁱⁱⁱ	2.112 (17)
P1—O4	1.510 (3)	Li2—O6 ^v	1.95 (3)
P1—O1 ⁱⁱ	1.553 (3)	Li2—O6 ^{vi}	1.98 (3)
P1—O2 ⁱⁱⁱ	1.560 (2)	Li2—O4 ^v	2.11 (3)
O5—H1	0.82 (7)	Li2—O5 ^{vii}	2.18 (3)
O5—H2	0.81 (2)		
B1 ^{viii} —O1—P1 ⁱⁱ	129.4 (2)	P1—O3—Mn1	128.38 (17)
B1—O2—P1 ^{ix}	131.1 (2)		

Symmetry codes: (i) $y, -x + y + 1, z + \frac{1}{6}$; (ii) $-y + 1, -x + 1, -z + \frac{1}{6}$; (iii) $x - y, -y + 1, -z$; (iv) $-y + 1, -x, -z + \frac{1}{6}$; (v) $-x + y + 1, y, -z + \frac{1}{2}$; (vi) $y, x, -z + \frac{5}{6}$; (vii) $y, -x + y, z + \frac{1}{6}$; (viii) $x - 1, y, z$; (ix) $x - y + 1, -y + 1, -z$.

Table 2

Hydrogen-bond geometry (Å, °).

$D-H\cdots A$	$D-H$	$H\cdots A$	$D\cdots A$	$D-H\cdots A$
O5—H1 \cdots O4 ^x	0.83 (7)	2.09 (7)	2.878 (5)	159.80
O5—H2 \cdots O2 ^z	0.81 (4)	2.09 (5)	2.845 (5)	155.74

Symmetry codes: (i) $y, -x + y + 1, z + \frac{1}{6}$; (x) $-x + y, y, -z + \frac{1}{2}$.

Data collection: *CrystalClear* (Rigaku, 2005); cell refinement: *CrystalClear*; data reduction: *CrystalClear*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *DIAMOND* (Brandenburg, 2005) and *ATOMS* (Dowty, 2004); software used to prepare material for publication: *SHELXL97*.

This project was supported by a fund from the National Natural Science Foundation of China (No. 40472027).

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: MG2052).

References

- Boy, I. & Kniep, R. (2001*a*). *Z. Kristallogr. New Cryst. Struct.* **216**, 7–8.
 Boy, I. & Kniep, R. (2001*b*). *Z. Kristallogr. New Cryst. Struct.* **216**, 9–10.
 Brandenburg, K. (2005). *DIAMOND*. Crystal Impact GbR, Bonn, Germany.
 Dowty, E. (2004). *ATOMS*. Shape Software, Kingsport, Tennessee, USA.
 Ewald, B., Prots, Yu., Kudla, C., Grüner, D., Cardoso-Gil, R. & Kniep, R. (2006). *Chem. Mater.* **18**, 673–679.
 Flack, H. D. (1983). *Acta Cryst.* **A39**, 876–881.
 Ge, M.-H., Mi, J.-X., Huang, Y.-X., Zhao, J.-T. & Kniep, R. (2003). *Z. Kristallogr. New Cryst. Struct.* **218**, 273–274.
 Kniep, R., Will, H.-G., Boy, I. & Röhr, C. (1997). *Angew. Chem. Int. Ed. Engl.* **36**, 1013–1014.
 Lin, J.-R., Huang, Y.-X., Wu, Y.-H. & Zhou, Y. (2008). *Acta Cryst.* **E64**, i39–i40.
 Rigaku (2005). *CrystalClear*. Rigaku Corporation, Tokyo, Japan.
 Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.

supporting information

Acta Cryst. (2008). E64, i46 [doi:10.1107/S1600536808018898]

Lithium manganese(II) diaquaborophosphate monohydrate

Rong-Chuan Zhuang, Xue-Yun Chen and Jin-Xiao Mi

S1. Comment

A large family of compounds contains helical borophosphate anions $\infty^1[\text{BP}_2\text{O}_8]^{3-}$ with various combinations of metal cations (M^{I} , $M_{0.5}^{\text{I}}$, M^{II} , M^{III}) (Kniep *et al.*, 1997; Ewald *et al.*, 2006). To date, the only Li-containing members are $\text{Li}M^{\text{II}}(\text{H}_2\text{O})_2[\text{BP}_2\text{O}_8]\cdot\text{H}_2\text{O}$ ($M^{\text{II}} = \text{Cu}, \text{Zn}, \text{Cd}, \text{Mg}$) (Boy & Kniep, 2001a, 2001b; Ge *et al.*, 2003; Lin *et al.*, 2008). The structure of $\text{LiMn}(\text{H}_2\text{O})_2[\text{BP}_2\text{O}_8]\cdot\text{H}_2\text{O}$ is reported here.


The borophosphate helices, built up of four-membered rings of alternating BO_4 and PO_4 tetrahedra, extend along the 6_5 screw axis (Fig. 1 and 2). These helices are interconnected by Jahn-Teller-distorted Mn^{2+} -centred octahedra, with four oxygen atoms (O3, O4) from PO_4 groups and two (O5) from water molecules at the vertices (Fig. 3). Unlike the compounds containing Cu and Zn (Boy & Kniep, 2001a, 2001b) but similar to those containing Cd and Mg (Ge *et al.*, 2003; Lin *et al.*, 2008), there are two distinct Li sites: Li1 is close to the outer wall of the borophosphate helices and Li2 is situated at the free loops (inner wall) of the helices. The sum of occupancies of these Li sites refines to almost unity, as required to maintain charge neutrality in the compound.

S2. Experimental

$\text{LiMn}(\text{H}_2\text{O})_2[\text{BP}_2\text{O}_8]\cdot\text{H}_2\text{O}$ was obtained in the presence of boric acid as a flux. A mixture of 0.1149 g MnCO_3 , 1.484 g H_3BO_3 , and 0.6235 g LiH_2PO_4 was ground to a homogeneous powder, which was transferred to a teflon autoclave with 10 ml inline (degree of filling 10%) where it was heated at 443 K for four days.

S3. Refinement

The hydrogen atoms connected to O5 were located from difference Fourier maps with displacement parameters fixed as $1.2 \cdot U(\text{O5})$, whereas those connected to O6 belonging to the disordered water molecules were not located. The sum of the occupancies of Li sites was restrained to maintain charge neutrality within the entire compound. The occupancy of the O6 site associated with the disordered water molecules was fixed at 0.5.

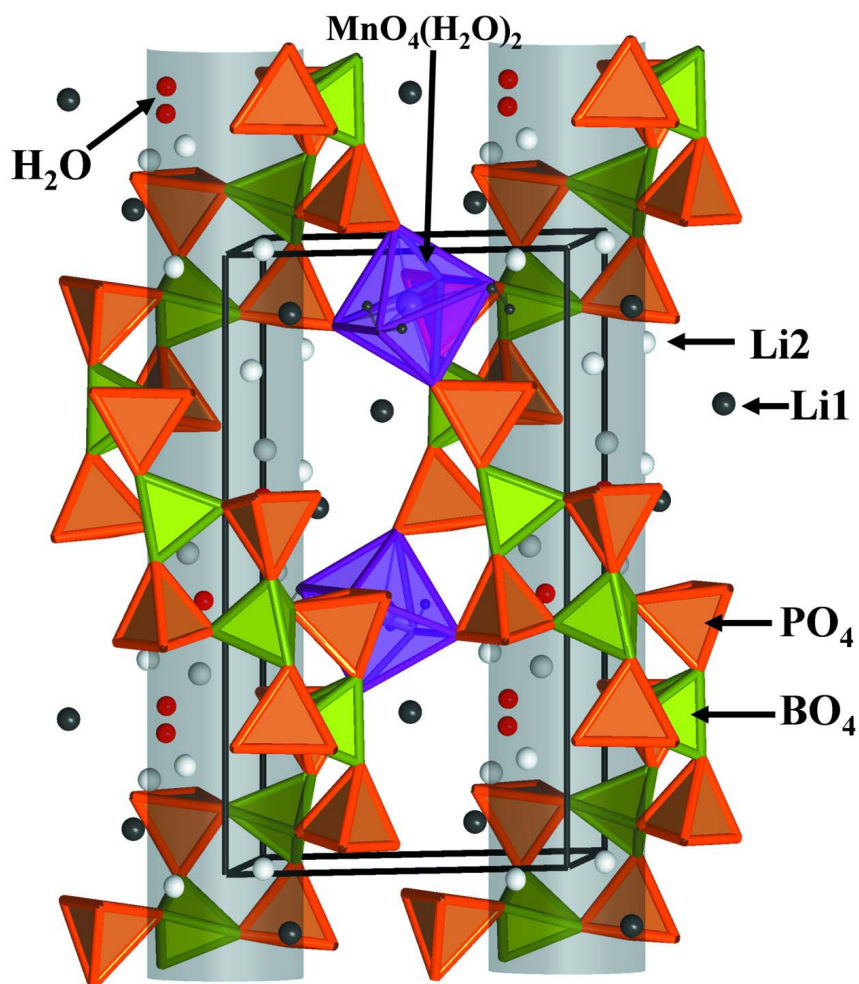**Figure 1**

Linkage of borophosphate helices in $\text{LiMn}(\text{H}_2\text{O})_2[\text{BP}_2\text{O}_8] \cdot \text{H}_2\text{O}$ through $\text{MnO}_4(\text{H}_2\text{O})_2$ octahedra (BO₄, green tetrahedra; PO₄, orange tetrahedra; MnO₆, violet octahedra; Li, black spheres; H₂O, red spheres).

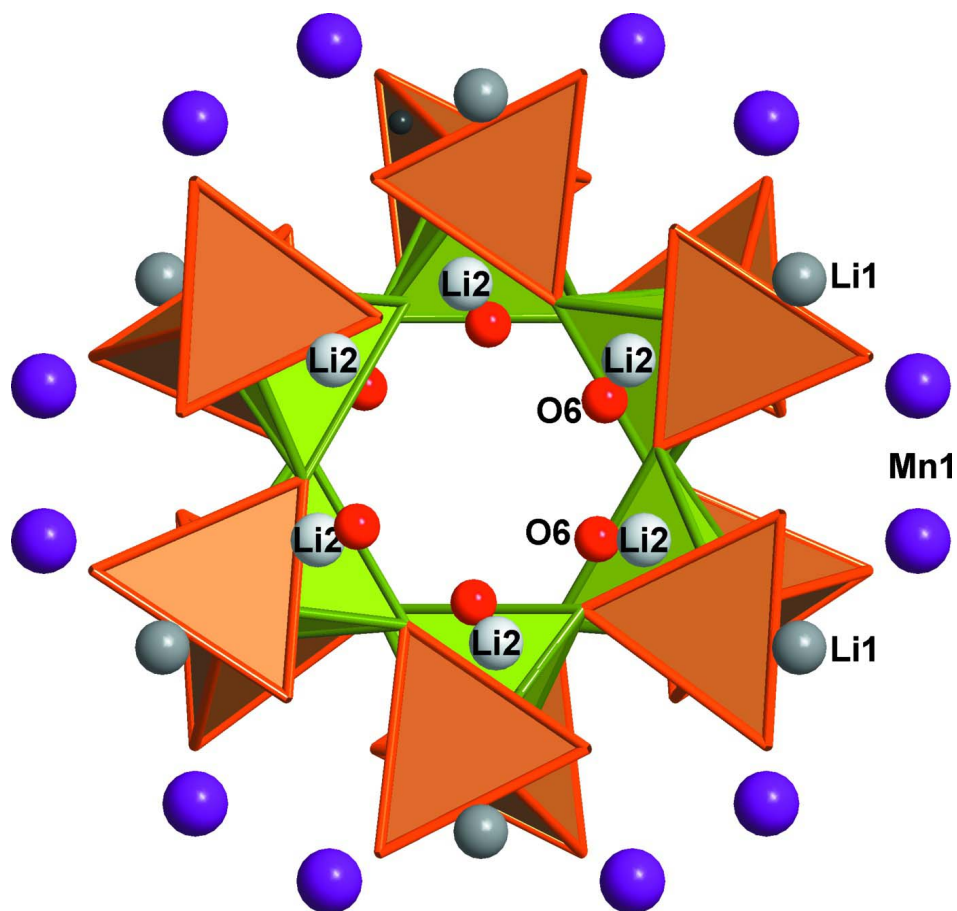
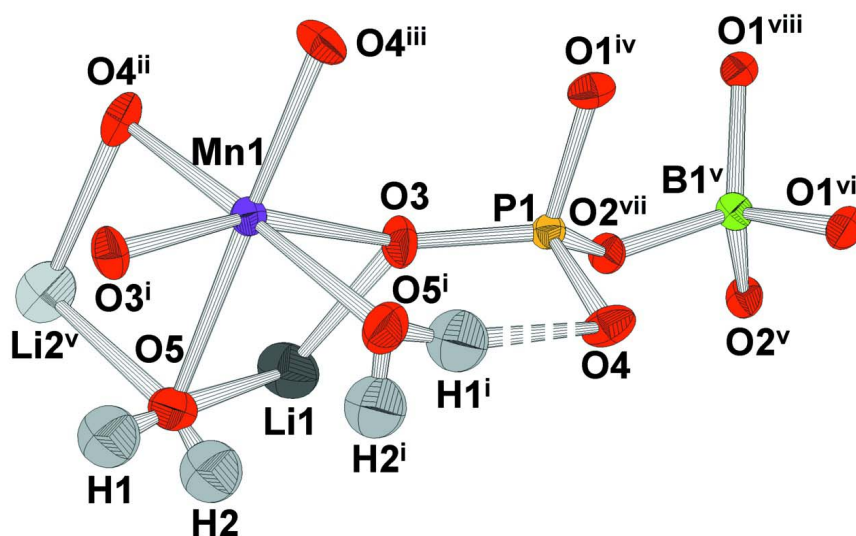


Figure 2

Section of $\text{LiMn}(\text{H}_2\text{O})_2[\text{BP}_2\text{O}_8] \cdot \text{H}_2\text{O}$ viewed along the c axis (colour scheme as in Fig. 1).

**Figure 3**

Coordination environment of Mn, B, and P atoms, with displacement ellipsoids drawn at the 50% probability level (symmetry codes: (i) $-x+y, y, 1/2-z$; (ii) $1-x, 1-x+y, 1/3-z$; (iii) $y, 1-x+y, 1/6+z$; (iv) $1-y, 1-x, 1/6-z$; (v) $x-y, x, -1/6+z$; (vi) $1+x-y, 1-y, -z$; (vii) $x-y, 1-y, -z$; (viii) $1+x-y, 1+x, -1/6+z$).

Lithium manganese diaquaborophosphate monohydrate

Crystal data

$\text{LiMn}(\text{H}_2\text{O})_2[\text{BP}_2\text{O}_8] \cdot \text{H}_2\text{O}$

$M_r = 316.68$

Hexagonal, $P6_322$

Hall symbol: $P\ 65\ 2\ (0\ 0\ 1)$

$a = 9.5765\ (4)\ \text{\AA}$

$c = 15.857\ (1)\ \text{\AA}$

$V = 1259.4\ (1)\ \text{\AA}^3$

$Z = 6$

$F(000) = 942$

$D_x = 2.505\ \text{Mg m}^{-3}$

Mo $K\alpha$ radiation, $\lambda = 0.71073\ \text{\AA}$

Cell parameters from 6263 reflections

$\theta = 2.5\text{--}33.2^\circ$

$\mu = 2.01\ \text{mm}^{-1}$

$T = 295\ \text{K}$

Hexagonal bipyramid, pale pink

$0.16 \times 0.12 \times 0.12\ \text{mm}$

Data collection

Rigaku AFC-7 CCD

diffractometer

Radiation source: fine-focus sealed tube

Graphite monochromator

Detector resolution: $14.6306\ \text{pixels mm}^{-1}$

thin-slice $\Delta\phi = 0.6$ & $\Delta\omega = 0.6$ scans

Absorption correction: multi-scan

(*CrystalClear*; Rigaku, 2005)

$T_{\min} = 0.740, T_{\max} = 0.795$

9731 measured reflections

1230 independent reflections

1223 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.032$

$\theta_{\max} = 30.0^\circ, \theta_{\min} = 2.5^\circ$

$h = -13 \rightarrow 13$

$k = -13 \rightarrow 12$

$l = -19 \rightarrow 22$

Refinement

Refinement on F^2
 Least-squares matrix: full
 $R[F^2 > 2\sigma(F^2)] = 0.040$
 $wR(F^2) = 0.097$
 $S = 1.19$
 1230 reflections
 85 parameters
 1 restraint
 Primary atom site location: structure-invariant
 direct methods
 Secondary atom site location: difference Fourier
 map
 Hydrogen site location: difference Fourier map

Only H-atom coordinates refined
 $w = 1/[\sigma^2(F_o^2) + (0.008P)^2 + 5.1269P]$
 where $P = (F_o^2 + 2F_c^2)/3$
 $(\Delta/\sigma)_{\max} < 0.001$
 $\Delta\rho_{\max} = 0.62 \text{ e } \text{Å}^{-3}$
 $\Delta\rho_{\min} = -0.44 \text{ e } \text{Å}^{-3}$
 Extinction correction: *SHELXL97* (Sheldrick,
 2008), $F_c^* = kFc[1 + 0.001x\text{Fc}^2\lambda^3/\sin(2\theta)]^{-1/4}$
 Extinction coefficient: 0.0054 (19)
 Absolute structure: Flack (1983), 443 Friedel
 pairs
 Absolute structure parameter: -0.01 (4)

Special details

Geometry. All esds (except the esd in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell esds are taken into account individually in the estimation of esds in distances, angles and torsion angles; correlations between esds in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell esds is used for estimating esds involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) etc. and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (Å^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$	Occ. (<1)
Mn1	0.44888 (4)	0.89775 (9)	0.2500	0.0163 (2)	
P1	0.61636 (10)	0.83327 (10)	0.08453 (6)	0.0134 (2)	
O1	0.0204 (3)	0.2129 (3)	0.06593 (16)	0.0181 (5)	
O2	0.7681 (3)	0.1804 (3)	0.01267 (14)	0.0158 (5)	
O3	0.4860 (3)	0.8589 (4)	0.12112 (17)	0.0227 (6)	
O4	0.6237 (4)	0.6903 (3)	0.11938 (17)	0.0228 (6)	
O5	0.1884 (4)	0.7081 (4)	0.2127 (2)	0.0340 (8)	
O6	0.9000 (19)	0.8166 (12)	0.2717 (7)	0.079 (3)*	0.50
B1	0.8493 (3)	0.1507 (3)	0.0833	0.0140 (9)	
Li1	0.2428 (18)	0.7572 (18)	0.0833	0.034 (4)	0.42 (3)
Li2	0.899 (4)	0.763 (3)	0.3479 (16)	0.034 (4)	0.289 (13)
H1	0.133 (8)	0.683 (7)	0.256 (4)	0.041*	
H2	0.179 (7)	0.620 (4)	0.218 (4)	0.041*	

Atomic displacement parameters (Å^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Mn1	0.0170 (3)	0.0165 (4)	0.0153 (3)	0.00826 (18)	0.0028 (2)	0.000
P1	0.0153 (4)	0.0131 (4)	0.0113 (3)	0.0068 (3)	0.0011 (3)	-0.0005 (3)
O1	0.0139 (11)	0.0196 (12)	0.0200 (12)	0.0077 (10)	-0.0012 (9)	-0.0060 (9)
O2	0.0195 (12)	0.0185 (11)	0.0106 (9)	0.0104 (10)	-0.0029 (9)	-0.0024 (8)
O3	0.0222 (14)	0.0306 (15)	0.0177 (12)	0.0151 (12)	0.0028 (10)	-0.0046 (11)
O4	0.0348 (16)	0.0150 (12)	0.0177 (11)	0.0117 (11)	-0.0008 (12)	0.0022 (10)

O5	0.0280 (17)	0.0233 (15)	0.0393 (17)	0.0041 (13)	0.0118 (14)	-0.0065 (14)
B1	0.0157 (17)	0.0157 (17)	0.011 (2)	0.0083 (19)	0.0013 (16)	0.0013 (16)
Li1	0.036 (7)	0.036 (7)	0.023 (8)	0.012 (8)	0.003 (6)	0.003 (6)
Li2	0.036 (7)	0.036 (7)	0.023 (8)	0.012 (8)	0.003 (6)	0.003 (6)

Geometric parameters (Å, °)

Mn1—O4 ⁱ	2.133 (3)	O5—H1	0.82 (7)
Mn1—O4 ⁱⁱ	2.133 (3)	O5—H2	0.81 (2)
Mn1—O3	2.139 (3)	O6—O6 ^{ix}	0.71 (2)
Mn1—O3 ⁱⁱⁱ	2.139 (3)	O6—Li2	1.31 (3)
Mn1—O5	2.311 (4)	O6—Li2 ^{ix}	1.95 (3)
Mn1—O5 ⁱⁱⁱ	2.311 (3)	O6—Li2 ^{xii}	1.98 (3)
P1—O3	1.504 (3)	O6—Li2 ^x	2.45 (3)
P1—O4	1.510 (3)	O6—Li ^{xiii}	2.53 (3)
P1—O1 ^{iv}	1.553 (3)	B1—O1 ^{xiv}	1.463 (4)
P1—O2 ^v	1.560 (2)	B1—O1 ^{xv}	1.463 (4)
O1—B1 ^{vi}	1.463 (4)	B1—O2 ^{iv}	1.470 (4)
O1—P1 ^{iv}	1.553 (3)	Li1—O5 ^{iv}	2.111 (4)
O1—Li2 ^{vii}	2.65 (3)	Li1—O3 ^{iv}	2.112 (17)
O2—B1	1.470 (4)	Li2—O6 ^{ix}	1.95 (3)
O2—P1 ^{viii}	1.560 (2)	Li2—O6 ^{xii}	1.98 (3)
O3—Li1	2.112 (17)	Li2—O4 ^{ix}	2.11 (3)
O4—Li2 ^{ix}	2.11 (3)	Li2—O5 ^{xiii}	2.18 (3)
O4—Mn1 ^x	2.133 (3)	Li2—Li2 ^{xii}	2.30 (6)
O5—Li1	2.111 (4)	Li2—O6 ⁱ	2.45 (3)
O5—Li2 ^{xi}	2.18 (3)		
O4 ⁱ —Mn1—O4 ⁱⁱ	97.89 (17)	O2—B1—O2 ^{iv}	102.6 (4)
O4 ⁱ —Mn1—O3	100.17 (11)	O5 ^{iv} —Li1—O5	177.6 (17)
O4 ⁱⁱ —Mn1—O3	91.22 (11)	O5 ^{iv} —Li1—O3 ^{iv}	85.4 (4)
O4 ⁱ —Mn1—O3 ⁱⁱⁱ	91.22 (11)	O5—Li1—O3 ^{iv}	96.0 (5)
O4 ⁱⁱ —Mn1—O3 ⁱⁱⁱ	100.17 (11)	O5 ^{iv} —Li1—O3	96.0 (5)
O3—Mn1—O3 ⁱⁱⁱ	162.68 (17)	O5—Li1—O3	85.4 (4)
O4 ⁱ —Mn1—O5	178.14 (13)	O3 ^{iv} —Li1—O3	112.6 (14)
O4 ⁱⁱ —Mn1—O5	83.95 (13)	O5 ^{iv} —Li1—O6 ⁱⁱ	80.8 (8)
O3—Mn1—O5	80.01 (12)	O5—Li1—O6 ⁱⁱ	96.8 (9)
O3 ⁱⁱⁱ —Mn1—O5	88.19 (12)	O3 ^{iv} —Li1—O6 ⁱⁱ	122.4 (7)
O4 ⁱ —Mn1—O5 ⁱⁱⁱ	83.95 (13)	O3—Li1—O6 ⁱⁱ	124.3 (8)
O4 ⁱⁱ —Mn1—O5 ⁱⁱⁱ	178.14 (14)	O5 ^{iv} —Li1—O6 ^{xi}	96.8 (9)
O3—Mn1—O5 ⁱⁱⁱ	88.19 (12)	O5—Li1—O6 ^{xi}	80.8 (8)
O3 ⁱⁱⁱ —Mn1—O5 ⁱⁱⁱ	80.01 (12)	O3 ^{iv} —Li1—O6 ^{xi}	124.3 (8)
O5—Mn1—O5 ⁱⁱⁱ	94.2 (2)	O3—Li1—O6 ^{xi}	122.4 (7)
O3—P1—O4	115.17 (17)	O6 ⁱⁱ —Li1—O6 ^{xi}	16.0 (5)
O3—P1—O1 ^{iv}	111.97 (16)	O6—Li2—O6 ^{ix}	10.8 (10)
O4—P1—O1 ^{iv}	104.62 (16)	O6—Li2—O6 ^{xii}	90.8 (17)
O3—P1—O2 ^v	105.62 (15)	O6 ^{ix} —Li2—O6 ^{xii}	101.7 (15)
O4—P1—O2 ^v	111.81 (15)	O6—Li2—O4 ^{ix}	119.9 (19)

O1 ^{iv} —P1—O2 ^v	107.54 (14)	O6 ^{ix} —Li2—O4 ^{ix}	110.3 (14)
B1 ^{vi} —O1—P1 ^{iv}	129.4 (2)	O6 ^{xii} —Li2—O4 ^{ix}	138.2 (14)
B1—O2—P1 ^{viii}	131.1 (2)	O6—Li2—O5 ^{xiii}	117.8 (18)
P1—O3—Mn1	128.38 (17)	O6 ^{ix} —Li2—O5 ^{xiii}	114.8 (14)
Li1—O5—H1	157 (4)	O6 ^{xii} —Li2—O5 ^{xiii}	102.8 (13)
Li2 ^{xi} —O5—H1	93 (4)	O4 ^{ix} —Li2—O5 ^{xiii}	87.8 (11)
Mn1—O5—H1	107 (4)	O6—Li2—O6 ⁱ	104.2 (18)
Li1—O5—H2	103 (4)	O6 ^{ix} —Li2—O6 ⁱ	115.0 (14)
Li2 ^{xi} —O5—H2	162 (4)	O6 ^{xii} —Li2—O6 ⁱ	13.8 (7)
Mn1—O5—H2	107 (4)	O4 ^{ix} —Li2—O6 ⁱ	125.5 (12)
H1—O5—H2	84 (5)	O5 ^{xiii} —Li2—O6 ⁱ	99.1 (11)
Li2—O6—Li2 ^{ix}	146 (2)	O6—Li2—O1 ^{xvi}	100.4 (16)
O1 ^{xiv} —B1—O1 ^{xv}	103.7 (4)	O6 ^{ix} —Li2—O1 ^{xvi}	100.1 (12)
O1 ^{xiv} —B1—O2	113.70 (14)	O6 ^{xii} —Li2—O1 ^{xvi}	89.1 (11)
O1 ^{xv} —B1—O2	111.75 (14)	O4 ^{ix} —Li2—O1 ^{xvi}	59.9 (8)
O1 ^{xiv} —B1—O2 ^{iv}	111.75 (14)	O5 ^{xiii} —Li2—O1 ^{xvi}	139.4 (13)
O1 ^{xv} —B1—O2 ^{iv}	113.70 (14)	O6 ⁱ —Li2—O1 ^{xvi}	83.4 (9)

Symmetry codes: (i) $y, -x+y+1, z+1/6$; (ii) $-x+1, -x+y+1, -z+1/3$; (iii) $-x+y, y, -z+1/2$; (iv) $-y+1, -x+1, -z+1/6$; (v) $x-y, -y+1, -z$; (vi) $x-1, y, z$; (vii) $-y+1, x-y, z-1/3$; (viii) $x-y+1, -y+1, -z$; (ix) $-x+y+1, y, -z+1/2$; (x) $x-y+1, x, z-1/6$; (xi) $x-y, x, z-1/6$; (xii) $y, x, -z+2/3$; (xiii) $y, -x+y, z+1/6$; (xiv) $-y+1, -x, -z+1/6$; (xv) $x+1, y, z$; (xvi) $-x+y+1, -x+1, z+1/3$.

Hydrogen-bond geometry (Å, °)

$D-H\cdots A$	$D-H$	$H\cdots A$	$D\cdots A$	$D-H\cdots A$
O5—H1 \cdots O4 ⁱⁱⁱ	0.83 (7)	2.09 (7)	2.878 (5)	159.80
O5—H2 \cdots O2 ⁱ	0.81 (4)	2.09 (5)	2.845 (5)	156

Symmetry codes: (i) $y, -x+y+1, z+1/6$; (iii) $-x+y, y, -z+1/2$.