



Title	Effect of decay on shear performance of dowel-type timber joints
Author(s)	Sawata, Kei; Sasaki, Takanobu; Doi, Shuichi; Iijima, Yasuo
Citation	Journal of Wood Science, 54(5), 356-361 https://doi.org/10.1007/s10086-008-0963-7
Issue Date	2008-10
Doc URL	http://hdl.handle.net/2115/39982
Rights	The original publication is available at www.springerlink.com
Type	article (author version)
File Information	sawata_JWS54.pdf



[Instructions for use](#)

Effect of decay on shear performance of dowel-type timber joints

Kei Sawata (*)

*Graduate School of Agriculture, Hokkaido University, N9 W9, Kita-ku, Sapporo
060-8589, Japan*

Takanobu Sasaki

*Institute of Wood Technology, Akita Prefectural University, Noshiro 016-0876,
Japan*

Shuichi Doi

*Graduate School of Life and Environmental Sciences, University of Tsukuba,
Tsukuba 305-8572, Japan*

Yasuo Iijima

*Institute of Wood Technology, Akita Prefectural University, Noshiro 016-0876,
Japan*

Phone: +81 11-706-2528

Fax: +81 11-706-3636

E-mail (Kei Sawata): ksawata@for.agr.hokudai.ac.jp

Keywords: Shear strength, Initial stiffness, Hysteresis properties, Brown rot
fungus, Moisture content

Footnote: Part of this paper was presented at the 5th Symposium on Timber
Bridges of Japan Society of Civil Engineers, Tokyo, July 2006; the 56th Annual
Meeting of the Japan Wood Research Society, Akita, August 2006; and the
Annual Meeting of Architectural Institute of Japan 2007, Fukuoka, August 2007

Abstract

Monotonic and reversed cyclic loading tests were conducted on dowel-type timber joints with varying degrees of wood decay due to *Fomitopsis palustris* (Berk. et Curt.), a brown rot fungus, and the effect of decay on various shear performances of dowel-type joints was investigated. For joints affected by the brown rot fungus, initial stiffness, yield load and maximum load of dowel-type joints were significantly decreased, even with a small mass loss of wood and reductions in shear performance were the largest for initial stiffness, followed by yield load and maximum load, in that order. For a 1% reduction of the yield load, initial stiffness and maximum load showed reductions of 1.15% and 0.77%, respectively. When dowel-type joints that had been exposed to the brown rot fungus were subjected to reversed cyclic loading, the gap between the dowel and the lead hole of the wood was increased and equivalent viscous damping was decreased. These results indicate that decay around the dowel lead hole especially affects the load-displacement behavior at small displacement level and dowel-type joints under cyclic loading have very low resistance to forces acting on wooden structure.

Keywords: Shear strength, Initial stiffness, Hysteresis properties, Brown rot fungus, Moisture content

Introduction

Safety and serviceability are necessary functions for wooden structure during the service period and these significantly depend on the structural performance of the elements and joints. If elements and joints are exposed to wood-decaying fungi or termites, their structural performance may be largely changed by the biological deterioration.

There are many studies for the strength of wood exposed to wood-decaying fungi and, as a consequence, it is well known that properties of wood are strongly affected by decay. For example, Takahashi and Nishimoto¹ and Wilcox² made a comprehensive report on the effect of decay on various measures of strength in wood. The authors had also previously carried out embedding tests of wood exposed to wood-decaying fungus and had investigated the strength reduction of four wood species³.

In recent years, the effects of decay have been experimentally investigated not only on wood strength but also on shear performance of nailed joints^{4,5}, but little data has been collected on shear performance of timber joints caused by wood-decaying fungi. Shear performance of timber joints frequently dominates the structural performance of wooden structure such that wood decay at timber joints may have a remarkable effect on the structural performance of the construction. Furthermore, the moisture intrusion required to promote decay also has an effect on the shear performance of timber joints⁶. Therefore, this study was carried out on dowel-type timber joints with high moisture content that had been exposed to the wood-decaying fungus and used monotonic and reversed cyclic loading tests to investigate the effect of decay on the shear performance of dowel-type joints.

Materials and methods

Specimens

Shear tests of dowel-type joints were conducted on spruce (*Picea Abies*) laminae. The dimensions of the specimen were 420 mm long, 105 mm wide and 30 mm thick, and the average wood density was 474.4 kg/m³ (standard deviation, 25.0 kg/m³). Control and inoculated samples were prepared from the same group.

Control samples comprised of air-dried samples and wet samples that had been immersed in a water bath for 2 weeks. The ranges of the moisture content for air-dried and wet samples were 12.6-13.9% and 50.8-86.6%, respectively. A hole with a diameter of 12 mm was predrilled in the wood.

Decay simulation

Wood samples were immersed in a water bath for 2 weeks to increase moisture content. This study assumed the case of wood decay occurring at the dowel lead hole of dowel-type joints. Accordingly, dowel lead holes were filled with tap water, including 2% malt extract and plugged with silicon stoppers for 1 week. The samples were placed in polyethylene bags with filter and sterilized by heating to 120°C for 60 min. Then, the dowel lead hole was filled up the sawdust covered with the mycelium. The sawdust from spruce (*Picea jezoensis*) was inoculated with a small piece of *Fomitopsis palustris* (Berk. et Curt.) mycelium mat and nutrient solution was tap water including 1% peptone and 2% malt extract. The inoculated samples were incubated at 26°C and 98% relative humidity for 5, 8 and 11 weeks. One of the objectives of this study was to investigate shear performance of dowel-type joints exposed to the fungus under wet conditions. Therefore, samples were immersed in a water bath for 1 week after the decay procedure. The moisture content of the inoculated samples was 41.1-115.9%.

Test methods

A diagram showing the preparation of the specimens and a summary of the preparation are shown in Fig. 1 and Table 1, respectively. The steel plates and the sample were connected with a dowel of 12 mm in diameter. The steel plates and dowels were of grade SS400 according to the Japanese Industrial Standard⁷. The wood thickness/dowel diameter ratio, the end distance/dowel diameter ratio and the edge distance/dowel diameter ratio were 2.5, 7.0 and 4.4, respectively. Dowel-type joints under lateral loads parallel to the grain were tested by monotonic tensile loading and reversed cyclic loading. The cycle loading protocol was defined in terms of average yield displacement obtained from the monotonic tensile tests, as shown in Fig. 2⁸. Initially, one cycle was applied for each

displacement level, which was 25% and 50% of the yield displacement. Then, the step of the cyclic test was repeated three times to produce 75%, 100%, 200%, 400%, 600%, 800%, and 1200% of yield displacement.

Displacement between the steel plate and the sample was measured with two displacement transducers. Tests were carried out at a constant rate of 1.0 mm/min and were terminated when the load decreased to 50% of the maximum load or when the crack reached the end of the sample.

Results and discussion

Load-displacement relation

Load-displacement hysteresis curves of the dowel-type joints obtained from the reversed cyclic loading tests are shown in Fig. 3. The load of air-dried and wet control samples shows a linear increase up to the yielding, and is almost constant after yielding. However, the shape of load-displacement curve for the inoculated sample differs significantly, having an uncertain yield point on the load-displacement curve and showing low load until the sample fractures in splitting. Initial stiffness (K_s), yield load (P_y), yield displacement (D_y), maximum load (P_{max}), displacement corresponding to maximum load (D_{max}), and dissipated energy until 80% of maximum load were obtained from monotonic loading tests using evaluation methods shown in Fig. 4. Initial stiffness was defined as the line that passes through points on the curves corresponding to 10% and 40% of the maximum load. By evaluation of yield load by the 5% offset method, according to ASTM D5652⁹, the line defining initial stiffness is shifted in the positive x-direction by 5% of the dowel diameter, and yield load is defined as the intersection of this line and the load-displacement curve. Yield displacement was defined as the displacement on the load-displacement curve corresponding to the yield load. The results obtained from air-dried and wet control samples are shown in Table 2.

Shear performance of dowel-type joints

Shear performance of dowel-type joints for each incubation period is shown in Fig. 5. Moisture content of the wet control samples and the inoculated samples was more than 30% (near the fiber saturation point). In a previous study, the authors found that the embedding strength of wood was almost constant when the moisture content of wood was higher than 30%³.

Initial stiffness, yield load, and maximum load of wet control samples were 0.52, 0.57 and 0.61 times, respectively, those of air-dried samples. In the case of dowel-type joints with high moisture content, those were exposed to the fungus, shear performance showed significant further reduction compared with those of air-dried samples. Shear strength of dowel-type joints is usually governed by the embedding strength of wood and fastener yield capacity in bending¹⁰. Since the dowel-type joint used in this study had a small wood thickness/dowel diameter ratio (2.5), shear strength of dowel-type joints was determined by embedding strength. However, when decay causes significant reduction of embedding strength, shear strength of the dowel-type joint may be determined only by embedding strength, even if the wood thickness/dowel diameter ratio is large. Therefore, findings of this study may also be applied to the prediction of shear strength of ordinary dowel-type joints caused by wood-decaying fungi.

Although yield displacement and displacement corresponding to the maximum load of inoculated samples were higher than for air-dried control samples, the dissipated energy of inoculated samples was decreased due to significant reduction of initial stiffness, yield load and maximum load.

Initial stiffness, yield load and maximum load of inoculated samples were divided by each mean value of wet control samples and the ratios of those shear performance values were obtained. Fig. 6 shows the relationship between the ratio of shear performance values of dowel-type joints and mass loss. After shear testing of dowel-type joints, subsamples taken to include the dowel lead hole (168 mm long, 105 mm wide and 30 mm thick) were cut from shear test samples, as shown in Fig. 1. Subsamples were oven-dried at 105°C for 24hr, and then were air-dried at room temperature. The percent mass loss (*ML*) was estimated from the difference in the air-dried weight of subsample and the weight calculated from air-dried density before the decay test. It is well known that the strength of wood against brown rot fungi is significantly decreased, even with a small mass loss of

wood^{1,2}. This study also revealed the same tendency, as initial stiffness, yield load and maximum load of dowel-type joints were significantly decreased with a small mass loss. The reduction of shear performance was the largest for initial stiffness, followed by yield load and maximum load, in that order.

The relationship between reduction of initial stiffness and maximum load and reduction of the yield load is shown in Fig. 7. The initial stiffness and the maximum load were linearly decreased with decreasing the yield load, and were 1.15% and 0.77% decreased for 1% reduction of the yield load, respectively.

Results described above showed that the effect of decay differed depending on the sort of shear performances of dowel-type joints.

Hysteresis property

The hysteresis loop at third cycle is shown in Fig. 8. Wet control sample showed pinched hysteresis loops and inoculated sample showed low peak load and thinner hysteresis loops. When dowel-type timber joint with a small thickness/dowel diameter ratio is cyclically loaded to the same displacement level, dowel-type joint exhibits pinched hysteretic behavior by irrecoverable crushing of wood. The irrecoverable crushing of inoculated sample became significant for decay degradation and, as a consequence, the deformation without wood support was increased and the hysteresis loops was thinner. To investigate the effect of decay on those hysteresis properties, the displacement due to the gap between the dowel and dowel lead hole and the equivalent viscous damping were calculated for second and third loops obtained from reversed cyclic loading tests. Hysteresis properties were obtained from wet control and inoculated samples.

Displacement due to the gap between the dowel and the lead hole (δs) was defined by displacement until the load reached 0.05kN, as shown in Fig. 4. The ratio of displacement due to the gap to peak displacement on the loop ($\delta s/\delta max$) is shown in Fig. 9. The values of ($\delta s/\delta max$) for inoculated sample was 1.20 to 2.29 times as large as that for wet control sample. The irrecoverable deformation of wood was significantly caused by the fungus, and accordingly, the gap between the dowel and the lead hole under cyclic loading was expanded and the values of ($\delta s/\delta max$) were increased.

Equivalent viscous damping (h_{eq}) was obtained from the ratio of the cyclic dissipated energy to the potential energy, as shown in Fig. 4. The relationship between the equivalent viscous damping and the absolute value of the peak displacement on the loop is shown in Fig. 10. Inoculated samples showing mass loss in the range of 3% to 16% showed almost the same equivalent viscous damping, a decrease of about 35% on average, as sound samples.

The increase of gap between dowel and dowel lead hole and pinched hysteretic behavior in dowel-type joints is attributed to loosening of the joints. The dowel-type joints exposed to the fungus would show very low resistance under cyclic loading conditions because of increase of deformation without wood support and thinner hysteresis loop in dowel-type joints.

Conclusions

The monotonic and the reversed cyclic loading tests conducted on the dowel-type joints that exposed to a brown rot fungus, *F. palustris*.

When dowel-type joints are placed in wet conditions, compared to air-dried samples, initial stiffness, yield load and maximum load show significant reduction, and further decrease by degradation of wood caused by the fungus. The reduction of shear performance caused by the fungus had the largest effect on the initial stiffness, followed by yield load and maximum load, in that order. For a 1% reduction of the yield load, the initial stiffness was decreased 1.15% and the maximum load was decreased 0.77%. When the dowel-type joint exposed to the fungus is subjected to reversed cyclic loading, the gap between the dowel and the lead hole is increased and equivalent viscous damping is decreased.

Therefore, decay around the dowel lead hole especially affects the load-displacement behavior at small displacement level and the dowel-type joints under cyclic loading conditions would show very low resistance to forces acting on wooden structure.

Acknowledgements

This research was supported by the TOSTEM Foundation for Construction Materials Industry Promotion.

References

1. Takahashi M, Nishimoto K (1967) Studies on the mechanism of wood decay. I. Changes in strengths of BUNA and SUGI wood as decay proceeds (in Japanese). *Wood Research* 41, Kyoto University, pp 75-89
2. Wilcox W (1978) Review of literature on the effects of early stages of decay on wood strength. *Wood and Fiber* 9:252-257
3. Takiuchi H, Sawata K, Sasaki T, Okazaki Y, Doi S, Iijima Y (2007) Embedding strength of wood exposed to decay fungi (in Japanese). *Mokuzai Gakkaishi* 53: 46-51
4. Kent S, Leichti R, Rosowsky D, Morrell J (2004) Effects of wood decay by *Postia placenta* on the lateral capacity of nailed oriented strandboard sheathing and Douglas-fir framing members. *Wood and Fiber Science* 36:560-572
5. Kent S, Leichti R, Rosowsky D, Morrell J (2005) Effects of decay on the cyclic properties of nailed connections. *Journal of Materials in Civil Engineering* 17:579-585
6. Harada M, Hayashi Y, Hayashi T, Karube M, Ohgawa T (2005) Effect of moisture content of members on mechanical properties of timber joints. *J Wood Sci* 51:282-285
7. Japanese Industrial Standard (1987) Rolled steel for general structure (in Japanese). JIS G 3101
8. Japan 2X4 Home Builders Association (2002) Structural design guidelines for wood frame construction (in Japanese). Japan 2X4 Home Builders Association, Tokyo, pp 239-240
9. American Society for Testing and Materials (1995) Standard test methods for bolted connection in wood and wood-based products. ASTM D-5652. ASTM, West Conshohocken, PA, USA
10. For instance, Sawata K, Yasumura M (2003) Estimation of yield and ultimate strengths of bolted timber joints by nonlinear analysis and yield theory. *J Wood Sci* 49:383-391

Figure Legend

Fig. 1. Set-up of dowel-type joint test

Fig. 2. Loading protocol for reversed cyclic test. D_y , yield displacement

Fig. 3. Load-displacement curves of dowel-type joint. a air-dried control sample; b wet control sample; c inoculated sample. ML , mass loss

Fig. 4. Method of evaluating shear performances of dowel-type joint. a diagram showing the definition of K_s , P_y , P_{max} , D_y , D_{max} and dissipated energy; b definition of δ_s ; c definition of heq . K_s , initial stiffness; P_y , yield load; P_{max} , maximum load; D_y , yield displacement; D_{max} , displacement corresponding to maximum load; δ_s , displacement corresponding to 0.05kN; δ_{max} , peak displacement; heq , equivalent viscous damping; ΔW , dissipated energy; W_{e1} , potential energy in tensile loading; W_{e2} , potential energy in compressive loading

Fig. 5. Relationship between shear performance of dowel-type joint and decay period. a K_s , P_y and P_{max} ; b D_y , D_{max} and dissipated energy

Fig. 6. Relationship between remaining ratio of shear performance of dowel-type joint and mass loss. a K_s ; b P_y ; c P_{max}

Fig. 7. Comparison of remaining ratio of initial stiffness and maximum load with remaining ratio of yield load

Fig. 8. Third cycle hysteresis loops of dowel-type joint. ML , mass loss

Fig. 9. Relationship between the value of (δ_s/δ_{max}) and peak displacement.

Fig. 10. Relationship between equivalent viscous damping and peak displacement.

Table Title

Table 1. Summary of dowel-type joint test.

Table 2. Results of shear tests of dowel-type joint using control sample. Numbers in parentheses show standard deviations. Cyclic (+) and (-) show results in tensile loading and compressive loading, respectively; MC, moisture content; K_s , initial stiffness; P_y , yield load; D_y , yield displacement; P_{max} , maximum load; D_{max} , displacement corresponding to maximum load

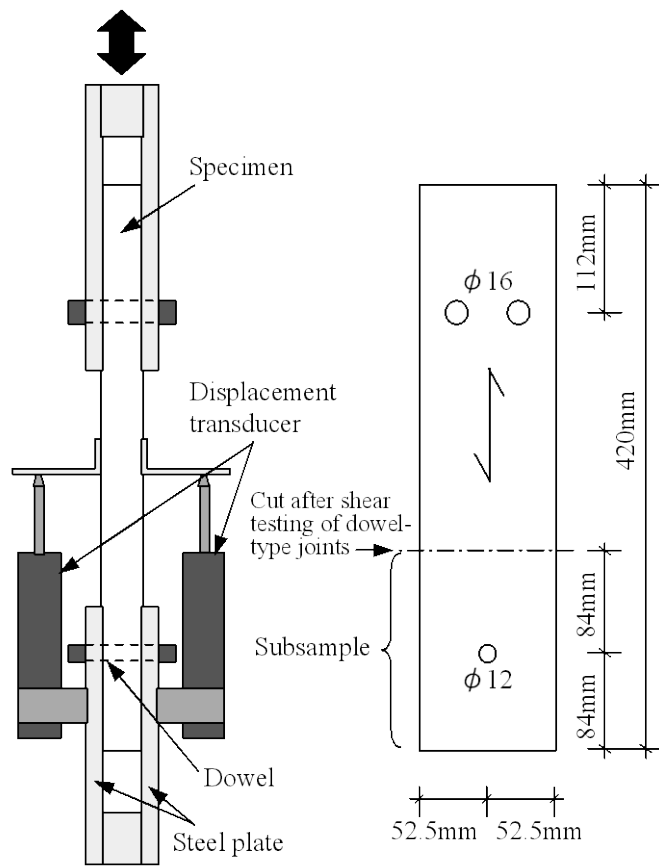


Fig. 1. Set-up of dowel-type joint test

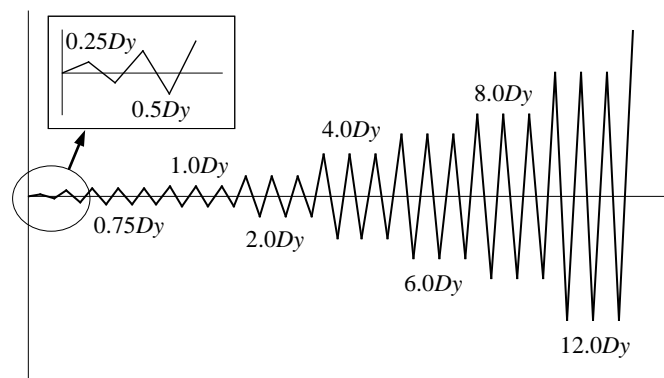


Fig. 2. Loading protocol for reversed cyclic test. D_y , yield displacement

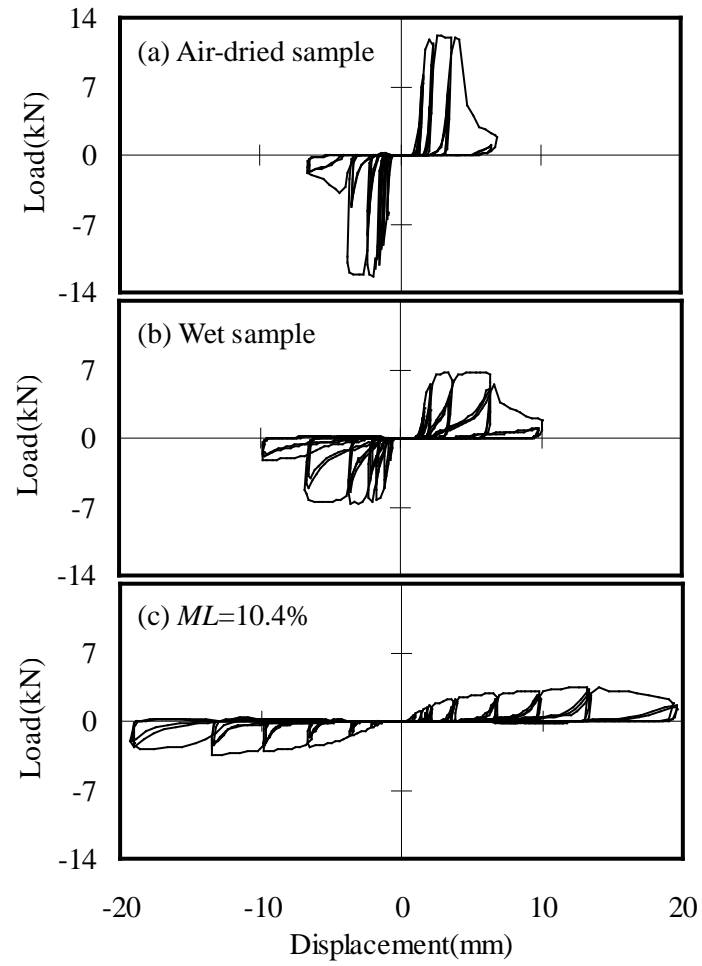


Fig. 3. Load-displacement curves of dowel-type joint. **a** air-dried control sample; **b** wet control sample; **c** inoculated sample. ML , mass loss

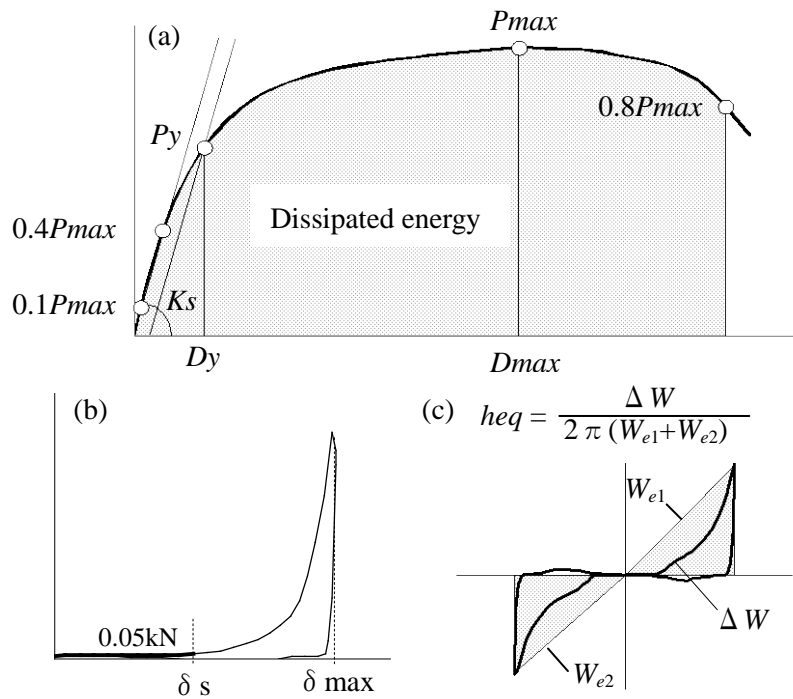


Fig. 4. Method of evaluating shear performances of dowel-type joint. **a** diagram showing the definition of K_s , P_y , P_{max} , D_y , D_{max} and dissipated energy; **b** definition of δs ; **c** definition of heq . K_s , initial stiffness; P_y , yield load; P_{max} , maximum load; D_y , yield displacement; D_{max} , displacement corresponding to maximum load; δs , displacement corresponding to 0.05 kN; δ_{max} , peak displacement; heq , equivalent viscous damping; ΔW , dissipated energy; W_{e1} , potential energy in tensile loading; W_{e2} , potential energy in compressive loading

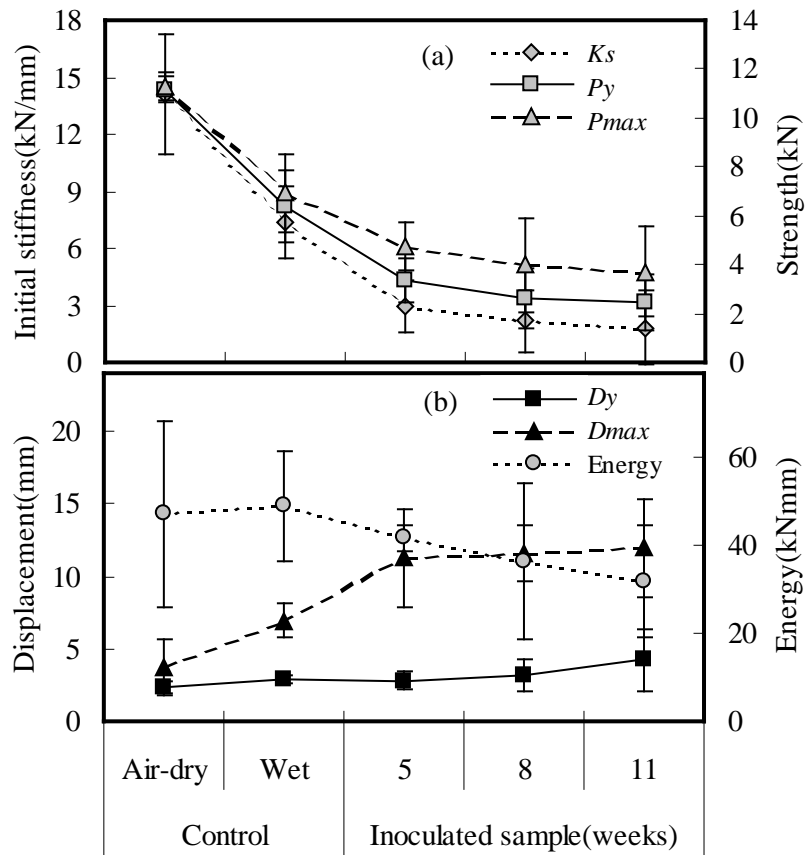


Fig. 5. Relationship between shear performance of dowel-type joint and decay period. **a** K_s , P_y and P_{max} ; **b** D_y , D_{max} and dissipated energy

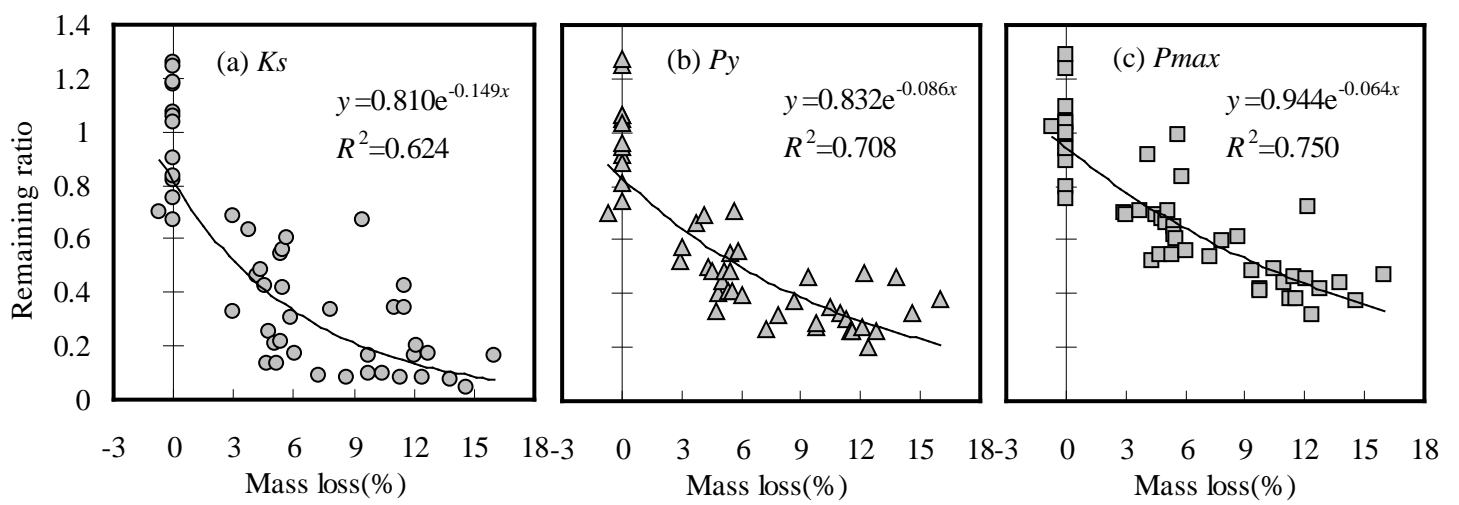


Fig. 6. Relationship between remaining ratio of shear performance of dowel-type joint and mass loss. **a** K_s ; **b** P_y ; **c** P_{max}

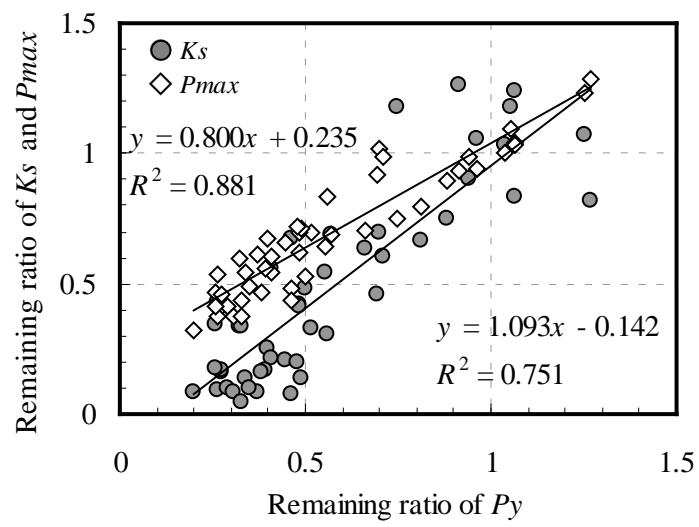


Fig. 7. Comparison of remaining ratio of initial stiffness and maximum load with remaining ratio of yield load

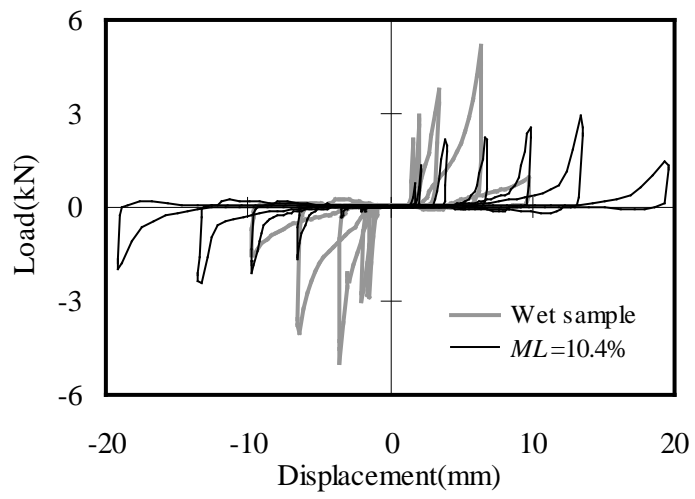


Fig. 8. Third cycle hysteresis loops of dowel-type joint. *ML*, mass loss

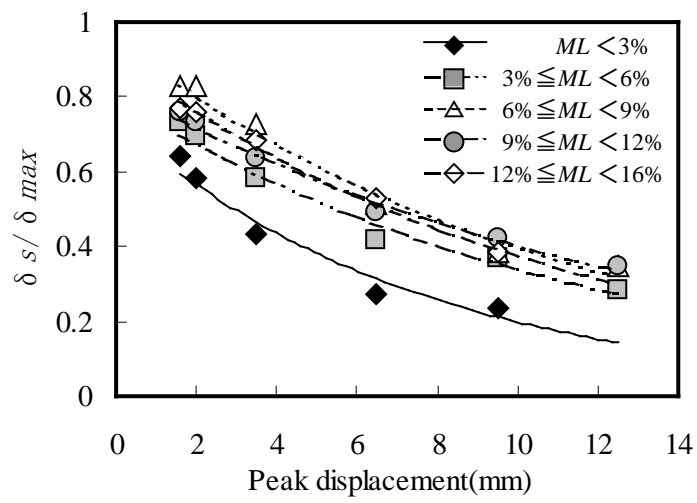


Fig. 9. Relationship between the value of (δ_s / δ_{max}) and peak displacement.

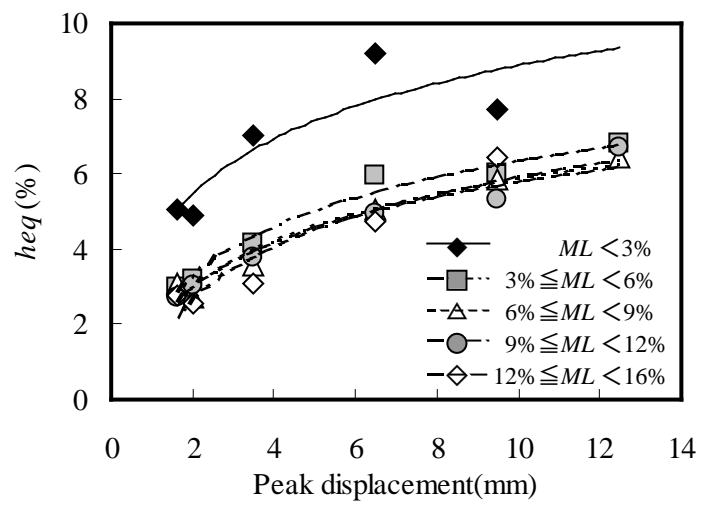


Fig. 10. Relationship between equivalent viscous damping and peak displacement.

Table 1. Summary of dowel-type joint test

Condition	Fungal exposure time	Loading type	Number of sample
Control sample			
Air-dry	0week	Monotonic	9
		Cyclic	3
Wet	0week	Monotonic	6
		Cyclic	6
Inoculated sample			
Wet	5weeks	Monotonic	6
		Cyclic	6
Wet	8weeks	Monotonic	6
		Cyclic	6
Wet	11weeks	Monotonic	6
		Cyclic	6

Table 2. Results of shear tests of dowel-type joint using control sample

Loading type	Density (kg/m ³)	MC (%)	<i>K_s</i> (kN/mm)	<i>P_y</i> (kN)	<i>D_y</i> (mm)	<i>P_{max}</i> (kN)	<i>D_{max}</i> (mm)	Energy (kNmm)
Air-dry condition								
Monotonic	472(24.6)	13.6(0.25)	14.1(3.16)	11.1(0.53)	2.33(0.45)	11.3(0.57)	3.68(1.95)	47.1(21.3)
Cyclic(+)	468(21.6)	12.9(0.25)	16.0(2.45)	11.3(0.27)	2.41(0.06)	12.5(0.75)	2.94(0.40)	27.3(6.11)
Cyclic(-)			20.0(6.20)	12.1(0.04)	1.84(0.09)	12.8(0.73)	1.99(0.09)	25.8(9.86)
Wet condition								
Monotonic	478(32.4)	64.5(11.1)	7.41(1.90)	6.38(1.47)	2.90(0.31)	6.92(1.59)	6.92(1.16)	48.8(12.4)
Cyclic(+)	470(24.1)	73.7(8.69)	6.64(0.98)	6.94(0.27)	2.88(0.18)	7.29(0.40)	6.33(0.28)	37.8(7.50)
Cyclic(-)			9.49(1.64)	6.34(0.50)	1.80(0.20)	7.05(0.36)	4.78(1.66)	34.5(14.6)

Numbers in parentheses show standard deviations

Cyclic (+) and (-) show results in tensile loading and compressive loading, respectively

MC, moisture content; *K_s*, initial stiffness; *P_y*, yield load; *D_y*, yield displacement; *P_{max}*, maximum load; *D_{max}*, displacement corresponding to maximum load