

## Synthesis, Crystal Structure, and Adsorption Properties of Werner-type Cu(II) Complex $[\text{Cu}(\text{CF}_3\text{SO}_3)_2(4\text{-methylpyridine})_4]$

Shin-ichiro Noro,<sup>\*1,2,3</sup> Katsuo Fukuhara,<sup>2</sup> Kazuya Kubo,<sup>1,2</sup> and Takayoshi Nakamura<sup>\*1,2</sup>

<sup>1</sup>Research Institute for Electronic Science, Hokkaido University, Sapporo, Hokkaido 001-0020

<sup>2</sup>Graduate School of Environmental Earth Science, Hokkaido University, Sapporo, Hokkaido 060-0810

<sup>3</sup>PRESTO, Japan Science and Technology Agency (JST), 4-1-8 Honcho, Kawaguchi, Saitama 332-0012


(Received May 14, 2012; CL-120603; E-mail: noro@es.hokudai.ac.jp)

A Werner-type Cu(II) complex,  $\alpha$ - $[\text{Cu}(\text{CF}_3\text{SO}_3)_2(4\text{-mepy})_4]$  ( $\alpha$ -PAC-1- $\text{CF}_3\text{SO}_3$ , PAC: porous assembly of coordination complex and 4-mepy: 4-methylpyridine), was synthesized, crystallographically characterized, and its adsorption properties were compared with those of the derivative  $\alpha$ - $[\text{Cu}(\text{PF}_6)_2(4\text{-mepy})_4]$  ( $\alpha$ -PAC-1-PF<sub>6</sub>).

Porous assemblies of coordination complexes (PACs), which are formed by the assembly of discrete coordination complexes without internal spaces via intermolecular interactions (van der Waals, electrostatic, and hydrogen-bonding interactions) that are weaker than coordination bonds,<sup>1–3</sup> have the potential to provide the following unique host–guest features: (i) diversity in assembled structures with guest molecules, resulting from weak and flexible intermolecular interactions;<sup>1h,1i</sup> (ii) formation of host frameworks consisting of two or more different discrete coordination complexes;<sup>1j</sup> (iii) facile fabrication of films because of high solubility;<sup>1k,1l</sup> and (iv) polymorphism without guest molecules, which is controlled by a kind of preadsorbed guests.<sup>1c,1i</sup> These characteristics of PACs could supply not only fundamental information about their pores but also unprecedented, useful porous functions.

The Werner-type complex  $[\text{Ni}(\text{NCS})_2(4\text{-mepy})_4]$  (4-mepy: 4-methylpyridine) and its derivatives are well known as examples of PACs; their preparation and guest-inclusion abilities were first reported in 1957.<sup>1a</sup> Among them,  $[\text{Ni}(\text{NCS})_2(4\text{-mepy})_4]$  has been thoroughly studied because of its interesting guest-inclusion properties derived from pseudopolymorphism, such as a dense  $\alpha$ -form, and guest-including  $\beta$ - and  $\gamma$ -forms. The  $\alpha$ -form has no space for including guest molecules because of its dense packing structure, whereas the  $\beta$ - and  $\gamma$ -forms are channel-type and layer-type clathrates, respectively.<sup>1i</sup> In particular, this complex easily affords an empty  $\beta$ -form that adsorbs several gases with type I isotherms.

We have recently found that a Cu(II)-based PAC,  $[\text{Cu}(\text{PF}_6)_2(4\text{-mepy})_4]$  (PAC-1-PF<sub>6</sub>), which is a quasi-Werner-type metal complex, has interesting guest-recognition abilities.<sup>4</sup> The dense  $\alpha$ -form,  $\alpha$ -PAC-1-PF<sub>6</sub>, has inorganic PF<sub>6</sub><sup>−</sup> anions covered with only fluorine atoms in the framework, and it adsorbs CO<sub>2</sub> gas with structural transformations; this is the first example of gas-adsorption properties in the dense  $\alpha$ -form. On the other hand, when  $\alpha$ -PAC-1-PF<sub>6</sub> is recrystallized from acetone/*n*-hexane and 2-butanone/*n*-hexane, some of the weakly coordinated PF<sub>6</sub><sup>−</sup> anions are easily released from the axial sites and Lewis-base guests (acetone and 2-butanone) attach to these sites instead, forming the guest-including  $\gamma$ -form,  $\gamma$ - $\{[\text{Cu}(\text{PF}_6)_2(4\text{-mepy})_4][\text{Cu}(\text{PF}_6)(4\text{-mepy})_4(\text{acetone})]\cdot\text{PF}_6\cdot 4\text{acetone}\}$  ( $\gamma$ -PAC-1-PF<sub>6</sub>⊃2.5acetone),  $\gamma$ - $\{[\text{Cu}(\text{PF}_6)_2(4$

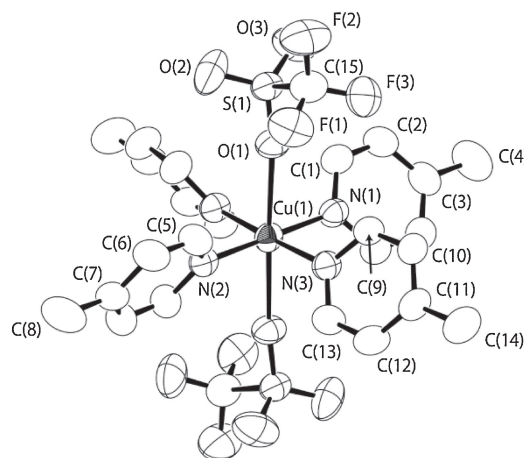


**Figure 1.** ORTEP drawing around the Cu(II) center in  $\alpha$ -PAC-1- $\text{CF}_3\text{SO}_3$ . The hydrogen atoms are omitted for clarity.

mepy)<sub>4</sub>][Cu(PF<sub>6</sub>)(4-mepy)<sub>4</sub>(2-butanone)]·PF<sub>6</sub>·3.5(2-butanone)} ( $\gamma$ -PAC-1-PF<sub>6</sub>⊃2.25(2-butanone)). The prefix “quasi-” derives from such labile axial bonds. These unprecedented phenomena have never been observed in any other Werner-type metal complexes. These results clearly indicate that Cu(II)-based PACs are useful for the construction of porous materials with multiguest-recognition properties.

In this letter, we report the synthesis, crystal structure, and adsorption properties of a derivative of  $\alpha$ -PAC-1-PF<sub>6</sub>,  $\alpha$ - $[\text{Cu}(\text{CF}_3\text{SO}_3)_2(4\text{-mepy})_4]$  ( $\alpha$ -PAC-1- $\text{CF}_3\text{SO}_3$ ), to investigate the effect of inorganic anions on the adsorption properties. The introduction of CF<sub>3</sub>SO<sub>3</sub><sup>−</sup> anions enhanced the intermolecular interactions through the oxygen atoms of the anions and inhibited gas adsorption with structural changes.

$\alpha$ -PAC-1- $\text{CF}_3\text{SO}_3$  was synthesized as follows: Cu(CF<sub>3</sub>SO<sub>3</sub>)<sub>2</sub> (362 mg, 1.0 mmol) and 4-mepy (466 mg, 5.0 mmol) were dissolved in acetone (20 mL) and excess *n*-hexane was added to the acetone solution, forming blue microcrystals of  $\alpha$ -PAC-1- $\text{CF}_3\text{SO}_3$ . Single crystals suitable for X-ray diffraction analysis were obtained by recrystallization from CHCl<sub>3</sub>/*n*-hexane.


The crystal structure of  $\alpha$ -PAC-1- $\text{CF}_3\text{SO}_3$  was determined by single-crystal X-ray diffraction analysis at 173 K.<sup>5</sup> Figure 1 shows the ORTEP view around the Cu(II) ion. The Cu(II) ion has an elongated octahedral environment with four 4-mepy molecules in the equatorial plane and two CF<sub>3</sub>SO<sub>3</sub><sup>−</sup> anions at the axial sites. The Cu–O bond distance of 2.468(2) Å is considerably longer than the equatorial Cu–N values (2.014(4)–2.025(3) Å), indicating that the Jahn–Teller axis is formed along the O–Cu–O direction. The axial bonds in  $\alpha$ -PAC-1- $\text{CF}_3\text{SO}_3$  are shorter than those in  $\alpha$ -PAC-1-PF<sub>6</sub> (Cu–F bond dis-

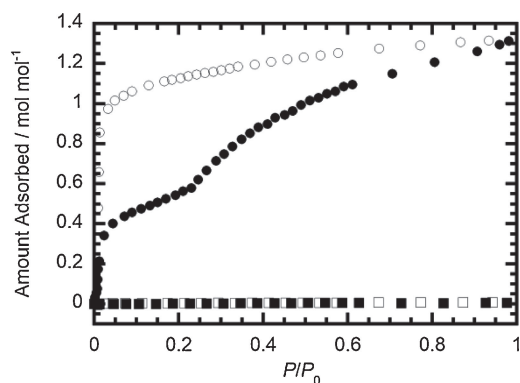

**Figure 2.** Adsorption (filled symbols) and desorption (open symbols) isotherms for CO<sub>2</sub> at 195 K on  $\alpha$ -PAC-1-CF<sub>3</sub>SO<sub>3</sub> (squares) and  $\alpha$ -PAC-1-PF<sub>6</sub> (circles).

tances = 2.478(2), 2.528(2), 2.586(2), and 2.629(2) Å),<sup>6</sup> which is a reasonable result because CF<sub>3</sub>SO<sub>3</sub><sup>−</sup> anions have stronger Lewis basicity than PF<sub>6</sub><sup>−</sup> anions.<sup>7</sup> Each mononuclear Cu(II) complex is densely packed, resulting in the assembled structure having no pores (accessible void space calculated using the PLATON program is 0%).<sup>8</sup>

The adsorption and desorption isotherms for CO<sub>2</sub> at 195 K on  $\alpha$ -PAC-1-PF<sub>6</sub> and  $\alpha$ -PAC-1-CF<sub>3</sub>SO<sub>3</sub> were measured to compare the effects of inorganic anions. As shown in Figure 2,  $\alpha$ -PAC-1-PF<sub>6</sub> shows CO<sub>2</sub> adsorption. Because  $\alpha$ -PAC-1-PF<sub>6</sub> possesses no vacant space, the observed adsorption behavior with large hysteresis should be associated with gate-opening processes, in which adsorption occurs with structural transformations.<sup>4</sup> On the other hand,  $\alpha$ -PAC-1-CF<sub>3</sub>SO<sub>3</sub> scarcely adsorbs CO<sub>2</sub> gas over the entire pressure range. In general, the gate-opening pressure depends on the strength of host–host and/or host–guest interactions. Weak host–host and strong host–guest interactions decrease the gate-opening pressure. First, host–host interactions were checked from the viewpoint of (1) the type of intermolecular interactions, and (2) their distances and angles. In  $\alpha$ -PAC-1-CF<sub>3</sub>SO<sub>3</sub>, there are weak intermolecular hydrogen bonds between noncoordinated oxygen atoms of CF<sub>3</sub>SO<sub>3</sub><sup>−</sup> anions and hydrogen atoms of 4-mepy ligands (O...C = 3.33, 3.40, and 3.42 Å, Figure 3).  $\alpha$ -PAC-1-PF<sub>6</sub> bears slightly shorter intermolecular contacts between noncoordinated fluorine atoms of PF<sub>6</sub><sup>−</sup> anions and hydrogen atoms of 4-mepy ligands (F...C = 3.19–3.32 Å, see Supporting Information).<sup>14</sup> However, considering the van der Waals radii of oxygen and fluorine atoms (1.52 and 1.47 Å, respectively) and the C–H(pyridyl)...O(F) angles (see Table S2),<sup>9,14</sup> the slight difference observed in the intermolecular distances may not reflect a difference in the strength of the intermolecular interactions. On the other hand, as confirmed by DFT calculations for  $\alpha$ -[Cu(A)<sub>2</sub>(py)<sub>4</sub>] ( $\alpha$ -PAC-2-A, A = PF<sub>6</sub> and CF<sub>3</sub>SO<sub>3</sub>, py: pyridine),  $\alpha$ -PAC-2-PF<sub>6</sub> bears an almost uniform negative potential over all the surface fluorine atoms of PF<sub>6</sub><sup>−</sup>. In contrast, the CF<sub>3</sub>SO<sub>3</sub><sup>−</sup> anions in  $\alpha$ -PAC-2-CF<sub>3</sub>SO<sub>3</sub> have negative potentials on their oxygen atoms; their magnitude is higher than that on the fluorine atoms in  $\alpha$ -PAC-2-PF<sub>6</sub>.<sup>10</sup> Moreover, a fluorine atom, with a small polarizability, weakens intermolecular interactions. These results imply that host–host interactions (including acid–base and van der Waals interactions) in  $\alpha$ -PAC-1-PF<sub>6</sub> are weaker than those in  $\alpha$ -PAC-1-

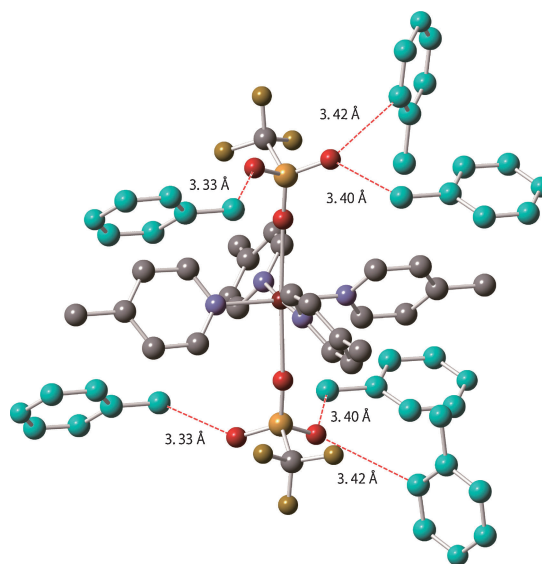

**Figure 3.** View of the intermolecular interactions in  $\alpha$ -PAC-1-CF<sub>3</sub>SO<sub>3</sub>, in which the red dashed lines indicate hydrogen bonds. The 4-mepy molecules of other mononuclear complexes are represented in sky blue. The hydrogen atoms are omitted for clarity.

CF<sub>3</sub>SO<sub>3</sub>. Next, host–guest interactions were compared. It is known that a CO<sub>2</sub> molecule interacts with these fluorinated anions via weak acid–base interactions in ionic liquids.<sup>11</sup> As mentioned above, the Lewis basicity of CF<sub>3</sub>SO<sub>3</sub><sup>−</sup> anions is stronger than that of PF<sub>6</sub><sup>−</sup> ones. Furthermore, the results of DFT and MP2 calculations show that the binding energy in the CF<sub>3</sub>SO<sub>3</sub><sup>−</sup>–CO<sub>2</sub> complex is slightly higher than that in PF<sub>6</sub><sup>−</sup>–CO<sub>2</sub>.<sup>12</sup> Hence, the host–guest interaction between the [Cu(PF<sub>6</sub>)<sub>2</sub>(4-mepy)<sub>4</sub>] unit and CO<sub>2</sub> is probably weaker than that between the [Cu(CF<sub>3</sub>SO<sub>3</sub>)<sub>2</sub>(4-mepy)<sub>4</sub>] unit and CO<sub>2</sub>. This comparison of host–host and host–guest interactions indicates that host–host interactions predominantly influence gate-opening adsorptions in these PACs.

A similar tendency has been observed in the two-dimensional Cu(II) porous coordination polymers (PCPs) [Cu(A)<sub>2</sub>(4,4′-bpy)<sub>2</sub>]<sub>n</sub> (A = PF<sub>6</sub> and CF<sub>3</sub>SO<sub>3</sub>, 4,4′-bpy: 4,4′-bipyridine).<sup>10,13</sup> Both PCPs have similar two-dimensional frameworks with weakly coordinated inorganic anions, PF<sub>6</sub><sup>−</sup> and CF<sub>3</sub>SO<sub>3</sub><sup>−</sup>, at the axial sites and show two kinds of adsorption events: micropore filling in open voids and gate-opening adsorption with expansion of the layers. The gate-opening pressures for [Cu(PF<sub>6</sub>)<sub>2</sub>(4,4′-bpy)<sub>2</sub>]<sub>n</sub> are considerably lower than those for [Cu(CF<sub>3</sub>SO<sub>3</sub>)<sub>2</sub>(4,4′-bpy)<sub>2</sub>]<sub>n</sub>. These results can also be explained by the difference in the strengths of host–host interactions.

In conclusion, we achieved the synthesis and crystallographic characterization of the Werner-type Cu(II)-based PAC  $\alpha$ -[Cu(CF<sub>3</sub>SO<sub>3</sub>)<sub>2</sub>(4-mepy)<sub>4</sub>] ( $\alpha$ -PAC-1-CF<sub>3</sub>SO<sub>3</sub>). The weak hydrogen-bonding interactions between the oxygen atoms of the CF<sub>3</sub>SO<sub>3</sub><sup>−</sup> anions and the hydrogen atoms of the 4-mepy ligands make the assembled structure rigid, resulting in the suppression of CO<sub>2</sub> adsorption with structural transformations. This finding could help in designing flexible PCPs that show gate-opening adsorption. In addition, although  $\alpha$ -PAC-1-CF<sub>3</sub>SO<sub>3</sub> did not

show porosity for CO<sub>2</sub> gas, other organic vapors, such as alcohols, ketones, and benzene, may adsorb on  $\alpha$ -PAC-1-CF<sub>3</sub>SO<sub>3</sub> with structural transformations.<sup>4</sup> Further work is therefore in progress to isolate the guest-including  $\beta$ - and  $\gamma$ -PAC-1-CF<sub>3</sub>SO<sub>3</sub> and check the vapor-adsorption properties of  $\alpha$ -PAC-1-CF<sub>3</sub>SO<sub>3</sub>.

The present research is supported by the PRESTO project, Japan Science and Technology Agency, and by a Grant-in-Aid for Science Research from the Ministry of Education, Culture, Sports, Science and Technology, Japan.

Paper based on a presentation made at the International Association of Colloid and Interface Scientists, Conference (IACIS2012), Sendai, Japan, May 13–18, 2012.

#### References and Notes

- a) W. D. Schaeffer, W. S. Dorsey, D. A. Skinner, C. G. Christian, *J. Am. Chem. Soc.* **1957**, *79*, 5870. b) D. Belitskus, G. A. Jeffrey, R. K. McMullan, N. C. Stephenson, *Inorg. Chem.* **1963**, *2*, 873. c) S. A. Allison, R. M. Barrer, *J. Chem. Soc. A* **1969**, 1717. d) D. H. Brown, R. H. Nuttall, J. McAvoy, D. W. A. Sharp, *J. Chem. Soc. A* **1966**, 892. e) I. S. Kerr, D. J. Williams, *Acta Crystallogr., Sect. B: Struct. Crystallogr. Cryst. Chem.* **1977**, *33*, 3589. f) J. Lipowski, P. Starzewski, W. Zielenkiewicz, *Thermochim. Acta* **1981**, *49*, 269. g) A. Y. Manakov, J. Lipowski, *Thermochim. Acta* **1996**, *277*, 199. h) A. Y. Manakov, J. Lipowski, J. Pielaszek, *J. Inclusion Phenom. Macrocyclic Chem.* **1999**, *35*, 531. i) D. V. Soldatov, G. D. Enright, J. A. Ripmeester, *Cryst. Growth Des.* **2004**, *4*, 1185. j) P. B. Durand, E. M. Holt, *Acta Crystallogr., Sect. C: Cryst. Struct. Commun.* **1995**, *51*, 850. k) H. O. Finklea, M. A. Phillippi, E. Lompert, J. W. Grate, *Anal. Chem.* **1998**, *70*, 1268. l) M. R. Jarrett, H. O. Finklea, *Anal. Chem.* **1999**, *71*, 353.
- a) S. A. Gromilov, I. A. Baidina, G. I. Zharkova, *J. Struct. Chem.* **1997**, *38*, 792. b) D. V. Soldatov, J. A. Ripmeester, S. I. Shergina, I. E. Sokolov, A. S. Zanina, S. A. Gromilov, Y. A. Dyadin, *J. Am. Chem. Soc.* **1999**, *121*, 4179. c) D. V. Soldatov, J. A. Ripmeester, *Chem. Mater.* **2000**, *12*, 1827. d) A. Y. Manakov, D. V. Soldatov, J. A. Ripmeester, J. Lipowski, *J. Phys. Chem. B* **2000**, *104*, 12111. e) A. V. Nossov, D. V. Soldatov, J. A. Ripmeester, *J. Am. Chem. Soc.* **2001**, *123*, 3563. f) D. V. Soldatov, E. V. Grachev, J. A. Ripmeester, *Cryst. Growth Des.* **2002**, *2*, 401. g) C. I. Ratcliffe, D. V. Soldatov, J. A. Ripmeester, *Microporous Mesoporous Mater.* **2004**, *73*, 71.
- a) S. A. Dalrymple, G. K. H. Shimizu, *J. Am. Chem. Soc.* **2007**, *129*, 12114. b) S. A. Dalrymple, G. K. H. Shimizu, *Chem. Commun.* **2006**, 956. c) S. Takamizawa, T. Akatsuka, T. Ueda, *Angew. Chem., Int. Ed.* **2008**, *47*, 1689. d) S. Takamizawa, M.-a. Kohbara, T. Akatsuka, R. Miyake, *New J. Chem.* **2008**, *32*, 1782.
- S.-i. Noro, T. Ohba, K. Fukuhara, Y. Takahashi, T. Akutagawa, T. Nakamura, *Dalton Trans.* **2011**, *40*, 2268.
- Crystallographic data of  $\alpha$ -PAC-1-CF<sub>3</sub>SO<sub>3</sub>. C<sub>26</sub>H<sub>28</sub>CuF<sub>6</sub>N<sub>4</sub>O<sub>6</sub>S<sub>2</sub>, *M<sub>r</sub>* = 734.19, Orthorhombic, *Pbcn* (#60), *a* = 10.9762(5) Å, *b* = 17.8294(10) Å, *c* = 16.5322(8) Å, *V* = 3235.4(3) Å<sup>3</sup>, *T* = 173 K, *Z* = 4, *D<sub>calcd</sub>* = 1.507 g cm<sup>-3</sup>, *F<sub>000</sub>* = 1500.00,  $\lambda$  = 0.71075 Å,  $\mu$ (Mo K $\alpha$ ) = 8.830 cm<sup>-1</sup>, 29498 measured reflections, 3687 unique (*R<sub>int</sub>* = 0.0312). *R<sub>1</sub>* = 0.0440 (*I* > 2 $\sigma$ (*I*)) and *wR<sub>2</sub>* = 0.1597 (all data) with GOF = 1.078. CCDC-877849. Selected bond distances and angles are listed in Table S1.<sup>14</sup>
- There are two crystallographically independent mononuclear Cu(II) complexes in  $\alpha$ -PAC-1-PF<sub>6</sub>.
- W. Linert, Y. Fukuda, A. Camard, *Coord. Chem. Rev.* **2001**, *218*, 113.
- The accessible void space was calculated with the program PLATON by using a probe with a radius of 1.2 Å: A. L. Spek, *J. Appl. Crystallogr.* **2003**, *36*, 7.
- Because we can not determine exact positions of the methyl hydrogen atoms, the C–H(methyl)–O(F) angles are unclear.
- Unpublished works.
- a) S. G. Kazarian, B. J. Briscoe, T. Welton, *Chem. Commun.* **2000**, 2047. b) S. N. V. K. Aki, B. R. Mellein, E. M. Saurer, J. F. Brennecke, *J. Phys. Chem. B* **2004**, *108*, 20355.
- B. L. Bhargava, S. Balasubramanian, *Chem. Phys. Lett.* **2007**, *444*, 242.
- A. Kondo, H. Kajiro, H. Noguchi, L. Carlucci, D. M. Proserpio, G. Ciani, K. Kato, M. Takata, H. Seki, M. Sakamoto, Y. Hattori, F. Okino, K. Maeda, T. Ohba, K. Kaneko, H. Kanoh, *J. Am. Chem. Soc.* **2011**, *133*, 10512.
- Supporting Information is available electronically on the CSJ-Journal Web site, <http://www.csj.jp/journals/chem-lett/index.html>.