

A Study of Small Particle Yttrium Oxide Type Phosphors prepared from Solution using a Sacrificial Micellar Phase as a Combustion Fuel

K. Saltoun, T.G. Ireland, G.R. Fern, R. Withnall, and J. Silver

Centre for Phosphors and Display Materials, Wolfson Centre for Materials Processing, Brunel University, Kingston Lane, Uxbridge, Middlesex UB8 3PH, UK; Email Robert.Withnall@brunel.ac.uk

INTRODUCTION

In 1999 the facile self-assembly of the red emitting phosphor yttrium oxide europium ($\text{Y}_2\text{O}_3:\text{Eu}^{3+}$) from solution using a sacrificial micellar phase was reported. The micellar phase was assembled using the alkyl ammonium salt ($\text{C}_{12}\text{H}_{25}\text{NH}_3$)Cl in an ethanolic solution. The resulting fine powder had smaller particles, ranging in size from 0.1 to 1.0 μm , than the commercial cubic $\text{Y}_2\text{O}_3:\text{Eu}^{3+}$ phosphor.¹ In this work we used a longer chained aliphatic amine, $\text{C}_{16}\text{H}_{33}\text{NH}_2$, as fuel.

RESULTS AND DISCUSSION

A typical preparation was carried out using the following method. A warm ethanolic solution of YCl_3 (55.37 g, in 25 ml, 0.25M) and EuCl_3 (1.76 g in 25ml, 0.02M) was added to a warm solution of $\text{C}_{16}\text{H}_{33}\text{NH}_3\text{Cl}$ in ethanol. This gave a stoichiometric ratio of 1:1 for the combined metal chloride to alkylammonium chloride present in the solution. In other preparations the metal chloride to alkylammonium chloride ratio was 1:3. The solution was heated on a hot plate to about 100°C where the initial yellow colour disappeared and the solution was reduced in volume until it became viscous and a pale yellow mass was then apparent. A portion of each product was then fired in a furnace (wherein the temperature was either set at 650°C or 900°C) for 30 min. This allowed the combustion of the alkylammonium chains.

For the samples that were produced at the furnace set temperature of 650°C, there was no evidence for cubic $\text{Y}_2\text{O}_3:\text{Eu}^{3+}$. On the other hand, the samples that were produced at the furnace set temperature of 900°C showed the presence of crystalline material and they showed a Raman spectrum and X-ray powder diffraction pattern identified as cubic $\text{Y}_2\text{O}_3:\text{Eu}^{3+}$.

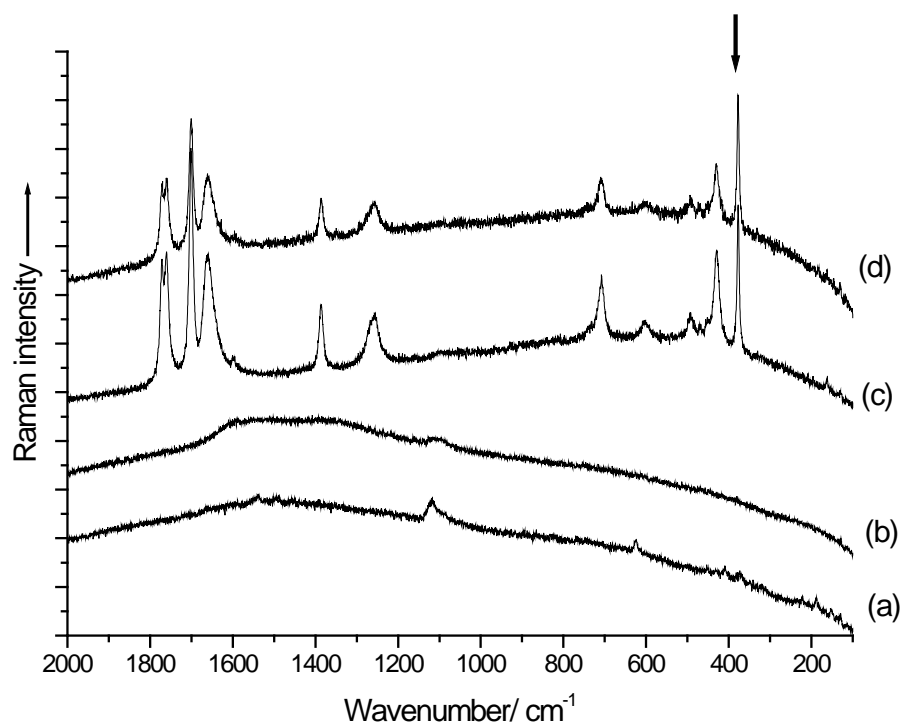


FIGURE 1. Raman spectra of phosphor samples prepared at metal chloride to alkylammonium chloride ratios of:- (a) 1:1 and fired at 650°C, (b) 1:3 and fired at 650°C, (c) 1:1 and fired at 900°C, and (d) 1:3 and fired at 900°C. The exciting wavelength was equal to 632.8 nm.

As can be seen from the Raman spectra shown in Figure 1, a strong Raman band at 377 cm⁻¹ (arrowed in Figure 1) is absent when the phosphor nanoparticles are fired at 650°C (see Figures 1a and 1b), but appears when the phosphor nanoparticles are fired at 900°C (see Figures 1c and 1d). This band is due to the cubic phase of Y₂O₃:Eu. In addition, a number of other strong bands also appear in Figures 1c and 1d; these are due to the photoluminescence of the Y₂O₃:Eu phosphors under 632.8 nm excitation.

In conclusion, when the oven temperature was set at 900°C (but not at 650°C), the combustion fuel present in the samples was sufficient to raise the temperature over 900°C for a long enough time period for nanometer sized crystallites of the cubic Y₂O₃:Eu³⁺ phase to form.

REFERENCES

1. T.G. Ireland, J. Silver, C. Gibbons and A. Vecht, *Electrochem. and Solid State Letts.*, **2**, 52-54, (1999).