



Journal of Biomedical
Materials Research
Part A

Effect of microgrooved surface topography on osteoblast maturation and protein adsorption

Journal:	<i>Journal of Biomedical Materials Research: Part A</i>
Manuscript ID:	JBMR-A-14-1013.R1
Wiley - Manuscript type:	Original Article
Date Submitted by the Author:	n/a
Complete List of Authors:	de Luca, Alba; University of Cambridge, Department of Engineering Zink, Mareike; University of Leipzig, Faculty of Physics and Earth Sciences, Institute for Experimental Physics I, Soft Matter Physics Division Weidt, Astrid; University of Leipzig, Faculty of Physics and Earth Sciences, Institute for Experimental Physics I, Soft Matter Physics Division Mayr, Stefan; University of Leipzig, Leibniz Institute for Surface Modification (IOM), Translational Centre for Regenerative Medicine and Faculty of Physics and Earth Sciences Markaki, Athina; University of Cambridge, Engineering
Keywords:	Fibronectin, Grooved Substrates , Osteoblast Cells, Surface Topography, Contact Guidance

SCHOLARONE™
Manuscripts

1
2
3 **Effect of microgrooved surface topography on osteoblast maturation and protein**
4 **adsorption**
5
6

7 A. C. de Luca¹, M. Zink², A. Weidt², S. G. Mayr³, A. E. Markaki^{1*}
8

9 *¹Department of Engineering, University of Cambridge, Trumpington Street,*
10 *Cambridge, CB2 1PZ, UK*
11

12 *²Faculty of Physics and Earth Sciences, Institute for Experimental Physics I, Soft*
13 *Matter Physics Division, University of Leipzig, Linnéstraße 5, 04103 Leipzig,*
14 *Germany*
15

16 *³Leibniz Institute for Surface Modification (IOM), Translational Centre for*
17 *Regenerative Medicine and Faculty of Physics and Earth Sciences, University of*
18 *Leipzig, Permoserstraße 15, 04318 Leipzig, Germany*
19

20 * Address for correspondence:
21

22 Department of Engineering
23

24 University of Cambridge
25

26 Trumpington Street
27

28 Cambridge, CB2 1PZ, UK
29

30 Telephone Number: +44-1223-766417
31

32 FAX Number: +44-1223-332662
33

34 E-mail address: am253@cam.ac.uk
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Abstract

Microgrooved surfaces have been used extensively to influence cell contact guidance. Guiding cell growth, extracellular matrix deposition, and mineralization is important for bone implant longevity. In this study, we investigated the osteoblast response to microgrooved metallic surfaces in serum-supplemented medium. Groove spacing was comparable to the spread osteoblast size. Focal adhesions were observed to confine to the intervening ridge/groove boundaries. Osteoblasts bridged over the grooves and were unable to conform to the concave shape of the underlying grooves. Microgrooved surfaces induced higher osteoblast proliferation and metabolic activity after 14 days in osteogenic medium compared to as-received surfaces, resulting in higher mineralization, and alignment of cell-secreted collagen after 28 days. To establish whether preferential cell attachment at the ridge/groove boundaries was influenced by the adhesion proteins contained in the serum supplemented media, fluorescently-labelled fibronectin was adsorbed onto the microgrooved substrates at low concentrations, mimicking the concentrations found in blood serum. Fibronectin was found to selectively adsorb onto the ridge/groove boundaries, the osteoblast focal adhesion sites, suggesting that protein adsorption may have influenced the cell attachment pattern.

Keywords

Fibronectin, Grooved Substrates, Osteoblast Cells, Surface Topography, Contact Guidance.

1. Introduction

Longitudinal parallel grooves have been widely investigated due to their ability to induce cell alignment, known as "contact guidance"¹, which is the ability of the cell to use topographical cues for orientation and migration. Studies into the efficacy of these channels suggest that cell behaviour is affected in a microgroove dimension-dependent manner (eg²⁻⁹). Morphological

1
2
3 cell changes do not necessarily alter phenotypic expression. For example, when human
4
5 connective tissue progenitor cells were cultured on **polydimethylsiloxane** (PDMS) substrates
6
7 with U-shape microgrooves (11 μm deep, 45 μm wide, separated by 5 μm wide ridge), the
8
9 microgroove topography had no effect on cell differentiation¹⁰. Similar observations were
10
11 made when myoblasts were cultured on polycarbonate substrates with square microgrooves (5
12
13 μm deep, 5-75 μm wide, separated by 5-75 μm wide ridge) in terms of myogenic
14
15 differentiation¹¹. However, not all cell types are insensitive to microgrooves, suggesting that
16
17 modulation of phenotypic expression may be cell type specific¹¹. For example, osteoblasts
18
19 seeded on **titanium** substrates with V-shape microgrooves (5 and 10 μm deep, 30/ 60 μm
20
21 wide, separated by 30/60 μm ridge) were found to express higher levels of **alkaline**
22
23 **phosphatase** (ALP) compared to smooth surfaces⁴. Similar observations involving osteoblast
24
25 cells are reported elsewhere (reviewed by Anselme¹).
26
27
28

29 Although the effects of surface topography on cells have been studied extensively, it is **not**
30
31 **possible** to draw **some** clear conclusions due to the huge range of surfaces, pattern geometries
32
33 and cell types employed. Furthermore, in many studies, the effect of surface topography is not
34
35 truly distinguished from that of surface chemistry. Research has **focused** on understanding the
36
37 effect of surface topography on cell response, but often the interactions between proteins
38
39 present in the cellular surrounding, i.e. extracellular matrix (ECM) or blood, and the
40
41 substrates are not considered. Specific cell responses are in fact promoted when proteins
42
43 containing the arginine-glycine-aspartic acid (RGD) motif, such as fibronectin or vitronectin,
44
45 are adsorbed onto the biomaterial surface prior to cell adhesion. The adhesion multifunctional
46
47 glycoproteins of the ECM, such as fibronectin and vitronectin, and their receptors have been
48
49 found to play an important role in osteoblast differentiation and mineralization¹²⁻¹⁴. In
50
51 particular, fibronectin is a protein dimer, consisting of two nearly identical polypeptide
52
53 chains. The central-binding domain has been repeatedly reported to play the most important
54
55
56
57
58
59
60

1
2
3 role in the osteogenicity of bone cells. Adding anti-fibronectin antibodies to the culture
4
5 medium^{12,13} was correlated with a reduced osteoblast adhesion and mineralization. It was
6
7 observed that the inhibition of the osteogenic gene expression in the early phase of
8
9 osteogenesis was reversible, with deposition of calcified nodules occurring when the
10
11 fibronectin-osteoblast interactions were reactivated¹². Furthermore, fibronectin expression
12
13 has been observed *in vivo* at bone surfaces and *in vitro* at the periphery of nodules, confirming
14
15 the importance of this protein in osteogenesis¹².

16
17
18 It has been found that micro-¹⁵ and nano-scale^{16,17} topographical cues can stimulate changes
19
20 in protein adsorption. For example, on “rough” (at the micrometer level) grit-blasted surfaces,
21
22 proteins have been found to accumulate on peaks rather than valleys¹⁵, possibly due to higher
23
24 accessibility of these sites and higher electrostatic forces¹⁸. However, following adsorption,
25
26 proteins were found to migrate into the valleys¹⁸, concealing or exposing specific sites that
27
28 may alter the biological function of the protein. Therefore, it could be hypothesized that
29
30 preferential protein adsorption may affect “cell contact guidance”.

31
32
33 In this study, osteoblast interactions with patterned substrates were investigated in serum-
34
35 supplemented medium, thus containing adhesion promoting fibronectin proteins. Parallel
36
37 grooves, with widths comparable to the spread osteoblast size, were produced by
38
39 photoetching on 316L stainless steel substrates. Cell morphology, proliferation and
40
41 mineralization, and collagen production were investigated. Protein adsorption experiments,
42
43 using fluorescently-labelled fibronectin, were carried out to investigate how the grooves
44
45 spatially control protein adsorption. Fibronectin adsorption was influenced by the local
46
47 topography. It was hypothesized that the observed cell attachment pattern on the
48
49 microgrooves may have been influenced by preferential adsorption of adhesion-promoting
50
51 proteins.
52
53
54
55
56
57
58
59
60

2. Materials & Methods

2.1 Material and Specimen Preparation

Mirror-finish 316L austenitic stainless steel sheets (1 mm thick), supplied by Aalco

(Roundtree Way, Mousehold Lane, Norwich, NR7 8SR, UK), were used for this study.

Microgrooves were photoetched on the surface of 316L samples by Precision Micro (Vantage Way, Birmingham, B24 9GZ, UK). The samples had a square cross-section with a side length of 8 mm. In addition, 9.5 mm diameter discs were cut out of the as-received sheets using a punch press. The latter served as a control surface.

For material characterization, the discs were ultrasonically cleaned, sequentially, for 5 min in acetone, ethanol and distilled water, and then dried in oven at 60 °C. For biological investigations, discs were further sterilized at 160 °C for 2 hours.

2.2 Topographic Characterization

2.2.1 Differential Interference Contrast (DIC) Microscopy

Surface topography was characterized with a DIC microscope equipped with an Enhanced Focal Imaging (EFI) control for 3D surface mapping (Olympus BX51m, Japan). Images were acquired at 10x magnification.

2.2.2 Scanning Electron Microscopy (SEM)

For SEM analysis, samples were mounted on aluminium stubs with double-sided carbon tape. Images were acquired using an Evo MA 15 scanning electron microscope (Zeiss, UK) with an accelerating voltage of 14 kV at 1000x magnification.

2.2.3 Analysis of Micropatterns

Cross-sections of the patterned surfaces were impregnated in Acri-Kleer cold mounting resin (MetPrep Ltd, UK), ground with a series of SiC papers (MetPrep Ltd, UK) and polished with alumina micro-particles. Samples were observed using an optical light microscope (Leica

1
2
3 DMLM, UK) at 20x and 50x magnifications, with bright-field illumination. Pattern
4
5 dimensions were measured using the ImageJ software (National Institute of Health, US, ¹⁹).

7 8 *2.2.4 X-ray Photoelectron Spectroscopy (XPS)*

9
10 XPS data were acquired using a Kratos Axis Ultra DLD (delay-line detector) system,
11
12 equipped with a monochromatized Al K α X-ray source (spot size 700 \times 300 μm^2). For survey
13
14 spectra, a pass energy of 160 eV, a dwell time of 0.1 s and a step size of 1 eV were used. For
15
16 high resolution spectra, the pass energy and the step size were changed to 40 eV and 0.1 eV
17
18 respectively. A measurement time of 60 s per sweep was used instead of a fixed dwell time
19
20 and the number of sweeps was adjusted for optimum element quantification.

22 23 *2.2.5 Atomic Force Microscopy (AFM)*

24
25 Surface roughness was measured in tapping mode using a Bruker Dimension Icon AFM
26
27 equipped with a Nanoscope V controller. The scanned area was 1 \times 1 μm^2 . Post-processing,
28
29 including roughness evaluation, was performed using the Scanning Probe Image Processor
30
31 (SPIP) 6.0.6 software, applying polynomial fits (1st order) and 1st order line-wise corrections
32
33 to all images.
34
35

36 37 2.3 Cell Culture Studies

38 39 *2.3.1 Sourcing and Culture of Cells*

40
41 Primary foetal human osteoblasts (fHObs; 406-05f, European Collection of Cells Cultures
42
43 (ECACC)) were selected for the present study and used at the 5th passage for all the
44
45 experiments. fHObs were maintained and subcultured in growth medium containing McCoy's
46
47 5A medium (Thermo Scientific, UK), 10 % foetal bovine serum (FBS, Invitrogen, UK), 1 %
48
49 penicillin-streptomycin (Sigma, UK) and 30 mg/ml vitamin-C (L-Ascorbic Acid Phosphate
50
51 Magnesium Salt n-Hydrate, Wako GmbH).

52
53 Cells were seeded in growth medium at a density of 10,000 cells/cm² on each substrate (in
54
55 triplicate per type) and each experiment was repeated three times ($n = 3$). After 4 days, growth
56
57
58
59
60

1
2
3 medium was replaced to osteogenic medium, supplemented with 10 nM dexamethasone
4 (Sigma, UK) and 2.5 mM β -glycerophosphate (Sigma, UK) to stimulate fHob differentiation.

7 2.3.2 Cell Metabolic Activity and Proliferations

8
9 Cell metabolic activity was assessed using the AlamarBlue assay (ADB Serotec, UK), at
10 several time points (1, 3, 7, 10, 14 days), monitoring the same cell-seeded samples over time.
11 At each time point, 10 % (v/v) of AlamarBlue solution was added to each well and cells were
12 incubated for 4 hours at 37 °C. Following incubation, 100 μ L of the supernatant were
13 transferred in triplicate to a black 96-well plate. Fluorescence was recorded using a FluoStar
14 Optima plate reader (BMG Labtech, Germany) at 530 nm excitation and 590 nm emission.
15 Samples were then washed with sterile Hank's Balanced Salt Solution (HBSS; Invitrogen,
16 UK). Fresh medium was added to each well before incubation for the next time point. The
17 percentage of reduction of AlamarBlue is given by
18
19
20
21
22
23
24
25
26
27
28

$$29 \quad \% \text{ reduction of AlamarBlue} = \frac{S_{AB}^x - S_{AB}^{control}}{S_{AB}^{100\% \text{ reduced}} - S_{AB}^{control}}$$

30
31 where S_{AB}^x is the AlamarBlue fluorescence signal of the sample at day x , $S_{AB}^{100\% \text{ reduced}}$ is the
32 signal of the 100% reduced form of AlamarBlue and $S_{AB}^{control}$ is the signal from the control: the
33 culture medium supplemented with 10% AlamarBlue dye. The 100% reduced form of
34 AlamarBlue was produced by autoclaving controls.
35
36
37
38
39
40
41
42

43 Cell proliferation was evaluated using the CyQUANT Cell Proliferation Assay (Invitrogen,
44 UK). At each time point (1, 3, 7, 14 days), the medium was aspirated and the samples were
45 frozen at -80 °C until measurement. After thawing, a CyQUANT lysis buffer was added to
46 each well according to the manufacturer's instructions. The multi-well plates were gently
47 agitated and the cell lysate was transferred to a black 96-well plate. The CyQUANT dye
48 solution was added to the cell lysate in equal volume. Fluorescence was then recorded at 480
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 nm excitation and 520 nm emission. Fluorescence readings were converted into cell numbers
4
5 through a standard curve and then normalized to surface area.
6

7 8 *2.3.3 Cell Morphology*

9
10 Cell morphology was investigated using scanning electron and confocal microscopy. For
11
12 SEM, fHObs were seeded on each substrate at a density of 10,000 cells/cm² and they were
13
14 cultured up to 7 days. After 1, 3 and 7 days, cell-seeded samples were carefully washed in
15
16 sterile PBS and fixed in 2.5 % glutaraldehyde (Sigma, UK) solution in PBS for 30 minutes at
17
18 4 °C. Samples were washed in PBS and dehydrated in graded ethanol series (50 %, 70 %, 90
19
20 %, 100 %). They were then rinsed with hexamethyldisilazane (HMDS; Alfa Aesar, US) and
21
22 left to air-dry overnight in a fume hood before mounting on stubs and gold sputtering for
23
24 SEM analysis. Images were acquired at 1000x magnification using an Evo MA 15 scanning
25
26 electron microscope with an accelerating voltage of 15 kV.
27

28
29 For confocal microscopy, 5,000 cells/cm² were seeded on each surface in triplicate to
30
31 characterize cell morphology via image analysis using a cell mask dye. At each time point (1,
32
33 3, 7 days), cell-seeded samples were carefully washed with sterile PBS before fixation in 4 %
34
35 paraformaldehyde (PFA) solution (Affymetrix, US) for 15 minutes at room temperature.
36
37 Samples were then washed again in PBS and permeabilized in 0.1 % Triton-X solution in
38
39 PBS for 15 minutes at room temperature. Samples were finally washed in PBS, incubated
40
41 with a cytoplasmic stain (HCS CellMask green, Life Technology, UK; 2 µg/ml) for 30
42
43 minutes at room temperature in the dark, and washed again before mounting on glass slides
44
45 for imaging. Images were captured with a 20x objective using an inverted fluorescence
46
47 microscope (CKX41 Olympus). Around 100-150 cells were analyzed per time point and the
48
49 experiment was repeated three times ($n = 3$). Images were processed using ImageJ and the
50
51 following parameters were evaluated: cell area, aspect ratio and orientation.
52
53
54

55 56 *2.3.4 Focal Adhesions and Cytoskeletal Organization*

57
58
59
60

1
2
3 Cell-seeded samples (10,000 cell/cm²) were fixed after 1 and 3 days of culture in 4 % PFA
4
5 solution for 15 minutes at room temperature after being carefully washed in sterile PBS.
6
7 Samples were washed again in PBS and immersed in a permeabilizing buffer containing 0.1
8
9 % Triton-X and 0.1 % Tween in PBS for 30 minutes at room temperature. They were then
10
11 carefully washed in PBST solution (0.05 % Tween in PBS) and non-specific antigens were
12
13 blocked with 5 % goat serum in PBST for 30 minutes at room temperature. For the detection
14
15 of focal adhesions, the Anti-Vinculin antibody (hVIN-1, Sigma, UK; 1:400) was applied for 1
16
17 hour at room temperature, after which samples were rinsed with PBST. The samples were
18
19 then dark-incubated with the secondary antibody (Alexa Fluor 594 goat anti-mouse IgG, Life
20
21 Technologies, UK; 1:500) for 1 hour at room temperature and rinsed again with PBST. Cells
22
23 were finally dark-incubated with phalloidin (Alexa Fluor 488, Life Technologies, UK; 1:40)
24
25 for 30 minutes at room temperature and rinsed with PBST. Prior to imaging, samples were
26
27 mounted on glass coverslips with DAPI mounting medium (Life Technologies, UK).
28
29 Fluorescence images were acquired using a Confocal Laser Scanning Microscopy (CLSM)
30
31 system (Leica DMIRE2, UK) with a 63x objective immersed in water.
32
33
34
35

36 *2.3.5 Cell Mineralization*

37
38 Cell mineralization was investigated after 14, 21 and 28 days in culture using Alizarin Red
39
40 staining. Briefly, at each time point, cell-seeded samples were washed with sterile PBS and
41
42 fixed in 70 % ethanol solution for 1 hour at 4 °C. Samples were rinsed three times with milliQ
43
44 water and stained in 40 mM Alizarin Red solution (pH = 4.1) for 10 minutes at room
45
46 temperature. Samples were carefully washed with distilled water until water turned clear and
47
48 images were captured using a light optical microscope (Olympus BX51m).
49
50 For optical density measurements, a 10 % acetic acid solution was added to each well and
51
52 samples were incubated for 30 minutes at room temperature, continuously agitating on an
53
54 orbital shaker to help cell monolayer detachment. The cells and the acetic acid solution were
55
56
57
58
59
60

1
2
3 transferred into microcentrifuge tubes and vortexed. The tubes were then heated to 85 °C for
4
5 10 minutes, cooled down to room temperature and centrifuged at 20,000 g for 15 minutes.
6
7 The pH of the solution was neutralized with 10% ammonium hydroxide. The solution was
8
9 then transferred in triplicate to a new transparent 96-well plate and the absorbance was
10
11 recorded at 405 nm. Results were converted into moles of Alizarin Red through a standard
12
13 curve and then normalized with surface area.
14
15

16 2.4 Collagen Deposition

17
18 After 28 days in culture, cell-seeded samples were carefully washed in sterile PBS and fixed
19
20 in 4 % paraformaldehyde solution for 30 minutes at room temperature. Samples were washed
21
22 with deionized water twice and incubated in a 0.2% phosphomolybdic acid (Sigma, UK)
23
24 solution for 2 minutes at room temperature. They were then incubated in a 0.1 % Picrosirius
25
26 Red solution (BDH Laboratory Supplies, UK) in saturated picric acid (May & Baker Ltd, UK)
27
28 for 1 hour at room temperature under a fume hood. Samples were finally rinsed in deionized
29
30 water until a clear solution was obtained, differentiated in a 0.01 % hydrochloric acid for 2
31
32 minutes and washed twice in water. Images were acquired using a CLSM system equipped
33
34 with an argon ion laser emitting at 514 nm, using a 63x objective immersed in water.
35
36
37

38 2.5 Protein Adsorption

39
40 Microgrooved samples were cleaned as described in §2.1. HiLyte Fluor™ 488 labelled
41
42 fibronectin from bovine plasma (Tebo-Bio GmbH, Offenbach, Germany) was resuspended in
43
44 milliQ water to 1 mg/ml. Samples were coated with a diluted fibronectin solution of 0.1
45
46 $\mu\text{g}/\text{cm}^2$ final concentration and allowed to air dry overnight at room temperature. Fibronectin
47
48 adsorbed on the substrates was imaged using a fluorescence microscope (502 nm excitation
49
50 and 527 nm emission wavelengths) and overlaid with bright field microscopy images of the
51
52 same surface areas. All images were acquired at 10x magnification and captured using a Zeiss
53
54
55
56
57
58
59
60

1
2
3 AxioCam ICm1 Rev.1 camera mounted on a Zeiss Axio Scope MAT (Jena, Germany).

4
5 Experiments were repeated three times.

6 7 2.6 Statistical Analysis

8
9 For all studies, averages of three independent experiments ($n = 3$), with three tested samples
10 per type, were expressed as the arithmetic mean \pm standard deviation (SD). Statistical
11 significance between groups was evaluated by two-way ANOVA with Bonferroni's post-test
12 (Prism 5, GraphPad software, Version 5.03). Levels of significance were expressed as p
13 values vs. controls (as-received surfaces) ($^a p < 0.05$, $^b p < 0.01$, $^c p < 0.001$).
14
15
16
17
18
19
20
21
22

23 **Results**

24 3.1 Surface Topography

25
26 **Figure 1 (a)** shows a schematic representation of the cross-sectional views of the
27 micropatterns. The design dimensions of the patterns are shown in Table I. The patterns are
28 designated as "40 μm ", "80 μm " and "120 μm " on the basis of their pitch dimensions. **Figures**
29 **1 (b)-(d)** show respectively 3D DIC maps, cross-sectional and top views of the as-received
30 and microgrooved surfaces. **From Figure 1 and Table 1, it can be seen that the ridge and the**
31 **groove dimensions, and also the groove depth, increased with increasing pitch size (the 40 μm**
32 **patterns had adjacent grooves – no ridges). The average surface roughness values associated**
33 **with the grooves increased with increasing pitch size as illustrated in Table 2.**
34
35
36
37
38
39
40
41
42
43
44

45 3.2 Surface Chemistry

46
47 The composition and chemical states of the as-received and patterned surfaces are indicated in
48 Table 3, as determined by high resolution XPS region spectra. Generally, they reveal only
49 minor differences, as discernible from the relative peak intensities. Photoetching results in
50 lower C-C, C-H and Cl 2p peak intensities, presumably due to removal of carbonaceous
51 surface deposits, as well as lower Cr 2p₃ peaks for both metallic and oxide states. A slight
52
53
54
55
56
57
58
59
60

1
2
3 increase of the C-C, C-H and Cl 2p peaks with pattern pitch size was observed which might
4
5 be attributed to the presence of etch residues from the photoetching process, thus reflecting
6
7 differences in etching time.
8

9 10 3.3 Cell Metabolic Activity and Proliferation

11 Cell metabolic activity and proliferation were assessed using the AlamarBlue (Figure 2 (a)),
12
13 and the CyQuant (Figure 2 (b)) assays respectively. Figures 2 (a) and 2 (b) show that
14
15 statistically significant results were only observed at day 14. In particular, cells seeded on
16
17 patterned surfaces exhibit statistically higher metabolic activity ($^a p < 0.05$) and cell numbers
18
19 ($^a p < 0.05$, $^b p < 0.01$) than those on the as-received surface. No significant differences were
20
21 observed between the different patterns.
22
23

24 25 3.4 Cell Morphology and Alignment

26
27 SEM images showing top views of the cell-seeded surfaces after 1, 3 and 7 days in growth
28
29 medium are illustrated in Figure 3. It can be seen that cell shape is strongly guided by the
30
31 grooves. On all patterns, cells aligned along the long axis of the grooves whereas on the as-
32
33 received surfaces they were randomly oriented. The vast majority of cells spread from one
34
35 groove/ridge boundary to the other by bridging the groove; a very small number of cells
36
37 preferred to reside inside the grooves.
38
39

40 Differences in cell morphology were investigated using image analysis of fluorescent images
41
42 of cells cultured on all surfaces after 1, 3 and 7 days in culture. As illustrated in Figures 4 (a)-
43
44 (c), cell morphology was characterized in terms of cell area, aspect ratio and orientation. The
45
46 latter is expressed as the angular distribution of cell orientation along the long axis of the
47
48 patterns.
49
50

51 Results show that cells cultured on as-received surfaces exhibit higher projected areas
52
53 compared to patterned surfaces (Figure 4 (a)). After 1 and 3 days of culture, there are some
54
55 differences in cell-projected areas between the different patterns, with the 120 μm patterns
56
57
58
59
60

1
2
3 showing higher cell areas, which may be due to the fact that cells have to bridge a wider
4
5 groove spacing. Differences between microgrooved and as-received surfaces became
6
7 statistically significant after 7 days of culture ($^c p < 0.001$), while no significant differences
8
9 were observed between the different patterns.
10

11
12 The cell aspect ratio is a measure of cell polarization and is defined as the ratio between the
13
14 maximum and the minimum length of the cell. **Figure 4 (b)** shows that cells were polarized on
15
16 the patterned surfaces due to the contact guidance induced by the grooves. At each time point,
17
18 measured values were statistically different compared to cells cultured on as-received
19
20 surfaces, onto which cells spread uniformly with no preferential alignment ($^a p < 0.05$, $^b p <$
21
22 0.01 and $^c p < 0.001$). No significant changes in the cell aspect ratio were observed with
23
24 culture time. The aspect ratio values were about 5 and 2 for the patterned and as-received
25
26 surfaces respectively.
27

28
29 **Figure 4 (c)** shows the angular distributions of the cell orientation on the different substrates
30
31 after 1 day of culture. The data are plotted using a circular graph, superimposed on the
32
33 patterns, showing the angle of the long axis of each cell in relation to the groove direction. On
34
35 the as-received surfaces, the angle is being measured relative to an arbitrary axis. As
36
37 expected, cells show a random distribution on the as-received surfaces whereas, on the
38
39 patterned surfaces, a clear contact guidance effect can be observed. The 80 μm patterns had
40
41 the broader distribution but also the highest fraction of cells along the long axis of the groove
42
43 whereas the 120 μm patterns exhibit the sharpest distribution. The orientation angles were
44
45 mostly of the order of 10-15°.
46
47
48

49 3.4 Cytoskeletal Organization and Formation of Focal Adhesions

50
51 Cells were stained against actin and vinculin in order to investigate respectively the F-actin
52
53 cytoskeleton organization and the formation of focal adhesions on the different surfaces. At
54
55 day 1 (**Figures 5 (a)-(d)**), stress fibers aggregated in a filamentous configuration on all
56
57
58
59
60

1
2
3 surfaces. F-actin filaments were aligned along the 40 μm patterns, partially oriented along the
4
5 80 μm and 120 μm patterns, and randomly distributed on the as-received substrates. At day 3
6
7 (Figure 5 (e)-(h)), F-actin filaments were oriented parallel to the long axis of the grooves on
8
9 all patterned surfaces and remained randomly oriented on the as-received surface. On the 80
10
11 and 120 μm patterns, focal adhesions were observed along the groove/ridge boundaries and
12
13 the ridges (Figures 5 (g) and (h)). On the 40 μm patterns, a smaller number of focal adhesions
14
15 were observed (Figure 5 (f)). This is probably because the available contact area adjacent to
16
17 the grooves is much smaller (no intervening ridges). On all patterns, very few / no focal
18
19 adhesions were observed along the grooves as the cells preferred to span across the grooves.
20
21 This is probably attributed to the high rigidity of the osteoblast cytoskeleton, causing cells to
22
23 bridge across the grooves without attaching conformally to the bottom of the grooves. Since
24
25 there were very few / no focal adhesions inside the grooves it can be postulated that
26
27 differences in groove depth and roughness between the patterns, shown in Tables 1 and 2,
28
29 haven't played important roles in the initial cell response.
30
31
32

33 34 3.5 Cell Mineralisation

35
36 fHObS were fixed after 14, 21 and 28 days of culture in osteogenic medium and stained with
37
38 Alizarin Red for nodule detection. No signs of mineralization were observed after 14 days of
39
40 culture. However, cells were able to deposit calcium after 21 days of culture with
41
42 mineralization increasing over time. Figures 6 (a)-(d) show very distinct Alizarin Red-stained
43
44 nodular areas on all surfaces after 28 days. All patterns induced higher mineralization
45
46 compared to as-received surfaces as measured with acetic acid extraction (Figure 6 (e); $^b p <$
47
48 0.01 ; $^c p < 0.001$), with particular formation of calcified nodules inside the grooves.
49
50 Comparison between patterns suggests that the 120 μm patterns induce less mineralization
51
52 than the 40 and 80 μm patterns (Figure 6 (e)).
53
54

55 56 3.6 Collagen Deposition

1
2
3 Representative fluorescence confocal images illustrated in Figure 7 show higher production of
4 collagen on patterned substrates compared to the as-received surface. Higher collagen
5 deposition occurred inside the grooves, with less matrix detected on the ridges. Cell-secreted
6 collagen was preferentially aligned along the patterns suggesting that the microgrooved
7 substrates stimulate higher production of ECM, with a well-organised structure.
8
9
10
11
12

13 3.7 Adsorption of Fibronectin on the Groove Edges

14
15 The adsorption of fluorescently-labelled fibronectin on the micropatterned substrates was
16 investigated using low fibronectin concentrations to mimic the concentrations found in blood
17 serum²⁰. As illustrated in Figure 8, fibronectin adsorbs predominantly onto the ridge/groove
18 boundaries. Almost no fibronectin was detected onto the ridges or grooves. The same
19 adsorption pattern was observed in all patterns. It should be noted that in the 40 μm patterns
20 (Figure 8 (a)), the bright areas correspond to the grooves since it was not possible to focus at
21 the ridges, whereas in Figures 8 (c) and (e) the bright areas correspond to the ridges of the 80
22 μm and 120 μm patterns.
23
24
25
26
27
28
29
30
31
32

33 **4. Discussion**

34
35
36 In this study, patterned 316L stainless steel substrates with different pitch-groove designs
37 were investigated; with groove spacing comparable to the spread osteoblast size. A surface
38 specific-technique, XPS, showed that the micro-grooved surfaces exhibit similar surface
39 chemistry to the as-received surfaces.
40
41
42
43
44
45

46
47 Osteoblast response and collagen deposition were monitored in serum conditions for up to 4
48 weeks. Osteoblasts were found to preferentially attach at the groove/ridge boundaries. They
49 were unable to conform to the groove curvature, resulting in bridging the distance between
50 two adjacent pitches. Grooves induced a clear contact guidance effect on the cells as they
51 aligned along the groove direction. Conversely, cells on as-received surfaces showed no
52
53
54
55
56
57
58
59
60

1
2
3 directional preference. In agreement with previous work²¹, as cells polarized, their total
4
5 projected area was reduced compared to those attached on the as-received surface. As
6
7 proposed in a previous study²², micro-discontinuities on substrates could result in the creation
8
9 of adhesive and non-adhesive areas for cell attachment. Furthermore, focal adhesions were
10
11 found to mostly confine to the groove/ridge boundaries. Statistically significant metabolic
12
13 activities were only observed at day 14 but these differences are probably attributed to
14
15 differences in cell numbers. After 21 days in culture, calcium minerals were deposited within
16
17 the ECM, indicative of osteogenesis. At day 28, all patterns induced statistically higher
18
19 mineralization compared to as-received surfaces. Collagen deposition was investigated after
20
21 28 days in culture, suggesting higher ECM production on patterned substrates as compared to
22
23 the as-received surfaces, with increased protein secretion within the microgrooves. No
24
25 significant differences were observed between the different patterns in terms of cell
26
27 proliferation, metabolism, mineralization, and collagen production.

28
29 To explain the differences **observed** in cell response between patterned and non-patterned
30
31 surfaces, an investigation was carried out to determine whether adhesion proteins contained in
32
33 the culture media, like fibronectin, are also involved.

34
35 The adhesion multifunctional glycoproteins of the ECM, such as fibronectin and vitronectin,
36
37 and their receptors have been found to play an important role in osteoblast differentiation and
38
39 mineralization^{4,12-14,23}. Fibronectin is one the most important adhesive proteins of the ECM,
40
41 consisting of two monomeric units joined together by disulphide bonds close to the carboxyl
42
43 terminus of the protein to form the characteristic dimeric structure. It is well known that
44
45 sulphur forms strong complexes with metal elements and its stability on stainless steel after
46
47 adsorption has been demonstrated via XPS analysis²⁴.

48
49 To investigate protein-surface interactions, fibronectin adsorption experiments were carried
50
51 out using concentrations similar to those found in blood serum²⁰. Fibronectin molecules were
52
53
54
55
56
57
58
59
60

1
2
3 found to aggregate at the groove/ridge boundaries where a higher concentration of vinculin, a
4
5 protein of cellular focal adhesion sites, was also observed. Almost no fibronectin was detected
6
7 onto the ridges or grooves. The same adsorption pattern was observed in all patterns.

8
9
10 The process of protein adsorption on implant surfaces is still not well understood and several
11
12 **competing** events are considered to be involved. It has been proposed ²⁵ that the preferred
13
14 adsorption of proteins on grooved substrates could be associated with wetting anisotropy, by
15
16 which a droplet would stick to the edges of grooves and stretch along the groove long axis.
17
18 Similar findings were obtained via numerical simulations on grooved nanostructures¹⁸. **These**
19
20 **simulations** ¹⁸ **showed** that, under physiological conditions, convex edges show better
21
22 accessibility for proteins due to a greater surrounding liquid volume and increased
23
24 electrostatic forces. Compared to smooth surfaces, topographical features can offer more
25
26 active sites for protein adsorption ^{16,26,27}; this phenomenon was particularly observed for
27
28 fibronectin ²⁸.

29
30
31 In summary, our study demonstrates that the fibronectin-substrate interaction that occurs
32
33 almost instantly after seeding, may affect the long-term osteoblast response, in particular
34
35 mineralization (as previously suggested ²³) and collagen deposition.
36
37
38
39

40 **5. Conclusions**

41
42 In this study, the osteoblast behaviour on micropatterned substrates was investigated. Focal
43
44 adhesions were found to confine to the groove/ridge boundaries. Grooved substrates induced
45
46 higher osteoblast proliferation and metabolic activity after 14 days in culture compared to as-
47
48 received surfaces, resulting in higher mineralization and production of cell-secreted collagen
49
50 after 28 days. Varying the groove spacing and depth, over the range tested, had no noticeable
51
52 effect on cell response. To establish whether the substrate-protein interactions could have
53
54 played a role in the observed cell response, fluorescently-labelled fibronectin, a mediator for
55
56
57
58
59
60

1
2
3 cell adhesion, was adsorbed onto microgrooved metallic substrates at concentrations similar
4
5 to those found in blood serum. Fibronectin was found to selectively adsorb onto the
6
7 groove/ridge boundaries, the osteoblast focal adhesion sites. This preferential attachment is
8
9 most likely due to better accessibility of available sites for protein adhesion. The results
10
11 confirm the significance of the spatial distribution of surface-bound proteins in cell
12
13 attachment, shape and maturation, and, potentially, in guiding tissue integration on an implant
14
15 surface.
16
17
18
19

20 21 **Acknowledgments**

22
23 This research was supported by the European Research Council (Grant No. 240446). XPS,
24
25 AFM and fibronectin experiments were carried out at the IOM Leipzig and the University of
26
27 Leipzig, and were funded in parts by the German Federal Ministry of Education and Research
28
29 (BMBF 1315883), the European Union and the Free State of Saxony (SAB 100121467).
30

31
32 The authors would like to acknowledge Dr. Jeremy Skepper from the Department of
33
34 Physiology, Development and Neuroscience, of Cambridge University, for his assistance with
35
36 the Picrosirius Red Staining. The authors are particularly grateful to Dr. J. Gerlach and A.
37
38 Landgraf of IOM Leipzig for carrying out the XPS and AFM measurements respectively, and
39
40 for useful discussions.
41
42
43
44

45 46 **References**

- 47 1. Anselme K. Osteoblast adhesion on biomaterials. *Biomaterials* 2000;21(7):667-81.
- 48 2. Curtis A, Wilkinson C. Topographical control of cells. *Biomaterials*
49
50 1997;18(24):1573-1583.
51
- 52 3. Nikkhah M, Edalat F, Manoucheri S, Khademhosseini A. Engineering microscale
53
54 topographies to control the cell-substrate interface. *Biomaterials* 2012;33(21):5230-46.
55
56
57
58
59
60

- 1
2
3 4. Lee MH, Oh N, Lee SW, Leesungbok R, Kim SE, Yun YP, Kang JH. Factors
4
5 influencing osteoblast maturation on microgrooved titanium substrata. *Biomaterials*
6
7 2010;31(14):3804-3815.
8
- 9
10 5. Brunette DM, Kenner GS, Gould TRL. Grooved titanium surfaces orient growth and
11
12 migration of cells from human gingival explants. *Journal of Dental Research*
13
14 1983;62(10):1045-1048.
15
- 16
17 6. Denbraber ET, Deruijter JE, Smits HTJ, Ginsel LA, Vonrecum AF, Jansen JA. Effect
18
19 of parallel surface microgrooves and surface-energy on cell-growth. *Journal of*
20
21 *Biomedical Materials Research* 1995;29(4):511-518.
22
- 23
24 7. Chou LS, Firth JD, Uitto VJ, Brunette DM. Substratum surface-topography alters cell-
25
26 shape and regulates fibronectin messenger-RNA level, messenger-RNA stability,
27
28 secretion and assembly in human fibroblasts. *Journal of Cell Science* 1995;108:1563-
29
30 1573.
31
- 32
33 8. Biggs MJP, Richards RG, McFarlane S, Wilkinson CDW, Oreffo ROC, Dalby MJ.
34
35 Adhesion formation of primary human osteoblasts and the functional response of
36
37 mesenchymal stem cells to 330 nm deep microgrooves. *Journal of the Royal Society*
38
39 *Interface* 2008;5(27):1231-1242.
40
- 41
42 9. Bettinger CJ, Langer R, Borenstein JT. Engineering Substrate Topography at the
43
44 Micro- and Nanoscale to Control Cell Function. *Angewandte Chemie-International*
45
46 *Edition* 2009;48(30):5406-5415.
47
- 48
49 10. Mata A, Boehm C, Fleischman AJ, Muschler G, Roy S. Analysis of connective tissue
50
51 progenitor cell behavior on polydimethylsiloxane smooth and channel micro-textures.
52
53 *Biomedical Microdevices* 2002;4(4):267-275.
54
55
56
57
58
59
60

- 1
2
3 11. Charest JL, Garcia AJ, King WP. Myoblast alignment and differentiation on cell
4 culture substrates with microscale topography and model chemistries. *Biomaterials*
5 2007;28(13):2202-2210.
6
7
- 8
9 12. Moursi AM, Damsky CH, Lull J, Zimmerman D, Doty SB, Aota S, Globus RK.
10 Fibronectin regulates calvarial osteoblast differentiation. *J Cell Sci* 1996;109 (Pt
11 6):1369-80.
12
13
- 14 13. Puleo DA, Bizios R. Mechanisms of fibronectin-mediated attachment of osteoblasts to
15 substrates in vitro. *Bone Miner* 1992;18(3):215-26.
16
17
- 18 14. Schneider G, Burrige K. Formation of focal adhesions by osteoblasts adhering to
19 different substrata. *Exp Cell Res* 1994;214:264-269.
20
21
- 22 15. Pegueroles M, Aparicio C, Bosio M, Engel E, Gil FJ, Planell JA, Altankov G. Spatial
23 organization of osteoblast fibronectin matrix on titanium surfaces: Effects of
24 roughness, chemical heterogeneity and surface energy. *Acta Biomaterialia*
25 2010;6(1):291-301.
26
27
- 28 16. Richert L, Variola F, Rosei F, Wuest JD, Nanci A. Adsorption of proteins on
29 nanoporous Ti surfaces. *Surface Science* 2010;604(17-18):1445-1451.
30
31
- 32 17. Scopelliti PE, Borgonovo A, Indrieri M, Giorgetti L, Bongiorno G, Carbone R,
33 Podesta A, Milani P. The Effect of Surface Nanometre-Scale Morphology on Protein
34 Adsorption. *Plos One* 2010;5(7).
35
36
- 37 18. Elter P, Lange R, Beck U. Electrostatic and Dispersion Interactions during Protein
38 Adsorption on Topographic Nanostructures. *Langmuir* 2011;27(14):8767-8775.
39
40
- 41 19. Schneider CA, Rasband WS, Eliceiri KW. NIH Image to ImageJ: 25 years of image
42 analysis. *Nature Methods* 2012;9(7):671-675.
43
44
- 45 20. Hayman EG, Ruoslahti E. Distribution of fetal bovine serum fibronectin and
46 endogenous rat cell fibronectin in extracellular matrix. *J Cell Biol* 1979;83(1):255-9.
47
48
49
50
51
52
53
54
55
56
57
58
59
60

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
21. Oakley C, Brunette DM. The Sequence of Alignment of Microtubules, Focal Contacts and Actin-Filaments in Fibroblasts Spreading on Smooth and Grooved Titanium Substrata. *Journal of Cell Science* 1993;106:343-354.
 22. Karuri NW, Nealey PF, Murphy CJ, Albrecht RM. Structural Organization of the Cytoskeleton in SV40 Human Corneal Epithelial Cells Cultured on Nano- and Microscale Grooves. *Scanning* 2008;30(5):405-413.
 23. Brunner M, Millon-Fremillon A, Chevalier G, Nakchbandi I, Mosher D, Block M. Osteoblast mineralization requires beta1 integrin/ICAP-1-dependent fibronectin. *J Cell Biol* 2011;194:307-322.
 24. Galtayries A, Warocquier-Clerout E, Nagel M, Marcus P. Fibronectin adsorption on Fe-Cr alloy studied by XPS. *Surf Interface Anal* 2006;38:186-190.
 25. Fadeeva E, Schlie S, Koch J, Chichkov BN. Selective Cell Control by Surface Structuring for Orthopedic Applications. *Journal of Adhesion Science and Technology* 2010;24(13-14):2257-2270.
 26. Dolatshahi-Pirouz A, Jensen T, Kraft DC, Foss M, Kingshott P, Hansen JL, Larsen AN, Chevallier J, Besenbacher F. Fibronectin Adsorption, Cell Adhesion, and Proliferation on Nanostructured Tantalum Surfaces. *Acs Nano* 2010;4(5):2874-2882.
 27. Peng WT, Qiao ZM, Zhang Q, Cao XD, Chen XF, Dong H, Liao JW, Ning CY. Micropatterned TiO₂ nanotubes: fabrication, characterization and in vitro protein/cell responses. *Journal of Materials Chemistry B* 2013;1(28):3506-3512.
 28. Hao L, Lawrence J, Phua YF, Chian KS, Lim GC, Zheng HY. Enhanced human osteoblast cell adhesion and proliferation on 316 LS stainless steel by means of CO₂ laser surface treatment. *Journal of Biomedical Materials Research Part B-Applied Biomaterials* 2005;73B(1):148-156.

Figure Captions

Fig. 1. Surface topography of micro-patterned surfaces: 40 μm (left), 80 μm (centre) and 120 μm (right). (a) Schematic representation of cross-sectional views (R = Ridge, G = Groove, P = Pitch and D = Groove Depth); (b) high-contrast 3-D DIC images; (c) cross-sectional (optical microscopy) and (d) top (SEM) views.

Fig. 2. fHOb response onto as-received (AR) and patterned surfaces. (a) Cell metabolic activity expressed as % of AlamarBlue reduction; (b) cell proliferation as cell number. All results are normalized per cm^2 ($^a p < 0.05$; $^b p < 0.01$).

Fig. 3. SEM images showing fHOb attached on the different surfaces at day 1 (a-d), 3 (e-h) and 7 (i-l). From left to right: as-received (AR), 40 μm , 80 μm and 120 μm surfaces.

Fig. 4. Morphological analysis of fHOb cultured on as-received (AR) and patterned surfaces. The following parameters were evaluated using image analysis of fluorescent images: (a) cell area; (b) aspect ratio; (c) cell orientation after 1 day of culture expressed as the angular distribution of cell orientation along the long axis of the patterns. Concentric circles indicate the percentage of cells. Statistical differences were defined as $^a p < 0.05$, $^b p < 0.01$ and $^c p < 0.001$.

Fig. 5. Fluorescence confocal images of fHOb cultured for 1 (a-d) and 3 (e-h) days on the different surfaces. From left to right: as-received (AR), 40 μm , 80 μm and 120 μm surfaces. Phalloidin488, AlexaFluor594 and DAPI respectively stained actin fibers (green), vinculin focal adhesions (red) and cell nuclei (blue). The dotted white lines drawn on the fluorescence images (f-h) show the location of the grooves (G) and ridges (R) on the different patterned surfaces.

Fig. 6. Optical microscopy images showing calcified nodules stained with Alizarin Red, on (a) as-received (AR); (b) 40 μm ; (c) 80 μm ; (d) 120 μm surfaces. fHOb were cultured in osteogenic medium for 28 days prior fixation. (e) Quantification of Alizarin Red, obtained

1
2
3 with acetic acid extraction, as a function of culture time. Results are normalized per cm^2 (^b $p <$
4
5 0.01; ^c $p < 0.001$).

6
7 **Fig. 7.** Confocal microscopy images showing collagen deposition after 28 days of culture in
8 osteogenic medium on (a) as-received (AR); (b) 40 μm ; (c) 80 μm ; (d) 120 μm surfaces.
9
10
11 Collagen was stained with Picrosirius Red. Images were acquired with a laser-scanning
12
13 confocal microscope equipped with an argon ion laser emitting at 514 nm.
14
15

16 **Fig. 8.** Confocal microscopy images showing fibronectin adsorption onto the micropatterned
17 surfaces: (a, b) 40 μm ; (c, d) 80 μm ; (e, f) 120 μm . The left-hand column shows the patterned
18
19 surfaces and the adsorbed fibronectin, while the right-hand column shows the adsorbed
20
21 fibronectin only. In the 40 μm patterns, the bright areas correspond to the grooves, whereas in
22
23 the 80 μm and 120 μm patterns, the bright areas correspond to the ridges.
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Table 1. Pattern design dimensions. The 40 μm patterns had adjacent grooves i.e. no ridges between the grooves.

Pattern	40 μm	80 μm	120 μm
Pitch, P (μm)	39.56 ± 0.28	79.99 ± 0.24	119.00 ± 0.80
Ridge, R (μm)	---	29.84 ± 0.39	39.67 ± 0.15
Groove, G (μm)	39.56 ± 0.28	50.15 ± 0.38	79.33 ± 1.40
Groove Depth, D (μm)	5.31 ± 0.21	15.37 ± 0.04	20.66 ± 1.10

For Peer Review

Table 2. Groove average roughness (R_a) values (scan area $1 \times 1 \mu\text{m}^2$), as measured by AFM.

Average roughness (R_a) (nm)		
40 μm	80 μm	120 μm
5.11 ± 1.92	5.90 ± 3.15	7.44 ± 4.31

For Peer Review

Table 3. Chemical state composition of as-received (AR) and micropatterned 316L stainless steel surfaces.

XPS peak	Chemical state	AR		40 μm		80 μm		120 μm	
		Ch. State (At%)	Elem. (At%)	Ch. State (At%)	Elem. (At%)	Ch. State (At%)	Elem. (At%)	Ch. State (At%)	Elem. (At%)
Zn 2p	element	0.72	0.72	0.56	0.56	0.60	0.60	0.23	0.23
Cu 2p	element	1.86	1.86	1.36	1.36	1.70	1.70	1.45	1.45
Fe 2p3	element	0.04	5.94	0.74	6.61	0.16	4.99	0.12	6.28
	Fe ₂ O ₃ (oxide)	5.90		5.87		4.83		6.16	
Mn 2p1	MnO _x (oxide)	0.91	0.91	2.05	2.05	1.45	1.45	1.13	1.13
Cr 2p3	element	0.04	1.11	0.54	3.81	0	2.90	0.97	3.14
	Cr ₂ O ₃ (oxide)	1.07		3.27		2.90		2.17	
O 1s	metal oxide	15.09	39.93	16.06	42.31	13.29	40.30	15.79	42.95
	other	24.84		26.25		27.01		27.16	
N 1s	nitride	1.01	1.01	1.11	1.11	1.44	1.44	1.15	1.15
C 1s	C-C, C-H	32.47	46.30	26.72	39.49	27.61	42.9	28.18	38.63
	C-OH	6.23		5.09		10.40		5.18	
	carbonate	7.60		6.68		4.89		5.27	
Cl 2p	element	0.27	0.27	0.57	0.57	0.62	0.62	0.98	0.98
Si 2s	element	1.31	1.31	2.24	2.24	2.61	2.61	3.30	3.30
P 2p	element	0.65	0.65	0.67	0.67	0.49	0.49	0.62	0.62
Ni 2p3	element	--	--	0.22	0.22	--	--	0.14	0.14

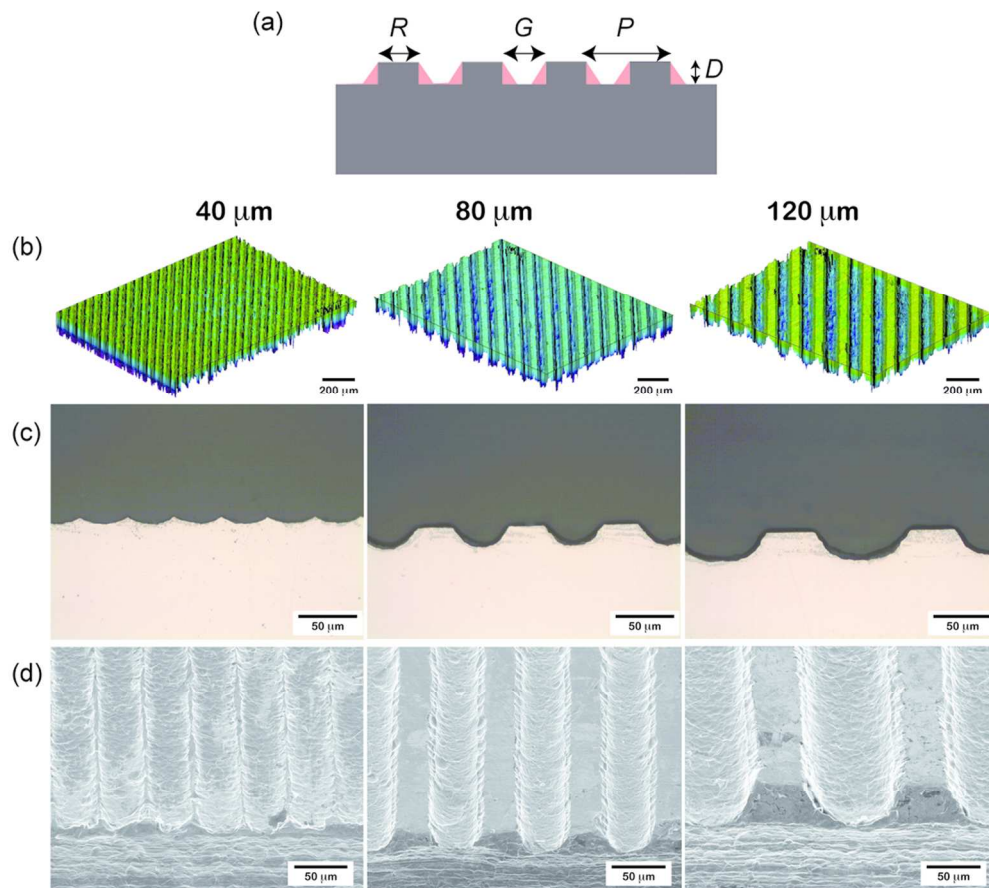


Figure 1
140x125mm (300 x 300 DPI)

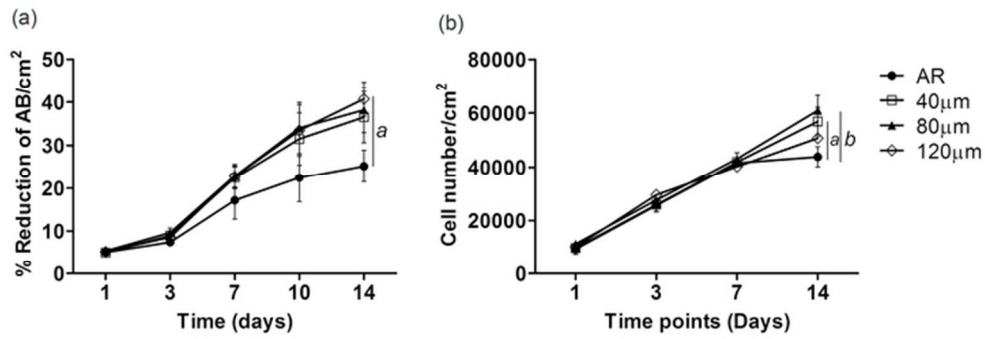


Figure 2
62x21mm (300 x 300 DPI)

Peer Review

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

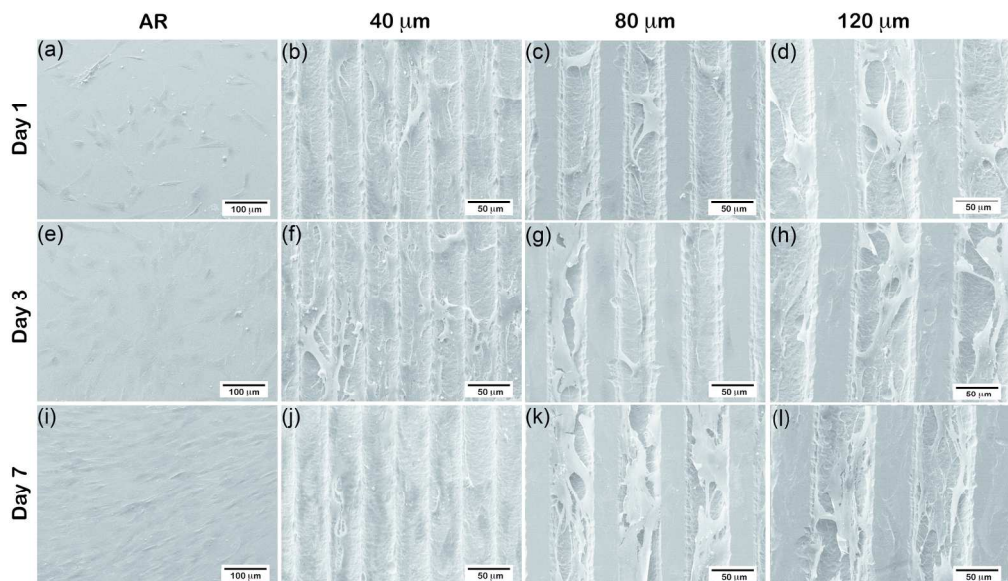


Figure 3
180x104mm (300 x 300 DPI)

er Review

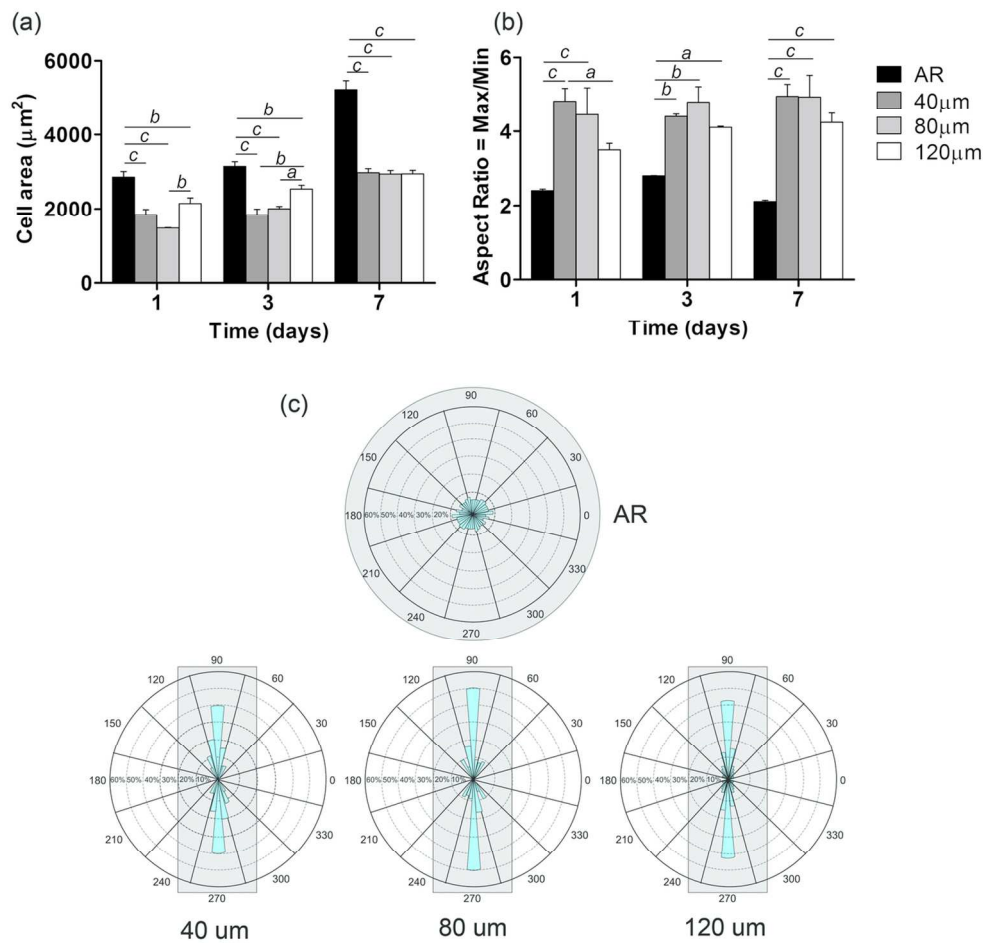


Figure 4
123x118mm (300 x 300 DPI)



1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

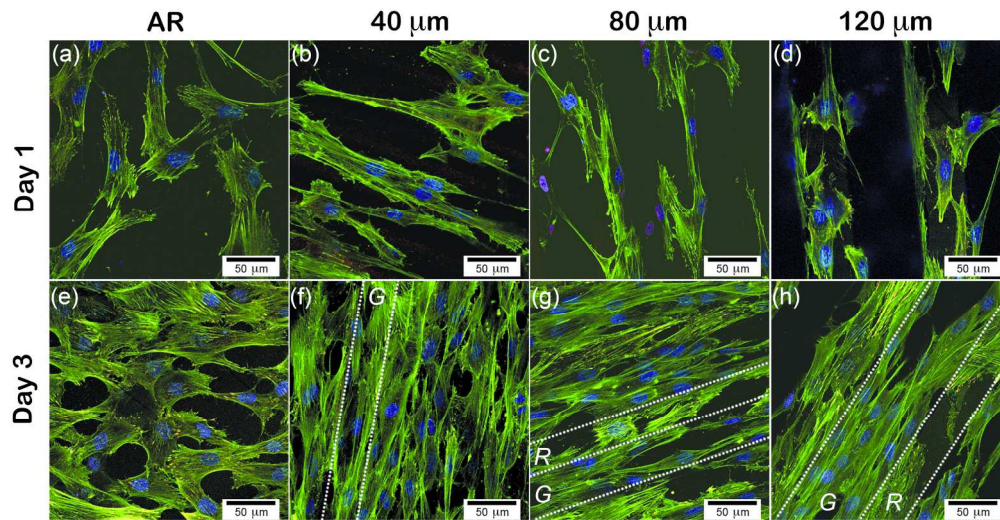


Figure 5
187x96mm (300 x 300 DPI)

Peer Review

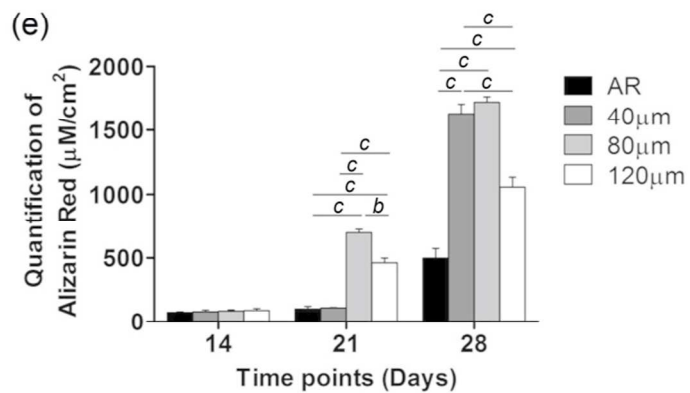
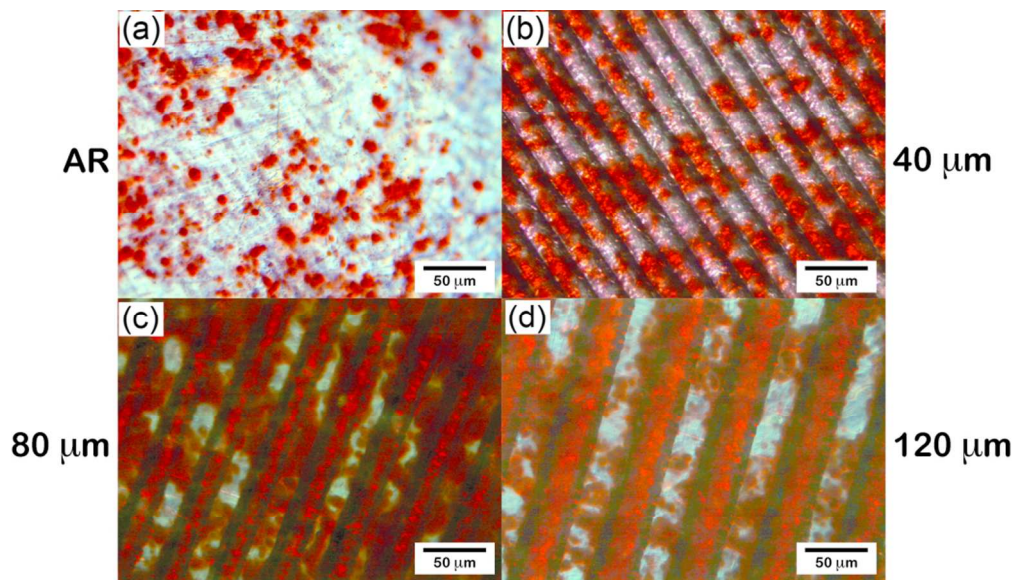


Figure 6
88x89mm (300 x 300 DPI)



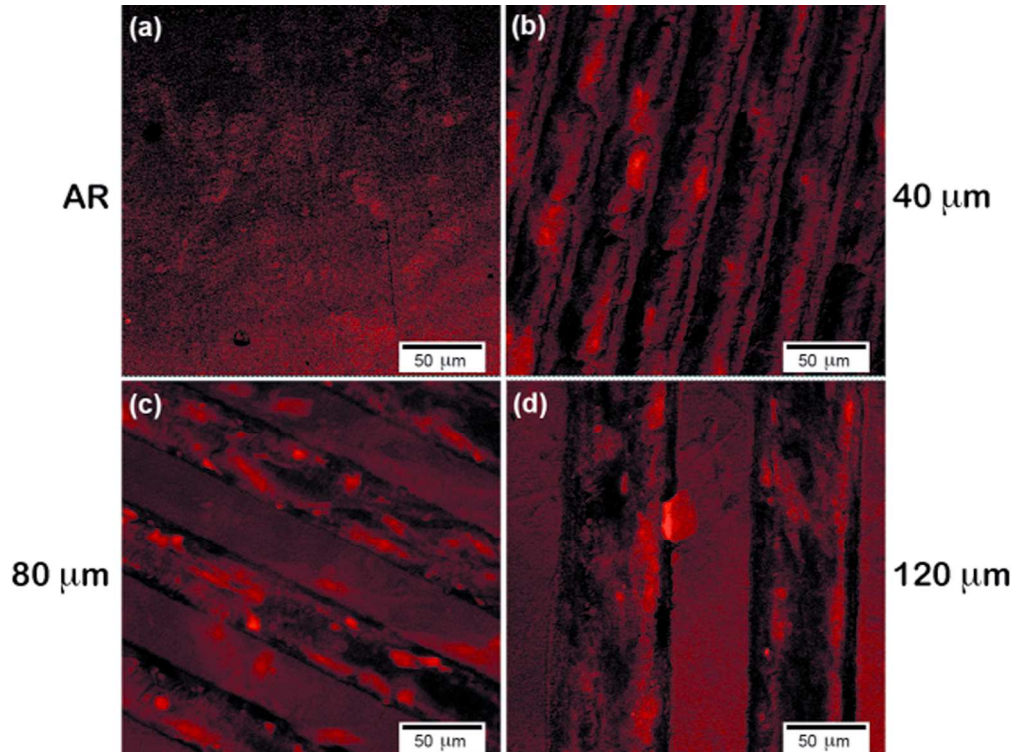


Figure 7
129x96mm (300 x 300 DPI)

Review

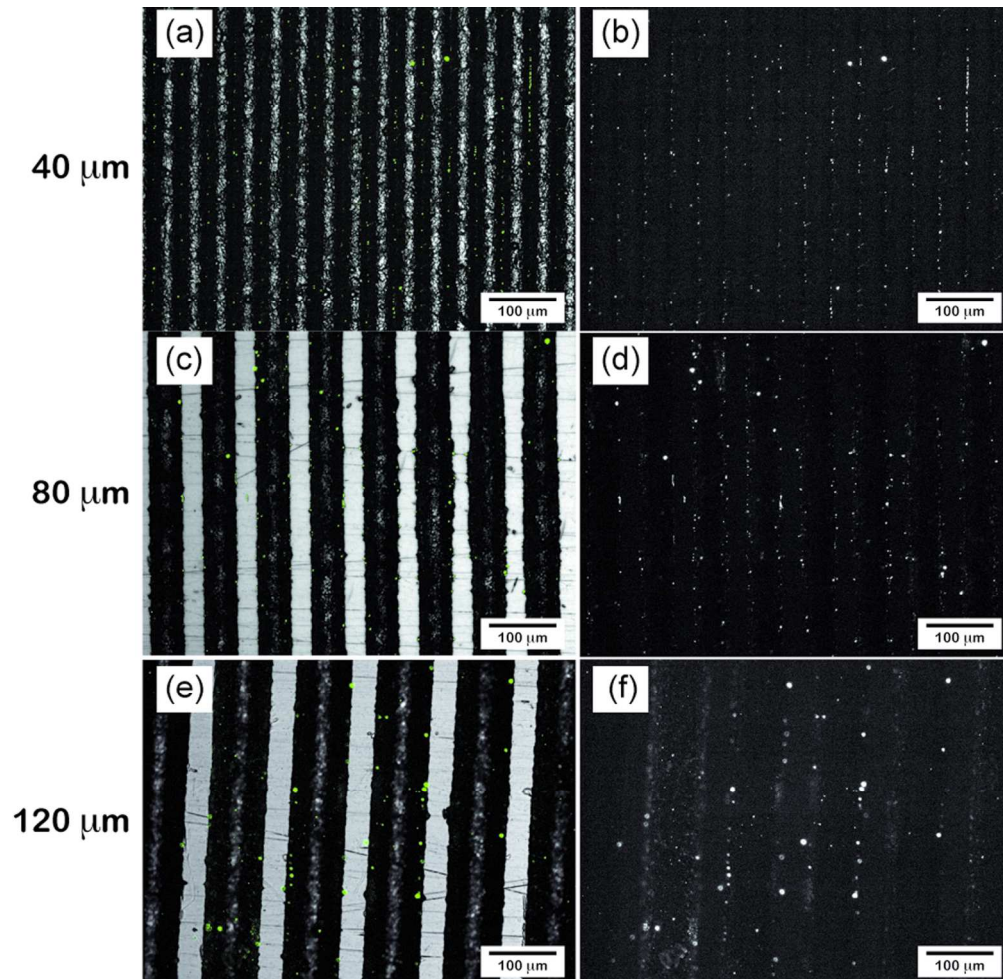


Figure 8
150x146mm (300 x 300 DPI)

