

Riobóo, Rafael J. Jiménez and Cuscó, Ramon and Prieto, Carlos and Kopittke, Caroline and Novikov, Sergei V. and Artús, Luis (2016) Surface acoustic wave velocity and elastic constants of cubic GaN. *Applied Physics Express*, 9 (6). 061001. ISSN 1882-0786

Access from the University of Nottingham repository:

http://eprints.nottingham.ac.uk/34798/1/cGaN_Brillouin_sn.pdf

Copyright and reuse:

The Nottingham ePrints service makes this work by researchers of the University of Nottingham available open access under the following conditions.

This article is made available under the University of Nottingham End User licence and may be reused according to the conditions of the licence. For more details see:
http://eprints.nottingham.ac.uk/end_user_agreement.pdf

A note on versions:

The version presented here may differ from the published version or from the version of record. If you wish to cite this item you are advised to consult the publisher's version. Please see the repository url above for details on accessing the published version and note that access may require a subscription.

For more information, please contact eprints@nottingham.ac.uk

Surface acoustic wave velocity and elastic constants of cubic GaN

Rafael J. Jiménez Riobóo,¹ Ramon Cuscó,² Carlos Prieto,¹ Sergei V. Novikov,³ and Lluís Artús⁴

¹*Instituto de Ciencia de Materiales de Madrid (CSIC),
Sor Juana Inés de la Cruz 3, E-28049 Madrid, Spain*

²*Institut Jaume Almera (ICTJA), Consell Superior d'Investigacions Científiques (CSIC),
Lluís Solé i Sabarís s.n., E-08028 Barcelona, Spain*

³*School of Physics and Astronomy,
University of Nottingham, Nottingham NG7 2RD, UK*

⁴*Institut Jaume Almera (ICTJA), Consell Superior d'Investigacions Científiques (CSIC),
Lluís Solé i Sabarís s.n., E-08028 Barcelona, Spain*

Abstract

We present high resolution Brillouin scattering measurements on cubic GaN layers grown on GaAs substrate. By using a suitable scattering geometry, scattering by surface acoustic waves was recorded for different azimuthal angles and the surface acoustic wave velocities were determined. The comparison of the experimental results with numerical simulations of the azimuthal dependence of the surface wave velocity shows good agreement and allowed us to determine a consistent set of elastic constants for *c*-GaN.

In recent years, the development of solid-state light-emitter technology has attracted much research effort into the group III nitrides. The InGaN-GaN material system has produced efficient light emitting diodes in the yellow, green and blue regions and form the basis of current solid-state lighting technology for white lighting applications.¹ On the other hand, the unique properties of GaN (wide bandgap, high breakdown electric field, high electron mobility) make this material a promising candidate for the next generation of microwave power electronics² and high temperature, high frequency devices.³ The group III nitrides normally crystallize in the stable, hexagonal, wurtzite structure. For conventional growth of quantum wells along the polar c axis, strong built-in electric fields caused by gradients of spontaneous and piezoelectric polarization develop which cause the charge separation of electron-hole pairs (quantum Stark effect). This results in the redshift of the emission wavelength and in a reduced emission efficiency.^{1,4} Growth on non-polar or semi-polar faces of hexagonal GaN is being explored to overcome this problem.^{4,5} An alternative route consists in using the metastable zinc-blende polytype of GaN which is free of built-in electric fields in the typical (100) growth direction.^{6,7}

The growth of non-polar (100) oriented cubic (zincblende) GaN layers can be achieved by molecular beam epitaxy (MBE) on (100) cubic substrates under specific growth conditions.⁸ Despite the increasing technological interest in zincblende GaN, this polytype has received so far much less attention than its wurtzite counterpart and their physical properties are not well known yet. Only recently a comprehensive study of the optical properties of cubic GaN in the near-band-gap excitonic region has been published.⁹ More recently, the anharmonic phonon decay in c-GaN has been investigated by means of Raman scattering.¹⁰ Whereas Brillouin scattering measurements providing a reliable experimental determination of the elastic constants were reported in wurtzite GaN,^{11,12} the present knowledge of the elastic constants of cubic GaN comes mainly from molecular-dynamics and density-functional-theory calculations.¹³⁻¹⁸ To our knowledge, only one of the three independent elastic constants of c-GaN has been experimentally determined by means of picosecond acoustic experiments.¹⁹

In this Letter, we present a high resolution Brillouin scattering (HRBS) study of the elastic constants of cubic GaN. Our measurements were performed on a high-quality zincblende GaN layer grown on a semi-insulating (100) GaAs substrate by plasma-assisted molecular beam epitaxy (PA-MBE) in a MOD-GENII system using As₂ as a surfactant to initiate the

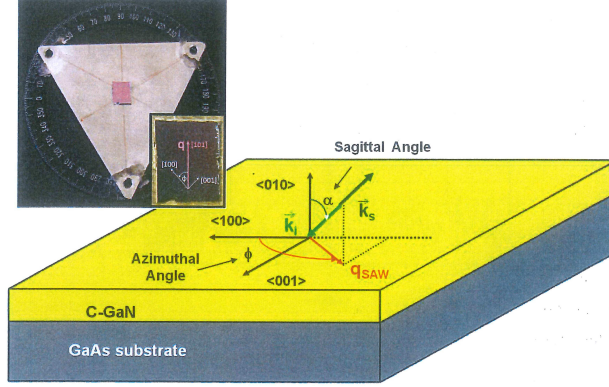


FIG. 2: Schematic representation of the surface Brillouin scattering geometry used in the measurements. The incident light of wave vector \mathbf{k}_i is at an angle α (sagittal angle) from the surface normal. The backscattered light is collected at 180° with wave vector \mathbf{k}_s . The light is polarized in the scattering plane and the scattered phonon wave vector is \mathbf{q}_{SAW} . The scattering plane is rotated about the $\langle 010 \rangle$ axis by an angle ϕ (azimuthal angle). Inset, a view of the cubic GaN sample mounted on the sample holder.

observed at 543 cm^{-1} corresponds to the TO mode of the cubic GaN. Although this mode is forbidden in backscattering from $\{100\}$ faces, it is detected in the Raman spectra due to the forward scattering contribution of the light reflected at the interface between the transparent layer and the substrate.^{10,23,24} No signal from the E_2^{high} mode of the wurtzite GaN can be observed in the spectra. Given the sizable intensity of the E_2^{high} peak characteristic of the hexagonal phase, its absence in the Raman spectrum indicates the high phase purity of the cubic GaN layer used in this study. For comparison, in the inset of Fig. 1 we display a Raman spectrum of a cubic GaN layer which contains also some hexagonal phase. In this sample, the emergence of a distinct, weak peak at 568 cm^{-1} corresponding to the E_2^{high} mode of the wurtzite GaN can be clearly observed. These spectra demonstrate the high sensitivity of Raman scattering for characterizing the phase purity of cubic GaN layers.

To obtain information about the elastic constants of cubic GaN, the surface acoustic wave velocity (v_{SAW}) was determined from HRBS measurements. Even though Brillouin scattering in transparent materials is dominated by the elasto-optic scattering by bulk modes, the observation of excitations localized near the surface (i.e. Rayleigh surface waves) is possible

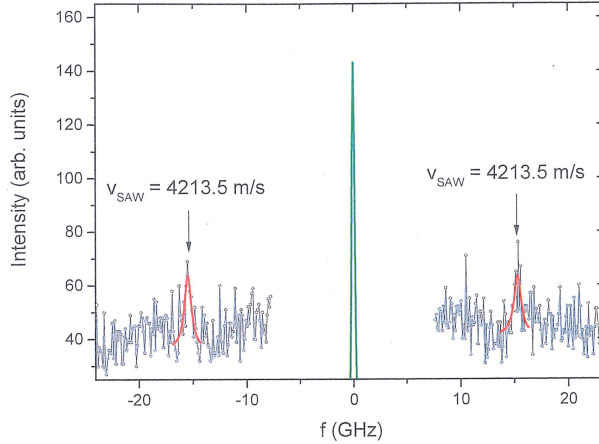


FIG. 3: HRSBS spectrum of the cubic GaN sample for $\alpha = 70^\circ$ in the [101] direction. Lorentzian line shapes have been fitted to the Rayleigh peaks to accurately obtain the spectral frequency shift of the light corresponding to scattering with the surface acoustic phonon mode.

in transparent films deposited on an opaque substrate.²⁵ In order to couple the incident light beam to the surface phonons, the incident beam was polarized in the scattering plane. The backscattered light was collected at 180° according to the scattering geometry shown in Fig. 2. In this backscattering geometry the SAW wave vector \mathbf{q}_{SAW} is parallel to the sample surface and its magnitude is given by $q_{\text{SAW}} = 4\pi \sin \alpha / \lambda_0$, where λ_0 is the laser wavelength in vacuum and α is the sagittal angle. The SAW propagation velocity can then be obtained from the surface phonon frequency ν_{SAW} as

$$v_{\text{SAW}} = \frac{\nu_{\text{SAW}} \lambda_0}{2 \sin \alpha}. \quad (1)$$

The scattering angle used in the measurements ($\alpha = 70^\circ$) provides a $q_{\text{SAW}}h$ value of 11.8, which is high enough for the Rayleigh modes to be in the asymptotic region where the influence of the substrate is negligible.²⁶ Figure 3 displays a typical HRSBS spectrum obtained for $\alpha = 70^\circ$ and $\phi = 45^\circ$ from the cubic GaN layer. A Lorentzian line-shape fit to the Rayleigh peak yields an accurate value of the SAW propagation velocity via Eq. (1).

Crystals with cubic symmetry exhibit four-fold symmetry in the v_{SAW} values within the (010) plane. By rotating the sample about the surface normal, the azimuthal angle can be varied and thus the direction of scattering wave vector \mathbf{q}_{SAW} can be selected within the (010) plane. For the HRSBS experiments, the sample was placed on a sample holder that was attached to a goniometer, so that it was possible to accurately fix the sagittal angle α and

rotate the sample about the surface normal to change the azimuthal angle ϕ , as can be seen in Fig. 2. In this way, the SAW propagation velocity in different crystallographic directions within the sample plane can be experimentally probed by HRSBS measurements.

Since the SAW propagation velocity is determined by the elastic constants of the material, we can extract information about the three independent elastic constants of the cubic layer from our HRSBS measurements.

For a crystal with cubic symmetry, the Rayleigh SAW velocities in the [100] and [101] directions are determined, respectively, by the secular equations^{27,28}

$$\rho v_{\text{SAW}}^2 - \left(\frac{c_{11}}{c_{44}} \times \frac{c_{44} - \rho v_{\text{SAW}}^2}{c_{11} - \rho v_{\text{SAW}}^2} \right)^{\frac{1}{2}} \left(c_{11} - \frac{c_{12}^2}{c_{11}} - \rho v_{\text{SAW}}^2 \right) = 0 \quad (2)$$

and

$$\rho v_{\text{SAW}}^2 - \left(\frac{c_{11}}{c_{44}} \times \frac{c_{44} - \rho v_{\text{SAW}}^2}{\frac{1}{2}(c_{11} + c_{12} + 2c_{44}) - \rho v_{\text{SAW}}^2} \right)^{\frac{1}{2}} \left(\frac{1}{2}(c_{11} + c_{12} + 2c_{44}) - \frac{c_{12}^2}{c_{11}} - \rho v_{\text{SAW}}^2 \right) = 0. \quad (3)$$

Here $\rho = 6.103 \text{ g cm}^{-3}$ is the mass density of cubic GaN estimated from the lattice parameter given in Ref. 29 and c_{11} , c_{12} , and c_{44} are the three independent elastic constants of cubic GaN. From the HRSBS measurements we have determined $v_{\text{SAW}}^{[100]} = 3866.9 \text{ m s}^{-1}$ and $v_{\text{SAW}}^{[101]} = 4220.4 \text{ m s}^{-1}$. Then, Eqs. (2) and (3) constitute an undetermined system of two equations with three unknowns. To reduce the number of unknowns and render the system determinate, we consider the longitudinal sound velocity and the corresponding elastic constant c_{11} experimentally measured in cubic GaN by picosecond acoustic measurements at 4.7 K.¹⁹ The sound velocity measured in wurtzite-type GaN was found to be independent of temperature within experimental error,¹⁹ so it is reasonable to consider the c_{11} value of 285 GPa determined at low temperature in our room temperature analysis. By solving Eqs. (2) and (3) with $\rho = 6.103 \text{ g cm}^{-3}$ and $c_{11} = 285 \text{ GPa}$ as input parameters, we can determine the elastic constants c_{12} and c_{44} from the measured SAW velocities. In Table I, the values we obtain are compared with theoretical values derived from a number of computational approaches such as density functional theory, molecular dynamics, and Keating model available in the literature.

Although the different calculational approaches yield a certain dispersion in the elastic constant values, it is worth noticing that the set of c_{ij} values determined from experimental

TABLE I: Elastic constants for c-GaN as determined in this work from HRBS measurements of the SAW compared with values predicted by theoretical calculations.

c_{11} (GPa)	c_{12} (GPa)	c_{44} (GPa)	Ref.
285 ± 8^a	149 ± 9^b	157.7 ± 0.6^b	
264	153	68	13
296	154	206	14
293	159	155	15
274.2	166.1	199	16
295	155.1	189.4	17
255	133	177	18
305	128	147	30
325	142	147	31

^a Experimental value taken from Ref. 19

^b This work: experimental values derived from HRBS measurements.

measurements of the Rayleigh SAW velocities in the present work are consistent with the predicted values and display relative deviations less than 2% in relation to the averaged theoretical values given in Table I.

In order to check the validity of the obtained results, the set of elastic constants have been used to simulate the scattered light intensity using the Green's function formalism introduced by Zhang *et al.*³² The dependence of the SAW velocity on the azimuthal angle for the c-GaN/GaAs sample studied is plotted in Fig. 4. An excellent agreement is found between the calculated azimuthal dependence and the SAW velocity measured by HRBS experiments along different directions, which confirms the consistency of the set of elastic constants determined in this work.

In summary, we have carried out HRBS measurements to determine the SAW velocity in a (010)-oriented c-GaN layer for the [100] and [101] propagation directions. From the analysis of the Rayleigh SAW peak frequency a consistent set of elastic constants c_{11} , c_{12} and c_{44} has been experimentally determined for the first time in c-GaN. The obtained values agree well with the mean values of the theoretical predictions found in the literature. The

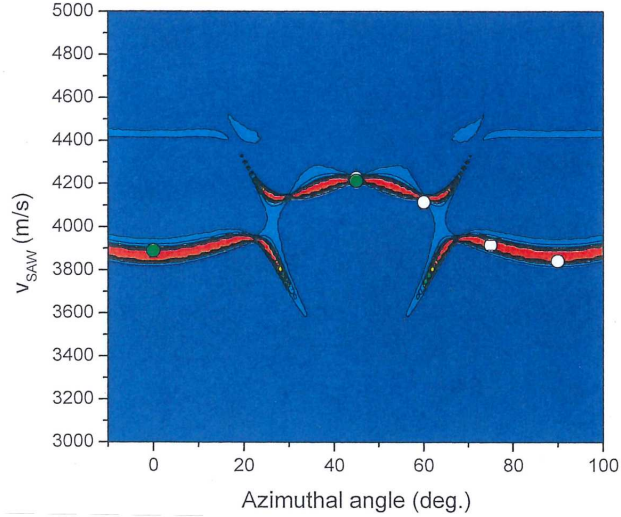


FIG. 4: Simulation of the azimuthal angle dependence of the SAW velocity for the c-GaN layer on GaAs using the set of elastic constants determined in this work (see Table I). The circles represent SAW velocities at different azimuthal angles determined by HRBS measurements.

azimuthal dependence of the SAW velocity found in the HRBS experiments can be accurately simulated using the obtained set of elastic constants.

Acknowledgments

This work was partially supported by the Spanish MINECO under project MAT2012-37276-C03-01 and from Comunidad de Madrid project S2013/MIT-2740 (PHAMA_2.0-CM).

-
- ¹ M. R. Krames, O. B. Shchekin, R. Mueller-Mach, G. O. Mueller, L. Zhou, G. Harbers, and M. G. Craford, *J. Disp. Technol.* **3**, 160 (2007).
 - ² U. Mishra, S. Likun, T. Kazior, and Y.-F. Wu, *Proc. IEEE* **96**, 287 (2008).
 - ³ M. Manfra, N. Weimann, Y. Baeyens, P. Roux, and D. Tennant, *Electron. Lett.* **39**, 694 (2003).
 - ⁴ S. Pleasants, *Nat. Photonics* **7**, 585 (2013).
 - ⁵ B. A. Haskell, F. Wu, S. Matsuda, M. D. Craven, P. T. Fini, S. P. DenBaars, J. S. Speck, and S. Nakamura, *Appl. Phys. Lett.* **83**, 1554 (2003).
 - ⁶ S. Li, J. Schörmann, D. J. As, and K. Lischka, *Appl. Phys. Lett.* **90**, 071903 (2007).

- ⁷ C. J. M. Stark, T. Detchprohm, S. C. Lee, Y.-B. Jiang, S. R. J. Brueck, and C. Wetzel, *Appl. Phys. Lett.* **103**, 232107 (2013).
- ⁸ S. V. Novikov, N. Zainal, A. V. Akimov, C. R. Staddon, A. J. Kent, and C. T. Foxon, *J. Vac. Sci. Technol. B* **28**, C3B1 (2010).
- ⁹ M. Feneberg, M. Röppischer, C. Cobet, N. Esser, J. Schörmann, T. Schupp, D. J. As, F. Hörich, J. Bläsing, A. Krost, et al., *Phys. Rev. B* **85**, 155207 (2012).
- ¹⁰ R. Cuscó, N. Domènech-Amador, S. Novikov, C. T. Foxon, and L. Artús, *Phys. Rev. B* **92**, 075206 (2015).
- ¹¹ A. Polian, M. Grimsditch, and I. Grzegory, *J. Appl. Phys.* **79**, 3343 (1996).
- ¹² M. Yamaguchi, T. Yagi, T. Azuhata, T. Sota, K. Suzuki, S. Chichibu, and S. Nakamura, *J. Phys. Cond. Mat.* **9**, 241 (1997).
- ¹³ M. E. Sherwin and T. J. Drummond, *J. Appl. Phys.* **69**, 8423 (1991).
- ¹⁴ K. Kim, W. R. L. Lambrecht, and B. Segall, *Phys. Rev. B* **50**, 1502 (1994).
- ¹⁵ A. F. Wright, *J. Appl. Phys.* **82**, 2833 (1997).
- ¹⁶ K. Shimada, T. Sota, and K. Suzuki, *J. Appl. Phys.* **84**, 4951 (1998).
- ¹⁷ F. Benkabou, H. Aourag, P. J. Becker, and M. Certier, *Mol. Simul.* **23**, 327 (2000).
- ¹⁸ Z. Usman, C. Cao, G. Nabi, D. Y. Kun, W. S. Khan, T. Mehmood, and S. Hussain, *J. Phys. Chem. A* **115**, 6622 (2011).
- ¹⁹ D. Moss, A. V. Akimov, S. V. Novikov, R. P. Champion, C. R. Staddon, N. Zainal, C. T. Foxon, and A. J. Kent, *J. Phys. D: Appl. Phys.* **42**, 115412 (2009).
- ²⁰ J. R. Sandercock, in *Light Scattering in Solids III, Topics in Applied Physics* (Springer-Verlag, Berlin, 1982), vol. 51, pp. 173–206.
- ²¹ R. J. Jiménez-Riobóo, M. García-Hernández, C. Prieto, J. J. Fuentes-Gallego, E. Blanco, and M. Ramírez-del Solar, *J. Appl. Phys.* **81**, 7739 (1997).
- ²² G. Mirjalili, T. Parker, S. Farjami Shayesteh, M. Bülbül, S. Smith, T. Cheng, and C. Foxon, *Phys. Rev. B* **57**, 4656 (1998).
- ²³ H. Siegle, L. Eckey, A. Hoffmann, C. Thomsen, B. Meyer, D. Schikora, M. Hankeln, and K. Lischka, *Solid State Comm.* **96**, 943 (1995).
- ²⁴ R. Cuscó, N. Domènech-Amador, T. Hatakeyama, T. Yamaguchi, T. Honda, and L. Artús, *J. Appl. Phys.* **117**, 185706 (2015).
- ²⁵ V. Bortolani, F. Nizzoli, G. Santoro, and J. R. Sandercock, *Phys. Rev. B* **25**, 3442 (1982).

- ²⁶ R. J. Jiménez-Riobóo, R. Cuscó, R. Oliva, N. Domènech-Amador, C. Prieto, J. Ibáñez, C. Boney, A. Bensaoula, and L. Artús, *Appl. Phys. Lett.* **101**, 062103 (2012).
- ²⁷ A. G. Every, L. M. Kotane, and J. D. Comins, *Phys Rev B* **81** (2010).
- ²⁸ L. M. Kotane, J. D. Comins, A. G. Every, and J. R. Botha, *J. Phys. Conf. Ser.* **278**, 012001 (2011).
- ²⁹ I. Vurgaftman and J. R. Meyer, *Journal of Applied Physics* **94**, 3675 (2003).
- ³⁰ A. A. Marmalyuk, R. K. Akchurin, and V. A. Groblyev, *Inorganic Materials* **34**, 691 (1998).
- ³¹ S. Y. Davydov and A. V. Solomonov, *Tech. Phys. Lett.* **25**, 601 (1999).
- ³² X. Zhang, J. D. Comins, A. G. Every, P. R. Stoddart, W. Pang, and T. E. Derry, *Phys. Rev. B* **58**, 13677 (1998).