

# ANSCHNITT

ZEITSCHRIFT FÜR KUNST UND KULTUR IM BERGBAU

BEIHEFT 26



## Archaeometallurgy in Europe II

Andreas Hauptmann  
Diana Modarressi-Tehrani



## Archaeometallurgy in Europe III



# Archaeometallurgy in Europe III

Proceedings of the 3<sup>rd</sup> International Conference  
Deutsches Bergbau-Museum Bochum

June 29 – July 1, 2011

Editors  
Andreas Hauptmann  
Diana Modarressi-Tehrani

Bochum 2015

Montanhistorische Zeitschrift

Der ANSCHNITT. Beiheft 26

= Veröffentlichungen aus dem Deutschen  
Bergbau-Museum Bochum, Nr. 202

The conference Archaeometallurgy in Europe III  
was supported by



Keyence



Analyticon



MLS GmbH



Zeiss



Thermo Scientific



Springer Verlag Berlin Heidelberg  
New York

#### Redaktion

Diana Modarressi-Tehrani, Andreas Hauptmann

#### Layout

Rolf Krause

#### Titelgestaltung

Karina Schwunk

#### Druck

Grafisches Centrum Cuno GmbH & Co. KG

Bibliografische Informationen der Deutschen Bibliothek

Die Deutsche Bibliothek verzeichnet diese Publikation in der  
Deutschen Nationalbibliografie; detaillierte bibliografische Daten  
sind im Internet über <http://dnd.ddb.de> abrufbar.

ISBN 10: 3-937203-74-5

ISBN 13: 978-3-937203-74-4

#### Cover

Domus Vettiorum / Casa dei Vettii, Pompeii (Campania, Italy, 63-79 BC), which was excavated in 1894. Section of a Pompeii-style scenic fresco showing Eros and Psyche in a gold assay laboratory. In the left corner, scales for weighing gold are put on a table. Next to it, one of the Erotes is working with a small hammer on an anvil. On the right side, an assay furnace is shown. Another of the Erotes is holding a small crucible with pincers with the right hand while using a blowpipe with his left hand, supplying the fire with air. The large bellow for the assay furnace is driven by the third of the Erotes.

#### DER ANSCHNITT

Herausgeber:

Vereinigung der Freunde von Kunst und Kultur im Bergbau e.V.

Vorsitzender des Vorstands:

Prof. Dr. Karl Friedrich Jakob

Vorsitzender des Beirats:

Bergassessor Dipl.-Kfm. Dr.-Ing. E.h. Achim Middelschulte

Geschäftsführer:

Museumsdirektor Prof. Dr. rer. nat. Stefan Brüggerhoff

Schriftleitung:

Dr. phil. Andreas Bingener M.A.

Editorial Board:

Prof. Dr. Stefan Brüggerhoff, Dr. Lars Bluma, Dr. Michael  
Farrenkopf, Prof. Dr. Rainer Slotta, Dr. Thomas Stöllner

Wissenschaftlicher Beirat:

Prof. Dr. Jana Geršlová, Ostrava; Prof. Dr. Karl-Heinz Ludwig,  
Bremen; Prof. Dr. Thilo Rehren, London; Prof. Dr. Wolfram  
Weber, Bochum

Anschrift der Geschäftsführung und der Schriftleitung:

Deutsches Bergbau-Museum  
Am Bergbaumuseum 28 - D-44791 Bochum  
Telefon (02 34) 58 77-0  
Telefax (02 34) 58 77-111

Einzelheft 9,- €, Doppelheft 18,- €;

Jahresabonnement (6 Hefte) 54,- €;

kostenloser Bezug für die Mitglieder der Vereinigung  
(Jahres-Mitgliedsbeitrag 50,- €)

# Archaeometallurgy in Europe III

## Scientific Advisory Board

Gilberto Artioli, Università di Padova, Italy

Roland Gauß, Fraunhofer-Institut für Silicatforschung,  
ISC, Alzenau

Alessandra Giumlia-Mair, Merano, Italy

Gert Goldenberg, University of Innsbruck, Austria

Sabine Klein, J.W. Goethe University of Frankfurt/  
Main, Germany

Marcos Martinon-Torres, University College London,  
United Kingdom

William O'Brien, University of Galway, Ireland

Vincent Serneels, University of Fribourg, Switzerland

## Standing Committee

Yannis Bassiakos, Athens, Greece

Alessandra Giumlia-Mair, Merano, Italy

Andreas Hauptmann, Bochum, Germany

Ivelin Kuleff, Sofia, Bulgaria

Susan LaNiece, London, United Kingdom

Ignacio Montero, Madrid, Spain

## Local Organizing Committee

Michael Bode

Andreas Hauptmann

Diana Modarressi-Tehrani

Michael Prange

Ünsal Yalçın

# Editorial

This volume comprises a range of articles, which were submitted and selected from all the presentations given on the International Conference "Archaeometallurgy in Europe III", held from the 29<sup>th</sup> of June to 1<sup>st</sup> of July 2011 at the Deutsches Bergbau-Museum Bochum, Germany.

The present volume is the third in the series "Archaeometallurgy in Europe", capturing the spirit of the successful series of international conferences on this special theme of research. The first conference "Archaeometallurgy in Europe" had been organized by the Associazione Italiana di Metallurgia and took place in Milano, Italy, from the 24<sup>th</sup> to the 26<sup>th</sup> of September 2003. The second conference was held in Aquileia, Italy, from the 17<sup>th</sup> to the 21<sup>st</sup> of June 2007. It was also organized by the Associazione Italiana di Metallurgia.

The splendid idea to launch this conference series, a scientific series of meetings limited to the countries of Europe, came from the late Prof. Dr. Walter Nicodemi, formerly President of the Associazione Metallurgia di Italia. Thanks to the efforts of Dr. Alessandra Giunliamair, Merano, these conferences have developed into increasingly productive events with a high scholarly quality. Since then three conferences have taken place and the fourth meeting is at an advanced stage of preparation and will take place in Madrid, Spain, from the 1<sup>st</sup> to the 3<sup>rd</sup> June 2015.

The title of the conference series covers a research field which is a distinctive part of archaeometry, and which so far was usually included as one of the topics in the program of the "International Symposium on Archaeometry" (ISA), organized every third year at different locations in Europe and in the United States. However it is our opinion, that in the last decade archaeometallurgy has developed as a very important research field, and we are observing a large number of scholarly activities all over the world. We are convinced that such an important topic needs to be organised and presented in conferences specifically dedicated to this field. Therefore the topic of this conference is the history of metals and metallurgy primarily in Europe, but it also includes other regions of the Old World.

The future prospects of the conference series are promising, especially because "Archaeometallurgy in Europe" constitutes an extremely useful broadening and a regional counterpoint to the well-established and successful conference series "The Beginnings of the Use of Metals and Alloys" (BUMA), which was launched in

1981 by Professors Tsun Ko, Beijing, China, and Robert Maddin, then Philadelphia, USA. The focus of the eight BUMA conferences held so far (the last one was held in Nara, Japan, in 2013) lays on the development of metallurgy in South-East Asia and the Pacific Rim. We firmly believe that the two conferences complement each other very effectively and should therefore continue to exist side by side.

With this special volume of *Der Anschnitt*, we are delighted to publish a selection of the lectures presented at the conference at the Deutsches Bergbau-Museum Bochum in 2011. Many of the authors contributed with very instructive and informative papers, which finally resulted in this volume.

We are very much obliged to all these authors who, with patience and persistence, cooperated with us and helped to shape this volume. We would also like to thank the reviewers who decisively contributed in the improvement of the scientific level of this volume.

Our thanks go first to all those colleagues and friends who helped to organize the conference in 2011. The former director of the Deutsches Bergbau-Museum, Prof. Dr. Rainer Slotta, and the present director, Prof. Dr. Stefan Brüggerhoff encouraged and promoted our efforts to organize this scholarly meeting. Dr. Michael Bode, Dr. Michael Prange, and Prof. Dr. Ünsal Yalçın supported the conference planning and realization in every aspect. Many colleagues of the staff of the Deutsches Bergbau-Museum, and many of the students working in our research laboratory offered their assistance and help.

Finally, our thanks go to Mrs. Karina Schwunk and Mrs. Angelika Wiebe-Friedrich who performed the editorial work, design, and layout for this volume.

Andreas Hauptmann  
Diana Modarressi-Tehrani

Contemporaneously to the conference in 2011 a volume with abstracts on every lecture given and every poster presented was published:

2011 HAUPTMANN, Andreas, MODARRESSI-TEHRANI, Diana & PRANGE, Michael (eds.), *Archaeometallurgy in Europe III. Abstracts*. METALLA, Sonderheft 4, 2011.

# Table of contents

## Early mining and metallurgical innovation stages in Europe

Hans Anderssson	
<b>Iron – a driving force in early urbanisation</b>	13
Florence Cattin, Matthias B. Merkl, Christian Strahm & Igor Maria Villa	
<b>Elemental and lead isotopic data of copper finds from the Singen cemetery, Germany – a methodological approach of investigating Early Bronze Age networks</b>	19
Guntram Gassmann, Sabine Klein & Gabriele Körlin	
<b>The Roman mines near Ulpiana, Kosovo</b>	33
Marc Pearce	
<b>The spread of early copper mining and metallurgy in Europe: an assessment of the diffusionist model</b>	
<b>A key-note lecture</b>	45
Ignacio Soriano	
<b>The earliest metallurgy in the north-eastern Iberian Peninsula: origin, use and socioeconomic implications</b>	55
Thomas Stöllner	
<b>Humans approach to resources: Old World mining between technological innovations, social change and economical structures.</b>	
<b>A key-note lecture</b>	63
Simon Timberlake, Tim Mighall & Thomas Kidd	
<b>Newresearch into Roman metal mining in Britain</b>	83

## Regional studies in Europe and beyond

Lucile Beck, Elise Alloin, Anne Michelin, Florian Téreygeol, Claire Berthier, Dominique Robcis, Thierry Borel & Ulrich Klein	
<b>Counterfeit coinage of the Holy Roman Empire in the 16<sup>th</sup> century: silvering process and archaeometallurgical replications</b>	97
Maryse Blet-Lemarquand, Arnaud Suspène & Michel Amandry	
<b>Augustus' gold coinage: investigating mints and provenance through trace element concentrations</b>	107
Velislav Bonev, Boika Zlateva & Ivelin Kuleff	
<b>Chemical composition of fibulae from the Iron Age in Thrace (Bulgaria)</b>	115



Carlo Bottaini, Claudio Giardino, Giovanni Paternoster <b>The Final Bronze Age hoard from Solveira (northern Portugal): a multi-disciplinary approach</b>	125
Jennifer Garner <b>Bronze Age tin mines in central Asia</b>	135
Alessandra Giunlia-Mair, Susan C. Ferrence & Philip P. Betancourt <b>Metallurgy of the copper-based objects from Gournia, east Crete</b>	145
Elisa M. Grassi <b>Roman metalworking in northern Italy between archaeology and archaeometry: two case studies</b>	155
Babara Horejs & Mathias Mehofer <b>Early Bronze Age metal workshops at Çukuriçi Höyük Production of arsenical copper at the beginning of the 3<sup>rd</sup> millennium BC</b>	165
Rüdiger Krause <b>New horizons: archaeometallurgy in eastern Europe and beyond A key-note lecture</b>	177
Janet Lang <b>The Anglo-Saxon cemetery at Dover Buckland, Kent, UK and the technology of some of the iron artefacts</b>	185
Lene Melheim <b>Late Bronze Age axe traffic from Volga-Kama to Scandinavia?</b>	193
Alicia Perea, Patricia Fernández-Esquivel, Salvador Rovira-Llorens, José Luis Ruvalcaba-Sil, Ana Verde, Oscar García-Vuelta & Fabián Cuesta-Gómez <b>Prehistoric gold metallurgy: the Arqeomeb research project</b>	203
Irina Ravich & Mikhail Treister <b>The mirrors of the early nomads of the foothills of south Urals: a complex archaeo-technological study</b>	211
Irina Segal, Miryam Bar-Matthews, Alan Matthews, Yehudit Harlavan & Dan Asael <b>Provenance of ancient metallurgical artifacts: implications of new Pb isotope data from Timna ores</b>	221
Béla Török, Árpád Kovács & Zsolt Gallina <b>Iron metallurgy of the Pannonian Avars of the 7<sup>th</sup> - 9<sup>th</sup> century based on excavations and material examinations</b>	229
Frank Willer, Roland Schwab & Kati Bott <b>Large Roman Bronze statues from the UNESCO World Heritage Limes</b>	239
Vladimir I. Zavyalov & Nataliya N. Terekhova <b>Three-fold welding technology in the blacksmith's craft of Medieval Rus' (concerning Scandinavian innovations)</b>	247

## Reconstructing ancient technologies

David Bourgarit & Nicolas Thomas <b>Ancient brasses: misconceptions and new insights</b>	255
Vagn F. Buchwald <b>On the characterization of slags and ancient iron artefacts applying the slag-analytical method</b>	263
Joseph Gauthier, Pierre Fluck, Alessandre Disser & Carmela Chateau <b>The Alsatian Altenberg: a seven-hundred-year laboratory for silver metallurgy</b>	271
Anno Hein, Ioannis Karatasios, Noémi S. Müller & Vassilis Kilikoglou <b>Material properties of pyrotechnical ceramics used in the Bronze Age Aegean and implications on metallurgical technologies</b>	279
Silviya Ivanova, Veselina Rangelova, Deyan Lesigyarski & Ivelin Kuleff <b>Observations on the technology of Bronze Age copper and copper alloy finds from Bulgaria</b>	287
David Killick <b>Archaeometallurgy as archaeology</b> A key-note lecture	295
Steffen Kraus, Christian Schröder, Susanne Klemm & Ernst Pernicka <b>Archaeometallurgical studies on the slags of the Middle Bronze Age copper smelting site S1, Styria, Austria</b>	301
Matthias Krismer, Gert Goldenberg & Peter Tropper <b>Mineralogical-petrological investigations of metallurgical slags from the Late Bronze Age fahlore-smelting site Mauken (Tyrol, Austria)</b>	309
Matthias B. Merkl <b>Some thoughts on the interpretation of the elemental composition of Chalcolithic copper finds from central Europe</b>	319
Nerantzis Nerantzis <b>Experimental simulation study of prehistoric bronze working: testing the effects of work-hardening on replicated alloys</b>	329
Barbara S. Ottaway <b>Experiments in archaeometallurgy</b> A key-note address	337
Alessandro Pacini <b>The Lombard fibula of the Arcisa: a substitution?</b>	347
Salvador Rovira, Martina Renzi, Auxilio Moreno & Francisco Contreras <b>Copper slags and crucibles of copper metallurgy in the Middle Bronze Age site (El Argar Culture) of Peñalosa (Baños de la Encina, Jaen, Spain)</b>	355

Sana Shilstein & Sarel Shalev  
**Comparison of compositional variations in modern European bronze coins with variations in some ancient coins** 363

Elena Silvestri, Paolo Bellintani, Franco Nicolis, Michele Bassetti, Siria Biagioni, Nicola Cappellozza, Nicola Degaspero, Marco Marchesini, Nicoletta Martinelli, Silvia Marvelli & Olivia Pignatelli  
**New excavations at smelting sites in Trentino, Italy: archaeological and archaeobotanical data** 369

Maria A. Socratous, Vasiliki Kassianidou & Gaetano Di Pasquale  
**Ancient slag heaps in Cyprus: the contribution of charcoal analysis to the study of the ancient copper industry** 377

## **New approaches, new technologies in archaeometallurgy**

Gilberto Artioli, Matteo Parisatto & Ivana Angelini  
**High energy X-ray tomography of Bronze Age copper ingots** 387

Elisa Barzagli, Francesco Grazi, Francesco Civita, Antonella Scherillo, Alessio Fossati & Marco Zoppi  
**Characterization of ancient Japanese sword hand guards through time-of-flight neutron diffraction and scanning electron microscopy** 391

**The authors** 401

# Archaeometallurgical studies on the slags of the Middle Bronze Age copper smelting site S1, Styria, Austria

## Summary

The copper smelting site S1 in the Eisenerzer Ramsau Valley, Styria, is the largest Bronze Age copper smelting site excavated in the Eastern Alps. The site was almost completely excavated from 1992 to 2006 and ten roasting hearths, six double furnaces, a number of pits of variable size, form and function, and three separate slag dumps have been recorded. The use of this smelting site covers the whole period of the Middle Bronze Age from the 16<sup>th</sup> to the 13<sup>th</sup> century BC and might extend as far as the 11<sup>th</sup> century BC. The aim of this archaeometallurgical study is the reconstruction of the smelting process at this site and the discovery of possible diachronic changes or developments in the technology of smelting during the different phases of use. Therefore slags of the different archaeological phases were analysed for their chemical and mineralogical composition. A few slags were analysed with Mössbauer spectroscopy to obtain further information about the conditions during the smelting process.

The results of the analyses show that nearly all slags belong to one particular step of the smelting process which was the production of raw copper or copper matte under reducing conditions at temperatures around 1250 °C.

## Introduction

During the Bronze Age copper ores were mined and smelted in many areas of the Eastern Alps, where copper sulphides (chalcopyrite) and fahlore are found in the ore mineralisations of the greywacke zone. In Styria, an extensive prehistoric copper mining area has been in the process of being recorded in the Eisenerzer Alps since the 1950s (Klemm 2003; Klemm 2006; Klemm 2010). The largest Bronze Age copper smelting site excavated in the Eastern Alps – the copper smelting site S1 – is situated in the north-eastern part of those Alps, close to the mining town of Eisenerz.

The focus of the archaeometallurgical study is the chemical and mineralogical investigation of the slag material

and associated finds. The aim of the archaeometallurgical investigation is to reconstruct the technology of the smelting process at this Bronze Age site. Furthermore, our intention was to discover possible diachronic changes or developments in the technology used for smelting copper ores during the different construction phases of the site.

## The archaeological excavation

The stratigraphic excavation at the copper smelting site S1 from 1992 to 2006 has revealed about 80% of this complex Bronze Age site (Fig. 1). The remains of ten roasting hearths, six double furnaces, a number of pits of variable size, form and function, and three separate large slag dumps have been recorded (Klemm 2003; Klemm, in preparation). The use of this smelting site covers the whole period of the Middle Bronze Age from the 16<sup>th</sup> to the 13<sup>th</sup> century BC and might extend as far as the 11<sup>th</sup> century BC.

In accordance with all other smelting sites in the Eastern Alps, the Middle Bronze Age copper-works consist of two furnaces and one roasting hearth. In the north-western part of the site three different construction phases for these have been revealed. The double furnaces 9/10 with roasting hearth 7 date back to the earliest phase of the smelting site. In the following phase these furnaces were levelled and the double furnaces 4/5 with roasting hearth 4 were built to the north of these early furnaces. The latest phase is represented by the double furnaces 1/2 with the roasting hearths 1, 2 and 3. The stratigraphy of the central and eastern part of the site is more complex. This is partly due to extensive disturbances which resulted from the construction of a large pit for charcoal production at the end of the 13<sup>th</sup> to the early 15<sup>th</sup> century AD, the late mediaeval period (Klemm et al. 2005); the Bronze Age features in this central and eastern area of the site cover a period from the 15<sup>th</sup> to the 12<sup>th</sup> century BC.

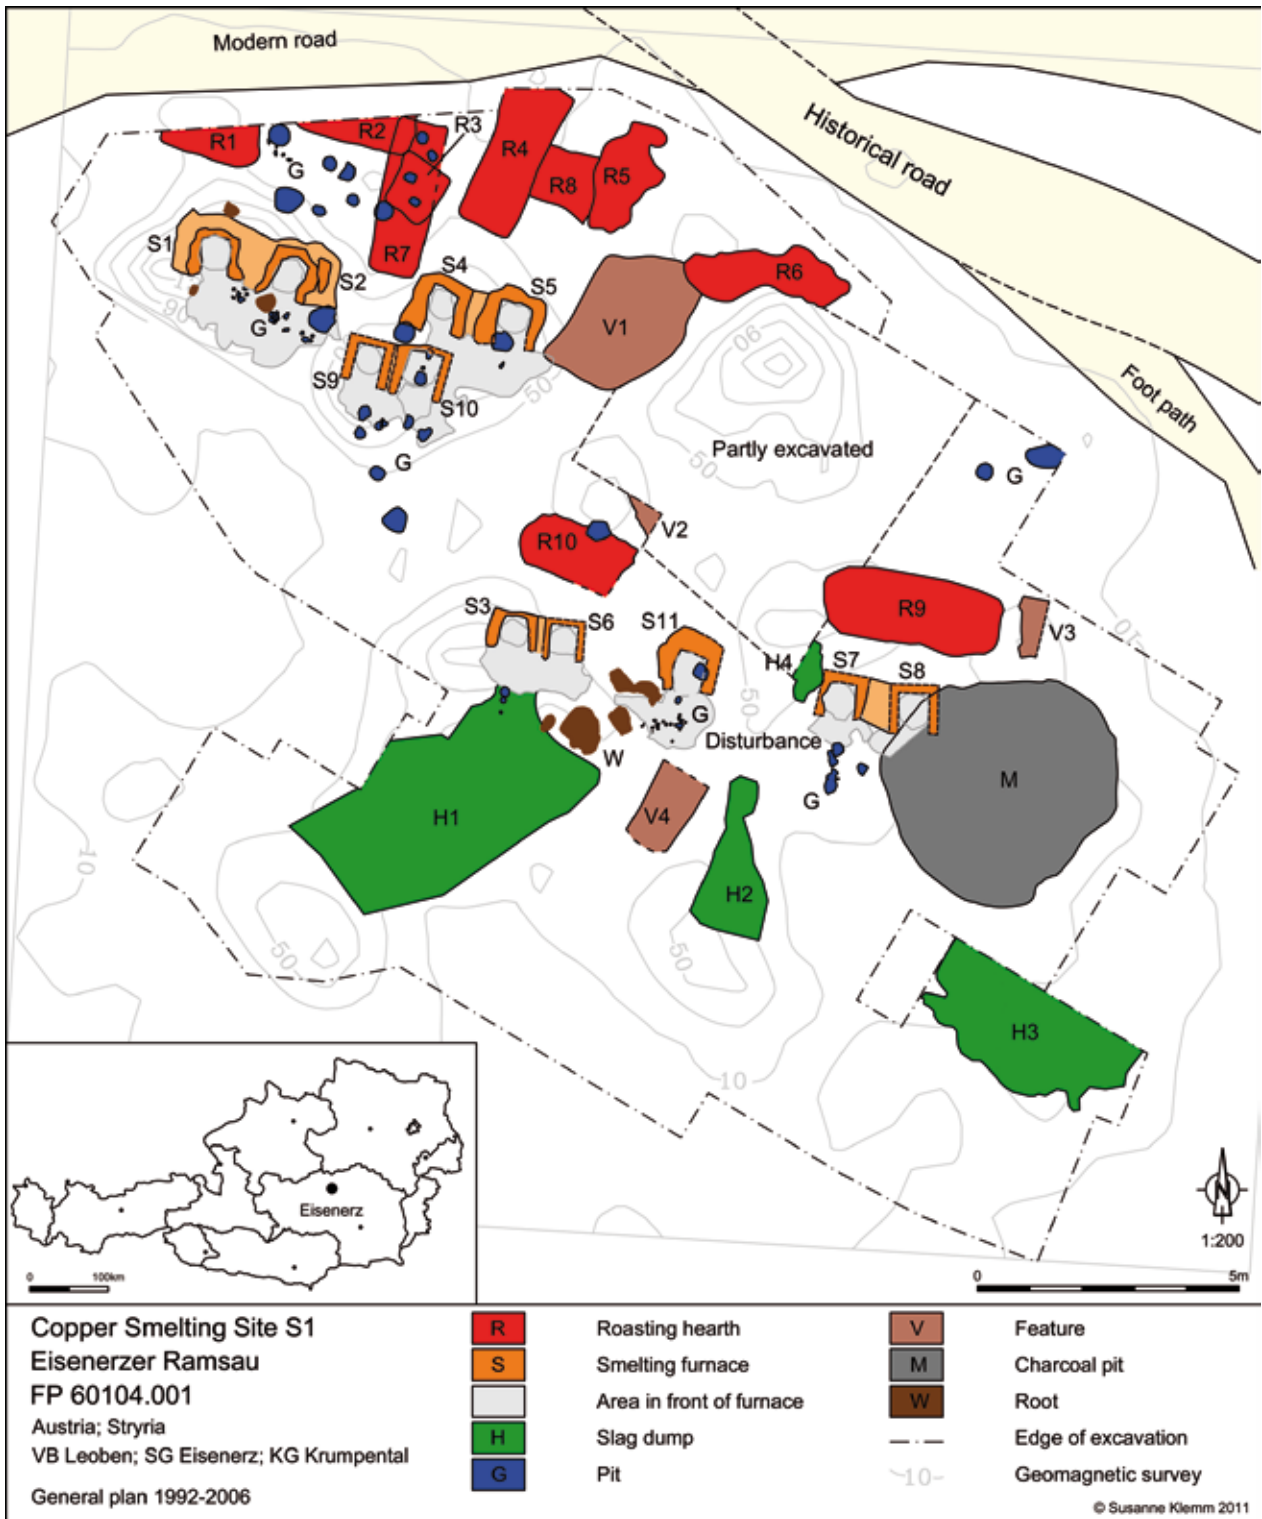


Fig. 1: General plan of the Bronze Age copper smelting site S1, Eisenerzer Ramsau, Styria. (S. Klemm, U. Schuh)

## Archaeometallurgical study

### Research objectives and methods

The mineralogical investigation included macroscopic analysis as well as optical microscopy in reflected and

transmitted light enhanced by scanning electron microscopy which also allows the semiquantitative chemical analysis of small areas or particles. The chemical bulk composition of the slags was determined with wavelength-dispersive X-ray fluorescence analysis. In addition some slags from the double furnaces 9/10 and samples of the slag lining from the double furnaces 4/5



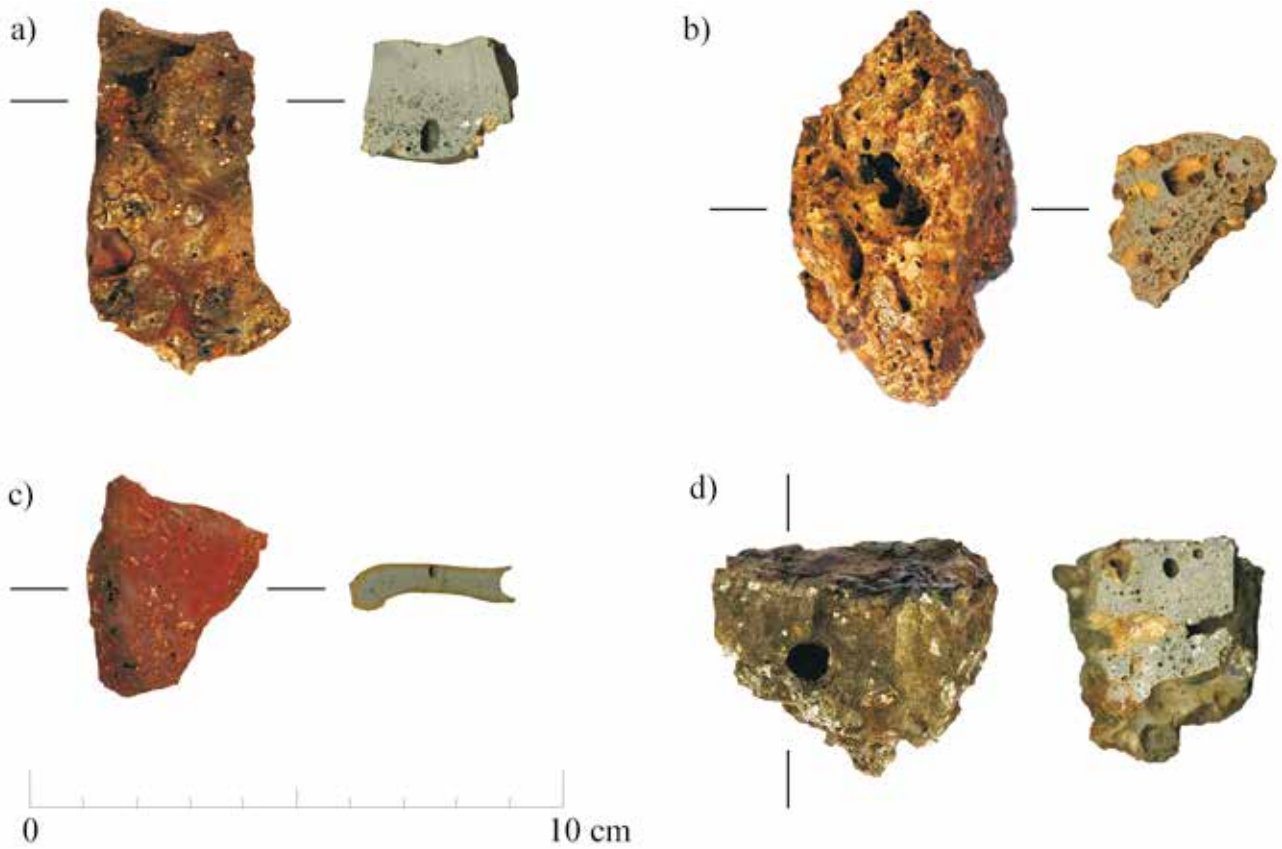


Fig. 2: Types of slags found at the copper smelting site S1: a) 'Laufschlacke' (type A); b) 'Blasenschlacke' (type B); c) 'Plattenschlacke' (type C); d) slag type A+B. (S. Kraus)

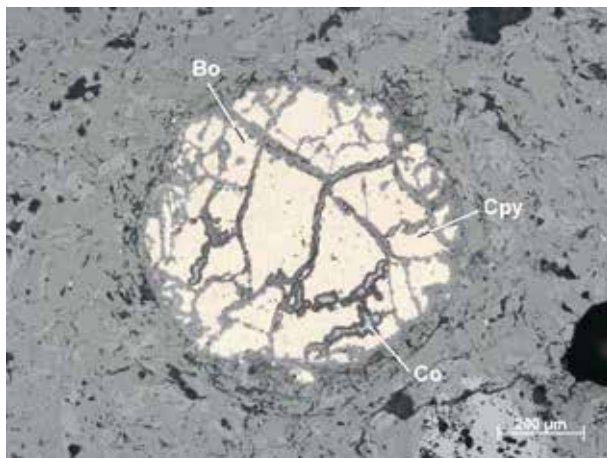


Fig. 3: Copper matte inclusion (Bo = bornite, Co = covellite, Cpy = chalcopyrite). (S. Kraus)

were analysed with Mössbauer spectroscopy to determine  $Fe^{2+}/Fe_{total}$  ratios and the abundance of Fe-bearing minerals. With this information it was possible to establish the temperature, oxygen partial pressure and cooling rate during the smelting process (Moesta et al. 1984; Moesta et al. 1989; Hauptmann 2000).

## Results

Following Doonan et al. 1996, the slags were divided into three different types according to their macroscopic properties (Fig. 2): 'Laufschlacke' (type A), 'Blasenschlacke' (type B) and the characteristically thin 'Plattenschlacke' (type C). Mostly slags of types A or B or combinations of these (types A+B) and occasionally type C slags were found at the site.

Under the microscope the slag types A 'Laufschlacke' and B 'Blasenschlacke' show similar structures of short prismatic to lath-shaped olivines and prismatic clinopyroxenes. The only differences between these two slag types are the higher porosity of type B 'Blasenschlacke' and the increased occurrence of unmelted quartz inclusions in it. Some of these quartz inclusions contain the remains of Cu/Fe-sulfides. These are mainly iron-rich sulfides which consist of agglomerates of copper bearing pyrrhotin and chalcopyrite. In contrast, the structure of 'Plattenschlacke' consists of thin, long fayalite needles in a glassy matrix. Nearly all slag samples contain matte inclusions (Fig. 3) of varying copper concentrations.

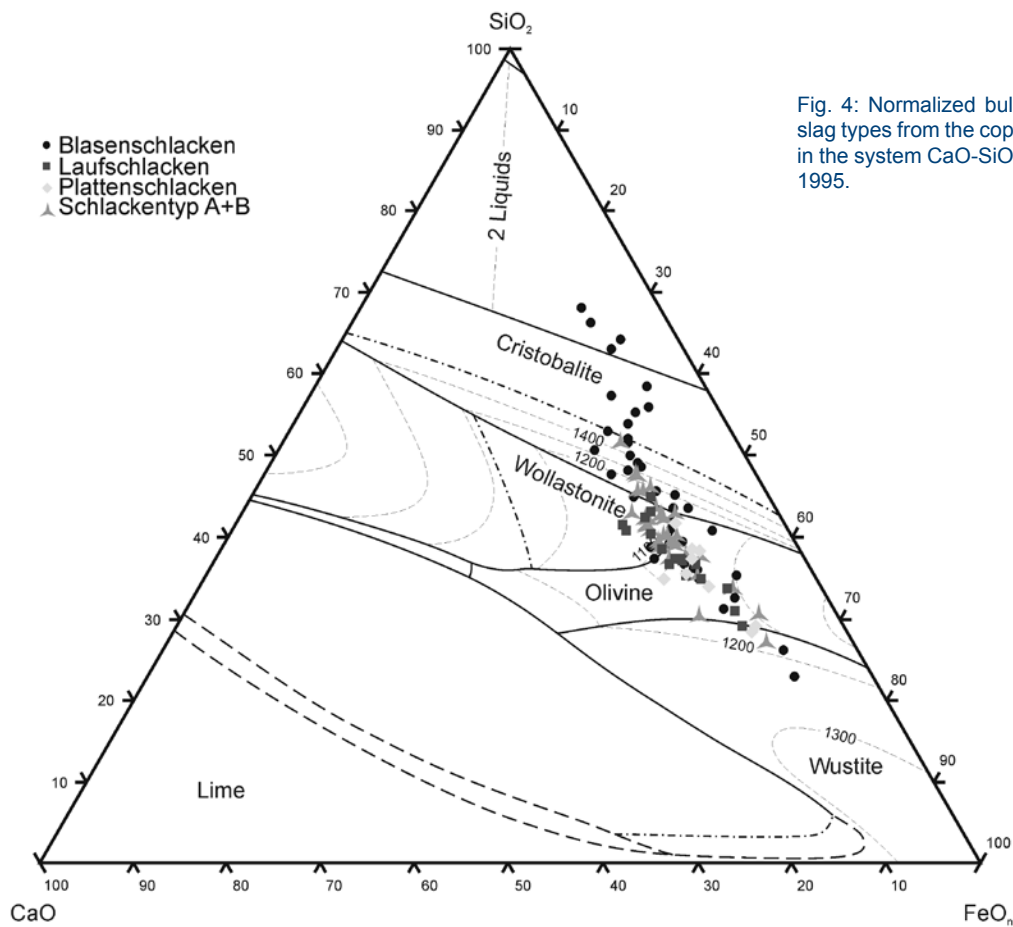


Fig. 4: Normalized bulk analyses of the different slag types from the copper smelting site S1 plotted in the system CaO-SiO<sub>2</sub>-FeO<sub>n</sub> after Kowalski et al. 1995.

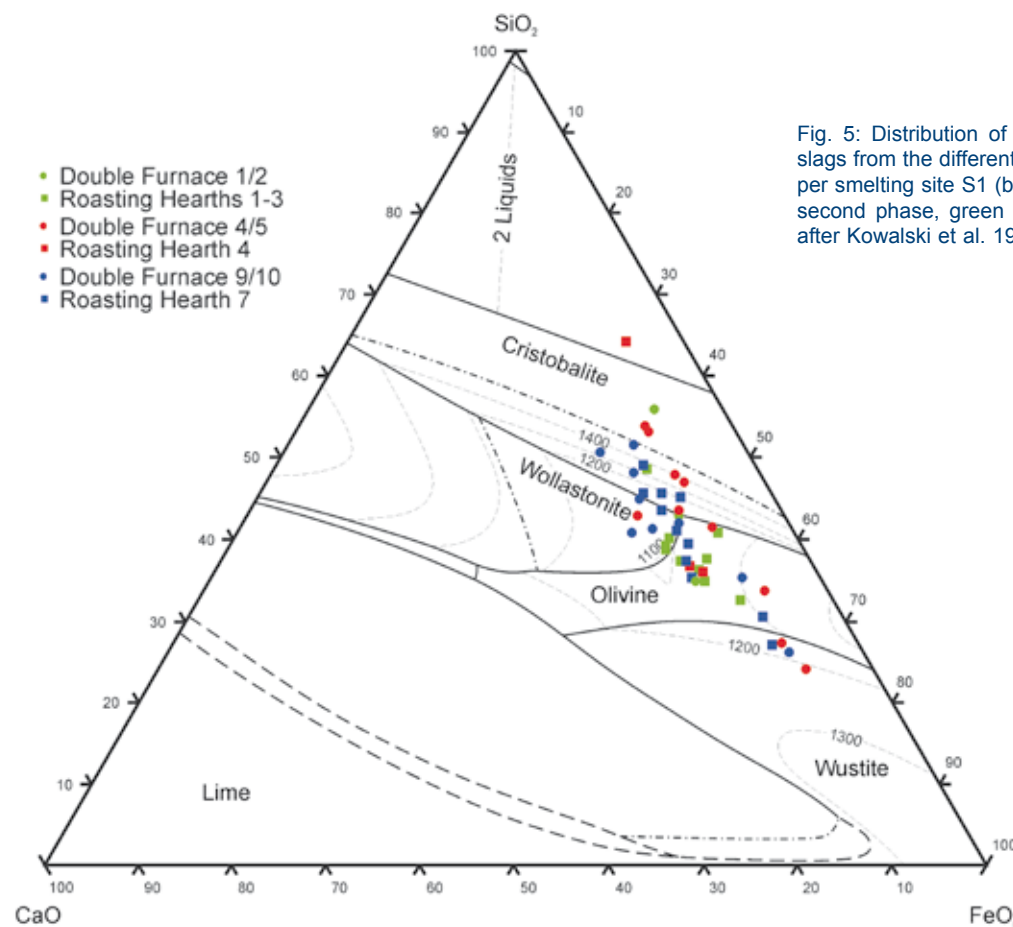
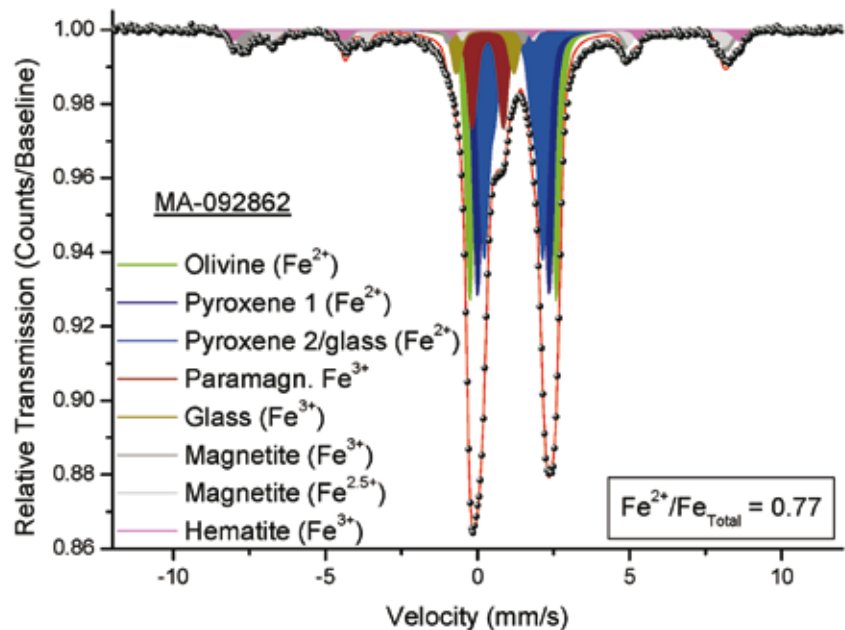


Fig. 5: Distribution of the main components for slags from the different phases of use of the copper smelting site S1 (blue = earliest phase, red = second phase, green = latest phase). (modified after Kowalski et al. 1995)

Table 1: Mössbauer model parameters, Fe oxidation state and mineral phase identification for samples MA-092862 and MA-101407 (1isomer shift relative to  $\alpha$ -Fe at room temperature, 2quadrupole splitting ( $\Delta E_Q$ ; doublet subspectra) or quadrupole shift ( $\epsilon$ ; sextet subspectra), 3internal magnetic field, 4Gaussian distribution of Voigt-based lineshapes; in mm/s (doublet subspectra) or T (sextets), 5area ratio; proportional to Fe content in mineral phase).

$\delta^1$ [mm/s]	$\Delta E_Q$ or $\epsilon^2$ [mm/s]	$B_{hf}^3$ [T]	$\sigma^4$ [mm/s or T]	$A^5$ [%]	Fe ox.	Mineral
<i>MA-092862</i>						
1.18	2.35	-	0.2	24	Fe <sup>2+</sup>	Pyroxene
1.17	2.85	-	0.2	25	Fe <sup>2+</sup>	Olivine
0.33	1.03	-	0.2	9	Fe <sup>3+</sup>	Paramagn. Fe <sup>3+</sup>
1.18	1.93	-	0.2	20	Fe <sup>2+</sup>	Pyroxene/glass
	1.23	-	0.2	6		
0.25	1.90	-	0.2	4	Fe <sup>3+</sup>	Glass
0.37	0.10	51.8	1.0	3	Fe <sup>3+</sup>	Hematite
0.26	0.00	49.2	1.0	5	Fe <sup>3+</sup>	Magnetite
0.67	0.00	46.1	1.0	4	Fe <sup>2.5+</sup>	Magnetite
<i>MA-101407</i>						
1.14	1.93	-	0.3	7	Fe <sup>2+</sup>	Pyroxene
1.04	2.75	-	0.2	5	Fe <sup>2+</sup>	Olivine
0.40	0.80	-	0.2	11	Fe <sup>3+</sup>	Paramagn. Fe <sup>3+</sup>
0.40	0.32	-	0.2	1	Fe <sup>3+</sup>	Delafossite
0.37	-0.1	51.8	1	6	Fe <sup>3+</sup>	Hematite
0.32	0.01	49.3	0.5	22	Fe <sup>3+</sup>	Magnetite
		47.5	0.5	6		
0.62	0.01	46.3	0.5	16	Fe <sup>2.5+</sup>	Magnetite
		44.7	0.5	11		
		42.9	0.5	6		
		40.2	0.5	3		
		48.1	0.5	5		

Fig. 6: Mössbauer-spectrum collected at room temperature of a 'Laufschlacke' (sample MA-092862) from the double furnace 9/10. The iron, made up of fayalite and pyroxene and very little magnetite with  $Fe^{2+}/Fe_{total} = 0.77$ , suggests a slow cooling of the melt within the furnace. (Graphics: C. Schröder)



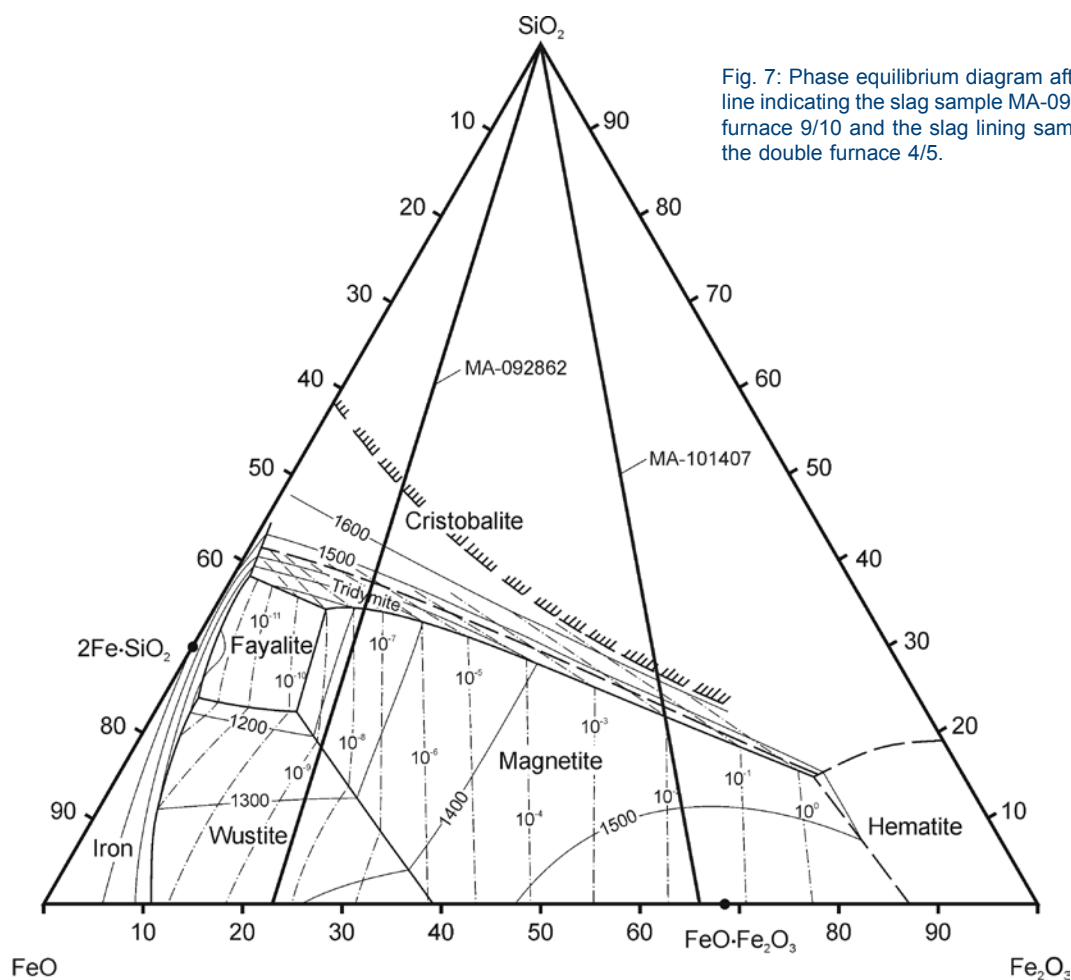


Fig. 7: Phase equilibrium diagram after Muan 1955 with a line indicating the slag sample MA-092862 from the double furnace 9/10 and the slag lining sample MA-101407 from the double furnace 4/5.


Figure 4 shows the distribution of the major components of the slag types in the ternary diagram CaO-FeO-SiO<sub>2</sub>. It is obvious that macroscopically different slags show no significant differences in their chemical composition. These are mainly fayalitic and silicate slags formed during the smelting of roasted chalcopiritic ores. Some slags of type B show higher concentration of SiO<sub>2</sub> which is due to several inclusions of quartz. The smelting temperatures of the slags which can be derived from their chemical and mineralogical composition were between 1150 °C and 1250 °C.

In order to discover possible diachronic changes or developments in the technology used for smelting copper ores, the chemical composition of the slags from the different archaeological phases of the copper smelting site S1 were compared as shown in Figure 5. It was found that the slags from the latest period (from furnaces 1 and 2) were lower in SiO<sub>2</sub> content but higher in CaO content which corresponds well with the mineralogical results which showed that there were fewer inclusions of unmelted quartz in those particular slags. It can be assumed that in the later periods of use of the copper smelting site S1 the smelting process was performed without or with less quartz than in the previous

periods. Nevertheless no evidence has been found of changes in the technique used for the smelting process. To obtain further information about the processing parameters, some slags were analysed with Mössbauer spectroscopy. Figure 6 shows the spectrum of a slag of the sample type 'Laufschlacke' and its associated Fe<sup>2+</sup>/Fe<sub>total</sub> ratio, which was used to deduce the oxygen partial pressure (pO<sub>2</sub>) relating to the system FeO-Fe<sub>2</sub>O<sub>3</sub>-SiO<sub>2</sub> developed by Muan 1955 (Fig. 7). Therefore a line from the SiO<sub>2</sub>-top was drawn to a point on the FeO-Fe<sub>2</sub>O<sub>3</sub> axis representing the measured Fe<sup>2+</sup>/Fe<sub>total</sub> ratio. For the 'Laufschlacke' the pO<sub>2</sub> was found to lie between 10<sup>-9</sup> and 10<sup>-8</sup> atmospheres. The drawn line also shows the range of temperature to be between 1200 to 1300 °C which is in accordance with the temperatures that were estimated on the basis of the chemical composition.

In contrast to the slag sample from the double furnaces 9/10, the slag lining sample from the double furnaces 4/5 shows a different spectrum (Fig. 8). The slag lining sample derives from the northwest corner of furnace 5 at a height of approximately 20–25 cm from the bottom. The deduced pO<sub>2</sub> is between 10<sup>-2</sup> and 10<sup>-1</sup> atmospheres indicating oxidizing conditions at this height in the furnace during the smelting process.

Fig. 8: Mössbauer-spectrum collected at room temperature of a 'Blasenschlacke' (sample MA-101407) from the double furnaces 4/5. The low  $\text{Fe}^{2+} / \text{Fe}_{\text{total}} = 0.34$  suggests more oxidizing conditions. (Graphics: C. Schröder)

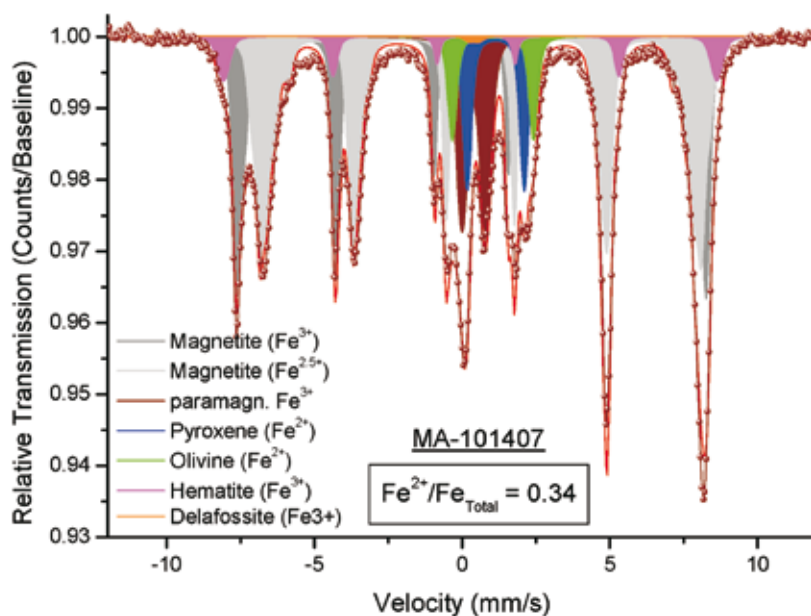

## Discussion

The macroscopically different slags found at the Copper Smelting Site S1 show no significant differences in their chemical composition so it seems that they belong to the same step of the smelting process. Based on the composition of the copper matte inclusions that were found in nearly all the analysed slags, it can be assumed that the slags derive from a particular step of the production process such as the production of raw copper or copper matte. The  $p\text{O}_2$  of  $10^{-9}$  to  $10^{-8}$  atmospheres indicates reducing conditions while smelting. The temperatures during the smelting process were determined to be between  $1150\text{ }^\circ\text{C}$ – $1250\text{ }^\circ\text{C}$ . The results of the Mössbauer spectrometry of the slag lining sample indicate oxidizing conditions in the lower part of the furnaces. Currently, there is no evidence of diachronic change or development in the smelting technology which means that throughout the Middle Bronze Age a most sophisticated metallurgical process was used to produce metallic copper at the site S1 and in this part of the Eastern Alps.

## Acknowledgements

This research was funded by the Austrian Science Fund (FWF), P21242-G19, and the Prehistoric Commission, Austrian Academy of Sciences, Vienna.

## Bibliography

- DOONAN, R. C. P., KLEMM, S., OTTAWAY, B. S., SPERL, G. & WEINEK, H.:  
1996 The east Alpine Bronze Age copper smelting process – Evidence from the Ramsau valley, Eisenerz, Austria. In: Ş. Demirci, A. M. Özer & G. D. Summers (eds.), *Archaeometry '94. The proceedings of the 29<sup>th</sup> International Symposium of Archaeometry*, 18–22.
- HAUPTMANN, A.:  
2000 Reconstructing Ancient Smelting Processes: Applied Mineralogy in Archaeometallurgy. In: D. Rammlmair (ed.), *Applied Mineralogy: in research, economy, technology, ecology and culture. Proceedings of the Sixth International Congress on Applied Mineralogy*, Göttingen, Germany, 17–19 July 2000, 29–31.
- KLEMM, S.:  
2003 Montanarchäologie in den Eisenerzer Alpen, Steiermark – Archäologische und naturwissenschaftliche Untersuchungen zum prähistorischen Kupferbergbau in der Eisenerzer Ramsau. Mit Beiträgen von J. Resch †, H. Weinek, H. Proske, B. Emmerer, E. Steinlechner, P. Trinkaus, W. Gössler, R. Drescher-Schneider. *Mitteilungen der Prähistorischen Kommission* 50, Wien.  
2006 Die Erforschung der prähistorischen Kupfergewinnung in den Eisenerzer Alpen 1955–2005. *res montanarum* 38, 26–36.  
2010 Bronze Age Copper Mining – Landscape Conditions and Land-Use in the Eisenerzer Alps, Styria (Austria). In: P. Anreiter, G. Goldenberg, K. Hanke, R. Krause, W. Leitner, F. Mathis, K. Nicolussi, K. Oeggel, E. Pernicka, M. Prast, J. Schibler, I. Schneider, H. Stadler, T. Stöllner, G. Tomedi & P. Tropper (eds.), *Mining in European History and its Impact on Environment and Human Societies – Proceedings for the 1<sup>st</sup> Mining in European History-Conference of the SFB-HIMAT*, 12–15 November 2009, Innsbruck, 271–276.  
in preparation Der bronzezeitliche Kupferschmelzplatz S1 in der Eisenerzer Ramsau, Steiermark. *Mitteilungen der Prähistorischen Kommission*, Wien.



KLEMM, S., NELLE, O., GRABNER, M., GEIHOFFER, D. & SCHNEPP, E.:

2005 Interdisziplinäre Untersuchungen von Kohlstätten aus Mittelalter und Neuzeit in der Eisenerzer Ramsau, Steiermark. *Archaeologia Austriaca* 89, 2005, 269–329.

MOESTA, H., SCHNAU-ROTH, G. & WAGNER, H.-G.:

1984 Mößbauer-Studien zu bronzezeitlichen Kupferhüttenprozessen. I. Schlacken, besonders der ostalpinen Kupfertechnik. *Berliner Beiträge zur Archäometrie* 9, 95–112.

MOESTA, H., RÜFFLER, R. & SCHNAU-ROTH, G.:

1989 Zur Verfahrenstechnik der bronzezeitlichen Kupferhütten am Mitterberg. Mößbauer- und mikroskopische Studien. In: A. Hauptmann, E. Pernicka & G. A. Wagner (eds.), *Archäometallurgie der Alten Welt – Beiträge zum Internationalen Symposium "Old World Archaeometallurgy"*, Heidelberg 1987 (Der Anschnitt, Beiheft 7), 141–153.

MUAN, A.:

1955 Phase Equilibria in the System  $\text{FeO-Fe}_2\text{O}_3\text{-SiO}_2$ . *Journal of Metals* 7/9, 965–976.