



Strathprints Institutional Repository

Barbera, D. and Chen, H.F. and Liu, Y.H. (2015) On the creep fatigue behavior of Metal Matrix Composites. Procedia Engineering, 130. pp. 1121-1136. ISSN 1877-7058 , <http://dx.doi.org/10.1016/j.proeng.2015.12.277>

This version is available at <http://strathprints.strath.ac.uk/55358/>

Strathprints is designed to allow users to access the research output of the University of Strathclyde. Unless otherwise explicitly stated on the manuscript, Copyright © and Moral Rights for the papers on this site are retained by the individual authors and/or other copyright owners. Please check the manuscript for details of any other licences that may have been applied. You may not engage in further distribution of the material for any profitmaking activities or any commercial gain. You may freely distribute both the url (<http://strathprints.strath.ac.uk/>) and the content of this paper for research or private study, educational, or not-for-profit purposes without prior permission or charge.

Any correspondence concerning this service should be sent to Strathprints administrator: strathprints@strath.ac.uk



14th International Conference on Pressure Vessel Technology

On the Creep Fatigue Behavior of Metal Matrix Composites

D. Barbera^a, H.F. Chen^{a,*}, Y.H. Liu^b

^a*Department of Mechanical & Aerospace Engineering, University of Strathclyde, Montrose Street 76, Glasgow, G1 1XJ, UK*

^b*Department of Engineering Mechanics, Tsinghua University, Beijing, 100084, China*

Abstract

The mechanical behaviour of Metal Matrix Composites (MMCs) subjected to a high temperature and cyclic load condition is difficult to understand. The significantly differing coefficients of thermal expansion between ceramic and metal give rise to micro thermal stresses. Their performance under varying load and high temperature is complex and inconsistent, where fatigue and creep damages become the main failures of MMCs. To improve current understanding of the relationship between creep fatigue interaction of MMCs, the history of thermal and mechanical loading, and the creep dwell period, a highly accurate but robust direct simulation technique on the basis of the Linear Matching Method (LMM) framework has been proposed in this paper, and been applied to model the fatigue and creep behaviour of MMCs. A homogenised FE model is considered in all analyses, which consist of continuous silicon carbide fibres embedded in a square 2024T3 aluminium alloy matrix array. Various factors that affect creep and fatigue behaviours of composites are analysed and discussed, including effects of the applied load level, dwell period and temperature on the MMC's performance. The effects of reversed plasticity on stress relaxation and creep deformation of MMC are investigated, and the behaviours of cyclically enhanced creep and elastic follow-up are presented. The applicability and accuracy of the proposed direct method has also been verified by the detailed step-by-step analysis via Abaqus.

© 2015 The Authors. Published by Elsevier Ltd. This is an open access article under the CC BY-NC-ND license

(<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

Peer-review under responsibility of the organizing committee of ICPVT-14

Keywords: Linear Matching Method (LMM); Creep; Fatigue; Cyclic Plasticity; Metal Matrix Composite (MMC)

1. Introduction

A Metal Matrix Composite (MMC) is composite material with at least two constituent parts, one being a metal. Due to the property of higher strength and lighter weight, MMCs have been applied to a wide range of engineering

* Corresponding author. Tel.: +44-141-548- 2036.

E-mail address: haofeng.chen@strath.ac.uk

components, such as automotive components including disc brakes and driveshaft, aircraft components, space systems, and explosion engine components. However, there are many important aspects, which cannot be underestimated especially when high-temperatures are considered. When operating conditions involve high temperatures and low frequency load, time-dependant creep behaviour dramatically affects the life time of the MMCs. The previously mentioned advantages are seriously downsized by creep behaviour, thermal fatigue, manufacturing processes and environment problems like oxidation [1]. Especially creep fatigue behaviour becomes an area of research interest, due to the lack of a unified and universal method to assess it, although different standard codes were developed for the assessment of creep fatigue life of high temperature component, including ASME BPV code and UK R5 [2, 3].

When creep is present, the structure's response to a cyclic loading condition changes dramatically [4-6], with respect to the low temperature case. Due to the induced residual stresses by creep and plasticity, a closed stress strain cycle may be formed when the reverse plastic strains completely recover the inelastic strain created during loading and creep dwell periods. With this situation, the lifetime of the MMCs is dominated by the combined damages from cyclically enhanced creep and increased fatigue by the stress relaxation during the dwell period. Alternatively, the hysteresis loop may become non-closed if the creep strains become too large for the reverse plastic strains to recover or vice versa. This leads to a critical failure mechanism called creep ratcheting, which is similar to the plastic ratcheting, for both the inelastic strain will be accumulated during each load cycle. However, the accumulation of inelastic strain for creep ratcheting is driven by either the creep strain or stress relaxation during the dwell period. In order to evaluate creep fatigue interactions and combined damages of MMCs under cyclic load and high temperature condition, various factors that affect creep and fatigue behaviours of composites need to be investigated, including effects of the applied cyclic load level, dwell period and temperature on the MMC's performance.

Numerical simulations and modelling of fibre or particle reinforced aluminium based MMC have been performed by many researchers [7-15], in particular for the low cycle fatigue damage due to the cyclic plasticity, and creep rupture under high temperature condition. Traditional Finite Element Analysis was adopted, using for each case the most convenient material model, able to fit the experimental results. The micromechanical model was also used to study the size effect of fibre or particle on the MMC response. The Linear Matching Method (LMM), as a powerful Direct Method for the shakedown and ratchet analysis, has been used to investigate the shakedown and ratchetting response of fibre [16] or particle [17] reinforced MMC. However very little research focused on the creep fatigue interaction of MMC on a numerical prospective, and great efforts are necessary when simulating different interacting mechanisms.

The LMM has been recently extended for the evaluation of fatigue creep interaction and validated by [5, 6] and further used for a more practical application, i.e. creep fatigue life assessment of weldment [16-18]. But despite this no study on creep fatigue interaction of MMCs was performed by using the LMM. Therefore, the aim of this paper is to adopt the latest extension of the LMM [6] to evaluate the steady state cycle response of a silicon carbide fibre reinforced 2024T3 aluminium alloy based MMC, subjected to a cyclic thermal and mechanical load with a creep dwell between the loading and unloading phase.

2. Numerical Procedures

2.1. General overview of the thermo-mechanical cyclic problem

Consider an Elastic Perfectly Plastic (EPP) body with a volume V and a surface S , which is subjected to a general cyclic load condition. On such body volume is applied a cycling temperature $\lambda_\theta\theta(x, t)$ instead on the surface a constant load $\lambda_p P(x, t)$ acting over part of the structure's surface S_T . The remaining surface is constrained to have no displacement. The time variation considered over a typical cycle is $0 \leq t \leq \Delta t$. Corresponding to these loading histories there exists a linear elastic stress history:

$$\hat{\sigma}_{ij}^e(x, t) = \lambda_\theta \hat{\sigma}_{ij}^\theta(x, t) + \lambda_p \hat{\sigma}_{ij}^p(x, t) \quad (1)$$

where $\hat{\sigma}_{ij}^\theta$ and $\hat{\sigma}_{ij}^p$ denotes the varying elastic stresses due to $\theta(x, t)$ and $P(x, t)$, respectively. By selecting the proper values for λ_θ and λ_p a whole class of loading histories can be considered. The general stress field for the cyclic problem involves three different components, the elastic, the constant and the changing residual stress fields.

$$\sigma_{ij}(x, t) = \hat{\sigma}_{ij}^e(x, t) + \bar{\rho}_{ij}(x) + \rho_{ij}^r(x, t) \tag{2}$$

The history ρ_{ij}^r is the change in the residual stress during the cycle and must be zero at both the start and end of each load cycle, so that the stress and strain rate histories are asymptotic to the cyclic state.

2.2. An Extended LMM Direct Steady Cycle Analysis considering creep

In the present work an extended procedure of the LMM Direct Steady Cycle Analysis (DSCA) is adopted to evaluate the low cycle fatigue response with creep dwell. As in other works the LMM procedure requires as input a series of linear elastic solutions, generated at discrete time points within the cycle where a significant stress range occurs and hence the most relevant plastic strain. Such strategy is quite significant in terms of efficiency, because it saves computing time by targeting the steady state cycle directly and neglecting insignificant loading conditions which are assumed to lie in the von Mises yield surface, comparing with other cycle-by-cycle analysis methods which must consider the entire load history.

The aim of this extended DSCA procedure is to calculate the cyclic stress history at the steady state due to the accumulation of the residual stress field by either plastic or creep responses. The associated inelastic plastic or creep strains are also evaluated for the steady state load cycle. The extended DSCA procedure is based on a series of iterative cycles which are defined as $m = 1, 2 \dots M$. Within each iterative sub-cycle, there will be a series of increments N , corresponding to each time points within the cycle ranging from $n = 1, 2 \dots N$. Each individual varying residual stress $\Delta\rho_{ij}^r(x, t_n)_m$ associated with each elastic solution $\hat{\sigma}_{ij}^e(x, t_n)$ at sub-cycle m will be calculated by the extended DSCA procedure in an iteratively way [5-6]. Upon reaching a converged solution, the constant residual stress term from equation (2) can be determined by

$$\bar{\rho}_{ij}(x) = \sum_{m=1}^M \sum_{n=1}^N \Delta\rho_{ij}^r(x, t_n)_m \tag{3}$$

The accumulated residual stress for n^{th} load instance at m^{th} cycle of iterations can be defined as;

$$\rho_{ij}^r(x, t_n)_m = \sum_{k=1}^{m-1} \sum_{n=1}^N \Delta\rho_{ij}^r(x, t_n)_k + \sum_{k=1}^n \Delta\rho_{ij}^r(x, t_k)_m \tag{4}$$

A flowchart of the LMM extended DSCA procedure is presented in Fig. 1, which shows how to evaluate steady state plastic and creep behaviors of structures in an iterative way.

For the load instance t_n without creep dwell period, the plastic strain amplitude $\Delta\varepsilon_{ij}^p(x, t_n)$ can be calculated by;

$$\Delta\varepsilon_{ij}^p(x, t_n) = \frac{1}{2\bar{\mu}(x, t_n)} \left[\hat{\sigma}_{ij}^e(x, t_n)' + \rho_{ij}^r(x, t_n)' \right] \tag{5}$$

where notation (') refers to the deviator component of stresses and $\bar{\mu}$ is the iterative shear modulus [6]. When adopting the Ramberg-Osgood (RO) material model, this plastic strain amplitude can be used to update the iterative yield stress. For the load instance with creep dwell period Δt , the effective creep strain $\Delta\bar{\varepsilon}^c$ can be calculated by

equation (6) when considering a time hardening creep constitutive equation (17) in [6].

$$\Delta \bar{\epsilon}^c = \frac{B(n-1)\Delta t^{m+1}(\bar{\sigma}_s - \bar{\sigma}_c)}{\left(\frac{1}{\bar{\sigma}_c^{n-1}} - \frac{1}{\bar{\sigma}_s^{n-1}}\right)(m+1)} \tag{6}$$

where B , m and n are the creep constants of the material. $\bar{\sigma}_c$ denotes the creep flow stress, which is the sum of the start-of-dwell stress $\bar{\sigma}_s$ and the residual stress $\Delta \rho_{ij}^r$ induced during the dwell period. The creep flow stress can be evaluated by equation (25) in [6], using the information of the creep strain rate at the end of dwell time, which is calculated by equation (23) and (24) in [6].

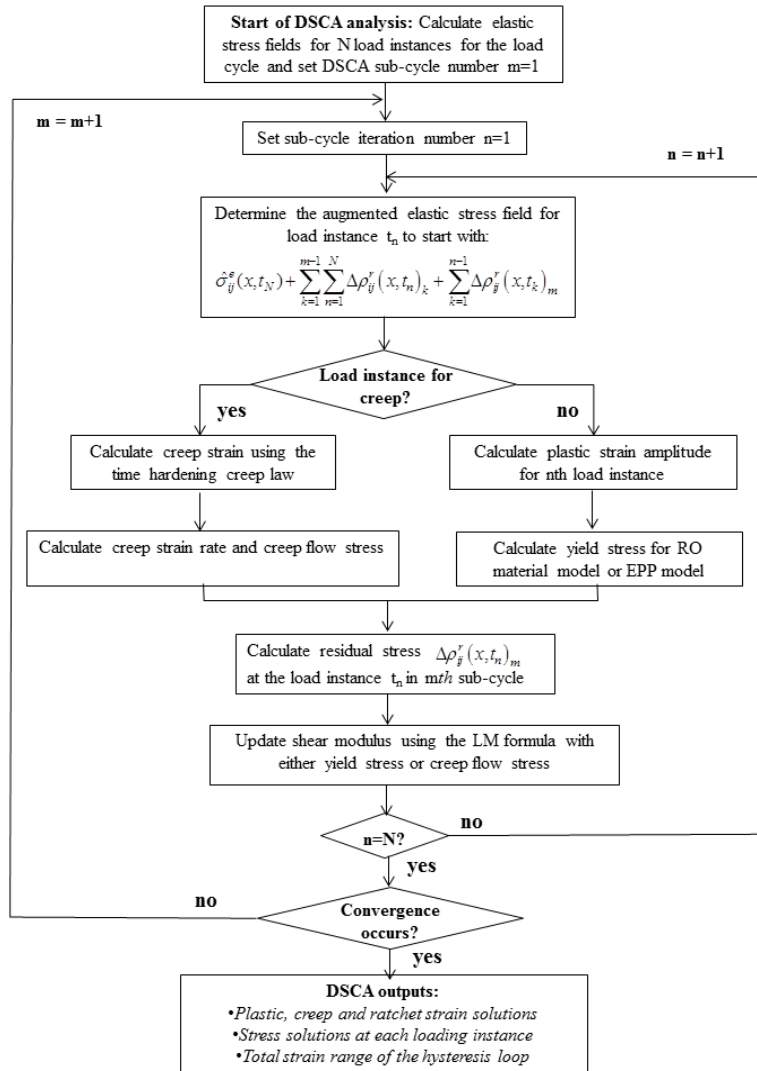


Fig. 1. Flow chart illustrating the LMM extended DSCA numerical procedure.

The calculation of the residual stress $\Delta\rho_{ij}^r$ at each increment is through the solution of a formulated linear problem (10) as described in [6]. When the procedure is completed the residual stress field is obtained and the iterative shear modulus $\bar{\mu}_m(x, t_n)$ is updated at each sub-cycle for each load instance t_n by adopting the linear matching equation;

$$\bar{\mu}_{m+1}(x, t_n) = \bar{\mu}_m(x, t_n) \frac{\sigma_y^R(x, t_n)_m}{\bar{\sigma}(\hat{\sigma}_{ij}^e(x, t_n) + \rho_{ij}^r(x, t_n)_m)} \quad (7)$$

where $\bar{\mu}_m(x, t_n)$ is the iterative shear modulus at the sub-cycle m for n th load instance. $\sigma_y^R(x, t_n)_m$ is the iterative von-Mises yield stress for RO material model or yield stress for the Elastic Perfectly Plastic (EPP) material model at load instance t_n . This yield stress $\sigma_y^R(x, t_n)_m$ will be replaced by creep flow stress $\bar{\sigma}_c$ when considering a load instance involving creep relaxation due to the introduced dwell period. At the end of each sub-cycle, the convergence will be checked. If the convergence criterion is not satisfied a subsequent sub-cycle starts, otherwise the results are outputted to provide all the crucial parameters for creep fatigue assessment.

3. Finite element model

3.1. Metal Matrix Composite numerical model

A long fibre reinforced MMC is analyzed in this work. Due to the periodic dispersion of the fibres in the matrix a unit cell can be identified for the micromechanical modelling. The MMC unit cell is subjected to a constant mechanical load on the right external face and uniform cycling temperature from 0 to θ_0 in the body (Fig. 2). To assess the creep effect on the cyclic behaviour of MMC, a dwell period Δt is introduced at each load cycle as shown in the Fig. 2. Due to geometric symmetries a quarter of the unit cell is adopted with two planes of symmetry applied as boundary conditions, in addition to the plain condition on the two external faces to introduce the periodic constraints.

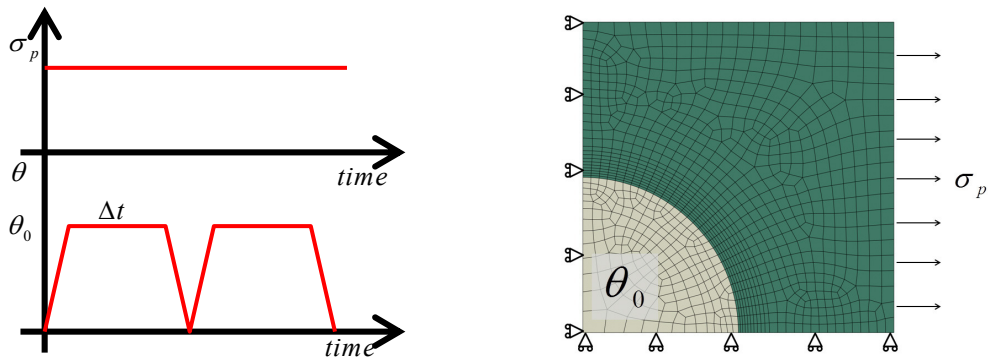


Fig. 2. Finite element model of the MMC unit cell and loading history.

The mesh is composed of 1039 8-node biquadratic plane strain quadrilateral elements, with a reduced integration scheme. The model is composed of two parts, a left corner spherical fibre and a surrounding metal matrix (Fig. 2). Due to the interaction between the fibre and the matrix a refined mesh is adopted in the “Interaction Boundary” where the failure mechanisms are mostly expected.

The material properties for both the matrix and fibre are reported in Table 1. Creep behaviour is evaluated using a time hardening creep constitutive relationship;

$$\dot{\varepsilon}^{cr} = A \cdot \sigma^n \cdot t^m \quad (8)$$

where n is the stress exponent, m is the time exponent for the primary creep stage and A is the power law multiplier. Creep is considered only for the matrix and the data for tensile creep is taken from [19] and reported in Table 2.

Table 1. MMC material properties.

	Al ₂ O ₃ Fibre	Al 2024 T3 Matrix
E [MPa]	450000	73000
ν	0.15	0.33
α	$4E^{-6}$	$2.3E^{-5}$
σ_y [MPa]	10000	345

Table 2. Creep parameters A, n and m for 2024T3 aluminium alloy.

	150°C	175°C	200°C	225°C
A	$0.763 \cdot 10^{-12}$	$3.461 \cdot 10^{-12}$	$4.079 \cdot 10^{-12}$	$5.1186 \cdot 10^{-12}$
n	3.246	3.299	3.395	3.5526
m	-0.303	-0.573	-0.535	-0.5199

In order to verify the LMM results, ABAQUS step-by-step analyses are used and the single operating load cycle consists of three ABAQUS load steps. The first one is a *STATIC step, which represents the loading phase where both temperature and mechanical load are applied. Then a *VISCO step is present to simulate the creep dwell time where mechanical load and temperature are constant. To implement equation (8) during the second step a user defined *CREEP subroutine is necessary, and the time-hardening formulation is adopted. The third step is a *STATIC step representing the unloading phase, where the mechanical load is constant and the temperature goes to zero.

4. Results and discussions

4.1. Effect of creep dwell on hysteresis loop

In order to provide a benchmark to define reasonable cyclic load conditions for the creep fatigue assessment of MMC, a shakedown limit interaction curve was calculated as shown in Fig. 3 by using the LMM shakedown analysis method [20], where a reference uniform cycling temperature range from $0^\circ C$ to θ_0 (where $\theta_0 = 200^\circ C$) is applied over the entire model. The ordinate and abscissa axes in Fig. 3 show the temperature and mechanical load, normalised to the reference temperature θ_0 and yield stress (345MPa) of matrix respectively.

The adopted LMM analysis is also able to estimate the overall failure mechanism of MMC including the most critical location, by showing the contour of cyclic plastic strain range. Fig. 4a shows the cell response to a cyclic load point at (0.7, 1.0) (Fig. 3), whereas Fig. 4b corresponds to the limit load. It is clear from Fig. 4 that the “Interaction Boundary” is the most critical location, and this will be the location where the fatigue and creep damage will accumulate, ultimately initiating cracking in the matrix. The evaluation of creep fatigue behaviour of MMCs is performed by a series of analyses considering six cyclic load points inside the shakedown limit: A₁(0.25,0.875), A₂(0.25,1.125), B₁(0.7, 0.875), B₂(0.7,1.125), C₁(0.5, 0.875) and C₂(0.5,1.125) as shown in Fig. 3. If without creep effect, all these cyclic load points within the shakedown limit should exhibit shakedown behaviour

only. The aim of our analysis is to investigate how cyclic behaviour of MMC changes with creep response due to the introduced high temperature dwell period. In order to understand the creep-fatigue interaction, each load point is evaluated for different dwell times 1, 100, 1000 and 10000 hours, respectively.

Four hysteresis loops are generated and presented in Fig. 5 for cyclic load points A₁ and C₁, where the blue and red line correspond respectively to a dwell time of 1 hour and 100 hours at 175°C. For a dwell time of 1 hour the closed hysteresis loop is present only for A₁, instead for C₁ a small total strain increment is present. Creep affects both cases and enhances the unloading plasticity, but no plastic straining occurs during loading due to the total stress level since it is below the yield. The loop shape changes when a larger dwell time is considered, and non-closed loop behaviour is observable also for A₁. In Fig. 5, the accumulation of total strain is entirely driven by the creep strain. Under such conditions the damage caused by creep is important even for low level primary load as seen for load point A₁.

Figure 6 shows the MMC response to the cyclic load points A₂ and C₂ for different dwell times at 225°C. The load point A₂ with smaller mechanical load also exhibits a closed loop for a 1 hour dwell time (blue line) as the load point A₁ (Fig. 5), but with a larger strain range due to the higher thermal load applied. Conversely load point C₂ with larger mechanical load shows a small creep ratchetting mechanism even for 1 hour dwell time. Furthermore for cyclic load point C₂ a small plastic strain also accumulates during the loading phase. Such behaviour is due to the larger mechanical load and the accumulated residual stresses during the cycle which lead some regions to yield also during the loading phase. For the 100 hours of dwell time both loading points behave in a similar way, where creep ratchetting become the dominant mechanism.

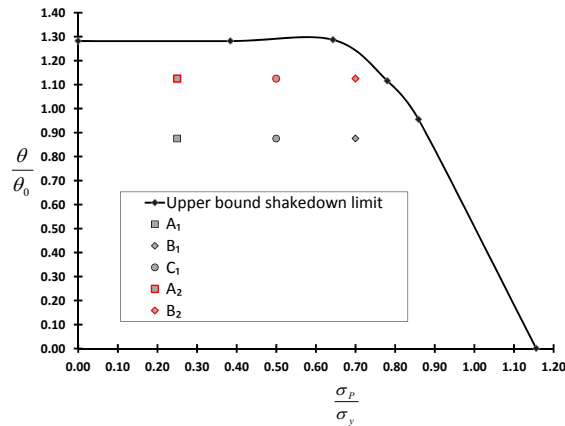


Fig. 3. Shakedown limit for the MMC under constant mechanical load and cycling thermal load.

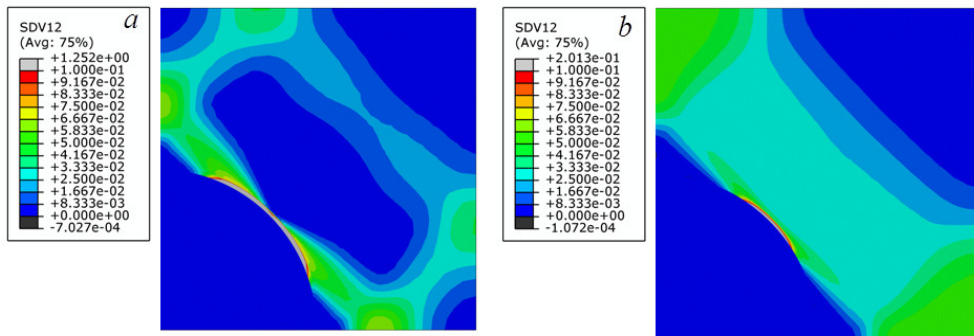


Fig. 4. Effective plastic strains at different cycling load points.

In order to have a complete overview of structure response to such cyclic loading conditions, cyclic load points B_1 and B_2 (Fig. 3) are investigated and the corresponding stress strain responses at the steady state are presented in Fig. 7. For both dwell times, both points B_1 and B_2 show the plastic loading phase and creep ratcheting behaviour due to the very large mechanical load. However point B_2 has a higher strain levels due to the higher temperature of 225°C applied. When the dwell time is increased from 1 hour to 100 hours, creep strain is increased greatly for both load points, and more significant creep ratcheting mechanism is present.

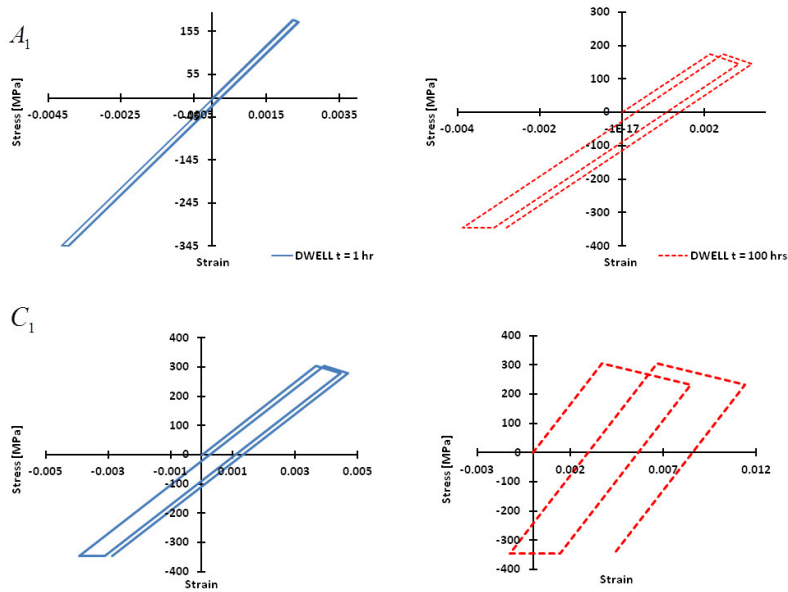


Fig. 5. Stress-strain responses at steady state at location with the maximum plastic strain for different dwell time for load points A_1 and C_1 .

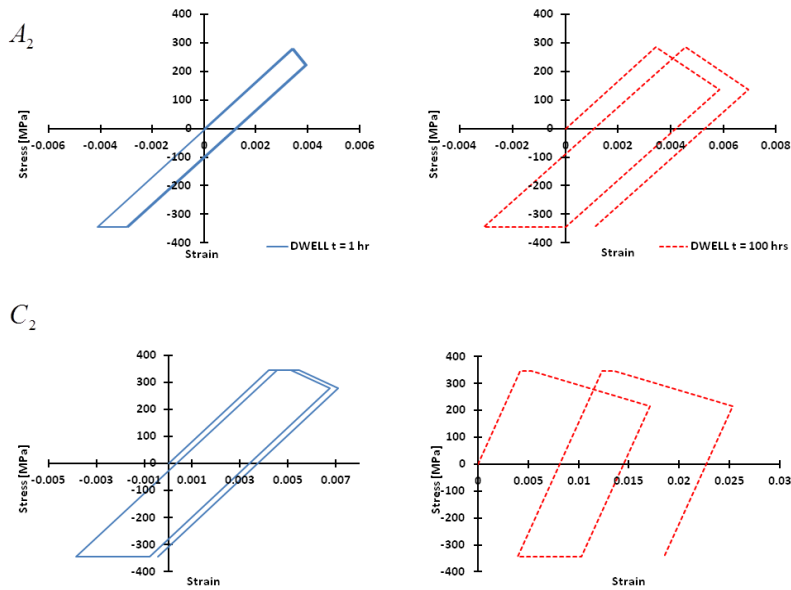


Fig. 6. Response of the steady state stress-strain path at location with the maximum plastic strain for different dwell time for load points A_2 and C_2 .

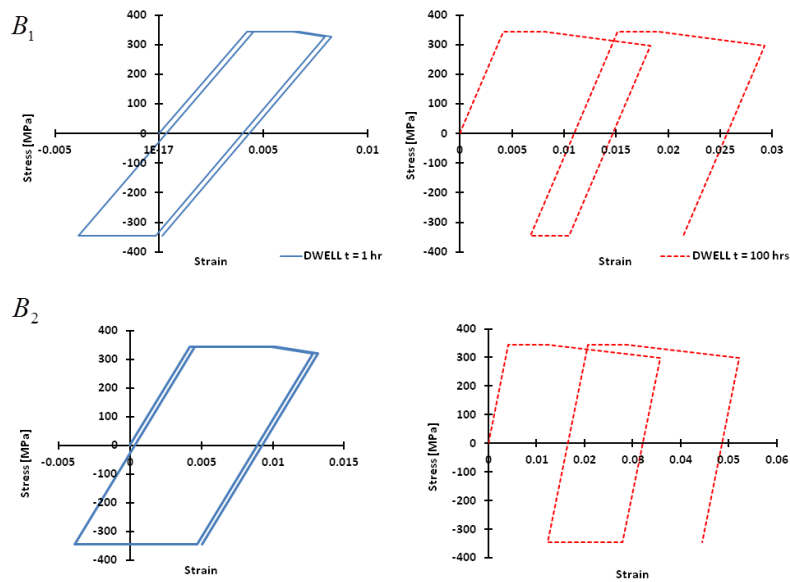


Fig. 7. Response of the steady state stress-strain path at location with the maximum plastic strain for different dwell time for load points B_1 and B_2 .

The detailed effects of different creep dwell times on plastic strains for both cyclic load points B_1 and B_2 are reported in Fig. 8. Fig. 8a and Fig. 8b show the plastic strain range during loading phase for point B_1 and B_2 respectively, which involves a small and localized area in the “*Interaction Boundary*”. When the creep dwell time is increased the plastic region does not increase significantly and still highly localized, but with a greater plastic strain magnitude. For point B_2 with higher temperature of 225°C the plastic region becomes bigger and also slightly increases for longer creep dwell. A similar trend is shown by Fig. 8c and Fig. 8d for cyclic load points B_1 and B_2 respectively, where the plastic strain at unloading phase is reported. Both Figs confirm the major plastic damage occurs at the unloading phase, and involves a quite large area of matrix. The increase of both the dwell time and the thermal load enhances such behavior significantly by dramatically increasing the plastic strain magnitude as shown in Fig. 8c and Fig. 8d. For both load points B_1 and B_2 , the creep ratchetting behavior becomes very significant as it is enhanced by the high level of primary load. Dwell time is also crucial for the cell response to the cyclic load.

All the results confirm that creep ratchetting mechanisms is affected by two key parameters, dwell time and the primary load level. The analyses performed for cyclic load case A1 and A2 showed a closed hysteresis loop. The increase of dwell time drastically changed the MMC response, introducing an evident creep strain accumulation even for such cases. In order to confirm the importance of the primary load on the creep ratchetting behaviour, the pure cyclic thermal load case is investigated, i.e. $\frac{\sigma_p}{\sigma_y} = 0.0$ $\frac{\theta}{\theta_0} = 1.0$.

This loading condition is investigated by considering varying dwell times from 1 hour to a maximum of 10000 hours. The calculated hysteresis loops for different dwell times are shown in Fig. 9. It is evident that when there is no primary load, despite the increase of creep dwell, the secondary thermal load is not capable of causing creep ratchetting in the MMCs. However, the increase of dwell time enhances the creep strain and the stress relaxation during the dwell period and consequentially enhances the plastic behaviour during the unloading phase. This will inevitably increase the total strain range of the closed hysteresis loop, until a limiting state is reached, where all thermal stresses are fully relaxed to zero, no further creep strain is induced, and hence there is no additional enhancement of reverse plasticity during the unloading phase. As presented in Fig. 9, when there is no primary load, the creep strain occurred during the dwell period will be fully recovered by the plastic strain during the unloading phase, leading to a closed hysteresis loop.

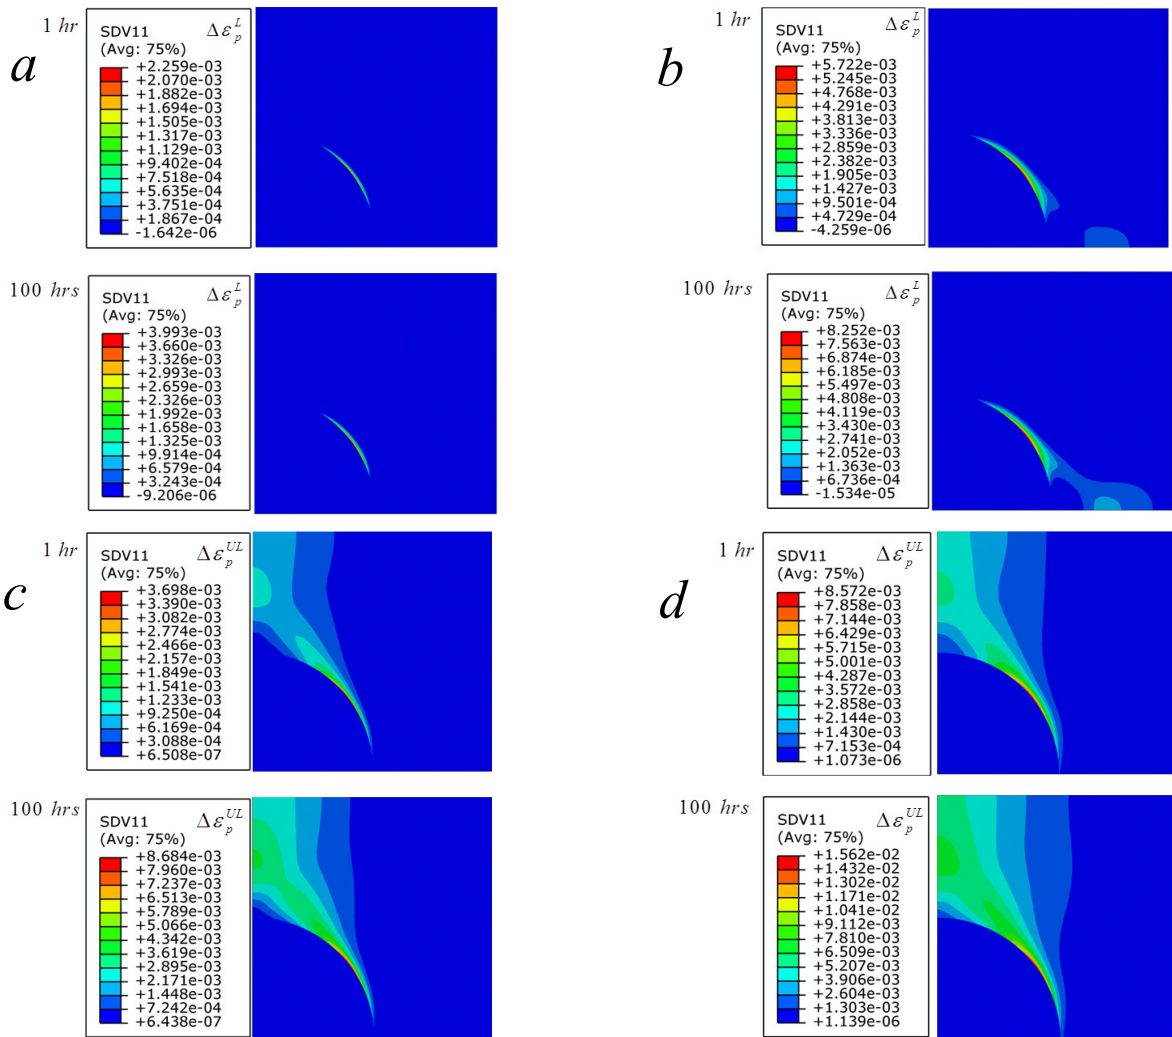


Fig. 8. Effect of dwell time on plastic strain increments at loading and unloading for cyclic load points B₁ and B₂.

In Fig. 10 an overview of the stress fields at the end of creep and unloading phase for different dwell times is presented. Due to the material mismatch, at both loading phases the highest stress of matrix develops around the fibre, starting from the “*Interaction Boundary*”. When the creep dwell is increased, a significant stress relaxation occurs and the affected area becomes larger. Longer dwell time allows wider area to yield during the unloading phase, as shown in Fig. 10. The increase of creep dwell also causes higher plastic strain during unloading, and such mechanism makes the size of the hysteresis loop larger.

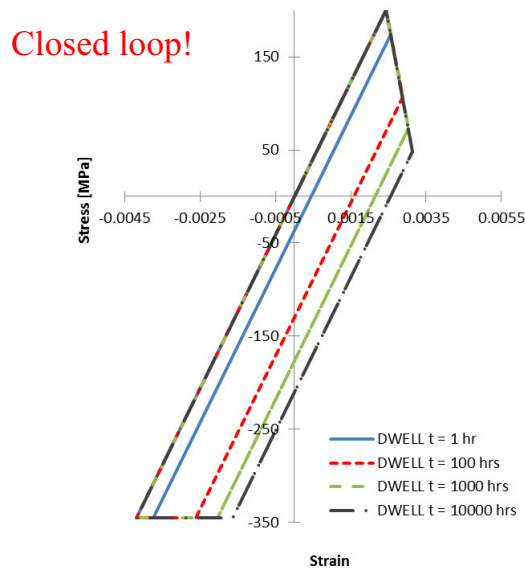


Fig. 9. Response of the steady state stress-strain path at location with the maximum plastic strain for different dwell times.

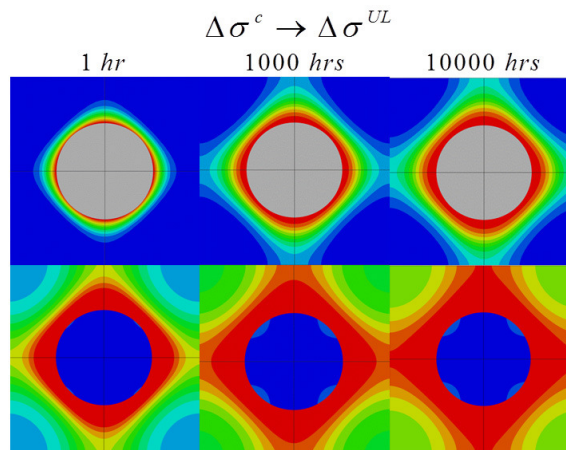


Fig. 10. Effect of dwell time on stress state at the end of creep and unloading phase respectively.

4.2. Effect of creep dwell on hysteresis loop

To further understand the effect of dwell time on the cyclic response of MMC, the plot of magnitudes of maximum plastic strain increments during loading and unloading phases against the applied dwell time is presented in Fig. 11a, and the plot of maximum creep ratchet strain (i.e. the accumulated inelastic strain) per cycle against the applied dwell time is given in Fig. 11b. It can be seen clearly from Fig. 11a that when the applied dwell time is more than 1000 hours, the plastic strain magnitudes at both loading and unloading phases nearly keep unchanged. This behaviour occurs as the creep stress at the end of the dwell period reaches a steady state. By this point the creep stress cannot relax anymore and the plastic strain magnitude during the unloading phase cannot increase with the

further increase of the dwell time. However it is observed from Fig. 11b that the maximum creep ratchet strain almost increases linearly with the dwell time when the applied dwell time is more than 1000 hours. This highlights the effects of creep dwell time on both the shape of hysteresis loop, and the creep-fatigue life of the MMC. For a long dwell time, creep damage dominates and a creep ratchetting mechanism occurs. This highlights the importance of the dwell time for the life assessment of component operating under such loading conditions, even when the operated loading condition is below the shakedown limit.

During the dwell period, both the stress relaxation and creep strain accumulation are observed for MMC. This is related to a phenomenon called elastic follow-up [2], and is typically quantified by an elastic follow up factor Z , defined by the ratio of the creep strain increment to the elastic strain increment during stress relaxation. Under constant displacement loading, the stress relaxation results in no change in the total strain, as creep strain replaces elastic strain with time, where $Z=1$. The elastic follow-up factor is known to be influenced by loading conditions [2, 6], and larger primary loads combined with longer dwell times produce larger Z . For the MMC investigated, the detailed elastic follow up factors at the location of maximum creep strain for different dwell times and 4 considered cyclic load conditions are presented in Table 3. This shows how the magnitude of the primary load affects the Z factor. When the MMC is subjected to a low mechanical load (A_1 A_2) only moderate increases occur when the dwell time is increased, whereas radical changes are observed when the primary load is increased (B_1 and B_2).

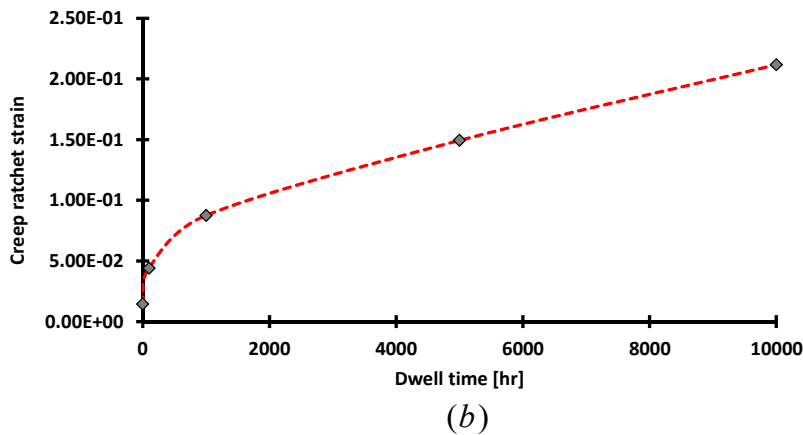
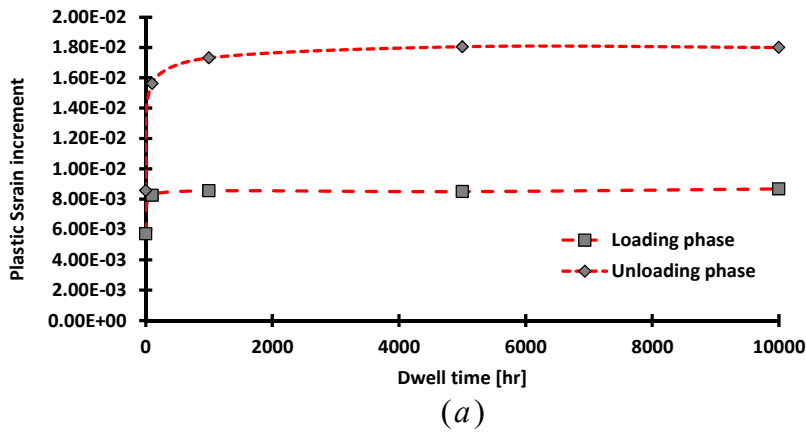


Fig. 11. (a) Plastic strain increments; (b) Creep ratchet strain per cycle against dwell time at cyclic loading point B_2 .

Table 3. Values of elastic follow-up factor at location with maximum creep strain, for different loading conditions and creep dwell times.

Load point	Z			
	Z $\Delta t = 1$	Z $\Delta t = 100$	Z $\Delta t = 1000$	Z $\Delta t = 10000$
A ₁	2.45	2.91	3.80	6.15
B ₁	7.65	22.8	51.8	128
A ₂	1.72	2.35	3.77	8.04
B ₂	11.4	60.4	159	441

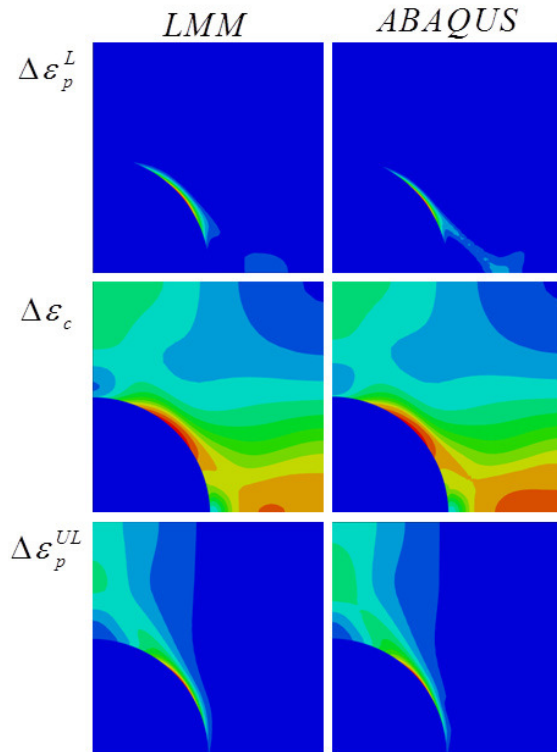


Fig. 12. Comparisons between LMM and ABAQUS step-by-step analysis for strain increments at loading, creep and unloading phase.

Table 4. Comparison between LMM and Step-by-Step Abaqus analyses, for different cyclic loading points.

Cyclic load point	$\Delta \epsilon_p^L$		$\Delta \epsilon_c$		$\Delta \epsilon_p^{UL}$	
	LMM	ABAQUS	LMM	ABAQUS	LMM	ABAQUS
A ₁	0.0	0.0	$2.21E^{-4}$	$2.53E^{-4}$	$1.80E^{-4}$	$2.00E^{-4}$
B ₁	$2.26E^{-3}$	$2.01E^{-3}$	$1.76E^{-3}$	$1.74E^{-3}$	$3.70E^{-3}$	$3.51E^{-3}$
A ₂	0.0	0.0	$1.20E^{-3}$	$1.25E^{-3}$	$1.13E^{-3}$	$1.20E^{-3}$
B ₂	$5.72E^{-3}$	$5.15E^{-3}$	$3.22E^{-3}$	$3.14E^{-3}$	$8.57E^{-3}$	$8.15E^{-3}$

In order to verify the LMM results a direct comparison with the ABAQUS step-by-step analyses is performed. Three quantities are considered in the verification procedure, the creep strain increment ($\Delta \epsilon_c$), the plastic strain increment at loading ($\Delta \epsilon_p^L$) and the plastic strain increment at unloading ($\Delta \epsilon_p^{UL}$). Direct comparisons of contours and magnitudes of these plastic and creep strains obtained by the LMM and ABAQUS step-by-step analyses are given in Fig. 12 and Table 4, respectively, and a perfect agreement is observed. It is evident that the LMM is capable of producing accurate solutions to estimate the cyclic response of MMC to the applied cyclic load condition with creep dwell. Furthermore, it is worth noting that the LMM creep fatigue analysis is much more efficient than the standard ABAQUS step-by-step analysis procedure. Based on a standard PC, the computational CPU cost to solve one cyclic loading case for any the dwell time required by the LMM analysis is approximately 149 seconds (150 total increments), against the 792 seconds (810 total increments) and 1268 seconds (2600 total increments) required by the ABAQUS step-by-step analysis for 1 hour and 10000 hours dwell times respectively. This comparison verifies the efficiency superiority of LMM.

4.3. Further discussion on MMC damaging and response to cyclic load

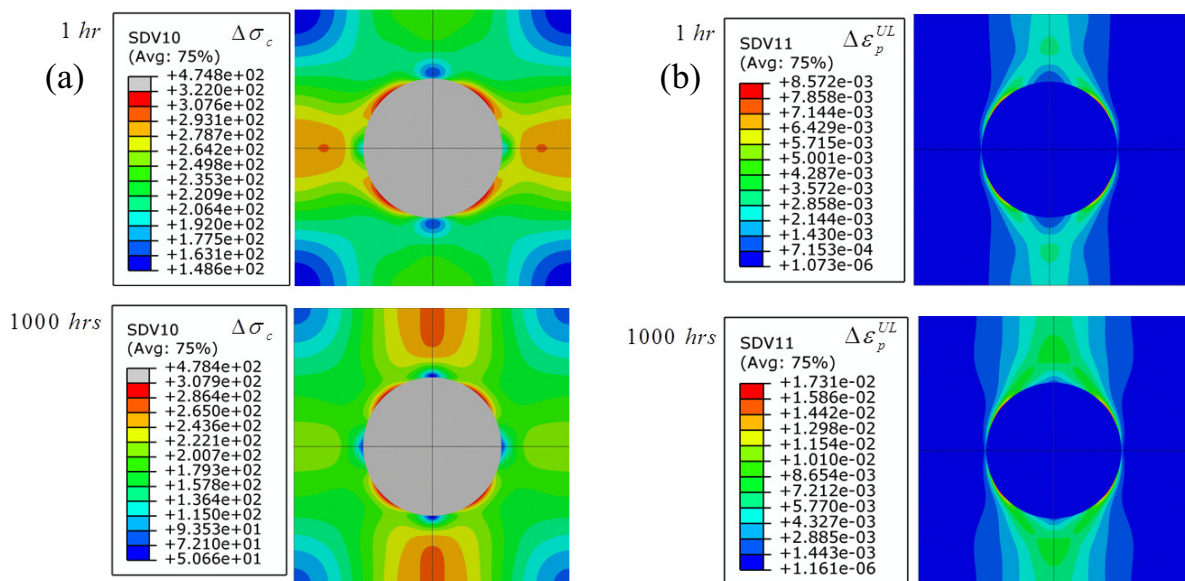


Fig. 13. (a) Effect of dwell time on the stress distribution for the complete unit cell at the end of creep dwell, for cyclic load point B₂; (b) Effect of dwell time on the plastic strain increment of the complete unit cell during unloading phase, for cyclic load point B₂.

Among 6 cyclic loading points shown in Fig. 3, the most critical one is B₂. Hence for this loading point a complete cell view is presented in Fig. 13(a) and Fig. 13(b) for the discussion. In previous sections it is well established that creep dwell time affects dramatically the structure response, due to the stress relaxation and redistribution, which are particularly damaging and responsible for the plasticity during the unloading and loading phase when the primary load level is high enough. Fig. 13a shows the stress distribution at the end of the creep dwell for two cases, 1 hour and 1000 hours of dwell time. The associated residual stress during the creep dwell makes it possible to yield regions which normally don't exhibit a plastic behaviour. This is highlighted by Fig. 13b where the plastic strain increment at unloading phase is reported. Both the plastic strain magnitude and area at unloading phase largely increases by longer dwell times. Due to the transverse direction of the mechanical load, the reinforcement fibre does not improve the tensile strength of MMC significantly under such load condition, which is the most critical load condition the structure may experience. The most dangerous mechanism shows plasticity in both loading and unloading phase. In such condition creep and creep ratchetting become extremely damaging when

the dwell time increases.

5. Conclusions

The work presented in this paper investigates the interactions between fatigue and creep damages of a fibre reinforced MMC subjected to a cyclic temperature and constant mechanical load by using the LMM extended DSCA with micromechanical modelling. The MMC is modelled using an idealised plain strain model, where both matrix and fibre materials are modelled as elastic-perfectly plastic. The time dependant creep behaviour is modelled using the Norton-Bailey relationship.

A detailed study on MMC responses to different cyclic load points within the shakedown limit is performed. The primary load level and dwell time are confirmed to be the two most important parameters for creep-fatigue interaction. When the dwell time is small enough (e.g. 1 hour) a closed hysteresis loop can be observed for a low level of primary load. Conversely when dwell time increases creep ratchetting become significant. The increasing dwell time increases the total strain range, by increasing the plastic strain increment during unloading phase, due to the stress relaxation during the creep dwell period. Once the steady state stress is reached at the end of the creep dwell no more increase of plastic strain increment is possible. Typically for a long dwell time (more than 1000 hours), creep ratchetting is present with an inelastic strain accumulation at each cycle, the magnitude of which increase almost linearly with the dwell time. When the primary load is zero, creep ratchetting does not take place for any thermal load level and dwell times. In addition to these results a discussion on the failure mechanisms is presented for the most critical cyclic load point (B₂), presenting a unit cell full view. The main contribution to the MMC damaging is the stress relaxation and redistribution during the dwell period, which makes it possible to yield regions which normally don't exhibit a plastic behaviour without the creep dwell. Overall, the life and integrity of MMC is reduced by the combined action of creep and fatigue damages, as well as the accumulated inelastic strain per cycle due to the creep ratchetting mechanism.

The accuracy and efficiency of the LMM extended DSCA for the evaluation of cyclic plastic creep behaviour of MMC has been confirmed by direct comparisons with a set of ABAQUS step-by-step analyses. All the comparisons demonstrate that LMM is capable of providing accurate solutions, with reduced computational efforts.

Acknowledgements

The authors gratefully acknowledge the support of the University of Strathclyde, the Royal Academy of Engineering, the Royal Society (IE140842), the International Cooperation and Exchange Project NSFC (11511130057) and the National Science Foundation for Distinguished Young Scholars of China (11325211) during the course of this work. All solutions provided in the work presented have been obtained using the finite element software ABAQUS.

References

- [1] Manson, S. and Halford, G.R., Fatigue and durability of metals at high temperatures. 2009: ASM International.
- [2] Ainsworth, R., R5: Assessment procedure for the high temperature response of structures. British Energy Generation Ltd, 2003. 3.
- [3] American Society of Mechanical Engineers, B. and C. Pressure Vessel, ASME boiler & pressure vessel code : an international code. 2007: New York, N.Y. : American Society of Mechanical Engineers.
- [4] Bree, J., Incremental growth due to creep and plastic yielding of thin tubes subjected to internal pressure and cyclic thermal stresses. The Journal of Strain Analysis for Engineering Design, 1968. 3(2): p. 122-127.
- [5] Chen, H. and Ponter, A.R., Linear Matching Method on the evaluation of plastic and creep behaviours for bodies subjected to cyclic thermal and mechanical loading. International Journal for Numerical Methods in Engineering, 2006. 68(1): p. 13-32.
- [6] Chen, W. and Ure, J., A Direct Method on the Evaluation of Cyclic Steady State of Structures With Creep Effect. Journal of Pressure Vessel Technology-Transactions of the ASME, 2014. 136(6).
- [7] Fleming, W.J. and Temis, J.M., Numerical simulation of cyclic plasticity and damage of an aluminium metal matrix composite with particulate SiC inclusions. International Journal of Fatigue, 2002. 24(10): p. 1079-1088.

- [8] Qing, H., Automatic generation of 2D micromechanical finite element model of silicon-carbide/aluminum metal matrix composites: Effects of the boundary conditions. *Materials & Design*, 2013. 44(0): p. 446-453.
- [9] Qing, H., 2D micromechanical analysis of SiC/Al metal matrix composites under tensile, shear and combined tensile/shear loads. *Materials & Design*, 2013. 51(0): p. 438-447.
- [10] Eehle, R. and Voyiadjis, G.Z., Simulation of damage evolution in a uni-directional titanium matrix composite subjected to high cycle fatigue. *International Journal of Fatigue*, 1999. 21(9): p. 909-923.
- [11] Schneider, Y., et al., Numerical and experimental investigations of the global and local behaviour of an Al(6061)/Al₂O₃ metal matrix composite under low cycle fatigue. *Procedia Engineering*, 2011. 10(0): p. 1515-1520.
- [12] Yuan, M.N., et al., Numerical analysis of the stress-strain distributions in the particle reinforced metal matrix composite SiC/6064Al. *Materials & Design*, 2012. 38(0): p. 1-6.
- [13] Guo, S., Kang, G. and Zhang, J., Meso-mechanical constitutive model for ratchetting of particle-reinforced metal matrix composites. *International Journal of Plasticity*, 2011. 27(12): p. 1896-1915.
- [14] Baxeivanis, T. and Charalambakis, N., A micromechanically based model for damage-enhanced creep-rupture in continuous fiber-reinforced ceramic matrix composites. *Mechanics of Materials*, 2010. 42(5): p. 570-580.
- [15] Pandorf, R. and Broeckmann, C., Numerical simulation of matrix damage in aluminium based metal matrix composites. *Computational Materials Science*, 1998. 13(1-3): p. 103-107.
- [16] Gorash, Y. and Chen, H., A parametric study on creep-fatigue endurance of welded joints. *PAMM*, 2013. 13(1): p. 73-74.
- [17] Gorash, Y. and Chen, H., On creep-fatigue endurance of TIG-dressed weldments using the linear matching method. *Engineering Failure Analysis*, 2013. 34(0): p. 308-323.
- [18] Gorash, Y. and Chen, H., Creep-fatigue life assessment of cruciform weldments using the linear matching method. *International Journal of Pressure Vessels and Piping*, 2013. 104(0): p. 1-13.
- [19] Maximov, J.T., et al., Modeling of strain hardening and creep behaviour of 2024T3 aluminium alloy at room and high temperatures. *Computational Materials Science*, 2014. 83(0): p. 381-393.
- [20] Chen, H., Lower and Upper Bound Shakedown Analysis of Structures with Temperature-Dependent Yield Stress, *Journal of Pressure Vessel Technology*, Transactions of the ASME, v 132, Feb 2010, p 1-8.