

AL LM6 HOLLOW CYLINDER FABRICATED USING CENTRIFUGAL CASTING

Saifulnizan Jamian¹, Safwan Yutiman² and Haffidzudin Hehsan³

¹Department of Engineering Mechanics, Universiti Tun Hussein Onn Malaysia, Batu Pahat, Malaysia, saifulnz@uthm.edu.my

²Faculty of Mechanical Engineering & Manufacturing, Universiti Tun Hussein Onn Malaysia, Batu Pahat, Malaysia, dd100008@siswa.uthm.edu.my

³Department of Mechanical Engineering Technology, Universiti Tun Hussein Onn Malaysia, Batu Pahat, Malaysia, haffiz@uthm.edu.my

ABSTRACT

The main purpose of this study was to investigate the silicon (Si) particles distribution of Al LM6 cylinder produced by centrifugal casting method. Al LM6 cylinder fabrication started by melting Al LM6 ingots. The melt is then poured into a rotating mould with constant speed of 1700 rpm (100 times of gravity value, 100G) at room temperature. After five hours left to freeze, LM6 Al cylinder is removed from the mold. The result is an Al LM6 hollow cylinder with the outer and inner diameter of 60 and 20 mm, respectively and the thickness of 35 mm. The temperatures of the molten ingot used in this study were 690, 710 and 725°C. The microstructure differences due to different melting temperatures observed using an optical microscope (OM). Microstructural observations show that the Si particles content are almost the same on the inside, center and outside the specimen. However, the sizes of Si particles in these three parts are different. The particle size of the specimens has a size larger than in the middle and the outside. The difference in size is due to the low density of Si particles than Al and the expansion of Si particles due to rapid melt cooling rate in the mold during centrifugal casting process. The three specimens with different values of melt temperature shows different size Si particles. The difference of Si particle size and distribution expected will influences the mechanical properties of Al LM6 fabricated.

Keywords: Functionally Graded Material (FGM), Centrifugal Casting, Aluminum (Al), Silicon (Si)

INTRODUCTION

Al LM6 an engineering material that is widely used in related industries as aerospace, automotive, construction and many others because the properties of natural light, good durability, high strength and high corrosion resistance either in the atmosphere normal or in the water. These alloys are usually very difficult to machine due to high Si content and tendency to distort and eventually cause wear on the tool quickly.

In addition to having high corrosion properties, Al LM6 also has good ductility, casting ability and fluidity. Good ductility alloy able to produce the desired casting form. The good fluidity makes it enables poured into a thin mold, complex parts. Indirectly, this allows the alloy produces a larger surface and free of any defects. Among the casting process in accordance with the use of Al LM6 is sand casting, gravity and centrifugal casting.

In this study, the centrifugal casting method on the horizontal axis is used to produce a hollow cylindrical Al LM6. Casting of this type is typically used to produce hollow products such as bearings, bushings and disc cutter. Product hollow cylinder produced by this method will usually have a precise result; the surface is smooth and free from any defect in the inner and outer diameter.

Chirita et al [1] discusses the advantages of using a centrifugal casting device for the production of structural components of Al-Si alloys. The study focused on the mechanical properties of the material produced by centrifugal casting technique compared to the mechanical properties of materials resulting from traditional gravity casting techniques. As a subject of study, an aluminum alloy AS12UN were used. From the results of experiments conducted, it was found that the use of a centrifugal casting capacity to increase by 35% breaking strength, breaking strain of 160% and a Young's modulus of 18%. This clearly shows that the production of mechanical

properties by using centrifugal casting is better than the traditional gravity casting techniques. The study also showed a difference of mechanical properties of both types of castings are due to parameters of centrifugal force, vibration and fluid dynamics.

Watanabe et al [2] have analyzed the formation of magnesium alloy cylinder ZK60A (Mg-Zn-5.5 mass% 0.6 mass% Zr) functionally graded materials (FGM) by using a centrifugal casting method. Centrifugal force used was 40, 80 and 120 G. cylinders to generate the geometry of length and diameter, respectively 18 and 13 mm. ZK60A material is then placed in a mold heated at 680 °C for the melting process. During this melting process, centrifugal force is reacted with the resulting melt temperature to form the desired cylinder. Cylinder cooling rate is at 0.05 °C / s. Results of the tests show that the microstructure no change in the microstructure of the G set. However, due to the use of EDX to study the microstructure gradient showed Zn concentration of particles in each area is almost the same. While Zr particles only exist on the outer wall of the cylinder. The factors that cause this to happen is due to the difference in density between the particle and the direction of centrifugal force. The higher the density of the particles, the easier it is for the dispersed particles to the top of the outer wall of the cylinder.

Based on previous studies [1-6], it can be concluded that the tool centrifugal casting foundry is a very efficient tool for the formation of a hollow cylinder. In addition, the centrifugal casting process is more effective for materials with different density or the density of the metal in the alloy of the same. It can also produce good mechanical properties. In addition, factors that affect the mechanical properties of the centrifugal force, the melt temperature, viscosity and density of the metal particles.

In this study, casting method, a cylindrical mold connected to a shaft at a set speed. Next, the molten metal is poured into a rotating mold. The molten metal flow is uniformly distributed throughout the mold cavity. The Al LM6 cylindrical shape formed is due to the centrifugal force. The mold will be kept rotating for a period up to the solidification process is complete. The research was conducted to study the microstructure and mechanical properties of the hollow cylindrical Al LM6 produced through centrifugal casting process. The difference in the temperature of the melt of 690, 710 and 725 ° C used as a parameter for this study in which the temperature difference will cause differences in terms of changes in hardness and strength along the radius of the cylinder. Furthermore, it will also affects the microstructure of the cylinder produced.

The process of forming a hollow cylinder started to melt Al LM6 LM6 Al ingot in the smelter. Al molten LM6 then poured into a mold which rotates at the speed set at room temperature. Al LM6 cylinder is removed from the mold after 5 hours to ensure that it solidifies and cools. The result is a hollow cylinder with a diameter of Al LM6 inside each 60dan 40 mm with a thickness of 20 mm.

METHODOLOGY

The material used for centrifugal casting was an Al LM6 with the following alloying composition: Magnesium- 0.27%, Manganese-0.23%, Silicon- (10.50-13.00)%, Zinc-0.852%, Nickel-0.1% and Tin-0.2%. Figure-1 shows the schematic diagram of the centrifugal casting setup, which consists mild steel cylindrical mold that connected to the shaft of a DC motor. The speed of the rotating mold is 1700rpm and the flow of molten metal into the mold is confined in the horizontally oriented, axially rotating cylindrical mold. The procedure started by cutting the Al LM6 ingot into a smaller size to make it melting easier inside the induction furnace. The ingot with approx. mass of 160g material was melted at 690, 710, 715°C and poured into the rotating mold which rotated by

the speed of centrifugal force value 100G (100 times of gravity).

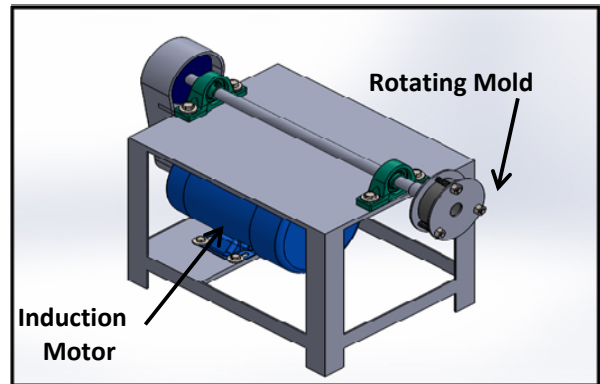


Figure-1. Schematic of centrifugal casting setup.

The dimensions of the castings made are 60mm for outer diameter, 40mm inner diameter, 35mm length and wall thickness 20mm. The centrifugal casting part shown in Figure-2 are then cut by using CNC wire cut in order to have specimens of 10mm height and 10mm length for microstructural observation. The microstructural observation is carried out using Optical Microscope (OM) in order for measurement of a volume fraction of silicon particles in aluminium Al LM6. The OM samples were grinded, polished and eroded by mixed acid-water solution (5%l HF and 95% H₂O). The centrifugal casting conditions of each Al LM6 cylinder fabricated are listed in Table 1.

Table 1: Parameter of centrifugal casting process

Specimen No.	Material/mass	Centrifugal force	Melting Temperature (°C)
1	Al LM6 / 160g	100G (1700rpm)	690
2			710
3			725

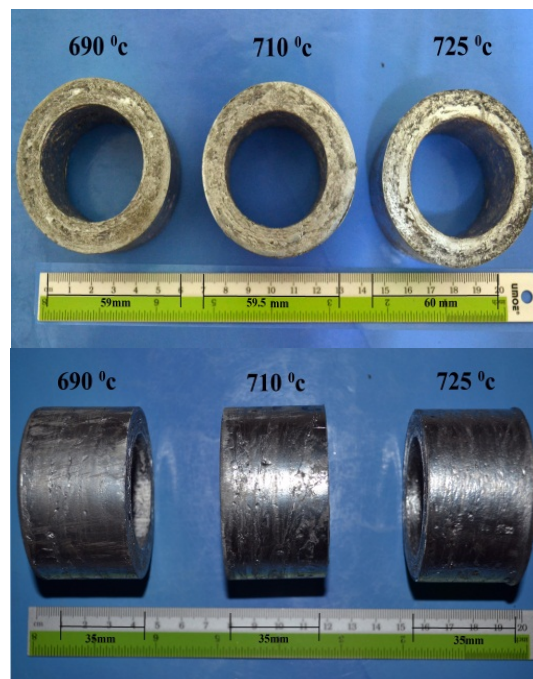


Figure-2. The Al LM6 cylinder fabricated.

RESULTS AND DISCUSSIONS

Figure-2 shows the Al LM6 cylinders fabricated at different melting temperature. There are little different in dimensions. Outer and inner diameter of the casting which melting temperature 690°C are 59 and 39mm, respectively. For the casting at melting temperature of 710 °C and 725°C, the outer diameter is 59.5 and 60mm, respectively. Meanwhile, for the inner diameter are 40 and 41mm, respectively. Besides that, the height of each casting is same, which is 35mm. The factors that causes the geometry size not constant is the volume of Al LM6 which is predetermined is not entirely successful poured

into the mold. Moreover, the mold which not preheated first also causes the differences in geometry size.

Figures-3 to 5 show the physical appearances of Al LM6 cylinders fabricated. It can be seen from these the figures, there are casting which having defects on its surface. Figures-3(a), 4(a) and 5(a) show the hot tear defects which concentrated on the inner surface of the casting. This kind of defect is due to the metal shrinkage inside the mold. In addition, there is also a banding defect on the outer surface as seen in Figures-3(c) and 4(c). This is caused by the motor introduced vibration during casting.

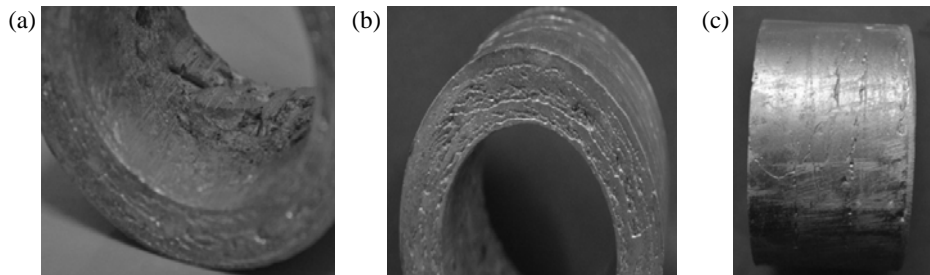


Figure-3. Physical properties of casting with temperature 690 °C. (a) Inner surface; (b) side surface; (c) outer surface

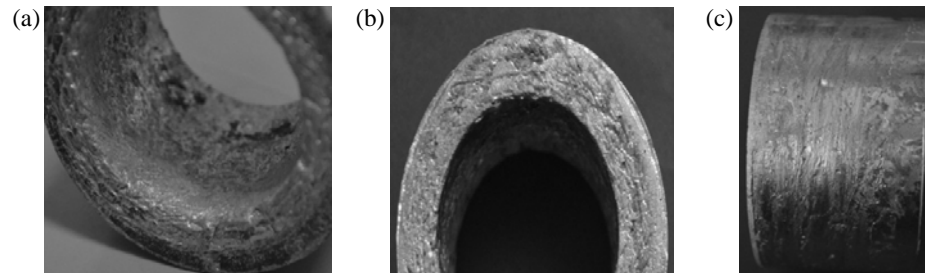


Figure-4. Physical properties of casting with temperature 710 °C. (a) Inner surface; (b) side surface; (c) outer surface

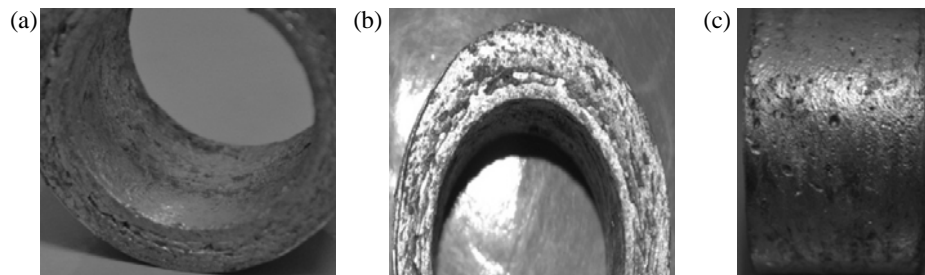


Figure-5. Physical properties of casting with temperature 725 °C. (a) Inner surface; (b) side surface; (c) outer surface

Figures-6, 7 and 8 show the microstructure along the thickness of Al LM6 cylinder fabricated at different melting temperatures. From the observation, it indicates that the microstructure at outer and inner surface have same distributions pattern of Al and Si particles. However, in Figures-6(a), 7(a) and 8(a) the texture size of Si particle has more concentrated on inner surface compared to the agglomerates of Al where more concentrated along the outer surface. The factors that influenced this condition is due to non-uniform of grain size. Furthermore, the density of Al is higher than Si particles.

Besides that, the distributions movement of Si particles is non-uniformly. According to Bonollo [3], low melting temperature and high viscosity in Al LM6 will cause the particles move freely and this will result that almost all parts are filled with Si particles which distributed with inconsistent. Moreover, as seen in Figure-6(c), the inner surface of the lower melting temperature casting has shown the presence of gas porosity. The gas bubbles present in the molten metal are thrown towards the inner surface of the casting by the centrifugal force due to their lower density [4]. Meanwhile, for the high melting temperature as seen in Figure-8(c) shows the absence of

any form of porosity on the surface of the specimen. On the middle surface of the casting as seen in Figure-6(b), 7(b) and 8(b), specimens have a distribution of Al and Si

particles which slightly. This occurred due to the higher rotational speed at mold which cause the particles disperse non-uniform at the middle part of the casting.

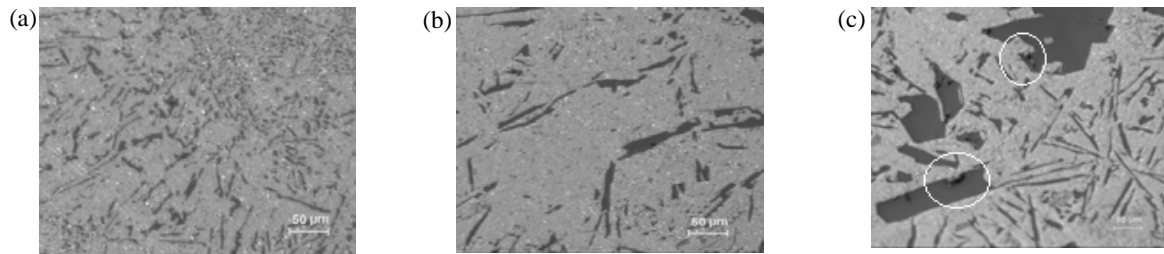


Figure-6. Microstructures of Al LM6 cylinder with melting temperature of 690 °C. (a) outer; (b) middle; (c) inner

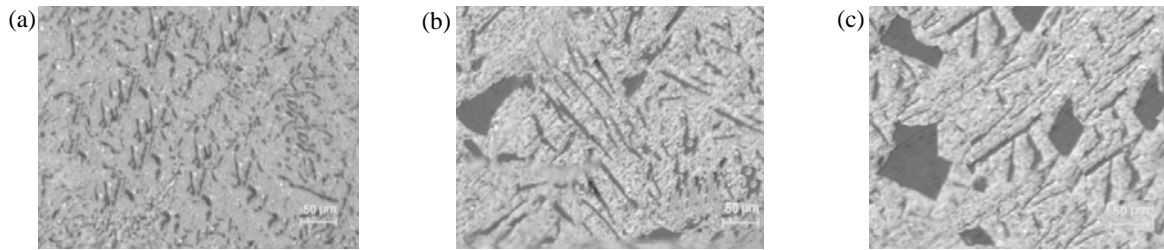


Figure-7. Microstructures of Al LM6 cylinder with melting temperature of 710 °C. (a) outer; (b) middle; (c) inner

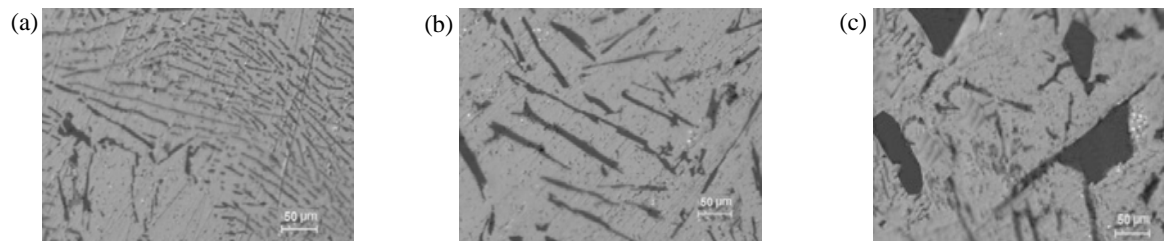


Figure-8. Microstructures of Al LM6 cylinder with melting temperature of 725 °C. (a) outer; (b) middle; (c) inner

CONCLUSION

From experiments performed, it can be proved that the study has achieved its objective of producing a hollow cylindrical Al LM6 using centrifugal casting method and determine the microstructure and mechanical properties of the hollow cylinder.

The melt temperature is an important parameter to produce a good casting. The results show that the microstructure of melt temperature for all three specimens microstructures matching the pattern of accumulation of Al in the outer surface and the accumulation of Si on the inside of the specimen. This is due to the different densities between Al and Si. In addition, the effect of low melt temperature causes the formation of large Si size and thus lead to the violence on the part of the specimen to be low.

A cooling rate is too fast due to the high rotational speed of the mold also causes the differences in Si particles distribution and size. This happens because Si is not melted and evenly when Al LM6 ingot melting process is carried out at a temperature of 690C melt. Si is not melted evenly causing the violence increased when mixed with Al at a mold which rotates with the set speed.

The Al LM6 cylinders fabricated have a smooth outer surface. This can reduce the finishing work which no need to do machining for a smooth and seamless. It thus

can save time and reduce the cost of casting production. In addition, the castings produced by this process has a high density structure which can increase the lifetime of casting and resist over-load and high impact without breaking. The result of uniformity and extra features found on centrifugal casting, machining time and the remaining waste is minimized. Furthermore, the defect on the result of such notch cast, hollow porosity and surface can be reduced. Indirectly, this condition can reduce the effects of pollution on the environment.

ACKNOWLEDGEMENT

The authors acknowledge the Ministry of Education (KPM) and Universiti Tun Hussein Onn Malaysia (UTHM) for funding this project.

REFERENCES

- [1] Chirita G., Soares D. and Silva, F.S. 2008. Advantages of the centrifugal casting technique for production of structural components with Al-Si alloys. *Material and Design*. 29: 20-27.
- [2] Watanabe Y., Sato R., Kim I.S., Miura S. and Miura H. 2005. Functionally graded material fabricated by a

- centrifugal method from ZK60A magnesium alloy. *Materials Transactions*. 46 (5): 944-949.
- [3] Bonollo F., Moret A., Gallo S. and Mus C. 2004. Cylinder liners in aluminium matrix composite by centrifugal casting. *La metallurgia italiana*. 6: 49-55.
- [4] Rajan T.P.D., Pillai R.M. and Pai B.C. 2010. Characterization of centrifugal cast functionally graded aluminium-silicon carbide metal matrix composites. *Material Characterization*. 61: 923-928.
- [5] Madhusudhan, Narendranaath S., Mohankumar G.C.S. and Mukunda P.G. 2010. Effect of mould wall thickness on rate of solidification of centrifugal casting. *International Journal of Engineering Science and Technology*. 2(11): 6092-6096.
- [6] Watanabe Y., Inaguma Y., Sato H. and Miura-Fujiwara E. 2009. A novel fabrication method for functionally graded materials under centrifugal force: The centrifugal mixed-powder method. *Materials*. 2: 2510-2525.