

Edinburgh Research Archive



Atmospheric Pressure Deposition of Fluorine-doped SnO₂ Thin Films from Organotin Fluorocarboxylate Precursors.

M. F. Mahon, K. C. Molloy, J. E. Stanley, D. W. H. Rankin, H. E. Robertson and B. F. Johnston.
Appl. Organomet. Chem., 2005, 658-671.

DOI: 10.1002/aoc.722

This is a pre-copy-editing, author-produced PDF of an article accepted for inclusion in **Applied Organometallic Chemistry**, published by **John Wiley & Sons, Ltd.** following peer review. The publisher-authenticated version is available online at <http://www3.interscience.wiley.com/cgi-bin/jhome/2676>. This online paper must be cited in line with the usual academic conventions. This article is protected under full copyright law. You may download it for your own personal use only.

Atmospheric Pressure Deposition of F-doped SnO₂ Thin Films from Organotin Fluorocarboxylate Precursors

Mary F Mahon, Kieran C Molloy* and Joanne E Stanley

Department of Chemistry, University of Bath, Claverton Down, Bath BA2 7AY, UK

David W H Rankin, Heather E Robertson and Blair F Johnston

School of Chemistry, University of Edinburgh, West Mains Road, Edinburgh, EH9 3JJ, UK


Nine organotin fluorocarboxylates R_nSnO₂CR_f (n = 3, R = Bu, R_f = CF₃, C₂F₅, C₃F₇, C₇F₁₅; R = Et, R_f = CF₃, C₂F₅; R = Me, R_f = C₂F₅; n = 2, R = Me, R_f = CF₃) have been synthesised; key examples have been used to deposit F-doped SnO₂ thin films by atmospheric pressure CVD.

Et₃SnO₂CC₂F₅, in particular, gives high quality films with fast deposition rates despite adopting a polymeric, carboxylate-bridged structure in the solid state, as determined by x-ray crystallography. Gas phase electron diffraction on the model compound Me₃SnO₂CC₂F₅ shows that accessible conformations do not allow contact between tin and fluorine, and that direct transfer is therefore unlikely to be part of the mechanism for fluorine incorporation in SnO₂ films. The structure of Me₂Sn(O₂CCF₃)₂(H₂O) has also been determined and adopts a *trans*-Me₂SnO₃ coordination sphere about tin in which each carboxylate group is monodentate

Keywords: *tin oxide, CVD, fluorocarboxylate, X-ray structure, electron diffraction*

Graphical Abstract

High quality F-doped SnO₂ thin films can be grown from single-source R₃SnO₂CC_f precursors.

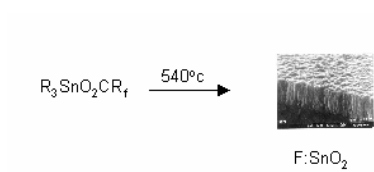

INTRODUCTION

There have been numerous studies on deposition of doped SnO₂ thin films, including both Group 15 and Group 17 dopants. Among these, by far the most widely studied is F-doped SnO₂, as this transparent conducting material has been commercially exploited in such diverse areas as liquid-crystal displays, electrochromic devices, and solar control coatings on glass. Thin films of this material have been deposited by a number of methods, including sol-gel, spray pyrolysis, and sputtering, but chemical vapour deposition (CVD) offers the most attractive route, particularly for producing uniform coating of large areas. The previous paper in this journal cites the relevant references to all these topics.

Single-source precursors that lead directly to F:SnO₂ are far less common than routes which involve multiple sources, and, as far as we are aware, detailed reports have only involved Sn(O₂CCF₃)₂,¹ Sn[OCH(CF₃)₂]₄(HNMe₂)₂,² Sn[OCH(CF₃)₂]₂.L (L = HNMe₂, C₅H₅N),^{3,2} and Bu₂Sn(O₂CCF₃)₂.⁴ Our own interest in this problem has caused us to evaluate a series of organotin(IV) fluoroalkanes, fluoroalkoxides and fluorocarboxylates as possible *single-source* solutions,⁵ and it is this latter compound class which is the focus of this report. The use of organotin fluorocarboxylates as CVD precursors, either alone,⁶ as one component of a mixture,⁷ has been reported by others, predominantly in the patent literature.⁸⁻¹⁰ The chemistry of organotin fluorocarboxylates has also attracted interest due to their potential anti-tumour activity.¹¹

EXPERIMENTAL

General

Infrared spectra (cm⁻¹) were recorded as nujol mulls between NaCl plates using a Nicolet 510P FT-IR spectrophotometer, and elemental analyses were performed using an Carlo-Erba Strumentazione E.A. model 1106 microanalyser operating at 500°C. ¹H and ¹³C NMR spectra were recorded on a Jeol JNM-GX270 FT spectrometer while ¹⁹F and ¹¹⁹Sn NMR spectra were recorded on a Jeol JNM-EX400 FT machine, all using saturated CDCl₃ solutions unless indicated otherwise; chemical shifts are in ppm with respect to either Me₄Si, Me₄Sn or CFCI₃, coupling constants in Hz. Details of our Mössbauer spectrometer and related procedures are given elsewhere;^{12,13,5} data are in mm s⁻¹. Thermogravimetric

studies were performed on a Perkin Elmer TGA7 analyser; samples were loaded in air then the temperature increased under a flow of dry N₂ gas.

Dry solvents were obtained by distillation under inert atmosphere from the following drying agents: sodium-benzophenone (toluene, ether, THF), calcium hydride (CH₂Cl₂), sodium (hexane). Standard Schlenk techniques were used throughout. Starting materials were commercially obtained and used without further purification.

Chemical Vapour Deposition

Details of our apparatus are given elsewhere.¹⁴ In all cases, the substrate used was 4 mm glass which was undercoated with a thin film of SiCO to act as a “blocking layer” to prevent sodium diffusion into the fluorine-doped tin oxide film. Approximately 10 g of precursor was used in each series of experiments; details of the relevant deposition conditions are given in Table 1. All films adhered well to the glass and could not be removed easily without relatively harsh treatment.

Film Analysis

The X-ray diffraction equipment consisted of a Philips PW1130 generator operating at 45 kV and 40 mA to power a copper long fine-focus X-ray tube. A PW 1820 goniometer fitted with glancing-angle optics and proportional X-ray detector was used. The non-focusing thin film optics employed a ¼ degree primary beam slit to irradiate the specimen at a fixed incident angle of 1.5°. Diffraction radiation from the sample was collimated with a flat plate collimator and passed through a graphite flat crystal monochromator to isolate diffracted copper K α peaks onto the detector. The equipment was situated in a total enclosure to provide radiation safety for the highly collimated narrow beams of X-rays. Data were acquired by a PW1710 microprocessor and processed using Philips APD VMS software. Crystalline phases were identified from the International Centre for Diffraction Data (ICDD) database. Samples of coating for XRD were of approximate dimensions 1.5 × 2.0 cm. Crystallite size was determined from line broadening using the Scherrer equation.¹⁵ The instrumental effect was removed using the NIST SRM660 lanthanum hexaboride standard. These operating conditions were used in preference to conventional Bragg-Brentano optics for thin films to give an order of magnitude increase in count rate from a fixed volume of coating with little contribution from the substrate.

Film thickness was determined by etching a thin strip of the film with zinc powder and 50% HCl solution. This created a step in the film, which was measured with a Dektak stylus technique.

Haze was measured on a Pacific Scientific Hazeguard meter and with a barium fluoride detector. The calculation of haze was carried out by measurement of the specular light and diffusive light. Specular light is defined as light transmitted straight through the sample within $\pm 2.5^\circ$ of normal incidence and the diffusive light is defined as light scattered beyond 2.5° . The initial measurement was carried out with the specular detector slot closed and therefore a value for the sum of the specular light and the diffusive light was obtained. The specular light slot was then opened and a measurement of the diffusive light was obtained.^{13,5}

Emissivity data (integral of total emittance between 5 and 50 μm divided by the integral from 5 - 50 μm of the total emittance of a blackbody at room temperature) were then calculated from the infra-red reflectance spectra, measured using a two-beam Perkin Elmer 883 machine and measured against a rhodium mirror standard.¹⁶

Sheet resistance was measured with a four-point probe on an electrically isolated scribed circle of film ($\square = 25 \text{ cm}^2$) and corrected using a conversion factor, the value being dependent on the diameter of the scribed circle.

Fluorine was determined by XRF measurements, made on a Philips PW1400 machine fitted with a scandium target X-ray tube. The penetration depth achieved was between 9 and 10 microns, so the result obtained was throughout the thickness of the coating. The analysis was performed on approximately 6 cm^2 of material.

Synthesis

Preparation of Tributyltin Trifluoroacetate - $\text{Bu}_3\text{SnO}_2\text{CCF}_3$ (1). Sodium trifluoroacetate (5.06 g, 37 mmol) in ethanol (100 ml) was added to a solution of tributyltin chloride (12.08 g, 37 mmol) in ethanol (75 ml). The mixture was refluxed for two hours before removing the solvent *in vacuo* to yield a white solid. This was recrystallised from $40^\circ - 60^\circ$ petroleum ether to yield white needles. The product was then dried under vacuum to give tributyltin trifluoroacetate (8.69 g, 58 %, m.p. $49-52^\circ\text{C}$). Analysis: found (calc. for $\text{C}_{14}\text{H}_{27}\text{F}_3\text{O}_2\text{Sn}$): C 41.8 (41.7)%; H 6.99 (6.77)%. Mössbauer: IS = 1.51; QS = 4.06 (lit: 1.62, 4.40 mms^{-1}).¹⁷ ^{119}Sn NMR: 172.3. ^1H NMR: 0.92 [9H, t, $\text{CH}_3(\text{CH}_2)_3$], $^3\text{J}(\text{}^1\text{H}-\text{}^1\text{H}) = 7 \text{ Hz}$; 1.38 [12H,

m, C₄H₉]; 1.64 [6H, m, C₄H₉]. ¹³C NMR: 13.5 [CH₃(CH₂)₃]; 17.3 [CH₃(CH₂)₂CH₂]; 26.9 [CH₃CH₂(CH₂)₂]; 27.5 [CH₃CH₂CH₂CH₂]. ¹J(¹³C-¹¹⁹Sn) = 334 Hz. C-F carbon not observed. IR : 1721, 1678 [ν_a(CO₂⁻)], 1586, 1447 [ν_s(CO₂⁻)], 1206, 1160, 849, 793, 700, 675, 604.

Preparation of Tributyltin Pentafluoropropionate - Bu₃SnO₂CC₂F₅ (2). The synthetic method described above for **1** was repeated using sodium pentafluoropropionate (6.16 g, 35 mmol) and tributyltin chloride (11.26 g, 35 mmol). White needles of tributyltin pentafluoropropionate (9.07 g, 60 %, m.p. 64-66 °C) were obtained. Analysis: found (calc. for C₁₅H₂₇F₅O₂Sn): C 40.0 (39.8)%; H 6.35 (6.02)%. Mössbauer: IS = 1.52; QS = 4.12. ¹¹⁹Sn NMR: 174.5. ¹H NMR : 0.92 [9H, t, CH₃(CH₂)₃], ³J(¹H-¹H) = 7 Hz; 1.37 [12H, m, C₄H₉]; 1.64 [6H, m, C₄H₉]. ¹³C NMR: 13.6 [CH₃(CH₂)₃]; 17.4 [CH₃(CH₂)₂CH₂]; 26.9 [CH₃CH₂(CH₂)₂]; 27.5 [CH₃CH₂CH₂CH₂]. ¹J(¹³C-¹¹⁹Sn) = 332 Hz. C-F carbons not observed. IR: 1678 [ν_a(CO₂⁻)], 1424 [ν_s(CO₂⁻)], 1329, 1292, 1221, 1169, 1078, 1034, 963, 880, 824, 702, 675.

Preparation of Tributyltin Heptafluorobutyrate - Bu₃SnO₂CC₃F₇ (3). Sodium heptafluorobutyrate (9.38 g, 40 mmol) and tributyltin chloride (12.95 g, 40 mmol) were used in the methodology described for **1** to produce crystals of tributyltin heptafluorobutyrate (11.00 g, 55 %, m.p. 58 °C) (lit: 62-4 °C).¹⁸ Analysis: found (calc. for C₁₆H₂₇F₇O₂Sn): C 38.2 (38.2)%; H 5.59 (5.42)%. Mössbauer: IS = 1.52; QS = 4.05. ¹¹⁹Sn NMR: 175.1. ¹H NMR: 0.92 [9H, t, CH₃(CH₂)₃], ³J(¹H-¹H) = 7 Hz; 1.36 [12H, m, C₄H₉]; 1.65 [6H, m, C₄H₉]. ¹³C NMR: 13.5 [CH₃(CH₂)₃]; 17.4 [CH₃(CH₂)₂CH₂]; 26.9 [CH₃CH₂(CH₂)₂]; 27.4 [CH₃CH₂CH₂CH₂]. ¹J(¹³C-¹¹⁹Sn) = 336 Hz. C-F carbons not observed. IR: 1678 [ν_a(CO₂⁻)], 1418 [ν_s(CO₂⁻)], 1275, 1190, 1086, 968, 934, 816, 673.

Preparation of Tributyltin Pentadecafluorooctanoate - Bu₃SnO₂CC₇F₁₅ (4). Penta-decafluorooctanoic acid (1.77 g, 4 mmol) in toluene (100 ml) was added to bis(tributyltin) oxide (1.19 g, 2 mmol) and the mixture refluxed for two hours. The water formed was azeotropically removed using a Dean and Stark apparatus. The solvent was removed *in vacuo* to leave the title compound as an oily semi-solid material (1.02 g, 36 %) (lit. m.p. 45-7 °C).¹⁸ Analysis: found (calc. for C₂₀H₂₇F₁₅O₂Sn): C 33.9 (34.2)%; H 3.88 (3.87)%. Mössbauer: IS = 1.53; QS = 4.07. ¹¹⁹Sn NMR: 167.2. ¹H NMR: 0.92 [9H, t, CH₃(CH₂)₃], ³J(¹H-¹H) = 7 Hz; 1.38 [12H, m, C₄H₉]; 1.65 [6 H, m, C₄H₉]. ¹³C NMR: 13.4 [CH₃(CH₂)₃];

17.5 [CH₃(CH₂)₂CH₂]; 26.9 [CH₃CH₂(CH₂)₂]; 27.5 [CH₃CH₂CH₂CH₂]. $^1J(^{13}\text{C}-^{119}\text{Sn}) = 343$ Hz. C-F carbons not observed. IR: 1688 [$\nu_a(\text{CO}_2^-)$], 1466 [$\nu_s(\text{CO}_2^-)$], 1362, 1242, 1140, 1106, 1020, 667.

Preparation of Triethyltin Trifluoroacetate - Et₃SnO₂CCF₃ (5). The method previously used to synthesise **1** was utilised. Sodium trifluoroacetate (1.36 g, 10 mmol) and triethyltin chloride (2.41 g, 10 mmol) were reacted to produce white crystals of triethyltin trifluoroacetate (0.72 g, 23 %, m.p. 119 °C) (lit: 120-1 °C).¹⁹ Analysis: found (calc. for C₈H₁₅F₃O₂Sn): C 30.2 (30.1)%; H 4.82 (4.75)%. Mössbauer: IS = 1.53; QS = 4.17. ¹¹⁹Sn NMR: 164.7. ¹H NMR: 1.34 [15H, m, C₂H₅]. ¹³C NMR: 8.88 [CH₃CH₂]; 9.54 [CH₃CH₂]. $^1J(^{13}\text{C}-^{119}\text{Sn}) = 322$ Hz. C-F carbon not observed. IR: 1680, 1653 [$\nu_a(\text{CO}_2^-)$], 1590, 1456 [$\nu_s(\text{CO}_2^-)$], 1196, 1150, 1019, 959, 851, 795, 679.

Preparation of Triethyltin Pentafluoropropionate - Et₃SnO₂CC₂F₅ (6). Sodium pentafluoropropionate (10.26 g, 55 mmol) and triethyltin chloride (13.36 g, 55 mmol) were used in the methodology described for **1** to form triethyltin pentafluoropropionate (9.08 g, 45 %, m.p. 94 °C) as a crystalline material. Analysis: found (calc. for C₉H₁₅F₅O₂Sn): C 29.3 (29.3)%; H 4.12 (4.10)%. Mössbauer: IS = 1.54; QS = 4.12. ¹¹⁹Sn: 160.5. ¹H NMR: 1.33 [15H, m, C₂H₅]. ¹³C NMR: 8.89 [CH₃CH₂]; 9.45 [CH₃CH₂]. $^1J(^{13}\text{C}-^{119}\text{Sn}) = 326$ Hz. C-F carbons not observed. IR: 1659 [$\nu_a(\text{CO}_2^-)$], 1462 [$\nu_s(\text{CO}_2^-)$], 1426, 1335, 1219, 1171, 1038, 1017, 957, 826, 677.

Preparation of Dimethyltin Bis-(trifluoroacetate) - Me₂Sn(O₂CCF₃)₂ (7). 1M sodium hydroxide was added to dimethyltin dichloride (25.00 g, 110 mmol) in distilled water (100 ml) until pH 9 was achieved, quantitatively precipitating dimethyltin oxide. The oxide was collected by filtration, washed several times with distilled water, then dried in an oven overnight. Dimethyltin oxide (6.00 g, 36 mmol) and a large excess of trifluoroacetic anhydride (20.00 ml, 140 mmol) were refluxed for three hours, then the excess anhydride distilled off under a nitrogen atmosphere to leave a white solid. This solid was subsequently sublimed under reduced pressure to yield the product as a white crystalline material (11.10 g, 82 %, sublimation temp. 80°C/1.5mm, m.p. 140°C). Analysis: found (calc. for C₆H₆F₆O₄Sn): C 19.1 (19.2)%; H 1.63 (1.62)%. Mössbauer: IS = 1.47; QS = 4.36.

Preparation of Dimethyltin Bis-(trifluoroacetate) Monohydrate - $\text{Me}_2\text{Sn}(\text{O}_2\text{CCF}_3)_2(\text{OH}_2)$ (8**).**

Compound **8** was obtained following recrystallisation of **7** from chloroform in air, m.p. 220°C. Analysis: found (calc. for $\text{C}_6\text{H}_8\text{F}_6\text{O}_5\text{Sn}$): C 18.3 (18.3)%; H 2.07 (2.06)%. Mössbauer: IS = 1.30; QS = 3.85. ^{119}Sn NMR: -139.4; -138.6. ^1H NMR: 1.25 [s, $(\text{CH}_3)_2\text{Sn}$]; $^2\text{J}(^1\text{H}-^{119}\text{Sn}) = 81$ Hz. ^{13}C NMR: 5.8 [$(\text{CH}_3)_2\text{Sn}$]; $^1\text{J}(^{13}\text{C}-^{119}\text{Sn}) = 702$ Hz; 116.5 [$\text{Sn}(\text{O}_2\text{CCF}_3)_2$]; 163.0 [$\text{Sn}(\text{O}_2\text{CCF}_3)_2$]. ^{19}F NMR: -75.6 [$\text{Sn}(\text{O}_2\text{CCF}_3)_2$]. IR: 3386, 1671 [$\nu_a(\text{CO}_2^-)$], 1453 [$\nu_s(\text{CO}_2^-)$], 1202, 1146, 855, 789.

Preparation of Trimethyltin Pentafluoropropionate - $\text{Me}_3\text{SnO}_2\text{CC}_2\text{F}_5$ (9**).** The synthetic method described above for **1** was repeated using sodium pentafluoropropionate (4.66 g, 25 mmol) and trimethyltin chloride (5.00 g, 25 mmol). White needles of trimethyltin pentafluoropropionate (6.20 g, 76%) were obtained from petroleum ether (m.p. 110-113 °C). Analysis : Found (calc. for $\text{C}_6\text{H}_9\text{F}_5\text{O}_2\text{Sn}$): C 22.0 (22.0)%; H 2.78 (2.78)%. ^{119}Sn NMR : 190.7. ^1H NMR : 0.64 [9H, s, CH_3]. ^{13}C NMR : -2.54 [CH_3]; $^1\text{J}(^{13}\text{C}-^{119,117}\text{Sn}) = 431, 411$; $^2\text{J}(^1\text{H}-^{117,119}\text{Sn}) = 56, 59$ Hz.

Crystallography

Crystallographic details for **6** and **8** are given in Table 2. Crystallographic quality crystals of $\text{Et}_3\text{SnO}_2\text{CC}_2\text{F}_5$ (**6**) were obtained by slow evaporation of a saturated solution in 40°-60° petroleum ether at room temperature. The crystals were stable to light and to atmosphere, but data collection had to be carried out at 170 K due to the decay of the compound in the X-ray beam at room temperature. Suitable crystals of $\text{Me}_2\text{Sn}(\text{O}_2\text{CCF}_3)_2(\text{OH}_2)$ (**8**), were obtained by slow vacuum sublimation onto a cold finger. The crystals were found to be sensitive to air and moisture, and data collection was carried out at 170 K.

In both cases, data were collected on a CAD4 automatic four-circle diffractometer and Lorentz and polarisation corrections were applied; for **6**, a correction was also made for absorption and crystal decay. All non-hydrogen atoms were treated anisotropically. Hydrogen atoms were included at calculated positions, except for the water hydrogens [H(1A), H(1B)] in **8** which were located and refined at a fixed distance of 0.98 Å from the parent atom O(5). Refinement was based on F^2 .

Software used: SHELXS 86,²⁰ SHELX 93,²¹ ORTEX,²² DIFABS.²³

Theoretical Methods

Calculations were performed on a DEC Alpha APX 1000A workstation using the GAUSSIAN 94 program.²⁴ An extensive search of the potential energy surface of $\text{Me}_3\text{SnO}_2\text{CC}_2\text{F}_5$ (**9**) was undertaken at the HF/3-21G* level in order to locate all structurally stable conformers. Two conformers for **9** were found; the lower energy conformer had C_s symmetry and the higher energy one was found to have C_1 symmetry (Figure 1). Further geometry optimisations were then undertaken for both minima with the D95 basis set²⁵ [a full double zeta basis set, including tin²⁶ (15s, 11p, 7d/ 11s, 7p, 4d)] at the HF level. The subsequent two sets of calculations used the LanL2DZ²⁷⁻²⁹ effective core potential (ECP) basis set (incorporating relativistic effects) for tin and D95 for the remaining atoms, at the HF and MP2 levels of theory. Vibrational frequencies were calculated from analytic second derivatives up to the D95 (F, C, H, O), LanL2DZ (Sn)/HF level to confirm both conformers as local minima on the potential energy surface. The force constants obtained from these calculations were subsequently used to construct harmonic force fields for both conformers using the ASYM40 program,³⁰ modified to work for molecules with more than 40 atoms. As no fully assigned vibrational spectra are available for the compound to scale the force fields, a scaling factor of 0.9 was adopted for bond stretches, angle bends and torsions.³¹ The scaled harmonic force fields were then used to provide estimates of amplitudes of vibration (u) for use in the GED refinements. The results of these theoretical calculations are in Table 3, and results for all levels are in the Supplementary data Table S1.

Gas-phase Electron Diffraction

Gas-phase electron diffraction scattering patterns were recorded for $\text{Me}_3\text{SnO}_2\text{CC}_2\text{F}_5$ (**9**) using the Edinburgh gas diffraction apparatus³² with an accelerating voltage of *ca.* 40 kV (electron wavelength *ca.* 6.0 pm). Sample and nozzle temperatures were ~128 K and ~175 K respectively. Scattering intensities were recorded at nozzle-to-plate distances of 95.47 and 197.83 mm on Kodak Electron Image plates. The weighting points for the off-diagonal weight matrices, correlation parameters and scale factors for the two camera distances are given in Table 4, together with electron wavelengths, which were determined from the scattering patterns of benzene vapour recorded immediately after the patterns of $\text{Me}_3\text{SnO}_2\text{CC}_2\text{F}_5$ and analysed in exactly the same way, to minimise systematic errors in





wavelengths and camera distances. A PDS densitometer at the Institute of Astronomy in Cambridge was used to convert the intensity patterns into digital form. Data reduction and least-squares refinements were carried out using the new 'ed@ed' program, employing the scattering factors of Ross *et al.*³³

Based on the *ab initio* MO calculations, a theoretical model containing two conformers, one with C_s and the other C₁ symmetry, was written for Me₃SnO₂CC₂F₅. To model the compound in the desired symmetries, 28 parameters were required. These consisted of eight bonded distance parameters (seven bond lengths and one difference parameter), 19 angles and one parameter to control the amount of conformer 1 in the two-conformer mixture. The starting values of these parameters for the *r_a* refinements were taken from the geometries optimised at the MP2 level. All 28 geometrical parameters and 11 groups of amplitudes of vibration were refined. Flexible restraints were employed during the refinement using the SARACEN method.^{34,35} Altogether, 15 geometric and ten amplitude restraints were employed.

Results and Discussion


Synthesis and Spectroscopy

A series of fluorinated organotin carboxylates R_nSn(O₂CR')_{4-n} has been prepared with a variation in both R and R', which has enabled the effects of both constituents in the CVD process to be explored. The majority of compounds synthesised were triorganotin derivatives, which were usually obtained *via* the conventional reaction of the triorganotin chloride and the sodium salt of the appropriate fluorinated carboxylic acid.




Recrystallisation from 40°-60° petroleum ether yielded the compounds as colourless needles of high purity and in yields of 23-60%, with tributyltin derivatives being recovered in higher quantities.

Compound **4** was prepared by the alternative route of reacting bis(tributyltin) oxide with the fluorinated carboxylic acid; the water generated was removed by a Dean and Stark separator.



To explore the effect of an additional fluorinated group in the precursor one diorganotin carboxylate was also prepared.



Compound **7** was obtained as a pure white solid by sublimation. Crystallisation from chloroform in air yielded the monohydrate $\text{Me}_2\text{Sn}(\text{O}_2\text{CCF}_3)_2 \cdot \text{H}_2\text{O}$ (**8**).

The tributyltin compounds were either oils (**4**) or low-melting solids (**1**: 49-52; **2**: 64-66; **3**: 58 °C). The melting points increased for the triethyl- (**5**: 119; **6**: 94 °C), trimethyl- (**9**: 113°C) and dimethyltin compounds (**7**: 140; **8**: 220°C). The melting point of **1** has been reported by others³⁶ as 255-260 °C, which we feel must be erroneous given the volatility of the compound.

In their infrared spectra, the difference in stretching frequency for $\nu_{\text{asym}}(\text{CO}_2)$ and $\nu_{\text{sym}}(\text{CO}_2)$ ($\Delta\nu$), which lies in the range 197 – 254 cm^{-1} , indicates a bidentate bonding mode for the carboxylate in all the anhydrous compounds **1** - **7**. The Mössbauer q_s values for the $\text{R}_3\text{SnO}_2\text{CR}'$ compounds lie in the range 4.05 – 4.17 mms^{-1} , indicating consistent *trans*- O_2SnC_3 geometry about tin, which is common to many triorganotin carboxylates;³⁷ data for **9** are consistent with these results.¹⁷ The two diorganotin compounds have different spectra. Data for anhydrous **7** (4.36 mms^{-1}) are typical of a six-coordinate *trans*- C_2SnO_4 geometry, as seen in the structure of the related compound $\text{Me}_2\text{Sn}(\text{O}_2\text{CCH}_3)_2$.³⁷ In contrast, q_s data for hydrated **8** are noticeably reduced (3.85 mms^{-1}), and crystallography identifies a change to a five-coordinated tin, incorporating monodentate carboxylate groups. $\Delta\nu$ for **8** (218 cm^{-1}) is somewhat misleading in this respect, but arises as a result of the extensive hydrogen-bonding in which each C=O group is involved (see *Crystallography*).

The NMR spectra of **1** – **6**, **9** are unexceptional. The ^1H and ^{13}C data confirm the integrity of the compounds, while $^1J(^{13}\text{C}-^{119}\text{Sn})$ (322 – 343 Hz) and $\delta(^{119}\text{Sn})$ (160.5 – 190.7 ppm) all indicate a four-coordinate tin atom in solution.³⁸ We have been unable to obtain reliable spectroscopic data for **7** in solution, due to the ease with which it becomes hydrated. However, for **8**, $^2J(^1\text{H}-^{119}\text{Sn})$ of 81 Hz correlates with a calculated³⁹ C-Sn-C angle of 132.1° (140.1° found in the solid-state), while the low frequency shifts for $\delta(^{119}\text{Sn})$ (-139.4, -138.6 ppm) are all consistent with a CN > 4 for this species, even in solution.³⁸

Crystallography

The structure of **6** is shown in Figure 2 and confirms the inferences made from the spectral data. The polymeric nature and *trans*- O_2SnC_3 coordination sphere is common for $\text{R}_3\text{SnO}_2\text{CR}'$.⁴⁰ The nature of the bridging is anisotropic, in which tin forms one short [Sn(1) - O(1) 2.218(4) Å] and one relatively long [Sn(1) - O(2') 2.481(4) Å; symmetry operation $1 - x, \frac{1}{2} + y, \frac{1}{2} - z$] bond to oxygen. These bond lengths are comparable to other Sn-O bonds found in typical polymeric triorganotin carboxylates, with short (2.12 - 2.246 Å) and long (2.24 - 2.65 Å) bonds, respectively. The O(1)-Sn(1)-O(2) angle [$174.93(14)^\circ$] is also comparable to other angles found in typical polymeric triorganotin carboxylates (168.6-178.7°).⁴⁰

The molecular structure of **8** is shown in Figure 3 and the unit cell contents are shown in Figure 4. The local geometry at tin is five-coordinate *cis*- $\text{Me}_2\text{Sn}(\text{O}_2\text{CCF}_3)_2(\text{H}_2\text{O})$ (i.e. *cis*-methyl groups) and each carboxylate is bonded in a unidentate manner to the metal; water is coordinated directly to tin in an equatorial site. This contrasts with the polymeric structure adopted by the anhydrous compound, in which tin is in a six-coordinated environment.⁴¹

The unidentate nature of the carboxylate groups is evident by the short C=O [C(1)-O(2) 1.219(5); C(3)-O(4) 1.214(5) Å] and long C-O [C(1)-O(1) 1.271(5); C(3)-O(3) 1.280(5) Å] bonds, while the Sn(1)-O(5) bond to water [2.238(3) Å] is the longest of the three Sn-O interactions [Sn(1)-O(1) 2.205(3), Sn(1)-O(3) 2.082(3) Å]. The C(5)-Sn(1)-C(6) angle [$140.1(2)^\circ$] represents a large deviation from an ideal angle of 120° .

Both hydrogen atoms of the coordinated water and the two carbonyl groups involve themselves in hydrogen bonding. H(1B) and O(4) link pairs of molecules into centrosymmetric dimers [O(4)-H(1B): 1.79(3) Å; $\angle\text{O(4)-H(1B)-O(5)}$: $165(5)^\circ$]. These dimers are further linked into two-dimensional sheets by

hydrogen bonds between H(1A) and O(2') [O(2')-H(1A): 1.74(3) Å; O(5)-H(1A)-O(2'): 171(6)°; symmetry transformation $1/2 - x, y - 1/2, 1/2 - z$].

It appears that three other structures of diorganotin dicarboxylates that contains a coordinated water molecule, namely $\text{Bu}_2\text{Sn}(\text{O}_2\text{CCH}_2\text{C}_6\text{H}_5)_2(\text{H}_2\text{O})$,⁴² $\text{Cy}_2\text{Sn}(\text{O}_2\text{CCH}_3)_2(\text{H}_2\text{O})$ ⁴³ and a diorganotin derivative of a germatrane-substituted propanoic acid,⁴⁴ have been reported. However, all three structures are very different and consist of a seven-coordinate tin atom with *trans*- C_2SnO_5 pentagonal bipyramidal geometry resulting from the presence of two bidentate, chelating carboxylate groups. The structure of **8** is both unique and important, as it completes a sequence of structures which can be used to depict the reaction pathway by which diorganotin carboxylates are hydrolysed to the corresponding dimeric distannoxanes, $\{[\text{R}_2\text{Sn}(\text{O}_2\text{CR}')]\}_2$ (Scheme 1).⁴⁵ The six-coordinated $\text{R}_2\text{Sn}(\text{O}_2\text{CR}')_2$ has numerous representatives,⁴⁰ e.g. $\text{R} = \text{R}' = \text{Me}$.³⁷ Water first coordinates to tin, represented by $\text{Bu}_2\text{Sn}(\text{O}_2\text{CCH}_2\text{C}_6\text{H}_5)_2(\text{OH}_2)$,⁴² then the carbonyl groups free themselves from coordination to tin **8** allowing H^+ transfer from water, liberating $\text{R}'\text{CO}_2\text{H}$ and generating the hydroxycarboxylate $\text{R}_2\text{Sn}(\text{OH})(\text{O}_2\text{CR}')$, which dimerises, as in the structure of $[\text{tBu}_2\text{Sn}(\text{OH})(\text{O}_2\text{CMe})]_2$,⁴⁶ condensation then affords the dimeric stannoxane, typified by $\{[\text{Me}_2\text{Sn}(\text{O}_2\text{CCl}_3)]_2\}_2$.⁴⁷

Gas-phase Electron Diffraction Study of $\text{Me}_3\text{SnO}_2\text{CC}_2\text{F}_5$ (**9**)

Using the SARACEN method^{34,35} to restrain 15 geometrical and 10 amplitudes parameters, all 28 geometrical parameters were refined. The parameters are listed in Table 5, relating to the atom numbering shown in Figure 1. Amplitudes of vibration for the most significant atom pairs are listed in Table 6, and a longer list is given in the Supplementary Table S2. The final R factors were $R_G = 0.069$ and $R_D = 0.075$. The radial distribution curve and molecular scattering intensity curves are shown in Figures 5 and 6 respectively, and the least-squares correlation matrix is given in Supplementary Table S3.

Neither the experimental data nor the *ab initio* calculations gave any evidence for a conformer in which a fluorine atom came close enough to the tin atom to interact with it significantly. Calculations showed there to be very little difference in most parameters for the two conformers, with the largest difference in bond length being observed for the C(5)-F(14) bond, which was 0.9 pm longer in

conformer 2 (135.0 pm compared to 134.1 pm in conformer 1). Bond angles were also very similar in the two conformers.

Changes in the theoretical treatment resulted in some significant variations in geometrical parameters. The average Sn-C bond length changed the most on switching from the D95 basis set to the LanL2DZ pseudo-potential, with a decrease in bond length of around 2 pm (~214.7 pm to ~212.6 pm). The unrestrained GED value for the average Sn-C bond was 214.1(3) pm, which is longer than calculated at the MP2 level by 1.5 pm. The Sn-O bond lengths also varied substantially with the theoretical treatment. At the D95/HF level it was calculated as 205.5 pm for the major conformer. It then shortened by around 5 pm with the switch to the LanL2DZ basis set on tin and finally lengthened by around 4.7 pm on moving to the MP2 level. The GED value of 201.6(10) pm suggests that the MP2 level of theory overestimates the length of the Sn-O bond (at least using this basis set). The C-C bond lengths were largely unaffected by changes in basis set and level of theory, and the average distance computed at the MP2 level (154.5 pm) falls within two standard deviations of the unrestrained GED value of 153.7(5) pm. C-F bonds lengthened by about 3 pm with the inclusion of electron correlation (at the MP2 level). C(4)-F(10/11) was found to be longer than C(5)-F(12/13/14) by about 1.5 pm. The C-O bond is not particularly sensitive to the addition of the pseudo-potential but does lengthen by 3 pm from 128.3 pm at the D95/HF level to 131.5 pm at the MP2 level. The GED value of 129.2(13) lies somewhere between those given by the HF and MP2 levels of theory. Similarly, the C=O bond lengthens by 4 pm from 119.5 pm at the D95/HF level to 123.3 pm at the MP2 level. The experimental GED value of 122.7(7) pm is close to that given by the MP2 level of theory.

The majority of bond angles varied little with changes in theoretical treatment. The exception to this is Sn(1)-O(2)-C(3). At the HF level Sn(1)-O(2)-C(3) is found to be around 122°. At the MP2 level the angle is found to decrease by 8° to around 114.2°. However, the GED experimental value of 119.0(14)° does not support the small value calculated at the MP2 level. The angle O(2)-Sn(1)-C(6) is also interesting. At 98.1° (MP2) it is 4° smaller than the equivalent angle [C(2)-Sn(1)-C(6)] in Me₃SnC₄F₉¹³ and around 7.4° smaller than the angles O(2)-Sn(1)-C(7) and O(2)-Sn(1)-C(8). The GED value of 98.1(13)°, with an extremely weak restraint, confirms this particularly small angle, which can be attributed to the additional coordination of O(9) to tin, with the Sn...O distance being only 312 pm; O(9) approaches tin approximately *trans* to C(6) [\angle O(9)-Sn(1)-C(6): 146.8°]. The average C(6)-Sn(1)-C(7) and C(6)-Sn(1)-C(8) angles are found to be correspondingly larger than their counterparts in

$\text{Me}_3\text{SnC}_4\text{F}_9$.⁶⁰ The existence of this non-bonded Sn...O interaction forces the C_2F_5 group to be directed away from the tin atom, and thus precludes any possibility of even passing contact between a fluorine atom and tin. The situation is thus quite different from that pertaining in $\text{Me}_3\text{SnC}_4\text{F}_9$.⁶⁰ Here it is only the fourth conformer that involves close Sn...F interaction, but its energy is such that at the temperature of the CVD experiments it is present in sufficient abundance to account for the observed degree of fluorine doping of the deposited tin oxide. In the present case, the mechanism of F-transfer to tin would appear to be different.

CVD Studies

Compounds tested were **1 - 3**, **6** and **7**. This selection allowed assessment of variations in the R groups (Bu, Et and Me), the length of the fluorinated chain (CF_3 , C_2F_5 and C_3F_7), and the number of fluorine-containing ligands (1 or 2). Although all of the triorganotin carboxylates form polymeric crystalline solids with melting points in the range 50-94°C, good volatility was achieved with bubbler temperatures approximately 60°C in excess of the melting points. The TGA of **9**, used in the gas-phase electron diffraction study, shows that complete sublimation of the sample has taken place by ca. 150°C (Figure 7). The diorganotin carboxylate **7** with a melting point of 140°C only required a 25°C increase in bubbler temperature in order to grow a suitable film. However, a higher temperature for the heater tapes was required for this precursor in order to prevent solidification in the pipework between bubbler and substrate.

Although the melting points of the ethyl and methyl tin compounds were higher than those of the butyltin compounds, the deposition duration for the former were markedly shorter than for the latter, for the production of films of similar thickness. Films of ca. 3000 Å could be achieved within reasonable deposition times (Tables 1, 7), and in the cases of **6** and **7**, which incorporate smaller hydrocarbon groups on tin, deposition times were reduced by an order of magnitude compared to those for the butyltin precursors. Films grown from the tributyltin carboxylates **1 - 3** were found to favour deposition at the front end of the substrate directly after the inlet, and only coated the first ca. 5 cm of the glass. Films derived from $\text{Et}_3\text{SnO}_2\text{CC}_2\text{F}_5$ (**6**) and $\text{Me}_2\text{Sn}(\text{O}_2\text{CCF}_3)_2$ (**7**) had a much more uniform appearance and the coating spanned the total length of the substrate. Scanning Electron Microscopy (SEM) was performed on the film deposited from $\text{Bu}_3\text{SnO}_2\text{CC}_2\text{F}_5$ (**2**) and revealed a uniform film with a smooth surface and homogeneous substrate coverage (Figure 8).

All the films were crystalline and glancing angle X-ray diffraction confirmed the film composition as tin oxide in all cases (Table 8); a typical diffraction pattern is shown for the film grown from $\text{Bu}_3\text{SnO}_2\text{CC}_2\text{F}_5$ (**2**) in Figure 9. It is known that for a random specimen of SnO_2 , the (200) reflection should make up 7% of the spectral intensity and that films of SnO_2 grown preferentially along the (200) direction contain fewer structural defects than randomly oriented materials.^{48,49} For all films deposited in this study the preferred orientations were shown by the more intense (110), (101), (200) and (211) peaks. The proportions found for the (200) reflection were very high for **1 – 3, 6** and were well in excess of 7%. In contrast, the contribution from the (200) reflection to the spectrum of the film from the diorganotin carboxylate (**7**) was very low at 4.2%, suggesting that the films grown from the triorganotin derivatives appeared to have greater structural integrity. From line broadening measurements of the (110) reflection it was possible to measure the approximate crystallite sizes of the samples, which lie in the range 150 – 320 Å.

EDAX analysis indicated fluorine was present in all the films, though X-ray fluorescence measurements showed that the amount of halogen remained approximately constant (ca. 1%) across the series of $\text{R}_3\text{SnO}_2\text{CR}'$ (**1 – 3, 6**), despite the increasing fluorine content of the R' group (Table 7). This suggests both a common decomposition pathway for all the precursors and that delivery of fluorine from only one carbon centre is important. Given that there are no close $\text{Sn}\cdots\text{F}$ contacts in the gas phase structures of the triorganotin fluorocarboxylates as evidenced by the GED study of **9**, direct transfer of halogen to tin is highly unlikely. The most plausible mechanism would involve loss of CO_2 to generate $\text{R}_3\text{SnR}'_i$, which we have shown to be viable, if relatively difficult to synthesise, precursors for $\text{F}:\text{SnO}_2$ in their own right.¹³ The EI mass spectrum of **9**, which gives some clues as to the mode of decomposition, has P-Me (m/z 313) as the major fragment (100%), along with minor fragments corresponding to Me_2Sn (m/z 150, 10%), MeSn (m/z 135, 25%) and Sn (m/z 120, 10%). In addition, there is a cluster of overlapping fragments with m/z 160 – 169 (80%), which probably include Me_3Sn (m/z 165), but this alone does not account for the isotope distribution profile. The most abundant fragment in this cluster at m/z 169 could reasonably correspond to Me_2SnF , which would be arrived at by loss of CO_2 and C_2F_4 from $\text{Me}_2\text{SnO}_2\text{CC}_2\text{F}_5$.

The high fluorine content in the film derived from **7** at 560°C (ca. 4.8 %) is surprising. $\text{Bu}_2\text{Sn}(\text{O}_2\text{CCF}_3)_2$ has been used to grow $\text{F}:\text{SnO}_2$ with fluorine contents of 0.5 – 1.5% at temperatures of 370 – 490°C, and, while the amount of fluorine incorporated was seen to increase with increasing

temperature, somewhat less than 4.8% that might have been anticipated had the decomposition been made at 70°C higher.⁴ This suggests that the decomposition pathway is different to that of **7**, possibly by virtue of the absence of β hydrogens on the hydrocarbon groups of the latter. Butyl groups attached to tin can undergo butene elimination generating Sn-H bonds, which then offer the possibility of HF elimination (by a radical mechanism involving H \cdot), a sequence that cannot be replicated by methyl tin precursors. Interestingly in this respect, inorganic tin precursors such as $\text{Sn}(\text{O}_2\text{CCF}_3)_2$ and $\text{Sn}[\text{OCH}(\text{CF}_3)_2]_4(\text{HNMe}_2)_2$ also generate more highly-doped F:SnO₂ films (ca. 2.5%).^{2,1}

Film Properties

The physical properties of the films are given in Table 7 and compared with those for films generated by a commercial dual-source approach.⁵⁰ All of the films generated have a thickness typical of those used in solar control coatings and those derived from **6** and **7** have comparable levels of haze (< 0.40%); films derived from **1** – **3**, however, are less visually clear (haze 0.59 – 0.99%). The films generated by **1** – **3** and **6** all have emissivity (0.118 – 0.175), sheet resistance (8 – 16 Ω / \square) and resistivity (0.43 – 0.54 $\times 10^{-3} \Omega \text{ cm}$) that compare favourably with a commercial product, despite the fact that in none of the deposition experiments have the experimental conditions been optimised. In contrast, the properties of the film produced by **7** are notably inferior to those of both the commercial sample and of the above experimental films. The nature of the fluorine doping seems to be crucial, as the dopant level from **7** is by far the highest. The deterioration of film properties, along with the reduced (200) preferred orientation, suggest that at least some of the fluorine is not necessarily integral to the SnO₂ lattice.

CONCLUSIONS

Fluorine-doped SnO₂ films with properties approaching those of commercial products can be achieved using the organotin fluorocarboxylates $\text{R}_3\text{SnO}_2\text{CR}_f$. The fastest growth rates are achieved from Et₃Sn (rather than Bu₃Sn) derivatives. The fluorine content of all the films is ca. 1%. In particular, Et₃SnO₂CC₂F₅ gives excellent films, with rapid growth rates and is a viable APCVD precursor, despite adopting a polymeric structure in the solid state. Films grown from $\text{Me}_2\text{Sn}(\text{O}_2\text{CCF}_3)_2$ contain higher

levels of fluorine dopant but exhibit diminished physical properties. The gas-phase structure of $\text{Me}_3\text{SnO}_2\text{CC}_2\text{F}_5$ indicates that accessible conformations do not allow contact between tin and fluorine, and that direct transfer is therefore unlikely to be part of the mechanism for fluorine incorporation in SnO_2 films. A mechanism which involves loss of CO_2 to generate R_3SnR_f *in situ* seems likely.

Acknowledgements


We acknowledge support from Pilkington plc (for J. E. S.), EPSRC (for J. E. S., B. F. G., and the gas electron diffraction service; [GR/R17768](#)). We thank Mr. J. Lewis (Institute of Astronomy, Cambridge) for tracing photographic plates and Dr. S. L. Hinchley for helpful discussions.

REFERENCES

- 1 Maruyama T, Tabata K. *J. Appl. Phys.* 1990; **68**:4282.
- 2 Suh S, Hoffman DM, Atagi LM, Smith DS, Liu J-R, Chu W-K. *Chem. Mater.* 1997; **9**:730.
- 3 Suh S, Hoffman DM. *Inorg. Chem.* 1996; **35**:6164.
- 4 Suh S, Zhang Z, Chu W-K, Hoffman DM. *Thin Solid Films* 1999; **345**:240.
- 5 Stanley JE (1997) The synthesis of Single-source Precursors for the CVD of F-doped Tin Oxide. In Bath, University of Bath
- 6 Elich JJP, Boslooper EC, Haitjema H. *Thin Solid Films* 1989; **177**:17.
- 7 Price LS, Parkin IP, Field MN, Hardy AME, Clark RJH, Hibbert TG, Molloy KC. *J. Mater. Chem.* 2000; **10**:527.
- 8 Menke AG. *Ger. Patent* 2246193; *Chem Abs.* 78, 150521 1973;
- 9 Bloss KH, Davis JA, Neuman GA, Harmon PP. *Euro. Patent* 338417; *Chem. Abs.* 112, 82817 1989;
- 10 Durant M, Merienne G, Valette D. *Eur. Patent* 623564; *Chem Abs.* 122, 62398 1994;
- 11 Kemmer M, Dalil H, Biesemans M, Martins JC, Mahieu B, Horn E, de Vos D, Tiekink ERT, Willem R, Gielen M. *J. Organomet. Chem.* 2000; **608**:63.
- 12 Molloy KC, Purcell TG, Quill K, Nowell I. *J. Organomet. Chem.* 1984; **267**:237.
- 13 Stanley JE, Swain AC, Molloy KC, Rankin DWH, Robertson HE, Johnston BF. *J. Appl. Organomet. Chem.* 2004; ?:?
- 14 Edwards DA, Harker RM, Mahon MF, Molloy KC. *J. Mater. Chem.* 1999; **9**:1771.
- 15 Kaelble EF (1967) Scherrer eqn. In Handbook of X-rays. New York, McGraw-Hill, Ch. 17.
- 16 Bass M (1995) Handbook of Optics, 2nd Edition ed. New York, McGraw Hill Inc.
- 17 Zuckerman JJ, Debye NW, Fenton DE, Ulrich SE. *J. Organomet. Chem.* 1971; **28**:339.

- 18 Laliberte BR, Reiff HF, Davidssohn WE. *Org. Prep. Proc.* 1969; **1**:173.
- 19 Anderson HH. *Inorg. Chem.* 1962; **1**:647.
- 20 Sheldrick GM (1986) SHELX 86S, A Computer Program for Crystal Structure Determination. In University of Göttingen, Göttingen
- 21 Sheldrick GM (1993) SHELX 93, A Computer Program for Crystal Structure Refinement. In University of Göttingen, Göttingen
- 22 McArdle P. *J. Appl. Crystallogr.* 1995; **28**:65.
- 23 Walker N, Stewart D. *Acta Crystallogr., Sect. A: Found. Crystallogr.* 1983; **39**:158.
- 24 Frisch MJ, Trucks GW, Schlegel HB, Gill PMW, Johnson BG, Robb MA, Cheesman JR, Keith TA, Petersson GA, Montgomery JA, Raghavachari K, Al-Laham MA, Zakrzewski VG, Ortiz JV, Foresman JB, Cioslowski J, Stefanov BB, Nanayakkara A, Challacombe M, Peng CY, Ayala PY, Chen W, Wong MW, Andres JL, Replogle ES, Gomperts R, Martin RL, Fox DJ, Binkley JS, Defrees DJ, Baker J, Stewart JP, Head-Gordon M, Gonzalez C, Pople JA (1995) Gaussian 94 (Revision C.2). In, Gaussian Inc., Pittsburgh, PA,
- 25 Dunning THJ, Hay PJ (1976) Modern Theoretical Chemistry. In Ed. H. F. Schaefer I, ed. New York, Plenum, 1
- 26 Dunning THJ. unpublished results;
- 27 Hay PJ, Wadt WR. *J. Chem. Phys.* 1985; **82**:270.
- 28 Wadt WR, Hay PJ. *J. Chem. Phys.* 1985; **82**:284.
- 29 Hay PJ, Wadt WR. *J. Chem. Phys.* 1985; **82**:299.
- 30 Hedberg L, Mills IM. *J. Mol. Spectrosc.* 1993; **160**:117.
- 31 Scott AP, Radom L. *J. Phys. Chem.* 1996; **100**:16502.
- 32 Huntley CM, Laurenson GS, Rankin DWH. *J. Chem. Soc., Dalton Trans.* 1980; 954.

- 33 Ross AW, Fink M, Hilderbrand R (1992) International Tables for Crystallography. In Wilson AJC, ed. Dordrecht, Boston and London, Kluwer Academic Publishers, 245
- 34 Blake AJ, Brain PT, McNab H, Miller J, Morrison CA, Parsons S, Rankin DWH, Robertson HE, Smart BA. *J. Chem. Phys.* 1996; **100**:12280.
- 35 Brain PT, Morrison CA, Parsons S, Rankin DWH. *J. Chem. Soc., Dalton Trans.* 1996; 4589.
- 36 Uesugi H, Kawai S, Inaba T. *Chem. Abs.* 1970; 90636.
- 37 Lockhart TP, Davidson F. *Organometallics* 1987; **6**:2471.
- 38 Davies AG, Smith PJ (1982) Tin. In Wilkinson G, Stone FGA, Abel EW, eds. Comprehensive Organometallic Chemistry. Oxford, Pergamon Press, 519.
- 39 Lockhart TP, Manders WF. *Inorg. Chem.* 1986; **25**:892.
- 40 Tiekink ERT. *Trends Organomet. Chem.* 1994; **1**:71.
- 41 Misty F, Rettig SJ, Trotter J, Aubke F. *Z. Anorg. Allg. Chem.* 1995; **621**:1875.
- 42 Ng SW, Chen W, Zainudin A, Kumar Das VG, Yip W-H, Wang R-J, Mak TCW. *J. Crystallogr. Spectrosc. Res.* 1991; **21**:39.
- 43 Dakternieks D, Kuan FS, Tiekink ERT. *Main Group Met. Chem.* 2001; **24**:291.
- 44 Xueqing S, Zhiqiang Y, Qingla X, Jinshan L. *J. Organomet. Chem.* 1998; **556**:103.
- 45 Davies AG (1997) In Organotin Chemistry. Weinheim, Verlag Chemie, 144.
- 46 Mokal VB, Jain VK, Tiekink ERT. *J. Organomet. Chem.* 1992; **431**:283.
- 47 Alcock NW, Roe SM. *J. Chem. Soc., Dalton Trans.* 1989; 1589.
- 48 Bélanger D, Dodelet JP, Lombos BA, Dickson JI. *J. Electrochem. Soc.* 1985; **132**:1398.
- 49 Smith A, Laurent J-M, Smith DS, Bonnet J-P, Clemente RR. *Thin Solid Films* 1995; **266**:20.
- 50 Soubeyrand MJ, Halliwell AC (1997) *US Patent* 5698262.

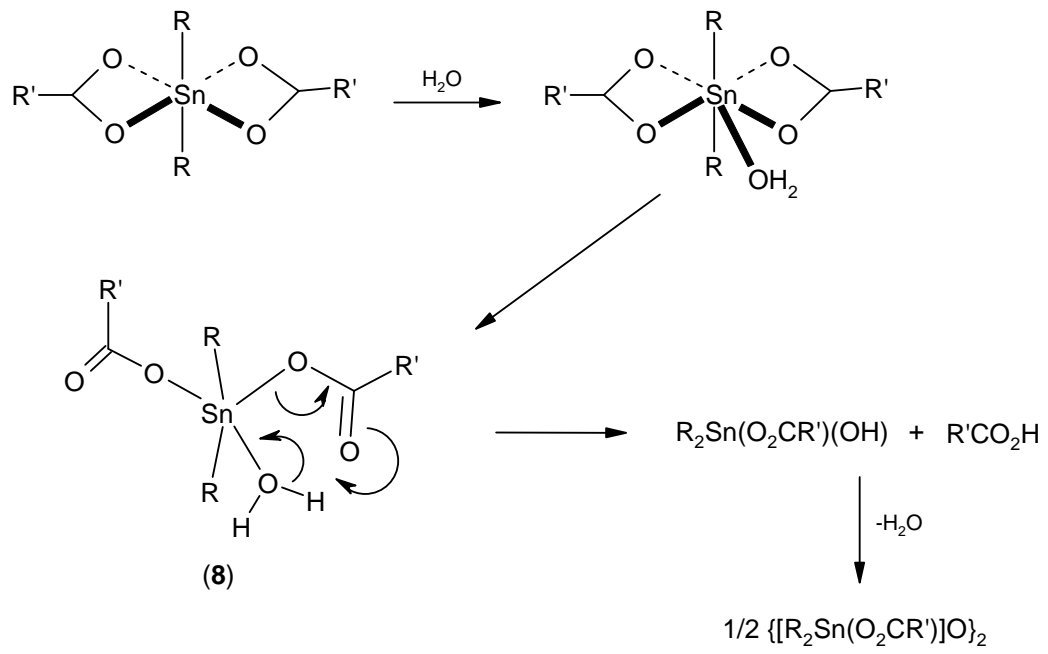

Scheme 1

Table 1. Conditions for the APCVD of F-doped SnO₂ using fluorinated organotin carboxylate precursors

	1	2	3	6	7
Reactor Temperature (°C)	564	564	570	541	560
Bubbler Temperature (°C)	110	125	116	150	165
Heater Tapes (°C)	200	200	200	200	250
Diluent Flow (L min ⁻¹)	3.00	3.00	3.00	2.75	2.75
Carrier Flow (L min ⁻¹)	1.0	1.0	1.0	1.0	1.0
Oxygen Flow (L min ⁻¹)	0.6	0.6	0.6	0.6	0.6
Run Time (min)	25	25	20	3	1.5

Table 2. X-ray crystallographic data for **6** and **8**

	6	8
Empirical formula	C ₉ H ₁₅ F ₅ O ₂ Sn	C ₆ H ₈ F ₆ O ₅ Sn
Formula weight	368.90	392.81
Crystal system	Monoclinic	Monoclinic
Space group	<i>P2₁/c</i>	<i>P2₁/n</i>
<i>a</i> , Å	8.057(1)	10.833(1)
<i>b</i> , Å	10.406(2)	11.436(2)
<i>c</i> , Å	16.254(3) ^o	10.893(2)
β , °	99.65(1)	107.81(1)
Volume, Å ³	1343.5(4)	1284.8(3)
<i>Z</i>	4	4
μ (Mo- k_{α}), mm ⁻¹	1.949	2.072
θ range	2.3 - 23.9	2.3 - 22.9
Independent reflections	2100 [<i>R</i> (int) = 0.0650]	1777 [<i>R</i> (int) = 0.0259]
Final <i>R</i> ₁ , <i>wR</i> ₂ [<i>I</i> > 2 σ (<i>I</i>)]	0.037, 0.092	0.023, 0.056
Final <i>R</i> ₁ , <i>wR</i> ₂ (all data)	0.066, 0.099	0.031, 0.061
CCDC number	228004	228905

Table 3. Calculated geometrical parameters for $\text{Me}_3\text{SnO}_2\text{CC}_2\text{F}_5$ (**9**) (distances in pm, angles in degrees) from the *ab initio* MO theory study.

	MP2/LanL2DZ (Sn) – D95	
	Conformer 1	Conformer 2
Bond distances		
Sn(1)-C(6)	212.7	212.7
Sn(1)-C(8)	212.6	212.5
Sn(1)-C(7)	212.6	212.6
C(3)-C(4)	154.3	154.5
C(4)-C(5)	154.5	154.7
C(4)-F(11)	136.2	136.3
C(4)-F(10)	136.2	135.3
C(5)-F(12)	134.6	134.2
C(5)-F(13)	134.1	133.9
C(5)-F(14)	134.1	135.0
Sn(1)-O(2)	205.2	205.0
C(3)-O(2)	131.4	131.6
C(3)=O(9)	123.3	122.9
Bond angles		
C(4)-C(5)-F(12)	109.4	110.5
C(4)-C(5)-F(13)	110.7	111.7
C(4)-C(5)-F(14)	110.7	109.0
F(10)-C(4)-F(11)	108.2	108.4
C(3)-C(4)-C(5)	114.5	112.8
O(2)-C(3)-C(4)	111.5	111.6
O(9)=C(3)-C(4)	122.0	121.6
C(6)-Sn(1)-O(2)	98.2	98.1
C(6)-Sn(1)-C(7)	114.2	114.4
C(7)-Sn(1)-C(8)	116.7	116.8
C(6)-Sn(1)-C(8)	114.2	113.9
C(8)-Sn(1)-O(2)	105.5	105.6
C(7)-Sn(1)-O(2)	105.5	105.4
Sn(1)-O(2)-C(3)	114.0	114.4
Sn(1)-C(7)-H(15)	110.5	110.6

Dihedral angles		
C(6)-Sn(1)-O(2)-C(3)	180.0	178.6
Sn(1)-O(2)-C(3)-C(4)	180.0	179.0
O(2)-C(3)-C(4)-C(5)	180.0	63.2
C(3)-C(4)-C(5)-F(12)	180.0	168.2

Table 4. Nozzle-to-plate distances (mm), weighting functions (nm^{-1}), correlation parameters, scale factors and electron wavelengths (pm) used in the electron-diffraction study.

Nozzle-to-plate distance ^a	95.47	197.83
Δs	4	2
s_{min}	192	32
s_{w1}	212	52
s_{w2}	256	172
s_{max}	300	204
Correlation parameter	-0.2517	-0.0617
Scale factor ^b	1.545(97)	0.747(14)
Electron wavelength	6.016	6.016

^a Determined by reference to the scattering pattern of benzene vapour.

^b Values in parentheses are the estimated standard deviations.

Table 5. Refined and calculated geometric parameters for Me₃SnO₂CC₂F₅ (**9**) in the gas phase (distances in pm, angles in degrees) from the GED study.^{a, b}

No.	Parameter	GED (<i>r_a</i>)	MP2/6-31G*	Restraint
<i>p</i> ₁	Average C-H	109.8(1)	109.8	109.8(1)
<i>p</i> ₂	Average Sn-C	214.1(3)	212.6	
<i>p</i> ₃	Average C-C	153.7(5)	154.5	
<i>p</i> ₄	Average C-F	134.5(2)	135.0	
<i>p</i> ₅	[Average C(4)-F(10/11)] - [Average C(5)-F(12/13/14)]	1.6(1)	1.7	1.7(1)
<i>p</i> ₆	Sn-O	201.6(10)	205.1	205.1(44)
<i>p</i> ₇	C-O	129.2(13)	131.5	131.5(20)
<i>p</i> ₈	C=O	122.7(7)	123.1	123.1(20)
<i>p</i> ₉	Average C(4)-C(5)-F(12/13/14)	111.4(4)	110.3	
<i>p</i> ₁₀	F-C-F	108.3(5)	108.3	108.3(5)
<i>p</i> ₁₁	C(3)-C(4)-C(5) in conformer 1	114.5(5)	114.5	114.5(5)
<i>p</i> ₁₂	O(2)-C(3)-C(4)	111.4(5)	111.6	111.6(5)
<i>p</i> ₁₃	O(9)=C(3)-C(4)	121.1(6)	121.8	121.8(7)
<i>p</i> ₁₄	O(2)-Sn(1)-C(6)	98.1(13)	98.1	98.1(142)
<i>p</i> ₁₅	Average C(6)-Sn(1)-C(7/8)	117.3(15)	116.7	116.7(15)
<i>p</i> ₁₆	Sn(1)-O(2)-C(3)	119.0(14)	114.2	114.2(50)
<i>p</i> ₁₇	Average Sn-C-H	110.5(3)	110.6	110.6(3)
<i>p</i> ₁₈	Average O(2)-Sn(1)-C(7/8)	105.6(5)	105.5	105.5(5)
<i>p</i> ₁₉	C(3)-C(4)-C(5) in conformer 2	111.5(9)	112.8	112.8(10)
<i>p</i> ₂₀	C(3)-C(4)-C(5)-F(12) in conformer 1	0.0	0.0	
<i>p</i> ₂₁	C(3)-C(4)-C(5)-F(12) in conformer 2	18.4(19)	11.8	
<i>p</i> ₂₂	O(2)-C(3)-C(4)-C(5) in conformer 1	180.0	180.0	
<i>p</i> ₂₃	O(2)-C(3)-C(4)-C(5) in conformer 2	71.5(31)	63.2	
<i>p</i> ₂₄	Sn(1)-O(2)-C(3)-C(4) in conformer1	180.0	180.0	
<i>p</i> ₂₅	Sn(1)-O(2)-C(3)-C(4) in conformer2	-171.6(29)	-179.0	
<i>p</i> ₂₆	Me ₃ twist in conformer 1	0.1(9)	0.0	
<i>p</i> ₂₇	Me ₃ twist in conformer 2	-16.4(73)	1.4	
<i>p</i> ₂₈	Weight of conformer 1	0.24	0.36	

^a Figures in parentheses are the estimated standard deviations of the last digits.

^b Unless stated, parameter definitions apply to both conformers.

Table 6. Interatomic distances (r_a /pm) and amplitudes of vibration (u /pm) for the restrained GED structure of $\text{Me}_3\text{SnO}_2\text{CC}_2\text{F}_5$.^a Only the most significant contributions to the molecular scattering intensity are listed.

No.	Atom pair	Conformer	r_a /pm	u /pm ^b		Restraint
u_1	H(18)-C(6)	1 and 2	109.8	7.7	(fixed)	
u_3	O(9)-C(3)	1 and 2	122.8	3.7(4)		3.7(3)
u_5	C(3)-O(2)	1 and 2	129.2	4.2	(tied to u_3)	
u_7	F(12/13/14)-C(5)	1 and 2	133.7	4.8(3)		4.3(4)
u_9	F(10/11)-C(4)	1 and 2	135.3	4.8	(tied to u_7)	
u_{11}	C(4)-C(5)	1 and 2	153.7	5.0	(fixed)	
u_{12}	C(3)-C(4)	1 and 2	153.7	5.1	(fixed)	
u_{17}	O(2)-Sn(1)	1 and 2	201.6	5.9(6)		5.7(6)
u_{19}	C(6/7/8)-Sn(1)	1 and 2	214.1	4.6(4)		
u_{31}	O(2)...O(9)	1 and 2	226.0	4.9/5.0	(tied to u_{39})	
u_{33}	C(4)...O(3)	1 and 2	234.1	6.9	(tied to u_{39})	
u_{35}	F(10/11)...C(5)	1 and 2	234.8	6.9	(tied to u_{39})	
u_{36}	F(10/11)...C(3)	1	234.8	6.9	(tied to u_{39})	
u_{38}	F(10/11)...C(7)	2	237.0	6.9	(tied to u_{39})	
u_{39}	F(12/13/14)...C(4)	1 and 2	237.7	6.7(4)/6.9		6.9(7)
u_{65}	C(3)...Sn(1)	1 and 2	287.4	6.8(7)/7.3		6.7(7)
u_{76}	O(9)...Sn(1)	1 and 2	311.7	11.3(10)/12.3		10.6(11)
u_{187}	C(4)...Sn(1)	2	426.2	8.2	(tied to u_{217})	
u_{209}	F(10)...Sn(1)	2	455.8	12.6	(tied to u_{217})	
u_{217}	F(10/11)...Sn(1)	1	464.0	12.6(12)		11.9(12)
u_{234}	F(11)...Sn(1)	2	482.6	19.7	(tied to u_{217})	
u_{259}	C(5)...Sn(1)	2	493.0	11.6	(tied to u_{217})	
u_{283}	F(13/14)...Sn(1)	2	522.0	13.3	(tied to u_{317})	
u_{309}	C(5)...Sn(1)	1	545.7	7.7	(tied to u_{317})	
u_{317}	F(13/14)...Sn(1)	1	567.6	14.3(14)		14.1(14)

^a Estimated standard deviations, obtained in the least-squares refinement, are given in parentheses.

^b Amplitudes not refined were fixed at the values obtained using the HF/LanL2DZ-D95 force field.

Table 7. Analysis of F-doped SnO₂ films from fluorinated organotin carboxylate precursors

	1	2	3	6	7	Std^a
Thickness (Å)	3600	5150	3000	3470	2935	3000
Haze (%)	0.56	0.99	0.59	0.39	0.28	< 0.40
Emissivity	0.147	0.118	0.175	0.167	0.304	< 0.150
Sheet Resistance (Ω/□)	13	8	18	16	39	15
Resistivity (× 10 ⁻³ Ω cm)	0.46	0.43	0.54	0.54	1.13	0.50
Fluorine Content (atom%)	1.02	1.02	0.88	1.16	4.80	2.00

^a Typical measurements for a good fluorine-doped tin oxide film derived from separate tin and fluorine sources⁵⁰

Table 8. X-Ray diffraction data for the F-doped SnO₂ films deposited from organotin fluorocarboxylate precursors

(hkl)	Angle (°)	1	2	3	6	7
(110)	26.6	513	175	165	145	127
(101)	33.9	221	332	316	302	154
(200)	37.9	673	566	340	254	21
(111)	39.0	0	0	0	0	0
(210)	42.6	27	27	27	28	0
(211)	51.7	457	537	500	481	154
(220)	54.8	98	40	29	31	3
(002)	57.8	0	0	0	0	0
(310)	61.9	109	122	85	75	19
(112)	64.7	0	27	0	0	0
(301)	66.0	82	66	37	28	9
Total Counts		2180	1893	1499	1344	488
(200) (Total as %)		30.9	29.9	22.7	18.9	4.2
Crystallite Size (Å)		320	193	183	151	^a

^a Could not be calculated

Figure Captions


- Figure 1. Structures determined *ab initio* for $\text{Me}_3\text{SnO}_2\text{CC}_2\text{F}_5$ (**9**) showing the atom numbering scheme; (a) the lowest energy conformer (1) and (b) the conformer higher in energy by 1.2 kJ mol^{-1} .
- Figure 2. The polymeric structure of **6**, showing the labelling scheme used; thermal ellipsoids are at the 30% probability level and hydrogen atoms have been omitted for clarity. Selected geometric data: Sn(1)-C(1) 2.119(6), Sn(1)-C(3) 2.137(7), Sn(1)-C(5) 2.119(6), Sn(1)-O(1) 2.218(4), Sn(1)-O(2') 2.481(4), O(1)-C(7) 1.284(7), O(2)-C(7) 1.224(7) Å; C(1)-Sn(1)-C(3) 127.0(3), C(1)-Sn(1)-C(5) 117.1(3), C(1)-Sn(1)-O(1) 96.0(2), C(1)-Sn(1)-O(2') 85.4(2), C(3)-Sn(1)-C(5) 114.7(3), C(3)-Sn(1)-O(1) 95.1(2), C(3)-Sn(1)-O(2') 87.9(2), C(5)-Sn(1)-O(1) 89.5(2), C(5)-Sn(1)-O(2') 85.6(2), O(1)-Sn(1)-O(2') 174.93(14) °; symmetry operation $1 - x, \frac{1}{2} + y, \frac{1}{2} - z$.
- Figure 3. The structure of **8**, showing the labelling scheme used; thermal ellipsoids are at the 30% probability level. Selected geometric data: Sn(1)-C(5) 2.102(4), Sn(1)-C(6) 2.098(4), Sn(1)-O(1) 2.205(3), Sn(1)-O(3) 2.082(3), Sn(1)-O(5) 2.238(3), C(1)-O(1) 1.271(5), C(1)-O(2) 1.219(5), C(3)-O(3) 1.280(5), C(3)-O(4) 1.214(5) Å; C(5)-Sn(1)-C(6) 140.1(2), C(5)-Sn(1)-O(1) 96.71(14), C(5)-Sn(1)-O(3) 113.7(2), C(5)-Sn(1)-O(5) 91.45(14), C(6)-Sn(1)-O(1) 93.86(14), C(6)-Sn(1)-O(3) 106.12(14), C(6)-Sn(1)-O(5) 89.80(14), O(1)-Sn(1)-O(3) 79.15(11), O(1)-Sn(1)-O(5) 162.35(11), O(3)-Sn(1)-O(5) 83.24(11) °.
- Figure 4. The lattice structure of **8** (viewed along 001) showing the hydrogen bonding interactions.
- Figure 5. Experimental and difference (experimental – theoretical) radial-distribution curves, $P(r)/r$, for $\text{Me}_3\text{SnO}_2\text{CC}_2\text{F}_5$. Before Fourier inversion the data were multiplied by $s.\exp(-0.00002s^2)/(Z_{\text{Sn}}f_{\text{Sn}})(Z_{\text{F}}f_{\text{F}})$.
- Figure 6. Combined experimental and final weighted difference (experimental – theoretical) molecular-scattering intensities for $\text{Me}_3\text{SnO}_2\text{CC}_2\text{F}_5$.
- Figure 7. TGA of **9**

Figure 8. SEM of the F:SnO₂ film deposited from precursor **2**.

Figure 9. Powder XRD of the F:SnO₂ film deposited from precursor **2**. Below is shown the pattern for a randomly oriented samples of SnO₂ (cassiterite, PDF 21-1250).

Fig. 1

(a)

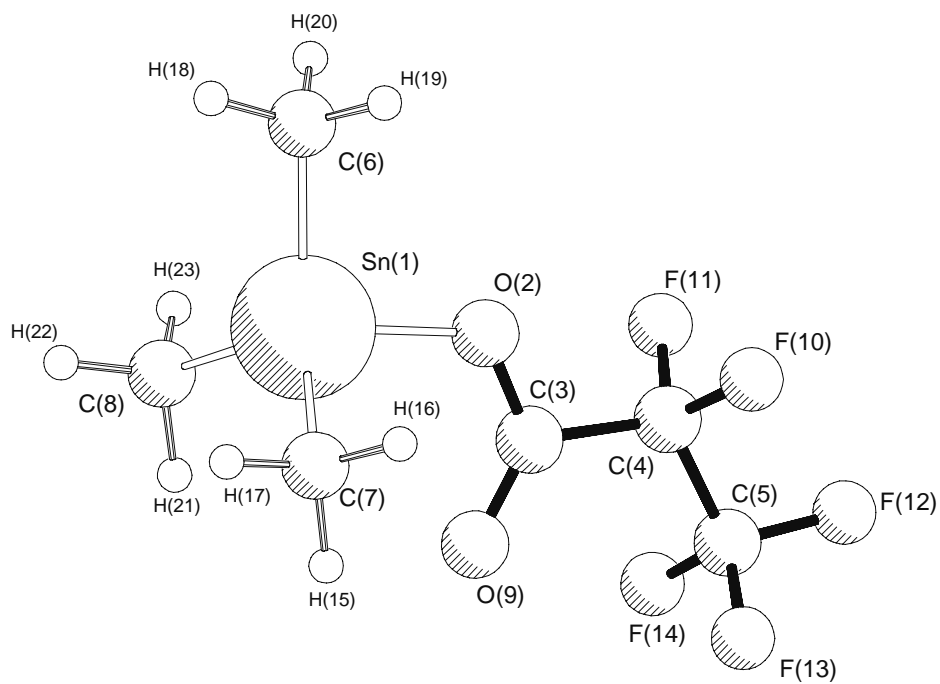

(b)

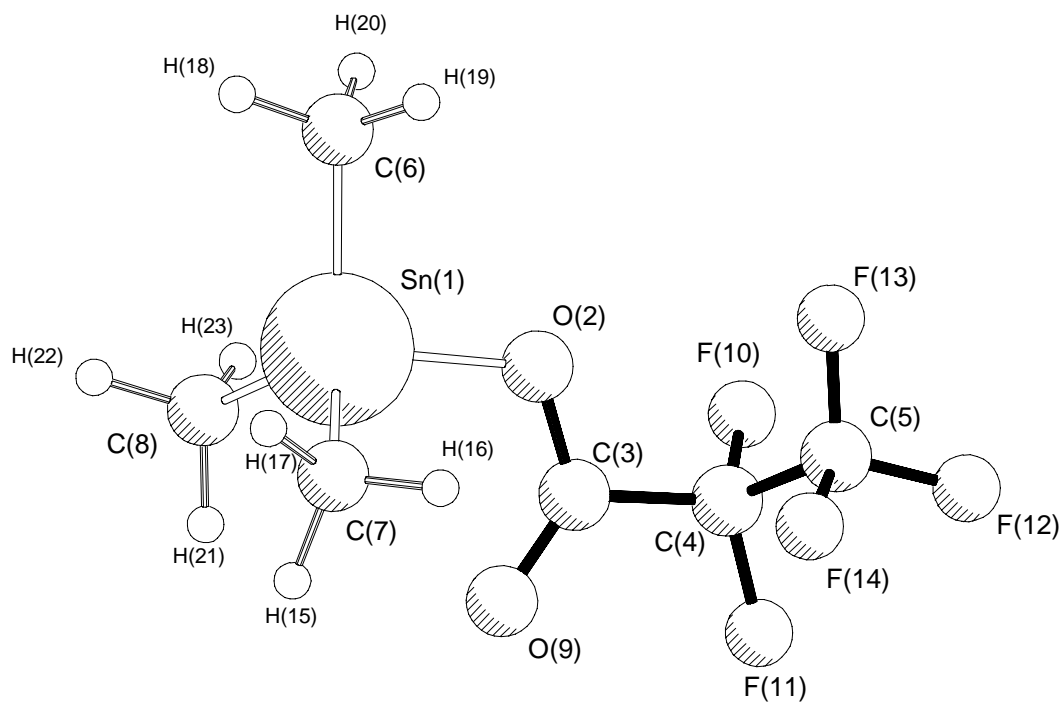


Fig. 2

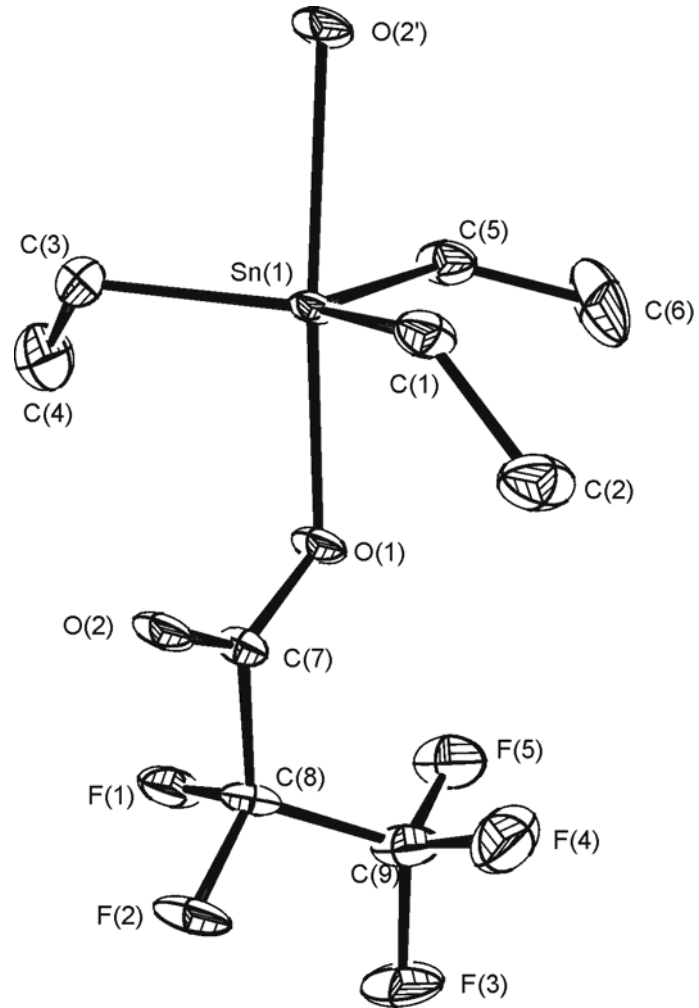


Fig. 3

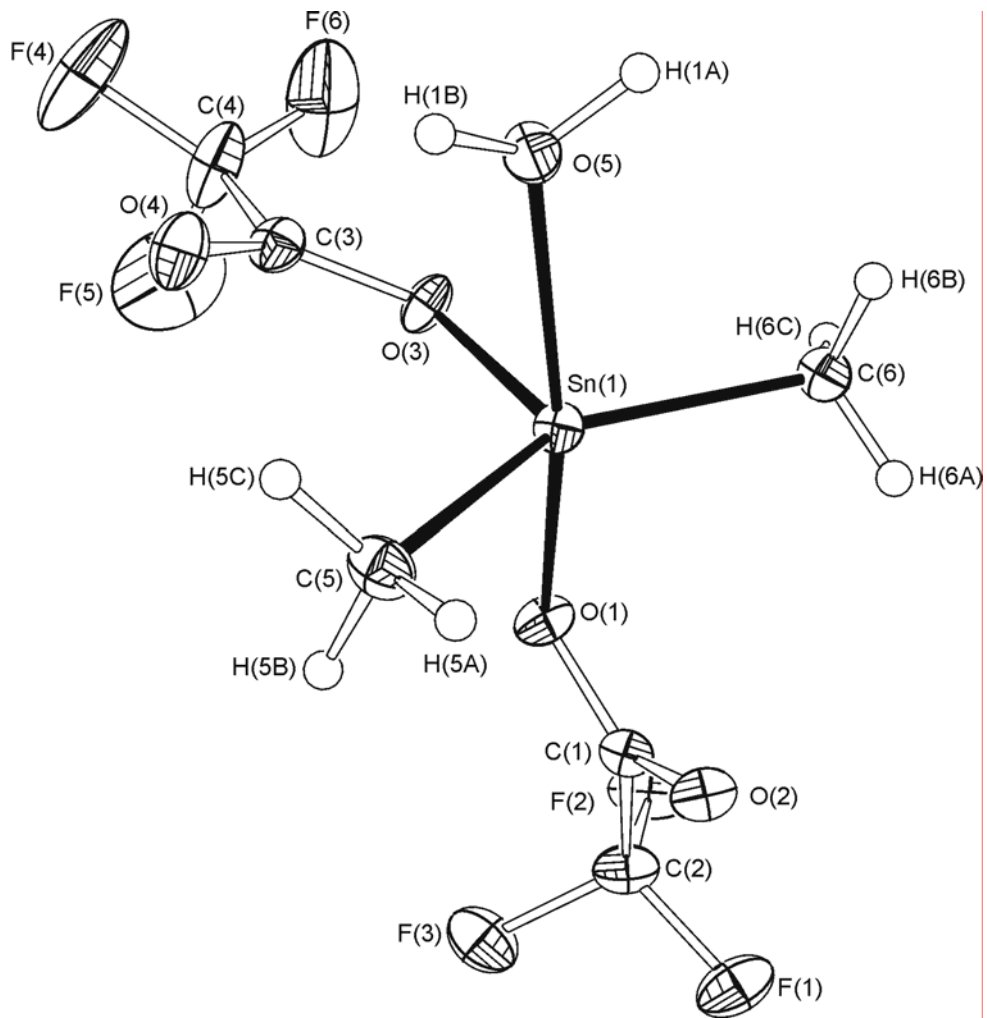


Fig. 4

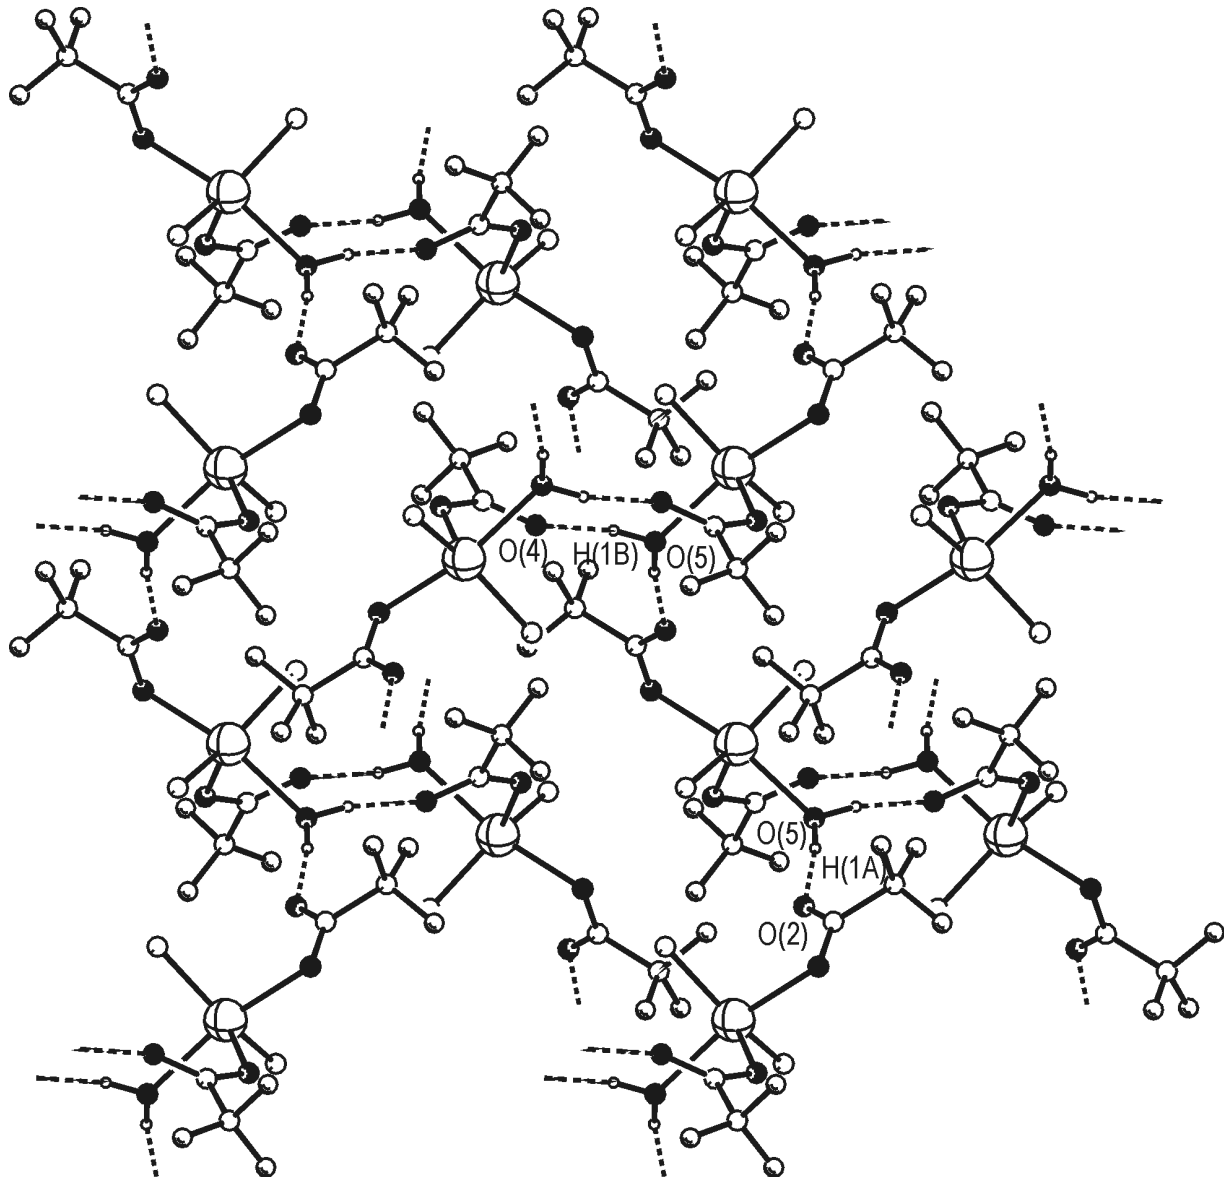


Fig. 5

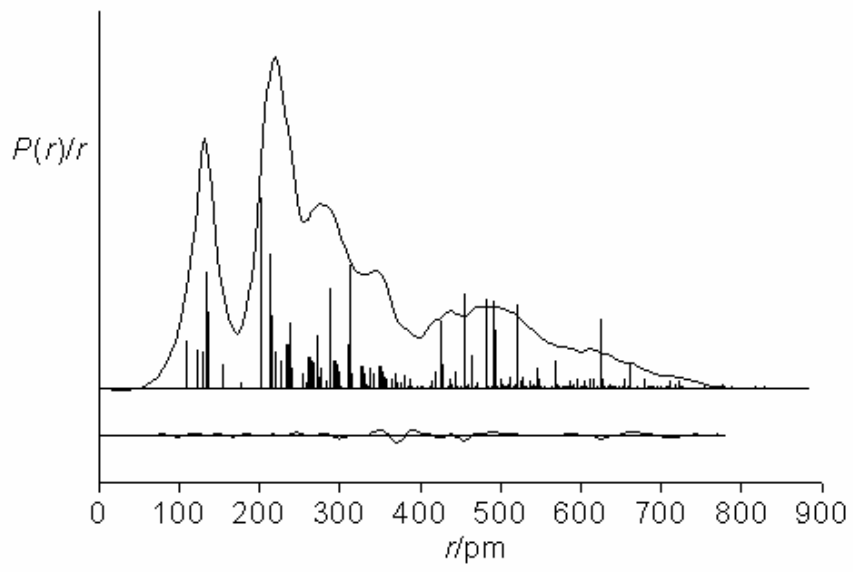


Fig. 6

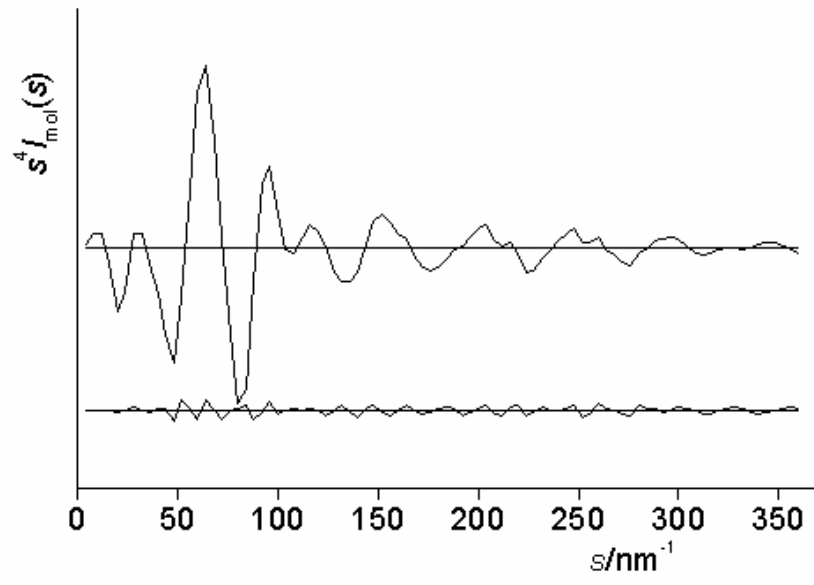


Fig. 7

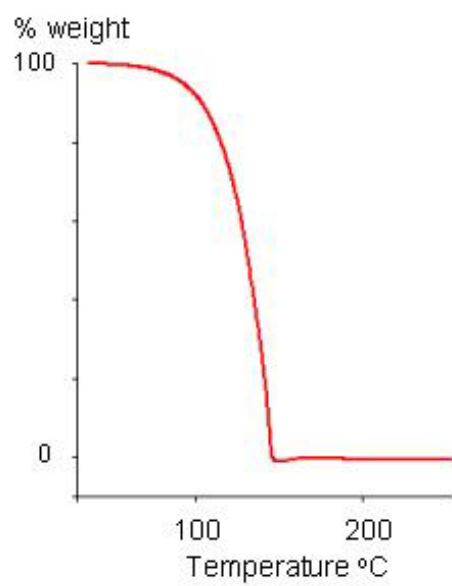


Fig. 8

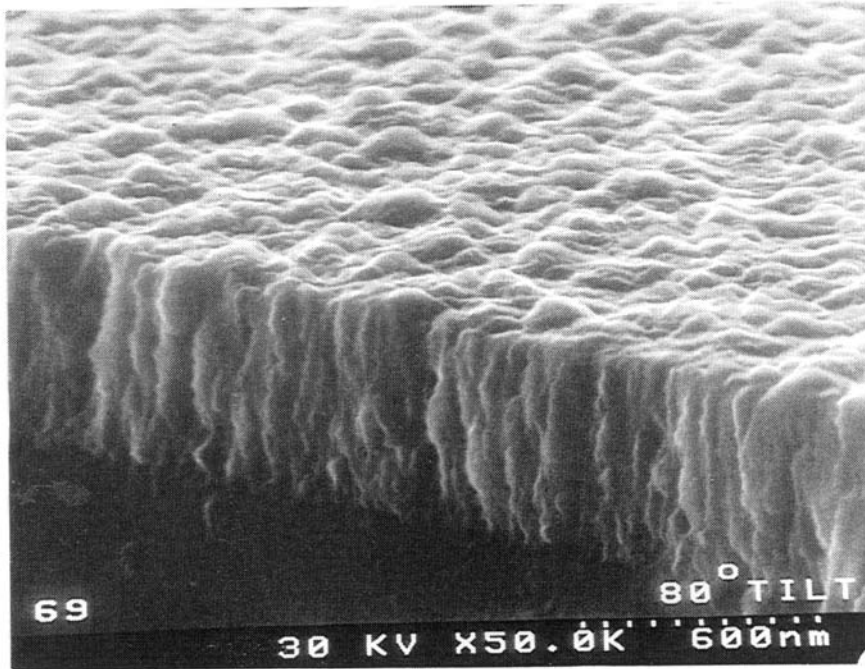


Fig. 9

