



THE UNIVERSITY *of* EDINBURGH

Edinburgh Research Explorer

Dodecanuclear [MnIII₆LnIII₆] species: synthesis, structures and characterization of magnetic relaxation phenomena

Citation for published version:

Tziotzi, TG, Tzimopoulos, DI, Lis, T, Inglis, R & Milios, CJ 2015, 'Dodecanuclear [MnIII₆LnIII₆] species: synthesis, structures and characterization of magnetic relaxation phenomena' Dalton Transactions, vol. 44, no. 26, pp. 11696-11699. DOI: 10.1039/C5DT01695A

Digital Object Identifier (DOI):

[10.1039/C5DT01695A](https://doi.org/10.1039/C5DT01695A)

Link:

[Link to publication record in Edinburgh Research Explorer](#)

Document Version:

Peer reviewed version

Published In:

Dalton Transactions

General rights

Copyright for the publications made accessible via the Edinburgh Research Explorer is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy

The University of Edinburgh has made every reasonable effort to ensure that Edinburgh Research Explorer content complies with UK legislation. If you believe that the public display of this file breaches copyright please contact openaccess@ed.ac.uk providing details, and we will remove access to the work immediately and investigate your claim.



Dalton Transactions

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Journal Name

COMMUNICATION

Dodecanuclear $[\text{Mn}^{\text{III}}_6\text{Ln}^{\text{III}}_6]$ species: Synthesis, structure and characterization of magnetic relaxation phenomena

Received 00th January 20xx,
Accepted 00th January 20xx

Thomas G. Tziotzi,^a Demetrios I. Tzimopoulos,^b Tadeusz Lis,^c Ross Inglis^{*,d} and Constantinos J. Milios^{*,a}


DOI: 10.1039/x0xx00000x

www.rsc.org/

The use of H_3L (= 2-(β -naphthalideneamino)-2-hydroxymethyl-1-propanol) in mixed-metal manganese-lanthanide carboxylate cluster chemistry has led to the isolation of two new dodecametallic heteronuclear isostructural $[\text{Mn}^{\text{III}}_6\text{Ln}^{\text{III}}_6]$ complexes (Ln = Gd, Dy), with the Dy analogue displaying temperature and frequency dependent out-of-phase signals suggesting possible single molecule magnetism behaviour.

The rationalization of the magnetic properties in molecular clusters has been attracting the focus of the scientific community over the last few decades; discrete complexes or polymeric compounds have been found to function as magnetic species, retaining their magnetization below a critical/blocking temperature, thus paving the way for applications in magnetic data storage. The former, termed as Single Molecule Magnets (SMMs),^[1] represent the lower limit in the size-scale of magnetic materials, while the latter, named as Single Chain Magnets (SCMs),^[2] may be regarded as the one-dimensional analogues of SMMs. To further understand and elucidate the phenomena that govern the magnetic behavior of such species, more compounds have to be isolated and studied.

We had previously reported the use of the naphthalene-based triol ligand 2-(β -naphthalideneamino)-2-hydroxymethyl-1-propanol, H_3L (Scheme 1),^[3] in Co(II/III), Ni(II) and Cu(II) chemistry,^[4] while very recently we expanded our studies in mixed-metal Mn/Ln chemistry reporting on a family of octanuclear $[\text{Mn}^{\text{III}}_6\text{Ln}^{\text{III}}_2]$ complexes.^[5] Herein, we move further in Mn/Ln/carboxylate cluster chemistry, and we present the synthesis, structures and magnetic properties of two mixed-metal dodecanuclear $[\text{Mn}^{\text{III}}_6\text{Ln}^{\text{III}}_6]$ clusters (Ln = Gd, Dy).

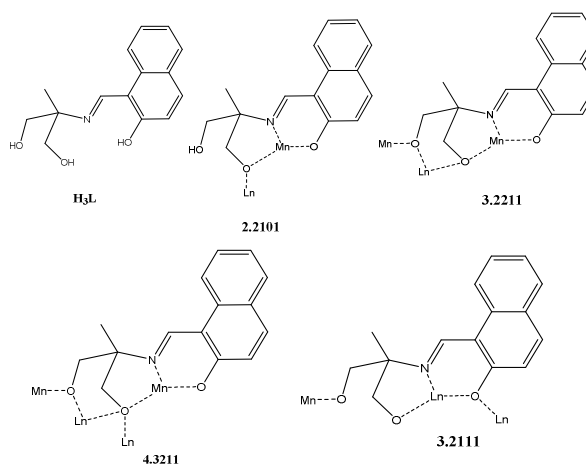

Scheme 1. The structure of H_3L and its coordination modes with corresponding Harris notation in **1** and **2**.

Reaction of $\text{Mn}(\text{O}_2\text{CPh})_2 \cdot 2\text{H}_2\text{O}$, $\text{Ln}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}$ (Ln = Gd, Dy) and H_3L in 1:1:1 ratio in the presence of base, NEt_3 , afforded two new heterometallic dodecametallic clusters with the general formula $[\text{Mn}^{\text{III}}_6\text{Ln}^{\text{III}}_6(\text{OH})_7(\text{H}_2\text{O})_3(\text{O}_2\text{CPh})_{11}(\text{L})_3(\text{HL})_4(\text{NO}_3)] \cdot 6.5\text{MeCN} \cdot \text{H}_2\text{O}$ (Ln: Gd, **1**·6.5MeCN·H₂O; Dy, **2**·6.5MeCN·H₂O). The structure of **1** was solved by single-crystal X-ray crystallography, while complex **2** is proposed to be isostructural with **1** based on elemental analyses, IR spectra and powder XRD patterns (Figs S1 and S2). Cluster **1** crystallizes in the triclinic P-1 space group (Figure 1, top); its magnetic core (Figure 1, bottom) consists of a central Gd^{III} ion (Gd1) which forms a $[\text{Gd}_3\text{Mn}(\text{OH})_3(\text{OR})]$ cubane-like unit with Gd3, Gd2 and Mn1 *via* three $\mu_3\text{-OH}^-$ and one $\mu_3\text{-OR}^-$ groups. In addition, Gd1 participates in the formation of two defective cubanes; one consisting of Gd1, Gd5 and Mn3 *via* two $\mu_3\text{-OH}^-$, one monoatomic $\mu\text{-O}_{\text{NO}_3}$ and one $\mu\text{-OR}^-$ bridges; and one consisting of Gd1, Gd4 and Mn2 held *via* three $\mu_3\text{-OH}^-$ and one $\mu\text{-OR}^-$ groups and one additional $\mu\text{-H}_2\text{O}$ molecule. Furthermore, on each of these three cubane units, smaller metallic fragments are attached; more specifically, on each of Gd2 and Gd4, a trivalent Mn center is attached *via* two $\mu\text{-OR}^-$

^a Department Of Chemistry, University of Crete, Voutes 71003, Herakleion, Greece. Fax: +30-2810-545001; Tel: +30-2810-545099; E-mail: kamil@chemistry.uoc.gr

^b Department of Chemistry, Aristotle University of Thessaloniki, 54124, Thessaloniki, Greece.

^c Faculty of Chemistry, University of Wroclaw, Joliot-Curie 14, Wroclaw 50-383, Poland.

^d School of Chemistry, The University of Edinburgh, David Brewster Road, EH9 3FJ, Edinburgh, UK. Email: ringlis@staffmail.ed.ac.uk

† Footnotes relating to the title and/or authors should appear here. Electronic Supplementary Information (ESI) available: Full details of the experimental microanalyses and crystallographic data. See DOI: 10.1039/x0xx00000x

bridges, while a quite rare 4.221 (Harris Notation)^[6] nitrate anion is responsible for the bridging of the dimetallic {MnGd(O_R)₂} unit containing Mn5 and Gd6 to Gd3 and Mn3. From the seven ligands present, three are fully deprotonated, L³⁻, while the remaining four are doubly deprotonated, HL²⁻. Concerning the three fully deprotonated ligands, one adopts the 3.2211 coordination mode, one is in the 4.3211 mode and the last assumes the 3.2111 mode. All four of the doubly deprotonated ligands adopt the 2.2101 binding fashion. From the eleven benzoate molecules present in the structure, eight are found in the usual *syn-syn* - η^1 : η^1 : μ mode, while the remaining three coordinate in a terminal monodentate fashion. Finally, the coordination environment is completed by the presence of two terminally bound water molecules. All manganese centers are in the 3+ oxidation state as confirmed by bond-valence sum calculations^[7] (BVS values: 3.10, 3.02, 3.17, 3.00, 3.15 and 3.22, for Mn1, Mn2, Mn3, Mn4, Mn5 and Mn6, respectively), with Mn1, Mn2 and Mn3 being six-coordinate adopting a *Jahn-Teller* distorted octahedral geometry, while Mn4, Mn5 and Mn6 are five-coordinate adopting a square pyramidal geometry (τ values^[8] of 3.53, 2.40 and 1.32 for Mn4, Mn5 and Mn6, respectively).

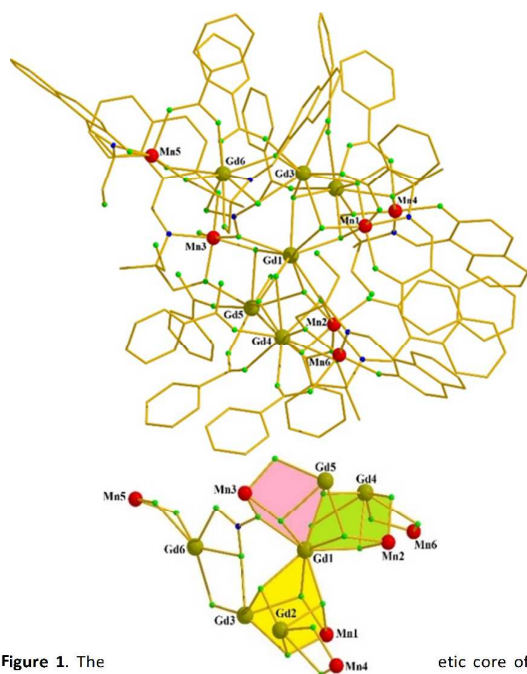


Figure 1. The structure of complex **1** (top) and the Mn core of **1** (bottom). Solvent molecules and H atoms are omitted for clarity. Color code: Mn^{III} = red, Gd^{III} = dark-yellow, O = green, N = blue, C = grey.

Using SHAPE-analysis,^[9] the lanthanide centers can be divided into four categories with respect to their geometry (Figure 2): i) Gd1 and Gd4 are nine-coordinate adopting spherical capped square antiprismatic geometry, ii) Gd2 is eight-coordinate with a triangular dodecahedral geometry, iii) Gd3 and Gd5 are eight-coordinate adopting square antiprismatic geometry, and iv) Gd6 is nine-coordinate with a capped square antiprismatic geometry.


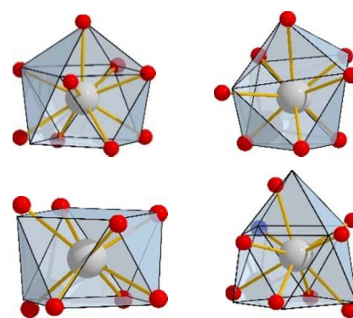


Figure 2. The coordination polyhedra for the lanthanide centers present in **1**; Gd1 and Gd4 (top-left), Gd2 (top-right), Gd3 and Gd5 (bottom-left) and Gd6 (bottom-right).

Variable temperature dc magnetic susceptibility data was collected for both complexes in the temperature range 5–300 K under an applied field of 0.1 T. These are plotted as $\chi_M T$ versus T plots in Figure 3. For **1**, the room temperature $\chi_M T$ value of 66.65 cm³ K mol⁻¹ is very close to the expected value of 65.25 cm³ K mol⁻¹ for six non-interacting Mn^{III} (with $g = 2.0$) and six non-interacting Gd^{III} ions ($g = 2.00$). Upon cooling the value of $\chi_M T$ increases slightly until ~15 K, below which it increases to a maximum value of 76.81 cm³ K mol⁻¹ at 5 K. For **2**, the room temperature $\chi_M T$ value of 96.72 cm³ K mol⁻¹ is slightly lower than the expected value of 102.57 cm³ K mol⁻¹ for six non-interacting Mn^{III} (with $g = 2.0$) and six non-interacting Dy^{III} ions ($S = 5/2$, $L = 5$, $J = 15/2$, $g_J = 4/3$). Upon cooling the value of $\chi_M T$ remains fairly constant until ~100 K, below which it decreases to a final value of 62.38 cm³ K mol⁻¹ at 5 K.

Figure 3. $\chi_M T$ vs. T plot for complexes **1** ([Mn₆Gd₆]) and **2** ([Mn₆Dy₆]) under an applied dc field of 0.1 T.

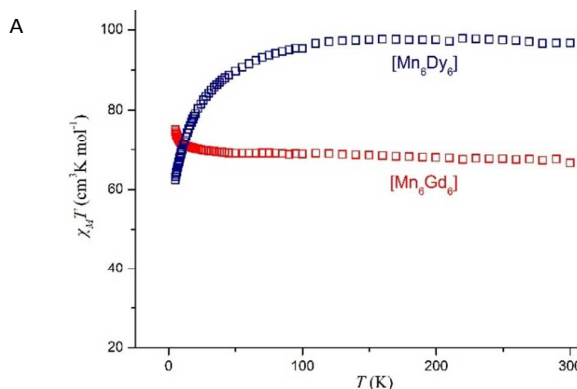

closer inspection of the two structures reveals that there are no bridges between Mn pairs with three or less bridging atoms, therefore suggesting that for **1** magnetic behavior mainly results from the Mn^{III}-Gd^{III} and Gd^{III}-Gd^{III} interactions. Of course, this is impossible to verify by means of fitting or simulating the magnetic susceptibility data due to the large size of the cluster.

In order to establish the ground state for **1** variable temperature and variable field dc magnetization data were collected in the ranges 2–7 K and 0.5–7 T. However, no satisfactory fit of the data was possible employing a model that assumes only the ground state is populated, possibly due

to the presence of the Gd^{III} ions mediating weak exchange interactions.

Given the large remaining magnetic moment for both clusters at low temperature and the lack of a superposition of the reduced magnetization (*RM*) versus *H/T* data on a single master curve (Figure S3), especially for **2**, suggest the presence of a moderate magnetic anisotropy and/or low-lying excited states, and therefore *ac* magnetic susceptibility measurements were performed on polycrystalline samples of **1** and **2** in the 1.8-8 K range in zero applied dc field and a 3.5 G ac field oscillating at 200-1000 Hz. For complex **2** the in-phase signal decreases upon decreasing temperature, indicating the presence of low-lying excited states with larger “*S*” values than the ground-state (Figure 4, top), while in addition frequency-dependent out-of-phase (χ_M'') signals, almost fully-formed, are observed below ~4.5 K (Figure 4, bottom), suggesting possible single molecule magnetism behaviour. On the contrary, complex **1** displays no out-of-phase signals.

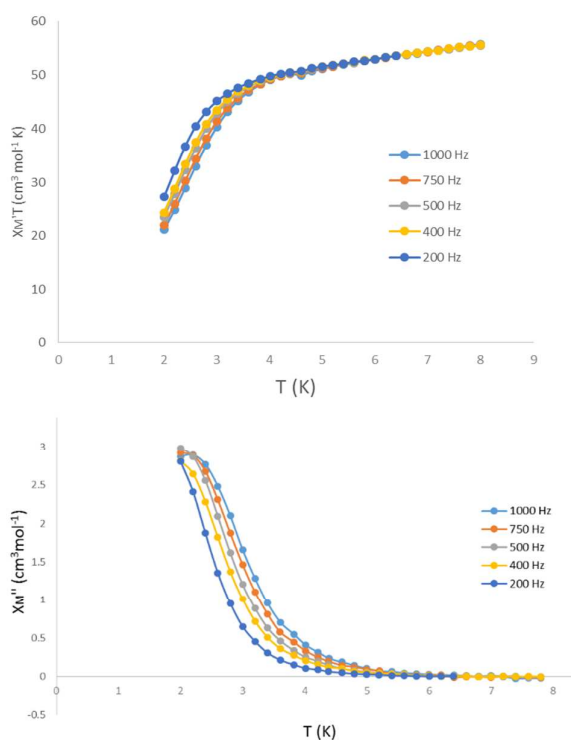


Figure 4. Plot of the in-phase χ_M' T (top) and out-of-phase χ_M'' signals (bottom) for **2** in *ac* susceptibility studies vs. *T* in a 3.5 G oscillating field at the indicated frequencies.

Complexes **1** and **2** join a very restricted family of [Mn₆Ln₆] complexes, comprising cluster [Mn^{III}₄Mn^{IV}₂Dy₆(H₂shi)₄(Hshi)₂(shi)₁₀(MeOH)₁₀(H₂O)₂·9MeOH·8H₂O (H₃shi = salicylhydroxamic acid) which also functions as a SMM,^[10] and cluster [Mn^{II}₆Dy₆(OH)₂(O₃PCH₂Ph)₆(O₂C^tBu)₁₆]·5MeCN,^[11] while **1** and **2** are the first examples containing exclusively trivalent manganese ions.

Conclusions

In conclusion, two new heterometallic dodecanuclear [Mn^{III}₆Ln₆] (Ln = Gd, Dy) clusters were synthesized by the use of the H₃L (= 2-(β-naphthalideneamino)-2-hydroxymethyl-1-propanol) ligand in mixed-metal manganese-lanthanide carboxylate cluster chemistry, and their magnetic properties were studied, revealing possible single molecule magnetism behaviour for the Dy analogue. Furthermore, clusters **1** and **2** represent elegant examples of how a small change in a reaction can affect the identity of the products, since in the absence of carboxylate ligands octanuclear [Mn^{III}₆Ln^{III}₂] species were obtained.^[5]

Acknowledgements

CJM would like to thank The Excellence Grant (ARISTEIA-2691) for funding. RI would like to thank The Royal Society of Edinburgh for funding. DIT would like to thank the 89439/2012 Grant of the Aristotle University of Thessaloniki.

Notes and references

§ Crystal data for **1**: C₁₉₅H_{190.50}Gd₆Mn₆N_{14.50}O₅₇, M = 4922.25, triclinic, space group P-1, a = 18.252 (6) Å, b = 19.702 (7) Å, c = 31.519 (10) Å, α = 82.74 (4)°, β = 78.67 (4)°, γ = 65.87 (4)°, V = 10129 (7) Å³, Z = 2, T = 80 K, R1 (I > 2σ) = 0.11 and wR2 (all data) = 0.291 for 67341 reflections collected, 18007 observed reflections (I > 2σ(I)) of 41988 (Rint = 0.082) unique reflections and 2145 parameters, GOF = 1.05. CCDC reference number: 1063249.

- See for example: G. Aromi and E. K. Brechin, *Struct. Bonding*, 2006, **122**, 1; R. Bircher, G. Chaboussant, C. Dobe, H. U. Güdel, S. T. Ochsenbein, A. Sieber and O. Waldman, *Adv. Funct. Mater.*, 2006, **16**, 209; D. Gatteschi and R. Sessoli, *Angew. Chem., Int. Ed.*, 2003, **42**, 268; G. Christou, D. Gatteschi, D. N. Hendrickson, and R. Sessoli, *MRS Bull.*, 2000, **25**, 66; C. J. Milios and R. E. P. Winpenny, *Struct. Bond.*, 2015, **164**, 1; D. N. Woodruff and R. E. P. Winpenny, R. A. Layfield, *Chem. Rev.* 2013, **113**, 5110; P. Zhang, Y.-N. Guo and J. Tang, *Coord. Chem. Rev.*, 2013, **257**, 1728; H. L. C. Feltham and S. Brooker, *Coord. Chem. Rev.*, 2014, **276**, 1; J. D. Rinehart and J. R. Long, *Chem. Sci.*, 2011, **2**, 2078; N. Magnani, *Int. J. Quantum Chem.*, 2014, **114**, 755; P. Zhang, L. Zhang and J. Tang, *Dalton Trans.*, 2015, **44**, 3923; C.-I. Yang, Z.-Z. Zhang and S.-B. Lin, *Coord. Chem. Rev.*, 2015, **289**, 289.
- Representative refs and refs therein: A. Caneschi, D. Gatteschi, N. Lalioti, C. Sangregorio, R. Sessoli, G. Venturi, A. Vindigni, A. Rettori, M. G. Pini and M. A. Novak, *Angew. Chem., Int. Ed.*, 2001, **40**, 1760; R. Clérac, H. Miyasaka, M. Yamashita and C. Coulon, *J. Am. Chem. Soc.*, 2002, **124**, 12837; L. Bogani, A. Vindigni, R. Sessoli and D. Gatteschi, *J. Mater. Chem.*, 2008, **18**, 4750; C. Coulon, H. Miyasaka and R. Clérac, *Struct. Bonding*, 2006, **122**, 163; H. Miyasaka and M. Yamashita, *Dalton Trans.*, 2007, 399; H.-L. Suna, Z.-M. Wang and S. Gao, *Coord. Chem. Rev.*, 2010, **254**, 1081; W.-X. Zhang, R. Ishikawa, B. Breedlove and M. Yamashita, *RSC Adv.*, 2013, **3**, 3772; D. Gatteschi and A. Vindigni, *Molecular Magnets in "Nanoscience and Technology"* book series, Eds. J. Bartolomé, J. F. Fernández and F. Luis, Springer-Verlag: Berlin Heidelberg, 2014; C. Coulon, Vivien Pianet and R. Clérac, *Struct. Bonding*, 2015, **164**, 143; R. Lescouëzec, J. Vaissermann, C. Ruiz-Pérez, F. Lloret, R. Carrasco, M. Julve, M. Verdager, Y. Dromzee, D. Gatteschi and W. Wernsdorfer, *Angew. Chem. Int. Ed.*, 2003, **42**, 1483; H.

- Miyasaka, M. Julve, M. Yamashita and R. Clérac, *Inorg. Chem.*, 2009, **48**, 3420; J. Ferrando-Soria, D. Cangussu, M. Eslava, Y. Journaux, R. Lescouëzec, M. Julve, F. Lloret, J. Pasán, C. Ruiz-Pérez, E. Lhotel, C. Paulsen and E. Pardo, *Chem. Eur. J.*, 2011, **17**, 12482; T. Liu, H. Zheng, S. Kang, Y. Shiota, S. Hayami, M. Mito, O. Sato, K. Yoshizawa, S. Kanegawa and C. Duan, *Nat. Commun.* 2013, **4**, 2826.
- 3 C. P. Rao, A. Sreedhara, P. V. Rao, B. M. Verghese, E. Kolehmainen, N. K. Lokanath, M. A. Sridhar and J. S. Prasad, *J. Chem. Soc., Dalton Trans.* 1998, 2383.
 - 4 A. B. Canaj, D. I. Tzimopoulos, A. Philippidis, G. E. Kostakis and C. J. Milios, *Inorg. Chem.*, 2012, **51**, 10461.
 - 5 T. G. Tziotzi, D. A. Kalofolias, D. I. Tzimopoulos, M. Siczek, T. Lis, R. Inglis and C. J. Milios, *Dalton Trans.*, 2015, **44**, 6082.
 - 6 R. A. Coxall, S. G. Harris, D. K. Henderson, S. Parsons, P. A. Tasker and R. E. P. Winpenny, *J. Chem. Soc., Dalton Trans.*, 2000, 2349.
 - 7 I. D. Brown and D. Altermatt, *Acta Crystallogr., B*, 1985, **41**, 244; H.H. Thorpe, *Inorg. Chem.*, 1992, **31**, 1585.
 - 8 A. W. Addison, T. N. Rao, J. Reedijk, J. van Rijn and G. C. Verschoor, *J. Chem. Soc., Dalton Trans.*, 1984, 1349.
 - 9 M. Llunell, D. Casanova, J. Girera, P. Alemany and S. Alvarez, SHAPE, version 2.0, Barcelona, Spain 2010.
 - 10 C. M. Zaleski, E. C. Depperman, J. W. Kampf, M. L. Kirk and V. L. Pecoraro, *Angew. Chem. Int. Ed.*, 2004, **43**, 3912.
 - 11 Y.-Z. Zheng, E. M. Pineda, M. Helliwell and R. E. P. Winpenny, *Chem. Eur. J.*, 2012, **18**, 4161.

Two dodecametallic heteronuclear manganese-lanthanide $[\text{Mn}^{\text{III}}_6\text{Ln}^{\text{III}}_6]$ (Ln= Gd, Dy) complexes were isolated and characterized by magnetic measurements.

