



UNIVERSITY OF LEEDS

This is a repository copy of *Embodied carbon dioxide in concrete: Variation with common mix design parameters*.

White Rose Research Online URL for this paper:  
<http://eprints.whiterose.ac.uk/86867/>

Version: Accepted Version

---

**Article:**

Purnell, P and Black, L [orcid.org/0000-0001-8531-4989](http://orcid.org/0000-0001-8531-4989) (2012) Embodied carbon dioxide in concrete: Variation with common mix design parameters. *Cement and Concrete Research*, 42 (6). pp. 874-877. ISSN 0008-8846

<https://doi.org/10.1016/j.cemconres.2012.02.005>

---

© 2012 Elsevier Ltd. Licensed under the Creative Commons Attribution-NonCommercial-NoDerivatives 4.0 International <http://creativecommons.org/licenses/by-nc-nd/4.0/>

**Reuse**

Unless indicated otherwise, fulltext items are protected by copyright with all rights reserved. The copyright exception in section 29 of the Copyright, Designs and Patents Act 1988 allows the making of a single copy solely for the purpose of non-commercial research or private study within the limits of fair dealing. The publisher or other rights-holder may allow further reproduction and re-use of this version - refer to the White Rose Research Online record for this item. Where records identify the publisher as the copyright holder, users can verify any specific terms of use on the publisher's website.

**Takedown**

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing [eprints@whiterose.ac.uk](mailto:eprints@whiterose.ac.uk) including the URL of the record and the reason for the withdrawal request.



[eprints@whiterose.ac.uk](mailto:eprints@whiterose.ac.uk)  
<https://eprints.whiterose.ac.uk/>

1 **Embodied carbon dioxide in concrete: variation with common mix design**  
2 **parameters**

3

4 *Phil Purnell \*, Leon Black*

5 *\* P.Purnell@leeds.ac.uk, +44 (0) 113 343 0370*

6 *Institute for Resilient Infrastructure, School of Civil Engineering, University of Leeds,*

7 *Leeds, LS2 9JT, UK.*

8

9 **Keywords:** C - Compressive Strength; E- Concrete; Embodied carbon dioxide.

10

11 **Abstract**

12 The transition towards a low-carbon infrastructure requires an understanding of the  
13 embodied carbon (eCO<sub>2</sub>) associated with concrete. However, much current work on  
14 eCO<sub>2</sub> underestimates the complexity of its relationship with concrete mix design. This  
15 paper demonstrates how eCO<sub>2</sub> of concrete is not a simple function of strength. Rather,  
16 for a given strength, considerable eCO<sub>2</sub> savings can be made by careful attention to  
17 basic mix design. Replacement of cement with PFA (pulverised fuel ash) can achieve  
18 considerable savings; additionally, using a concrete of lower workability, employing a  
19 superplasticiser, using crushed rather than rounded aggregate and using a higher  
20 strength of cement can have comparably significant effects. The analysis is presented  
21 in terms of embodied carbon per unit strength; this shows that there is an optimum  
22 strength for all concretes (with regard to minimising eCO<sub>2</sub> per unit of structural  
23 performance) of between 50 and 70 MPa.

24

25

## 26 **1. Introduction**

27 Carbon dioxide emissions attributed to construction in the UK amount to almost 52  
28 Mt per year [1], accounting for 9.6% of the UK's 'carbon footprint' [2]. Legislation  
29 binds the UK Government to an 80% reduction in CO<sub>2</sub> emissions by 2050, and hence  
30 their reduction is a government priority [3]. Since operational CO<sub>2</sub> (oCO<sub>2</sub>), defined as  
31 those emissions associated with the energy used in heating, lighting, air-conditioning,  
32 IT services, maintenance etc [4], makes the greatest contribution to emissions, current  
33 guidelines rightly concentrate exclusively on reducing these emissions.

34

35 Yet the embodied CO<sub>2</sub> (eCO<sub>2</sub>) emissions – those associated with the construction and  
36 disposal phase of the lifecycle – are a significant proportion of the total lifecycle  
37 emissions. Sturgis and Roberts [4] quote figures of 30% for housing, 20% for a  
38 supermarket, 45% for an office and 60% for a warehouse. This proportion will  
39 approach unity as low-carbon operational paradigms – better insulation, low-energy  
40 lighting, fabric energy storage etc. – are introduced, pushing towards the target of  
41 reducing oCO<sub>2</sub> to zero by 2019 [5]. Furthermore, for infrastructure, operational  
42 emissions are either negligible (e.g. for a dam) or attributed to users (e.g. exhaust  
43 emissions from vehicles using a bridge). Thus it is important that we begin to  
44 understand the eCO<sub>2</sub> associated with construction.

45

46 Most analyses of eCO<sub>2</sub> in construction conclude that it is dominated by the emissions  
47 associated with the industrial production of materials [e.g. 6]. Concrete is the most  
48 predominant construction material, with global production approaching  $20 \times 10^{12}$  kg  
49 per annum, significantly more than all other construction materials combined; and  
50 increasing at several percentage points annually as large developing nations upgrade

51 and install infrastructure [7]. Thus, formulating policy for reducing the overall carbon  
52 emissions of the built environment will require that the eCO<sub>2</sub> of concrete is known  
53 with some degree of confidence, and that approaches to maximise the efficiency of  
54 concrete use are developed.

55

56 In contrast to many other major structural materials, concrete is a complex composite.  
57 Its wide palette of engineering properties – compressive strength, workability,  
58 permeability, chemical resistance etc – is under the nominal control of the structural  
59 designer, rather than the materials supplier. Each of these properties can vary  
60 dramatically depending on mix recipe; in most cases there are many mix recipes that  
61 will result in a concrete which fulfils the designer's requirements. This multiplicity  
62 offers the structural designer an effectively infinite range of concretes, each of which  
63 will have its own eCO<sub>2</sub> value. Any notion that concrete has a single, easily defined  
64 eCO<sub>2</sub> is clearly deficient.

65

66 Despite this, many commentators have published eCO<sub>2</sub> values for concrete, either as  
67 individual values or a small range depending on certain properties (mainly  
68 compressive strength grade and the use of supplementary cementitious materials).  
69 Hammond and Jones [8] give a general value of 0.107 and a monotonic relationship  
70 between eCO<sub>2</sub> (0.061 – 0.188) and characteristic cube strength (8 – 50 MPa) for CEM  
71 I and CEM II concretes (see below). However, they do advise against the  
72 indiscriminate use of these values. Meanwhile, Hacker [9] uses a value of 0.200 with  
73 no strength discrimination, whilst Harrison [10] uses 0.13 for plain concrete and 0.24  
74 for “2% reinforced”; the additional CO<sub>2</sub> attributable to the steel. Among those  
75 reporting on a volumetric basis, Flower & Sanjayan [11] use values of 0.225 - 0.322

76 kg/m<sup>3</sup> for normal and blended cement concretes, corresponding to eCO<sub>2</sub> ~ 0.09 –  
77 0.12. However, none of these studies give systematic details of mix designs (i.e.  
78 relative proportions of constituent materials).

79

80 The purpose of this paper is to demonstrate how changing some of the independent  
81 mix design variables that have the greatest effect on a concrete mix – cement grade,  
82 crushed vs uncrushed aggregate, use of superplasticisers, use of PFA (pulverised fuel  
83 ash, also known as fly ash) and workability (i.e. slump) – affects eCO<sub>2</sub> in traditional  
84 concrete mixes. It will also introduce a ‘normalised’ eCO<sub>2</sub> value to account for the  
85 trade-off between higher cement content (and thus increased eCO<sub>2</sub> per unit of  
86 material) and higher strength (and thus use of less material and decreased eCO<sub>2</sub> per  
87 component), and by extension the concept of a functional unit for correct analysis of  
88 the eCO<sub>2</sub> of structural elements. This goes some way towards aligning the treatment  
89 of such problems from an engineering perspective with formal life cycle analysis  
90 methods (e.g. ISO 14040).

91

## 92 **2. Methodology**

93 In summary, we calculated the eCO<sub>2</sub> and predicted mean compressive strength at 28  
94 days standard curing of cube specimens (target mean strength) for 512 theoretical,  
95 ‘virtual’ concrete mixes, as a function of the most important mix design variables.  
96 These model mixes were derived from a widely accepted and validated mix design  
97 method used throughout UK academia and industry. Whilst it was clearly not feasible  
98 to manufacture and test over 500 mixes in a preliminary study of this nature, a number  
99 of real trial mixes were prepared, cured and tested for compressive strength in the lab  
100 to check the validity of the model.

101

102 The BRE mix design method [12] was used as the basis for this work by transferring  
103 the graphical method therein to a spreadsheet in order that the entire range of  
104 theoretical mix designs could be explored. The five design variables having the  
105 greatest effect on the concrete mix specification were varied from their maximum to  
106 their minimum values, i.e.:

107

- 108 • CEM I Cement strength class: 52.5 or 42.5 MPa
- 109 • Addition of PFA: 0% or 40% replacement of cement
- 110 • Use of super-plasticiser (1% by mass of binder content as liquid additive): no  
111 or yes
- 112 • Aggregate type: uncrushed or crushed
- 113 • Slump value: low (L, 0 – 10 mm) or high (H, 60 – 180 mm).

114

115 All other mix design factors (aggregate size, grading etc) were kept constant as they  
116 have minimal effect on strength for normal concrete mixes. This approach gave  $2^5 =$   
117 32 mix families, as described in table 1. For each mix family, individual mixes were  
118 designed for 16 target mean compressive cube strengths between 17 and 120 MPa  
119 (approximately corresponding to the 16 characteristic strength classes between C8/10  
120 and C100/115 specified in Eurocode 2 [13]; assuming a standard deviation in  
121 compressive strength of 4 MPa), giving a total of 512 virtual mix designs (i.e. 32 mix  
122 families  $\times$  16 strength classes).

123

124 The embodied carbon dioxide (on a mass basis i.e. kg CO<sub>2</sub> per kg of concrete and thus  
125 a dimensionless quantity) for each virtual mix was calculated according to the

126 contribution from each of its constituents, using the values given in table 2 [8, 11, 14,  
127 15]. These values are considered by the authors to be the most authoritative available  
128 in the open literature. Note that the eCO<sub>2</sub> value for the concrete is overwhelmingly  
129 dominated (>95% in most cases) by that associated with the cement content.

130

131 To validate the strength predictions of the model, eight real trial mixes for mean  
132 compressive cube strengths of between 27 and 70 MPa were manufactured in  
133 triplicate. A plot of predicted virtual strength vs. measured real strength at 28 days  
134 was obtained and the resultant calibration curve was linear with slope of 1.04 and a  
135 correlation coefficient of >0.95 i.e. the model tended to slightly, but not significantly,  
136 underestimate strength.

137

### 138 **3. Results & Discussion.**

139 Figure 1a shows eCO<sub>2</sub> vs. target mean strength for all 32 concrete mix families. This  
140 represents the entire envelope of data generated by the mix design model; each curve  
141 corresponds to a single mix family. The figure is intended merely to show general  
142 trends and thus for clarity, only the maximal (mix family 18) and minimal (mix  
143 family 15) curves are labelled. As expected, eCO<sub>2</sub> rises with concrete strength, owing  
144 to the higher cement contents required of such mixes to preserve workability and  
145 compaction. However, for a given concrete strength, eCO<sub>2</sub> varies by a factor of ~3;  
146 thus, any notion that eCO<sub>2</sub> is a simple monotonic function of strength is clearly overly  
147 simplistic and explains the scatter encountered by Habert [16]. The eCO<sub>2</sub> of the  
148 concrete mixes where the binder is a blend of CEM I and PFA (dashed lines in Figure  
149 1) is typically lower than the eCO<sub>2</sub> of concrete mixes with only CEM I (solid lines in  
150 Figure 1). However, this is not always the case. It is possible to have a PFA-CEM I

151 concrete with a higher eCO<sub>2</sub> than a CEM I concrete of the same strength; i.e. there is  
152 some overlap between the sets of dashed and solid lines in Figure 1. Thus the  
153 commonly held view that a concrete made with a blended cement binder will  
154 automatically and necessarily have a lower carbon footprint than a traditional concrete  
155 is also erroneous.

156

157 As presented in Figure 1, the observation that eCO<sub>2</sub> increases with compressive  
158 strength is not surprising, and has been reported elsewhere [8, 11]. However, it is not  
159 realistic to consider the eCO<sub>2</sub> of concrete solely in terms of its mass. It is clear that to  
160 resist a given compressive load, using a higher strength concrete will result in the use  
161 of a lower mass of concrete. Rather, the concrete should be considered in terms of its  
162 structural performance; thus the simple eCO<sub>2</sub> plot in Figure 1a is of limited value.  
163 Therefore, Figure 1b normalises eCO<sub>2</sub> with respect to compressive strength.

164

165 The embodied CO<sub>2</sub> of concrete is dominated by the contribution from the cement and  
166 so rises approximately linearly with cement content. Yet the relationship between  
167 strength and cement content is non-linear and dominated by the well-known (and also  
168 non-linear) interaction with water:binder ratio [see e.g. 17] . Consequently, as clearly  
169 demonstrated in Figure 1b, there is an optimum concrete strength with regard to  
170 minimising eCO<sub>2</sub> per unit of structural performance, at around 60 MPa. For weaker  
171 concretes, the reduction in eCO<sub>2</sub> associated with lower cement content is outweighed  
172 by the need to use more concrete for any given structural component. For stronger  
173 concretes, the reduction in material use afforded by the increased strength is  
174 outweighed by the increased cement content required to achieve that strength. Using  
175 the optimum strength concrete will result in eCO<sub>2</sub> reductions of up to 40% for any



176 given mix family. Fortunately the minima are quite broad, which allows the designer  
177 to retain considerable flexibility in mix design without a large carbon penalty.

178

179 In addition to the data presented in Figures 1a and 1b, it was also possible to use the  
180 raw data to extract the effect of the individual mix design variables (there is negligible  
181 interaction) and assess their relative importance. As expected, an important factor was  
182 moving from 100% CEM I binder to 40% replacement by PFA, producing a reduction  
183 in  $eCO_2$  (for a given concrete strength) of  $35 \pm 1\%$ . Note that this is contrary to the  
184 simple expectation that replacing 40% of the PFA reduces  $eCO_2$  by  $\sim 40\%$ . For a  
185 given target 28 day strength, adding PFA requires that the water/binder mass ratio  
186 (w/b) be reduced to compensate for the lower reactivity of the PFA (a  $k$  value of 0.3  
187 has been assumed, [12]). Even though PFA is  $\sim 30\%$  less dense than cement and thus  
188 replacing cement with PFA tends to increase binder volume, the net effect is that in  
189 order to keep the paste (i.e. cement + PFA + water) fraction of the concrete constant,  
190 the total binder mass content must be increased by  $\sim 13\%$  and thus the cement content  
191 is only reduced by  $\sim 35\%$ , not 40%.

192

193 The specification of workability had a surprisingly large effect on  $eCO_2$ . Moving from  
194 a slump class of 60-180 mm to 0-10 mm decreased  $eCO_2$  by  $35 \pm 1\%$  i.e. was as  
195 significant a factor as the use of PFA. Increasing the workability of a normal concrete  
196 mix (all other factors remaining the same) requires that the water content of the mix  
197 be increased. In order that the w/b ratio remains constant, preserving strength, the  
198 binder content must again be increased correspondingly.

199

200 Use of a superplasticiser was found to reduce overall eCO<sub>2</sub> by  $26 \pm 1\%$ , since a given  
201 workability could be achieved at reduced water content and thus to keep the w/b ratio  
202 constant the binder content could be reduced correspondingly. This saving could be  
203 achieved because the eCO<sub>2</sub> imparted by the superplasticiser itself was negligible.

204

205 Changing the aggregate type from uncrushed to crushed, or the cement strength class  
206 from 42.5 to 52.5 MPa, both had a relatively small effect on eCO<sub>2</sub> (savings of  $9 \pm 1\%$   
207 and  $7 \pm 1\%$  respectively). Therefore, to more clearly visualise the impact of the key  
208 variables on eCO<sub>2</sub>, the data are re-plotted in Figure 2, with the curves for cement  
209 strength class 42.5 and/or uncrushed aggregate having been removed. Additionally,  
210 the curve focuses on the strength range from 20 to 80 MPa, since this is the region in  
211 which extensive laboratory experience suggests we can be confident in the model.

212

213 Overlaid in Figure 2 are eCO<sub>2</sub> and normalised eCO<sub>2</sub> values for selected mix designs  
214 from the literature spanning >20 years [18-20]. The mix designs arrived at via  
215 traditional means [18, 19], fall into the envelope predicted by the model. The designs  
216 supposedly optimised for 'ecological effects' using a neural network model however  
217 [20], would appear to be rather expensive in terms of eCO<sub>2</sub>. The two monotonic  
218 relationships presented by Hammond [8] are also overlaid. They are almost coincident  
219 with the upper bound curves for both normal (mix 4) and PFA (mix 12) concretes.

220

## 221 **Conclusions**

222 This work has shown that it is an oversimplification to consider the embodied carbon  
223 of concrete either as a fixed value or as a direct function of compressive strength. It is  
224 clear that carbon savings may be achieved by carefully considering the mix recipe in

225 detail. Replacement of cement clinker with PFA can achieve considerable savings, as  
226 is often reported, but using a concrete of lower workability, employing a  
227 superplasticiser, using crushed rather than rounded aggregate and/or using a higher  
228 strength of cement can have comparably significant effects. Furthermore, analysing  
229 eCO<sub>2</sub> normalised for compressive strength as a function of mix design clearly  
230 indicates that there is an optimum strength, typically about 60 MPa, at which the  
231 eCO<sub>2</sub> per unit of structural performance is minimised.

232

233 The absolute values presented here should emphatically not be taken as a definitive  
234 guide to the eCO<sub>2</sub> of concrete. Rather, they serve to highlight that considerable CO<sub>2</sub>  
235 savings can be achieved by adjusting everyday parameters without recourse to e.g.  
236 exotic cements.

237

238

239 **Figure captions.**

240

241 Figure 1: variation of eCO<sub>2</sub> (a) and eCO<sub>2</sub> per unit strength (b) for 32 mix families.

242 Solid lines represent concrete with a CEM I binder. Dashed lines represent concrete

243 with a 60% CEM I – 40% PFA binder.

244

245 Figure 2: detail of selected mixes from Figure 1, with selected data points from

246 literature overlaid [8, 18-20]. Closed symbols indicate CEM I mixes; open symbols

247 indicate 30 to 50% cement replacement by PFA. NB. Curves for mixes 12 & 3, and

248 16 & 7 overlap

249

250

251 **Table captions**

252

253 Table 1: Mix design families

254

255 Table 2: eCO<sub>2</sub> values for major concrete constituents.

256

257

258 **References**

---

1 *Low Carbon Construction – Innovation and Growth Team 2010, Final Report.*

HM Government Department for Business, Innovation and Skills, Crown

Copyright, 2010, BIS/11/10/NP, URN 10/1266, 230pp.

- 
- 2 DECC (2009) Statistical release: UK climate change sustainable development indicator: 2009 greenhouse gas emissions, final figures.  
[http://www.decc.gov.uk/en/content/cms/statistics/climate\\_stats/gg\\_emissions/uk\\_emissions/2009\\_final/2009\\_final.aspx](http://www.decc.gov.uk/en/content/cms/statistics/climate_stats/gg_emissions/uk_emissions/2009_final/2009_final.aspx), retrieved 10th October 2011.
  - 3 Climate Change Act 2008. HMSO, UK, 2008. 103pp.
  - 4 S. Sturgis, G. Roberts. Redefining Zero: Carbon Profiling as a solution to whole life carbon emission measurement in buildings. RICS Research Report May 2010. [http://www.rics.org/site/scripts/download\\_info.aspx?fileID=6878](http://www.rics.org/site/scripts/download_info.aspx?fileID=6878) retrieved Nov 2011.
  - 5 Zero carbon for new non-domestic buildings - Consultation on policy options. Department for Communities and Local Government. Communities and Local Government Publications, 2009, Crown Copyright 09BD06162, 67pp.
  - 6 Estimating the Amount of CO<sub>2</sub> Emissions that the Construction Industry can Influence - Supporting material for the Low Carbon Construction IGT Report <http://www.bis.gov.uk/assets/biscore/business-sectors/docs/e/10-1316-estimating-co2-emissions-supporting-low-carbon-igt-report> retrieved 10<sup>th</sup> October 2011.
  - 7 F. Krausman, S. Gingrich, N. Eisenmenger, K.-H. Erb, H. Haberl, M. Fischer-Kowalski, Growth in Global Materials Use, GDP and Population During the 20<sup>th</sup> Century. *Ecological Economics* 68 (2009) 2696–2705.
  - 8 G. P. Hammond, C. I. Jones, Embodied energy and carbon in construction materials. *Proc. Inst. Civ. Eng. – Energ.* 161 (2), 2008, 87-98 and subsequent online revisions available from [www.bath.ac.uk/mech-eng/sert/embodied/](http://www.bath.ac.uk/mech-eng/sert/embodied/).

- 
- 9 J.N. Hacker, T.P. De Saulles, A.J. Minson, M.J. Holmes, Embodied and Operational Carbon Dioxide Emissions from Housing: A Case Study on the Effects of Thermal Mass and Climate Change, *Energy and Buildings* 40 (2008) 375–384
  - 10 G.P. Harrison, E.J. Maclean; S. Karamanlis; L.F. Ochoa. Life cycle assessment of the transmission network in Great Britain. *Energ. Policy* 2010, 38 (7), 3622-3631. DOI:10.1016/j.enpol.2010.02.039
  - 11 D. J. M. Flower, J. G. Sanjayan, Green House Gas Emissions Due to Concrete Manufacture. *Int J LCA*, 12 (5), 2007, 282–288
  - 12 D. C. Teychenne, R. E. Franklin, H. C. Erntroy, B.K. Marsh Design of normal concrete mixes 2<sup>nd</sup> edition. Building Research Establishment Ltd, Garston, UK, 1997.
  - 13 BS EN 1992-1-1, Eurocode 2: Design of concrete structures. British Standards Institute (BSI), 2007.
  - 14 BCA CSMA UKQAA. Embodied CO<sub>2</sub> of UK cement, additions and combinations. Information Sheet P1. November 2008.  
[http://www.sustainableconcrete.org.uk/low\\_carbon\\_construction/embodied\\_co2.aspx](http://www.sustainableconcrete.org.uk/low_carbon_construction/embodied_co2.aspx), retrieved Nov 2011.
  - 15 Scottish Water 2008, Scottish Water carbon footprint report 2007-2008. Scottish Water.  
[http://www.scottishwater.co.uk/portal/page/portal/SWE\\_PGP\\_NEWS/SWE\\_PGE\\_NEWS/INFO\\_CLIM\\_CHANGE/Scottish%20Water%20carbon%20footprint%20report%20final%202007-2008\\_0.pdf](http://www.scottishwater.co.uk/portal/page/portal/SWE_PGP_NEWS/SWE_PGE_NEWS/INFO_CLIM_CHANGE/Scottish%20Water%20carbon%20footprint%20report%20final%202007-2008_0.pdf), retrieved May 2011.

- 
- 16 G. Habert, N. Roussel, Study of Two Concrete Mix-Design Strategies to Reach Carbon Mitigation Objectives, *Cem. Conc. Comp.* 31 (2009) 397–402.
  - 17 P. Domone, J. Illston, *Construction Materials: their nature and behaviour* 4<sup>th</sup> Ed. Spon, UK, 2010.
  - 18 M. K.Gopalan, M. N. Haque, Mix Design for Optimal Strength Development of Fly Ash Concrete, *Cem. Conc. Res.* 19 (1989), 634-641, 1989.
  - 19 M. I. A. Khokhar, E. Roziere, P. Turcry, F. Grondin, A. Loukili, Mix Design of Concrete with High Content of Mineral Additions: Optimisation to Improve Early Age Strength. *Cem. Conc. Comp.* 32 (2010) 377–385.
  - 20 T. Ji, T. W. Lin, X. Lin. A Concrete Mix Proportion Design Algorithm Based on Artificial Neural Networks. *Cem. Conc. Res.* 36 (2006) 1399 – 1408.






Purnell, Black – “Embodied ... parameters” – Table 2

<b>Constituent</b>	<b>eCO2</b>	<b>Reference</b>
Cement	0.93	8, 14
PFA	0.01	8
Aggregate	0.005	8
Superplasticiser	0.01	11
Water	0.001	15

Purnell, Black – “Embodied ... parameters” – Figure 1

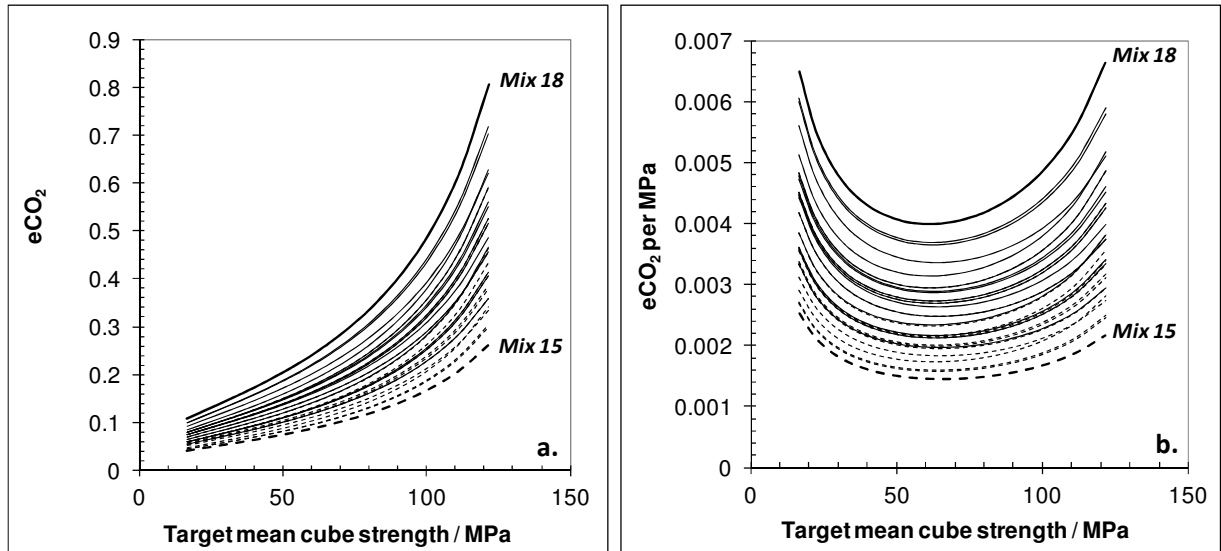

Purnell, Black – “Embodied ... parameters” – Figure 2

