Mineral sequestration of CO2 by aqueous carbonation of coal combustion fly-ash

G. Montes-Hernandez, R. Perez-Lopez, F. Renard, J.-M. Nieto, L. Charlet

▶ To cite this version:

HAL Id: insu-00351921

https://hal-insu.archives-ouvertes.fr/insu-00351921

Submitted on 12 Jan 2009

Mineral sequestration of CO_2 by aqueous carbonation of coal combustion fly-ash

G. Montes-Hernandez [*, a], R. Pérez-López [a, b], F. Renard [a, c], J.M. Nieto [b], L. Charlet [a]

[a] LGIT, CNRS-OSUG-UJF, Université Joseph Fourier, Maison de Géosciences, BP 53, 38041 Grenoble Cedex, France

[b] Department of Geology, University of Huelva, Campus 'El Carmen', 21071, Huelva, Spain

[c] Physics of Geological Processes, University of Oslo, Norway

[*] Corresponding author: German Montes-Hernandez

E-mail address: German.MONTES-HERNANDEZ@obs.ujf-grenoble.fr

german_montes@hotmail.com

Abstract

The increasing CO_2 concentration in the Earth's atmosphere, mainly caused by fossil fuel combustion, has led to concerns about global warming. A technology that could possibly contribute to reducing carbon dioxide emissions is the in-situ mineral sequestration (long term geological storage) or the ex-situ mineral sequestration (controlled industrial reactors) of CO_2. In the present study, we propose to use coal combustion fly-ash, an industrial waste that contains about 4.1 wt.% of lime (CaO), to sequester carbon dioxide by aqueous carbonation. The carbonation reaction was carried out in two successive chemical reactions, firstly the irreversible hydration of lime:

$$CaO + H_2O \rightarrow Ca(OH)_2$$

secondly, the spontaneous carbonation of calcium hydroxide suspension:

$$Ca(OH)_2 + CO_2 \rightarrow CaCO_3 + H_2O$$

A high CaO-$CaCO_3$ chemical transformation (approximately 82%) was estimated by mass balance after two hours of reaction at 30°C. The carbonation of CaO was independent on the initial pressure of CO_2 (10, 20, 30 and 40 bar) and it was slightly affected by the temperature of reaction (30 and 60 °C). The precipitate calcium carbonate was characterized by isolated micrometric particles and micrometric agglomerates of calcite (SEM observations). In addition, the calcite precipitation and lime dissolution were confirmed by comparison of X-ray diffraction spectra. This experimental study demonstrates that one ton of fly-ash could sequester up to 26 kg of CO_2. This confirms the possibility to use the alkaline liquid-solid waste for CO_2 mitigation.

Keywords: Mineral sequestration of CO_2; Fly-ash; Aqueous carbonation; Calcium oxide; Calcite

1. Introduction

The global warming of Earth's near-surface, air and oceans in recent decades is a direct consequence of anthropogenic emission of greenhouse gases into the atmosphere such as CO_2, CH_4, N_2O and CFCs (*1*). The CO_2 emissions contribute approximately 60% to this climate change. From the time of the industrial revolution that started the 1860's, 75% of CO_2 emissions discharged into the atmosphere are caused by the burning of fossil fuels (26.4 ± 1.1 Gt CO_2 yr^{-1} for the 2000-2005 period), and the remaining 25% by land use change (*1*). Although oceans and terrestrial biosphere can take up high amounts of the CO_2 emitted, about 45% remains in the atmosphere as stable specie that may stay for many thousands of years (*1*). The continuous increase of atmospheric CO_2 might lead to stress on drinking water availability, species extinction, melting of ice sheets and coastal flooding (*2*).

Motivated by concerns about climate change, technical solutions are searched to minimize these harmful consequences. The main actions include: (I) the increase of the efficiency of energy conversion, (II) the reduction of energy demand and (III) the use of carbon free energy sources (nuclear, solar, wind, geothermal and biomass energy) (*3*). However, fossil fuels account for 85% of world energy needs in the current energy system, and hence, rapid variations of the demand or the prices in the market may seriously harm the global economy. Likewise, the use of fossil fuels will likely continue at the next decades owing to both its low cost and high availability.

An alternative to reduce the CO_2 emission without modifying the energy production system is the retention or sequestration of carbon dioxide in stable geological reservoirs (*4-7*). Such a strategy, so-called geological carbon sequestration, consists of capturing gaseous CO_2 from emissions sources and injecting it as a supercritical fluid in terrestrial reservoirs, such as saline aquifers, depleted oil and gas fields or deep coal seams. In geological reservoirs, the supercritical CO_2 could be retained by stratigraphic or structural trapping (physical isolation),

solubility trapping (dissolved in the aqueous phase) and/or hydrodynamic trapping (associated to long residence time of dissolved CO_2-bearing fluids in aquifers). However, the main scientific concerns inquiring the geological carbon sequestration applicability are the high pressure and temperature variations caused by the large CO_2 accumulation on the reservoirs. These thermodynamic variations could exert forces that diminish the reservoir confinement due to the formation of cracks and faults either in reservoir itself or in the cap rocks. Moreover, the CO_2 dissolution into the pore water and the consecutive carbonic acid formation can result in the dissolution of several minerals (mainly carbonate, oxides and hydroxide minerals) affecting the long-term confinement properties of the reservoirs (*8*).

In terrestrial reservoirs, the CO_2 pressure can decrease in the long term as a consequence of another retention mechanism: mineral trapping or mineralogical carbon sequestration. The stored CO_2 may transform to stable carbonate minerals by reactions with aqueous ions (mainly calcium, magnesium and iron) resulting from silicate weathering (*9-12*). Although this mechanism favours the permanent CO_2 sequestration, it is expected to be slow in geological formation (hundreds of years) due to the slow kinetics of silicate mineral dissolution and carbonate mineral precipitation. However, mineralogical carbon sequestration could contribute significantly to CO_2 sequestration in the proximity of the emission source, without the need of storing the gas into a geological reservoir.

Soong et al. (*13*) proposed the use of mineralogical carbon sequestration in controlled reactors as a viable approach to reduce CO_2 emissions into the atmosphere using by-products from coal combustion in power plants (fly-ash) and oil and gas production (brine solutions). Brine solutions act as calcium and magnesium source favouring the CO_2 retention by carbonate precipitation. Fly-ash was used to increase the pH level of the reactant brine and also as an additional source of calcium to enhance reaction efficiency for the carbonation process.

1   Coal combustion in power plants provides approximately 40% of world electricity

2   generation. At present, the coal reserves are estimated around 900 billion ton (*14*).

3   Considering that coal consumption reached 5 billion tonnes in 2003, coal-energy production

4   will continue, and even increase, in the next centuries due to the energy demand for industrial

5   and domestic uses (*15*). Therefore, the continuous building of power plants is envisaged to

6   hold this energy production system. This may cause serious disruption to the global climate

7   since each 500 MW coal power plant emits about 3 million tonnes of CO_2 per year. Likewise,

8   the worldwide production of fly-ash, estimated currently at 600 million tonnes per year, will

9   also increase exponentially in the near future. The main producers of fly-ashes are China,

10   Russia and the United States of America.

11   Fly-ash material is used as cement raw material and as a partial replacement for cement in

12   concrete. However, the global production of fly-ash exceeds their potential uses (*16*), and

13   hence, it is considered a residual by-product. Only around a 30% of the total production is

14   used as a construction material. At present, numerous investigations are focused on the search

15   of new applications for this residue. Three main research lines use fly-ash: i) to synthesize

16   zeolites to be applicable as filter material in water decontamination and gas retention (*17,18*),

17   ii) as an effective technique in metal retention processes in contaminated soils (*19,20*) and, iii)

18   for the treatment of mining wastes producers of acid mine drainage (*21,22*). Although Soong

19   et al. (*13*) propose the use of fly ash to sequester CO_2, brine solutions were the main agent

20   acting in the carbonation process. Moreover, these authors do not calculate the amount of CO_2

21   sequestered during the process.

22   The objective of integrated waste management is the search for sustainable development,

23   i.e. to balance the fulfilment of human needs with the protection of the natural environment in

24   the present and indefinite future. With this in mind, the main aim of this work is precisely to

25   quantify the CO_2 amount that may be sequestered by calcite precipitation using fly-ash-water

1 dispersion. This study is in our opinion especially attractive since the residual solid by-

2 products from power plants could be used to mitigate the residual gaseous wastes produced by

3 the same plants.

4

5 **2. Materials and methods**

6

7 2.1 Fly-ash material

8   The fly-ash used in the present study is a waste residue generated from coal combustion at

9 Los Barrios power station, Cádiz, south Spain. It is a powder composed mainly of spherical

10 microparticles collected from electrostatic precipitators located at the outlet of the chimney

11 were combustion gasses are liberated into the atmosphere. Size distribution analysis indicates

12 that the particles have a median diameter of 40 μm. The specific surface area is 0.63 ± 0.022

13 $m^2 \ g^{-1}$ determined by BET gas adsorption method (MICROMERITICS ASAP 2000

14 instrument). Mineral abundances are similar to those reported by Querol *et al*. (*23*), and show

15 that fly-ash is composed of mullite (20.8 wt.%), quartz (4.5 %), lime (4.1%), anhydrite

16 (1.3%), K-feldspar (2.5 %), magnetite (0.5 %) and a chalco-aluminosilicate glass phase

17 (66.4%). The chemical composition measured by X-ray fluorescence (XRF, BRUKER

18 PIONEER instrument) shows that Los Barrios fly-ash is a residue rich in Si (41.3 wt.% SiO_2),

19 Al (27.5 wt.% Al_2O_3), C (16 wt.% CO_2), Ca (5 wt.% CaO), and Fe (3.3 wt.% Fe_2O_3) with

20 minor elements (wt.%): Sr (0.3%), Cl (0.02%), Cr (0.01%), Ni (0.02%), Zn (0.01%), V

21 (0.01%), Cu (0.01%), Co (0.01%) and Sc (0.003%). The presence of lime (CaO, 4.1 wt%) in

22 fly-ash accounts for the high potential of both alkalinity and dioxide carbon sequestration as

23 discussed below.

24

25

1   2.2 CO$_2$ sequestration experiments in a stirred reactor

2   One litre of high-purity water with electrical resistivity of 18.2 MΩ cm and 100g of fly-ash

3   were placed in a titanium reactor (autoclave Parr with internal volume of two litres). The fly-

4   ash particles were immediately dispersed by mechanical stirring (450 rpm). The dispersion

5   (solution + solid particles) was then heated to 30 or 60°C using an oven specifically adapted

6   to the reactor. When the dispersion temperature was reached, 10, 20, 30 or 40 bar of CO$_2$

7   (provided by Linde Gas S.A.) was injected in the reactor (see Fig. 1). This was the initial

8   pressure of CO$_2$ which was equal to the total initial pressure in the system. Previous

9   experiments showed that after two hours of reaction the pressure drop was close to the

10   thermodynamic equilibrium in the system. For this reason, we considered a reaction time of

11   two hours for all experiments in the present study.

12   Obviously, both the sorption-dissociation of CO$_2$ in the solution and aqueous carbonation

13   process produce a global pressure drop in the system, $P_{global\_pressure-drop}$. In order to estimate

14   the pressure drop produced only by the process of CaO carbonation (noted $P_{carbonation\_pressure-}$

15   $_{drop}$), two complementary systems were proposed for each experiment. Firstly, the pressure

16   drop $P_{water\_pressure-drop}$ related to the sorption-dissociation of CO$_2$ into pure water only was

17   measured. Secondly, the pressure drop $P_{Ca-rich\_pressure-drop}$ related to the sorption-dissociation of

18   CO$_2$ in a Ca-rich solution was measured independently. In this second experiment, a

19   concentration of 1g/L of calcium was chosen, that represented the average concentration after

20   fly-ash dispersion in water. These two experiments demonstrated that the Ca-concentration

21   (0-1g/L) has no measurable effect on the sorption-dissociation of CO$_2$ because the monitored

22   pressure drop in pure water $P_{water\_pressure-drop}$ was equivalent to the monitored pressure drop in

23   presence of Ca $P_{Ca-rich\_pressure-drop}$. Consequently, the pressure drop produced by the

24   carbonation process of CaO was calculated by a simple pressure balance:

25   $$P_{carbonation\_pressure-drop} = P_{global\_pressure-drop} - P_{water\_pressure-drop} \qquad (1)$$

1   Under isothermal conditions, $P_{global\_pressure-drop}$ and $P_{water\_pressure-drop}$ are proportional to the

2   initial CO_2 pressure.

3   At the end of the experiment, the reactor was removed from the heating system and was

4   immersed into cold water. The reaction cell was depressurized for 15 minutes during the

5   water cooling period. Then, water cooling at 30°C the reactor was disassembled, and the solid

6   product was separated by centrifugation (30 minutes at 12,000 rpm), decanting the

7   supernatant solutions. Finally, the solid product was dried directly in the centrifugation flasks

8   for 48 h at 65°C. The supernatant solutions were filtered through a 0.2-µm Teflon filter.

9   Adsorption on the filter and filter holder was considered negligible. The filtered solutions

10   were immediately acidified for measurement of [Ca], [Ni], [Zn], [Cu] and [Sr] by Inductively

11   Coupled Plasma Atomic Emission Spectrometry (ICP-AES).

12

13   2.3 Characterization of the solid phase

14   The mineralogical characterization of the starting material and solid products was carried

15   out by X-ray diffraction (XRD, powder method) using a D501 SIEMENS diffractometer.

16   Working conditions were CoKα monochromatic radiation (λ=1.7902 Å), 37.5 mA and 40 kV.

17   The experimental measurement parameters were 12s counting time per 0.02° 2θ step in the 5-

18   80º 2θ range. The detection is performed by a kevex Si(Li) detector. Morphological analyses

19   were also characterized by means of a scanning electron microscopy (SEM), with a JEOL

20   JSM-5410 instrument, equipped with an energy dispersive system (EDS) for the chemical

21   microanalysis.

22

23

24

25

3. Results and discussion

A previous investigation showed that the carbonation of calcium hydroxide suspension at high pressure of CO_2 (initial P_{CO2}=55 bar) and moderate and high temperature (30 and 90°C) is a potential method to synthesize fine particles of calcite (*24*). In addition, the reported results have important ecological implications for the ex-situ mineral sequestration of CO_2 by alkaline liquid-solid waste such as fly-ash, bottom ash, Ca/Mg-rich silicates, alkaline waste water, etc. For this reason, the current study was focussed on the mineral sequestration of CO_2 by aqueous carbonation of fly-ash. In the following sub-sections, the chemical reactions of CO_2 sequestration by fly-ash and, the calculation of the sequestrated quantity of CO_2 by calcite precipitation and kinetic modelling of sequestered CO_2 in a fly-ash-water suspension are described and discussed.

3.1 Chemical reactions of CO_2 sequestration by fly-ash

The SEM images of solid product (Figure 2), the comparison of x-ray diffraction spectra of the starting material and the solid product (Figure 3) and ICP-AES analysis in the solutions, suggest a simple reaction mechanism for CO_2 mineral sequestration by fly-ash in two successive steps: firstly the irreversible hydration of calcium oxide or lime:

$$CaO + H_2O \rightarrow Ca(OH)_2 \qquad (2)$$

secondly, the spontaneous carbonation of calcium hydroxide suspension:

$$Ca(OH)_2 + CO_2 \rightarrow CaCO_3 + H_2O \qquad (3)$$

The precipitate calcium carbonate is characterized by isolated micrometric particles and micrometric agglomerates of calcite (Figure 2). In addition, the calcite precipitation and lime (CaO) dissolution were confirmed by comparison of X-ray diffraction spectra (Figure 3).

1   Finally, the chemical-element concentrations for Ca, Ni, Zn, Cu and Sr in the solution after

2   two hours of fly-ash-pure water-carbon dioxide interactions suggest a preferential and rapid

3   dissolution of lime phase and possibly a slight dissolution of the glass phase ([Ca] $\approx$

4   800mg/L) (22). Concerning, the trace elements (contained initially in the fly-ash) only the

5   strontium was detected in the solution by ICP-AES ([Sr] $\approx$ 8mg/L). Consequently, the

6   concentrations of Ni, Zn and Cu were considered to be smaller than 6 ppb (detection limit).

7   This demonstrates that the fly-ash dispersion into pure water did not favour the liberation of

8   toxic metallic ions after two hours of solid-fluid interaction at moderate temperature. In fact,

9   preliminary experiments show that the carbonation process favours the co-precipitation and/or

10   incorporation of the dissolved impurities into the calcite crystallographic network.

11

12   3.2 The sequestered quantity of CO_2 by calcite precipitation

13   A simplified method was developed to estimate the sequestered quantity of CO_2 by carbonate

14   precipitation. This method was partially described in the section 2.2. Herein, the pressure drop

15   produced by the carbonation process of CaO (Eqs. 2 and 3) in the system was calculated by a

16   simple pressure balance (Eq. 1). The carbonation pressure drop, $P_{carbonation\_pressure-drop}$ was

17   equal to 1.5 bar for all experiments (Figure 4b). It was independent on the initial pressure of

18   CO_2 (10, 20, 30, 40 bar) and was slightly affected by the temperature of reaction (30 and

19   60°C). The results of the pressure drop kinetics for 30 bar (as initial pressure of CO_2) are

20   shown on Figure 4a. Here, it was observed that the equilibrium of pressure drop was reached

21   after about five hours of solid-fluid interaction.

22   Considering that CO_2 is an ideal gas, the quantity of CO_2 consumed by the carbonation

23   process can be calculated as follows:

24   $$n_{CO2} = \frac{P_{carbonation\_pressure\_drop} V}{RT}$$ (4)

where, the V is the reactor volume occupied with gas (1L), T is the temperature of reaction ($\approx303°K$) and R is the gas constant (0.08314472 L.bar/°K.mol). Using the measured value $P_{carbonation\_pressure-drop}$ = 1.5 bar, we calculated that 0.05954 mol of CO_2 were consumed by the carbonation process. Taking into account reactions (2-3) and the fact that the fly-ash contains 4.1wt.% of lime (CaO), the carbonation efficiency CE can be calculated by the following expression:

$$CE = \frac{n_{CO2} * M_{CO2}}{\frac{w_{CaO}}{M_{CaO}} * M_{CO2}} *100 \tag{5}$$

where, n_{CO2} is the mol number of consumed CO_2, calculated by Eq. 4 (0.05954 mol), M_{CO2} is the molar mass of CO_2 (44.01 g/mol), w_{CaO} is the starting mass of CaO in the reactor (4.1g) and M_{CaO} is the molar mass of CaO (56.077g/mol). The carbonation efficiency was equal to 82% after two hours of solid-fluid interactions at 30 and 60°C.

Theoretically one ton of fly-ash containing 4.1% of lime could sequester 32.17kg of CO_2. With our experimental protocol, 26.19kg of CO_2 per ton of fly-ash could be successfully sequestered into stable calcite. Indeed, this is an attractive result concerning the ex-situ mineral sequestration of CO_2.

3.3 Kinetic modelling of sequestered CO_2 in a fly-ash-water suspension

The monitoring of the pressure drop for any controlled system under ideal gas conditions allows the kinetic modelling of sequestered CO_2 after gas injection in a solid-liquid system (fly-ash-water dispersion for this study). This can be done using a simple correlation function, $n_{total\_CO2}=f(t)$, where n_{total_CO2} is the total mol quantity of sequestered CO_2 in the fly-ash-water dispersion and t is the time after gas injection.

Several kinetic models including first-order, pseudo-first-order, second-order, pseudo-second-order, parabolic diffusion and power function kinetic expressions are reported in the literature

1 for fitting the kinetic experimental or calculated data of the solid-fluid interaction processes.

2 For this study, the kinetic modelling concern the total sequestered quantity of CO_2 in a fly-

3 ash-water dispersion, i.e. the CO_2 sorption-dissociation in water, possibly the CO_2 adsorption

4 on the fly-ash and, sequestered CO_2 by carbonation process. For this case, the best fit (attested

5 by a correlation factor close to 1) of the experimental-calculated data was achieved when

6 using a pseudo-second-order kinetic model according to the following expression:

7 $$\frac{dn_{total\_CO2,t}}{dt} = k_s \left(n_{total\_CO2,max} - n_{total\_CO2,t} \right)^2 \qquad (6)$$

8 where k_s is the rate constant of sequestered CO_2 [1/mol s] for a given initial pressure of CO_2

9 in the system, $n_{total\_CO2,max}$ is the maximum sequestered quantity of carbon dioxide at

10 equilibrium [mol], $n_{total\_CO2,t}$ is the sequestered quantity of carbon dioxide at any time, t,

11 [mol].

12 The integrated form of Equation (6) for the boundary conditions $t = 0$ to $t = t$ and $n_{total\_CO2,t} =$

13 0 to $n_{total\_CO2,t} = n_{total\_CO2,t}$ is represented by a hyperbolic equation:

14 $$n_{total\_CO2,t} = \frac{n_{total\_CO2,max} * t}{\left(\dfrac{1}{k_s * n_{total\_CO2,max}} \right) + t} \qquad (7)$$

15 In order to simplify the fitting of experimental-calculated data, we have defined the constant

16 $t_{1/2} = 1/k_s * n_{total\_CO2,max}$. Physically, $t_{1/2}$ represents the time after which half of the maximum

17 sequestered quantity of carbon dioxide was reached and is called "half-sequestered CO_2

18 time". It can be used to calculate the initial rate of sequestered CO_2, $v_{0,s}$, [mol/s].

19 $$v_{0,s} = \frac{n_{total\_CO2,max}}{t_{1/2}} = k_s \left(n_{total\_CO2,max} \right)^2 \qquad (8)$$

20 The numerical fit of the experimental-calculated kinetic curve at 30 bar and 30°C ($n_{total\_CO2,t}$

21 vs. t) using Eq. (7) is shown on Figure 5. The parameters $t_{1/2}$ and $n_{total\_CO2,max}$ were estimated

22 by applying a non-linear regression using the least-squares method. The initial rate of

sequestered CO_2 was calculated using Eq. 8 ($v_{0,s}$ = 8.28×10^{-4} mol/s) at 30°C. This value

indicates that the mass transfer of compressed CO_2 in contact with solid-water dispersion is

higher that CO_2 transfer at atmospheric conditions or at low pressure (*25-26*).

3.4 Conclusion

The results presented in this study showed that the ex-situ mineral sequestration of CO_2 by

aqueous carbonation of fly-ash could be an attractive and potential method to reduce the CO_2

emission in the atmosphere from power plants. This experimental investigation demonstrated

that one ton of fly-ash, an industrial waste that contains about 4.1 wt.% of lime (CaO), could

sequester up to 26 kg of CO_2. This confirms the possibility to use the alkaline liquid-solid

waste for CO_2 mitigation.

1 **Acknowledgements**

2

7

8

9

10

11

12

13

14

15

16

17

18

19

20

21

22

23

24

25

References

(1) IPCC (Intergovernmental Panel on Climate Change). Climate Change 2007: The Physical Science Basis: Summary for Policymakers, 2007, http://ipcc-wg1.ucar.edu/wg1/Report/AR4WG1_Pub_SPM-v2.pdf

(2) IPCC (Intergovernmental Panel on Climate Change). Climate Change 2007: Climate Change Impacts, Adaptations, and Vulnerability, 2007, http://ipcc-wg2.org/index.html

(3) Schrag, D. P. Confronting the Climate-Energy Challenge. *Elements* **2007**, *3*, 171-178.

(4) Bachu, S. Sequestration of CO_2 in geological media: criteria and approach for site selection in response to climate change. *Energy Convers. Manage.* **2000**, *41*, 953-970.

(5) Bachu, S. Sequestration of CO_2 in geological media in response to climate change: road map for site selection using the transform of the geological space into the CO_2 phase space. *Energy Convers. Manage.* **2002**, *43*, 87-102.

(6) Bachu, S; Adams, J. J. Sequestration of CO_2 in geological media in response to climate change: capacity of deep saline aquifers to sequester CO_2 in solution. *Energy Convers. Manage.* **2003**, *44*, 3151–3175.

(7) Friedmann, S. J. Geological Carbon Dioxide Sequestration. *Elements* **2007**, *3*, 179-184.

(8) Kharaka, Y. K.; Cole, D. R.; Hovorka, S. D.; Gunter, W. D.; Knauss, K. G.; Friefeld, B. M. Gas-water-rock interactions in Frio Formation following CO_2 injection: Implications for the storage of greenhouse gases in sedimentary basins. *Geology* **2006**, *34*, 577-580.

(9) Gunter, W. D.; Perkins, E. H.; Hutcheon, I. Aquifer disposal of acid gases: modeling of water–rock reactions for trapping of acid wastes. *Appl. Geochem.* **2000**, *15*, 1085-1095.

(10) Kaszuba, J. P.; Janecky, D. R.; Snow, M. G. Carbon dioxide reaction processes in a model brine aquifer at 200 ºC and 200 bars: implications for geologic sequestration of carbon. *Appl. Geochem.* **2003**, *18*, 1065-1080.

1 (11) Kaszuba, J. P.; Janecky, D. R.; Snow, M. G. Experimental evaluation of mixed fluid

2 reactions between supercritical carbon dioxide and NaCl brine: Relevance to the

3 integrity of a geologic carbon repository. *Chem. Geol.* **2005**, *217*, 277-293.

4 (12) Giammar, D. E.; Bruant, R. G.; Peters, C. A. Forsterite dissolution and magnesite

5 precipitation at conditions relevant for deep saline aquifer storage and sequestration of

6 carbon dioxide. *Chem. Geol.* **2005**, *217*, 257-276.

7 (13) Soong, Y.; Fauth, D. L.; Howard, B. H.; Jones, J. R.; Harrison, D. K.; Goodman, A. L.;

8 Gray, M. L.; Frommell, E. A. CO_2 sequestration with brine solution and fly ashes.

9 *Energy Convers. Manage.* **2006**, *47*, 1676-1685.

10 (14) BP (British Petroleum). Statistical Review of World Energy, 2006,

11 http://www.bp.com/productlanding.do?categoryId=6848&contentId=7033471

12 (15) Energy Information Administration. International Energy Annual. Department of

13 Energy, Washington, DC, 2006, www.eia.doe.gov/iea

14 (16) Manz, O. E. Worldwide production of coal ash and utilization in concrete and other

15 products. *Fuel* **1997**, *76*, 691-696.

16 (17) Querol, X.; Umaña, J. C.; Plana, F.; Alastuey, A.; Lopez-Soler, A.; Medinaceli, A.;

17 Valero, A.; Domingo, M. J.; Garcia-Rojo, E. Synthesis of zeolites from fly ash at pilot

18 plant scale. Examples of potential applications. *Fuel* **2001**, *80*, 857-865.

19 (18) Cama, J.; Ayora, C.; Querol, X.; Ganor, J. Dissolution kinetics of synthetic zeolite NaP1

20 and its implication to zeolite treatment of contaminated waters. *Environ. Sci. Technol.*

21 **2005**, *39*, 4871-4877.

22 (19) Brake, S. S.; Jensen, R. R.; Mattox, J. M. Effects of coal fly ash amended soils on trace

23 element uptake in plants. *Environ. Geol.* **2003**, *45*, 680-689.

24 (20) Dermatas, D.; Meng, X. Utilization of fly ash for stabilization/solidification of heavy

25 metal contaminated soils. *Eng. Geol.* **2003**, *70*, 377-394.

1   (21) Pérez-López, R.; Nieto, J. M.; Almodóvar, G. R. Immobilization of toxic elements in

2   mine residues derived from the mining activities in the Iberian Pyrite Belt (SW Spain):

3   laboratory experiments. *Appl. Geochem.* **2007**, in press,

4   doi:10.1016/j.apgeochem.2007.03.055.

5   (22) Pérez-López, R.; Cama, J.; Nieto, J. M.; Ayora, C. The iron-coating role on the

6   oxidation kinetics of a pyritic sludge doped with fly ash. *Geochim. Cosmochim. Acta*

7   **2007**, *71*, 1921-1934.

8   (23) Querol, X.; Umaña, J. C.; Alastuey, A.; Ayora, C.; Lopez-Soler, A; Plana, F. Extraction

9   of soluble major and trace elements from fly ash in open and closed leaching systems.

10   *Fuel* **2001**, *80,* 801-813.

11   (24) Montes-Hernandez, G., Renard, F., Geoffroy, N., Charlet, L., Pironon, J. Calcite

12   precipitation from CO_2-H_2O-$Ca(OH)_2$ slurry under high pressure of CO_2. *J. Cryst.*

13   *Growth* **2007**, 308, 228-236

14   (25) Akanksha, Pant, K. K., Srivastava, V. K. Mass transport correlation for CO_2 absorption

15   in aqueous monoethanolamine in a continuous film contactor. Chem. Eng. Process.

16   **2007**, doi:10.1016/j.cep.2007.02.008.

17   (26) Haubrock, J., Hogendoorn, J. A., Versteeg G. F. The applicability of activities in kinetic

18   expressions: A more fundamental approach to represent the kinetics of the system CO_2-

19   OH^--salt in terms of activities. Chem. Eng. Sci. **2007**, doi:10.1016/j.ces.2007.06.018.
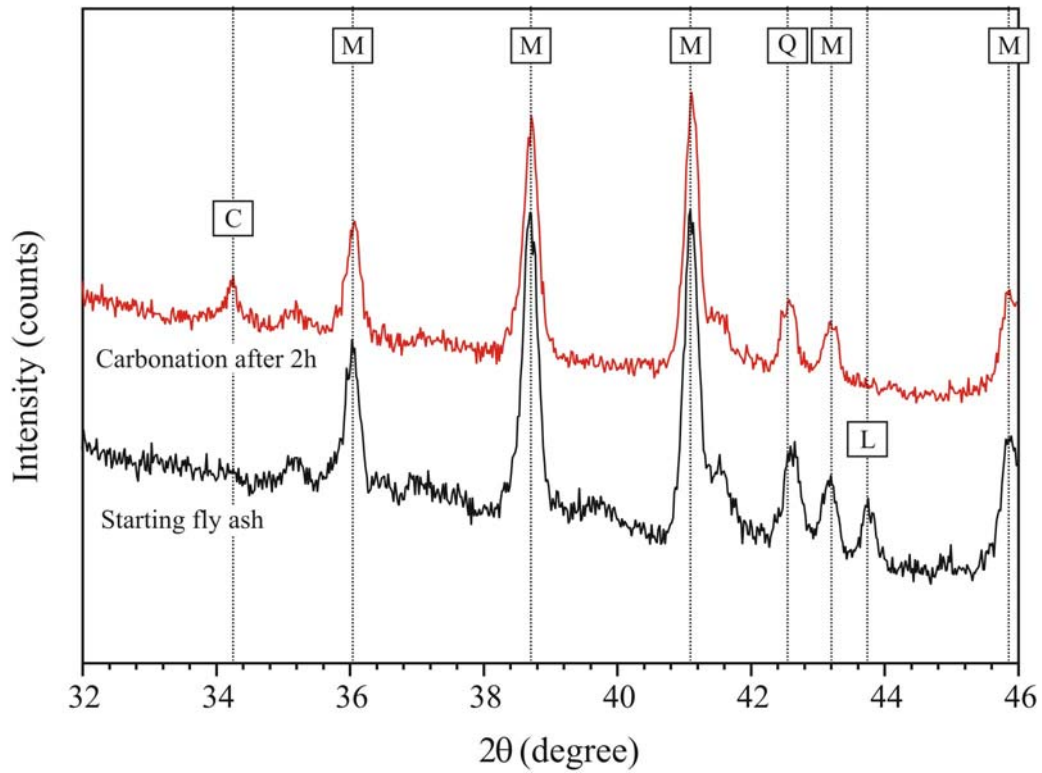
20

21

22

23

24

25
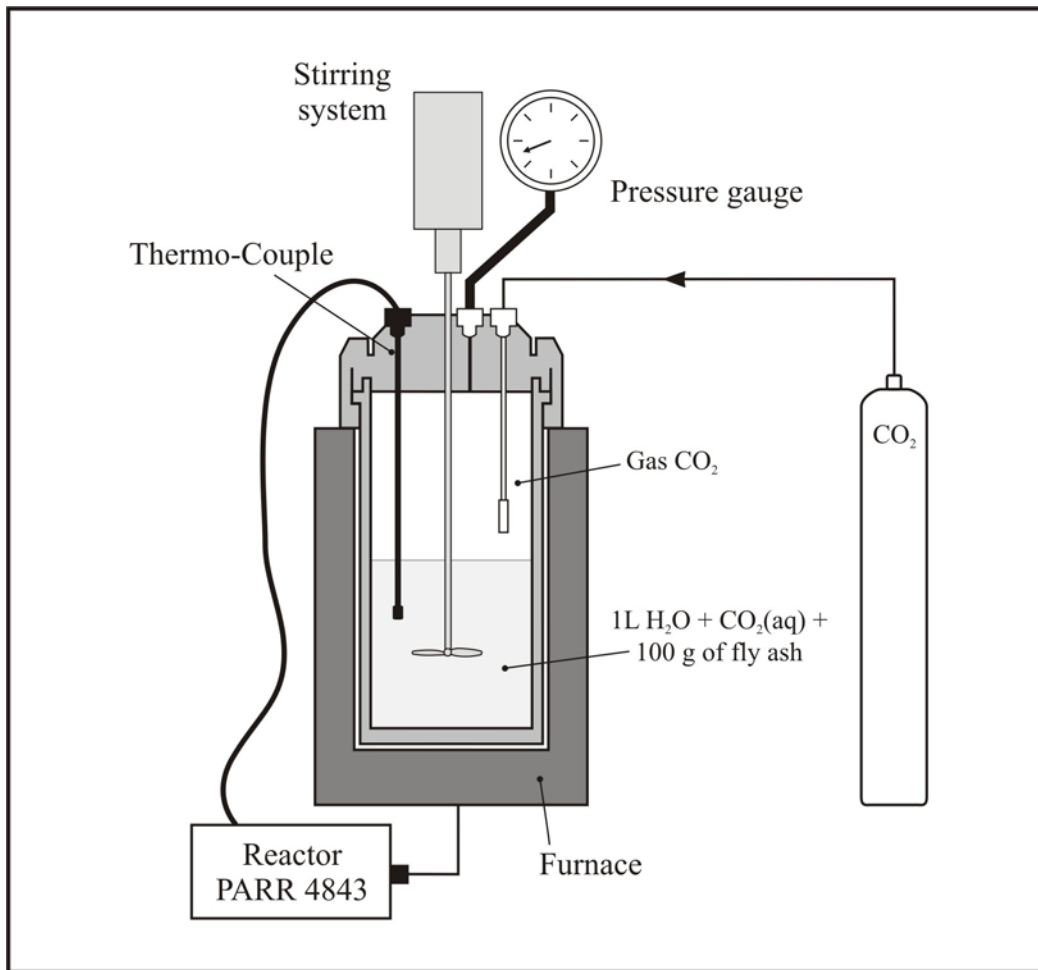
Figure 1. Schematic experimental system for mineral sequestration of CO_2 by aqueous carbonation of fly-ash in a stirred reactor.
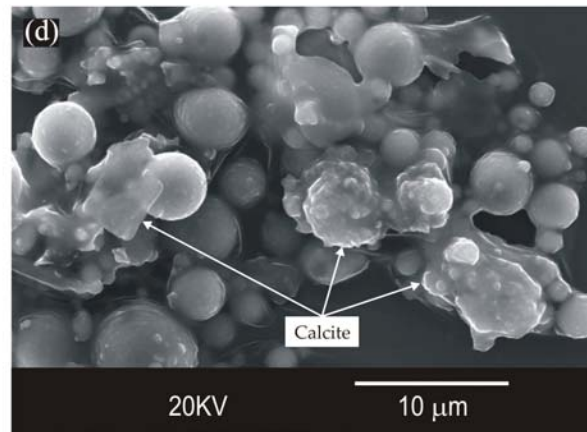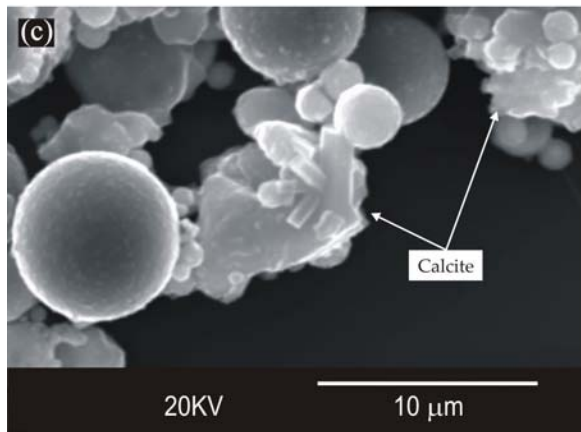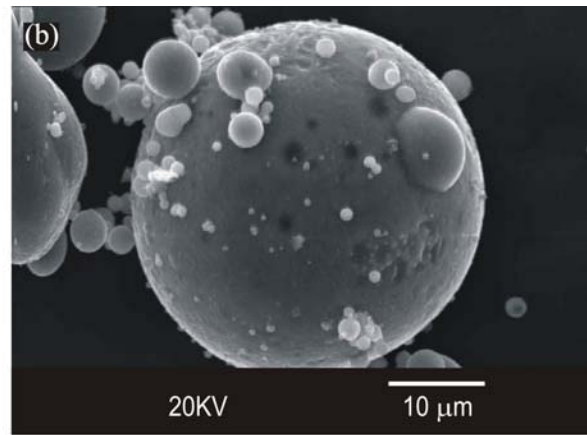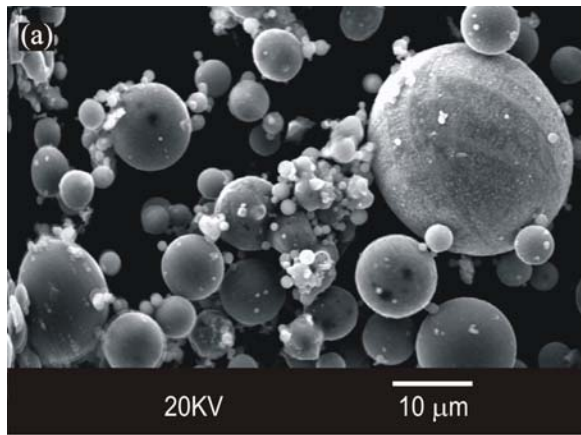
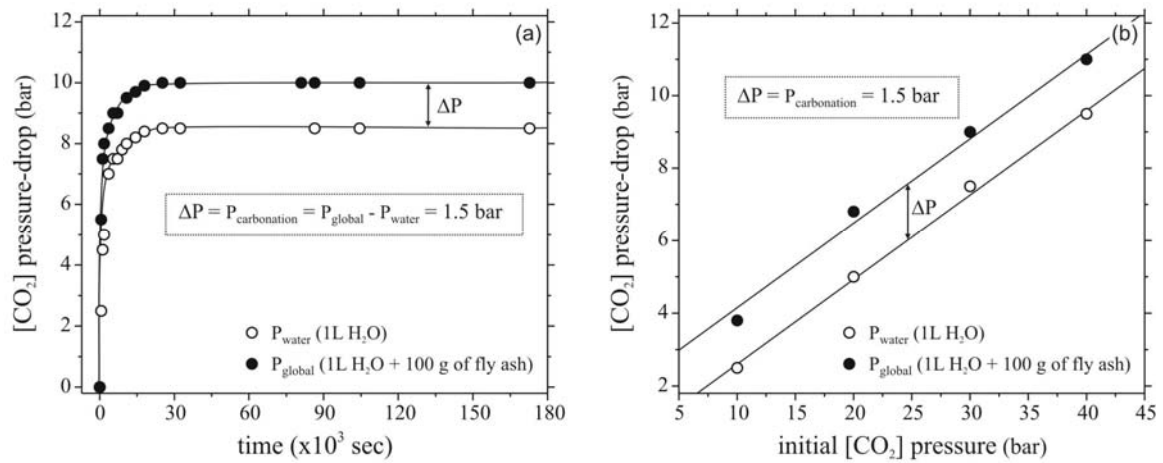Figure 2. (a-b) SEM images of fly-ash before reaction. (c-d) Calcite particles precipitated during CO_2 sequestration experiments.
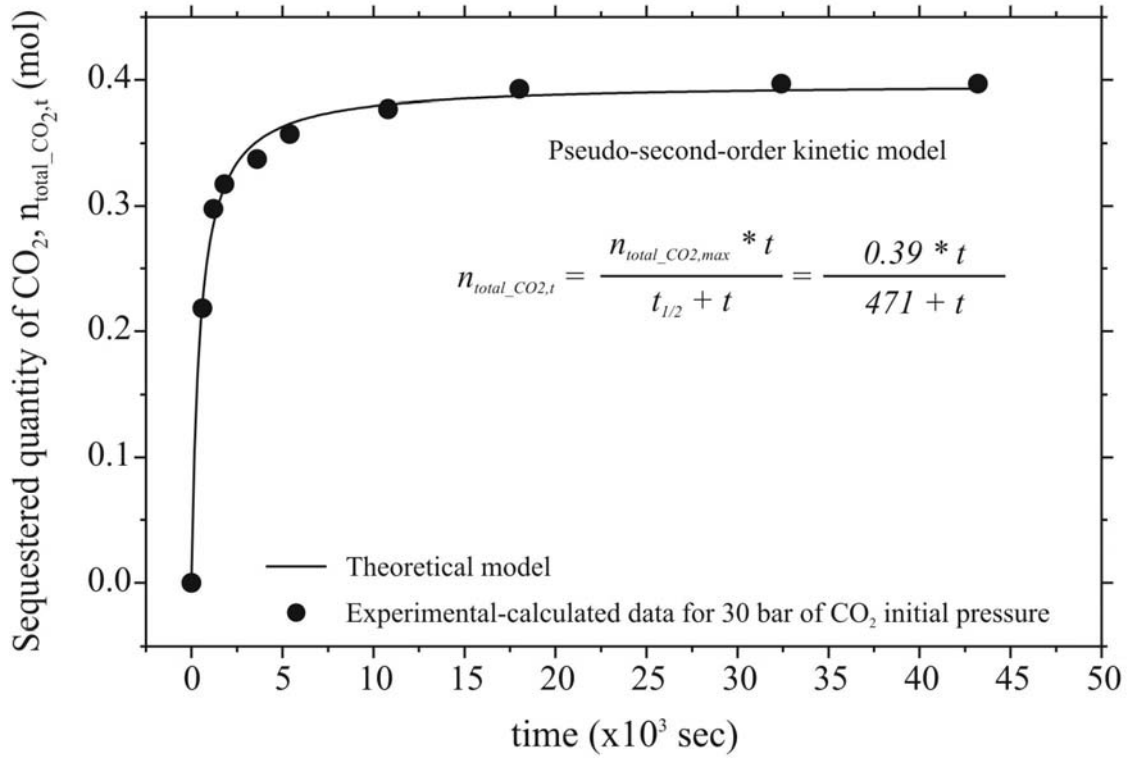
Figure 3. XRD spectra of starting fly-ash and solid products after carbonation during 2 h. C: Calcite, M: Mullite, Q: Quartz, L: Lime. These spectra demonstrate the total consumption of lime and the production of calcite.

Figure 4. (a) Kinetic behaviour of pressure decrease in the reactor at 30°C and for 30 bar initial pressure of CO_2. (b) Linear correlation between the pressure decrease at equilibrium and the initial pressure of CO_2.

$$n_{total\_CO2,t} = \frac{n_{total\_CO2,max} * t}{t_{1/2} + t} = \frac{0.39 * t}{471 + t}$$

Pseudo-second-order kinetic model

Theoretical model

Experimental-calculated data for 30 bar of CO_2 initial pressure

Figure 5. Kinetic modeling of sequestered CO_2 in a fly-ash-water suspension for 30 bar initial pressure of CO_2.