

# Nanoscale Advances

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: N. Groybeck, M. Donzeau, A. Stoessel, A. M. Haeberlé, S. Ory, D. Spehner, P. Schultz, O. Ersen, M. Bahri, D. Ihiwakrim and G. Zuber, *Nanoscale Adv.*, 2021, DOI: 10.1039/D1NA00256B.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

## ARTICLE

# Gold labelling of Green Fluorescent Protein (GFP)-tag inside cells using recombinant nanobodies conjugated to 2.4 nm thiolate-coated gold nanoparticles

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Nadja Groysbeck,<sup>a</sup> Mariel Donzeau,<sup>a</sup> Audrey Stoessel,<sup>a</sup> Anne-Marie Haeberle,<sup>b</sup> Stéphane Ory,<sup>b</sup> Danièle Spehner,<sup>c</sup> Patrick Schultz,<sup>c</sup> Ovidiu Ersen,<sup>d</sup> Mounib Bahri,<sup>d</sup> Dris Ihiwakrim,<sup>d</sup> Guy Zuber<sup>a\*</sup>

The advances in the microscopy technology have prompted efforts to improve the reagents required to recognize specific molecules within the intracellular environment. For high-resolution electron microscopy, conjugation of selective binders originating from the immune response arsenal to gold nanoparticles (AuNPs) as contrasting agents is the method of choice to obtain labeling tools. However, conjugation of the minimal sized 15 kDa nanobody (Nb) to AuNP remains challenging in comparison to the conjugation of 150 kDa IgG to AuNP. In here, effective Nb-AuNP assemblies are built using the selective and almost irreversible non-covalent associations between two peptide sequences deriving from a p53 heterotetramer domain variant. The 15 kDa GFP-binding Nb is fused to one dimerizing motif to obtain a recombinant Nb dimer with improved avidity for GFP while the other complementing dimerizing motif is equipped with thiols and grafted to a 2.4 nm substituted thiobenzoate-coordinated AuNP via thiolate exchange. After pegylation, the modified AuNPs are able to non-covalently anchor Nb dimers and the subsequent complexes demonstrate the ability to immunogold label GFP-protein fusions within various subcellular locations. These tools open an avenue for precise localization of targets at high resolution by electron microscopy.

## 1. Introduction

The investigation of protein trafficking and localization is fundamental to understand cell functioning. Fluorescent microscopy (FM) and Electron Microscopy (EM) are two valuable tools in this endeavour.<sup>1</sup> Continuous technological advances in both FM and EM are steadily pushing the resolution boundaries and providing new insights on how cellular constituents precisely organize together and participate in the life and wellbeing of biological organisms. Pinpointing selected elements within the subcellular organization is unfortunately not always feasible due to the lack of contrast differential between the various cellular constituents. Specific labelling methodologies must therefore be developed and optimized to accompany the progress of microscopy technology. The *Aequorea victoria* Green Fluorescent Protein (GFP) and fluorescent derivatives are popular tags to label chosen proteins through genetically

made fusion proteins and to localize them with FM even in living cells and organisms. For EM, gold nanoparticles (AuNPs) are the contrasting agents of choice.<sup>2</sup> The traditional AuNP-antibody conjugates first reported by Faulk and Taylor,<sup>3</sup> consisting of 150 kDa antibodies that are physically adsorbed onto colloidal AuNPs of 10-15 nm, are still in use today. Yet, the large size of AuNPs and IgG molecules, as well as the difficult to define bonds between the AuNP and the IgG hamper the efficiency of labelling as well as accurate target localization.<sup>4</sup> Reduction of the AuNP's diameter to less than 1.4 nm led to improved labelling agents with favourable diffusion and penetration abilities into tissues.<sup>5</sup> Replacement of the full 150 kDa IgG with the smaller 50 kDa fragment antigen-binding domain (Fab) was also beneficial.<sup>6,7</sup> In a step toward further optimization, 12-15 kDa single-domain camelid antibody fragments (VHH) or nanobodies (Nbs) appear highly appealing.<sup>8-10</sup> They are interesting not only because of their compactness (molecular weight (MW) of ca. 15 kDa for a size of 4 nm x 2.5 nm), but also due to their bioengineering properties.<sup>11</sup> Point mutations of selected amino-acids to cysteines<sup>12,13</sup> afford precise attachment sites for thiol-reactive fluorophores. The resulting fluorescently-labelled Nbs have known spacing distances between the targeted epitope and the fluorescent signal,<sup>14</sup> affording probes with enhanced target localization accuracy suited for super-resolution microscopy imaging of biological targets.<sup>15,16</sup> Nanobodies have also been applied to EM immunolabelling.

<sup>a</sup> Université de Strasbourg – CNRS, UMR 7242 Laboratoire de Biotechnologie et Signalisation Cellulaire, Boulevard Sébastien Brant, 67400 Illkirch, France.

<sup>b</sup> Centre National de la Recherche Scientifique, Université de Strasbourg, Institut des Neurosciences Cellulaires et Intégratives, F-67000 Strasbourg, France.

<sup>c</sup> Université de Strasbourg – Department of Integrated Structural Biology, Institut de Génétique et de Biologie Moléculaire et Cellulaire, 67400 Illkirch, France


<sup>d</sup> Université de Strasbourg – CNRS, UMR 7504, Institut de Physique et Chimie des Matériaux de Strasbourg (IPCMS) 23 rue de Loess, 67034 Strasbourg, France.

\* zuber@unistra.fr

Electronic Supplementary Information (ESI) available: Additional experimental protocols and Data . See DOI: 10.1039/x0xx00000x



## ARTICLE

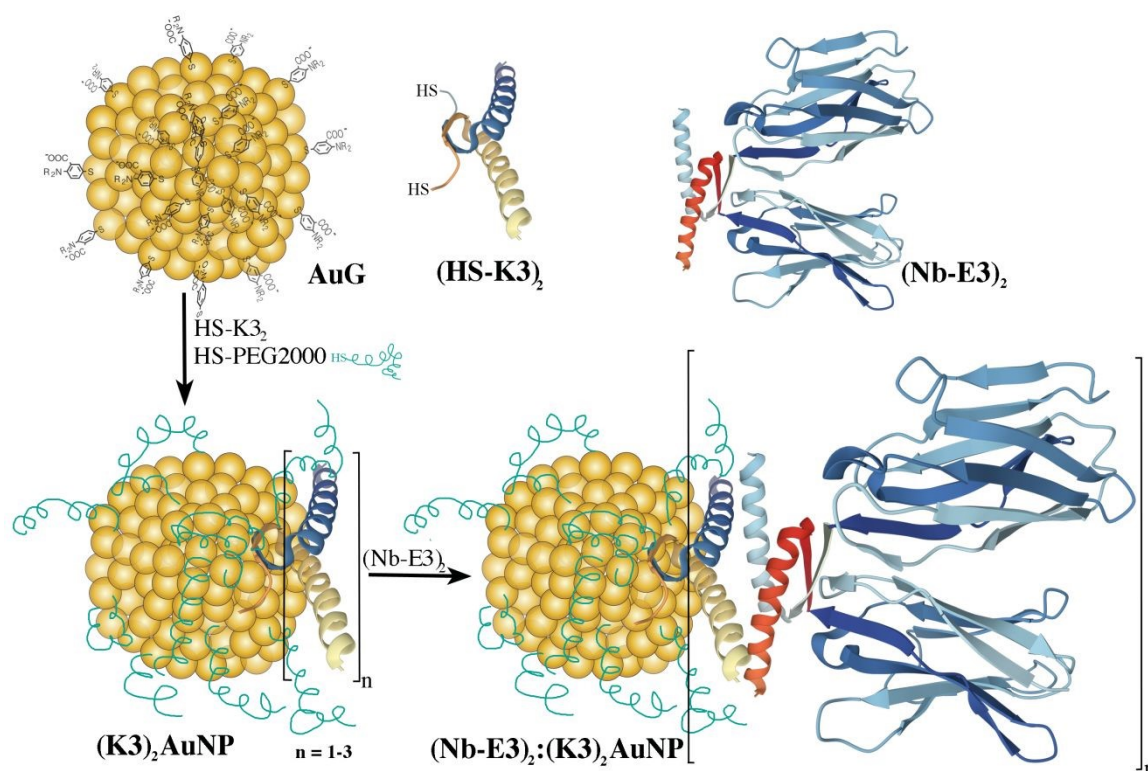

**Figure 1.** Schematic route for the synthesis of the Nb<sub>2</sub>-AuNP conjugates using the strong and mutual associating ability of E3 and K3 dimers originating from a p53 heterotetramer.<sup>17,18</sup> According to the structure of the p53 tetramerization domain (pdb1OLG),<sup>19</sup> the dimers mainly fold into  $\alpha$ -helices. The GFP binding nanobody (Nb) mainly folds into  $\beta$ -sheets (in blue pdb30GO).<sup>20</sup>

Kijanka and colleagues developed a protocol for the labelling of HER2 using an HER2 binding Nb followed by a secondary anti-Nb antibody and then a protein A-gold particle conjugate.<sup>21</sup> Ariotti and colleagues developed fusion proteins between GFP-binding Nbs and a soybean ascorbate peroxidase to locally produce a stain upon addition of diaminobenzidine (DAB) and H<sub>2</sub>O<sub>2</sub>.<sup>22,23</sup> The brownish stain visible by optical microscopy (OM) could be further converted into an electron dense product through treatment with OsO<sub>4</sub>, permitting correlative light and electron microscopy observation. Investigation of the direct conjugation of Nbs to 10-15 nm AuNPs by adsorption has been reported by Goossens and colleagues.<sup>24</sup> Functional conjugates were obtained but maintaining the colloidal stability of the nanobody-AuNP conjugates was clearly extremely challenging because of the huge difference in bulkiness between the Nb and the AuNP. Decreasing the difference can be achieved by decreasing the diameter of the AuNP.<sup>25</sup> However, decreasing the diameters weakens the strength of protein adsorption onto the AuNP surface, leading to highly dynamic protein coronas.<sup>26,27</sup> If the gold-bound protein layer is mandatory for target recognition, linkage of the protein to the AuNP should hence be performed

using stronger coordination links such as the Au-S bonds<sup>28,29</sup> and/or functionalization strategies involving covalent bonds.<sup>30</sup> To design Nb-AuNP conjugates with usefulness for gold immunolabelling application of cellular specimen, we explored methods for strongly linking thionitrobenzoates-coated AuNPs (AuG)<sup>31,32</sup> to bioengineered GFP binding Nbs.<sup>8,20</sup> We discovered that the non-covalent conjugation approach based on the complementary associating dimers originating from a p53 heterotetramer variant,<sup>17,18,33</sup> led to Nb:AuNP assemblies with excellent immunogold labelling abilities (Figure 1).


## 2. Results and discussion

### 2.1 Synthesis of GFP nanobody-AuNP conjugate

To generate immunogold probes based on Nbs, we selected the GFP binding Nb cAbGFP4 with a previously determined structure. It displays a dissociation constant ( $K_d$ ) within the nanomolar range.<sup>20</sup> For the gold domain, we used the 2.4 nm AuG that was previously described and extensively characterized.<sup>32</sup>






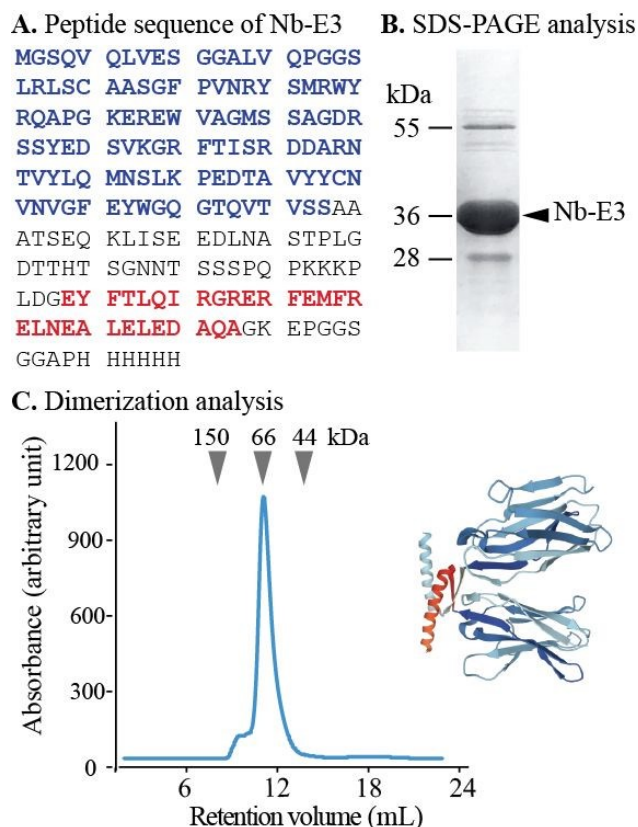

**Figure 2.** Characterization of the recombinant E3 tagged GFP binding nanobody. A. Peptide sequence. The GFP VHH (blue) is fused to the E-enriched p53 oligomerization domain (red) and to a polyhistidine tag. B. SDS PAGE analysis of the bacteria-expressed and purified protein after Ni-NTA chromatography showed monomeric Nb-E3. C. Size exclusion chromatography of the purified E3-fused nanobody. Elution of a species with an apparent molecular weight of 66 kDa confirmed dimerization.

This AuG is water-soluble and contains a single layer of substituted thiobenzoates that can be readily replaced with other thiol-containing molecules via a thiolate-for-thiolate exchange. Functionalized AuNPs with robust Au-S coordination bonds might hence be conveniently synthesized.

In our first attempts, we investigated the preparation of nanobody-AuNP conjugates directly from Nbs that were point-mutated to contain an additional thiol.<sup>14</sup> The GFP binding Nb sequence was bioengineered to possess either a C-terminal cysteine (C143-Nb) or a cysteine at the position 7 (C7-Nb). The C143-Nb displayed severe proteolytic instability and was not further used (Supporting Information, Figure S1). The C7-Nb was stable at 4°C for more than six months, had GFP binding ability similar to that of the wild type Nb (Supporting Information, Figure S2) and could be linked to AuG via Au-S coordination. The conjugates could be further purified and characterized by SDS-PAGE (Supporting Information, Figure S3). Unfortunately, in contrast to the covalent appending of fluorescent molecules,<sup>14</sup> the direct coordination of C7-Nb onto the 2.4 nm AuNP dramatically altered its ability to bind GFP and labelling potency (Figures S3). The direct Au-S coordination bond at this C7 position may have exposed the nanobody to the AuNP's corona, resulting in obliteration of the nearby GFP-Nb binding interface.

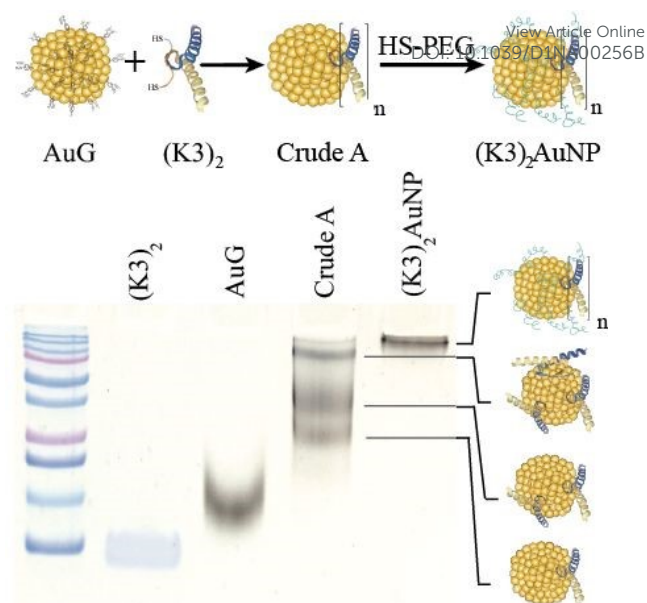

**Figure 3.** PAGE analysis of reaction products obtained by reaction of AuG with 3 molar equivalent of thiolated K3 dimer (Crude A) and then thiolated PEG 2000 Da ((K3)<sub>2</sub>AuNP).

Such alteration of the Nb specificity for its target after conjugation has already been pointed out in the literature.<sup>10</sup> Even the functionalization of Nbs with fluorophores of M.W. smaller than 1000 Da fluorophores via random coupling to lysines can drastically reduce Nb binding.<sup>14</sup>

To work out a Nb-AuNP conjugate without loss of binding affinity of the Nb for its target and loss of protein integrity, we could have played around by comprehensive modification of the peptide sequence at the C-terminus. Instead of undergoing this classical approach, we chose to investigate a non-covalent functionalization approach using the properties of 2 peptides derived from the p53 protein to specifically form a stable heterotetramer composed of two homodimers (Figure 1). Relative to the native p53 tetramerization domain, one sequence was enriched in lysine (K) while replacement of one K with glutamic acid (E) provided a E-enriched sequence (E3).<sup>17</sup> These E- and K-enriched sequences, named E3 and K3 respectively, were recently demonstrated to conveniently favour the selective non-covalent union of 2 distinctly tagged functional proteins into highly stable heterotetramers even in complex biological fluids crowded with all sorts of proteins and diverse compounds.<sup>18,33</sup>


First, the Nb was genetically engineered at its C-terminal end with the aspartate-enriched variant of the p53 heterotetramer domain (E3) along with a polyhistidine sequence (Figure 2).<sup>18</sup> The recombinant Nb-E3 fusion protein was then produced in *E. coli* and purified by immobilized metal affinity chromatography followed by size exclusion chromatography (SEC) with high yield and purity (Figure 2B). The SEC profile showed elution of a species with an apparent Molecular Weight (MW) close to 66 kDa corresponding to the MW of a dimer of Nb-E3 (Figure 2C). The integrity of the Nb-E protein was fully maintained upon storage at -80°C. Proteolytic cleavage was nonetheless




observed upon storage > 120 days at 4°C (Supporting information, Figure S4).

The K-enriched sequence K3<sup>17,18</sup> was fused to the CALNN motif.<sup>34</sup> According to extrapolation from the structure of the p53 domain,<sup>19</sup> the two cysteines at the N-terminal end are 2 nm apart with little chance to cross react. They can also point toward the same direction, offering possible bidentate coordination to AuG upon thiolate exchange reaction. Functionalization of the AuG with this dimer in 0.1 M HEPES buffer, pH 7.5 was then assayed at increasing dimer/AuG ratios (Supporting Information, Figure S5). After a 3h incubation time at 25°C to allow thiolate-to-thiolate exchange of Au(I)-coordinated ligands on the AuG surface, the crude reactions were analysed by SDS-PAGE. Functionalization of the AuNP with the dimer via exchange of ligands proceeded smoothly with an increased number of dimer attachment per particle by increasing the dimer/AuG ratios. At the dimer/AuG ratio of 3, the mixture was devoid of unreacted AuG. Three distinctive AuNP species with different electrophoretic mobility were produced, likely corresponding to AuNPs equipped with 1, 2 and 3 dimers. To note, the masking of the gold surface of AuG by coordination of thiolated PEG 2000 Da was mandatory to minimize non-specific adsorption of the probe onto cellular ultrastructure (Supporting Information, Figure S6). Therefore, this reaction condition was scaled-up and immediately followed by the addition of excess thiolated PEG 2000 Da to ensure full PEG-mediated shielding of the AuNP surface (Figure 3). The end product (K3)<sub>2</sub>AuNP, barely migrated into the polyacrylamide gel, likely because of the properties of PEG to shield the superficial charge of nanomaterial.<sup>35,36</sup>


#### A. Analysis of (Nb-E3)<sub>2</sub> binding to (K3)<sub>2</sub>AuNP

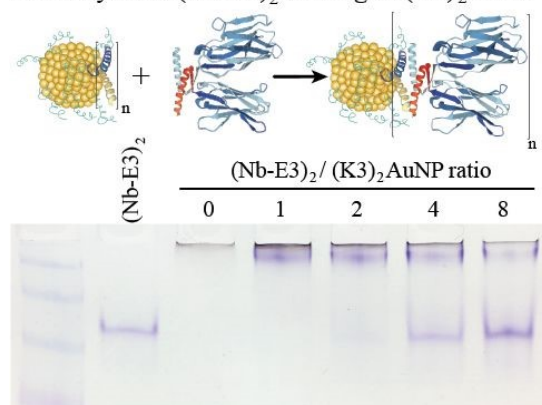

#### B. HAADF-STEM of (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP

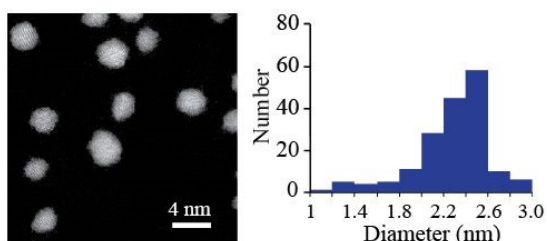

**Figure 4.** Characterization of the non-covalent (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP assemblies. A. Native PAGE analysis to determine the average stoichiometry for complete assembly of (Nb-E3)<sub>2</sub> with (K3)<sub>2</sub>AuNP. B. Scanning Transmission Electron Microscopy (STEM) analysis of the (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP.

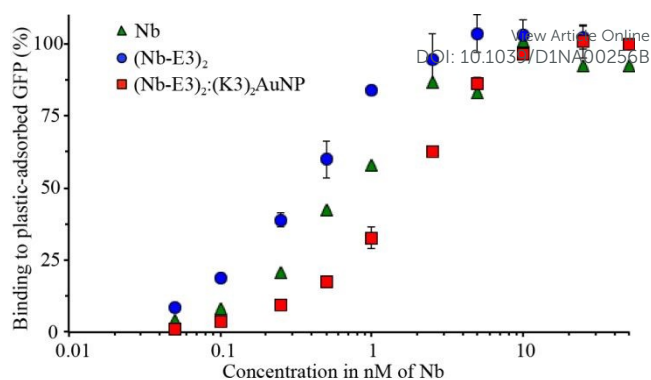

**Figure 5.** Apparent binding abilities of the GFP-binding nanobody (green triangle), the dimerized (Nb-E3)<sub>2</sub> (blue dot) and the non-covalent (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP assemblies (red square). The binding to GFP was determined using indirect ELISA analysis and plate-adsorbed GFP

The non-covalent association of (Nb-E3)<sub>2</sub> to (K3)<sub>2</sub>AuNP was next evaluated by titrating the (K3)<sub>2</sub>AuNP PAGE with increasing amounts of (Nb-E3)<sub>2</sub>. A PAGE analysis in non-denaturing conditions allowed the assessment of binding by detecting free/unbound (Nb-E3)<sub>2</sub> (Figure 4). A small amount of free (Nb-E3)<sub>2</sub> started to be detected at the (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP ratio of 2 indicating that each (K3)<sub>2</sub>AuNP can anchor slightly less than 2 (Nb-E3)<sub>2</sub>. In the next experiments, the non-covalent (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP assemblies were generated by mixing the modified AuNP with 2 molar equivalents of (Nb-E3)<sub>2</sub>.


The High-Angle annular dark field Scanning Transmission Electron Microscopy (HAADF-STEM) observation of (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP assemblies revealed gold particles of roughly spherical shape (Fig. 4 B). Analysis of a TEM image containing 180 gold particles (The sizes of the AuNP were distributed mostly between 2 and 2.6 nm TEM image containing 180 gold particles indicates that the diameters were mostly within the 2.0 to 2.6 nm range (average diameter: 2.31 nm; standard deviation: 0.31 nm) (Supporting information, Figure S7). Moreover, the image was almost devoid of clustered particles (less than 2%) indicating that the used synthetic condition mainly favours coordination of the two thiols of the bidentate K3 dimer onto gold atoms of one single AuNP, as drawn in the illustration (Figure 1).

#### 2.2 Binding ability of non-covalent (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP to GFP

In order to use the complex as a probe for GFP in microscopy, we had to check whether the (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP complex maintained its ability to bind GFP. To do so, we performed an indirect ELISA assay using purified GFP as the plastic-immobilized antigen and compared the binding profiles of the wild type Nb, (Nb-E3)<sub>2</sub> and (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP complex (Figure 5). The dose-dependent binding of the various Nbs tested showed similar sigmoidal profiles from which we assessed the apparent K<sub>d</sub>s. Accordingly, we found a K<sub>d</sub> of 0.8 nM for the wild type Nb, 0.4 nM for each Nb of (Nb-E3)<sub>2</sub> and 2 nM for each Nb of (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP.



## ARTICLE

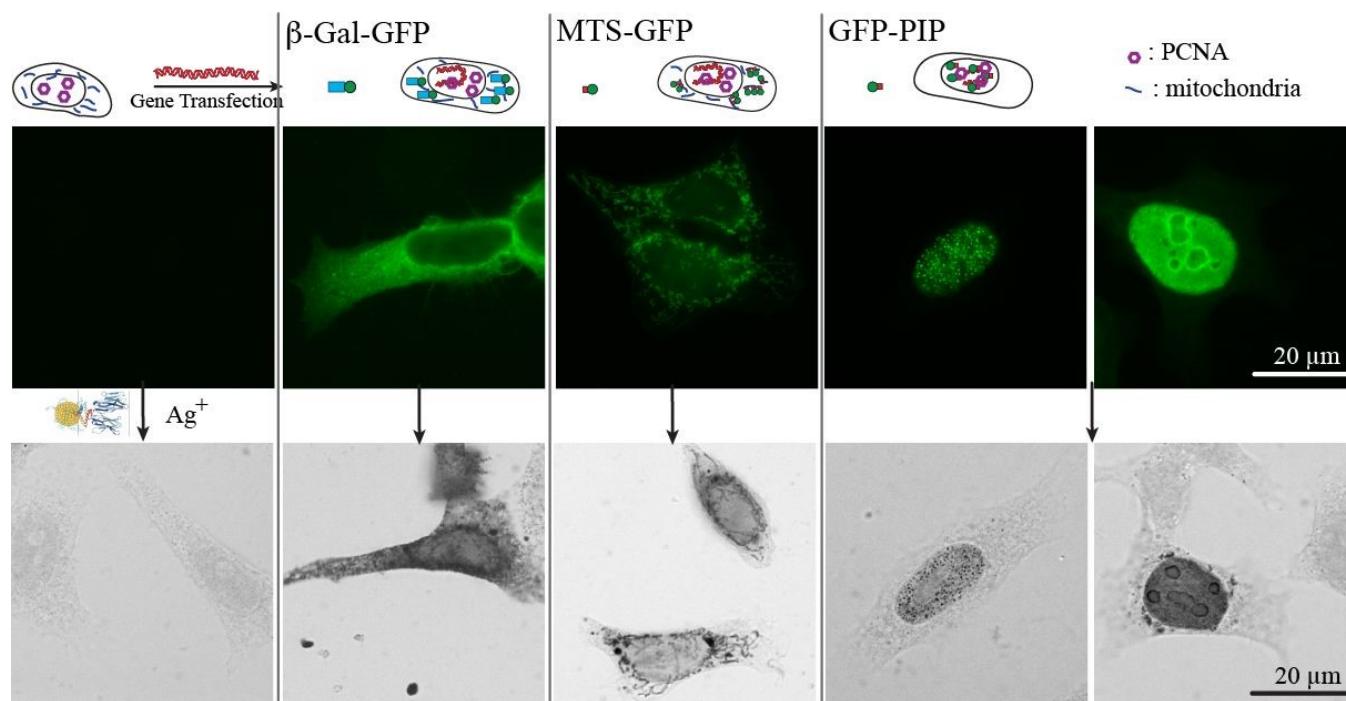

**Figure 6.** Fluorescent and  $(\text{Nb-E3})_2:(\text{K3})_2\text{AuNP}$ -mediated detection of protein-GFP fusions after transient gene transfection. HeLa cells were transiently transfected with DNA plasmids to express different GFP-protein fusions as indicated:  $\beta$ -Galactosidase-GFP ( $\beta$ -Gal-GFP), Mitochondria-Targeting Signal tagged GFP (MTS-GFP), GFP tagged-PCNA-Interacting Peptide (GFP-PIP). Upper images: Detection of the GFP signal in PFA-fixed HeLa cells 24 hours after DNA plasmid transfection. Lower images: the cell membrane was permeabilized, the cells were incubated with 6 nM  $(\text{Nb-E3})_2:(\text{K3})_2\text{AuNP}$ , washed and the gold nanoparticles bound to cellular components were detected by extensive silver enhancement visible by BFM

The  $K_d$  values indicated that the E3-mediated dimerization of Nb results in a gratifying avidity effect (four fold increased in apparent affinity when the  $(\text{Nb-E3})_2$  is compared to Nb).<sup>18,37</sup> In contrast, the grafting of about 2  $(\text{Nb-E3})_2$  onto  $(\text{K3})_2\text{AuNP}$  resulted in a 5-fold affinity loss relative to the  $(\text{Nb-E3})_2$ .

The reason behind the apparent affinity loss of  $(\text{Nb-E3})_2$  after anchorage to the  $(\text{K3})_2\text{AuNP}$  might be explained by the presence of the PEG. The PEG is required to minimize unspecific association of proteins to the AuNP surface. However, its bulkiness and vicinity to the Nb-anchored AuNP may entail a weakening of the apparent binding affinity of the AuNP-attached nanobodies for GFP.



The efficiency of the  $(\text{Nb-E3})_2:(\text{K3})_2\text{AuNP}$  complex to mark GFP-protein fusions with a AuNP inside cells was then evaluated using immunocytochemistry method followed by bright field microscopy (BFM) (Figure 6). HeLa cells were transiently transfected with DNA plasmids encoding a  $\beta$ -Galactosidase-GFP ( $\beta$ -Gal-GFP), a Mitochondria-Targeting Signal tagged GFP (MTS-GFP) and a GFP tagged-PCNA-Interacting Peptide (PIP) (GFP-PIP). The cells expressing various levels of each exogenous protein were then observed by FM (Figure 6, upper images). The subcellular localization of these GFP-protein fusions were then assayed by immunogold labelling

with  $(\text{Nb-E3})_2:(\text{K3})_2\text{AuNP}$  followed by silver enhancement to sizes observable by BFM (Figure 6, lower images). Comparison between the FM and BFM images of the transfected HeLa cells showed an excellent correlation between the fluorescent signal and the silver-enhanced AuNPs. The 520 kDa  $\beta$ -galactosidase-GFP fusion protein was seen inside the cytosol but not inside nuclei in agreement with the function of the nuclear envelop to block passive diffusion of macromolecules above 50 kDa. When the 520 kDa  $\beta$ -galactosidase-GFP fusion was further equipped with a Nuclear Localization Signal (NLS), FM and immunogold labelling experiments showed also the expected transport of  $\beta$ -Gal-GFP-NLS into the cell nuclei (Supporting Information, Figure S8). The preferential accumulation of MTS-GFP in mitochondria (filamentous ultrastructure near surrounding the nucleus) was also observed by the immunogold labelling protocol. The GFP-PIP can be used as a marker for cell replication.<sup>38</sup> Two patterns could be observed in transfected cells: GFP-PIP fluorescent foci in the nucleus corresponding to early DNA replication initiation sites, or the nucleus filled with GFP-PIP with accumulation near the nucleoli corresponding to a more advanced state of DNA replication. Both of these patterns were also observed using  $(\text{Nb-E3})_2:(\text{K3})_2\text{AuNP}$ .






## A. H2B-GFP HeLa

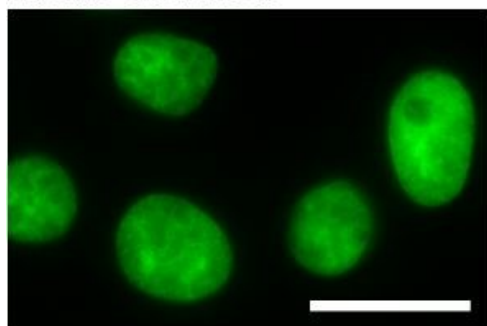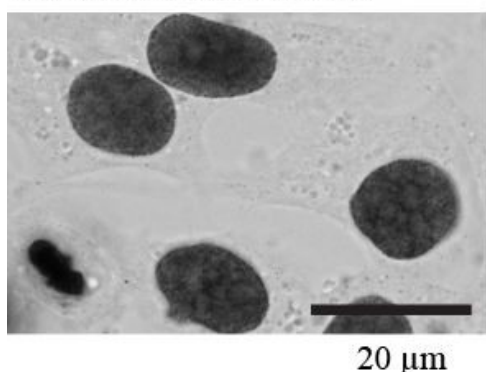B. H2B-GFP HeLa labeled with (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP

## C. HAADF-STEM of gold labeled H2B-GFP HeLa

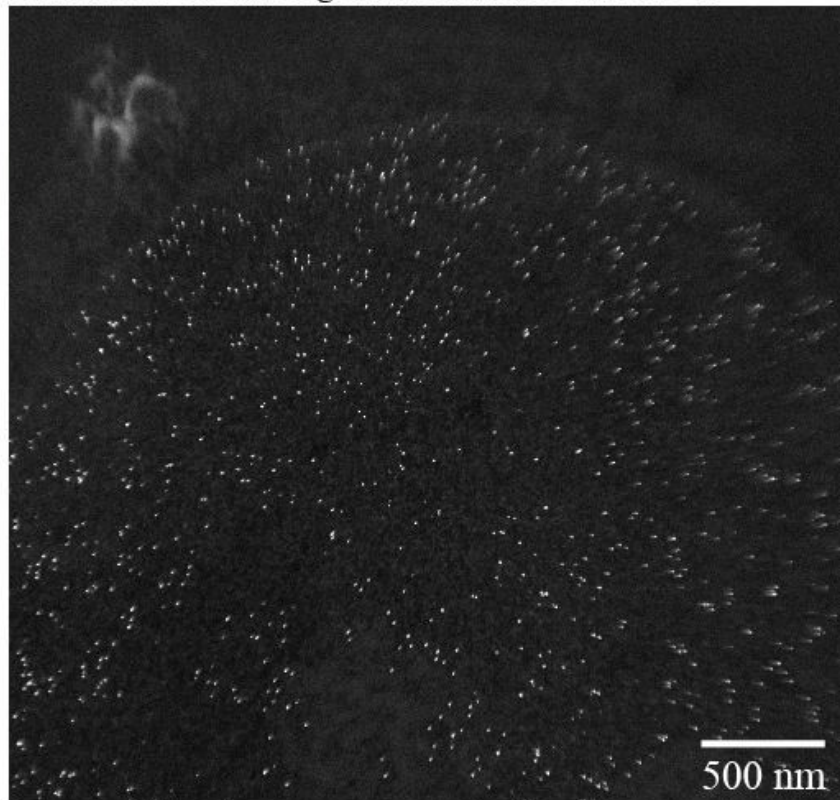

**Figure 7.** Fluorescent and (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP-mediated detection of H2B-GFP fusions inside the nuclei of HeLa cells transformed to stably express H2B-GFP fusions. A. Fluorescence detection of GFP in H2B-GFP HeLa. B. BFM image of H2B-GFP HeLa with (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP and extensive silver enhancement. C. HAADF-STEM image of H2B-GFP HeLa after labelling with (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP and mild silver enhancement.

The ability of the (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP to detect GFP in cellular specimen fixed with low percentage of glutaraldehyde<sup>39</sup> was preserved although with a loss in sharpness (Supporting information, Figures S9 and S10). For comparison of labelling activity, a mouse anti-GFP antibody-gold particle conjugate made from the same TAB-, TNB- coated gold particle and a monoclonal 150 kDa IgG was prepared (Supporting Information, Figure S11). Its gold labelling ability was similar to the one of (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP (Supporting Information, Figures S12-S14). A tendency of the anti-GFP IgG-AuNP conjugate to preferentially label the nuclear periphery of the H2B-GFP HeLa was noticed (Figures S12 and S14). If the (K3)<sub>2</sub>AuNP is preferably mixed with the (Nb-E3)<sub>2</sub>: right before use, the (K3)<sub>2</sub>AuNP complex was seen to remain active 7 days after storage at 4°C (Supporting Information, Figures S15). The selectivity of E3 dimer for the K3 dimer could also be exploited by detecting the specimen-bound (GFP Nb-E3)<sub>2</sub> with (K3)<sub>2</sub>AuNP through sequential incubations (Supporting Information, Figure S15). Altogether, the experiments clearly demonstrate the usefulness of (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP as probe to label GFP and fusion proteins with gold particles either inside the cytosol or inside the nucleus.

### 2.3 (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP assemblies for immunogold labelling of GFP-protein fusion inside cells by Electron Microscopy

We next evaluated whether (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP complexes were suitable for EM labelling of GFP-tagged proteins in cells using a stably transformed HeLa cell line that expresses the nuclear histone protein H2B fused to GFP.<sup>40</sup> First, the stable H2B-GFP HeLa and wild type HeLa cell lines were fixed and permeabilized for immunocytochemistry labelling with extensive silver-mediated amplification of AuNPs for FM and BFM imaging (Figure 7, Images A and B). Since the silver staining correlated well with the GFP signal, the cells were processed for gold immunolabelling and moderate silver enhancement before resin embedding, sectioning and EM observation of the specimen. We also prepared an EM specimen of the immunolabelled HeLa H2B-GFP without the silver enhancement step. This non-silver enhanced specimen was analysed for gold content in the nucleus using Energy Dispersive X-ray (EDX) spectroscopy (Supporting Information, Figure S16). The EDX spectrum clearly demonstrated the presence of gold atoms inside the cell nucleus ( $Au_{Ma} = 2.123$  keV,  $Au_{Mb} = 2.203$  keV,  $Au_{La} = 9.713$  keV,  $Au_{Lb} = 11.443$  keV). Unfortunately, in our hands, the direct visualization of the AuNPs in the cell sections was unfruitful for the moment due to the low contrast of the specimen and



difficulty to find the nucleus in where to zoom in. We therefore performed a mild silver enhancement procedure of the specimen containing (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP-labeled H2B-GFP HeLa cells to grow the size of the particle to size below 20 nm. After sectioning, the specimen was analysed by TEM. HAADF-STEM (Figure 7, image C) clearly showed the presence of discrete particles inside the nucleus. EDX spectroscopy confirmed that these particles were composed of silver and gold (Supporting Information, Figure S17). The density of AuNPs in the different subcellular compartments was then measured by compiling data from six images to obtain: 37 AuNPs per  $\mu\text{m}^2$  in the heterochromatin (HC) near the nuclear periphery; 14 AuNPs per  $\mu\text{m}^2$  within the perinucleolar compartment (PC) and; 4 AuNPs per  $\mu\text{m}^2$  within the euchromatin (EC) regions within the nucleus. The nucleoli and the cytosol were almost devoid of probes (0.5 and 0.2 AuNPs per  $\mu\text{m}^2$  for the Nucleoli and cytosol, respectively). A similar H2B-GFP nuclear labelling pattern was also obtained using conventional TEM whereas the wild type HeLa was devoid of any particles (Supporting Information, Figure S18). A preferential localization of H2B-GFP in the heterochromatin near the nuclear or nucleolar periphery was in agreement with published studies.<sup>40,41</sup> We can nonetheless note a discrepancy between nuclear staining seen by OM and inhomogeneous nuclear labelling observed by EM. This variation likely results from the silver staining procedure (sizes of AuNP-seeded silver particles for BFM imaging were made larger than the ones for EM imaging) and from the difference in specimen thickness (BFM images were projections of light intensity variation throughout the whole cell; EM were performed on about 100 nm thick specimen). The density of gold labelling inside the nuclei was lower than the expected calculated density of nearly  $10^4$  H2B per  $\mu\text{m}^2$  (one human cell nucleus contains approximately 30 million nucleosomes, corresponding to 60 million H2B molecules).<sup>42</sup> However, the immunogold labelling protocol often underestimates the real number because PFA might preclude recognition of a proportion of target epitope. High local concentration of targets might also play a role.<sup>43</sup> In our specific case, the H2B-GFP fusion was moreover expressed in addition to the endogenous non-labelled H2B, likely at a low percentage.

### 3. Materials and methods

#### 3.1 Genetic engineering of the Nb-E3 construct

The GFP binding nanobody was engineered to contain the E3 peptide sequence<sup>18</sup> and polyhistidine at the C terminal end. The GFP binding nanobody<sup>20</sup> gene was amplified using PCR and primers of sequences: CGTCAG CCATGG GGTCCC AGGTTTCAGC and CCACAG GAATTC ACAATG GTGATG ATGGTG ATGTGCG. The DNA fragment was then inserted into a pETOM vector containing the E3 tag DNA sequence using *NcoI* and *SpeI* restriction sites.<sup>18</sup>

#### 3.2 Expression and purification of (Nb-E3)<sub>2</sub>

The Recombinant nanobody was expressed in *E. coli* BL21(DE3)pLys after induction with 1 mM IPTG in 100 mL LB medium at 20°C for 24h. The bacteria were lysed by ultrasonication. The his-tagged proteins were then purified by immobilized metal affinity chromatography using a HisTrap HP column (1 mL) charged with NiSO<sub>4</sub> and then by gel filtration on a HiLoad Superdex 200PG preparative column operating at a flow rate of 0.5 mL/min. Protein fractions were analysed by SDS-PAGE. Selected fractions were pooled and protein solutions were concentrated with Amicon Ultra 4 mL centrifugal devices (MWCO 3 kDa).

#### 3.3 Synthesis of AuNP-nanobody conjugates

Typically, the AuG in 0.1 M HEPES, pH 7.5 solution (70  $\mu\text{L}$ , 3 nmol) was added to the peptide of sequence [CALNNGEYFTLQIRGRERFEMFRKLNKALELKDAQA] (176  $\mu\text{L}$  of a 1 mM solution, 18 nmol) freshly prepared in 0.1 M HEPES, pH 7.5. After 3 h at 25°C the remaining exchangeable thiolates on the AuG surface were then exchanged to polyethyleneglycol 2000 Da by addition of alpha-methoxy-omega-mercapto poly(ethylene glycol) 2000 Da (276  $\mu\text{L}$  of a 1 mM solution, 276 nmol) followed by a 3h incubation time at 25°C. The crude mixture was then purified by ultrafiltration (30 kDa cut-off) (5 times 0.5 mL of 0.1 M HEPES, pH 7.5) to yield 50  $\mu\text{L}$  of the modified AuNP ((K3)<sub>2</sub>AuNP). The concentration of AuNP was determined spectrophotometrically to be 18  $\mu\text{M}$ .<sup>44,45</sup> The (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP was finally obtained by addition of (Nb-E3)<sub>2</sub> (20  $\mu\text{L}$  of a 5  $\mu\text{M}$  solution, 100 pmol) with the (K3)<sub>2</sub>AuNP (5  $\mu\text{L}$  of a 10  $\mu\text{M}$  solution).

#### 3.4 Transfection experiments

The plasmids encoding Mitochondria Targeting Signal-GFP fusion (MTS-GFP), GFP- $\beta$ -galactosidase fusion (GFP- $\beta$ -gal), GFP-PCNA Interacting Peptide fusion (GFP-PIP) were gifts from Prof. Étienne Weiss and Dr. Mariel Donzeau.<sup>44</sup> They were transfected into HeLa cells using PEI derivatives.<sup>46,47</sup> Cells were seeded onto glass coverslips in 24-well plates at 50000 cells/well the day before the transfection experiment. Transgene expression was analysed after 24 h.

#### 3.5 Immunocytochemistry for bright field microscopy

Coverslip-adhered cells were fixed with 4% PFA in PBS for 20 min at 20°C. The coverslips were then washed with PBS (3 x 0.5 mL, 5 min), PBS containing 50 mM glycine (0.5 mL, 20 min) and the cell plasma membranes were permeabilized with 0.05% Triton X-100 in PBS (0.5 mL, 5 min). The coverslips were soaked in PBS containing 10% (w/v) BSA for 1h, washed with 0.2% acetylated BSA (BSA-c) in PBS (2 x 0.5 mL, 5 min) and then incubated with 6 nM (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP in 0.2% BSA-c containing 10% FCS, 0.5 mL for 1 h. Next the cells were washed with 0.2% BSA-c (2 x 0.5 mL, 5 min) and with 80 mM citrate buffer pH 6.2 (3 x 0.5 mL, 5 min). Finally the AuNPs were made visible using a silver staining protocol modified from the Danscher method as reported previously.<sup>48</sup>





### 3.6 Pre-embedding immunolabelling and sample preparation for EM

Cells were fixed with 4% PFA in PBS for 20 min at 20°C. The coverslips were washed with PBS (3 x 0.5 mL, 5 min), PBS containing 50 mM glycine (0.5 mL, 20 min) and the cell plasma membranes were permeabilized with 0.05% Triton X-100 in PBS (0.5 mL, 5 min). The coverslips were soaked in PBS containing 10% (w/v) BSA for 1h, washed with 0.2% BSA-c in PBS (2 x 0.5 mL, 5 min) and then incubated with (Nb-E3)<sub>2</sub>:(K3)<sub>2</sub>AuNP (12 nM in 0.2% BSA-c containing 10% FCS) overnight at 4°C. The next day the cells were washed with PBS (5 x 0.5 mL, 8 min) and were post-fixed with 1% glutaraldehyde in PBS (15 min). The cells were washed with PBS (3 times), with H<sub>2</sub>O (5 times) and the AuNPs were enlarged using R-Gent SE-EM Silver Enhancement Reagent (Aurion, 80 min of development). The specimen was then washed with H<sub>2</sub>O (5 times) and post-fixed with 0.5% osmium tetroxide (15 min). The specimen was again washed with H<sub>2</sub>O, dehydrated with increasing concentrations of ethanol, treated with propylene oxide and flat embedded in Epon. The resin-embedded sample was sectioned into 60 nm thick slices that were deposited onto copper 200 mesh grids (Electron Microscopy Sciences).

**High-angle annular dark-field scanning transmission electron microscopy (HAADF-STEM) and energy dispersive X-ray spectroscopy (EDX):** Cellular samples were imaged using a Cs-corrected JEOL JEM-2100F scanning transmission electron microscope operating at 200 kV and equipped with a High Angle Annular Dark Field Detector. EDX analysis was performed on the same instrument equipped with a JEOL Silicon Drift Detector (DrySD60GV, sensor size 60 mm<sup>2</sup>) with a solid angle of 0.6 srad.

## 4. Conclusion

During our investigation to precisely functionalize AuNPs with the minimal sized Nb, we discovered that the conjugation approach involving the non-covalent assembly between complementary associating peptide tags appended to the AuNP and the nanobody, respectively, yielded probes that specifically bind to GFP. These probes proved highly effective for the visualization of various GFP-protein fusions inside cells by BFM and high resolution HAADF-STEM, thus pointing out the versatility of these gold-tagged Nbs for labelling applications using two different imaging modalities. The synthesis of the probe is convenient to perform: the synthetic steps can be monitored in a straightforward manner and the building blocks can be separately synthesized and stored in accordance with their stability. Moreover, the linkage of the recombinant nanobody to the AuNP at the latest synthetic step (in here after the required pegylation to protected the AuNP from interacting with encountered proteins) is extremely convenient as it limits possible chemical or structural denaturation of the protein. Even if the current probes are mixtures of species (the number of dimerized E3-Nbs per (K3)<sub>2</sub>AuNP oscillates around 2), this approach offers by far more control over stoichiometry and orientation of the

attached E3-Nbs than the nanoparticle functionalization via adsorption or EDC chemistry. This non-covalent conjugation approach is clearly implementable for other nanobodies and therefore unlocks the usefulness of future nanobodies targeting proteins for the individual localization of protein inside the cell by EM and possibly cryo EM at unprecedented high resolution.

## Author Contributions

NG, MD, GZ, DS, MB, DI and AMH designed and performed experiments; NG, GZ, PS, SO, OE conceived experiments, analysed the data and revised the manuscript, NG and GZ drafted the manuscript.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This research was supported by the CNRS 80prime program attributed to GZ, OE and PS, the ITI Innovec (IdEx (ANR-10-IDEX-0002), SFRI (ANR-20-SFRI-0012)) and La Ligue contre le Cancer CCIR-Est). NG was funded by a PhD fellowship from the IdEX Unistra (Université de Strasbourg and Investissement d'Avenir). Transmission electron microscopy observation was performed at Plateforme Imagerie in vitro, CNRS UPS 3156, Strasbourg. We are grateful to Robert Drillien for style-edition of the text.

## Notes and references

- 1 L. Schermelleh, A. Ferrand, T. Huser, C. Eggeling, M. Sauer, O. Biehlmaier, Gregor P. C. Drummen, *Nature Cell Biology*, 2019, **21**, 72–84.
- 2 Z. Jiang, X. Jin, Y. Li, S. Liu, X.-M. Liu, Y.-Y. Wang, P. Zhao, X. Cai, Y. Liu, Y. Tang, X. Sun, Y. Liu, Y. Hu, M. Li, G. Cai, X. Qi, S. Chen, L.-L. Du and W. He, *Nature Methods*, 2020, **17**, 937–946.
- 3 W. P. Faulk and G. M. Taylor, *Immunochemistry*, 1971, **8**, 1081–1083.
- 4 E. V. Polishchuk and R. S. Polishchuk, *Tissue and Cell*, 2019, **57**, 103–110.
- 5 R. C. N. Melo, E. Morgan, R. Monahan-Earley, A. M. Dvorak and P. F. Weller, *Nat Protoc*, 2014, **9**, 2382–2394.
- 6 I. Orlov, A. Schertel, G. Zuber, B. Klaholz, R. Drillien, E. Weiss, P. Schultz and D. Spehner, *Scientific reports*, 2015, **5**, 8324.
- 7 M. S. Sirerol-Piquer, A. Cebrián-Silla, C. Alfaro-Cervelló, U. Gomez-Pinedo, M. Soriano-Navarro and J.-M. G. Verdugo, *Micron*, 2012, **43**, 589–599.
- 8 U. Rothbauer, K. Zolghadr, S. Tillib, D. Nowak, L. Schermelleh, A. Gahl, N. Backmann, K. Conrath, S. Muyldermans, M. C. Cardoso and H. Leonhardt, *Nature Methods*, 2006, **3**, 887–889.
- 9 K. Farnaz, B. Mahdi, R. Abbas and K.-L. Fatemeh, *International Reviews of Immunology*, 2018, **37**, 316–322.
- 10 D. Schumacher, J. Helma, A. F. L. Schneider, H. Leonhardt



- and C. P. R. Hackenberger, *Angew. Chem. Int. Ed.*, 2018, **57**, 2314–2333.
- 11 T. Hebbrecht, J. Liu, O. Zwaenepoel, G. Boddin, C. Van Leene, K. Decoene, A. Madder, K. Braeckmans and J. Gettemans, *New Biotechnology*, 2020, **59**, 33–43.
- 12 S. Massa, C. Xavier, J. De Vos, V. Caveliers, T. Lahoutte, S. Muyltermans and N. Devoogdt, *Bioconjug. Chem.*, 2014, **25**, 979–988.
- 13 E. Platonova, C. M. Winterflood, A. Junemann, D. Albrecht, J. Faix and H. Ewers, *Methods*, 2015, **88**, 89–97.
- 14 T. Pleiner, M. Bates, S. Trakhanov, C.-T. Lee, J. E. Schliep, H. Chug, M. Böhning, H. Stark, H. Urlaub and D. Görlich, *Elife*, 2015, **4**, e11349.
- 15 G. Carrington, D. Tomlinson and M. Peckham, *Mol. Biol. Cell*, 2019, **30**, 2737–2740.
- 16 Ben N G Giepmans, *frontiers in Cellular Neuroscience*, 2020, **14**.
- 17 R. D. Brokx, E. Bolewska-Pedyczak and J. Gariépy, *Journal of Biological Chemistry*, 2003, **278**, 2327–2332.
- 18 M. Vigneron, F. Dietsch, L. Bianchetti, A. Dejaegere, Y. Nominé, A. Cordonnier, G. Zuber, B. Chatton and M. Donzeau, *Bioconjug. Chem.*, 2019, **30**, 1734–1744.
- 19 G. M. Clore, J. G. Omichinski, K. Sakaguchi, N. Zambrano, H. Sakamoto, E. Appella and A. M. Gronenborn, *Science*, 1994, **265**, 386–391.
- 20 M. H. Kubala, O. Kovtun, K. Alexandrov and B. M. Collins, *Protein Science*, 2010, **19**, 2389–2401.
- 21 M. Kijanka, E. G. van Donselaar, W. H. Müller, B. Dorresteyn, D. Popov-Čeleketić, M. el Khattabi, C. T. Verrips, P. M. P. van Bergen en Henegouwen and J. A. Post, *Journal of Structural Biology*, 2017, **199**, 1–11.
- 22 N. Ariotti, T. E. Hall, J. Rae, C. Ferguson, K.-A. McMahon, N. Martel, R. E. Webb, R. I. Webb, R. D. Teasdale and R. G. Parton, *Developmental Cell*, 2015, **35**, 513–525.
- 23 N. Ariotti, J. Rae, N. Giles, N. Martel, E. Sierrecki, Y. Gambin, T. E. Hall and R. G. Parton, *PLoS Biol*, 2018, **16**, e2005473.
- 24 J. Goossens, H. Sein, S. Lu, M. Radwanska, S. Muyltermans, Y. G. J. Sterckx and S. Magez, *Anal. Methods*, 2017, **9**, 3430–3440.
- 25 G. Zuber, E. Weiss and M. Chiper, *Nanotechnology*, 2019, **30**, 352001.
- 26 L. Boselli, E. Polo, V. Castagnola and K. A. Dawson, *Angew. Chem.*, 2017, **129**, 4279–4282.
- 27 M. Zhou, C. Zeng, Y. Chen, S. Zhao, M. Y. Sfeir, M. Zhu and R. Jin, *Nature Communications*, 2016, **7**, 1–7.
- 28 C. J. Ackerson, P. D. Jadzinsky, G. J. Jensen and R. D. Kornberg, *Journal of the American Chemical Society*, 2006, **128**, 2635–2640.
- 29 C. J. Ackerson, R. D. Powell and J. F. Hainfeld, in *Methods in Enzymology*, Elsevier, 2010, vol. 481, pp. 195–230.
- 30 C. Leduc, S. Si, J. Gautier, M. Soto-Ribeiro, B. Wehrle-Haller, A. Gautreau, G. Giannone, L. Cognet and B. Lounis, *Nano Lett.*, 2013, **13**, 1489–1494.
- 31 D. Desplancq, N. Groysbeck, M. Chiper, E. Weiss, B. Frisch, J.-M. Strub, S. Cianferani, S. Zafeiratos, E. Moeglin, X. Holy, A. L. Favier, S. De Carlo, P. Schultz, D. Spohner and G. Zuber, *ACS Applied Nano Materials*, 2018, **1**, 4236–4246.
- 32 N. Groysbeck, A. Stoessel, M. Donzeau, E. C. da Silva, M. Lehmann, J.-M. Strub, S. Cianferani, K. Dembélé and G. Zuber, *Nanotechnology*, 2019, **30**, 184005.
- 33 A. Stoessel, N. Groysbeck, L. Guyot, L. Barret, Y. Nominé, L. Nguekeu-Zebaze, A. Bender, L. Voilquin, T. Lutz, N. Pallaoro, M. Blocat, C. Deville, M. Masson, G. Zuber, B. Chatton and M. Donzeau, *Bioconjug. Chem.*, 2020, **31**, 2421–2430.
- 34 R. Lévy, N. T. K. Thanh, R. C. Doty, I. Hussain, R. J. Nichols, D. J. Schiffrin, M. Brust and D. G. Fernig, *Journal of the American Chemical Society*, 2004, **126**, 10076–10084.
- 35 G. Zuber, L. Zammuto-Italiano, E. Dauty and J.-P. Behr, *Angew. Chem. Int. Ed. Engl.*, 2003, **42**, 2666–2669.
- 36 M. Chiper, N. Tounsi, R. Kole, A. Kichler and G. Zuber, *J Control Release*, 2017, **246**, 60–70.
- 37 G. Vauquelin and S. J. Charlton, *British Journal of Pharmacology*, 2013, **168**, 1771–1785.
- 38 H. D. Herce, M. Rajan, G. Lättig-Tünnemann, M. Fillies and M. C. Cardoso, *Nucleus*, 2014, **5**, 590–600.
- 39 B. M. Humbel, M. D. de Jong, W. H. Müller and A. J. Verkleij, *Microsc. Res. Tech.*, 1998, **42**, 43–58.
- 40 H. Kimura and P. R. Cook, *J. Cell Biol.*, 2001, **153**, 1341–1353.
- 41 T. Kanda, K. F. Sullivan and G. M. Wahl, *Curr. Biol.*, 1998, **8**, 377–385.
- 42 W. K. M. Lai and B. F. Pugh, *Nat Rev Mol Cell Biol*, 2017, **18**, 548–562.
- 43 U. Schnell, F. Dijk, K. A. Sjollem and B. N. G. Giepmans, *Nature Methods*, 2012, **9**, 152–158.
- 44 G. Freund, D. Desplancq, A. Stoessel, R. Weinsanto, A.-P. Sibling, G. Robin, P. Martineau, P. Didier, J. Wagner and E. Weiss, *J. Mol. Recognit.*, 2014, **27**, 549–558.
- 45 X. Liu, M. Atwater, J. Wang and Q. Huo, *Colloids and Surfaces B: Biointerfaces*, 2007, **58**, 3–7.
- 46 C. Chandrashekar, B. Pons, C. D. Muller, N. Tounsi, R. Mulherkar and G. Zuber, *Acta Biomater.*, 2013, **9**, 4985–4993.
- 47 J. B. Gossart, E. Pascal, F. Meyer, E. Heuillard, M. Gonçalves, F. Gossé, E. Robinet, B. Frisch, C. Seguin and G. Zuber, *Global Challenges*, 2017, **1**, 1700013.
- 48 R. W. Burry, D. D. Vandredre and D. M. Hayes, *J. Histochem. Cytochem.*, 1992, **40**, 1849–1856.



View Article Online  
DOI: 10.1039/D1NR02568B