

ACCEPTED MANUSCRIPT • OPEN ACCESS

Enhanced solar photocatalysis of TiO₂ nanoparticles and nanostructured thin films grown on paper

To cite this article before publication: Tomas Freire *et al* 2021 *Nano Ex.* in press <https://doi.org/10.1088/2632-959X/abed40>

Manuscript version: Accepted Manuscript

Accepted Manuscript is “the version of the article accepted for publication including all changes made as a result of the peer review process, and which may also include the addition to the article by IOP Publishing of a header, an article ID, a cover sheet and/or an ‘Accepted Manuscript’ watermark, but excluding any other editing, typesetting or other changes made by IOP Publishing and/or its licensors”

This Accepted Manuscript is © 2021 The Author(s). Published by IOP Publishing Ltd.

As the Version of Record of this article is going to be / has been published on a gold open access basis under a CC BY 3.0 licence, this Accepted Manuscript is available for reuse under a CC BY 3.0 licence immediately.

Everyone is permitted to use all or part of the original content in this article, provided that they adhere to all the terms of the licence <https://creativecommons.org/licenses/by/3.0>

Although reasonable endeavours have been taken to obtain all necessary permissions from third parties to include their copyrighted content within this article, their full citation and copyright line may not be present in this Accepted Manuscript version. Before using any content from this article, please refer to the Version of Record on IOPscience once published for full citation and copyright details, as permissions may be required. All third party content is fully copyright protected and is not published on a gold open access basis under a CC BY licence, unless that is specifically stated in the figure caption in the Version of Record.

View the [article online](#) for updates and enhancements.

Enhanced solar photocatalysis of TiO₂ nanoparticles and nanostructured thin films grown on paper

T. Freire¹, A.R. Fragoso¹, M. Matias¹, J. V. Pinto¹, A.C. Marques¹, A. Pimentel¹, P. Barquinha¹, R. Huertas², E. Fortunato¹, R. Martins^{1,*}, D. Nunes^{1,*}

¹*i3N/CENIMAT, Department of Materials Science, Faculty of Sciences and Technology, Universidade NOVA de Lisboa, Campus de Caparica, 2829-516 Caparica, Portugal*

²*iBET-Instituto de Biologia Experimental e Tecnologica, Oeiras, Portugal*

Abstract

Titanium dioxide nanoparticles and nanostructured thin films were simultaneously synthesized using a microwave-assisted hydrothermal method. The synthesis formed very fine particles, appearing as nanospheres in the 11 nm size range. As for the nanostructured film, they have displayed similar structural characteristics to the nanoparticles, with thickness of 130 nm. These films covered uniformly and homogeneously the Whatman paper, while maintaining its flexibility. The materials processed had their photocatalytic activity assessed from rhodamine B degradation under solar radiation (91 % degradation after 40 min for the powder material and 68 % after 6 h for the nanostructured thin film). Reusability experiments were also carried out, revealing superior performance concerning the Degussa P25, the most common photocatalyst used. The results of the present work can be thought as an option for the existing photocatalysts activated under solar light, namely for water purification, as it simultaneously produces enhanced photocatalytic powders and photocatalytic papers fully disposable and that can be easily recycled.

Keywords: TiO₂ nanoparticles, nanostructured films; paper substrates; photocatalysis; microwave irradiation.

**Corresponding Authors:* Daniela Nunes and Rodrigo Martins, *i3N/CENIMAT*, Department of Materials Science, Faculty of Sciences and Technology, Universidade NOVA de Lisboa, Campus de Caparica, 2829-516 Caparica, Portugal, Tel: (+351) 212948562, Fax: (+351) 21 294 8558, e-mails: daniela.gomes@fct.unl.pt (D. Nunes) and rm@uninova.pt (R. Martins).

1. Introduction

Water is an essential resource for all known forms of life, and it is used in every industrial sector. Despite covering 70 % of the earth's surface, just 2.5 % of this water is fresh for consumption and even this small percentage is not accessible for every human in the planet Earth.[1,2] This scarcity and misuse led to the necessity to develop techniques and products that facilitated the treatment of wastewater and helped decreasing the amount of people without access to it.[3,4]

Since the beginning of the millennium, companies and governments [5–8] have been addressing sustainability issues, approaches to decrease the problems caused by human activities and industrial sectors and ways to make responsible choices regarding natural resources' exploitation, which culminated in the Sustainable Development Goals by the UN, such as the Goal 6: Clean Water and Sanitation.[9] To make this possible some metal oxides, like Titanium Dioxide (TiO_2), are being used as photocatalytic agents to breakdown different water pollutants.

TiO_2 is an environmentally friendly, earth abundant[10], versatile n-type semiconductor used for several applications, like photocatalysis[11–14], dye-sensitized solar cells[15–18], electrochromic devices[18–21], and is even used as an antibacterial agent[22–24]. This material can exhibit different structural phases, being the most common the rutile, anatase and brookite[18,21,25], typically TiO_2 displaying an optical bandgap of 3.0 and 3.2 eV for rutile and anatase, respectively, and a bandgap for brookite ranging from 3.1 and 3.4 eV[21,25,26]. TiO_2 is extensively used as a photocatalyst in the forms of anatase, rutile, brookite or as mixed phases [27–30].

Photocatalysis is described as the process of altering reactions' rate upon exposure to a light source. In this process, the material absorbs photons that will give sufficient energy to an electron (e^-) in the valence band to get excited and jump to the conduction band, leaving behind a positive charge particle (h^+) and generating an electron-hole pair, which will be responsible for reducing and oxidizing the compounds on the photocatalyst surface.[31–33] The water splitting induced by the TiO_2 photocatalytic properties is a widely studied phenomenon, in which this material, through the reduction and oxidation of the solution, originates O_2^* and OH^* radicals that are effective in the decomposition of organic substances, pollutants and microorganisms. In the field of photocatalysis, TiO_2 appears as a common solution for several applications related with water treatment since

1
2
3 this material displays strong oxidizing abilities for the organic pollutants' decomposition,
4 its hydrophilicity, chemical stability and low cost.[34–37]

5
6 TiO₂ films can be integrated in flexible and rigid substrates and used as water filters.
7
8 Despite being an efficient process, TiO₂ photocatalysis is most likely to be activated by
9 UV irradiation, which only comprises a reduced portion of the solar spectrum. Taking
10 advantage of the rest of the solar spectrum is the future of photocatalysis.[13,32,38,39]
11
12 Thus, approaches for making TiO₂ photoactive under solar radiation are highly sought.
13
14

15 The synthesis method for the TiO₂ as a photocatalyst material is a key factor in its
16 final cost and performance and should also take in account the type of substrate used for
17 deposition. Several methods have been reported in the literature for the production of
18 TiO₂ films for photocatalytic applications, including CVD [40,41], spray pyrolysis
19 [40,42], sol-gel [40,43], hydrothermal synthesis [40,44], and microwave-assisted
20 synthesis [12,40,45]. The latter synthesis route enables the use of flexible substrates, like
21 paper [11,19], and allows reproducibility while being an inexpensive, fast and simple
22 method.
23
24
25
26
27
28

29 The following study will describe the synthesis and further characterization of TiO₂
30 nanoparticles and nanostructured thin films grown on paper and produced simultaneously
31 by microwave-assisted hydrothermal technique. The main goal was the production of
32 stable, environmentally friendly, and cost-effective TiO₂ materials with improved
33 photocatalytic behaviour under solar radiation, and also achieving an enhanced
34 disposable photocatalytic paper.
35
36
37
38
39

40 **2. Experimental procedure**

41 *2.1. Materials*

42
43 Both TiO₂ nanoparticles and nanostructured thin films were synthesized
44 simultaneously using a microwave-assisted hydrothermal method. The materials were
45 produced at least 3 times to demonstrate the technique reproducibility. The TiO₂ synthesis
46 used deionized water, titanium (IV) isopropoxide (Ti[OCH(CH₃)₂]₄, TTIP, 97% from
47 Sigma Aldrich), and hydrochloric acid (HCl, 37% from Merck). For the microwave
48 synthesis, it has been mixed 57.5 mL of water on 2.5 mL of HCl under stirring during
49 5 min. 2 mL of TTIP was then added to the solution and stirred for 10 min prior to
50 synthesis. A CEM Focused Microwave Synthesis System (CEM Discover SP) was used
51 in this work. The microwave parameters were set at 75 min, 100 W, 110 °C and 200 Psi,
52 for synthesis time, power, temperature, and pressure, respectively. Quartz vessels of 35
53
54
55
56
57
58
59
60

1
2
3 mL were used, and a piece of the Whatman substrate was added for the TiO₂ film to grow.
4
5 Afterwards, 20 mL of the mixed solutions were transferred into it. The microwave
6
7 parameters selected have been previously employed in Refs. [11,19,46] when using paper
8
9 as substrate.

10 The substrate used was the Whatman chromatography paper grade 2 with sizes of 2
11
12 x 2.5 cm². The selection of this paper was due to the absence of impurities or additives
13
14 associated to its uniform hydrophilic properties [11,47]. There was no need of a seed layer
15
16 to assist TiO₂ growth [11].

17 18 2.2. Characterization Techniques

19 The X-Ray diffraction (XRD) measurements were achieved using a diffractometer
20
21 PANalytical's X'Pert PRO MPD equipped with a X'Celerator 1D detector and using
22
23 CuK α radiation. XRD diffractograms were recorded in the 20–75° 2 θ range with a step
24
25 size of 0.033°. The rutile, anatase, brookite simulated powder diffractograms were
26
27 obtained using PowderCell [48] and crystallographic data from reference [49].

28 Raman spectroscopy measurements were carried out using an inVia Qontor confocal
29
30 Raman microscope from Renishaw. It has been used a 17 mW He–Ne laser operating at
31
32 532 nm, with a 10 s exposure time and settings of 3 accumulations. The Raman spectra
33
34 were recorded in the range of 100–700 cm⁻¹.

35 Surface scanning electron microscopy (SEM) images were obtained with a Carl Zeiss
36
37 AURIGA CrossBeam SEM-FIB microscope equipped for energy dispersive X-Ray
38
39 spectroscopy (EDS) analyses. The nanoparticles and films' dimensions have been
40
41 estimated using SEM images and ImageJ software [50].

42 The optical bandgap was estimated through diffuse reflectance measurements carried
43
44 out at room temperature using a Perkin Elmer lambda 950 UV/VIS/NIR
45
46 spectrophotometer equipped with a diffuse reflectance module (integrating sphere with
47
48 150 mm diameter and internally coated with Spectralon). A standard reflector sample was
49
50 used calibration (reflectance, R = 1.00 from Spectralon disk). The reflectance (R)
51
52 measurements were carried out from 250 to 800 nm.
53
54
55
56
57
58
59
60

2.3. Photocatalysis experiments

The TiO₂ nanoparticles and nanostructured thin film had their photocatalytic behaviour assessed by the photodegradation of rhodamine B (RhB) from Sigma-Aldrich at room temperature. The samples were positioned at the bottom of a beaker with 50 mL of the RhB solution (20 mg/L) and left to stir for 30 min in the dark to establish absorption–desorption equilibrium. Absorbance measurements were taken every 10 min up to 70 min in the case of powder materials, and every 2 hours up to a total of 6 hours in the case of paper-based materials, using Shimadzu UV-3101PC UV-Vis-NIR Scanning Spectrophotometer. For powder materials, 4 mL of the rhodamine B solution with the photocatalyst was collected after light exposure and separated by centrifugation for 5 min at 6000 rpm. After absorbance measurements, the 4 mL solution was returned for further measurements. The reusability experiments consisted in recovering the powder and centrifuging it with further discard of the total liquid. The recovered slurry was dried at 50 °C for 3 h. The recovered dried powder was then poured into fresh solution and exposed to solar light for 70 min along several weeks [27]. The commercial Degussa P25 TiO₂ was tested in the same proportion as the produced powders (20 mg).

The irradiation was achieved by using a LED solar simulator LSH-7320 (AM 1.5 spectrum) with an intensity of 1 Sun, and the photocatalytic experiments considered the International Standard ISO 10678 [51].

3. Results and Discussion

TiO₂ nanoparticles and the nanostructured TiO₂ thin film were successfully synthesized under microwave irradiation using a cellulose-based substrate. i.e., Whatman paper. The produced nanostructures and thin film were systematically investigated and correlated to their final photocatalytic behaviour under solar radiation. All samples showed that the process is reproducible and reliable, where deviations observed on the set of the materials' characteristics analysed were below 4% and 10 % for the powder and thin films, respectively. The approach presented opens-up to the simultaneous production of photocatalytic powders and disposable photocatalytic paper activated under solar light.

3.1. Structural Characterization

Figure 1 (a) depicts the SEM images of TiO₂ nanoparticles. The microwave synthesis resulted in very fine particles, appearing as nanospheres. These nanoparticles appear in an agglomerate, since after drying the powder there is aggregation in larger particles in the micrometer range. The average sphere diameter calculated was 11 ± 0.5 nm. The powder produced was also analysed by X-Ray diffraction and the XRD diffractograms are presented in Figure 1 (b). Most peaks of the experimental diffractogram could be assigned to the anatase phase, nevertheless the presence of brookite could also be observed (as a minor second phase or impurity). It has not been detected peaks coming from impurities such as Ti(OH)₄ and the XRD results demonstrate that the materials are well crystallized and highly nanostructured. This mixture of phases was previously reported with small amounts of brookite in TiO₂ anatase nanocrystals when synthesized by hydrothermal synthesis [52]. The mean particle size calculated from Scherrer's equation was 5 nm [53]. In analogous studies, HCl played a central role in the determination of the final TiO₂ crystalline phase. Both studies reported the presence of a mixture of rutile and brookite when using higher amounts of acid [19,27]. When comparing with Ref. [19], where 5 mL of HCl has been used, it can be concluded that after a certain amount of acid, the formation of anatase phase is preferred. In the present work, 2.5 mL of HCl resulted in mostly anatase with residual presence of brookite.

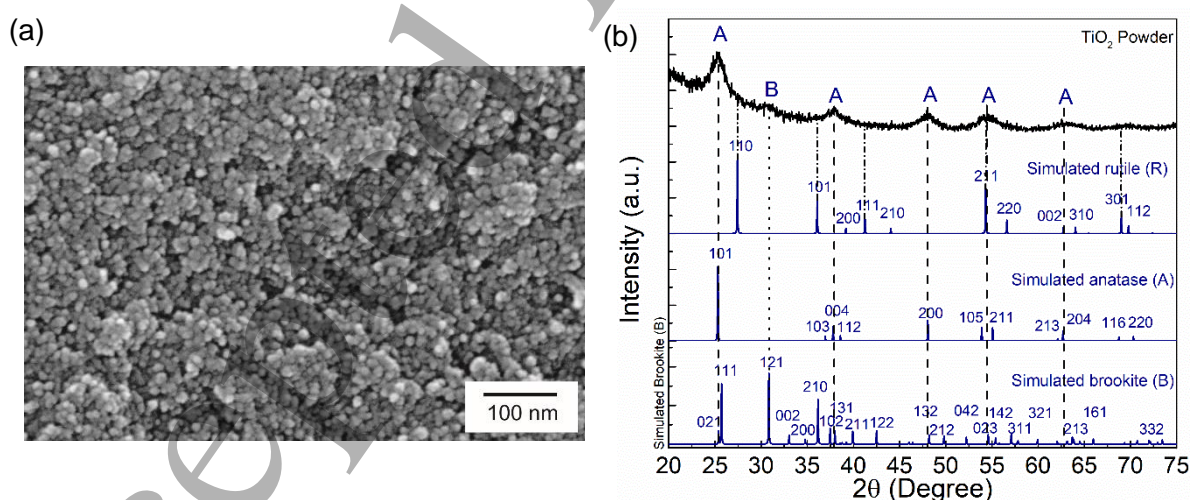


Figure 1 - SEM image of the TiO₂ nanoparticles (a) together with its XRD diffractogram (b), where the simulated rutile, brookite and anatase diffractograms are presented for comparison.

In Figures 2 (a) and (b) it is presented the SEM images of the TiO₂ nanostructured films grown on the Whatman paper substrate without any seed layer. The paper roughness promoted nucleation and fixation of the TiO₂ nanostructures without any additional process [11,19,46]. After microwave synthesis, the Whatman paper fibres remain unaltered, and when magnifying the observed area, it is clear the presence of nanostructures forming a continuous film. The nanoparticles resultant from the microwave synthesized powder were uniformly covering the paper substrate. The inset shows the cross section of the film, and it could be observed a compact film of agglomerated nanoparticles, with thickness around 130 nm. From EDS analysis, it can be observed the homogenous distribution of Ti within the substrate (Figure 2 (c)), together with the presence of C and O (Figures 2 (d) and (e)), where C is related to the use of a paper substrate. No impurities were detected.

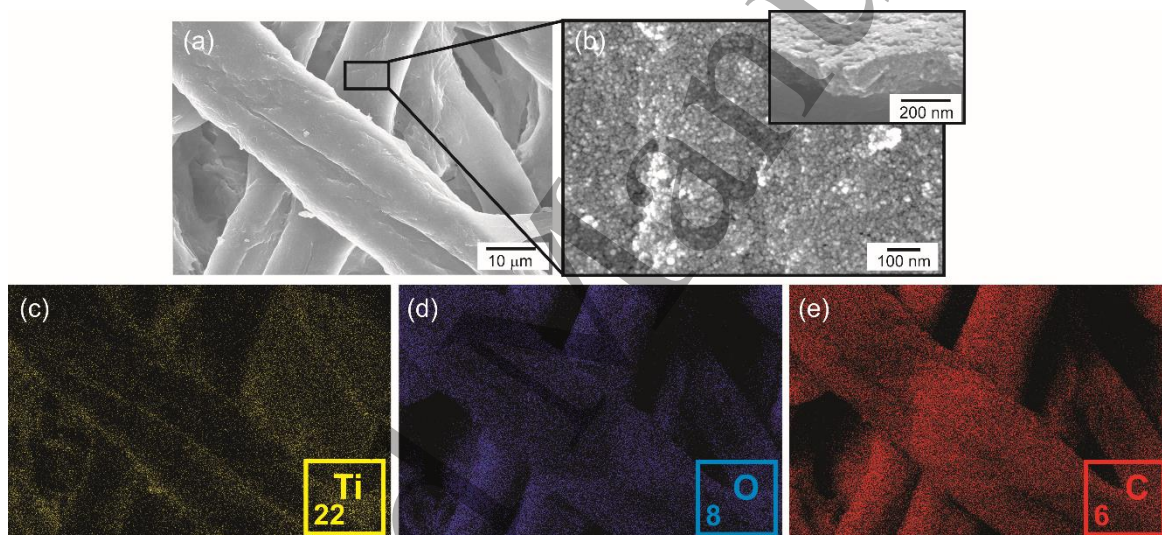


Figure 2 – SEM and EDS analysis on the TiO₂ nanostructured thin film grown on Whatman paper.

From previous studies, it has been concluded that paper hinders the TiO₂ signal on XRD measurements [11,19], and for that reason Raman spectroscopy has been employed. The Raman spectra of the TiO₂ nanoparticles and the thin film grown on Whatman paper are presented in Figure 3. The Raman spectrum of the pristine Whatman paper is also shown for comparison, and the minor bands marked with the star are associated to the substrate. The Raman spectra attested for the presence of the anatase and brookite phases (more evident in the powder Raman spectrum). The Raman bands associated to anatase were detected with a blue shift and can be assigned to 153 cm⁻¹ (*E_g*), 204 cm⁻¹ (*E_g*), 405 cm⁻¹ (*B_{1g}*), 512 cm⁻¹ (*B_{1g}* + *A_{1g}*), and 640 cm⁻¹ (*E_g*) for anatase [52,54–56] This Raman band shift can be related to the structural defects present in the TiO₂

lattice, oxygen vacancies [52–57] or minor deviations from the TiO₂ films' stoichiometry [58]. Some Raman bands associated to brookite have also been observed (246, 322 and 365 cm⁻¹ [59,60]). In fact, the Raman spectra of brookite phase display a characteristic intense band at 153 cm⁻¹, which can be similar and coincident with E_g mode of anatase at 144 cm⁻¹ [52]. However, being brookite a minor phase or impurity, it can be assumed that the 153 cm⁻¹ band comes from anatase phase. XRD measurements on powder confirmed the Raman spectroscopy results (Figure 1 (b)).

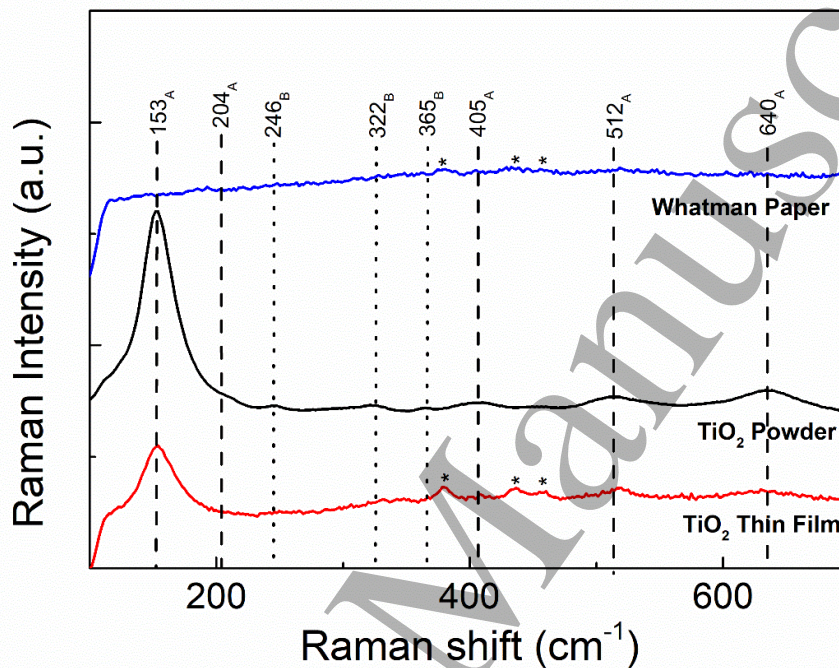


Figure 3 - Raman spectra of the pristine Whatman paper, TiO₂ nanoparticles and nanostructured thin film grown on paper. Dashed lines indicate the anatase bands and the dot ones indicate the brookite bands. The stars represent the contribution from Whatman paper.

3.2 Optical characterization

Both powder and thin film materials had their optical band gap assessed through reflectance data using the Tauc plot [61,62]. The direct band gap values estimated were 3.07 eV and 3.44 eV for the TiO₂ nanoparticles and nanostructured thin film, respectively (Figure 4). The estimated band gaps are within the reported values for the different TiO₂ phases [26,63,64]. Regarding the band gap determination, Reddy et. al. [65] reported both the direct and indirect band gap measurements, being the direct transition more favourable for anatase TiO₂ nanoparticles with sizes of 5-10 nm. Moreover, the disparity observed between the powder and the thin film materials is expected since the band gap depends

on several factors including defects [66], residual strain [67], degree of compactness and densification [68], among others.

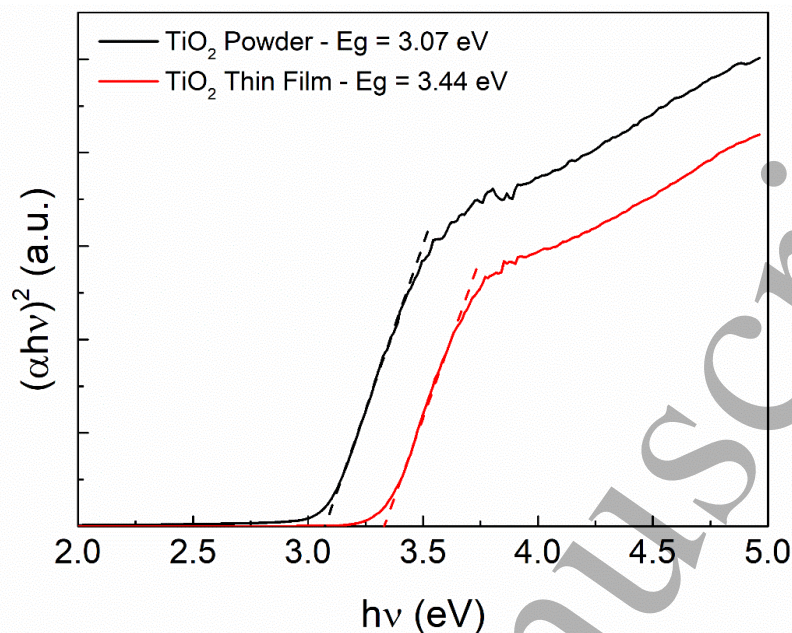


Figure 4 – Tauc plot ($(\alpha h\nu)^2$ variation versus photon energy $h\nu$) for the TiO₂ nanoparticles and nanostructured thin film grown on paper for the evaluation of the materials' optical band gap.

3.2. Photocatalytic Behaviour

Both TiO₂ nanoparticles (powder) and the nanostructured thin film grown on paper had their photocatalytic activity evaluated through the rhodamine B photodegradation under solar radiation. It can be seen the gradual RhB degradation for the powder material (Figure 5 (a)), reaching degradation values of 91 % after 40 min. From 50 min, the reaction has reached a stable degradation pattern, reaching 93 % at 70 min (last measurement) for the powder TiO₂. The degradation ratio (C/C_0) vs. exposure time is presented in Figure 5 (b) for the powder materials, where C is the concentration of the pollutant at each exposure time and C_0 is the initial solution concentration. When compared to the TiO₂ Degussa P25 catalyst, the synthesized powder revealed an enhanced photocatalytic activity under solar radiation (see Figure 5 (b)). Pure TiO₂ is photo-active under UV radiation, however in the present work, it can be observed an enhanced photocatalytic activity under solar radiation. This behaviour has been reported before and is associated to the presence of nano-sized TiO₂ [69]. Other factors also influence the photocatalytic activity and will be discussed in detail.

The photocatalytic activity relies on numerous factors including the band gap, crystallite size, degree of crystallinity, specific surface area, active facets, among others [12, 70, 71]. The band gap estimated for the TiO₂ nanoparticles are within what is

1
2
3 expected for the different TiO₂ phases. Regarding the crystallite size, and as observed in
4 Figure 1 (a) and calculated by XRD results, the microwave synthesis resulted in very fine
5 particles (~11 nm). It is known that due to quantum size effect, the nanosized particles
6 display enhanced redox ability. The migration of electrons and holes of smaller particles
7 to their surface is facilitated, and the electron-hole recombination is reduced which
8 increases the photocatalytic performance [72]. Thus, it is expected a substantial size
9 contribution to the enhanced photocatalytic activity observed. Moreover, in general the
10 specific surface area increases with the decrease of particle size [71], also contributing to
11 the behaviour observed.
12
13
14
15
16
17

18 In terms of crystalline phases, XRD, Raman, and SEM (Figures 1 and 3) showed
19 that the microwave synthesis produced TiO₂ nanoparticles with mostly anatase and
20 residual amounts of brookite (or impurities). Anatase is largely explored for
21 photocatalytic applications [72], however it has also been reported that a combination of
22 distinct TiO₂ phases will result in higher photocatalytic activity and efficiency than single
23 phases [72–74], reducing the recombination of photogenerated holes and electrons [75].
24 Moreover, the mixture of anatase-brookite nanomaterials has been reported to have higher
25 photocatalytic activity than just anatase or P25 [74,76,77]. Thus, some contribution to the
26 photocatalytic performance observed can be expected coming from the mixture of anatase
27 and brookite. Reusability tests were carried out for the TiO₂ powder, demonstrating
28 reusability characteristics over time (Figure 5 (c)). Nevertheless, as can be observed, there
29 is a clear deterioration with the number of photocatalytic experiments [78,79], which can
30 be related to the powder saturation with rhodamine B [79] or weight loss of the powder
31 during experiments [80]. The blank rhodamine B solution was not significantly
32 influenced under solar radiation, so all the degradation observed is due to the
33 photocatalytic effect of the catalyst in both Figures 5 and 6. Nevertheless, it is possible to
34 observe a slight increase in the RhB concentration during exposure to a max of 4 % of
35 the initial concentration. This phenomenon can be explained by the evaporation of some
36 of the solvent, which cannot be visible when the photocatalyst is present.
37
38
39
40
41
42
43
44
45
46
47
48
49
50

51 The photocatalytic activity of the TiO₂ nanostructured thin film was also studied
52 and is presented in Figure 6. The RhB degradation observed in Figure 6 (a) is
53 accompanied by a slight hypsochromic shift of absorption bands [81], however in Figure
54 6 (b), it is clear its gradual degradation under solar radiation up to 6 h.
55
56
57

58 When comparing the thin film with the powder material (Figures 5 and 6), it has
59 been observed that the nanoparticles had a more effective RhB degradation than the
60

1
2
3 nanostructured thin film. This is associated to the better adsorption activity of powders
4 and photocatalytic efficiency when compared to films as a result of the larger surface area
5 and higher amount of material available for reaction [82]. Nevertheless, the
6 nanostructured thin film has reached a degradation value of 68 % after 360 min (6 h). As
7 explained for the powder materials, a size effect contribution to the photocatalytic activity
8 can be thought for the film as well. As observed in Figure 2, the film is composed by fine
9 nanoparticles agglomerated to form a compact thin film. Several studies described the
10 higher photocatalytic activity of films composed by nanoparticles [83–85], thus as in
11 powder material, it is expected a significant contribution to the observed photocatalytic
12 efficiency coming from the nanosized particles present. Moreover, as can be seen in
13 Figure 6 (a), the 3D structure of paper contribute to the photocatalytic activity observed
14 [46], associated to partial solution absorption by the Whatman paper which can be observed
15 by the pinkish coloration on it after degradation (see inset in Figure 6 (a)). The contribution
16 coming from Whatman paper absorption is expected to be ~27 % of the total RhB
17 degradation, thus the RhB photodegradation value of 68 % is the joint contribution of
18 Whatman paper and the TiO₂ nanostructured thin film.
19
20
21
22
23
24
25
26
27
28
29
30

31 Regarding the phase's contribution, both nanoparticles and nanostructured thin
32 film must have the same crystalline phases, even if it could not be seen clearly in Figure
33 3 due to the cellulose signal contribution, hindering some TiO₂ bands. Thus, mixture of
34 TiO₂ phases must have contributed to the enhanced photocatalytic performance just as
35 observed for the powder material. The photocatalytic performance obtained by the
36 nanostructured thin film is largely superior when compared to an analogous studies [11],
37 mostly due to the structural differences observed. Thus, it can be stated that the
38 microwave synthesis parameters selected, and acid amount demonstrated to be of great
39 importance to the final photocatalytic activity of the materials produced.
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

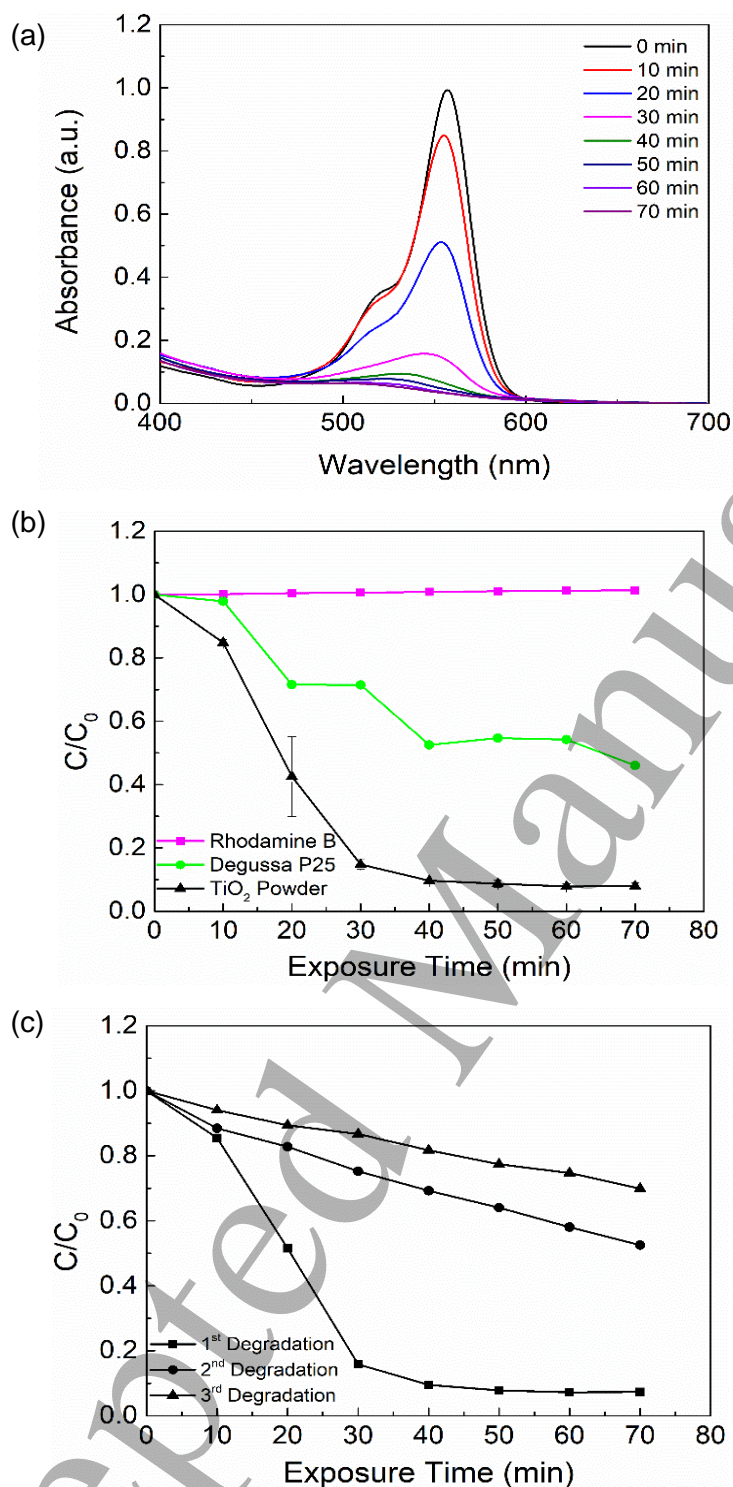


Figure 5 - Rhodamine B absorbance spectra of the TiO₂ nanoparticles at different solar light exposure times up to 70 min (a). Rhodamine B degradation ratio (C/C_0) vs. solar radiation exposure time, where the blank rhodamine B is also presented (b). Degussa P25 was subjected to the same experiments and is shown for comparison. Three different degradation measurements were carried out for the TiO₂ powder material in (b). Several solar radiation exposure experiments were carried out to attest the reusability of the material (c).

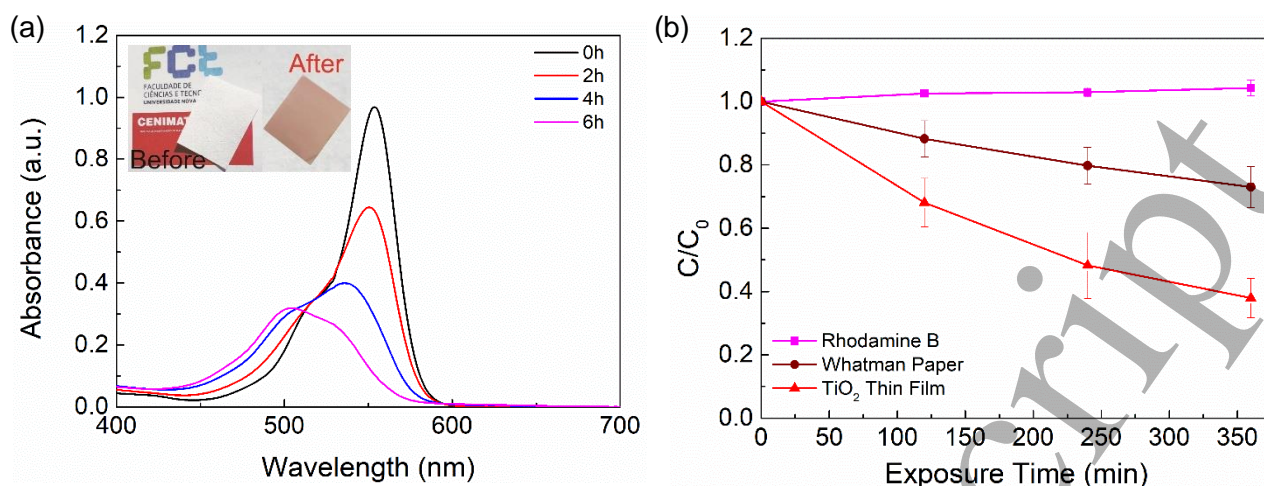


Figure 6 - Rhodamine B absorbance spectra of the TiO₂ nanostructured thin film at different solar light exposure times up to 360 min. Inset shows the photograph of the paper after synthesis and after photocatalysis (a). Rhodamine B degradation ratio (C/C_0) vs. solar radiation exposure time (b). Three different degradation measurements were carried out for each material.

The materials were designed to be a reliable alternative for the commercial photocatalysts used nowadays, and to produce fully disposable materials, that can effectively contribute to the environmental protection, while diminishing production costs. The photocatalytic paper developed in the present study can easily be employed as filters or several other applications, as it easily adapts to different surfaces due to its highly flexibility, despite its green character.

4. Conclusions

TiO₂ nanoparticles and nanostructured thin films were simultaneously produced using a hydrothermal method assisted by microwave irradiation. Whatman paper has been selected as substrate for the thin film due to its lack of impurities. All materials were composed by a mixture of anatase and brookite polymorphs, with brookite appearing as a minor phase or impurity. It has been observed very fine particles appearing as spheres, that were also observed in the thin film. The nanostructured thin film revealed to be a compact film of agglomerated nanoparticles. Photocatalytic activity was evaluated with the rhodamine B degradation, with the nanoparticles showing the highest photocatalytic activity under solar radiation (91 % after 40 min) and revealing reusability characteristics over time. The nanoparticles revealed to have around 12 times higher photocatalytic activity when compared to the commercial Degussa P25 photocatalyst. The nanostructured thin film demonstrated also enhanced photocatalytic performance reaching 68 % of RhB degradation after 6 h of solar radiation exposure. The present study

1
2
3 showed that this approach is a real and appealing option for the commercial photocatalysts
4 and capable of producing disposable and inexpensive photocatalytic materials in flexible
5 and green substrates.
6
7

8 9 **Acknowledgments**

10
11 This work is funded by National Funds through the FCT - Fundação para a Ciência
12 e a Tecnologia, I.P., under the scope of the project UIDB/50025/2020-2023. The authors
13 acknowledge Fundação para a Ciência e a Tecnologia for funding the Project ICARUS
14 under the reference PTDC/EAM-AMB/30989/2017. The work was also partially funded
15 by the Nanomark collaborative project between INCM (Imprensa Nacional - Casa da
16 Moeda) and CENIMAT/i3N. A.C.M. acknowledges funding to the National Foundation
17 for Science and Technology, I.P., through the PhD Grants SFRH/BD/115173/2016.
18 Thanks are also due to EC project SYNERGY H2020-WIDESPREAD-2020-5, CSA,
19 proposal n° 952169. The authors also acknowledge funding from the European Research
20 Council through the Starting Grant TREND, grant 716510 and from the European
21 Community's H2020 program under grant agreement No. 787410 (ERC-2018-AdG
22 DIGISMART).
23
24
25
26
27
28
29
30
31
32

33 34 **Additional Information**

35
36 **Competing financial interests:** The authors declare no competing financial interests.
37
38

39 40 **References**

- 41 [1] N. Geographic, Freshwater Crisis - A Clean Water Crisis, (n.d).
42 <https://www.nationalgeographic.com/environment/freshwater/freshwater-crisis/>
43 (accessed September 3, 2020).
44
45 [2] W.H. Organization, Drinking-Water, (2019). [http://www.who.int/es/news-room/fact-](http://www.who.int/es/news-room/fact-sheets/detail/drinking-water)
46 [sheets/detail/drinking-water](http://www.who.int/es/news-room/fact-sheets/detail/drinking-water) (accessed September 3, 2020).
47
48 [3] Our World in Data, M. Roser, H. Ritchie, Clean Water, (2019).
49 <https://ourworldindata.org/water-access> (accessed September 3, 2020).
50
51 [4] USGS, Wastewater Treatment Water Use, (n.d.). [https://www.usgs.gov/special-](https://www.usgs.gov/special-topic/water-science-school/science/wastewater-treatment-water-use?qt-science_center_objects=0#qt-science_center_objects)
52 [topic/water-science-school/science/wastewater-treatment-water-use?qt-](https://www.usgs.gov/special-topic/water-science-school/science/wastewater-treatment-water-use?qt-science_center_objects=0#qt-science_center_objects)
53 [science_center_objects=0#qt-science_center_objects](https://www.usgs.gov/special-topic/water-science-school/science/wastewater-treatment-water-use?qt-science_center_objects=0#qt-science_center_objects) (accessed September 3, 2020).
54
55 [5] R.W. Kates, T.M. Parris, A.A. Leiserowitz, What Is Sustainable Development? Goals,
56 Indicators, Values, and Practice, *Environment Sci. Policy Sustain. Dev.* (2016) 1–13.
57 <http://www.environmentmagazine.org/Editorials/Kates-apr05-full.html>.
58
59 [6] J. Sarkis, Manufacturing's role in corporate environmental sustainability, (2005) 666–686.
60
[7] C. O'Brien, Sustainable production - a new paradigm for a new millennium, *Int. J. Prod.*

- Econ. 60 (1999) 1–7. [https://doi.org/10.1016/S0925-5273\(98\)00126-1](https://doi.org/10.1016/S0925-5273(98)00126-1).
- [8] D. Griggs, M. Stafford-Smith, O. Gaffney, J. Rockström, M.C. Öhman, P. Shyamsundar, W. Steffen, G. Glaser, N. Kanie, I. Noble, Sustainable development goals for people and planet, *Nature*. 495 (2013) 305–307. <https://doi.org/10.1038/495305a>.
- [9] U. Nations, Goal 6: Ensure access to water and sanitation for all, (n.d.). <https://www.un.org/sustainabledevelopment/water-and-sanitation/> (accessed September 3, 2020).
- [10] R.K. Zinke, W.H. Werkheiser, Critical mineral resources of the United States—Economic and environmental geology and prospects for future supply: U.S. Geological Survey Professional Paper 1802, *Encycl. Toxicol. Third Ed.* (2014) 797.
- [11] M.L. Matias, D. Nunes, A. Pimentel, S.H. Ferreira, R. Borda D’Agua, M.P. Duarte, E. Fortunato, R. Martins, Paper-based nanoplatfoms for multifunctional applications, *J. Nanomater.* 2019 (2019). <https://doi.org/10.1155/2019/6501923>.
- [12] D. Nunes, A. Pimentel, J. V. Pinto, T.R. Calmeiro, S. Nandy, P. Barquinha, L. Pereira, P.A. Carvalho, E. Fortunato, R. Martins, Photocatalytic behavior of TiO₂ films synthesized by microwave irradiation, *Catal. Today*. 278 (2016) 262–270. <https://doi.org/10.1016/j.cattod.2015.10.038>.
- [13] J. You, Y. Guo, R. Guo, X. Liu, A review of visible light-active photocatalysts for water disinfection: Features and prospects, *Chem. Eng. J.* 373 (2019) 624–641. <https://doi.org/10.1016/j.cej.2019.05.071>.
- [14] A.J. Haider, Z.N. Jameel, I.H.M. Al-Hussaini, Review on: Titanium dioxide applications, *Energy Procedia*. 157 (2019) 17–29. <https://doi.org/10.1016/j.egypro.2018.11.159>.
- [15] A. Aboulouard, B. Gultekin, M. Can, M. Erol, A. Jouaiti, B. Elhadadi, C. Zafer, S. Demic, Dye sensitized solar cells based on titanium dioxide nanoparticles synthesized by flame spray pyrolysis and hydrothermal sol-gel methods: A comparative study on photovoltaic performances, *J. Mater. Res. Technol.* 9 (2020) 1569–1577. <https://doi.org/10.1016/j.jmrt.2019.11.083>.
- [16] F.-Q. Bai, W. Li, H.-X. Zhang, Theoretical Studies of Titanium Dioxide for Dye-Sensitized Solar Cell and Photocatalytic Reaction, in: M. Janus (Ed.), *Titan. Dioxide, InTech*, 2017. <https://doi.org/10.5772/intechopen.68745>.
- [17] M.I. Dar, A.K. Chandiran, M. Grätzel, M.K. Nazeeruddin, S.A. Shivashankar, Controlled synthesis of TiO₂ nanoparticles and nanospheres using a microwave assisted approach for their application in dye-sensitized solar cells, *J. Mater. Chem. A*. 2 (2014) 1662–1667. <https://doi.org/10.1039/c3ta14130f>.
- [18] M.A.K.L. Diasanayake, G.K.R. Senadeera, H.N.M. Sarangika, P.M.P.C. Ekanayake, C.A. Thotawattage, H.K.D.W.M.N.R. Divarathne, J.M.K.W. Kumari, TiO₂ as a Low Cost, Multi Functional Material, *Mater. Today Proc.* 3 (2016) S40–S47. <https://doi.org/10.1016/j.matpr.2016.01.006>.
- [19] D. Nunes, T. Freire, A. Barranger, J. Vieira, M. Matias, S. Pereira, A. Pimentel, N.J.A. Cordeiro, E. Fortunato, R. Martins, TiO₂ nanostructured films for electrochromic paper based-devices, *Appl. Sci.* 10 (2020). <https://doi.org/10.3390/app10041200>.
- [20] N.N. Dinh, N.T.T. Oanh, P.D. Long, M.C. Bernard, A.H. Le Goff, Electrochromic properties of TiO₂ anatase thin films prepared by a dipping sol-gel method, *Thin Solid Films*. 423 (2003) 70–76. [https://doi.org/10.1016/S0040-6090\(02\)00948-3](https://doi.org/10.1016/S0040-6090(02)00948-3).
- [21] A. Di Paola, M. Bellardita, L. Palmisano, Brookite, the least known TiO₂ photocatalyst, 2013. <https://doi.org/10.3390/catal3010036>.

- 1
2
3 [22] C. López de Dicastillo, M. Guerrero Correa, F. B. Martínez, C. Streitt, M. José Galotto, Antimicrobial Effect of Titanium Dioxide Nanoparticles, in: *Antimicrob. Resist.* [Working Title], IntechOpen, 2020: p. 13. <https://doi.org/10.5772/intechopen.90891>.
- 4
5
6
7 [23] L. Armelao, D. Barreca, G. Bottaro, A. Gasparotto, C. Maccato, C. Maragno, E. Tondello, U.L. Štangar, M. Bergant, D. Mahne, Photocatalytic and antibacterial activity of TiO₂ and Au/TiO₂ nanosystems, *Nanotechnology*. 18 (2007). <https://doi.org/10.1088/0957-4484/18/37/375709>.
- 8
9
10
11
12 [24] U. Joost, K. Juganson, M. Visnapuu, M. Mortimer, A. Kahru, E. Nõmmiste, U. Joost, V. Kisand, A. Ivask, Photocatalytic antibacterial activity of nano-TiO₂ (anatase)-based thin films: Effects on *Escherichia coli* cells and fatty acids, *J. Photochem. Photobiol. B Biol.* 142 (2015) 178–185. <https://doi.org/10.1016/j.jphotobiol.2014.12.010>.
- 13
14
15
16 [25] Q. Guo, C. Zhou, Z. Ma, X. Yang, Fundamentals of TiO₂ Photocatalysis: Concepts, Mechanisms, and Challenges, *Adv. Mater.* 31 (2019) 1–26. <https://doi.org/10.1002/adma.201901997>.
- 17
18
19
20 [26] D. Reyes-Coronado, G. Rodríguez-Gattorno, M.E. Espinosa-Pesqueira, C. Cab, R. De Coss, G. Oskam, Phase-pure TiO₂ nanoparticles: Anatase, brookite and rutile, *Nanotechnology*. 19 (2008). <https://doi.org/10.1088/0957-4484/19/14/145605>.
- 21
22
23
24 [27] D. Nunes, A. Pimentel, L. Santos, P. Barquinha, E. Fortunato, R. Martins, Photocatalytic TiO₂ nanorod spheres and arrays compatible with flexible applications, *Catalysts*. 7 (2017). <https://doi.org/10.3390/catal7020060>.
- 25
26
27
28 [28] T. Luttrell, S. Halpegamage, J. Tao, A. Kramer, E. Sutter, M. Batzill, Why is anatase a better photocatalyst than rutile? - Model studies on epitaxial TiO₂ films, *Sci. Rep.* 4 (2015). <https://doi.org/10.1038/srep04043>.
- 29
30
31
32 [29] M. Andersson, L. Österlund, S. Ljungström, A. Palmqvist, Preparation of nanosize anatase and rutile TiO₂ by hydrothermal treatment of microemulsions and their activity for photocatalytic wet oxidation of phenol, *J. Phys. Chem. B*. 106 (2002) 10674–10679. <https://doi.org/10.1021/jp025715y>.
- 33
34
35
36 [30] S.I. Tetsuro Kawahara, Yasuhiro Konishi, Hiroaki Tada, Noboru Tohge, Junji Nishii, A Patterned TiO₂ (Anatase)/TiO₂ (Rutile) Bilayer-Type Junction on the Photocatalytic Activity, *Angew. Chemie*. 41 (2002) 2811–2813.
- 37
38
39
40 [31] R. Ameta, M.S. Solanki, S. Benjamin, S.C. Ameta, Photocatalysis, in: *Adv. Oxid. Process. Waste Water Treat.*, Elsevier, 2018: pp. 135–175. <https://doi.org/10.1016/B978-0-12-810499-6.00006-1>.
- 41
42
43
44 [32] Y. Lan, Y. Lu, Z. Ren, Mini review on photocatalysis of titanium dioxide nanoparticles and their solar applications, *Nano Energy*. 2 (2013) 1031–1045. <https://doi.org/10.1016/j.nanoen.2013.04.002>.
- 45
46
47
48 [33] K. Kalyanasundaram, Photochemical applications of solar energy: Photocatalysis and photodecomposition of water, 2013. <https://doi.org/10.1039/9781849737722-00182>.
- 49
50
51
52 [34] A. Fujishima, X. Zhang, Titanium dioxide photocatalysis: present situation and future approaches, *Comptes Rendus Chim.* 9 (2006) 750–760. <https://doi.org/10.1016/j.crci.2005.02.055>.
- 53
54
55
56 [35] J. Schneider, M. Matsuoka, M. Takeuchi, J. Zhang, Y. Horiuchi, M. Anpo, D.W. Bahnemann, Understanding TiO₂ photocatalysis: Mechanisms and materials, *Chem. Rev.* 114 (2014) 9919–9986. <https://doi.org/10.1021/cr5001892>.
- 57
58
59 [36] K. Nakata, A. Fujishima, TiO₂ photocatalysis: Design and applications, *J. Photochem. Photobiol. C Photochem. Rev.* 13 (2012) 169–189.
- 60

- <https://doi.org/10.1016/j.jphotochemrev.2012.06.001>.
- [37] M.N. Subramaniam, P.S. Goh, W.J. Lau, B.C. Ng, A.F. Ismail, Development of nanomaterial-based photocatalytic membrane for organic pollutants removal, Elsevier Inc., 2018. <https://doi.org/10.1016/B978-0-12-814503-6.00003-3>.
- [38] F. Fresno, R. Portela, S. Suárez, J.M. Coronado, Photocatalytic materials: recent achievements and near future trends, *J. Mater. Chem. A*. 2 (2014) 2863–2884. <https://doi.org/10.1039/C3TA13793G>.
- [39] J.J. Rueda-Marquez, I. Levchuk, P. Fernández Ibañez, M. Sillanpää, A critical review on application of photocatalysis for toxicity reduction of real wastewaters, *J. Clean. Prod.* 258 (2020). <https://doi.org/10.1016/j.jclepro.2020.120694>.
- [40] P. Nyamukamba, O. Okoh, H. Mungondori, R. Taziwa, S. Zinya, Synthetic Methods for Titanium Dioxide Nanoparticles: A Review, in: *Titanium Dioxide - Mater. a Sustain. Environ.*, InTech, 2018. <https://doi.org/10.5772/intechopen.75425>.
- [41] S. Seifried, M. Winterer, H. Hahn, Nanocrystalline titania films and particles by chemical vapor synthesis, *Chem. Vap. Depos.* 6 (2000) 239–244. [https://doi.org/10.1002/1521-3862\(200010\)6:5<239::AID-CVDE239>3.0.CO;2-Q](https://doi.org/10.1002/1521-3862(200010)6:5<239::AID-CVDE239>3.0.CO;2-Q).
- [42] R. Taziwa, E. Meyer, Fabrication of TiO₂ Nanoparticles and Thin Films by Ultrasonic Spray Pyrolysis: Design and Optimization, *Pyrolysis*. (2017). <https://doi.org/10.5772/67866>.
- [43] A. Haider, Z.N. Jameel, Synthesis and Characterization of TiO₂ Nanoparticles via Sol-Gel Method by Pulse Laser Ablation Synthesis and Characterization of TiO₂ Nanoparticles via Sol-Gel Method by Pulse Laser Ablation *تلار لابل ج - لوصلا لتقير طب تيونانلا* 33 (3-4) 2015(موبناتيتلا ديسكوا ي نانت ت, 33
- [44] N. Liu, X. Chen, J. Zhang, J.W. Schwank, A review on TiO₂-based nanotubes synthesized via hydrothermal method: Formation mechanism, structure modification, and photocatalytic applications, *Catal. Today*. 225 (2014) 34–51. <https://doi.org/10.1016/j.cattod.2013.10.090>.
- [45] P. Periyat, N. Leyland, D.E. McCormack, J. Colreavy, D. Corr, S.C. Pillai, Rapid microwave synthesis of mesoporous TiO₂ for electrochromic displays, *J. Mater. Chem.* 20 (2010) 3650–3655. <https://doi.org/10.1039/b924341k>.
- [46] D. Nunes, A. Pimentel, A. Araujo, T.R. Calmeiro, S. Panigrahi, J. V. Pinto, P. Barquinha, M. Gama, E. Fortunato, R. Martins, Enhanced UV Flexible Photodetectors and Photocatalysts Based on TiO₂ Nanoplatfoms, *Top. Catal.* 61 (2018) 1591–1606. <https://doi.org/10.1007/s11244-018-0968-4>.
- [47] T.H. Joubert, P.H. Bezuidenhout, H. Chen, S. Smith, K.J. Land, Inkjet-printed Silver Tracks on Different Paper Substrates, *Mater. Today Proc.* 2 (2015) 3891–3900. <https://doi.org/10.1016/j.matpr.2015.08.018>.
- [48] W. Kraus, G. Nolze, POWDER CELL - A program for the representation and manipulation of crystal structures and calculation of the resulting X-ray powder patterns, *J. Appl. Crystallogr.* 29 (1996) 301–303. <https://doi.org/10.1107/S0021889895014920>.
- [49] P. Villars, L.D. Calvert, *Pearson's Handbook of Crystallographic Data for Intermetallic Phases.*, (1986).
- [50] C.A. Schneider, W.S. Rasband, K.W. Eliceiri, NIH Image to ImageJ: 25 years of image analysis, *Nat. Methods*. 9 (2012) 671–675. <https://doi.org/10.1038/nmeth.2089>.
- [51] I. Standard, Iso 10678:2010(E), *Int. Stand.* 2010 (2010) 1–18.

- 1
2
3 [52] M.C. Ceballos-Chuc, C.M. Ramos-Castillo, J.J. Alvarado-Gil, G. Oskam, G. Rodríguez-
4 Gattorno, Influence of brookite impurities on the raman spectrum of TiO₂ anatase
5 nanocrystals, *J. Phys. Chem. C.* 122 (2018) 19921–19930.
6 <https://doi.org/10.1021/acs.jpcc.8b04987>.
7
- 8 [53] B.D. Cullity, *Elements of X-Ray Diffraction*, 1978.
- 9
10 [54] L. Stagi, C.M. Carbonaro, R. Corpino, D. Chiriu, P.C. Ricci, Light induced TiO₂ phase
11 transformation: Correlation with luminescent surface defects, *Phys. Status Solidi Basic*
12 *Res.* 252 (2015) 124–129. <https://doi.org/10.1002/pssb.201400080>.
13
- 14 [55] Q. Zhang, L. Ma, M. Shao, J. Huang, M. Ding, X. Deng, X. Wei, X. Xu, Anodic oxidation
15 synthesis of one-dimensional TiO₂ nanostructures for photocatalytic and field emission
16 properties, *J. Nanomater.* 2014 (2014). <https://doi.org/10.1155/2014/831752>.
17
- 18 [56] G.C. Vásquez, M.A. Peche-Herrero, D. Maestre, B. Alemán, J. Ramírez-Castellanos, A.
19 Cremades, J.M. González-Calbet, J. Piqueras, Influence of Fe and Al doping on the
20 stabilization of the anatase phase in TiO₂ nanoparticles, *J. Mater. Chem. C.* 2 (2014)
21 10377–10385. <https://doi.org/10.1039/c4tc02099e>.
22
- 23 [57] E.L. Castellanos-Leal, P. Acevedo-Peña, V.R. Güiza-Argüello, E.M. Córdoba-Tuta, N and
24 F codoped TiO₂ thin films on stainless steel for photoelectrocatalytic removal of cyanide
25 ions in aqueous solutions, *Mater. Res.* 20 (2017) 487–495. [https://doi.org/10.1590/1980-](https://doi.org/10.1590/1980-5373-MR-2016-0214)
26 [5373-MR-2016-0214](https://doi.org/10.1590/1980-5373-MR-2016-0214).
27
- 28 [58] S. Nezar, N. Saoula, S. Sali, M. Faiz, M. Mekki, N.A. Laoufi, N. Tabet, Properties of TiO
29 2 thin films deposited by rf reactive magnetron sputtering on biased substrates, *Appl. Surf.*
30 *Sci.* 395 (2017) 172–179. <https://doi.org/10.1016/j.apsusc.2016.08.125>.
31
- 32 [59] Y. Wang, L. Li, X. Huang, Q. Li, G. Li, New insights into fluorinated TiO₂ (brookite,
33 anatase and rutile) nanoparticles as efficient photocatalytic redox catalysts, *RSC Adv.* 5
34 (2015) 34302–34313. <https://doi.org/10.1039/c4ra17076h>.
35
- 36 [60] Y. Hu, H.L. Tsai, C.L. Huang, Effect of brookite phase on the anatase-rutile transition in
37 titania nanoparticles, *J. Eur. Ceram. Soc.* 23 (2003) 691–696.
38 [https://doi.org/10.1016/S0955-2219\(02\)00194-2](https://doi.org/10.1016/S0955-2219(02)00194-2).
39
- 40 [61] Y. Du, M.S. Zhang, J. Wu, L. Kang, S. Yang, P. Wu, Z. Yin, Optical properties of SrTiO₃
41 thin films by pulsed laser deposition, *Appl. Phys. A Mater. Sci. Process.* 76 (2003) 1105–
42 1108. <https://doi.org/10.1007/s00339-002-1998-z>.
43
- 44 [62] C. Aydın, M. Benhaliliba, A.A. Al-Ghamdi, Z.H. Gafer, F. El-Tantawy, F. Yakuphanoglu,
45 Determination of optical band gap of ZnO:ZnAl₂O₄ composite semiconductor
46 nanopowder materials by optical reflectance method, *J. Electroceramics.* 31 (2013) 265–
47 270. <https://doi.org/10.1007/s10832-013-9829-5>.
48
- 49 [63] J.G. Yu, H.G. Yu, B. Cheng, X.J. Zhao, J.C. Yu, W.K. Ho, The Effect of Calcination
50 Temperature on the Surface Microstructure and Photocatalytic Activity of TiO₂ Thin
51 Films Prepared by Liquid Phase Deposition, *J. Phys. Chem. B.* 107 (2003) 13871–13879.
52 <https://doi.org/10.1021/jp036158y>.
53
- 54 [64] J.M. Wu, H.C. Shih, W.T. Wu, Formation and photoluminescence of single-crystalline
55 rutile TiO₂ nanowires synthesized by thermal evaporation, *Nanotechnology.* 17 (2006)
56 105–109. <https://doi.org/10.1088/0957-4484/17/1/017>.
57
- 58 [65] K.M. Reddy, S. V. Manorama, A.R. Reddy, Bandgap studies on anatase titanium dioxide
59 nanoparticles, *Mater. Chem. Phys.* 78 (2003) 239–245. [https://doi.org/10.1016/S0254-](https://doi.org/10.1016/S0254-0584(02)00343-7)
60 [0584\(02\)00343-7](https://doi.org/10.1016/S0254-0584(02)00343-7).
61
- 62 [66] A. Pimentel, S.H. Ferreira, D. Nunes, T. Calmeiro, R. Martins, E. Fortunato, Microwave

- synthesized ZnO nanorod arrays for UV sensors: A seed layer annealing temperature study, *Materials (Basel)*. 9 (2016). <https://doi.org/10.3390/ma9040299>.
- [67] J.P. Enríquez, X. Mathew, Influence of the thickness on structural, optical and electrical properties of chemical bath deposited CdS thin films, *Sol. Energy Mater. Sol. Cells*. 76 (2003) 313–322. [https://doi.org/10.1016/S0927-0248\(02\)00283-0](https://doi.org/10.1016/S0927-0248(02)00283-0).
- [68] L. Pereira, P. Barquinha, E. Fortunato, R. Martins, D. Kang, C.J. Kim, H. Lim, I. Song, Y. Park, High k dielectrics for low temperature electronics, *Thin Solid Films*. 516 (2008) 1544–1548. <https://doi.org/10.1016/j.tsf.2007.03.088>.
- [69] J. Moma, J. Baloyi, Modified Titanium Dioxide for Photocatalytic Applications, *Photocatal. - Appl. Attrib.* (2019). <https://doi.org/10.5772/intechopen.79374>.
- [70] Y. Guo, H. Li, J. Chen, X. Wu, L. Zhou, TiO₂ mesocrystals built of nanocrystals with exposed {001} facets: Facile synthesis and superior photocatalytic ability, *J. Mater. Chem. A*. 2 (2014) 19589–19593. <https://doi.org/10.1039/c4ta05068a>.
- [71] J. He, Y. Du, Y. Bai, J. An, X. Cai, Y. Chen, P. Wang, Nanocomposites with Enhanced Photocatalytic Activity, *Molecules*. 24 (2019) 1–14.
- [72] W. Fu, G. Li, Y. Wang, S. Zeng, Z. Yan, J. Wang, S. Xin, L. Zhang, S. Wu, Z. Zhang, Facile formation of mesoporous structured mixed-phase (anatase/rutile) TiO₂ with enhanced visible light photocatalytic activity, *Chem. Commun.* 54 (2017) 58–61. <https://doi.org/10.1039/c7cc05750d>.
- [73] H. Wang, X. Gao, G. Duan, X. Yang, X. Liu, Facile preparation of anatase-brookite-rutile mixed-phase N-doped TiO₂ with high visible-light photocatalytic activity, *J. Environ. Chem. Eng.* 3 (2015) 603–608. <https://doi.org/10.1016/j.jece.2015.02.006>.
- [74] A. Di Paola, M. Bellardita, R. Ceccato, L. Palmisano, F. Parrino, Highly active photocatalytic TiO₂ powders obtained by thermohydrolysis of TiCl₄ in water, *J. Phys. Chem. C*. 113 (2009) 15166–15174. <https://doi.org/10.1021/jp904673e>.
- [75] B.K. Mutuma, G.N. Shao, W.D. Kim, H.T. Kim, Sol-gel synthesis of mesoporous anatase-brookite and anatase-brookite-rutile TiO₂ nanoparticles and their photocatalytic properties, *J. Colloid Interface Sci.* 442 (2015) 1–7. <https://doi.org/10.1016/j.jcis.2014.11.060>.
- [76] J.C. Yu, J. Yu, W. Ho, L. Zhang, Preparation of highly photocatalytic active nano-sized TiO₂ particles via ultrasonic irradiation, *Chem. Commun.* 1 (2001) 1942–1943. <https://doi.org/10.1039/b105471f>.
- [77] J.C. Yu, L. Zhang, J. Yu, Direct sonochemical preparation and characterization of highly active mesoporous TiO₂ with a bicrystalline framework, *Chem. Mater.* 14 (2002) 4647–4653. <https://doi.org/10.1021/cm0203924>.
- [78] R. Wang, X. Cai, F. Shen, Preparation of TiO₂ hollow microspheres by a novel vesicle template method and their enhanced photocatalytic properties, *Ceram. Int.* 39 (2013) 9465–9470. <https://doi.org/10.1016/j.ceramint.2013.05.064>.
- [79] K. Nagaveni, G. Sivalingam, M.S. Hegde, G. Madras, Solar photocatalytic degradation of dyes: High activity of combustion synthesized nano TiO₂, *Appl. Catal. B Environ.* 48 (2004) 83–93. <https://doi.org/10.1016/j.apcatb.2003.09.013>.
- [80] L. Chen, S. Yang, E. Mäder, P.C. Ma, Controlled synthesis of hierarchical TiO₂ nanoparticles on glass fibres and their photocatalytic performance, *Dalt. Trans.* 43 (2014) 12743–12753. <https://doi.org/10.1039/c4dt00977k>.
- [81] F. Chen, J. Zhao, H. Hidaka, Highly selective deethylation of Rhodamine B: Adsorption

- 1
2
3 and photooxidation pathways of the dye on the TiO₂/SiO₂ composite photocatalyst, *Int.*
4 *J. Photoenergy.* 5 (2003) 209–217. <https://doi.org/10.1155/S1110662X03000345>.
5
6 [82] Y.H. Chen, K.J. Tu, Thickness dependent on photocatalytic activity of hematite thin films,
7 *Int. J. Photoenergy.* 2012 (2012). <https://doi.org/10.1155/2012/980595>.
8
9 [83] J. Huang, Y. He, L. Wang, Y. Huang, B. Jiang, Bifunctional Au@TiO₂ core-shell
10 nanoparticle films for clean water generation by photocatalysis and solar evaporation,
11 *Energy Convers. Manag.* 132 (2017) 452–459.
12 <https://doi.org/10.1016/j.enconman.2016.11.053>.
13
14 [84] J. Liqiang, S. Xiaojun, C. Weimin, X. Zili, D. Yaoguo, F. Honggang, The preparation and
15 characterization of nanoparticle TiO₂/Ti films and their photocatalytic activity, *J. Phys.*
16 *Chem. Solids.* 64 (2003) 615–623. [https://doi.org/10.1016/S0022-3697\(02\)00362-1](https://doi.org/10.1016/S0022-3697(02)00362-1).
17
18 [85] D.M.A. Alrousan, P.S.M. Dunlop, T.A. McMurray, J.A. Byrne, Photocatalytic
19 inactivation of *E. coli* in surface water using immobilised nanoparticle TiO₂ films, *Water*
20 *Res.* 43 (2009) 47–54. <https://doi.org/10.1016/j.watres.2008.10.015>.
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60